NASA/CP—2001–210883

The 2000 NASA Aerospace Battery Workshop

J.C. Brewer, Compiler
Marshall Space Flight Center, Marshall Space Flight Center, Alabama

Proceeding of a workshop sponsored by the
NASA Aerospace Flight Battery Systems Program
and held in Huntsville, Alabama, November 14–16, 2000

March 2001

Main Menu

- *STI Program Profile*
- *Title Page*
- *Report Available From*
- *Preface*
- *Introduction*
- *Table of Contents*
- *General Session*
- *Focused Session I*
  Status of Aerospace Battery Technology Heading into the 21st Century
- *Nickel-Hydrogen Session*
- *Lithium/Lithium-Ion Session*
- *Focused Session II*
  Lithium-Ion Cell and Battery Safety
- *Attendance List*
- *Report Document Page*

Search

Adobe® Acrobat® Menu Bar Functions

Adobe® Acrobat® Online Guide

NASA/CP—2001–210883

The 2000 NASA Aerospace Battery Workshop

J.C. Brewer, Compiler
Marshall Space Flight Center, Marshall Space Flight Center, Alabama

Proceeding of a workshop sponsored by the
NASA Aerospace Flight Battery Systems Program
and held in Huntsville, Alabama, November 14–16, 2000

National Aeronautics and
Space Administration

Marshall Space Flight Center • MSFC, Alabama 35812

March 2001

The NASA STI Program Office...in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- TECHNICAL PUBLICATION. Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA's counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.

- TECHNICAL MEMORANDUM. Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.

- CONTRACTOR REPORT. Scientific and technical findings by NASA-sponsored contractors and grantees.

- CONFERENCE PUBLICATION. Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.

- SPECIAL PUBLICATION. Scientific, technical, or historical information from NASA programs, projects, and mission, often concerned with subjects having substantial public interest.

- TECHNICAL TRANSLATION. English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results...even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at ***http://www.sti.nasa.gov***

- E-mail your question via the Internet to help@sti.nasa.gov

- Fax your question to the NASA Access Help Desk at (301) 621–0134

- Telephone the NASA Access Help Desk at (301) 621–0390

- Write to:
  NASA Access Help Desk
  NASA Center for AeroSpace Information
  7121 Standard Drive
  Hanover, MD 21076–1320
  (301)621–0390

NASA/CP—2001–210883

The 2000 NASA Aerospace Battery Workshop

J.C. Brewer, Compiler
Marshall Space Flight Center, Marshall Space Flight Center, Alabama

Proceeding of a workshop sponsored by the
NASA Aerospace Flight Battery Systems Program
and held in Huntsville, Alabama, November 14–16, 2000

National Aeronautics and
Space Administration

Marshall Space Flight Center • MSFC, Alabama 35812

March 2001

Available from:

NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076–1320
(301) 621–0390

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
(703) 487–4650

Preface

This disk contains the proceedings of the 33rd annual NASA Aerospace Battery Workshop, hosted by the Marshall Space Flight Center on November 14-16, 2000. The workshop was attended by scientists and engineers from various agencies of the U.S. Government, aerospace contractors, and battery manufacturers, as well as international participation in like kind from a number of countries around the world.

The subjects covered included lithium-ion, nickel-hydrogen, and silver-zinc technologies.

Introduction

The NASA Aerospace Battery Workshop is an annual event hosted by the Marshall Space Flight Center. The workshop is sponsored by the NASA Aerospace Flight Battery Systems Program, which is managed out of NASA Glenn Research Center and receives support in the form of overall objectives, guidelines, and funding from Code R, NASA Headquarters.

The 2000 Workshop was held on three consecutive days and was divided into five sessions. The first day consisted of a General Session and a Focused Session (Status of Aerospace Battery Technology Heading into the 21st Century). The second day consisted of a short Nickel-Hydrogen Session followed by a Lithium / Lithium-Ion Session. The third and final day was a second Focused Session dealing with Lithium-Ion Cell and Battery Safety.

On a personal note, I would like to take this opportunity to thank all of the many people that contributed to the organization and production of this workshop:

The NASA Aerospace Flight Battery Systems Program, for their financial support as well as their input during the initial planning stages of the workshop;

Holiday Inn – Research Park, for doing an outstanding job in providing an ideal setting for this workshop and for the hospitality that was shown to all who attended;

Joe Stockel, National Reconnaissance Office, and Rao Surampudi and Kumar Bugga, Jet Propulsion Laboratory, for organizing and conducting this year's focused sessions.

Marshall Space Flight Center employees, for their help in registering attendees, handling the audience microphones, and flipping transparencies during the workshop.

Finally, I want to thank all of you that attended and/or prepared and delivered presentations for this workshop. You were the key to the success of this workshop.

Jeff Brewer
NASA Marshall Space Flight Center

Table of Contents

General Session (Tuesday AM)

Recent Developments in Silver/Zinc Rechargeable Cell Studies
Harlan L. Lewis, NAVSEA Crane

Advances in Lithium-Sulfur Rechargeable Batteries
Terje Skotheim, Jim Akridge, and Bob Hyland, Moltech Corporation

Effects of AEA Cell-Bypass-Switch Closure on Charged EOS-Aqua Ni-H_2 Cell
Denney Keys, Gopalakrishna M. Rao, and David Sullivan, NASA Goddard Space Flight Center; and Harry Wannemacher, QSS Group, Inc.

Focused Session I -- Status of Aerospace Battery Technology Heading into the 21st Century (Tuesday AM & PM)

High Specific Energy NiH_2 Batteries for GEO Satellites
Y. Borthomieu, Defense and Space Division SAFT Poitiers; and M. Fabre, Alcatel Space Industries Cannes

Capacity Management and Walkdown During LEO Cycling of Nickel-Hydrogen Cells and Batteries
Lawrence H. Thaller, Albert H. Zimmerman, and Gloria To, The Aerospace Corporation

Effects of Dry Storage on NiH_2 Slurry Electrode Cells
Jon Armantrout, LMMS; and Dale Gordon, EPT, LLC

Mathematical Modeling of Ni/H_2 and Li-Ion Batteries
John W. Weidner, Ralph E. White, and Roger A. Dougal, University of South Carolina

Thermal and Cycle-Life Behavior of Commercial Li-Ion and Li-Polymer Cells
Albert H. Zimmerman and M. V. Quinzio, The Aerospace Corporation

Li-Ion Battery Cell Balancing Requirements
Mark J. Isaacson and Vincent L. Teofilo, Lockheed Martin Space Systems

Characterization and Simulated LEO Cycling of SAFT Lithium Ion Cells
Chuck Lurie and Philip Johnson, TRW; and Robert J. Staniewicz, SAFT America, Inc.

GEO and LEO Life Test Results on VES140 SAFT Li-Ion
Y. Borthomieu, J.P. Planchat, SAFT Poitiers

Lithium Ion DD Cells Evaluation for Space Application
Haiyan Croft and Bob Staniewicz, SAFT R&D Center

Nickel-Hydrogen Session (Wednesday AM)

Crane Cell Testing Support of Goddard Space Flight Center: An Update
Mike Strawn and Jerry David, NAVSURFWARCENDIV Crane; and Gopalakrishna Rao, NASA Goddard Space Flight Center

Large Capacity Single Pressure Vessel (SPV) Battery Development
Jeff Dermott and Jack Brill, Eagle-Picher Technologies, LLC

Effect of Handling, Storage and Cycling on Ni-H_2 Cells: Second Plateau Phenomenon
Hari Vaidyanathan, Lockheed Martin Global Telecommunications; and Gopalakrishna M. Rao, NASA Goddard Space Flight Center

Lithium / Lithium-Ion Session (Wednesday AM & PM)

Characterization of Electrolytes by Computer Modeling
Brandy Moore, Richard Whiteley, James Currie, and Kevin Johnson, Pacific University

Progress Toward a Li-Ion Spacecraft Battery
Chad Kelly and James DeGruson, Eagle-Picher Technologies, LLC

Large Lithium Ion Batteries for Aerospace and Aircraft Applications
Gregg C. Bruce and Lynn Marcoux, Eagle-Picher Energy Products

R&D Status of Li-Ion Secondary Cells at Tsukuba Space Center, NASDA
Y. Sone, X. Liu, H. Kusawake, K. Kanno, and S. Kuwajima, National Space Development Agency of Japan

NASA/GSFC Testing of Li-Ion Cells: Update
Hari Vaidyanathan, Lockheed Martin Global Telecommunications; and Gopalakrishna M. Rao, NASA Goddard Space Flight Center

Li-Ion EMU Battery Testing
Raymond Rehm, Lockheed Martin Space Operation; Bobby Bragg, NASA Johnson Space Center; and Brad Strangways, Symmetry Resources

Performance and Abuse Testing of 5 Year Old Low Rate and Medium Rate Lithium Thionyl Chloride Cells
Rick Frerker and Wenlin Zhang, Ph. D., Schlumberger; Judith Jeevarajan, Lockheed Martin / NASA-JSC; and Bobby J. Bragg, NASA-JSC

Lithium-Ion Satellite Batteries Using Small Cells
David Lizius and Phil Cowles, COM DEV; Rob Spurrett and Carl Thwaite, AEA Technology

Simulated LEO Cycling of AEA-STRV Lithium-Ion Battery Modules
Philip Johnson and Chuck Lurie, TRW; and R. Spurrett, AEA Technology

Focused Session II – Lithium-Ion Cell and Battery Safety (Thursday AM)

Safety & Abusive Tests on Different Li-Ion Systems
James DeGruson and Chad Kelly, Eagle-Picher Technologies, LLC

Lithium Ion Battery Design and Safety
George Au and Laura Locke, US Army CECOM RDEC

Performance and Safety of Lithium Ion Cells
B.V. Ratnakumar, M.C. Smart, L. Whitcanack, and S. Surampudi, Jet Propulsion Laboratory; and R. Marsh, Wright-Patterson Air Force Base

Safety Evaluation of Large Lithium-Ion Cells
R. Gitzendanner, C. Marsh, and F. Puglia, Yardney Technical Products, Inc.

On the Behavior of Lithium Ion Batteries During Short Circuit and Extended Overcharge
Randolph A. Leising, Marcus J. Palazzo, David M. Spillman, and Esther S. Takeuchi, Wilson Greatbatch Ltd.; and Kenneth J. Takeuchi, SUNY at Buffalo

Lithium-Ion Battery Technology Configured to Tolerate Overcharge and Overdischarge
S. Hossain, Y. Saleh, and R. Loutfy, LiTech, LLC

Secondary Lithium-Ion Cell and Battery Safety
Rob Spurrett and Carl Thwaite, AEA Technology; and Philip Cowles, COM DEV

2000 NASA Aerospace Battery Workshop Attendance List

Jon D. Armantrout
Lockheed Martin Space Systems Company
Orgn. L2-01, Bldg. 102
1111 Lockheed Martin Way
Sunnyvale, CA 94089
Ph. (408) 742-1800 FAX (408) 742-2731
E-mail jon.armantrout@lmco.com

Doug Bearden

NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. FAX
E-mail doug.bearden@msfc.nasa.gov

Jim Bell
Boeing
Bldg. 231 / Mail Stop 2011
3100 W. Lomita Blvd.
Torrance, CA 90509
Ph. (310) 517-7607 FAX (310) 517-7676
E-mail james.bell@boeing.com

Yannick Borthomieu
SAFT Advanced Batteries
BP 1039
Rue G. Leclanche
86060 Poitiers Cedex 9
France

Ph. 33-549-55-4014 FAX 33-549-55-4780
E-mail yannick.borthomieu@saft.alcatel.fr

Bobby J. Bragg
NASA Johnson Space Center

MS EP52
NASA Rd. 1
Houston, TX 77058
Ph. (281) 483-9060 FAX (281) 483-3096
E-mail bbragg@ems.jsc.nasa.gov

Jeffrey C. Brewer
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3345 FAX (256) 544-5841
E-mail jeff.brewer@msfc.nasa.gov

Jack N. Brill
Eagle-Picher Technologies, LLC
1216 West C Street
Joplin, MO 64801
Ph. (417) 623-8000 X346 FAX (417) 623-6661
E-mail jbrill@epi-tech.com

Bob Brown
Eagle-Picher Technologies, LLC
1216 West C Street
Joplin, MO 64801
Ph. (417) 623-8000 FAX
E-mail bbrown@epi-tech.com

Ratnakumar Bugga
Jet Propulsion Laboratory
MS 277-207
4800 Oak Grove Dr.
Pasadena, CA 91109
Ph. (818) 354-0110 FAX (818) 383-6951
E-mail ratnakumar.v.bugga@jpl.nasa.gov

Jack Bullman
NASA Marshall Space Flight Center
ED10
Marshall Space Flight Center, AL 35812
Ph. (256) 544-9009 FAX
E-mail jack.bullman@msfc.nasa.gov

2000 NASA Aerospace Battery Workshop Attendance List

Mike Conley
Aero Astro
520 W Huntmar Park Dr.
Herndon, VA 20170
Ph. (703) 709-2240 x132 FAX (703) 709-0790
E-mail mike@aeroastro.com

William L. Crabtree
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-5305 FAX (256) 544-5841
E-mail larry.crabtree@msfc.nasa.gov

Karen Cunningham
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-5618 FAX
E-mail karen.cunningham@msfc.nasa.gov

Eric C. Darcy
NASA Johnson Space Center
MS EP5
Houston, TX 77058
Ph. (281) 483-9055 FAX (281) 483-3096
E-mail edarcy@ems.jsc.nasa.gov

Jerry W. David
Naval Surface Warfare Center - Crane
300 Highway 361
Crane, IN 47522-5001
Ph. (812) 854-4193 FAX (812) 854-3589
E-mail david_j@crane.navy.mil

James A. DeGruson
Eagle-Picher Technologies, LLC
3220 Industrial Road
Joplin, MO 64802
Ph. (417) 659-9635 x203 FAX (417) 626-2078
E-mail jdegruson@epi-tech.com

Andrew F. Dunnet
Fraser-Dunnet Consulting
5112 Bradford Drive
Annandale, VA 22003
Ph. (703) 256-4092 FAX (703) 256-4094
E-mail adunnet@aol.com

Ted Edge
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3381 FAX (256) 544-5841
E-mail ted.edge@msfc.nasa.gov

Henry B. Flauaus
The Boeing Company
POB 516
M/C S106-7250
St. Louis, MO 63166
Ph. (314) 233-2477 FAX (314) 232-3722
E-mail henry.b.flauaus@boeing.com

Christopher L. Fox
Eagle-Picher Technologies, LLC
C & Porter Streets
Joplin, MO 64801
Ph. (417) 623-8000 X367 FAX (417) 781-1910
E-mail cfox@epi-tech.com

2000 NASA Aerospace Battery Workshop Attendance List

Pete George
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3331 FAX (256) 544-5841
E-mail pete.george@msfc.nasa.gov

Donald K. Georgi

Batteries Digest Newsletter
1261 Townline Road
Maple Plain, MN 55359
Ph. (763) 479-6190 FAX (763) 3657
E-mail donald@batteriesdigest.com

Albert Himy
Navy / JJMA
4300 King Street
Suite 400
Alexandria, VA 22302-1503
Ph. (703) 418-4257 FAX (703) 416-1792
E-mail ahimy@jjma.com

Nathan D. Isaacs
Mine Safety Appliances Company
38 Loveton Circle
Sparks, MD 21152
Ph. (410) 472-7700 FAX (410) 472-7800
E-mail nedizakmsa@aol.com

Thierry Jamin
CNES
18 Av E Belin
31401 Toulouse Cedex
France

Ph. 05 61 27 49 38 FAX 05 61 28 21 62
E-mail thierry.jamin@cnes.fr

Philip Johnson
TRW
One Space Park
Redondo Beach, CA 90278
Ph. (310) 812-7249 FAX (310) 812-4978
E-mail philip.johnson@trw.com

Bob Kapustka
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3302 FAX
E-mail bob.kapustka@msfc.nasa.gov

Chad O. Kelly
Eagle-Picher Technologies, LLC
3220 Industrial Drive
Joplin, MO 64801
Ph. (417) 659-9635 FAX (417) 626-2078
E-mail ckelly@epi-tech.com

Dr. Harlan L. Lewis
Naval Surface Warfare Center - Crane
300 Highway 361
Code 609 B3287
Crane, IN 47522
Ph. (812) 854-4104 FAX (812) 854-1212
E-mail lewis_h@crane.navy.mil

Eric Lowery
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-0080 FAX (256) 544-5841
E-mail eric.lowery@msfc.nasa.gov

2000 NASA Aerospace Battery Workshop Attendance List

Steve Luna
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3402 FAX (256) 544-5841
E-mail steve.luna@msfc.nasa.gov

Chuck Lurie
TRW
MS R4/1082
One Space Park
Redondo Beach, CA 90278
Ph. (310) 813-4888 FAX (310) 812-4978
E-mail chuck.lurie@trw.com

Michael Mackowski
Spectrum Astro
1022 W. Juanita Ave.
Gilbert, AZ 85233
Ph. (480) 892-8200 FAX (480) 892-2949
E-mail mackowski@specastro.com

Dr. Tyler X. Mahy
U.S. Government
c/o OATP, NHB
Washington, DC 20505
Ph. (703) 874-0739 FAX (703) 641-9830
E-mail

Michelle Manzo
NASA Glenn Research Center
MS 309-1
21000 Brookpark Rd.
Cleveland, OH 44135
Ph. (216) 433-5261 FAX (216) 433-6160
E-mail michelle.manzo@grc.nasa.gov

Jeff Martin
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. FAX
E-mail jeff.martin@msfc.nasa.gov

Dean W. Maurer
Loral Skynet
POB 7018
Bedminster, NJ 07921
Ph. (908) 470-2310 FAX (908) 470-2457
E-mail dwm@loralskynet.com

George Methlie
2120 Natahoa Ct.
Falls Church, VA 22043
Ph. (202) 965-3420 FAX (703) 641-9830
E-mail

Martin Milden
Consultant
2212 So. Beverwil Dr.
Los Angeles, CA 90034-1034
Ph. (310) 836-7794 FAX (310) 836-4494
E-mail mmilden@mediaone.net

David O'Dell
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3416 FAX
E-mail david.odell@msfc.nasa.gov

2000 NASA Aerospace Battery Workshop Attendance List

Gopal Rao
NASA Goddard Space Flight Center
Code 563
Greenbelt, MD 20771
Ph. (301) 286-6654 FAX (301) 286-1751
E-mail grao@pop700.gsfc.nasa.gov

Dean J. Roukis

INTELSAT
3400 International Dr. NW
Washington, DC 20008
Ph. (202) 944-8194 FAX (202) 944-7333
E-mail dean.roukis@intelsat.int

Frank J. Scalici
INTELSAT
3400 International Dr. NW
Box 34
Washington, DC 20008
Ph. (202) 944-7353 FAX (202) 944-7333
E-mail frank.scalici@intelsat.com

Darren L. Scoles
Lockheed Martin Space Systems Co.
GPS IIR Flight Operations
440 Discoverer St.
Suite 79 / Rm 201
Schriever AFB, CO 80912
Ph. (719) 567-3217 FAX (719) 567-3927
E-mail darren.l.scoles@lmco.com

Annie L. Sennet
SAFT America
107 Beaver Court
Cockeysville, MD 21030
Ph. (410) 771-3200 x 170 FAX (410) 771-1144
E-mail annie.sennet@saftamerica.com

Dr. Pinakin M. Shah
Mine Safety Appliances Company
38 Loveton Circle
Sparks, MD 21152
Ph. (410) 472-7720 FAX (410) 472-7800
E-mail pinakins@aol.com

Rami Shamir
MBT / IAI
DPT 3901
Yahud Israel

Ph. 972-3-5314176 FAX 972-3-5314640
E-mail

Yoshitsugu Sone
National Space Development Agency of Japan
Tsukuba Space Center
2-1-1 Sengen, Tsukuba-city
Ibaraki-pref. 305-8505 Japan

Ph. 81-(0)298-52-2285 FAX 81-(0)298-52-2299
E-mail sone.yoshitsugu@nasda.go.jp

David M. Spillman
Wilson Greatbatch Ltd.
10000 Wehrle Drive
Clarence, NY 14031
Ph. (716) 759-5378 FAX (716) 759-8579
E-mail dspillman@greatbatch.com

Rob Spurrett
AEA Technology
Space
Culham Science Centre
Abingdon, OX14 3ED
UK

Ph. 44 1235 463304 FAX 44 1235 463285
E-mail rob.spurrett@aeat.co.uk

2000 NASA Aerospace Battery Workshop Attendance List

Brian J. Stein
Mine Safety Appliances Company
38 Loveton Circle
Sparks, MD 21152
Ph. (410) 472-7713 FAX (410) 472-7800
E-mail bjsteinmsa@aol.com

Joe Stockel
National Reconnaissance Office
14675 Lee Rd.
Chantilly, VA 20151
Ph. (703) 808-4088 FAX (703) 808-4931
E-mail joeskl@ucia.gov

Lawrence Thaller
The Aerospace Corporation
MS M2/275
POB 92957
Los Angeles, CA 90009
Ph. (310) 336-5180 FAX (310) 336-1636
E-mail lawrence.h.thaller@aero.org

Greta Tracinski
Applied Power International
1236 N. Columbus Ave., #41
Glendale, CA 91202-1672
Ph. (818) 243-3127 FAX (818) 243-3127
E-mail gtracinski@earthlink.net

Walter A. Tracinski
Applied Power International
1236 N. Columbus Ave., #41
Glendale, CA 91202-1672
Ph. (818) 243-3127 FAX (818) 243-3127
E-mail watracinski@earthlink.net

Dr. Hari Vaidyanathan
Lockheed Martin Global Telecommunications
22300 Comsat Dr.
Clarksburg, MD 20871
Ph. (301) 428-4507 FAX (301) 540-8208
E-mail hari.vaidyanathan@comsat.com

Harry E. Wannemacher
QSS Group, Inc.
3502 Moylan Dr.
Bowie, MD 20715
Ph. (301) 286-7551 FAX (301) 286-1739
E-mail harrywannemacher@erols.com

Richard V. Whiteley, Jr.
Pacific University
Chemistry Dept.
2043 College Way
Forest Grove, OR 97116
Ph. (503) 359-2127 FAX (503) 359-2933
E-mail whiteler@pacificu.edu

Tom Whitt
NASA Marshall Space Flight Center
ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3313 FAX (256) 544-5841
E-mail tom.whitt@msfc.nasa.gov

Daphne Xu
INTELSAT
3400 International Dr. NW
Washington, DC 20008
Ph. (202) 944-7250 FAX (202) 944-7333
E-mail daphne.xu@intelsat.int

2000 NASA Aerospace Battery Workshop Attendance List

Albert H. Zimmerman
The Aerospace Corporation
MS M2/275
POB 92957
Los Angeles, CA 90009-2957
Ph. (310) 336-7415 FAX (310) 336-6801
E-mail albert.h.zimmerman@aero.org

Dr. Catherine Marsh

Yardney Technical Products
82 Mechanic Street
Pawcatuck, CT 06379
Ph. (860) 599-1100 FAX
E-mail cmarsh@yardney.com

Craig Courtney
NEA Electronics, Inc.
9259 Eton Avenue
Chatsworth, CA 91311
Ph. (818) 998-5788 FAX (818) 998-5681
E-mail neaelec@aol.com

Richard J. Frerker
Schlumberger
14910 Airline Road
Rosharon, TX 77583
Ph. (281) 285-5596 FAX (281) 285-5575
E-mail frerker@rosharon.wireline.slb.com

Wallace J. Izzo
Moltech Power Systems
8307 Cherry Lane
Laurel, MD 20707
Ph. (301) 362-5665 FAX (301) 362-0255
E-mail wallace.izzo@moltech.com

Cacey Jennings
Space Systems / Loral
3825 Fabian Way
MS G69
Palo Alto, CA 94303
Ph. (650) 852-4682 FAX (650) 852-4695
E-mail jennings.cacey@ssd.loral.com

Vijayakumar Krishnamurthy
Intelsat
3400 International Dr. NW
Box 34
Washington, DC 20008
Ph. (202) 295-8883 FAX (202) 944-7333
E-mail vijayakumar.krishnamurthy@intelsat.int

David Lizius
COM DEV Space Group
155 Sheldon Drive
Cambridge Ontario
CANADA

Ph. (519) 622-2300 x2844 FAX (519) 622-1691
E-mail david.lizius@comdev.ca

Brandy K. Moore
Pacific University
Chemistry Dept.
2043 College Way
UC Box 602
Forest Grove, OR 97116
Ph. (503) 359-6247 FAX (503) 359-2933
E-mail moorebk@pacificu.edu

Satish R. Muley
Space Systems / Loral
3825 Fabian Way
M/S G69
Palo Alto, CA 94303-4604
Ph. (650) 852-4420 FAX (651) 852-4695
E-mail muley.satish@ssd.loral.com

2000 NASA Aerospace Battery Workshop Attendance List

Raymond B. Rehm
Lockheed Martin Space Operations
2101 NASA Rd 1
M/S EP5
Houston, TX 77058
Ph. (281) 483-9214 FAX (281) 483-3096
E-mail rrehm@ems.jsc.nasa.gov

Jo'el Roth
Advanced Battery Technology Magazine
3707 5th Ave.
#806
San Diego, CA 92103
Ph. 1-888-795-5623 FAX 1-888-795-5623
E-mail gypsijo@aol.com

Edward Rudoy
NEA Electronics, Inc.
Cell Bypass Systems
9259 Eton Avenue
Charsworth, CA 91311
Ph. (818) 998-5788 FAX (818) 998-5681
E-mail neaelec@aol.com

David M. Strawn
Naval Surface Warfare Center - Crane
300 Highway 361
Crane, IN 47522-5001
Ph. (812) 854-4153 FAX (812) 854-3589
E-mail strawn_mike@crane.navy.mil

David J. Surd
BAE Systems, Applied Technologies, Inc.
Battery Technology Center
1601 Research Blvd.
Rockville, MD 20850-3673
Ph. (301) 838-6234 FAX (301) 838-6222
E-mail david.surd@baesystems.com

Gilberto Varela
NASA Johnson Space Center
NASA Rd. 1 / EP5
Houston, TX 77058
Ph. (281) 483-9008 FAX (281) 483-3096
E-mail gvarela@ems.jsc.nasa.gov

John W. Weidner
University of South Carolina
Center for Electrochemical Engineering
Department of Chemical Engineering
Columbia, SC 29208
Ph. FAX
E-mail weidner@engr.sc.edu

Gregg C. Bruce
Eagle-Picher Energy Products
1155 West 15th St.
North Vancouver, BC
Canada V7P 1M7
Ph. (604) 986-4020 FAX (604) 986-1048
E-mail gbruce@epi-tech.com

George W. Au
U.S. Army CECOM RDEC
AMSEL-RD-C2-AP-B
Building 2700, 2D301
Ft. Monmouth, NJ 07703
Ph. (732) 427-4886 FAX (732) 427-3665
E-mail george.au@mail1.monmouth.army.mil

Sohrab Hossain
LiTech, LLC
7906 S. Kolb Road
Tucson, AZ 85706
Ph. (520) 574-1980 FAX (520) 574-1983
E-mail shossain@mercorp.com

2000 NASA Aerospace Battery Workshop Attendance List

Paul J. Kasztejna
SAFT America
107 Beaver Court
Cockeysville, MD 21030
Ph. (410) 771-3200 FAX (410) 771-0234
E-mail paul.kasztejna@saftamerica.com

Robert T. Curtis

The Boeing Company
3800 Lewiston St., Ste 100
Aurora, CO 80011
Ph. (303) 307-3300 FAX (303) 307-3310
E-mail rtcurtis@home.com

Hampton M. DeJarnette
Naval Surface Warfare Center - Carderock
Code 644
9500 MacArthur Blvd.
West Bethesda, MD 20817-5700
Ph. (301) 227-4763 FAX (301) 227-5457
E-mail dejarnettehm@nswccd.navy.mil

Matthew W. LeMay
Boeing
M/S JW63
799 James Record Rd.
Huntsville, AL 35824
Ph. (256) 461-5725 FAX (256) 461-3045
E-mail matthew.w.lemay@boeing.com

Haiyan Croft
SAFT America
107 Beaver Court
Cockeysville, MD 21030
Ph. (410) 771-3200 FAX
E-mail haiyan.croft@saftamerica.com

James Turner
NASA Marshall Space Flight Center
MS ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-4287 FAX (256) 544-5841
E-mail james.turner@msfc.nasa.gov

Tom Dietrich
NASA Marshall Space Flight Center
MS ED11
Marshall Space Flight Center, AL 35812
Ph. (256) 544-3409 FAX (256) 544-5841
E-mail tom.dietrich@msfc.nasa.gov

Mark Isaacson
Lockheed Martin Missiles and Space Operations
B/102, L2-30
1111 Lockheed Martin Way
Sunnyvale, CA 95051
Ph. (408) 756-9791 FAX (408) 743-2020
E-mail mark.isaacson@lmco.com

Jim Hill
Boeing
Bldg. 231 / Mail Stop 2011
3100 W. Lomita Blvd.
Torrance, CA 90509
Ph. (310) 517-5098 FAX (310) 517-7676
E-mail james.m.hill@boeing.com

Takefumi Inoue
Japan Storage Battery Co., Ltd.
1 Inobabacho, Nishinosho,
Kisshoin, Minami-ku
Kyoto, Japan 601-8520

Ph. 81-75-312-2131 FAX 81-75-316-3052
E-mail takefumi_inoue@gs.nippondenchi.co.jp

2000 NASA Aerospace Battery Workshop Attendance List

Robert Hyland
Moltech Power Systems
9062 South Rita Road
Tucson, AZ 85747
Ph. (520) 799-7526 FAX (520) 799-7501
E-mail bob.hyland@moltech.com

Bob Danielak

Lockheed Martin
100 Campus Drive
Newtown, PA 08721
Ph. (215) 497-1665 FAX (215) 497-1564
E-mail robert.m.danielak@lmco.com

Jeffery Taylor
Boeing
Bldg. 231 / Mail Stop 2011
3100 W. Lomita Blvd.
Torrance, CA 90509
Ph. (310) 517-5769 FAX
E-mail jeffery.taylor@boeing.com

2000 NASA Aerospace Battery Workshop

Recent Developments in Silver/Zinc Rechargeable Cell Studies

Harlan L. Lewis
NAVSEA Crane

14-16 November 2000

Silver/Zinc
20011766 53730 8s 21

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Introduction – History of cellophane and sausage casing model cell studies.

Objective – Reduce number of layers of separation on cathode while maintaining cell performance.

Experimental – Five cell sets of thirteen cells each. Eight cycle life and five wet life. Periodic cell removal for design performance analysis.

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Cell Separation Configurations;

Set 1 – Reference standard set – six layer of 1-mil untreated Flexel clear cellophane provided by Yardney Technical Products (YTP), cathode wrap.

Set 2 – Reference standard set – six layers of 1-mil Flexel cellophane silver-treated (C-19) by YTP, cathode wrap.

Set 11 – Double layer SC set – one layer of 1-mil tubular SC followed by one layer of 2-mil PVA, followed by two layers of 2.3-mil SC from split SC tubing, cathode wrap.

Set 12 – Single layer SC set – one layer of 1-mil tubular SC followed by one layer of 2-mil PVA, followed by one layer of 2.3-mil SC from split SC tubing, cathode wrap. Cells were shimmed with cell case plastic to provide constant internal stack pressure vs. set 1.

Set 13 – Split wrap set – three layers of 1-mil Flexel cellophane silver-treated (C-19) by YTP, cathode wrap, plus three layers anode wrap. (The anodes were wrapped in a split L-configuration to seal the bottom of the anodes.)

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

- Results and Discussion
  - Discharge capacity comparisons
  - Silver migration comparisons

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Cycle life data show approx. equivalent performance.

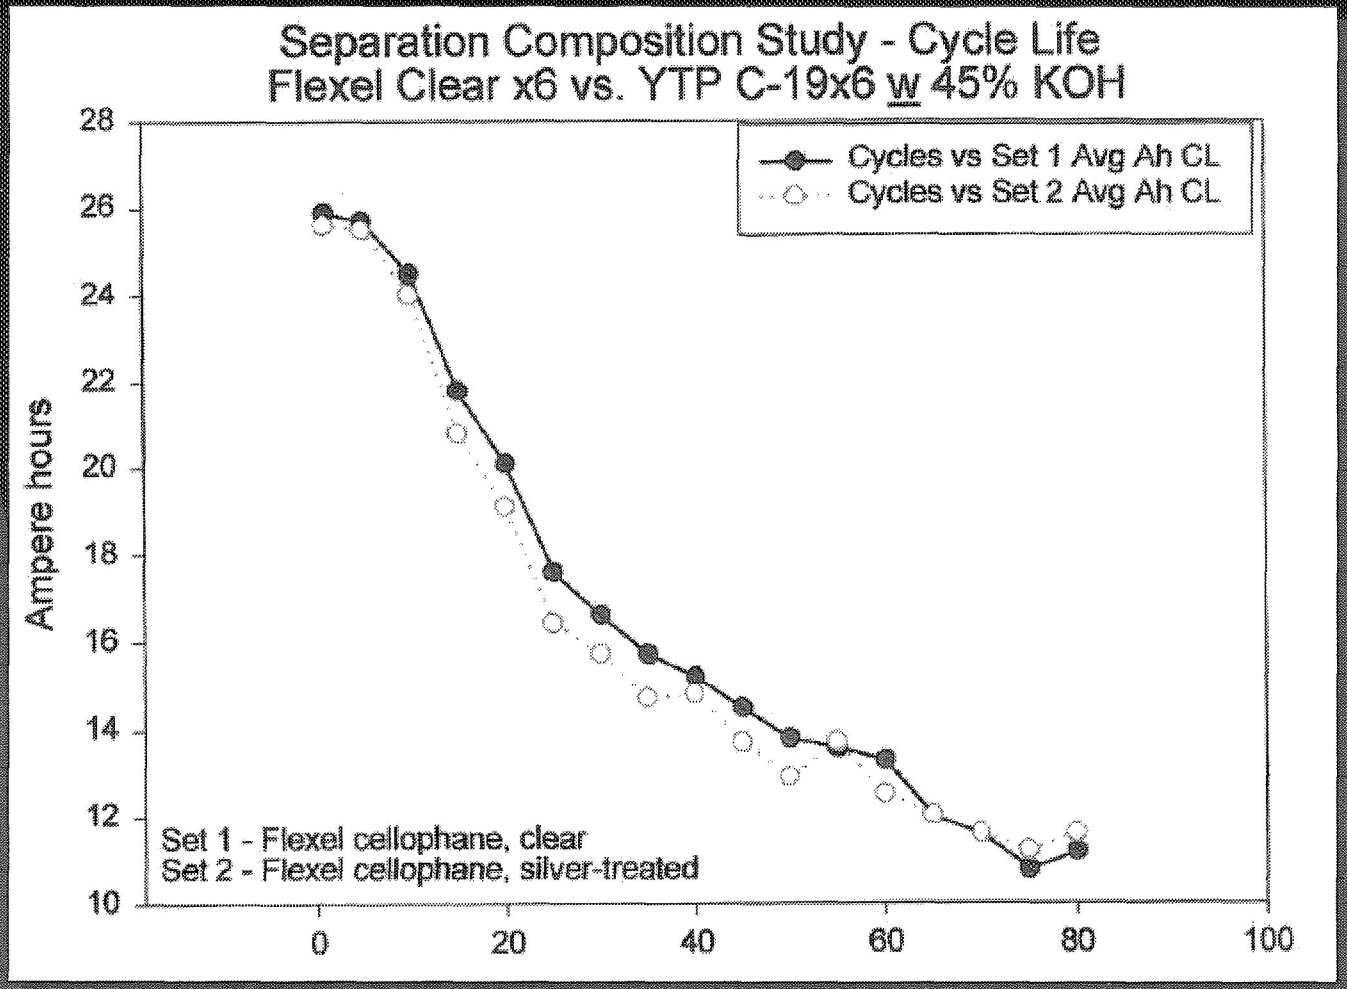

Recent Developments In Silver/Zinc Rechargeable Cell Studies

All but one of the clear Flexel wet life cells shorted out by the tenth month, while none of the C19 cells shorted, so comparison is flawed.

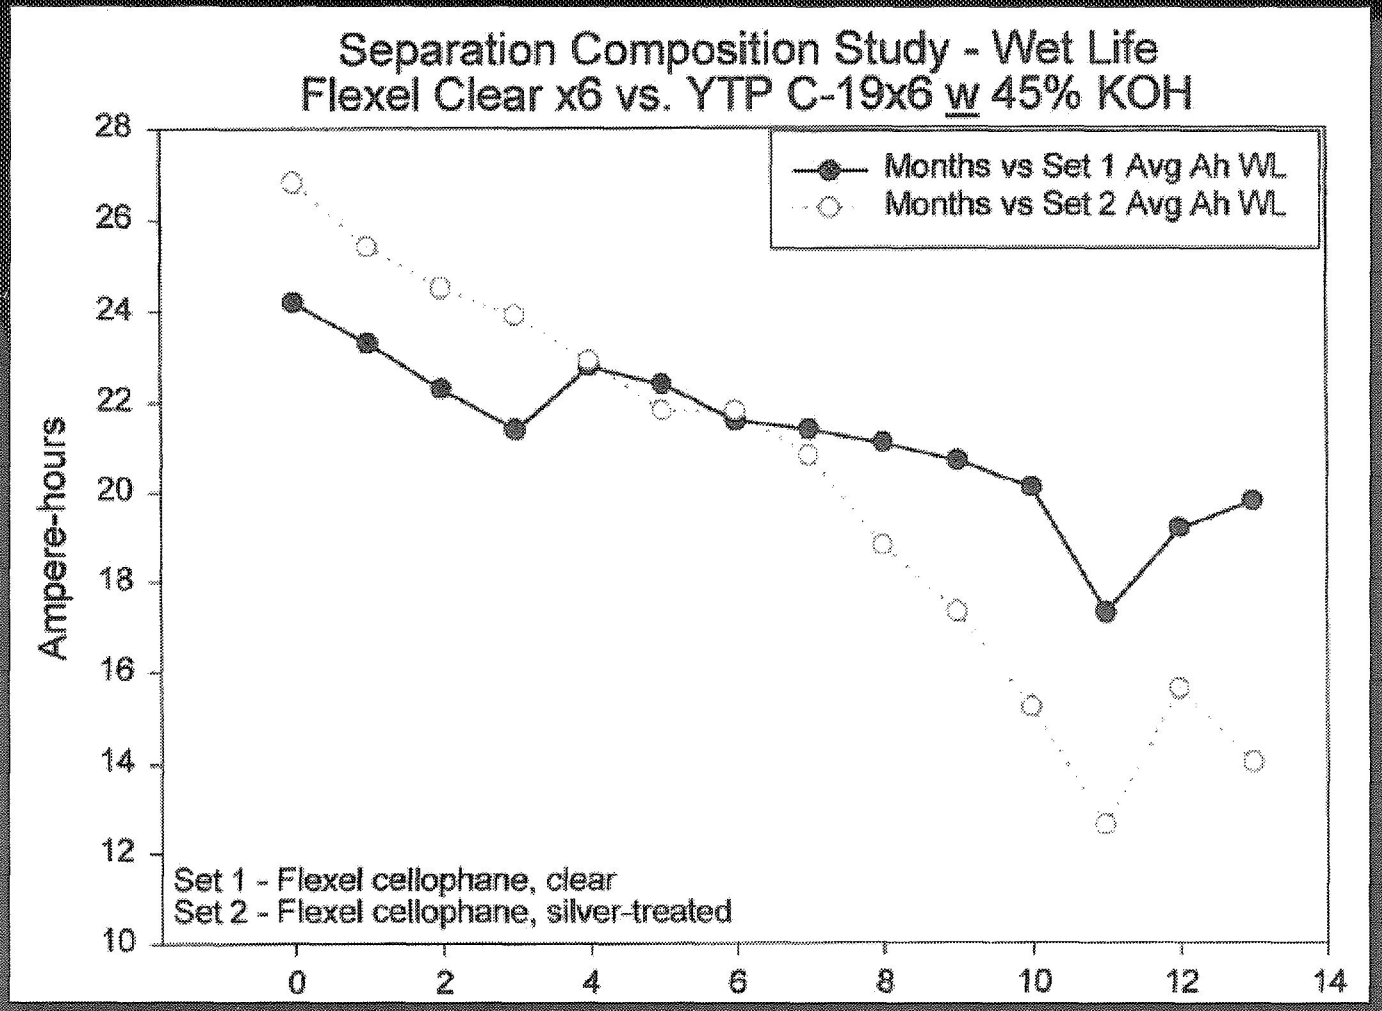

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Cycle life data show a significant performance advantage for split wrap.

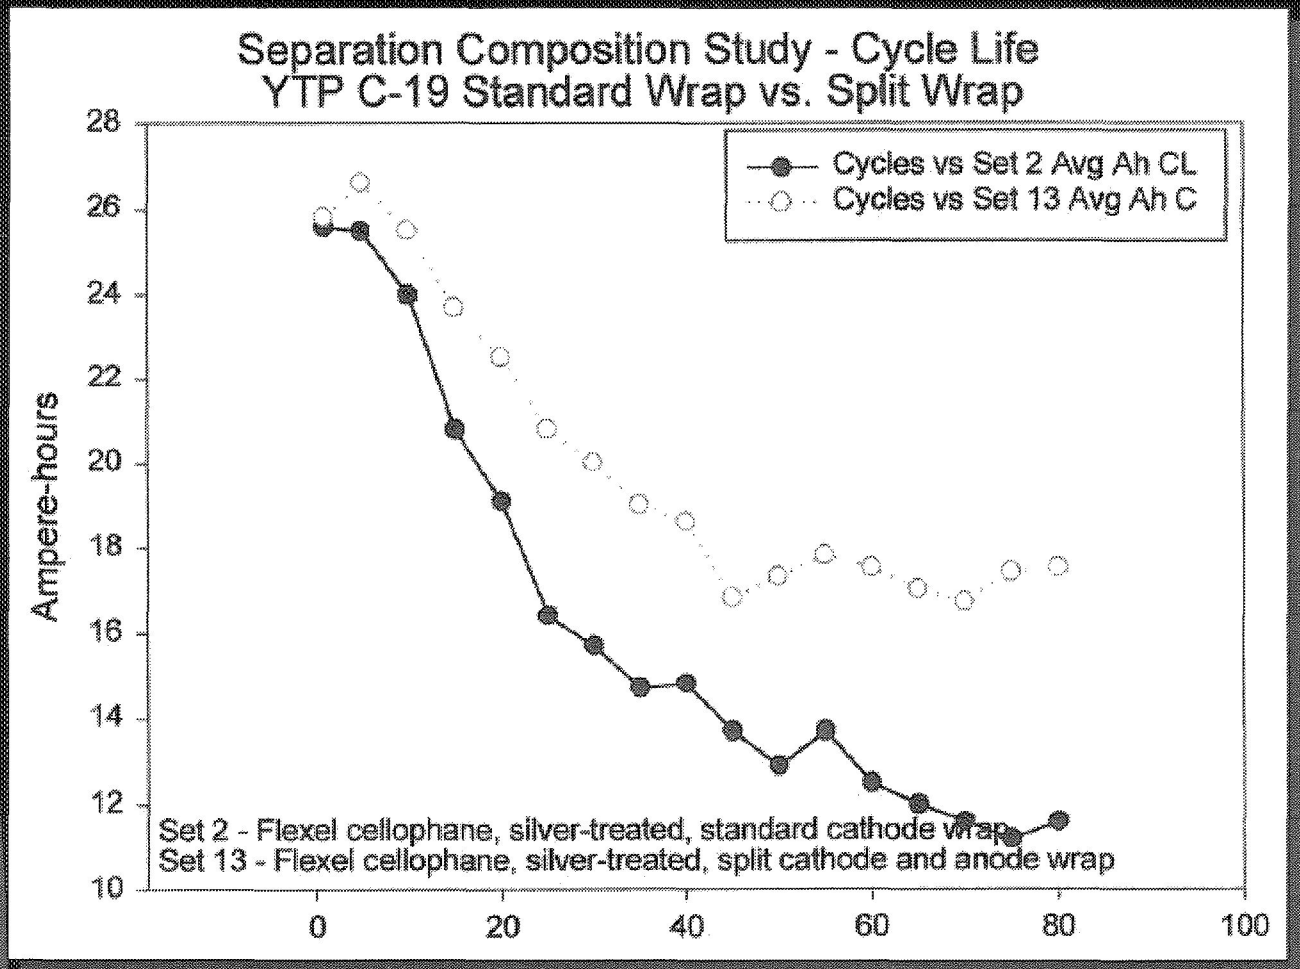

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Wet life data also show a significant capacity advantage for split wrap.

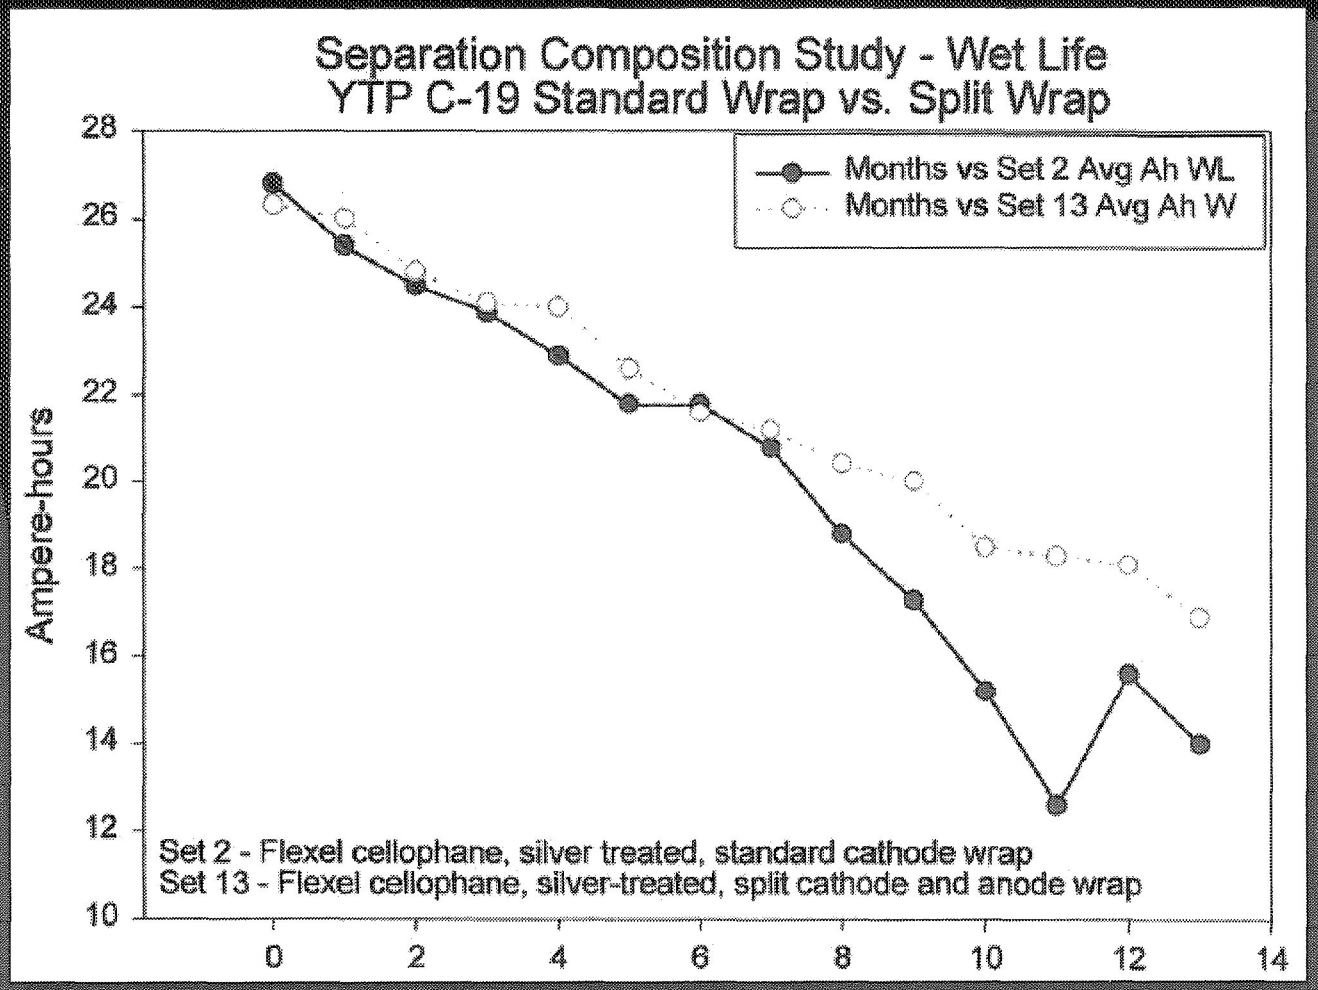

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Combined plots for split wrap vs. both standard wraps in cycle life. The split wrap performance is clearly superior.

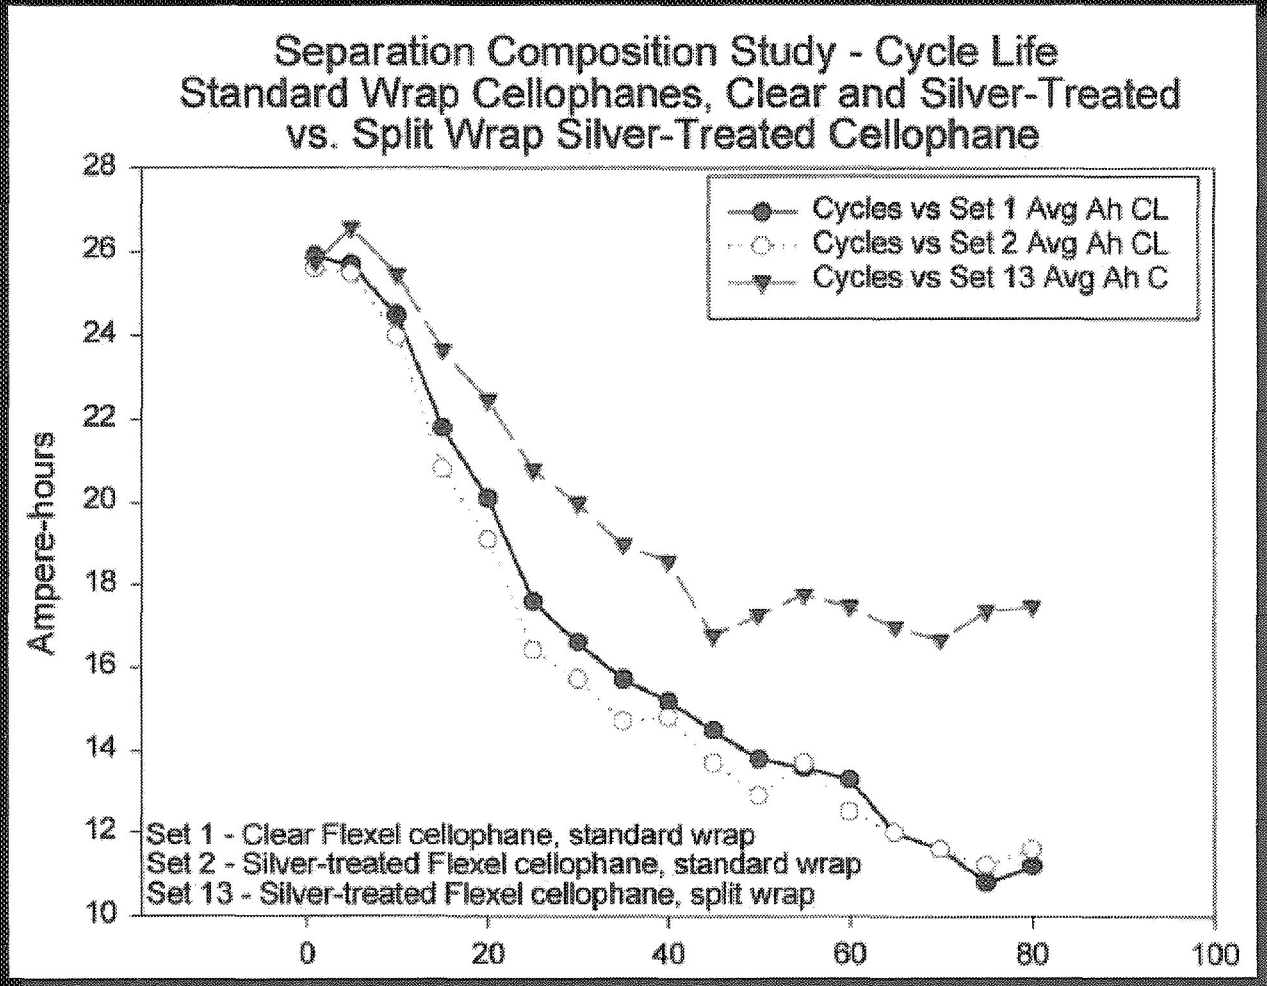

Recent Developments In Silver/Zinc Rechargeable Cell Studies

The Set 1 cells shorted out beginning at the 6th month, while no cells in Sets 2 and 13 shorted at all, so the discharge capacity averages do not reflect the actual performance adequately. Sets 2 and 13 were actually superior to Set 1, overall.

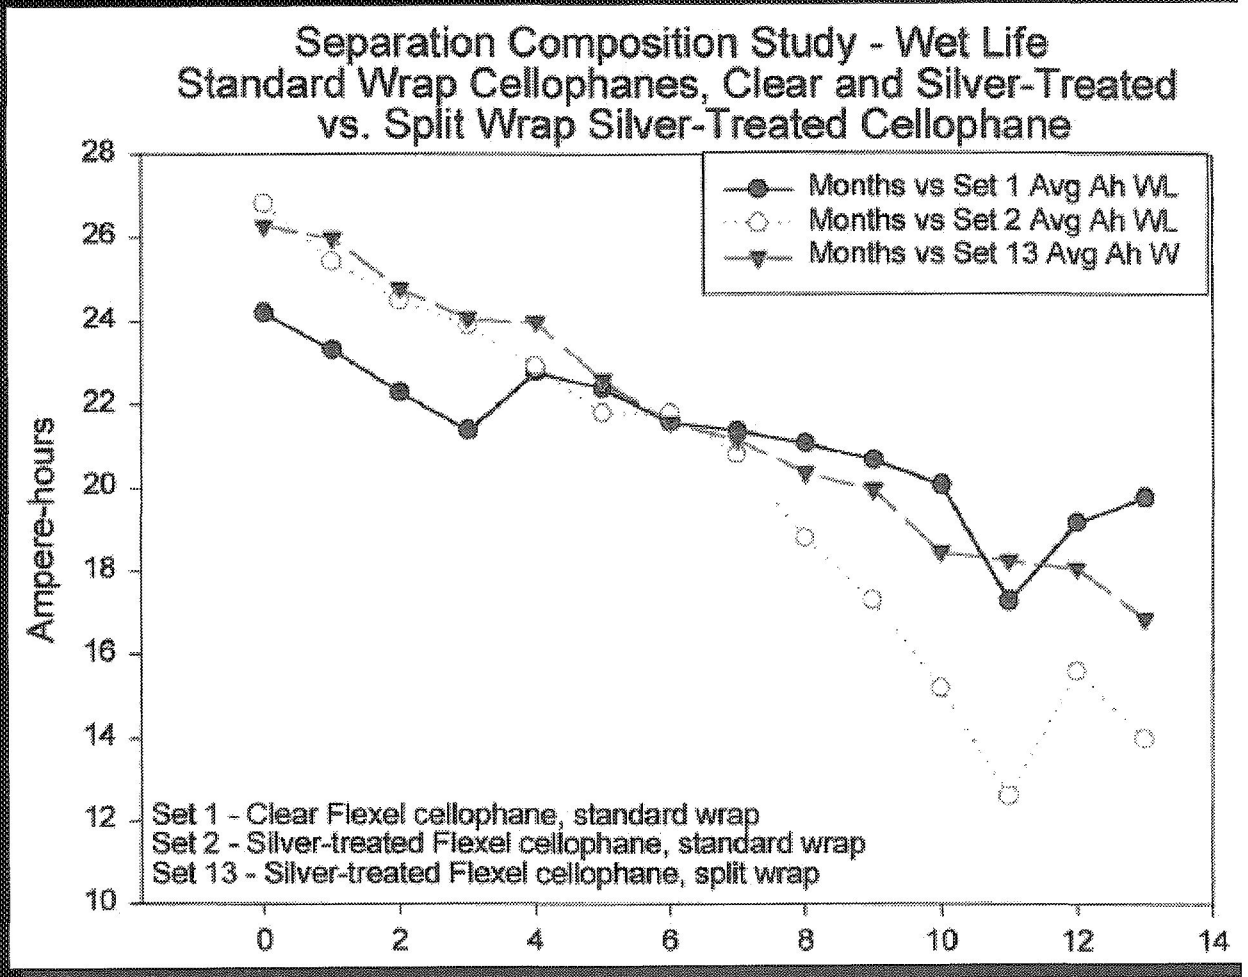

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Cycle life data for the two SC configurations exhibit slightly lowered capacity vs. C19, but no shorts occurred in any Set.

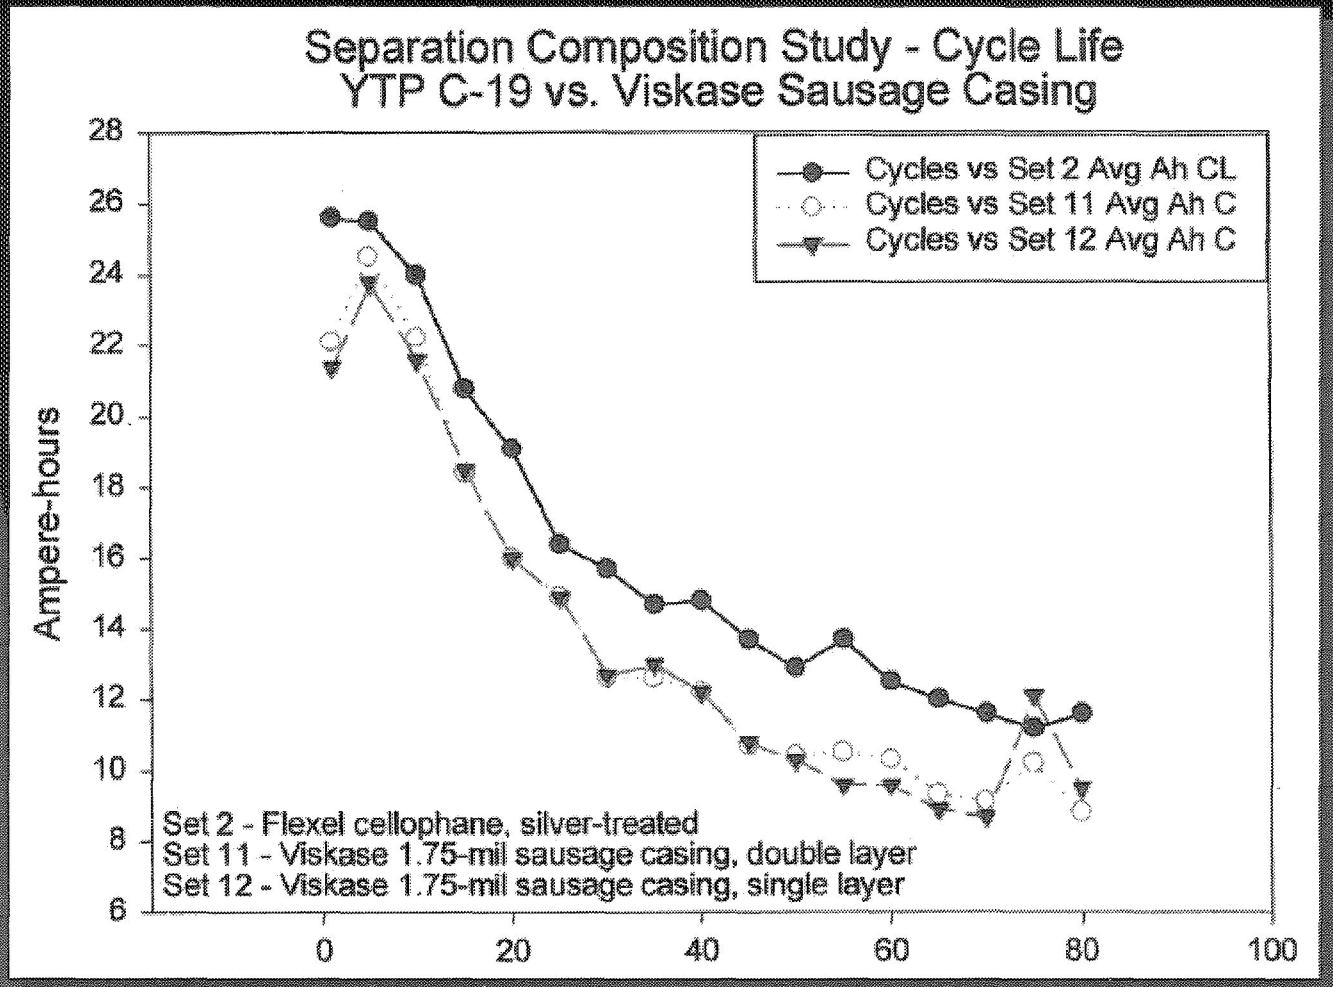

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Wet life data indicate that single layer SC performed as well as C19 in late life.

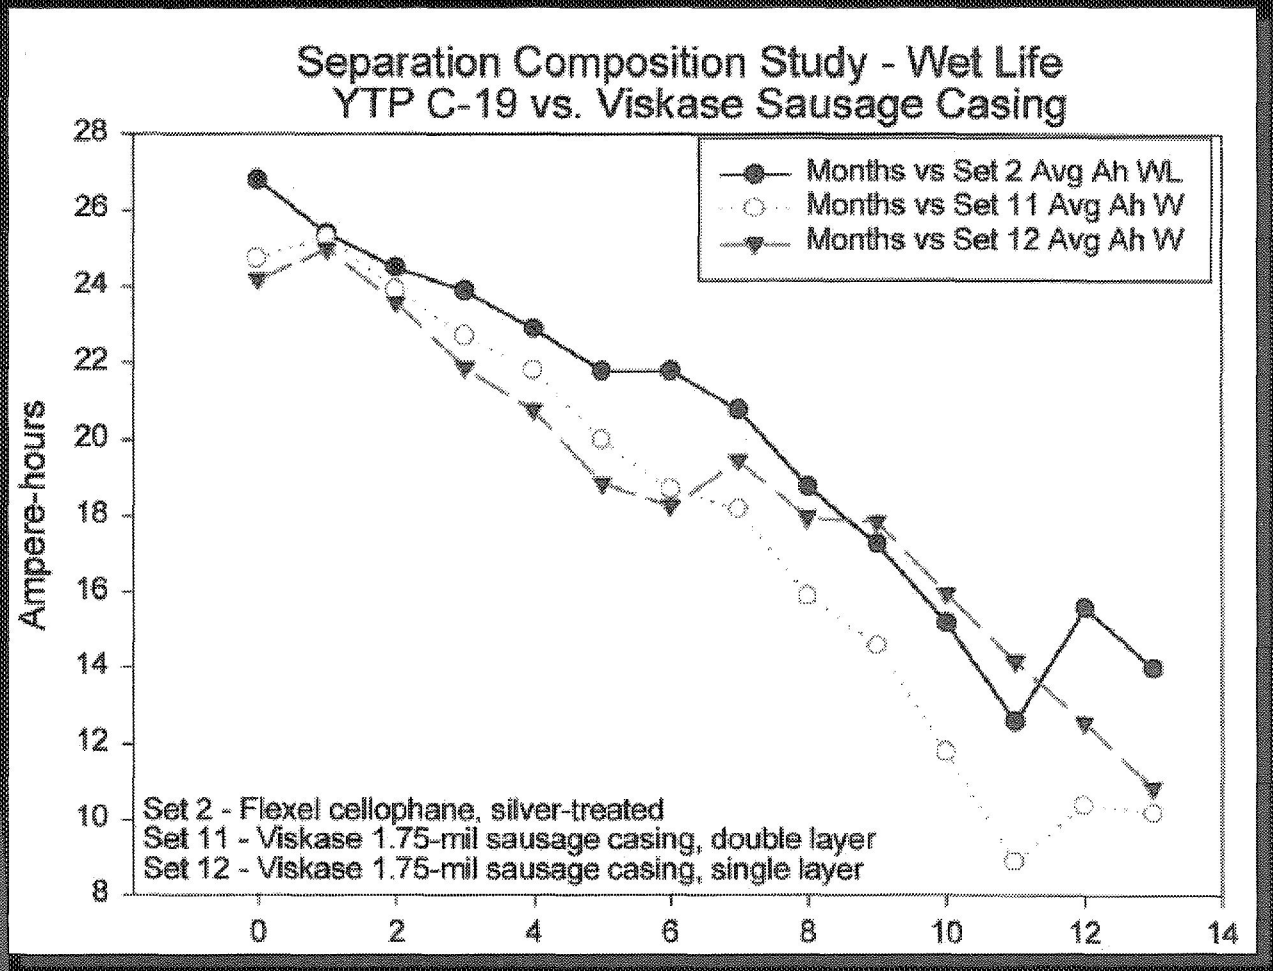

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Silver migration in cycle life cells was identical for clear vs. silver-treated cellophane.

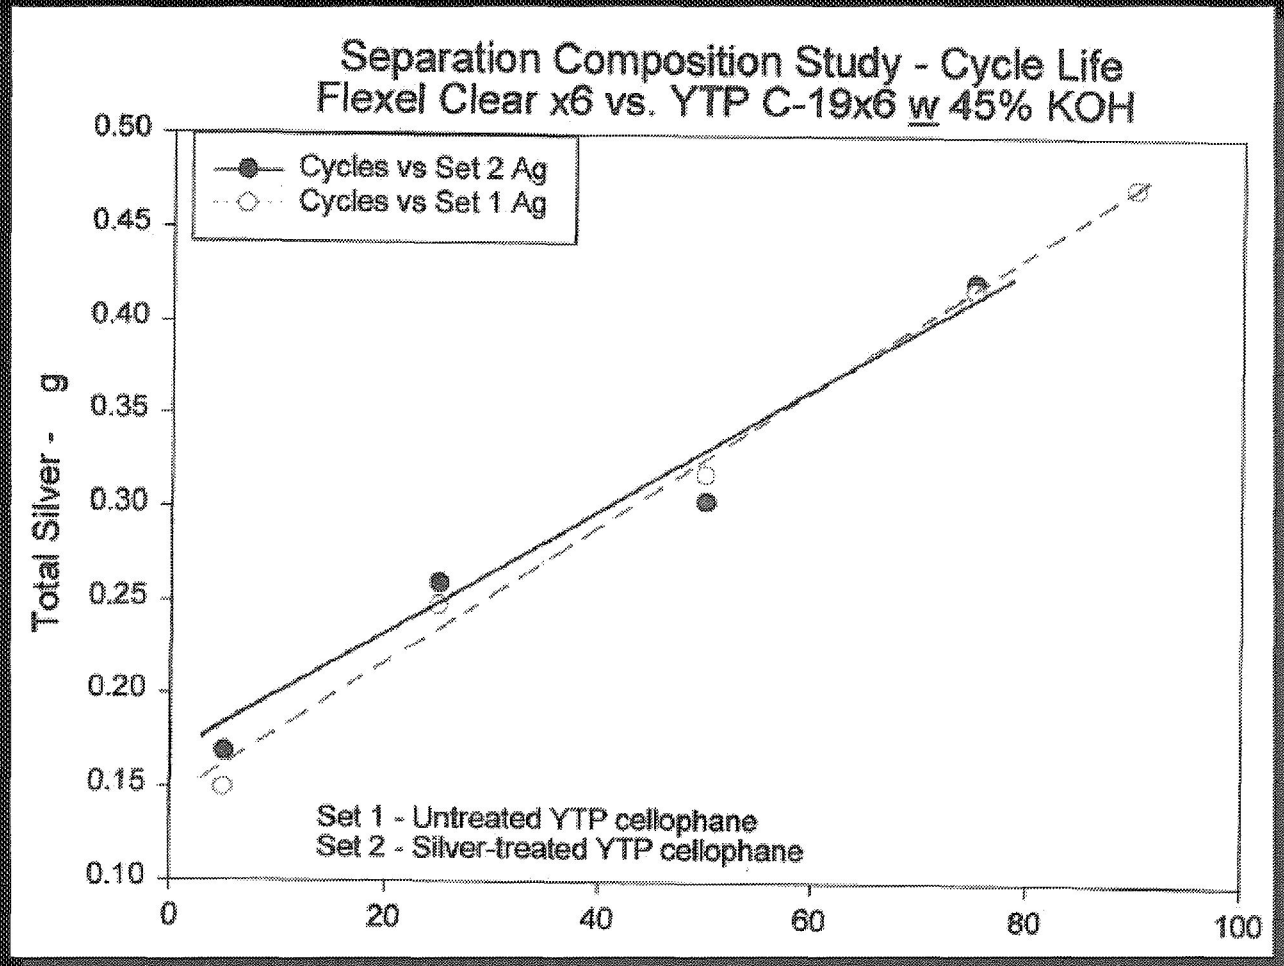

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Silver migration in wet life cells occurred at a much lower rate for C19 cells.

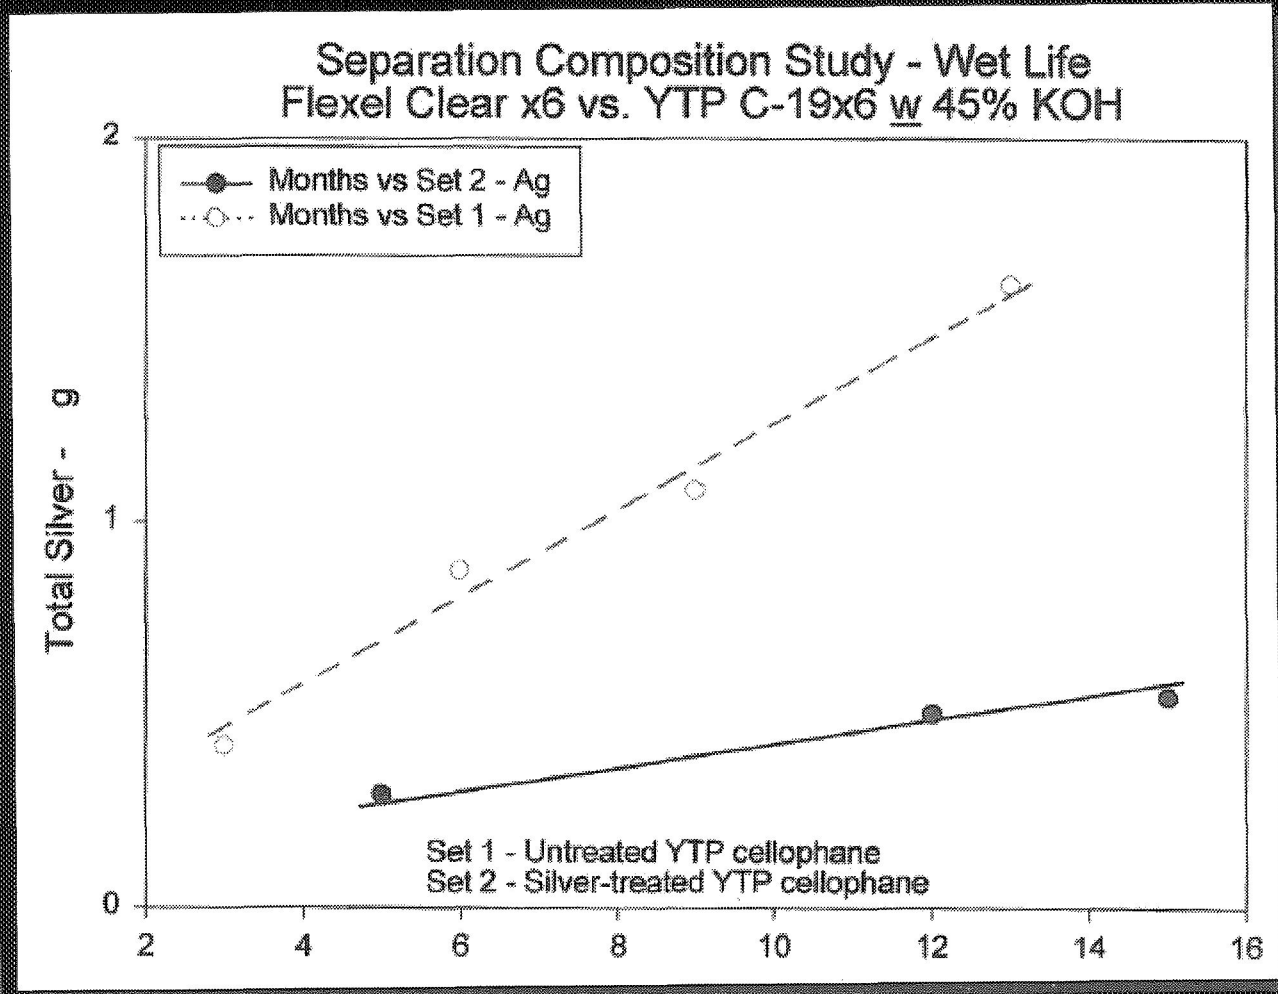

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Silver migration for split wrap similar to standard wrap in cycle life.

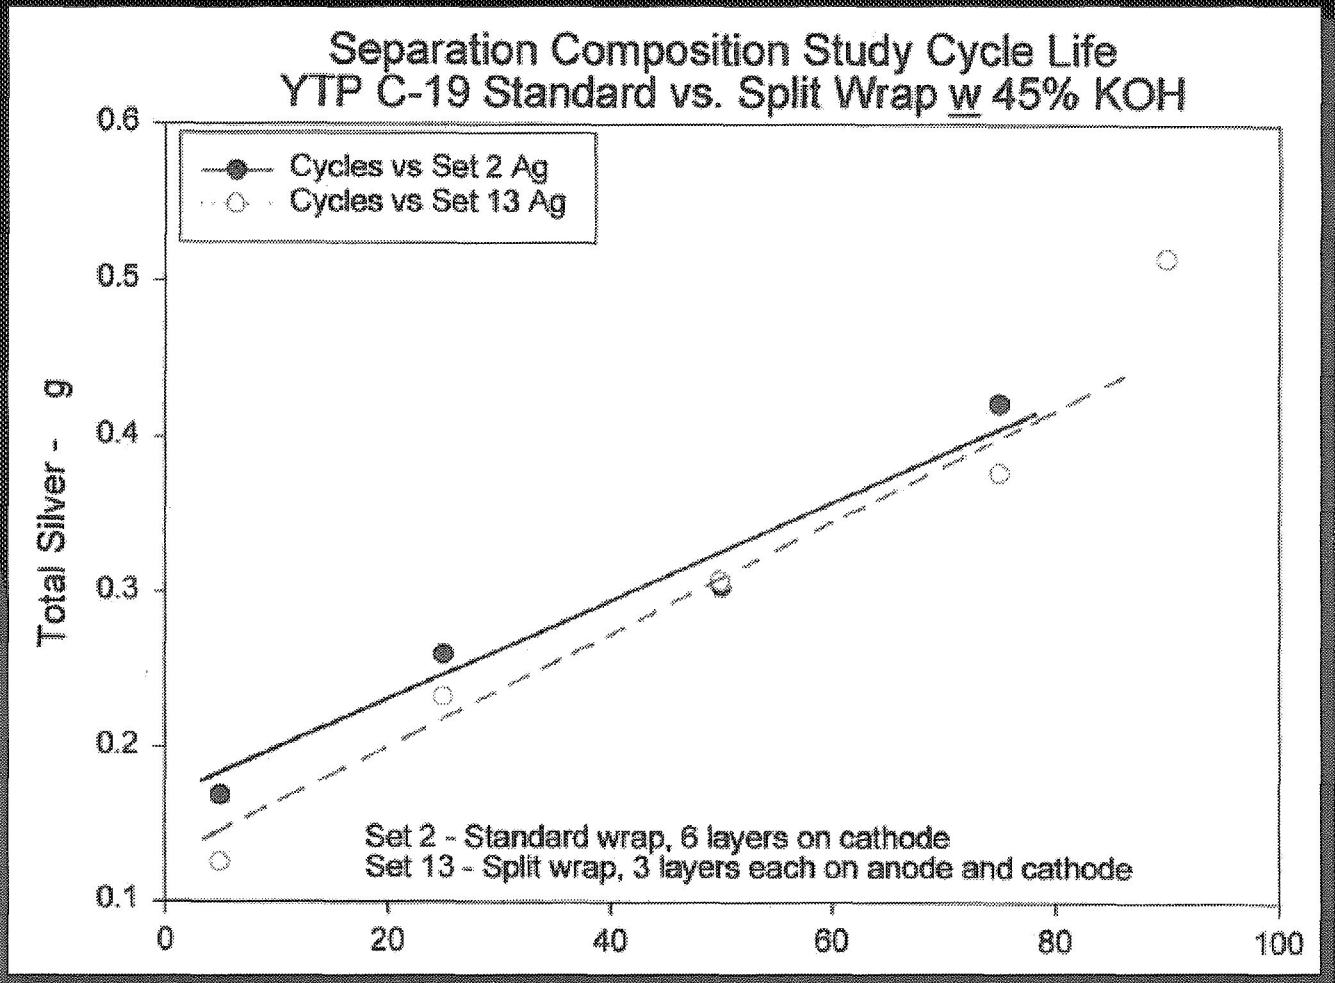

Recent Developments In Silver/Zinc Rechargeable Cell Studies

Silver migration in split wrap cells occurred at a much greater rate than for standard wrap cells in wet life.

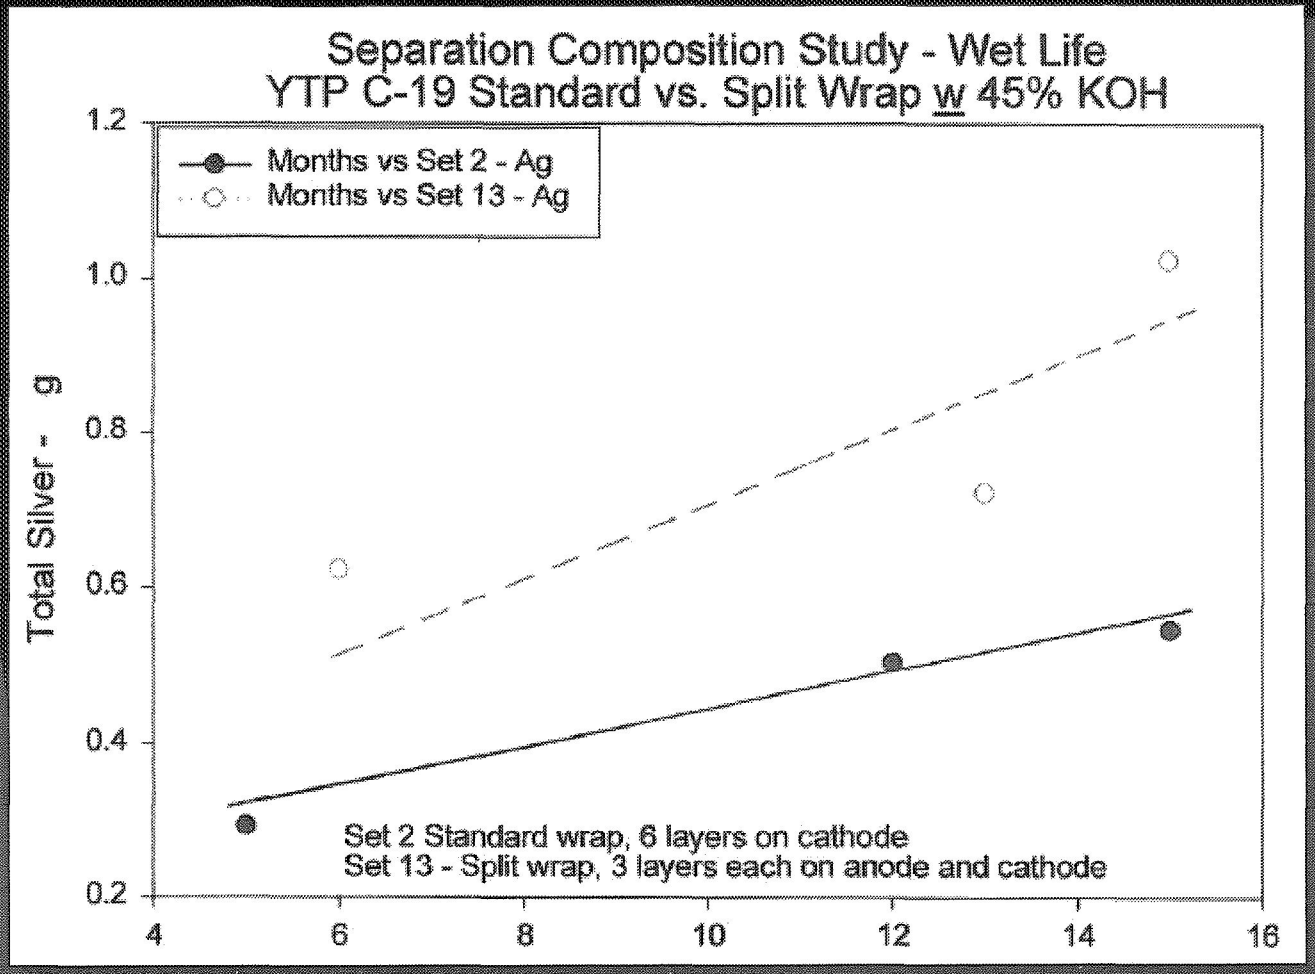

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Although it appears that the single SC layer cells have a much higher silver migration rate than C19, layer-by-layer data show that all the silver in both SC sets was trapped at the PVA layer.

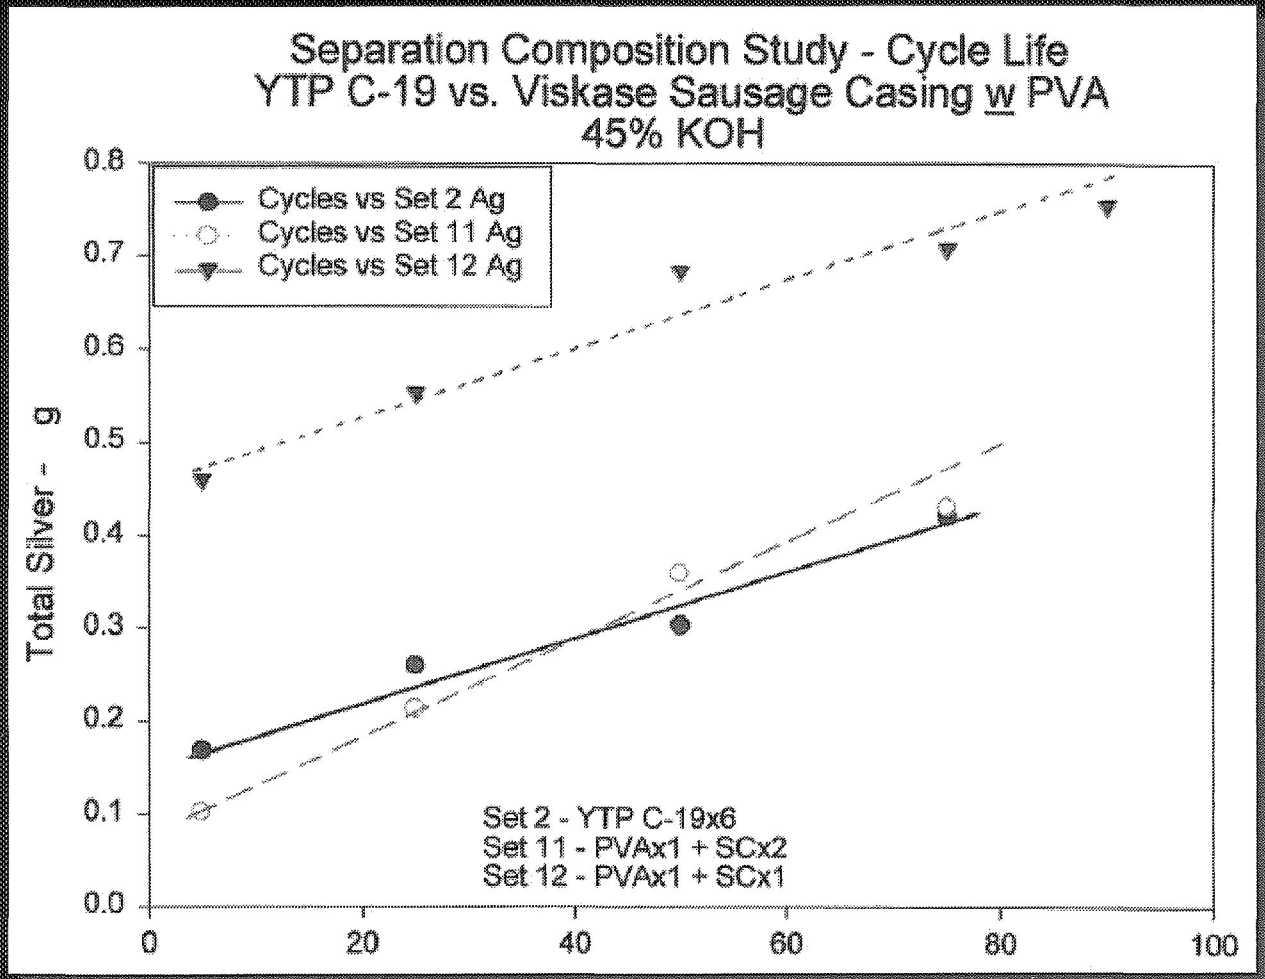

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

As in the cycle life data, here also the layer-by- layer data show that all the silver in the SC cells was stopped by the PVA film.

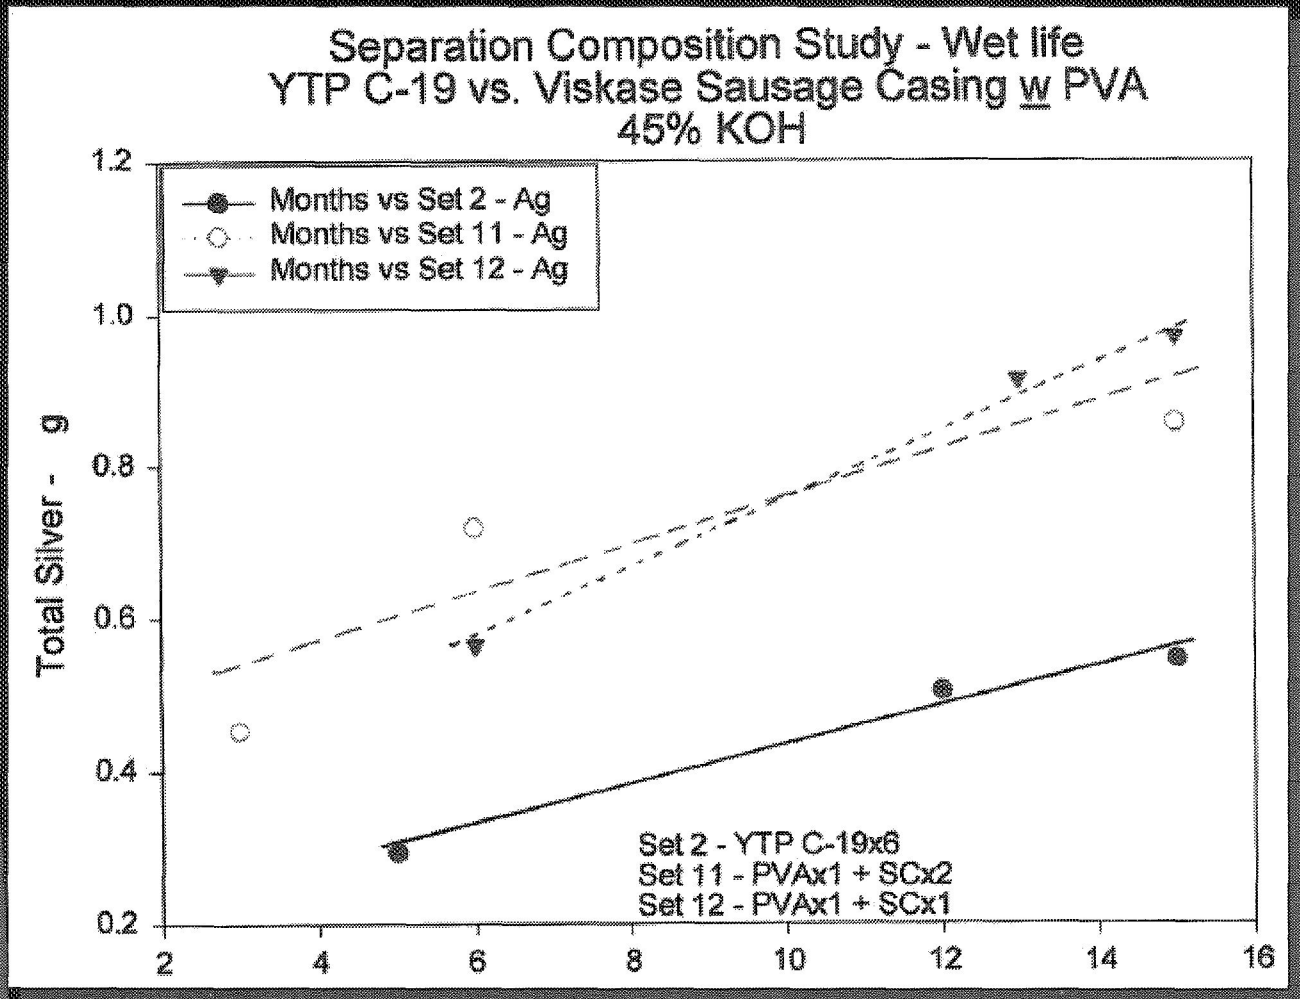

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Conclusions

- Clear vs. Silver-Treated Cellophane
- Split wrap vs. "Standard" Wrap
- Cellophane vs. Sausage Casing

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Recommendations

- Use silver-treated cellophane instead of clear cellophane
- Use split wrap for cellophane whenever possible
- Strongly consider use of sausage casing with PVA film in the following configuration:
  - 1-mil (tubular) SC/1-mil PVA film/2.3-mil plain or 6-mil fiber-reinforced SC tubular

Recent Developments In Silver/Zinc Rechargeable Cell Studies

NAVSEA CRANE

Acknowledgements

Cellophane film samples were purchased from Yardney Technical Products

Sausage Casing samples were furnished by Viskase Corporation

Funding support came from NAVSEA 03Z, SPECWARCOM, and Viskase Corporation

MOLTECH
CORPORATION

Advances in Lithium-Sulfur Rechargeable Batteries

Powering the Electronic Future

MOLTECH
CORPORATION

Corporate Overview

52/CP/IN/144
2001 7691 53 7945

Moltech' s Mission

- To be the leader in Energy Storage Products

Moltech Corporate Offices, Tucson, Arizona

Corporate Structure

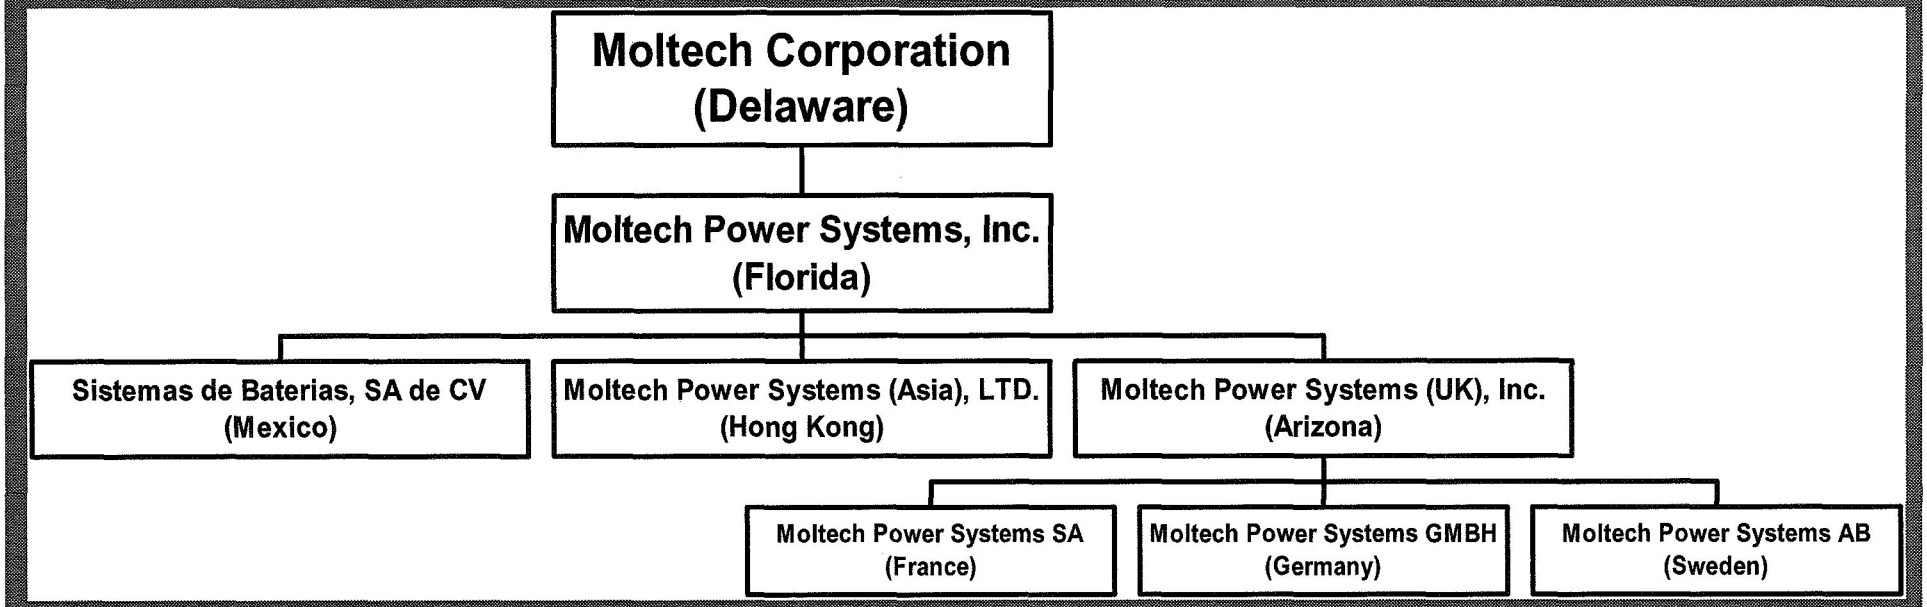

Moltech Corporation History

1988	Founded by Dr. Terje Skotheim as a spin-off from the Brookhaven National Laboratory
1994	First venture capital funding
1995	Signed development agreements with Ericsson, Atlas-Copco and Electrolux
1998-99	Development of Lithium Sulfur (Li-S™) sample cells

Moltech Power Systems History

1962	General Electric begins NiCd business in Gainesville, FL
1987	Gates Rubber acquires GE rechargeable business
1993	Eveready acquires Gates Nickel rechargeable business
Apr 99	Eveready decides to sell Energizer Power Systems (EPS)
Nov 99	Moltech acquires Energizer Power Systems and Energizer acquires equity in Moltech

Moltech Operating Structure

Gainesville, Florida
Corporate Headquarters
North & South American Marketing & Sales
NiCd / NiMH / Li-S Cell Manufacturing
NiCd / NiMH R & D
Intelligent Electronics
Development
Employees 675

Tucson, Arizona
Lithium Sulfur R & D
Employees 60

Newcastle-**Under-Lyme, UK**
European Marketing & Sales
Battery Design and Assembly
Employees 70

Juarez, Mexico
Battery Design & Assembly
NiCd / NiMH Cell Formation and Test
Employees 1400

Hong Kong
Asian Marketing & Sales
Battery Design & Assembly
Employees 70

Product Attributes

Rechargeable Li-S Cells

- *2 x Specific Energy vs Li-Ion*
- Lightweight (lithium & sulfur)
- Rate capability exceeds Li-Ion
- Environmentally benign
- Low Material Costs

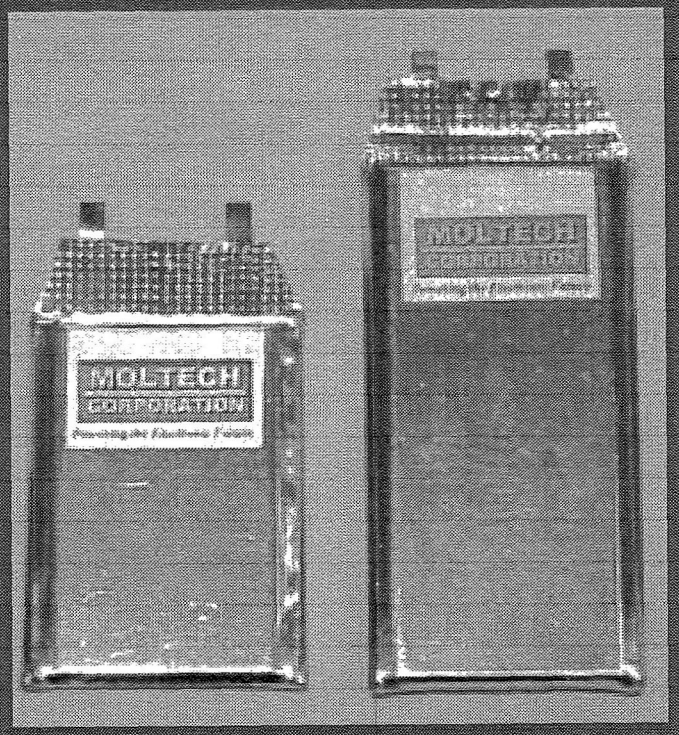

Technology can be applied to:

- *Primary Batteries*
- *Supercapacitors*

Li-S Adapted Products

Mobile Phones

2.0 – 2.5 Amps

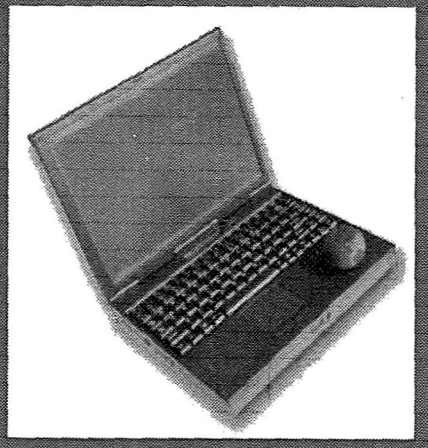

Laptop Computers

3.5 – 6.0 Amps

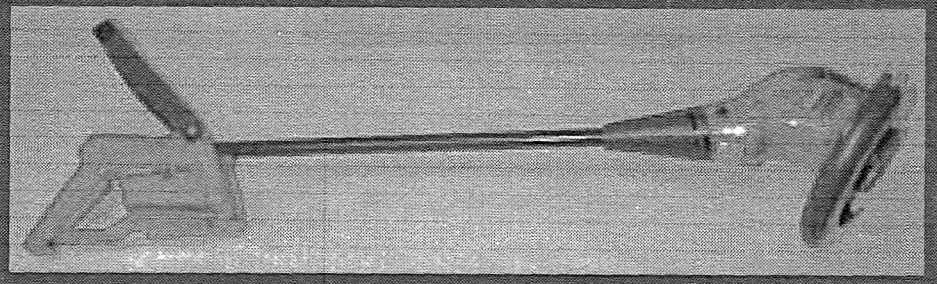

Cordless Grass Trimmer

14 Amps

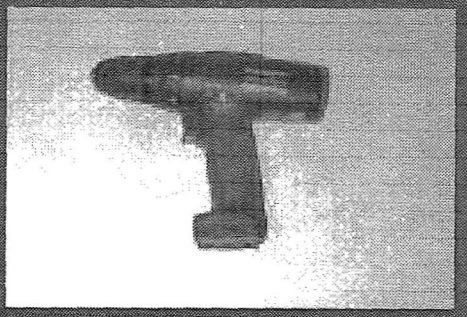

Cordless Drill

20 – 30 Amps

Cell Construction

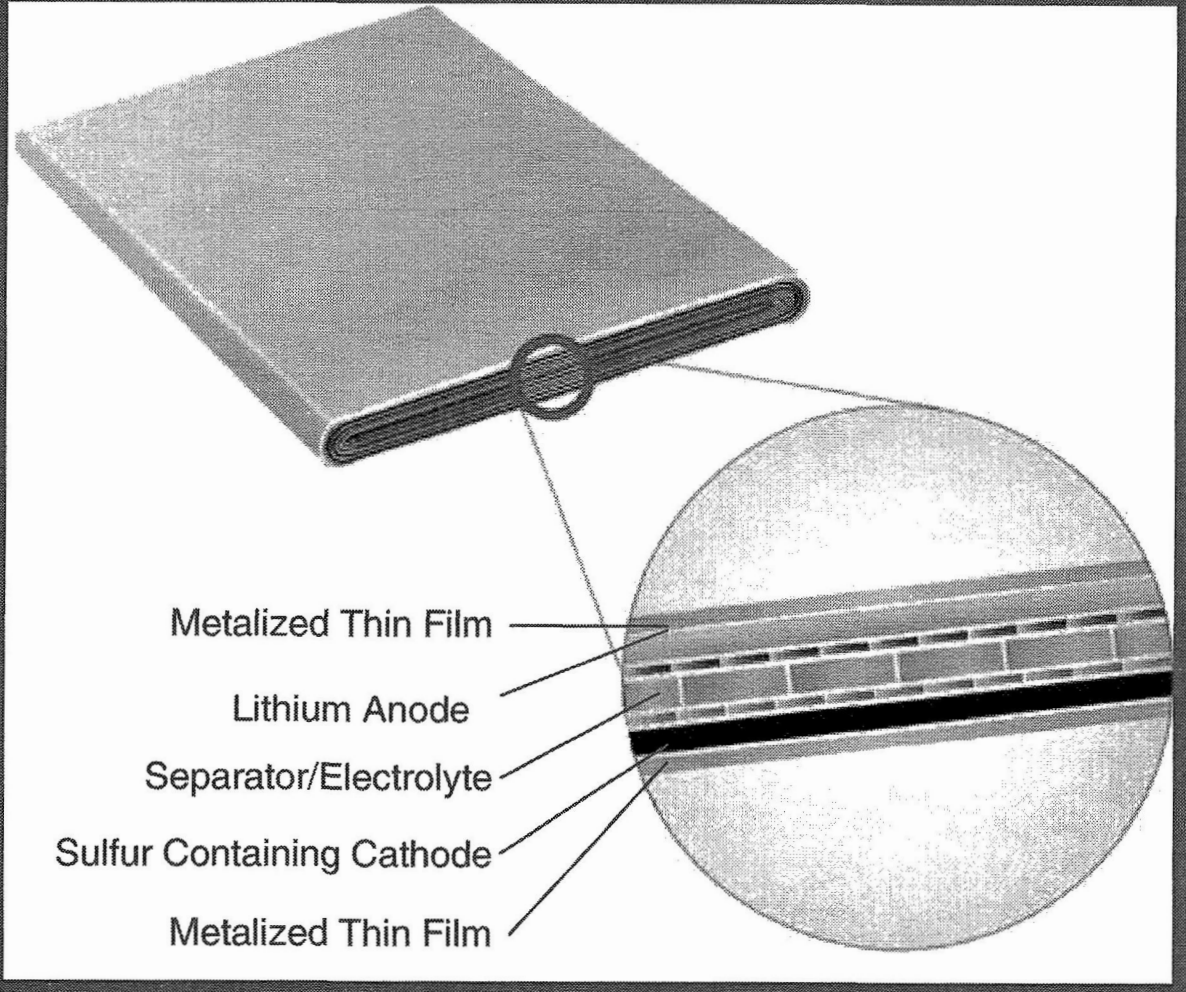

Low Manufacturing Costs

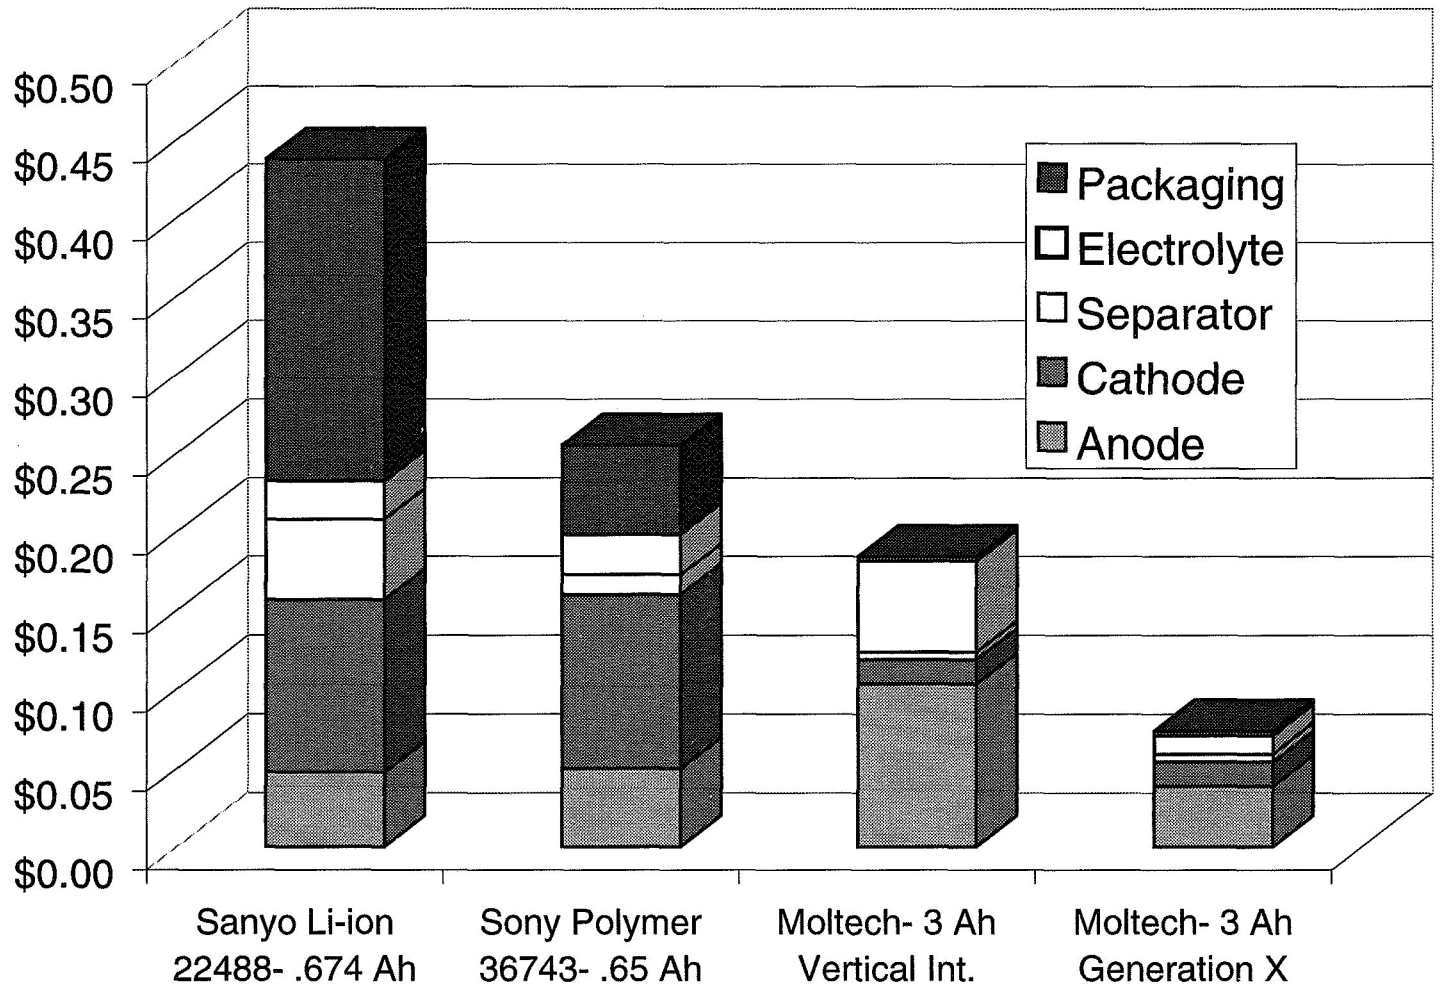

Specific Energy Comparisons

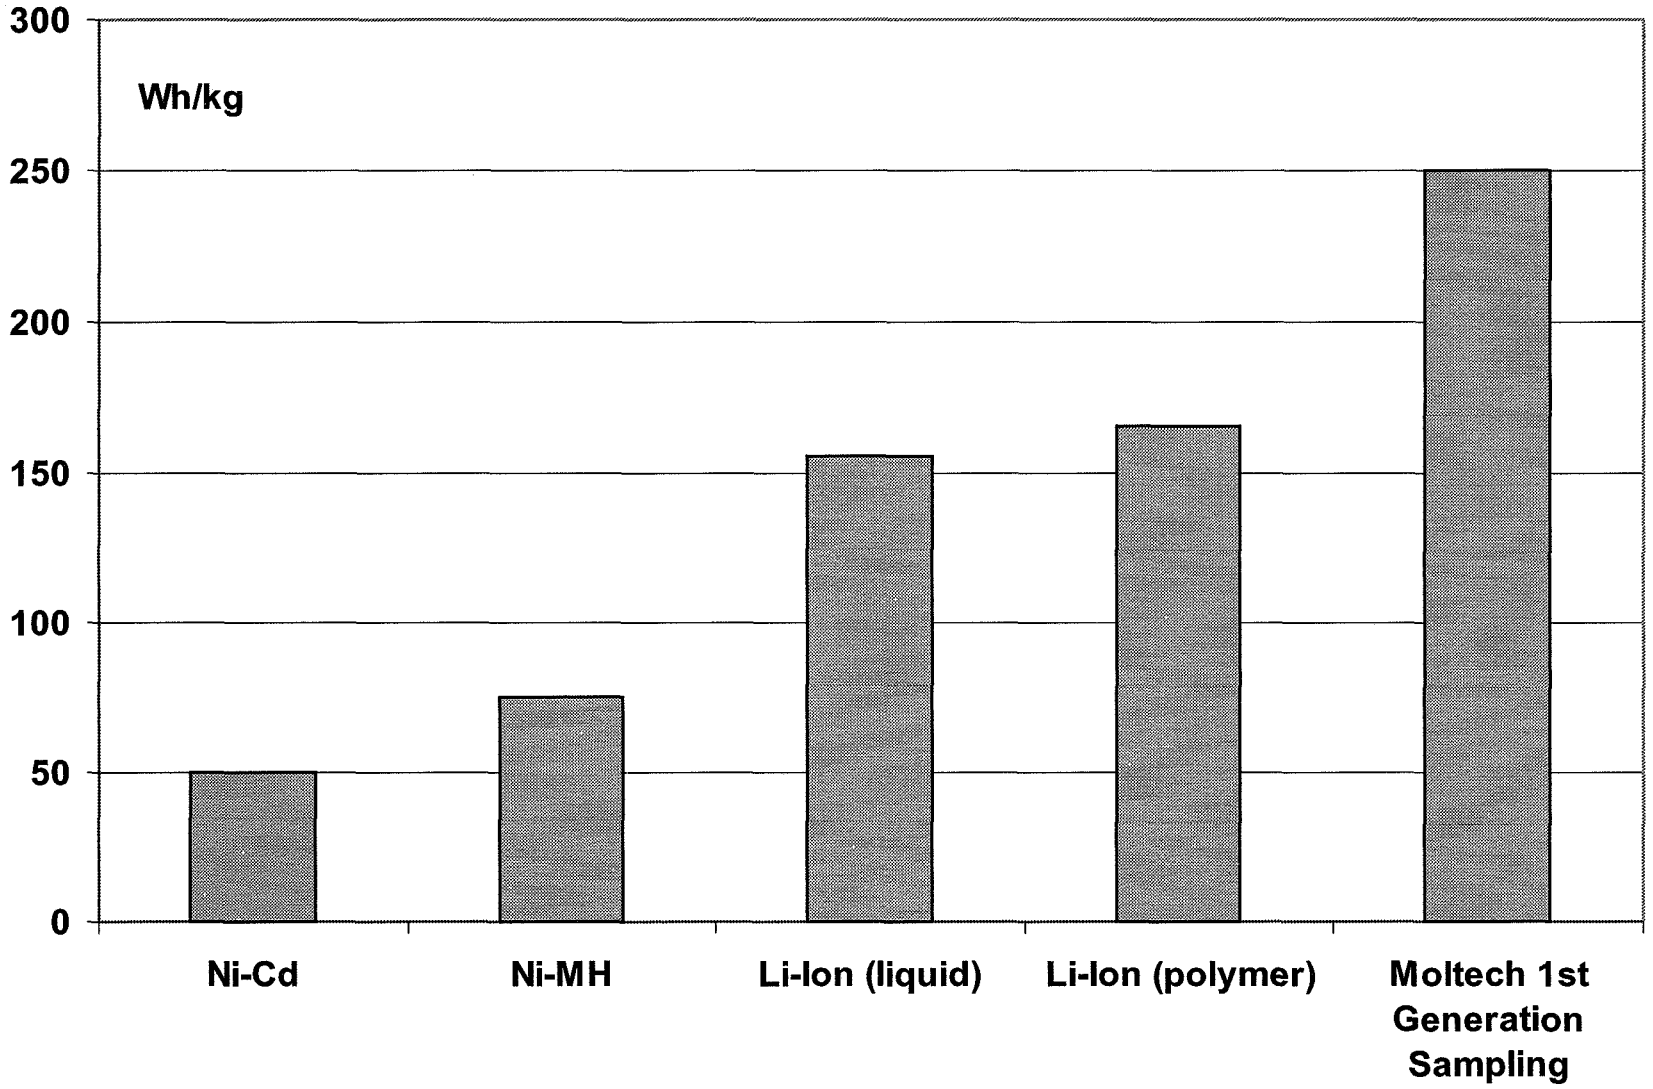

Product Requirements for Second Generation Li-S

- Cycle life to reach 300 at 80% of rated capacity
- Specific energy to 300 WH/Kg
- Volumetric energy to 400 WH/L
- Self-discharge <5%/month
- 70% of ambient capacity @ 1C at -10° C
- 90% of rated capacity at 3C at 25° C
- 80% of rated capacity at 5C at 25° C
- All safety requirements met

Active Materials Transformation Diagram

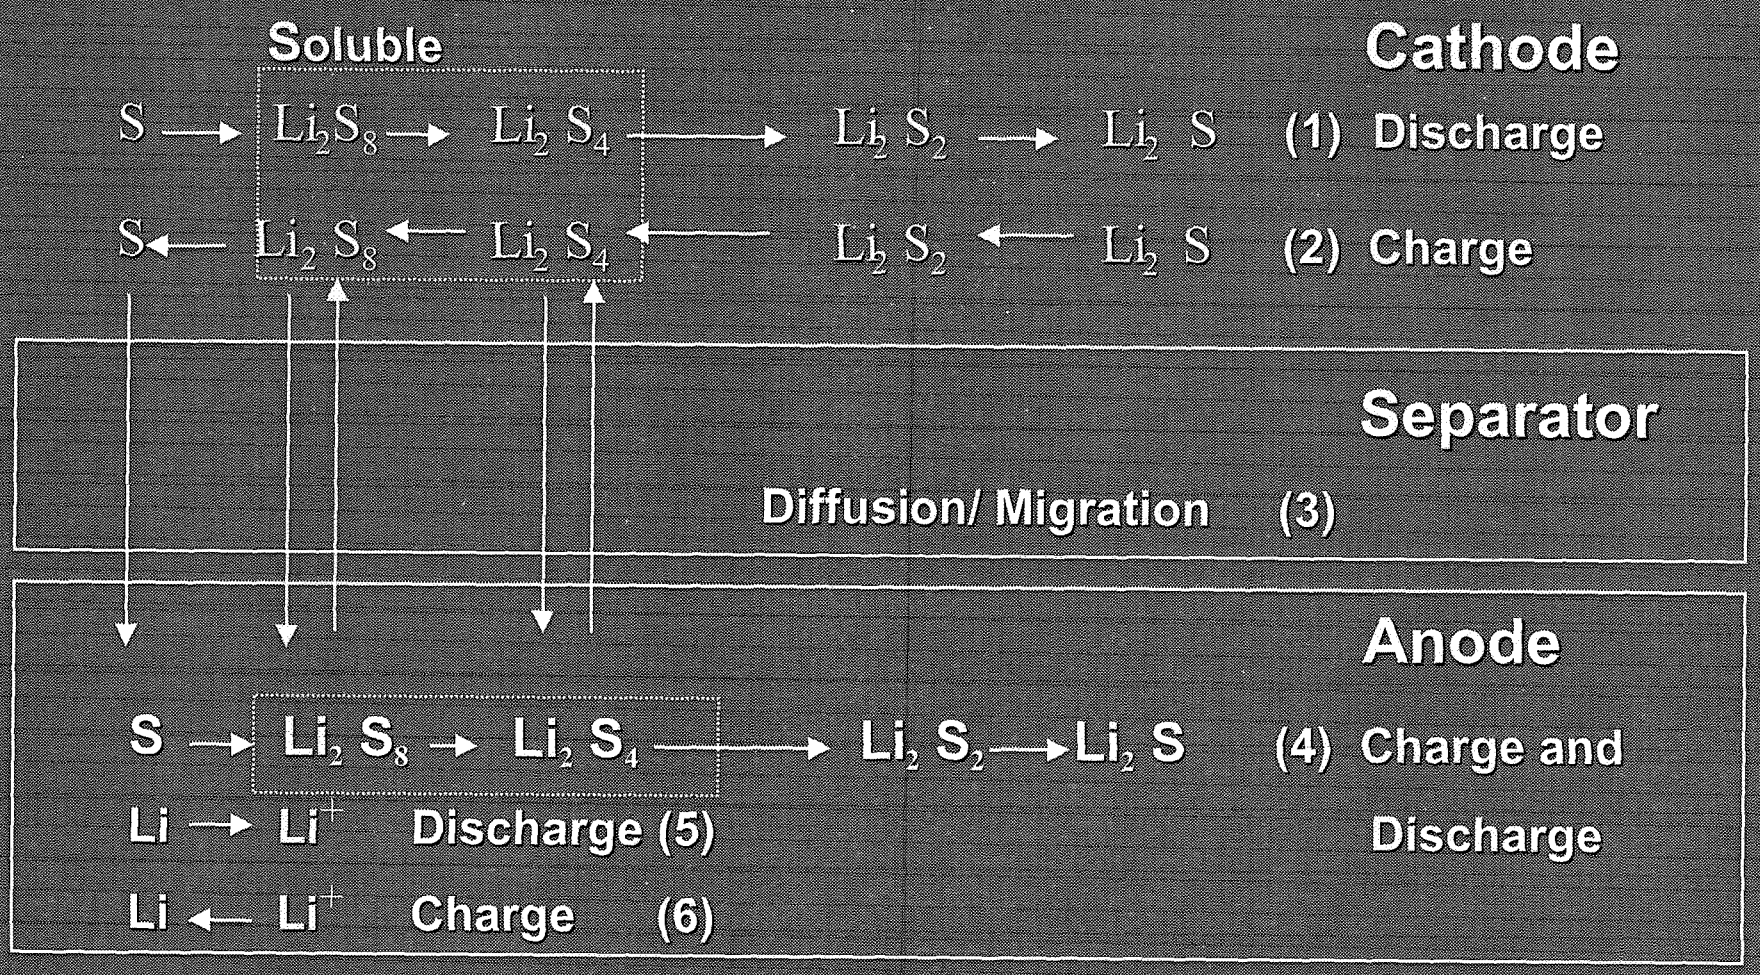

(1) (5) Discharge

(2) (6) Charge

(4+5) (3) Self-discharge

(4+5) (3) (2) Over-charge protection : Shuttle current

Internal Shuttle Protection

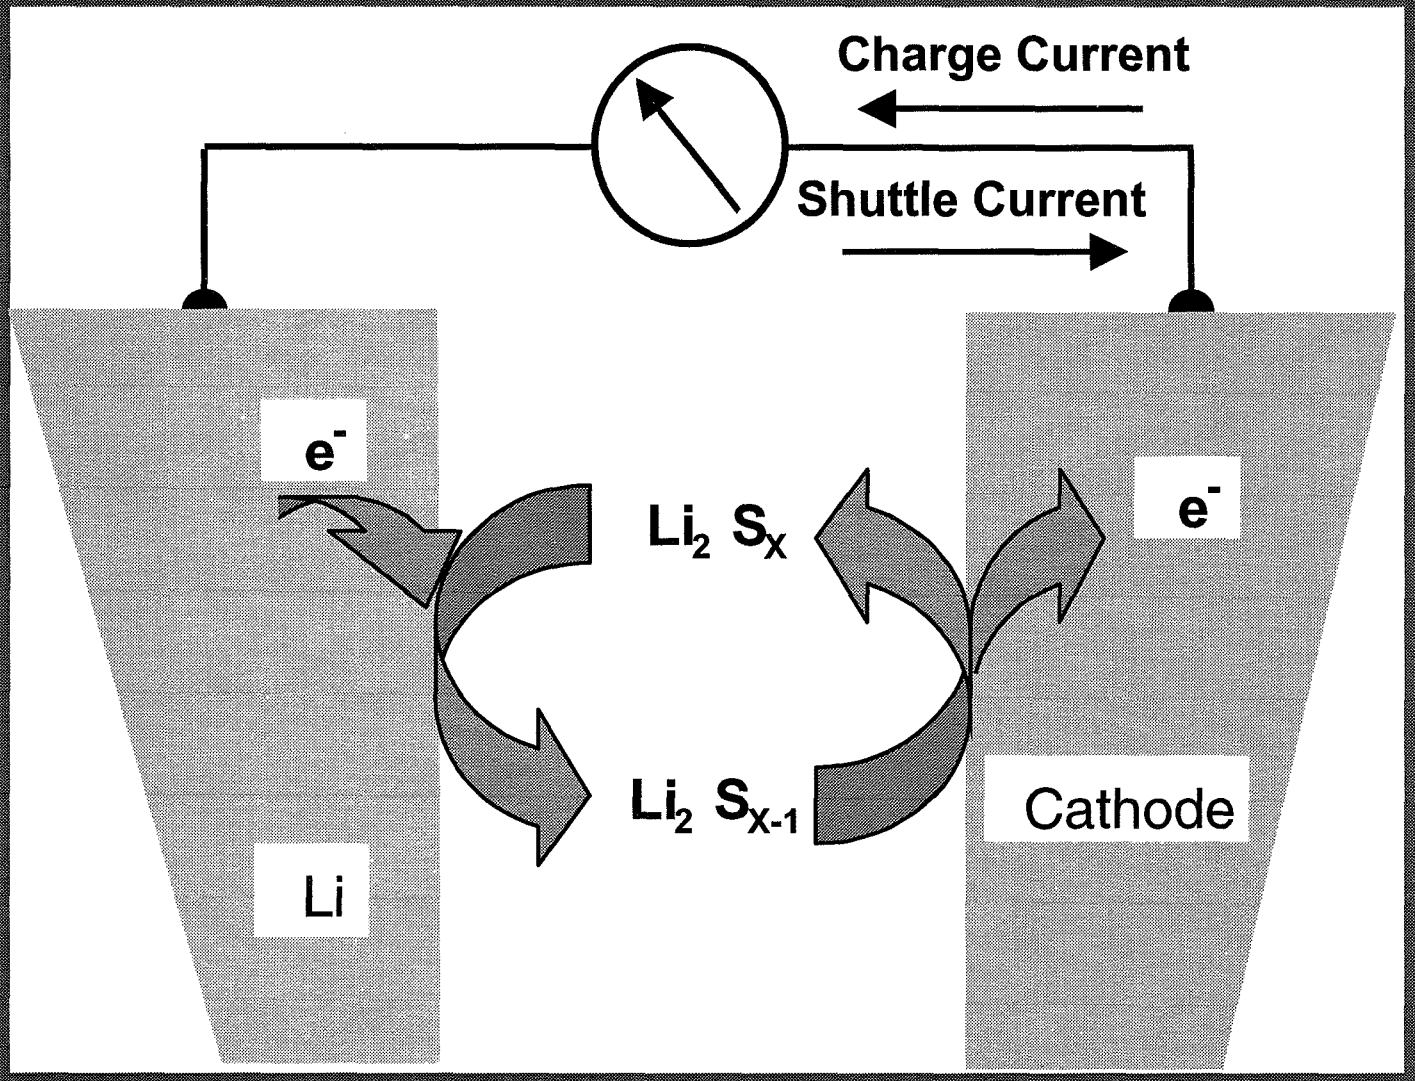

Overcharge protection - Shuttle current diagram

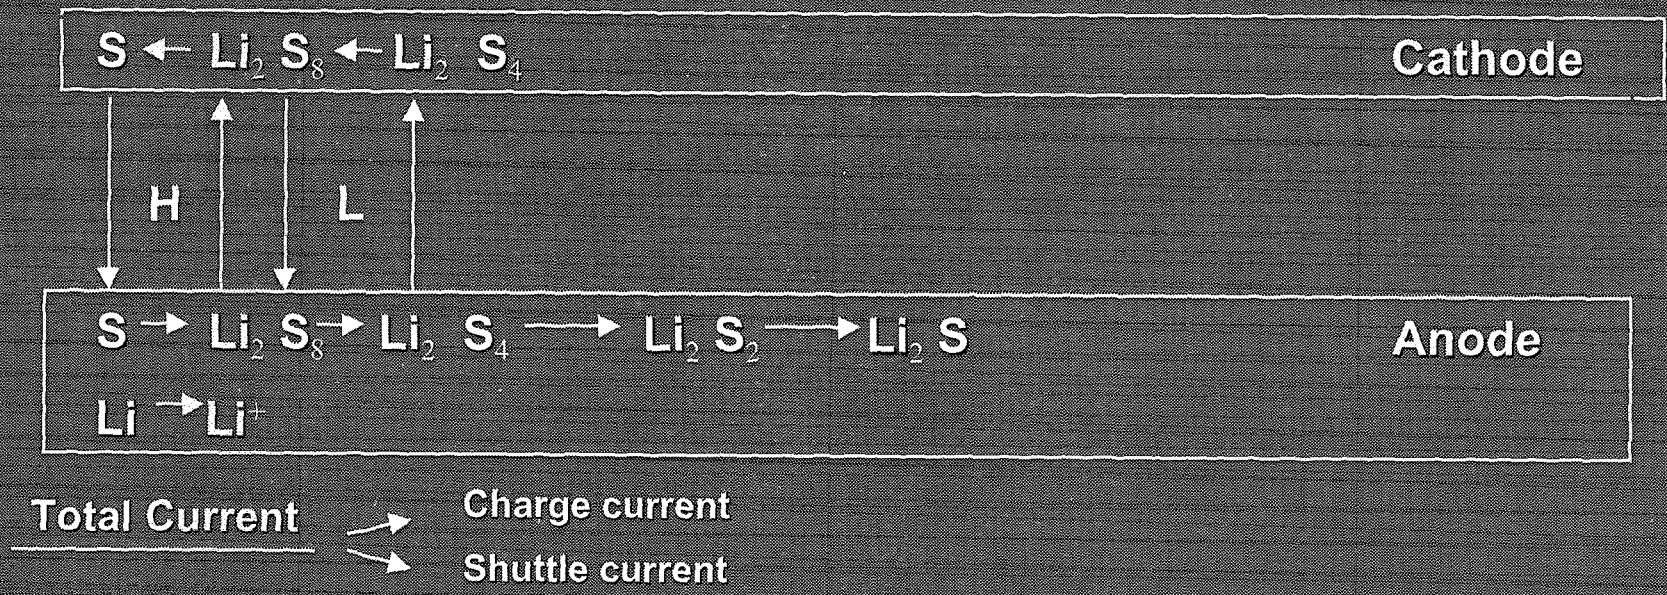

Cycle L	Voltage	
	Shuttle current	~ 0.05 mA/cm^2
	Charge efficiency	95 - 98%
Cycle H	Voltage	2.35 - 2.60 V
	Shuttle Current	0.1 - 0.2 mA/cm^2
	Charge efficiency	40 - 60%

Typical Performance

Discharge Capacity vs Cycle Number

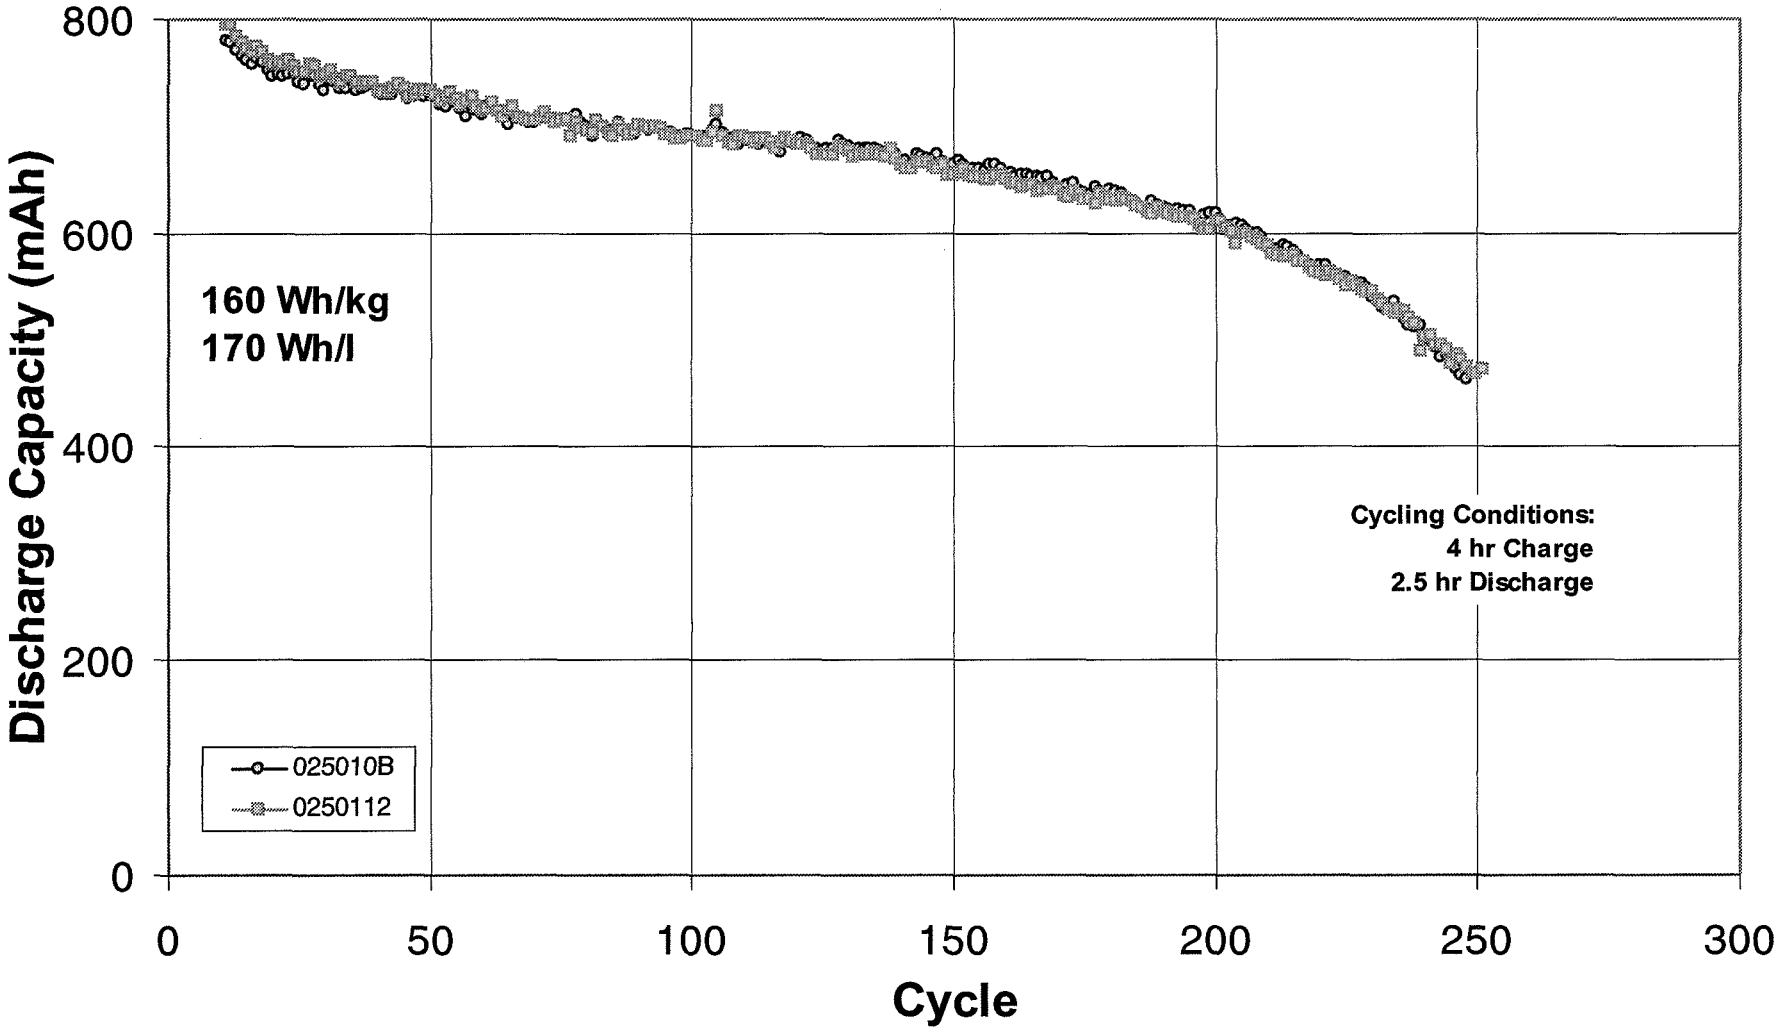

Typical Performance
GSM Discharge Profile

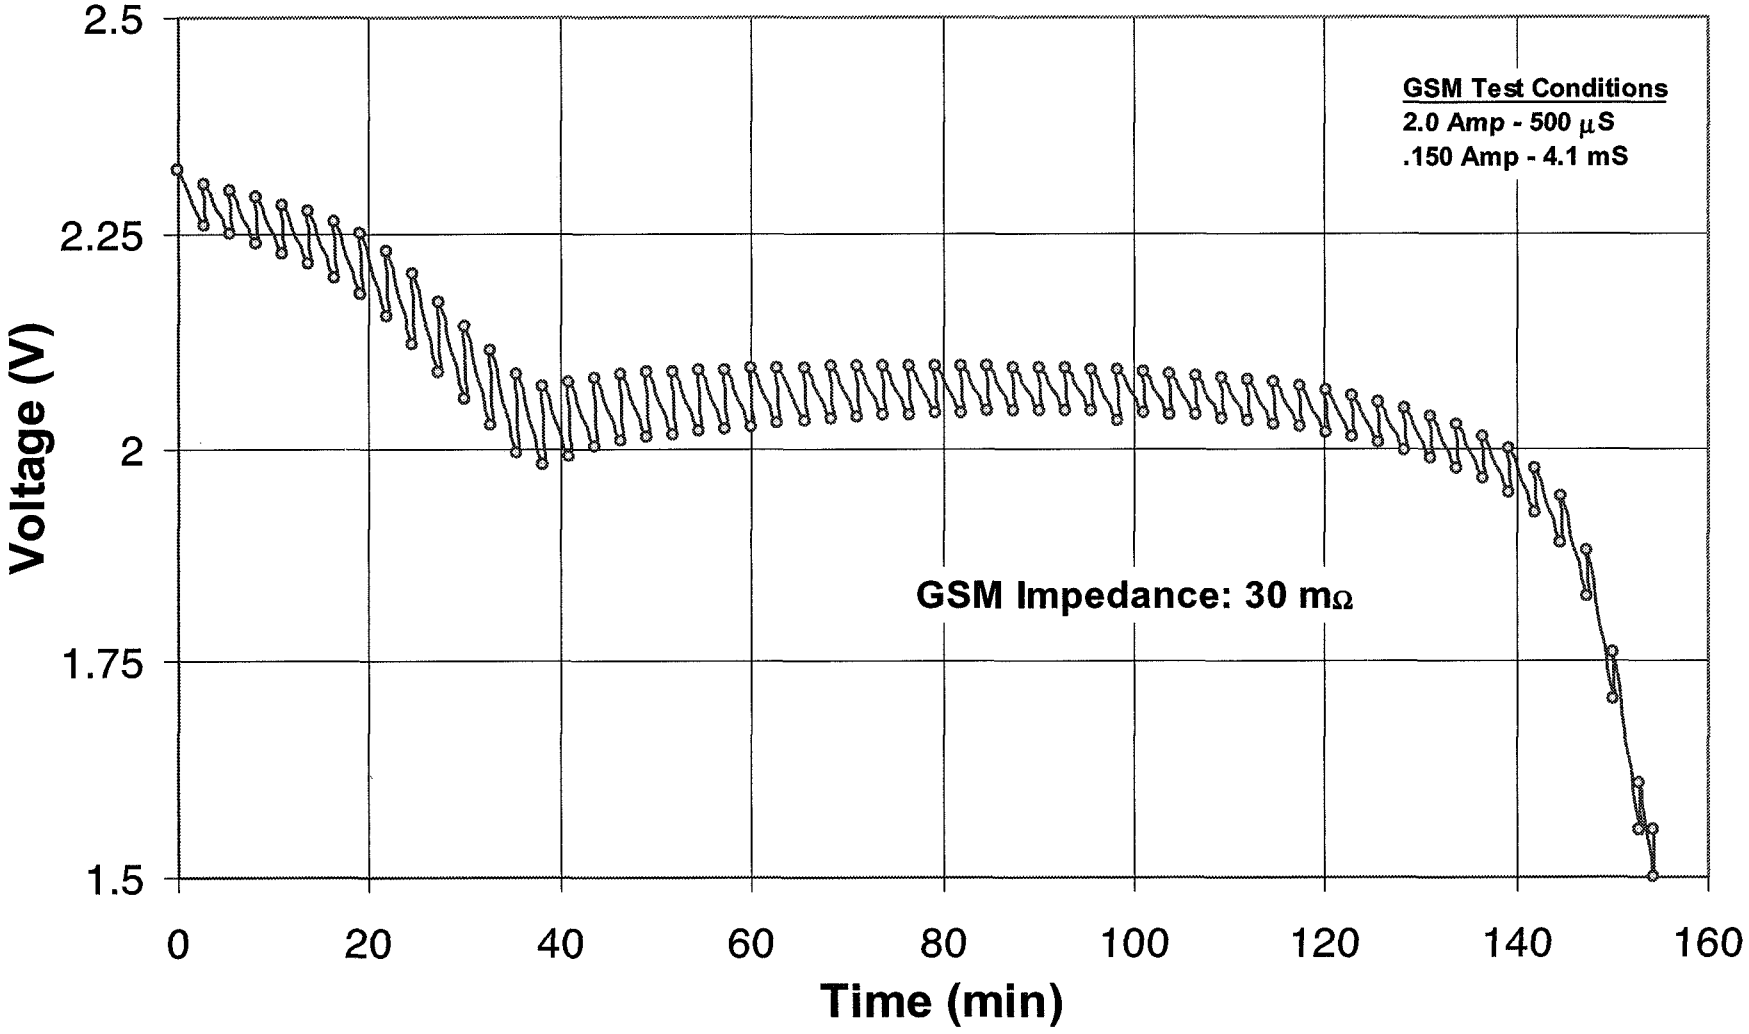

Ragone Plot

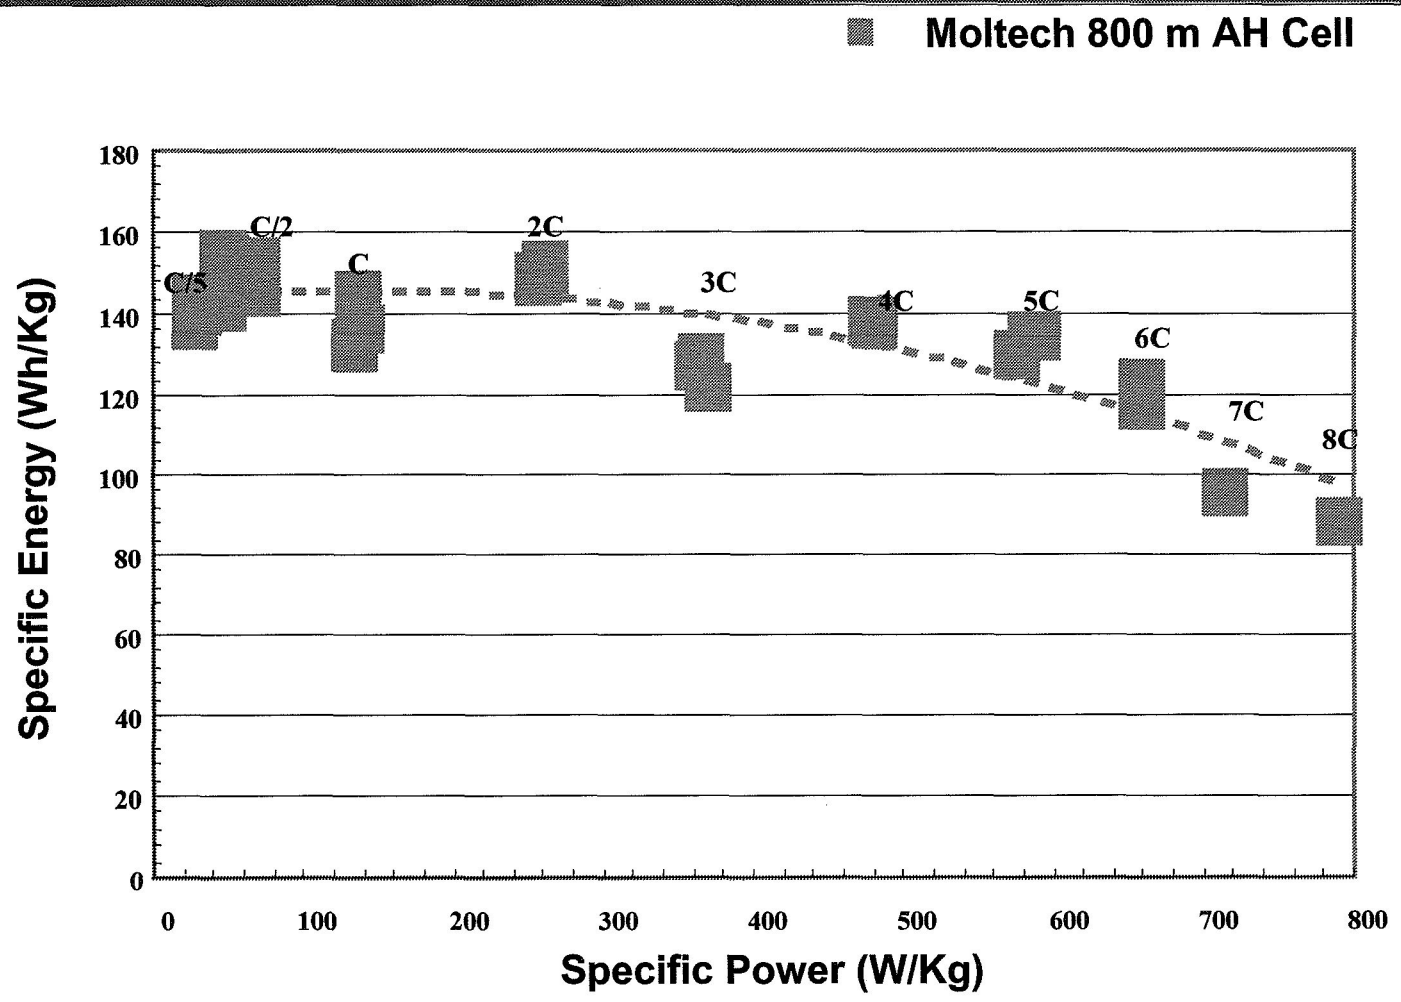
Moltech 800 m AH Cell
Specific Energy (Wh/Kg)
Specific Power (W/Kg)
0
20
40
60
80
100
120
140
160
180
0
100
200
300
400
500
600
700
800
C/5
C/2
C
2C
3C
4C
5C
6C
7C
8C

UL 1642 Safety Test Results on Lithium Sulfur Cells
No Safety Circuitry - Bare Cells

Test	UL	1 Cycle		50 Cycles		100 Cycles		150 Cycles	
	Required?	Passed	Failed	Passed	Failed	Passed	Failed	Passed	Failed
Short Circuit (60°C)	Yes	5	0	3	0	3	0		
Forced Discharge (.8Ax2.5h)	No	5	0						
Forced Discharge (.2Ax12.5h)	Yes			3	0	3	0		
Free Fall	Yes	5	0	3	0	3	0		
Flaming Particles (Fire Exposure)	Yes	5	0	3	0	5	0		
Projectile Test (Fire Exposure)	Yes	5	0	3	0	5	0		
Crush	Yes	5	0	3	0	3	0		
Impact	Yes	5	0	3	0	3	0		
Nail Penetration	No	5	0	3	0				
Overcharge (0.8A)	No	5	0						
Overcharge (0.2A)	Yes			6	0	5	0		
Thermal Exposure (Ramped)	Yes	0	5	5	0	5	0		
Thermal Exposure (Preheated Oven)	No	0	5						
High Rate Charge (2.4A)	No	4	1*						
High Rate Charge (.6Ax3.5h)	Yes	5	0	4	3*	5	1*		

* These failures could be interaction between cells and test equipment.

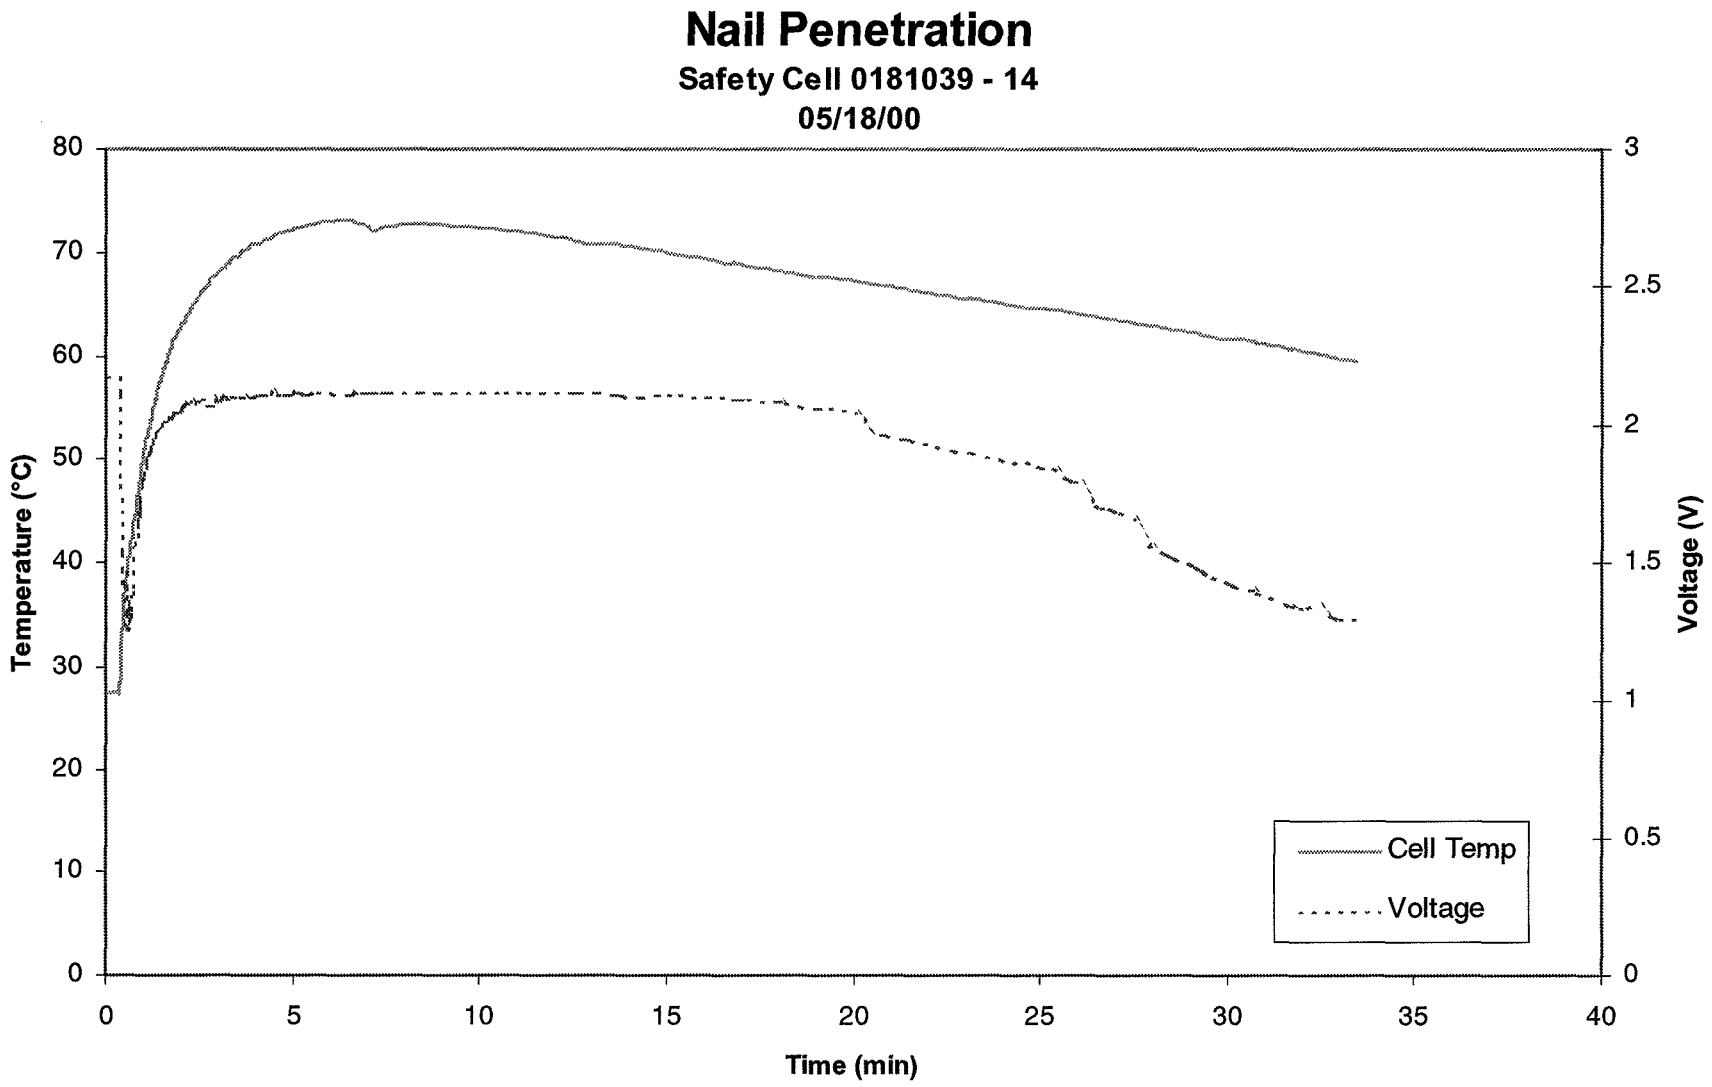
Nail Penetration
Safety Cell 0181039 - 14
05/18/00
Temperature (°C)
Voltage (V)
Time (min)
Cell Temp
Voltage
0
10
20
30
40
50
60
70
80
0
0.5
1
1.5
2
2.5
3
0
5
10
15
20
25
30
35
40

Core Intellectual Property

- Li-Sulfur Chemistry and Materials
- Advanced Materials and Processing
- Thin Film Technology
- Product Design and Manufacturing

Patent Portfolio Status

- 140 Patents & Applications
- Cover all aspects of materials, product design & manufacturing
- Control of Intellectual Property
- Protection in major battery markets

Battery Patents

- Organo-sulfur polymers
- Cathode compositions
- New separator technology
- Electrolyte compositions
- Anode stabilization and cycleability
- Cell design and engineering
- Cell assembly and manufacturing processes

Moltech Corporation
Li-S Commercialization

- Technology Research & Engineering Development
  - Tucson, AZ
- Production infrastructure in Gainesville, FL
  - Buildings
  - Land
  - Equipment
  - People
- UL Certified Test Laboratory
  - Gainesville, FL
- Electronics Design & Development Laboratory
  - Gainesville, FL

Moltech Corporation
Li-S Commercialization

- Battery Pack Design & Development Laboratory
  - Gainesville, FL
- Battery Pack Assembly
  - Juarez, Mexico
  - Hong Kong
  - UK
  - Malaysia
- Global Marketing/Sales Force

Summary

- Technology advancement from 150 cycles @ 50% rated capacity to 200 cycles@ 80% of rated capacity from January 2000 to September 2000.
- Current Status of development represents 40% of potential for cycle life and energy densities.
- Chemistry today shows safety performance compatible with commercialization.
- Moltech Corporation has all infrastructure required for commercialization.

MOLTECH
CORPORATION

Advanced Rechargeable Lithium Batteries

Powering the Electronic Future

53/cp/1W/44

Effects of AEA Cell-Bypass-Switch Closure on Charged EOS-Aqua NiH_2 Cell

2000 NASA Aerospace Battery Workshop

Denney Keys
Gopalakrishna M. Rao
David Sullivan
Harry Wannemacher*

NASA GODDARD SPACE FLIGHT CENTER
*QSS GROUP, INC

2001117704
24 pgs
537969

Objectives

- Verify the Performance of AEA Cell Bypass Protection Device (CBPD) under simulated EOS- Aqua/Aura flight hardware configuration
- Assess the Safety of the hardware under an inadvertent firing of CBPD switch, as well as the closing of CBPD switch under simulated high cell impedance
- Confirm that the mode of operation of CBPD switch is the formation of a continuous low impedance path (a homogeneous low melting point alloy)

EOS-Aqua Flight Hardware

- Battery Cells:
  - Eagle-Picher 160 Ah NiH_2 (RNH 160-3)
  - Size: ~ 12cm Diameter
    ~ 32cm overall Height
  - Weight: ~ 4.3kg
- Cell-Bypass-Switch:
  - AEA Technology
    Cell Bypass Protection Device (CBPD)

AEA Hardware Tested

- A total of five (5) CBPDs were tested using the charged EOS Cell
  - Three FLIGHT devices
    (F01, F02 and F03)
  - Two ENGINEERING MODEL devices
    (EM01 & EM02)
- The two types of CBPDs are basically the same, with a change in separator and minor outer dimension changes

AEA Bypass Switch Schematic

CBPD - LMPA Schematic
(Low Melting Point Alloy)

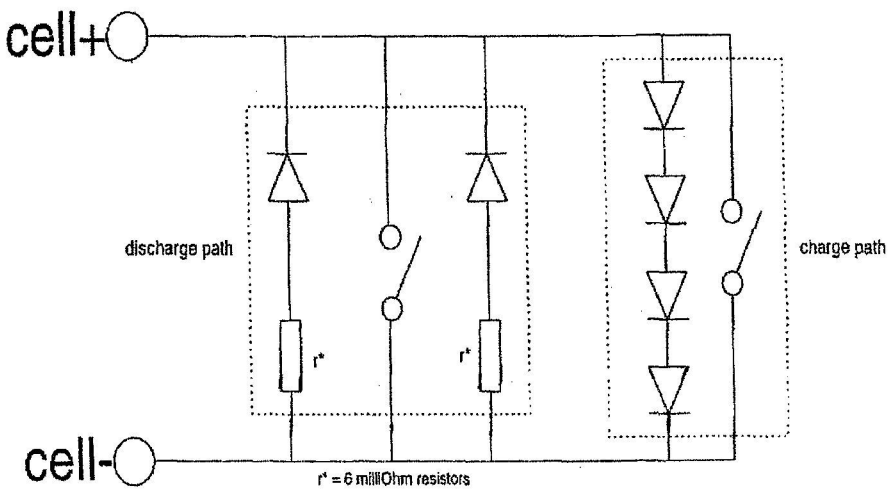

AEA Technology

Slide serial no 6
© 1997 AEA Technology plc

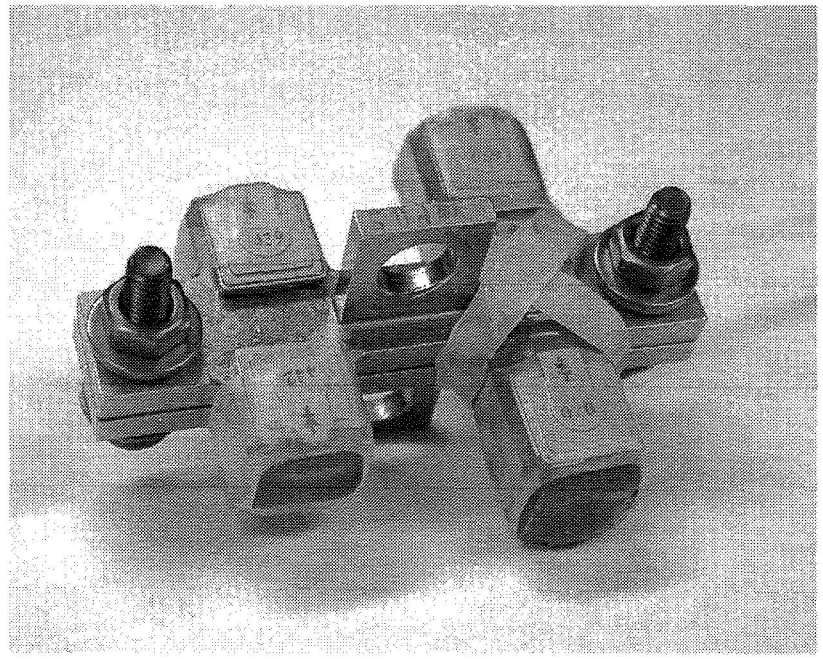

FLIGHT CBPD

NOTE: Tested devices have 6 series diodes in charge path (not 4 as shown)

AEA Cell-Bypass-Switch Spec

TRW spec for Aqua	CBPD - Specification
90 grams	• 75grams
Icharge ~ 75A	• Icharge < 35A
	• I discharge < 235A
	• Triggering - see operation summary
R ~ 500 microOhms	• R ~ 200 microOhms
	• I operation < 400A - dependent on leads and mounting

AEA Technology

Slide serial no 13

© 1997 AEA Technology plc

Tests Performed

- Test#1: CBPD F01
  Activated with heatgun
  Switch-axis ~45° from Horizontal
- Tests #2 & 3: CBPD EM01 & EM02
  Activated through charge diodes
  Switch -axis Vertical
- Test#4: CBPD F02
  Activated through charge diodes
  Switch-axis Horizontal (launch orientation)
- Test#5: CBPD F03
  same as Test#4, with added 50 mΩ
  resistance in current path

Test #1 setup (switch activated with heatgun)

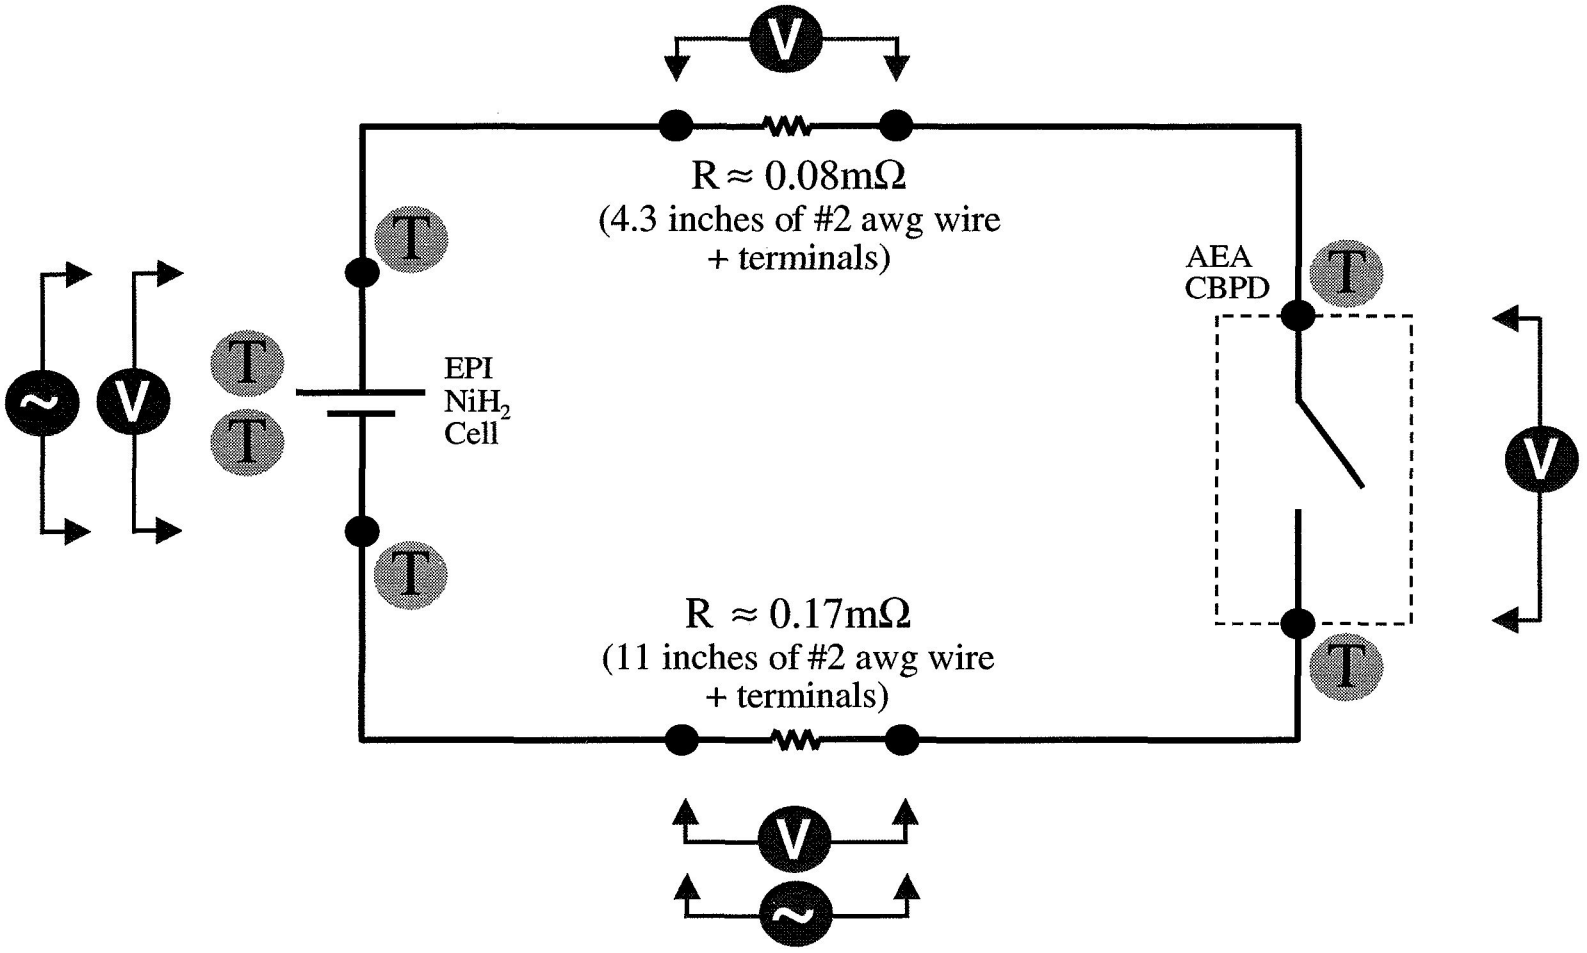

Test #1

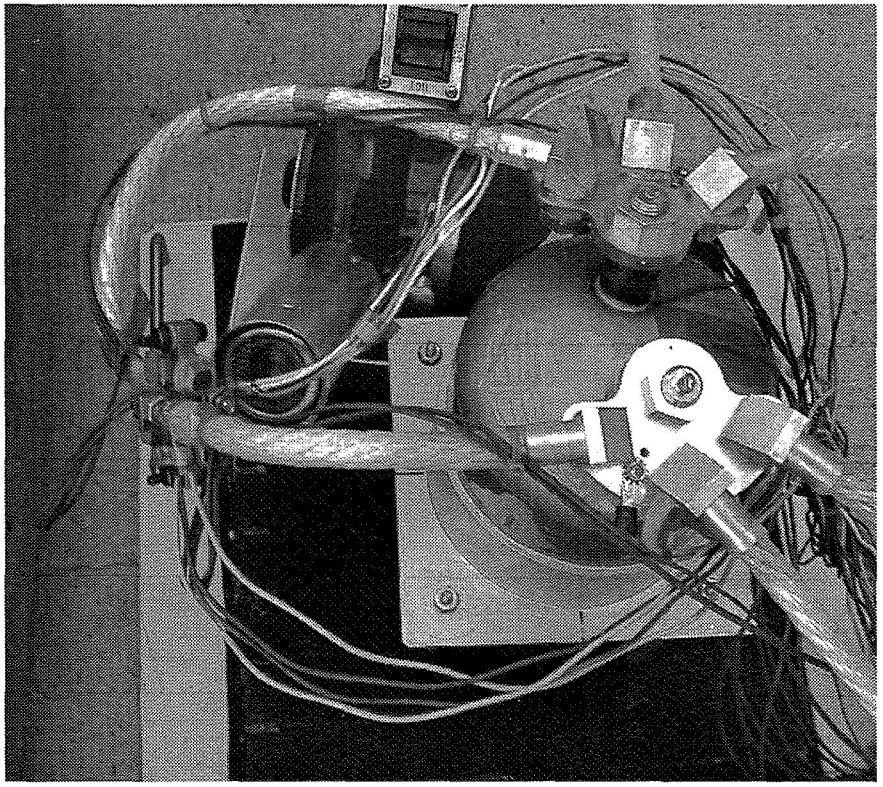

First application of heatgun

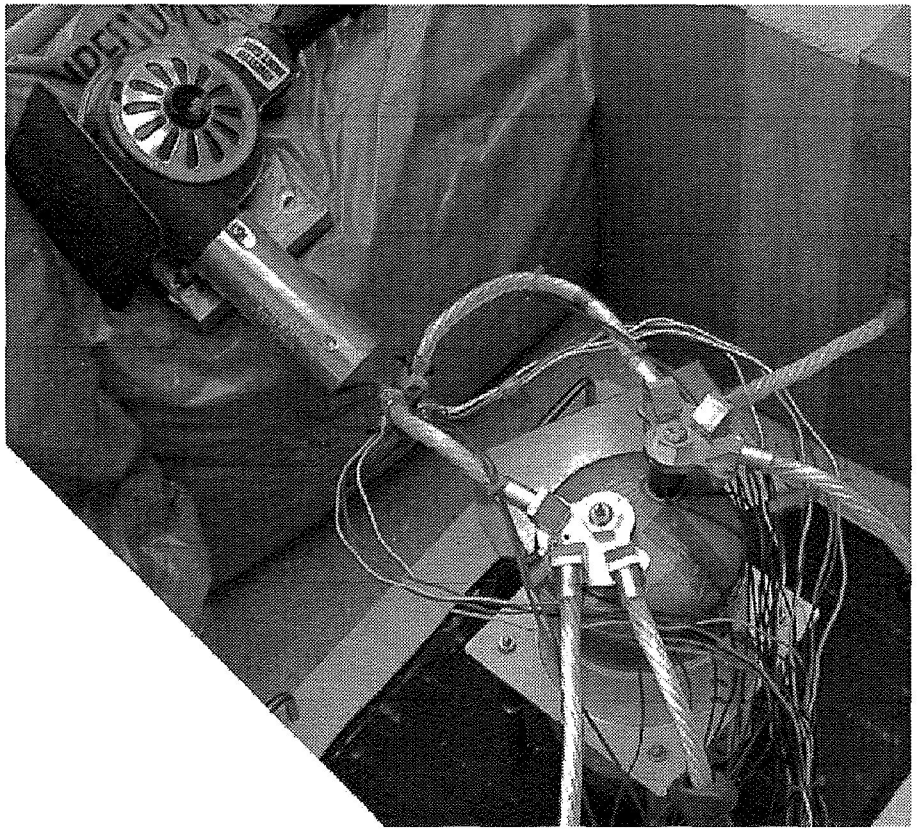

Heatgun repositioned for second application

Test #1 Scope Traces

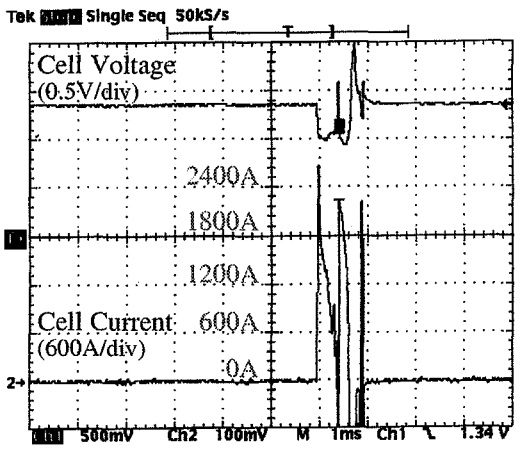

Time (1ms/div)

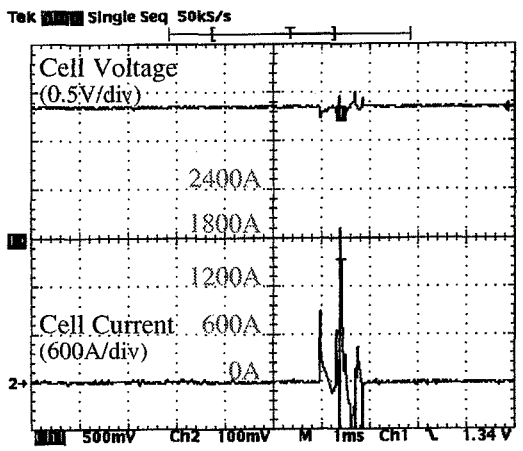

Time (1ms/div)

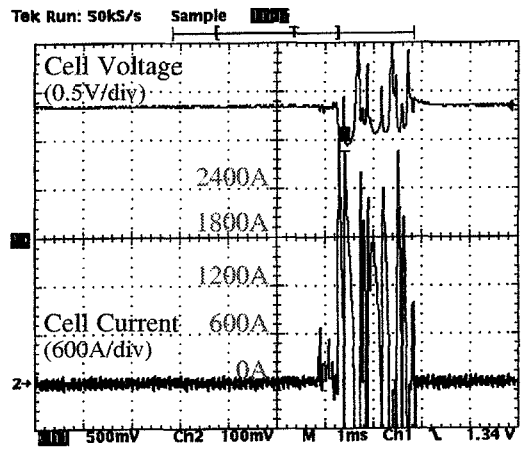

Time (1ms/div)

Test #1 Data

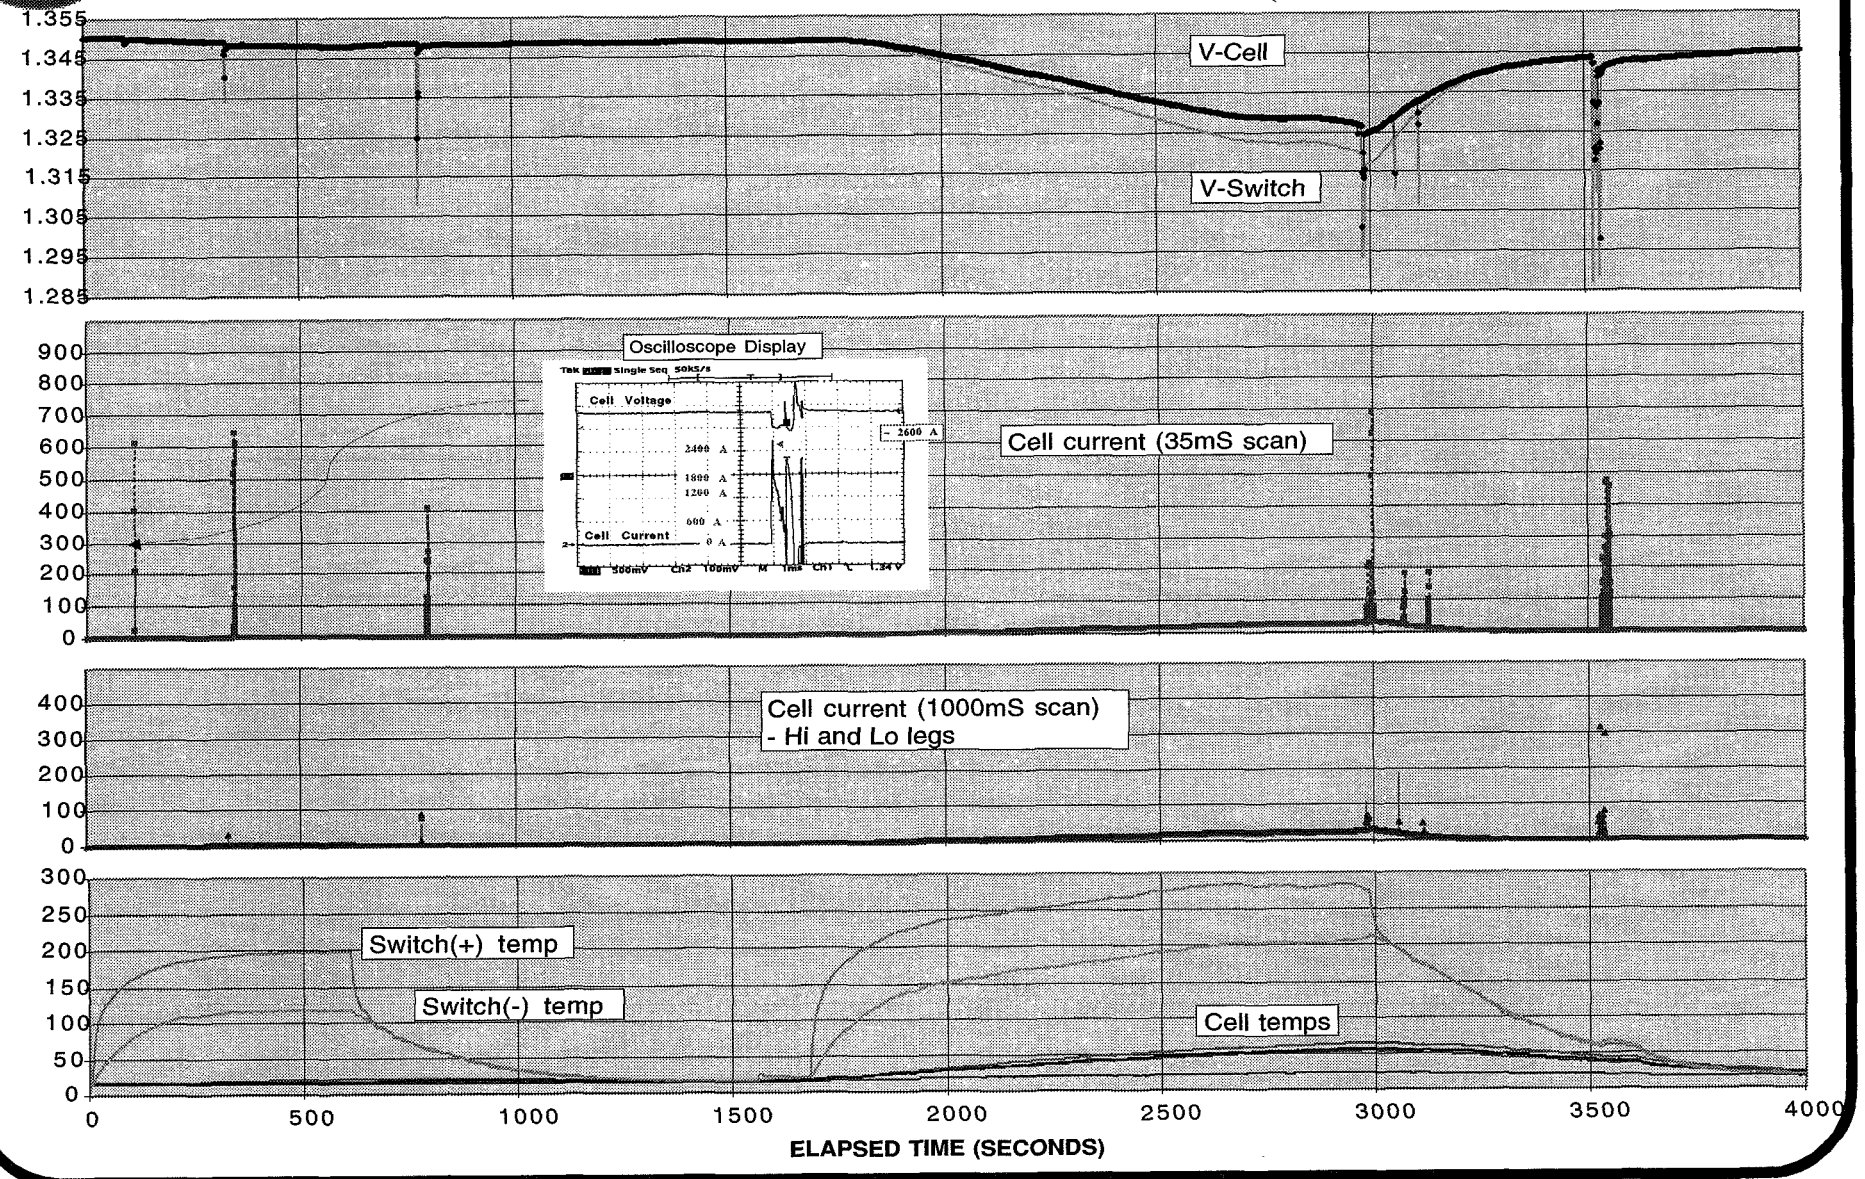
V-Cell
V-Switch
Oscilloscope Display
Cell Voltage
Cell Current
Cell current (35mS scan)
Cell current (1000mS scan)
- Hi and Lo legs
Switch(+) temp
Switch(-) temp
Cell temps
ELAPSED TIME (SECONDS)

Test #2 thru 5 setup (switch activated through diodes)

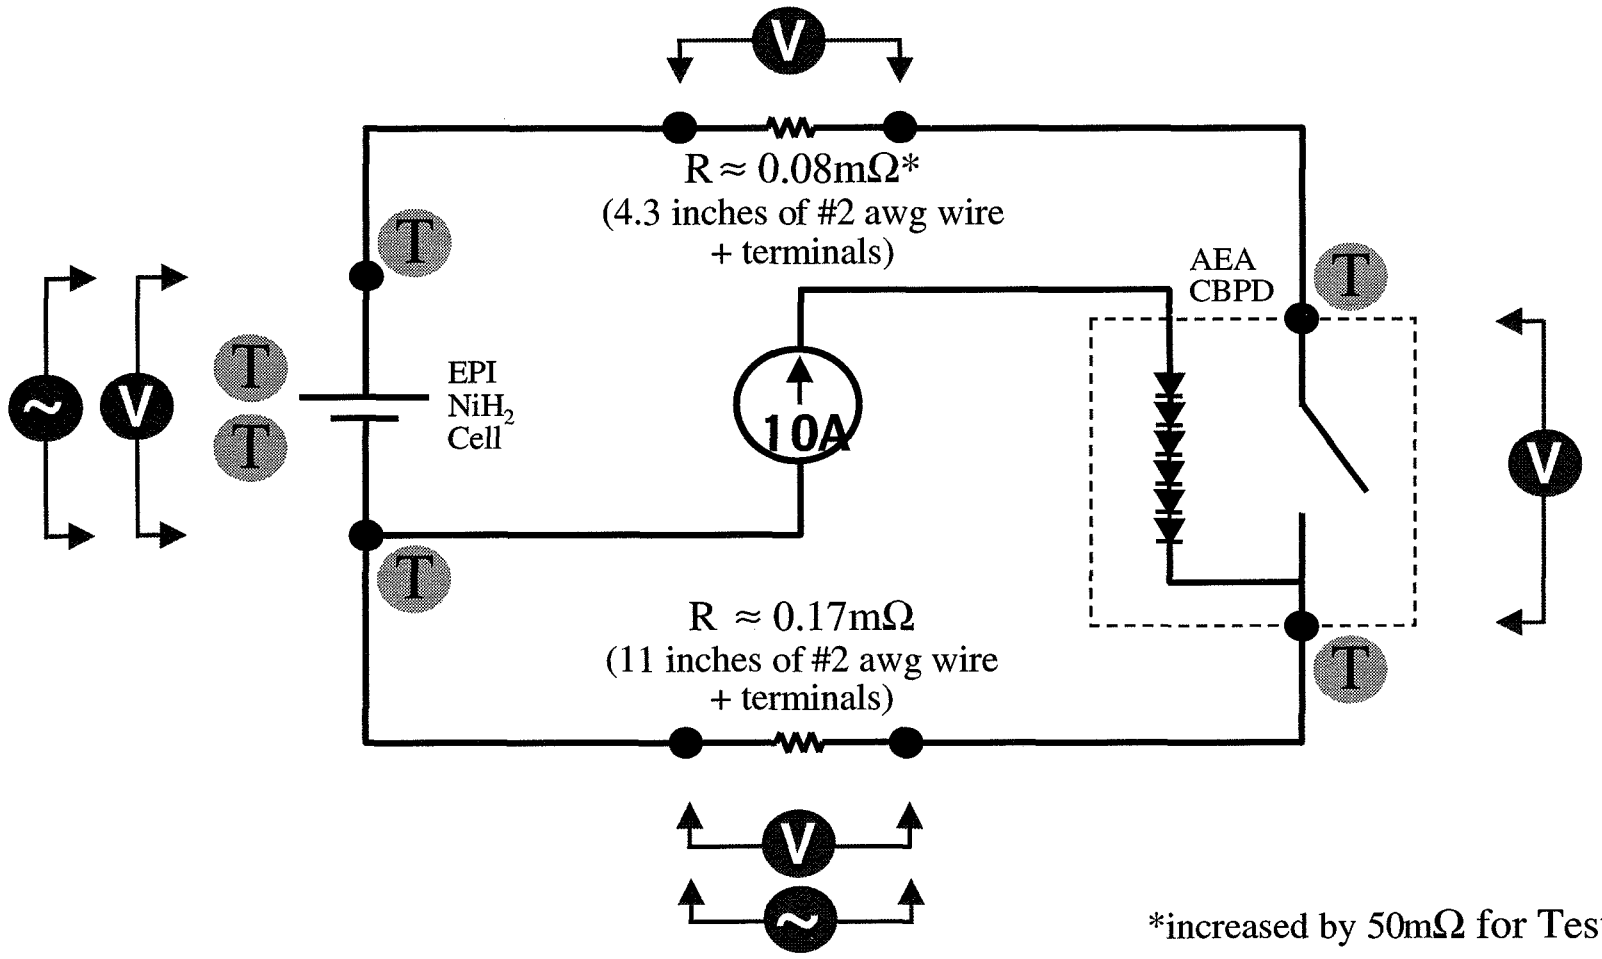

*increased by 50mΩ for Test #5

Test #2

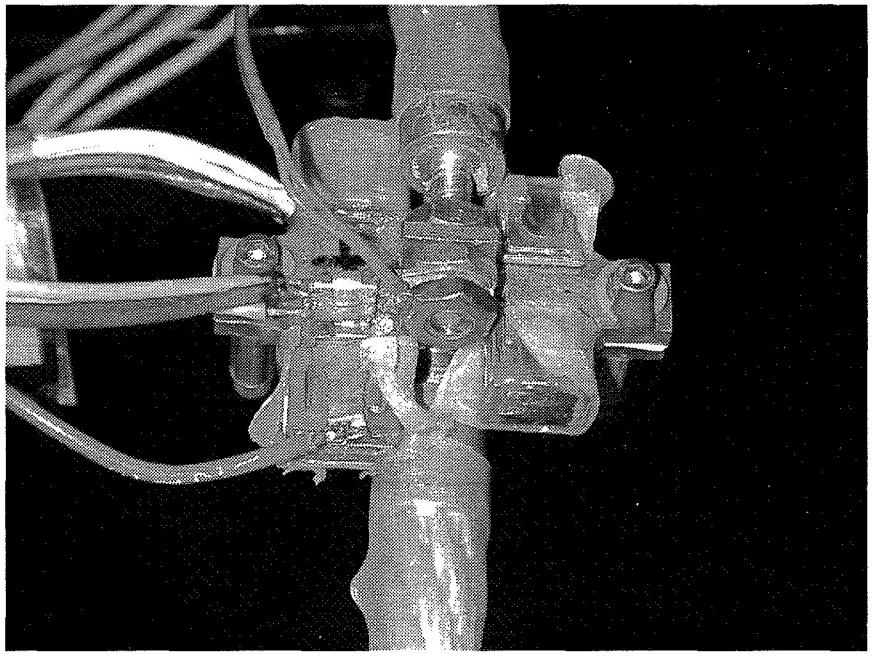

Engineering Model CBPD after test

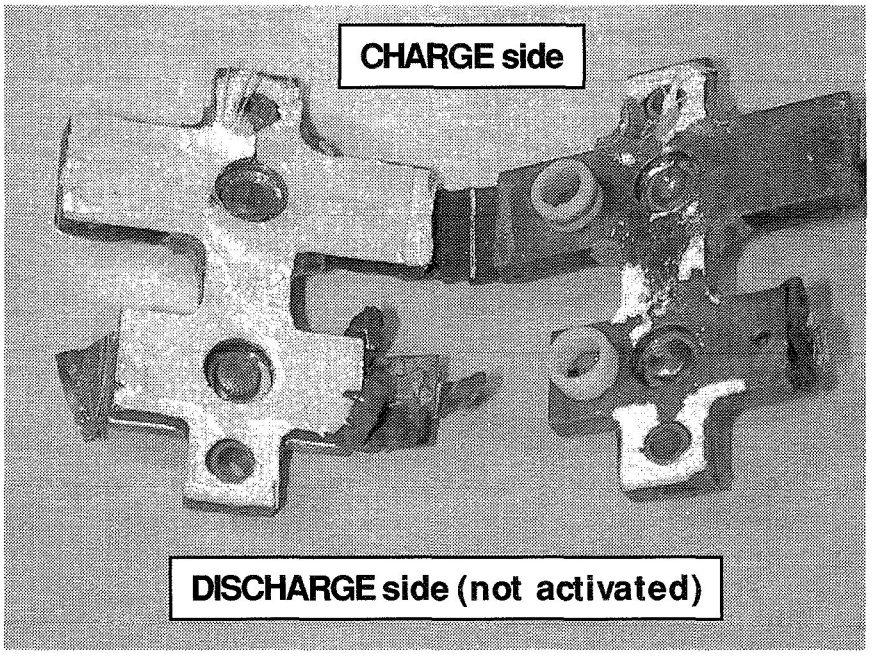

CBPD opened after test.

Test #2 & 3 Scope Traces

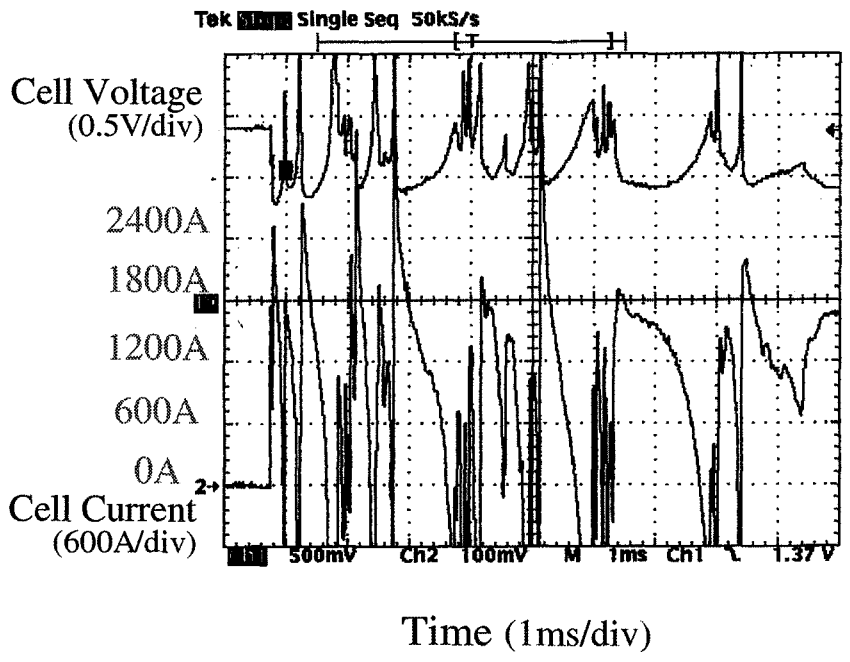

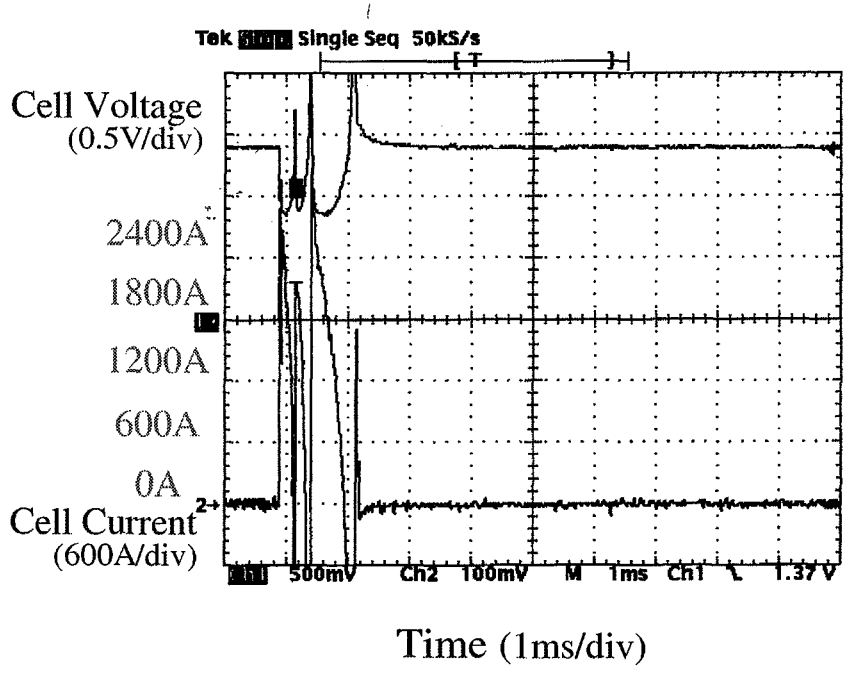

Test #4

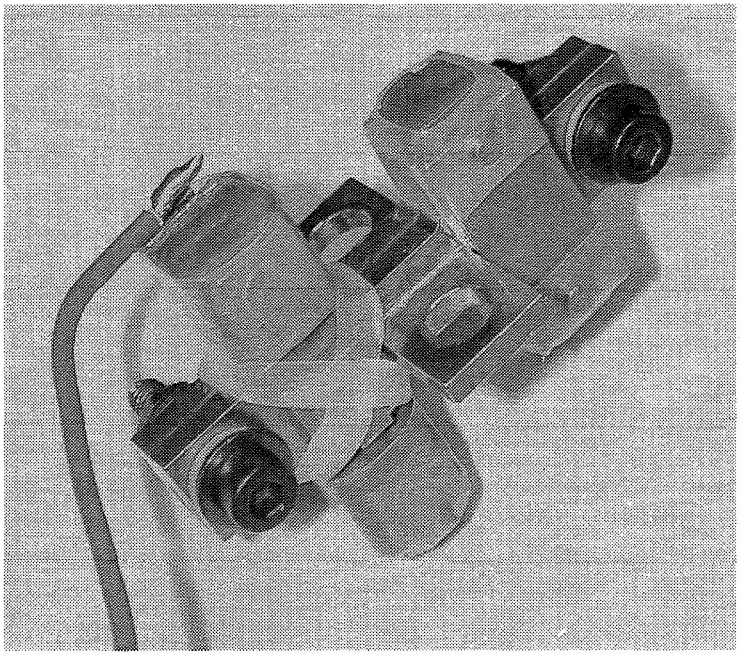

Charge diode string connection

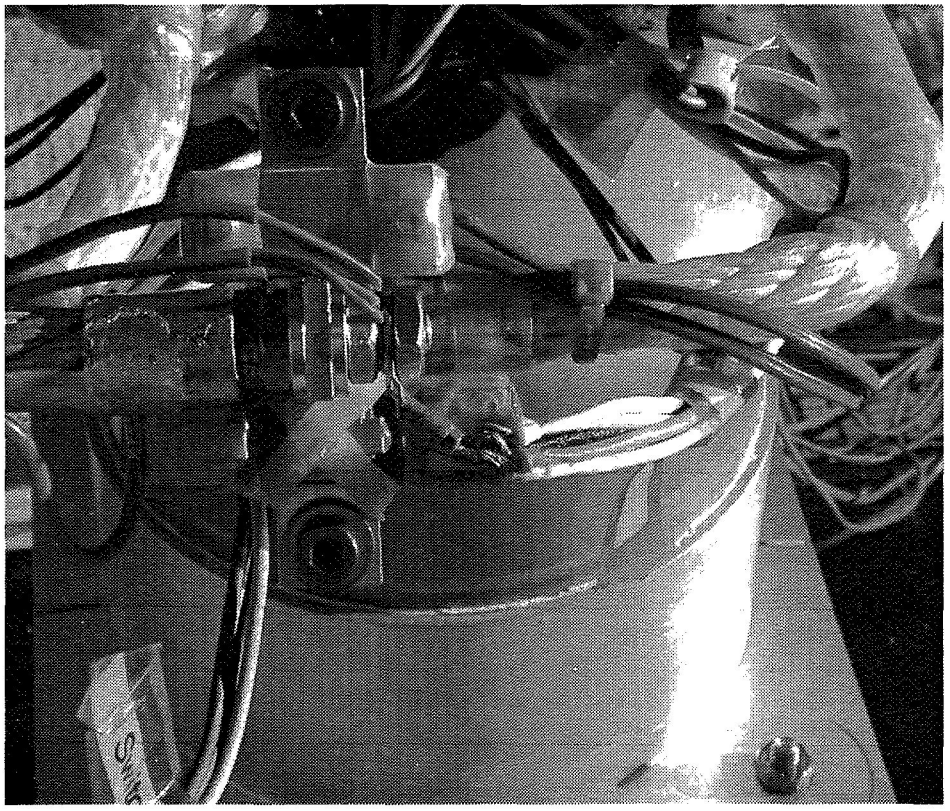

CBPD in launch orientation.

Test #4 Scope Trace

Cell Voltage
(0.5V/div)

Cell Current
(600A/div)

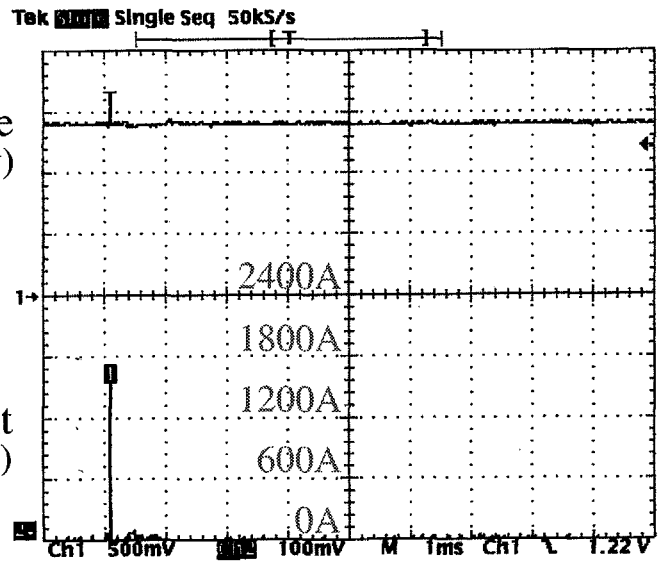

Time (1ms/div)

Test #4 Data

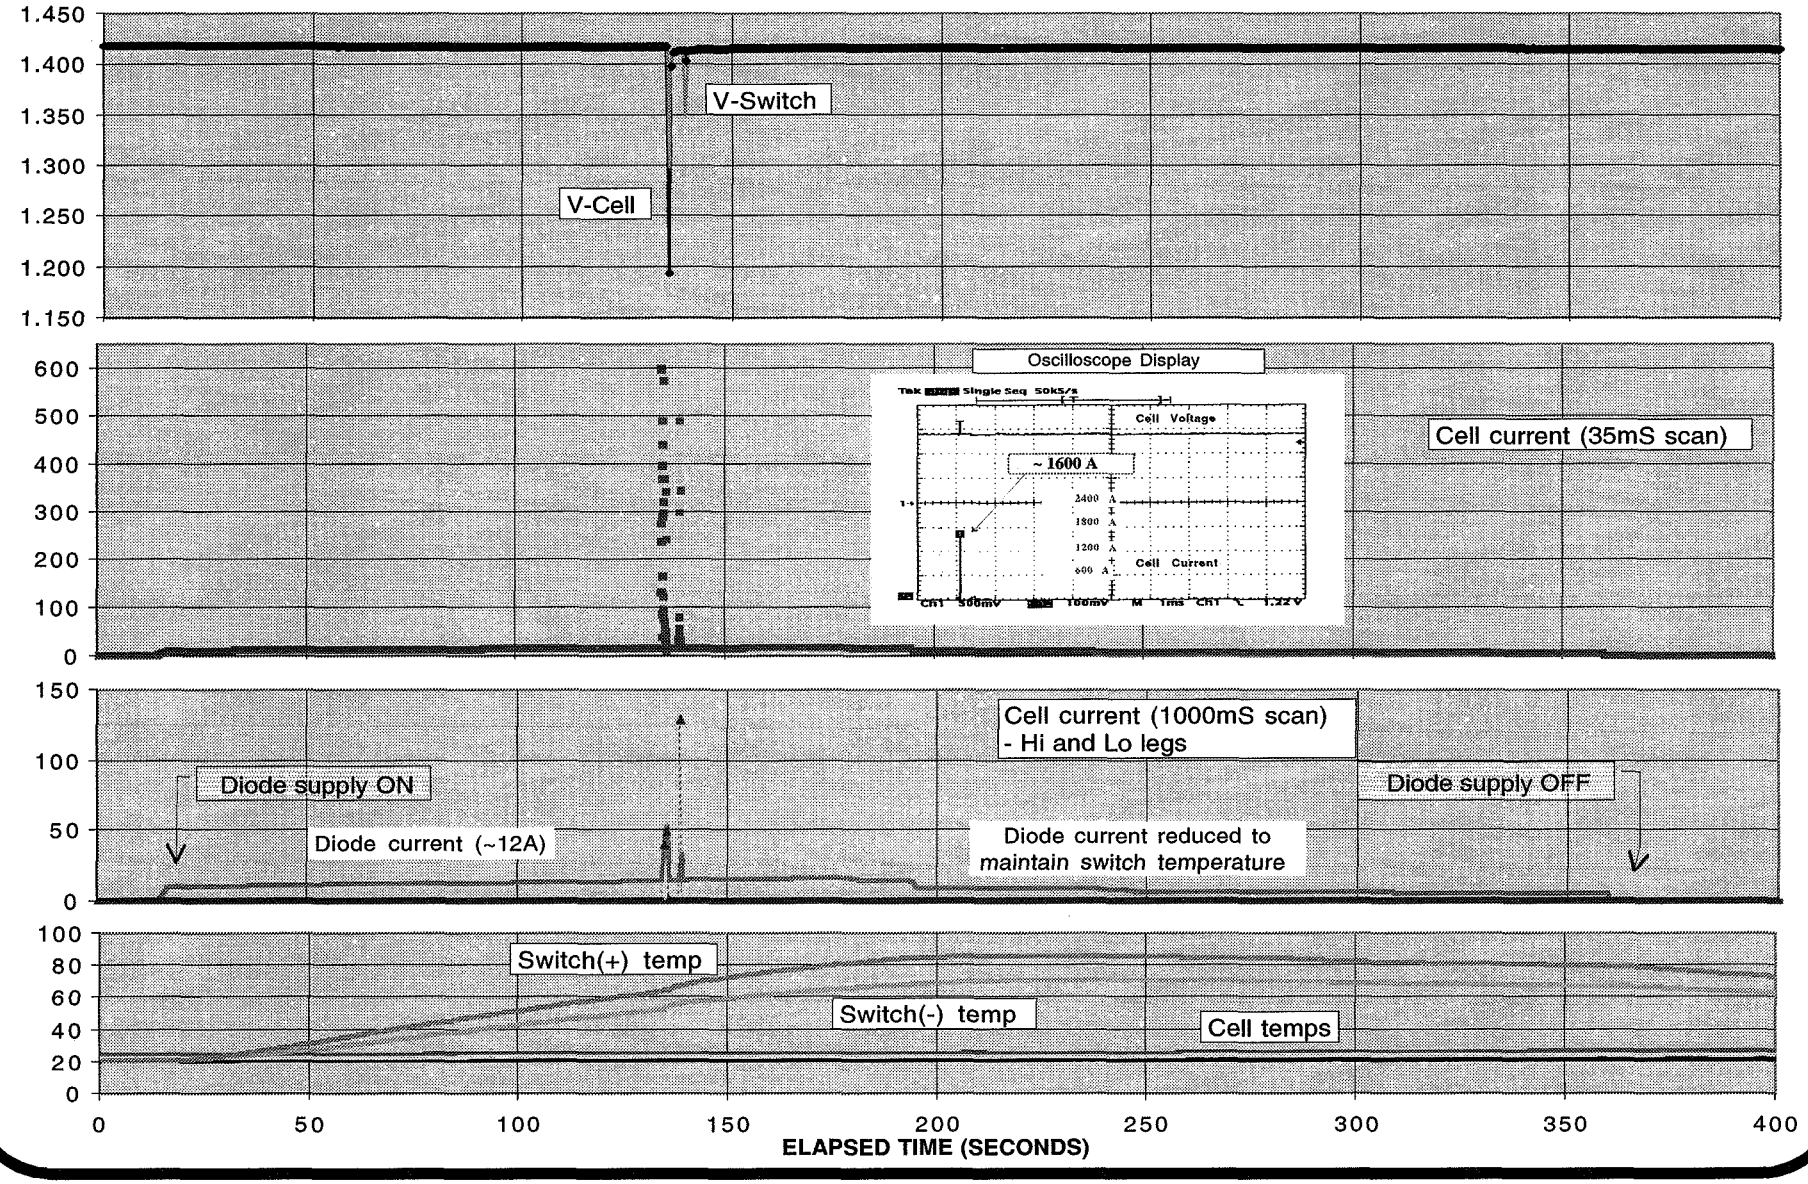
1.450
1.400
1.350
1.300
1.250
1.200
1.150
V-Switch
V-Cell
600
500
400
300
200
100
0
Oscilloscope Display
Cell Voltage
~ 1600 A
Cell Current
Cell current (35mS scan)
150
100
50
0
Cell current (1000mS scan)
- Hi and Lo legs
Diode supply ON
Diode current (~12A)
Diode current reduced to
maintain switch temperature
Diode supply OFF
100
80
60
40
20
0
Switch(+) temp
Switch(-) temp
Cell temps
0
50
100
150
200
250
300
350
400
ELAPSED TIME (SECONDS)

Test #5

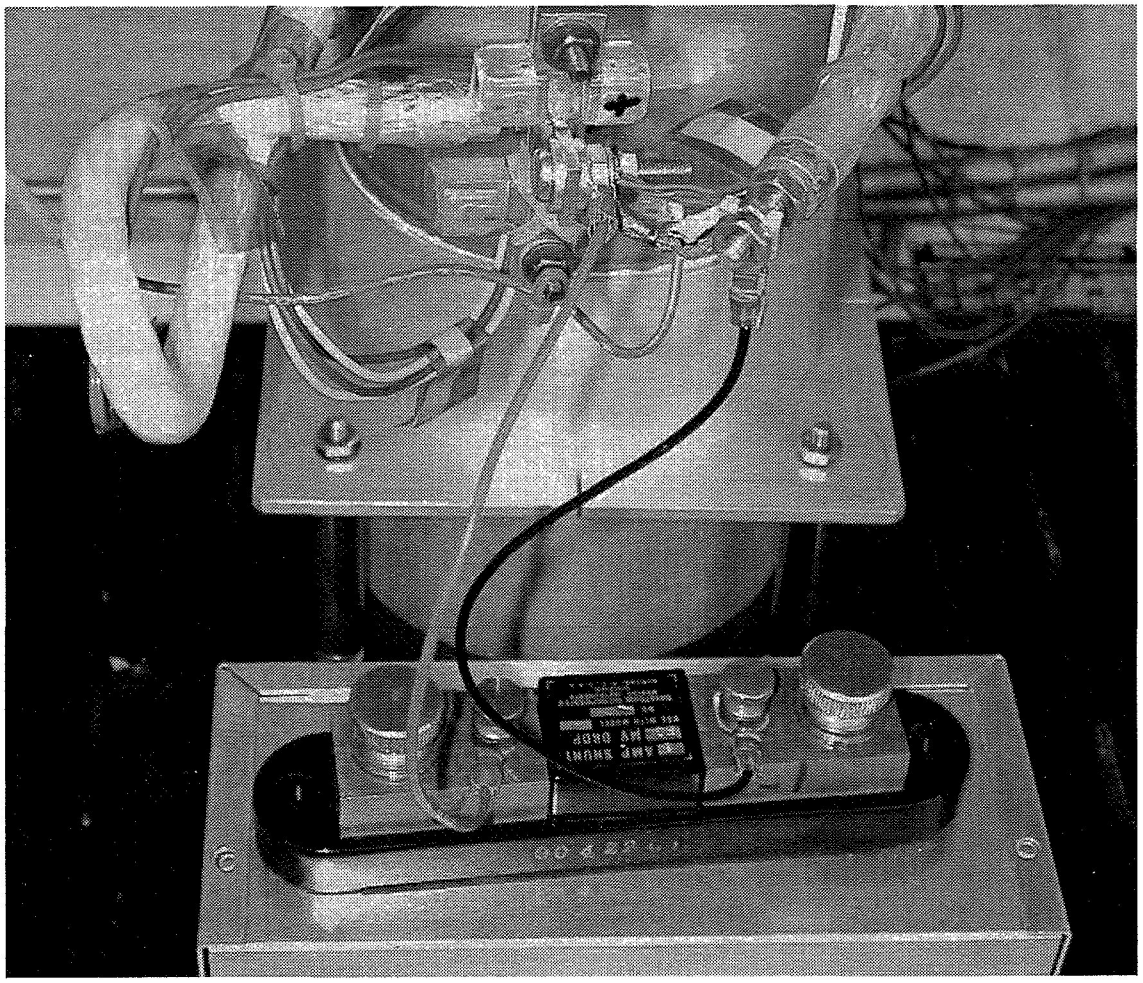

50 mΩ resistance added to positive current path

Test #5 Data (with added 50mΩ)

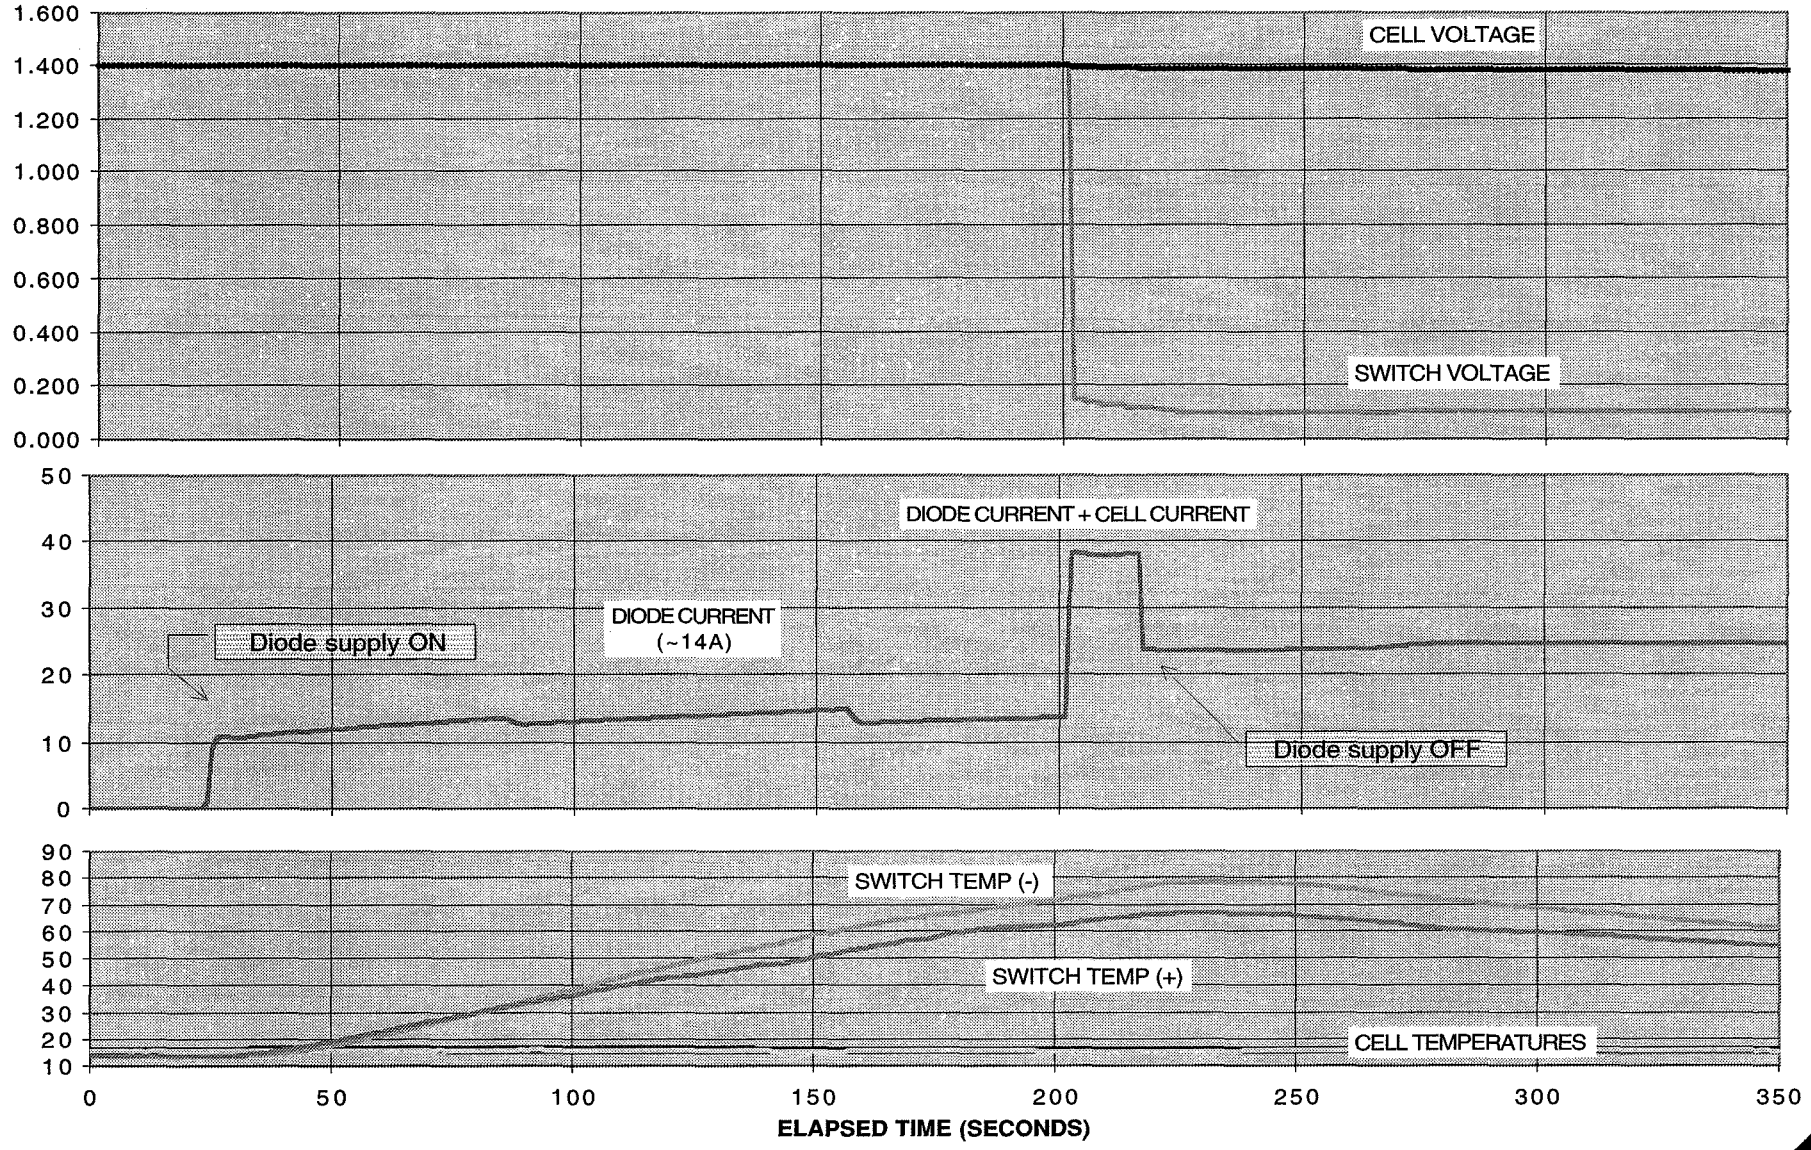

Scope traces for Tests #1 thru 4

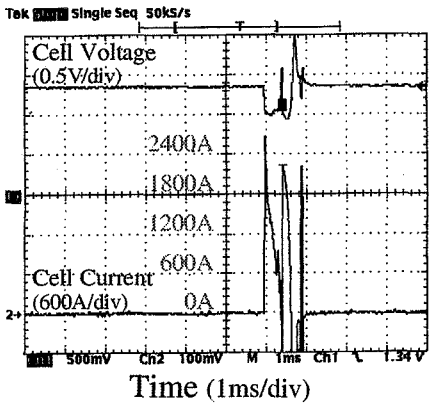

Test #1 (F01)

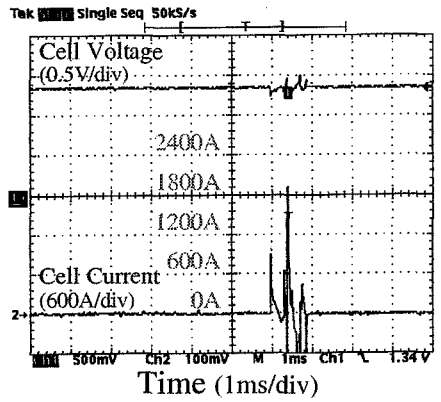

Test #1 (F01)

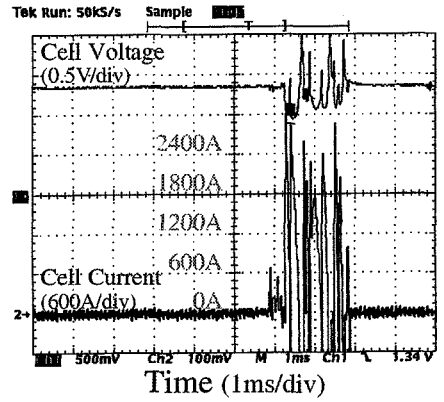

Test #1 (F01)

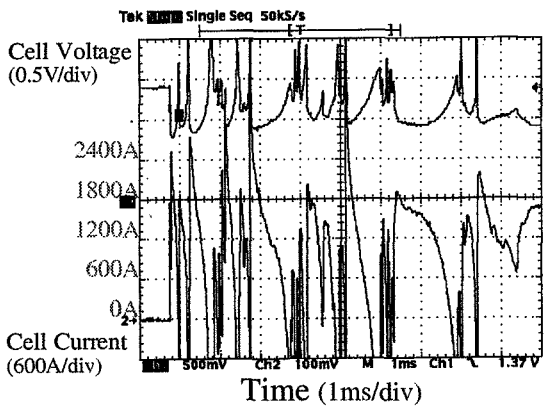

Test #2 (EM01)

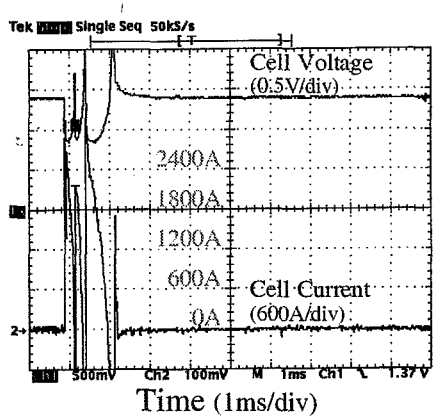

Test #3 (EM02)

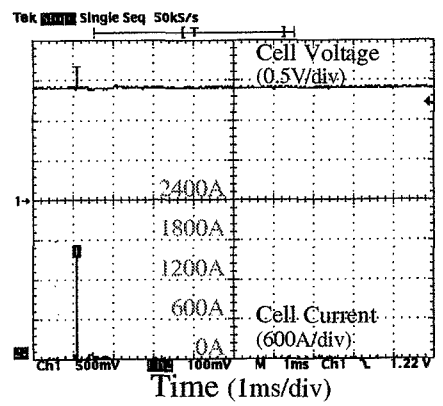

Test #4 (F02)

Test Summary

Test #	CBPD #	Result
1	F01	- Seven distinct current bursts were recorded - Switch failed to provide continuous short even after heating to near 300°C - It is expected that both charge and discharge switches were activated by the high temperature
2	EM01	- One distinct current burst was recorded - Switch failed to provide continuous short
3	EM02	- One distinct current burst was recorded - Switch failed to provide continuous short
4	F02	- One distinct current burst was recorded - Switch temperature was maintained over three minutes past the event, and switch still failed to provide continuous short
5	F03	- With 50 milliohms added to the current path, switch closed as expected, and maintained low impedance after diode current was removed and switch cooled

Conclusions

- The nominal performance of AEA CBPD under simulated EOS-Aqua/Aura flight hardware configuration has been demonstrated.
- There is no evidence of cell rupture or excessive heat production during or after CBPD switch activation under simulated high cell impedance (open-circuit cell failure mode).
- Inadvertent CBPD switch activation with a charged cell (low impedance path) intermittently closes and opens up the switch, therefore the device may or may not provide protection against future open-circuit cell failure.
  Further testing with switches F01 and F02 may provide clarification.
- The formation of a continuous low impedance path (a homogeneous low melting point alloy), has been confirmed - which is the expected mode of operation.

Further Work

- DPA of F03 (the only device to operate and carry continuous current) is in progress to confirm the formation of a stable, low impedance path
- Retest of F01 and F02 using added 50mΩ resistance is planned, with DPAs to follow

Acknowledgements

- Mr. G. Morrow, GSFC, Aqua Project Support
- Dr. R Tobias, TRW, Hardware and Technical Advice
- Mr. B. Beaman, GSFC, Technical Assistance
- Mr. T. Rozanski, GSFC, Technical Assistance
- Mr. R. Stickle, GSFC, Technical Assistance
- Mr. H. Stintz, GSFC, Technical Support
- Mr. A. Teverovsky, GSFC, Technical Support
- Mr. D. Wise, GSFC, Technical Support

SAFT

High Specific Energy NiH_2 Batteries for GEO Satellites

Y. Borthomieu*, M.Fabre**

* Defense and Space Division SAFT POITIERS

** Alcatel Space Industries CANNES

54/CP/IN/44

2001117715

24pr

537915

AGENDA

- Qualification Status
- Cell modifications
- Battery changes
- Conclusions

SAFT

Qualification Status

- Development started in 91
- Based on VHS design
- Qualification acquired in November 93
  - 3.5 inches cells
  - 12 to 32 cells per battery
  - 50 to 104 Ah
  - Adaptation to AN cells in 95

SAFT

Qualification Status

Battery concept :

- Cell equipped with tubular aluminum sleeve
- Aluminum base-plate with alveolus
- From 12 to 32 cells
- Individual by-pass system
- Two redundant heater circuits
- Cells equipped with strain gages
- Thermistor and connectors
- Aluminum or Copper wiring

SAFT

NiH_2 Battery for GEO

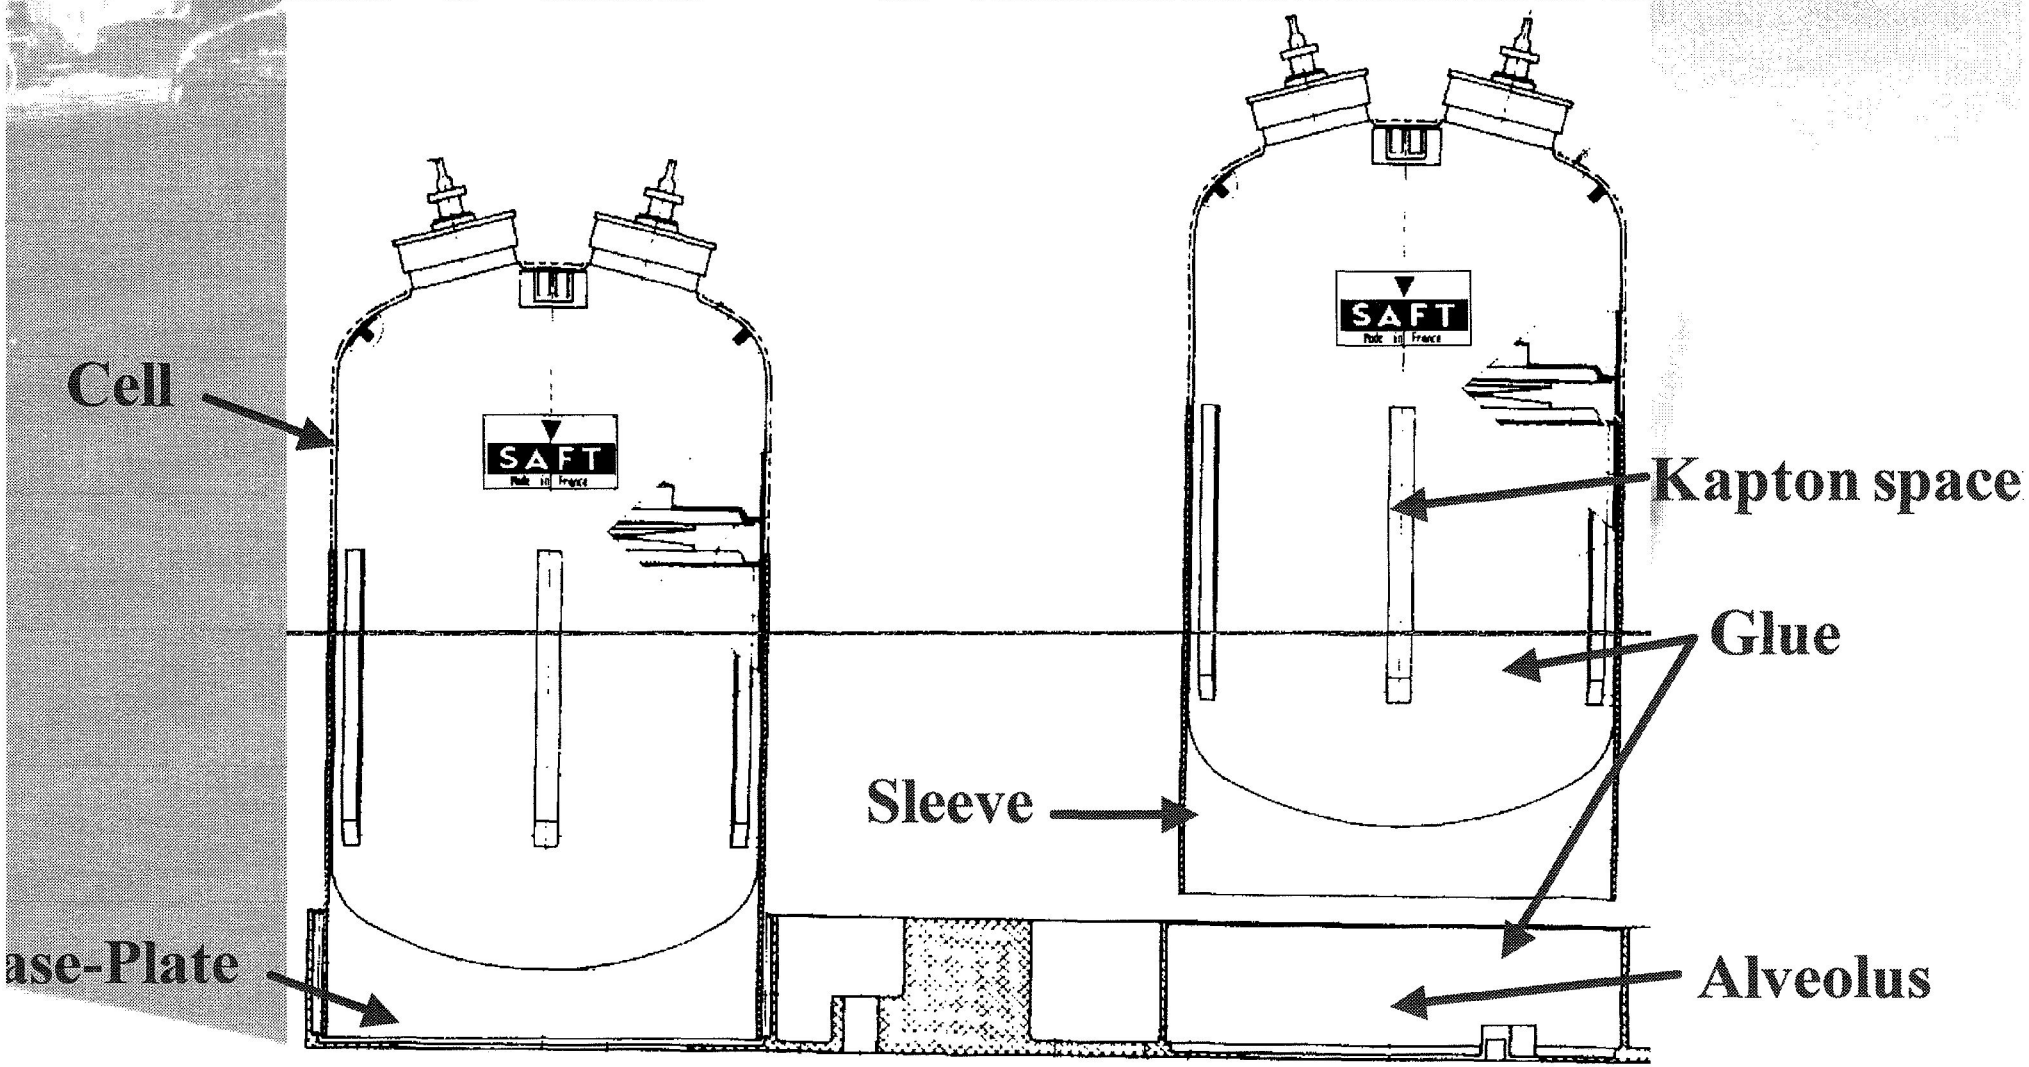

Main characteristics

- Specific energy : 48 Wh/kg for 27 cells of 63 Ah
- Weight ratio cell/battery : 82 %
- Volume : 61*44*21 cm3 (2.4*1.7*0.82 inch3) for 27 cells battery
- DOD max : 80 % with one failed cell
- Thermal gradient (in failed case conditions) :
  - → Maximum Internal cell : 2.5 °C
  - → Maximum Between 2 cells : 9 °C
- Vibration : qualification up to 20 G both sine and random

PROGRAMS

Satellite	Battery Type	Nb Battery per Satellite	Status
ARABSAT 2A	27*50 VHS	4+1 QM	Launched
ARABSAT 2B	27*50 VHS	4	Launched
ARTEMIS	23*60 VHS	2+1QM	Delivered
INDOSTAR (CAKRAWARTA)	22*52AN	2+2 IM	Launched
SINOSAT	27*56AN	4	Launched
SIRIUS 2 A	27*63AN	4 including 1 PFM	Launched
SIRIUS 2 B	27*63AN	4	Launched on EutelsatW4
ARABSAT 3A FM1	27*71AN	4 including 1 PFM	Launched
ATLANTIC BIRD 2	27*71AN	4	in manufacturing
HISPASAT1C	27*63AN	4	Launched
EURASIASAT	27*93AN	4 including 1 PFM	Delivered
ATLANTIC BIRD 1	23*97AN	2	In manufacturing
HOT BIRD 6	27*101AN	4 including 1PFM	In Design
STELLAT	27*93AN	4	In Design
GE12	27*89AN	4	In Design

32 Batteries in operation

SAFT

NiH_2 Battery for GEO

- **To Improve specific energy at battery level :**
  - Increase cell specific energy
  - Optimize battery mounting

SAFT

NiH_2 Cell

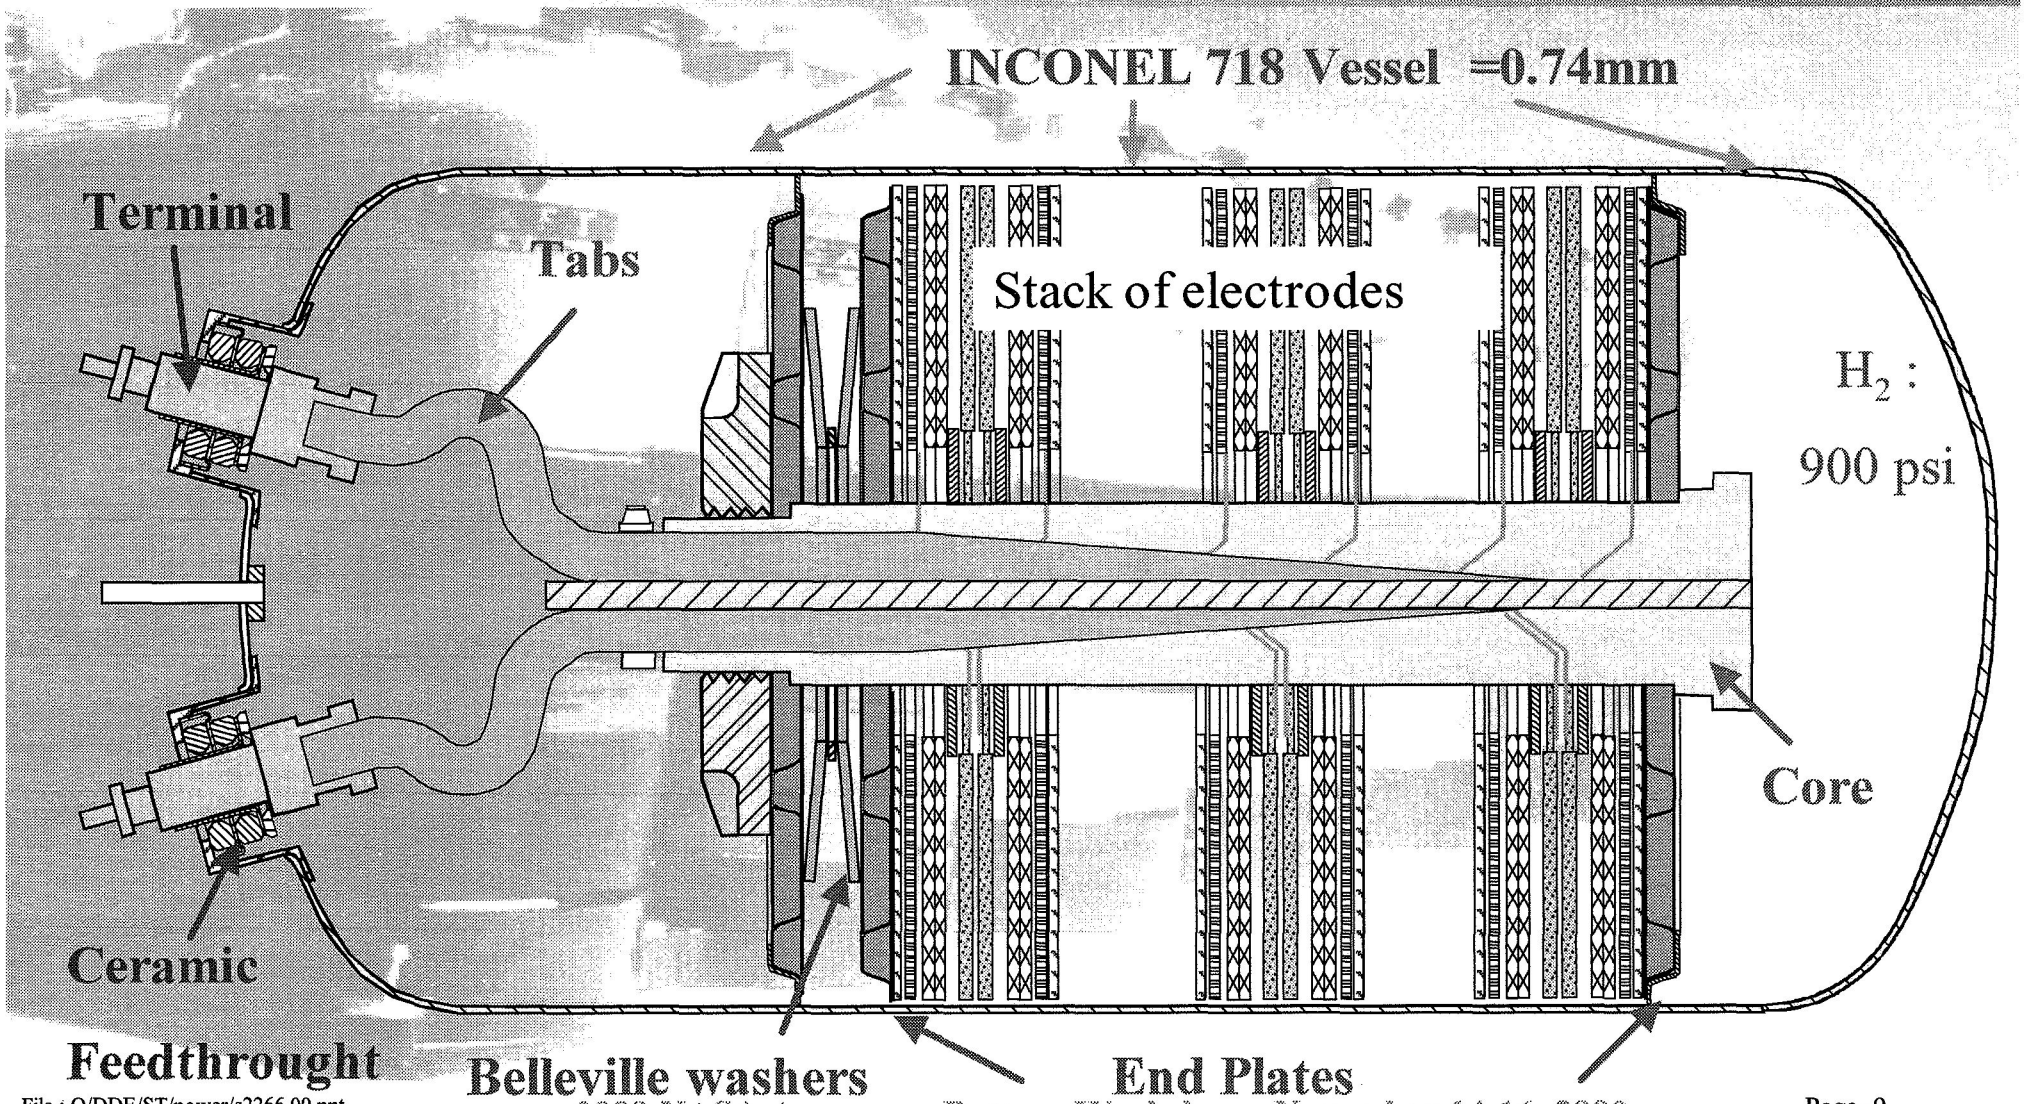

SAFT

NiH_2 Cell change 1

- Reduction bottom dome length

900 PSI
k=3.2

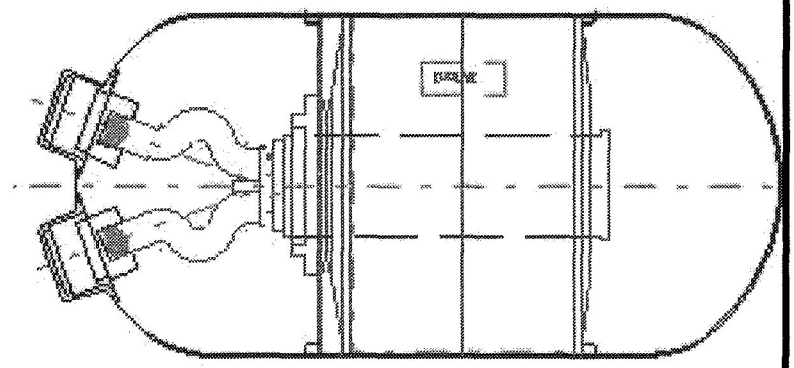

1000 PSI
k=2.8

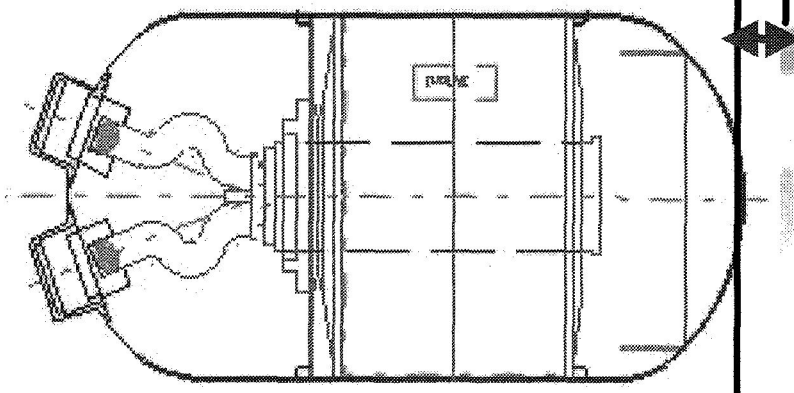

Already use on 4.5

SAFT

NiH_2 Cell change 1

- Impact of bottom dome length reduction:

  - At cell level for AN 101 :
    - 2.5 % Weight reduction over 2 294 g

  - At battery level for 9 kW satellite with 4 packs of 27AN101 :
    - 2.2 % Weight reduction over 291.6 kg

SAFT

NiH_2 Cell change 2

- Transfert from top dome cyclindrical part to bottom dome

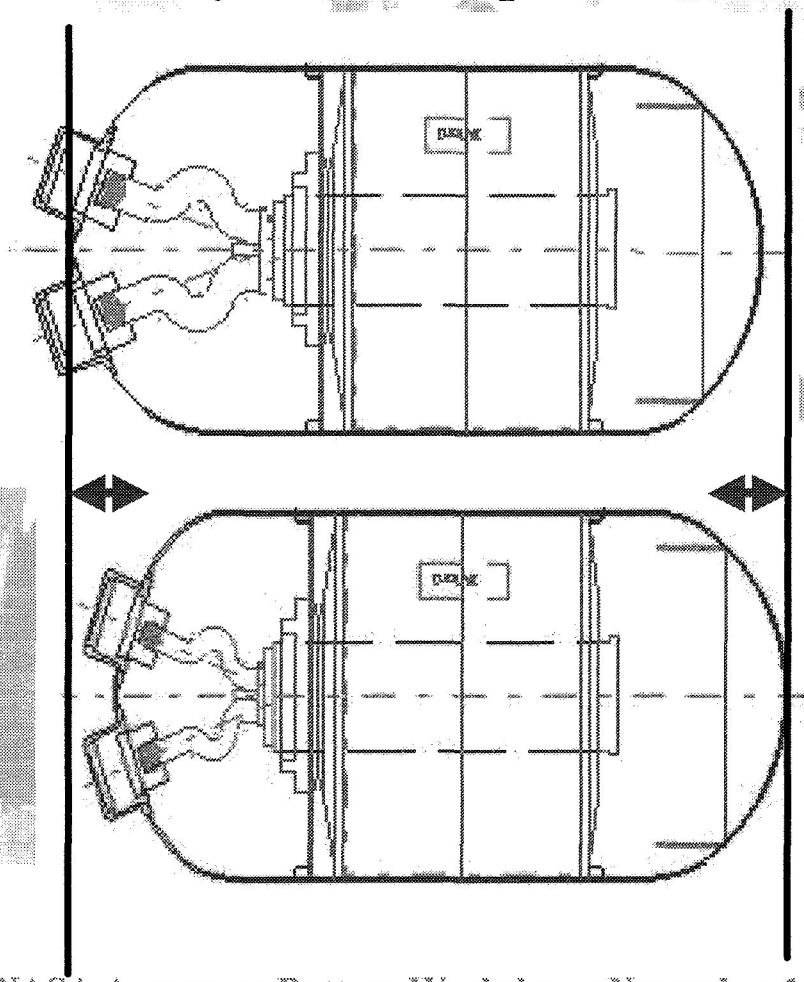

Reduction of tabs length

SAFT

NiH_2 Cell change 2

- Impact of transfering top dome cyclindrical part to bottom dome

  - At cell level for AN 101 :
    - 5.8 % Weight reduction over 2 236 g

  - At battery level for 9 kW satellite with 4 packs of 27AN101 :
    - 4 % Weight reduction over 285 kg

SAFT

NiH_2 Cell change 3

- Decrease of width and/or thickness of tabs

  - Tabs were oversized considering current
    - Criteria : voltage drop less than 45 mV at C rate

  - At cell level for AN 101 :
    - 2 % Weight reduction over 2 105 g

  - At battery level for 9 kW satellite with 4 packs of 27AN101 :
    - 1.7 % Weight reduction over 274 kg

SAFT

NiH_2 Cell changes

- Change 1 and 2 have been used for Eurasiasat batteries
  - Life test performed to validate the change
    - 4 cells tested
    - Semi-accelerated conditions :
      - charge C/10 k=1.15 + Trickle charge C/100
      - discharge C/1.5, 72 min, 80 % DOD
      - 2 cycles per day
      - no solstice
- Change 3 is using on current programs
  - Life test will be performed on HB6

SAFT

Eurasiasat life test

Average End of discharge voltage

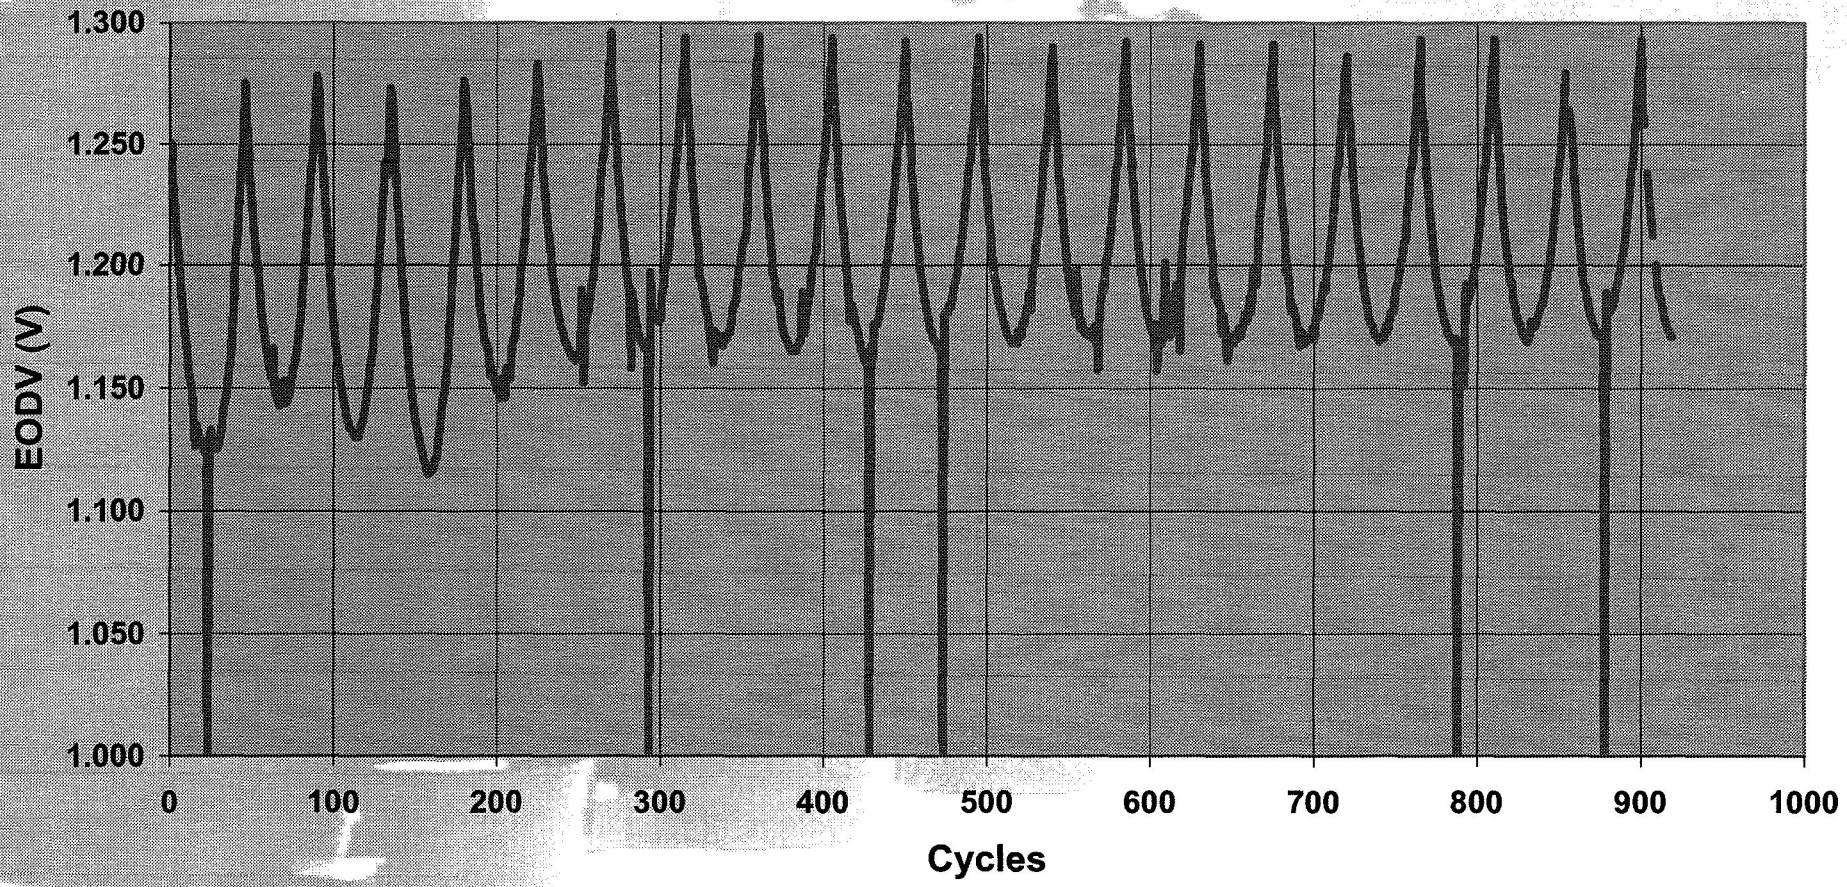

SAFT

Battery change 1

- Use of the Aluminum wiring instead of Copper
  - Qualification acquired in 96
  - Use of the ESA rules forderating
  - Weight saving at battery level for 9 kW :
    - 2.2 % over 280 kg

SAFT

Battery change 2

- Charge management modification :
  - Decrease of the charge temperature from 0 °C to -10 °C
    - Increase of the delivered capacity
  - Weight saving at battery level for 9 kW :
    - 3 % over 274 kg
  - Is planned to be used on Hot Bird 6

SAFT

Battery Performances

- By performing ASPI test :
  - One orbital cycle 80 % DOD
  - Recharge k=1.15 and discharge C/1.5 down to 1 V

FIRST DESIGN WITH ALUMINUM WIRING

	C Ah	T °C	Weight (kg)	Sp En (Wh/kg)
Sirius II : AN63	65.2	0 °C	186	47.3
Arabsat 3 : AN71	72	0 °C	204	47.6

SAFT

Battery Performances : Arabsat 3 A

SAFT

Battery Performances : Arabsat 3 A

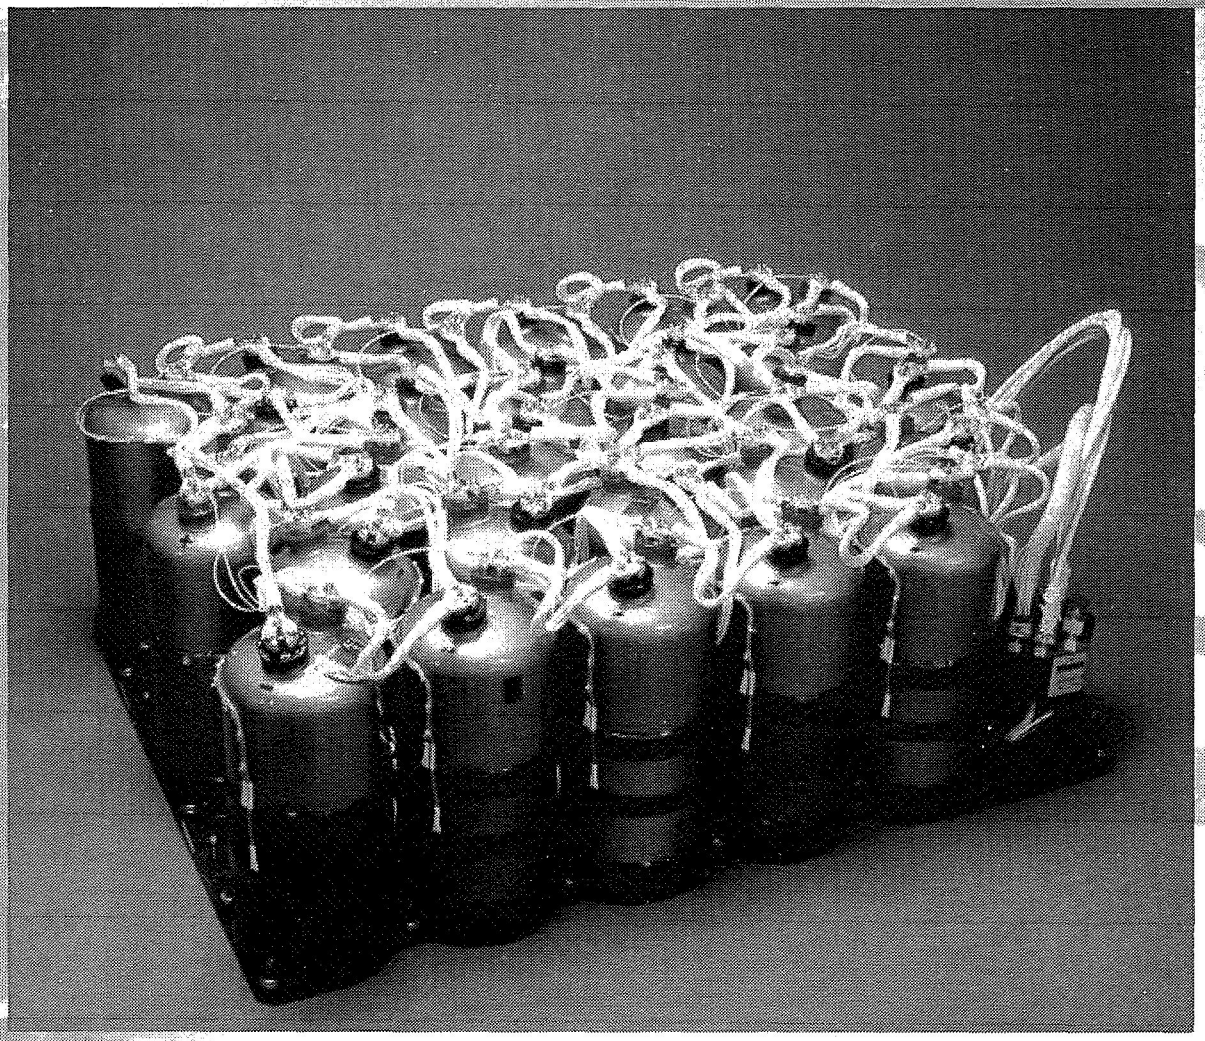

SAFT

Battery Performances

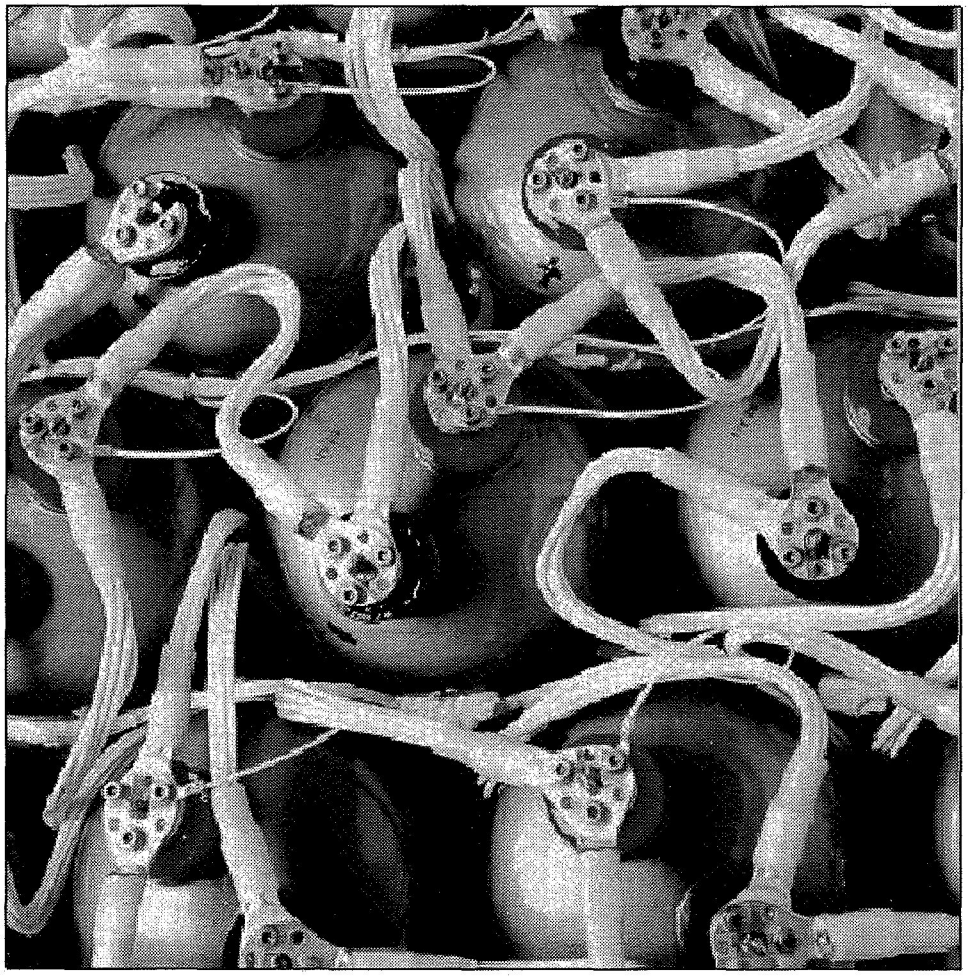

SAFT

Battery Performances

DESIGN WITH CHANGES 1 and 2 AT CELL LEVEL

(MOP and Upper Stack)

ALUMINUM WIRING

	C Ah	T °C	Weight (kg)	Sp En (Wh/kg)
Eurasiasat : AN93	99	-2.5 °C	255	51

MORE THAN 8 % SPECIFIC ENERGY INCREASE

SAFT

CONCLUSION

- First phase of improvement done on EURASIASAT (changes on MOP and upper stack)
  - weight gain over the prediction (8 % over 6 %)

- Second phase in validation on current programs, Hot Bird 6, (changes on tabs, charge management) will give 5 % weight gain more to reach

53 Wh/kg at battery level

CAPACITY MANAGEMENT AND WALKDOWN DURING LEO CYCLING OF NICKEL-HYDROGEN CELLS AND BATTERIES

By:

Lawrence H. Thaller, Albert H. Zimmerman,

and Gloria To

The Aerospace Corporation

El Segundo, CA

Presented at:

The 2000 NASA Aerospace Battery Workshop

Huntsville, Alabama

November 14-16, 2000

Electronics And Photonics Laboratory
Energy Technology Department

THE AEROSPACE CORPORATION

55/20 1N/44
2001117722
53788
24p

OUTLINE OF PRESENTATION

- CAPACITY WALKDOWN DEFINED AND ILLUSTRATED
- IMPORTANCE OF CAPACITY WALKDOWN
- FOUR APPROACHES TO UNDERSTANDING THE PHENOMENON
  - Pressure Trend Studies
  - Charging Curve Studies
  - Electrochemical Voltage Spectroscopy Studies
  - Destructive Physical Analysis Studies
- RESULTS OF THE INTERRELATED STUDIES
- SUGGESTED MECHANISM FOR CAPACITY WALKDOWN
- CHARGING PROTOCOLS TO AVOID THE PROBLEM
- SUMMARY STATEMENTS

CAPACITY WALKDOWN

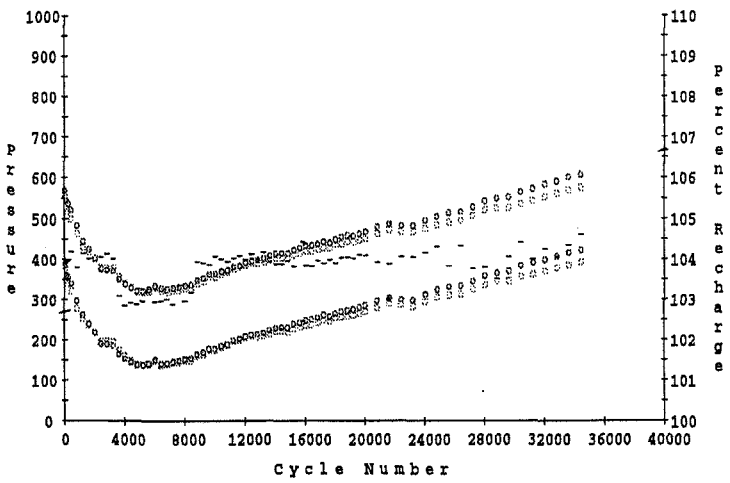

Characteristics

- Very Slow
- 2000 - 8000 Cycles
- Recoverable
- 30% to 40%Capacity Loss
- Monitored Using Strain Gauge

IMPORTANCE OF CAPACITY WALKDOWN

- RESULTS IN A SIGNIFICANT REDUCTION IN THE RESERVE CAPACITY FOLLOWING A NORMAL DISCHARGE
  - The Gradual Drop in State of Charge for a Fixed Depth of Discharge will Result in Less and Less Reserve Capacity Following a Discharge
- WHEN THE CHARGEING PROTOCOL IS BASED ON A FIXED RECHARGE RATIO ADJUSTMENTS ARE REQUIED AS CYCLING CONTINUES
  - Accuracy to the Nearest One Tenth of a Percent May be Needed

APPROACHES USED TO QUANTIFY AND UNDERSTAND CAPACITY WALKDOWN

- PRESSURE TRENDS DURING LEO CYCLING AT THE NAVY FACILITY AT CRANE INDANA
  - Air Force, NASA Glenn, and NASA Space Station Tests
- CHARGING CURVES OF SELECTED AIR FORCE AND NASA SPONSORED LEO TESTS
- ELECTROCHEMICAL VOLTAGE SPECTROSCOPY STUDIES OF SELECTED SAMPLES OF PLATE MATERIAL FROM A VARIETY OF SOURCES
- EXTENSIVE DESTRUCTIVE PHYSICAL ANALYSES ON SIMILAR CELLS
  - One Cycled Under Conditions With No Walkdown
  - One Cycled Under Conditions With Significant Amount of Walkdown

WALKDOWN AS A FUNCTION OF CYCLING CONDITIONS

- CELLS CYCLED AT 40% DOD AND -5°C DID NOT SHOW WALKDOWN
- CELLS CYCLED AT 40% DOD AND +10°C SHOWED VARIABLE AMOUNTS OF WALKDOWN
- CELLS CYCLED AT 60% DOD AND +10°C SHOWED NO WALKDOWN
- CELLS CYCLED AT 60% DOD AND -5°C SHOWED NO WALKDOWN BUT VERY SHORT CYCLE LIVES

CAPACITY LOSS AT 40% DOD AND +10°C

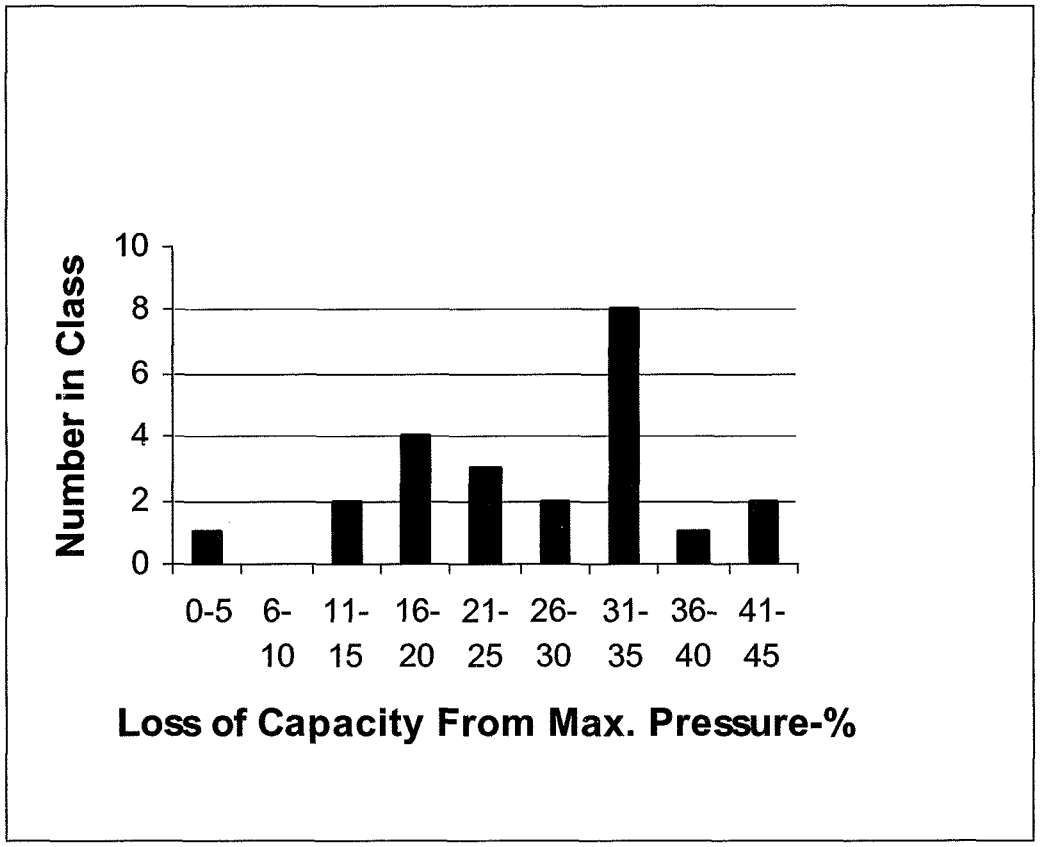

TYPICAL TEST SHOWING NO WALKDOWN

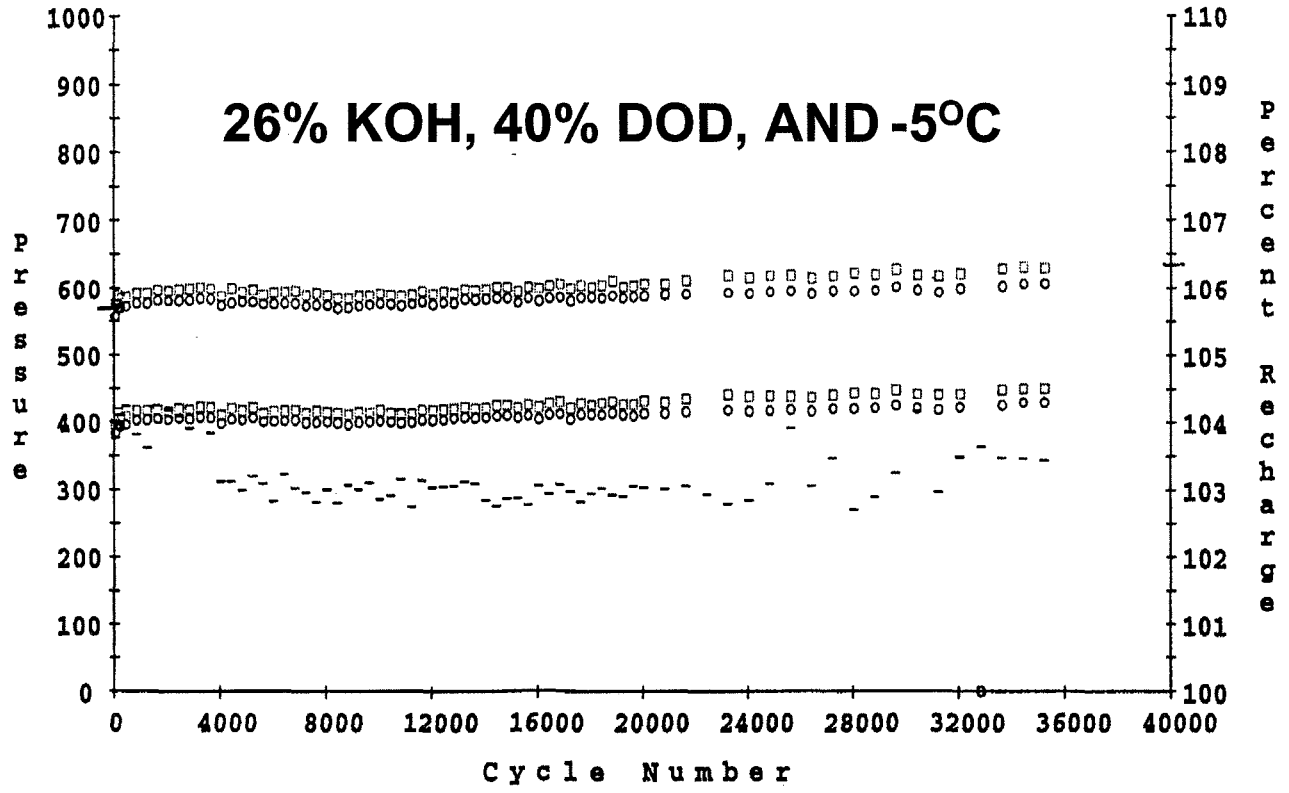

CHARGE CURVES FOR TWO CELLS: ONE AT +10°C AND ONE AT -5°C

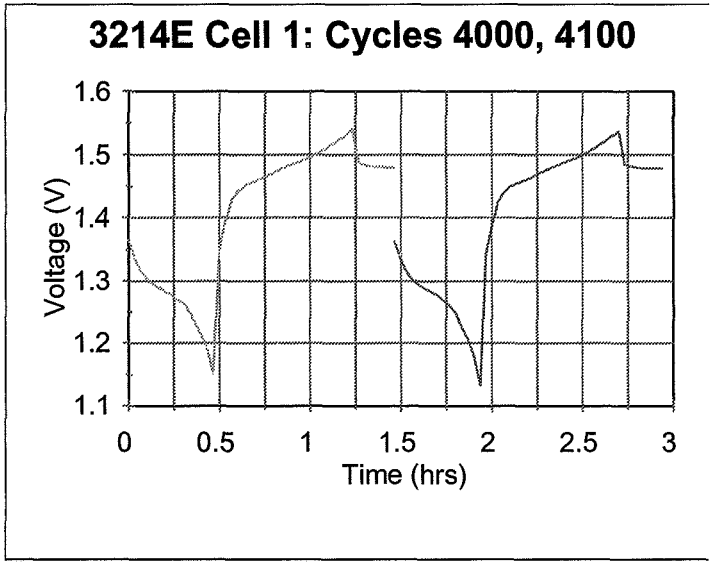

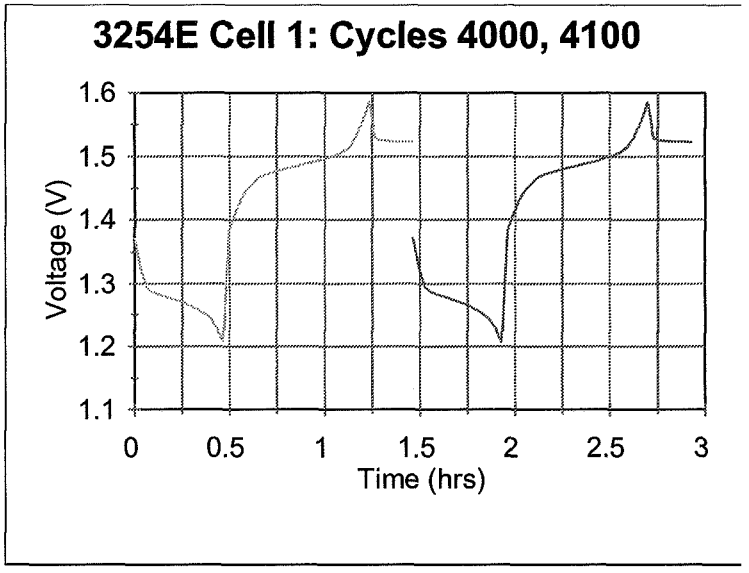

+10°C, 40% DOD, RR = 1.04

-5°C, 40% DOD, RR = 1.03

DIFFERENCES IN CHARGING CURVES

- CYCLE 4000 WAS NEAR THE MINIMUM OF PRESSURE FOLLOWING WALKDOWN FOR CELLS IN PACK 3214E
- CELL #1 IN PACK 3214E DOES NOT SHOW THE SHARP ROLLUP AT THE END OF THE CHARGING PROCESS
- CELL #1 IN PACK 3254E HAS A SHARP ROLLUP INDICATIVE OF LESS OXYGEN EVOLUTION
  - This Results in a Higher Charging Efficiency and Therefore a Higher State of Charge at the End of the Charging Process for the Cell Cycled at -5°C

ELECTROCHEMICAL VOLTAGE SPECTROSCOPY STUDIES

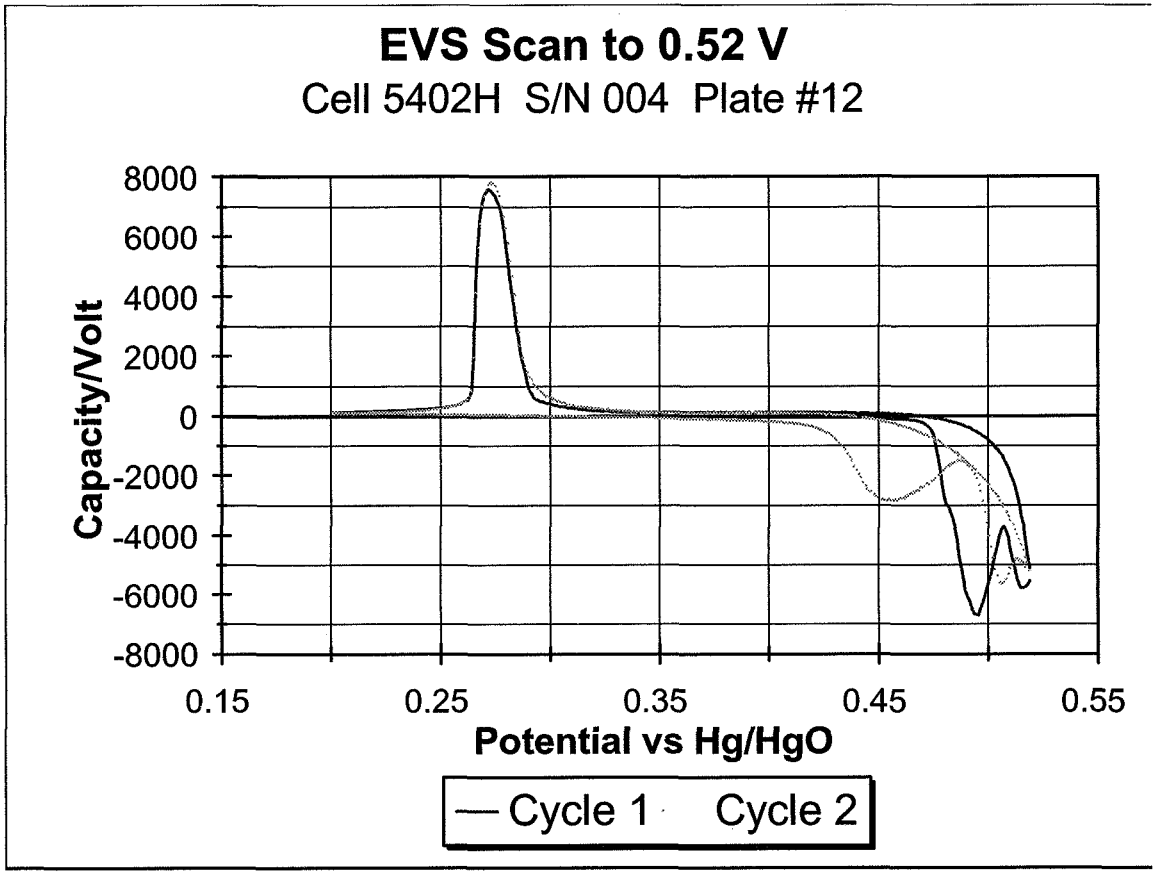

EVS REVEALED THE SOURCE OF THE WALKDOWN PHENOMENON

- THE BETA MATERIAL DURING THE FIRST CYCLE IS MORE DIFFICULT TO CHARGE BY 30 TO 40 MILLIVOLTS
- AFTER CHARGING TO THE GAMMA PHASE AND ONE FULL DISCHARGE, THE BETA MATERIAL IS REFERRED TO A BEING IN THE 'ACTIVE' FORM
- THE POSITION OF THE CHARGING PEAKS OF THE SECOND CYCLE IS INDICATIVE OF A DIFFERENT ACTIVE SPECIE
- IT HAS BEEN SUGGESTED THAT THEY ARE DIFFERENT CRYSTALINE FORMS OF BETA NICKEL HYDROXIDE
- WE HAVE NOT BEEN ABLE TO DESCERN ANY IDENTIFICABLE DIFFERENCES IN THE TWO DIFFERENT FORMS

RESULTS OF EVS SCANS TO DIFFERENT END OF CHARGE VOLTAGES

- MULTIPLE ~1.0 CM^2 SAMPLES SELECTED FROM THE SAME PLATE TAKEN FROM A GOOD CELL WITH ONLY 100 CYCLES
- TWO COMPLETE CHARGE DISCHARGE CYLES WERE USED AS PER THE PREVIOUS CHART
- THE END OF CHARGE VOLTAGE RANGED FROM 0.48 V vs. Hg/HgO REFERENCE ELECTRODE TO 0.54 V
- THE VOLTAGE PEAK FOR CHARGING THE BETA $Ni(OH)_2$ DURING THE SECOND CYCLE WAS RECORDED
- IT WAS FOUND THAT IF THE END OF CHARGE VOLTAGE WAS BELOW A CERTAIN VALUE, THE DISCHARGED FORM OF THE ACTIVE MATERIAL WAS NOT CONVERTED TO THE ACTIVE FORM
- FOR THIS ELECTRODE THE DIFFERENCE IN POTENTIAL OF THE TWO FORMS WAS 20 MILLIVOLTS

POSITION OF THE BETA PEAK DURING THE SECOND EVS SCAN

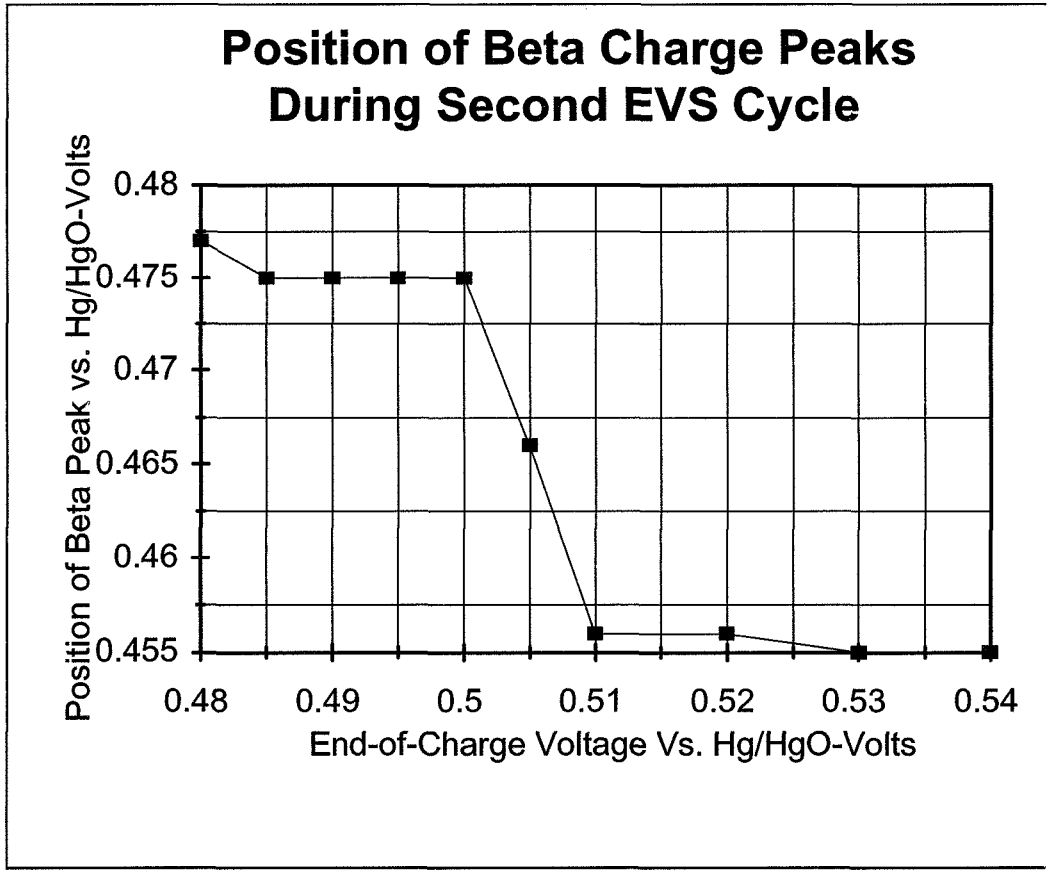

EXTENSIVE EVS STUDIES REVEALED THE FOLLOWING

- THE DEACTIVATED FORM OF NICKEL HYDROXIDE IS THE THERMDYNAMICALLY STABLE FORM
- THE ACTIVATED FORM OF NICKEL HYDROXIDE CAN BEGINE TO CONVERT BACK TO THE STABLE INACTIVE FORM IN ONLY A FEW DAYS
- ONCE IN THE ACTIVATED FORM, THE MATERIAL WILL REMAIN IN THE ACIVATED FORM AS LONG AS IT IS CHARGED ABOVE THE CRITICAL TRANSITION VOLTAGE
- THE DISCHARGE BETA AND GAMMA PEAKS SEPARATE AS ONE OR THE OTHER MATERIAL DOMINATES THE DISCHARGE TRACE

POST TEST AND DPA STUDIES ON SIMILAR CELLS

- CELL FROM PACK 3214E
  - +10 Degrees, 1.04 Recharge Ratio, 26% KOH
- CELL FROM PACK 3254E
  - -5 Degrees, 1.03 Recharge Ratio, 26% KOH
- CELLS WERE 50 Ah, DOUBLE LAYER ZIRCAR, SLURRY, BACK TO BACK CELLS CYCLING UNDER AIR FORCE SPONSORSHIP
- CELLS WITHDRAWN FROM ONGOING TESTS FOR OUR FURTHER STUDIES
- CRANE CONDUCTED TWO POST CEST CYCLES

SUMMARY OF CRANE POST TEST EVALUATION

Discharge	Charge	+10°C Cells	-5°C Cells
	Normal	1.04 recharge ratio	1.03 recharge ratio
C-rate		21.7 Ah discharged	46.8 Ah discharged
C/10-rate		11.3 Ah discharged	7.7 Ah discharged
Total 1st discharge		33.0 Ah discharged	54.5 Ah discharged
	C/2-rate	48.9 Ah charged	48.9 Ah charged
	C/10-rate	14.8 Ah charged	14.9 Ah charged
	Total 1st charge	63.7 Ah charged	63.8 Ah charged
C-rate		49.9 Ah discharged	50.2 Ah discharged
C/10-rate		7.7 Ah discharged	9.0 Ah discharged
Total 2ed Discharge		57.6 Ah discharged	59.2 Ah discharged

AEROSPACE DPA ACTIVITIES

- CELLS PUNCTURED IN SPECIAL CHAMBER TO MEASURE RESIDUAL GAS PRESSURE AND COMPARE WITH STRAIN GAUGE READINGS OF OTHER CELLS WITHIN THE PACK
- RESIDUAL GAS SAMPLES SENT FOR MASS SPEC. ANALYSIS
- FLOODED UTILIZATION AND EVS TESTING OF PLATE SAMPLES FROM FOUR SECTORS OF THE CELLS
- CHEMICAL ANALYSIS CARRIED OUT ON SINTER AND ACTIVE MATERIAL

RESIDUAL PRESSURE AND GAS ANALYSIS

Cell Pack	3214 E	3254 E
Cycling Temp. - °C	+ 10	-5
Residual Pressure - psia	118.0	1.3
Composition - %		
Hydrogen	97.8	3.0
Water Vapor	1.8	16.3
Nitrogen	0.3	77.9
Average Plate Expansion - %	15.7	15.0

SUGGESTED MECHANISM

- CHARGING TO HIGHER VOLTAGES CONVERTS BETA NICKEL OXYHYDROXIDE TO THE GAMMA PHASE
- UPON DISCHARGE, THE UNSTABLE ALPHA FORM OF NICKEL HYDROXIDE IS FORMED
- THIS MATERIAL DISSOLVES IN KOH AND PRECIPITATES AS A VERY SMALL CRYSTALINE FORM OF BETA NICKEL HYDROXIDE
- THIS IS THE ACTIVATED FORM AND CAN EASILY BE CHARGED TO THE GAMMA FORM VIA THE BETA NICKEL OXYHYDROXIDE
- OSTWOLD RIPENING CONVERTS THE ACTIVATED FORM BACK TO THE DEACTIVATED FORM
- LOWER TEMPERATURES FACILITATE THE CHARGING TO THE GAMMA PHASE AND RETARDS THE RATE OF COVERSION BACK TO THE DEACTIVATED FORM

SUGGEST RECHARGE PROTOCOL TO AVOID OR MINIMIZE WALKDOWN

- CYCLING TEMPERATURE MUST BE LOW ENOUGH TO PERMIT CHARGING TO THE GAMMA PHASE
- DETERMINE MINIMUM VOLTAGE REQUIRED TO CONVERT MATERIAL TO THE ACTIVE FORM
- CHARGE TO A CUTOFF PRESSURE OR MONITOR THE END OF CHARGE PRESSURE
- CORRECT PRESSURE READING FOR STRAIN GAUGE DRIFT AND SINTER CORROSION VIA RECONDITIONING

SUMMARY

- CAPACITY WALKDOWN A CONSEQUENCE OF THE INABILITY TO MAINTAIN A HIGHT STATE OF CHARGE
- CAPACITY LOSS IS TYPICALLY 35% WHICH WOULD BE EXPECTED BY THE VALENCE DIFFERNCE BETWEEN GAMMA AND BETA NICKEL OXYHYDROXIDE
- CYCLING AT -5 DEGREES FACILITATES THE FORMATION OF THE GAMMA PHASE
- EXCESSIVE OVERCHARGE CAN ALSO FACILITATE GAMMA PHASE FORMATION AT THE EXPENCE OF CYCLE LIFE
- CONDITIONS CAN NOW BE SUGGESTED TO HELP MINIMIZE CAPACITY WALKDOWN

OMIT
THIS
PAPER

The author has respectfully requested that this paper be withheld from publication in these proceedings.

Mathematical Modeling of Ni/H_2 and Li-Ion Batteries

John W. Weidner, Ralph E. White
Department of Chemical Engineering
and
Roger A. Dougal
Department of Electrical Engineering

Center for Electrochemical Engineering
University of South Carolina
Columbia, SC 29208

Sep 10/01/44
537999 398
20011172

Analysis of Battery Systems

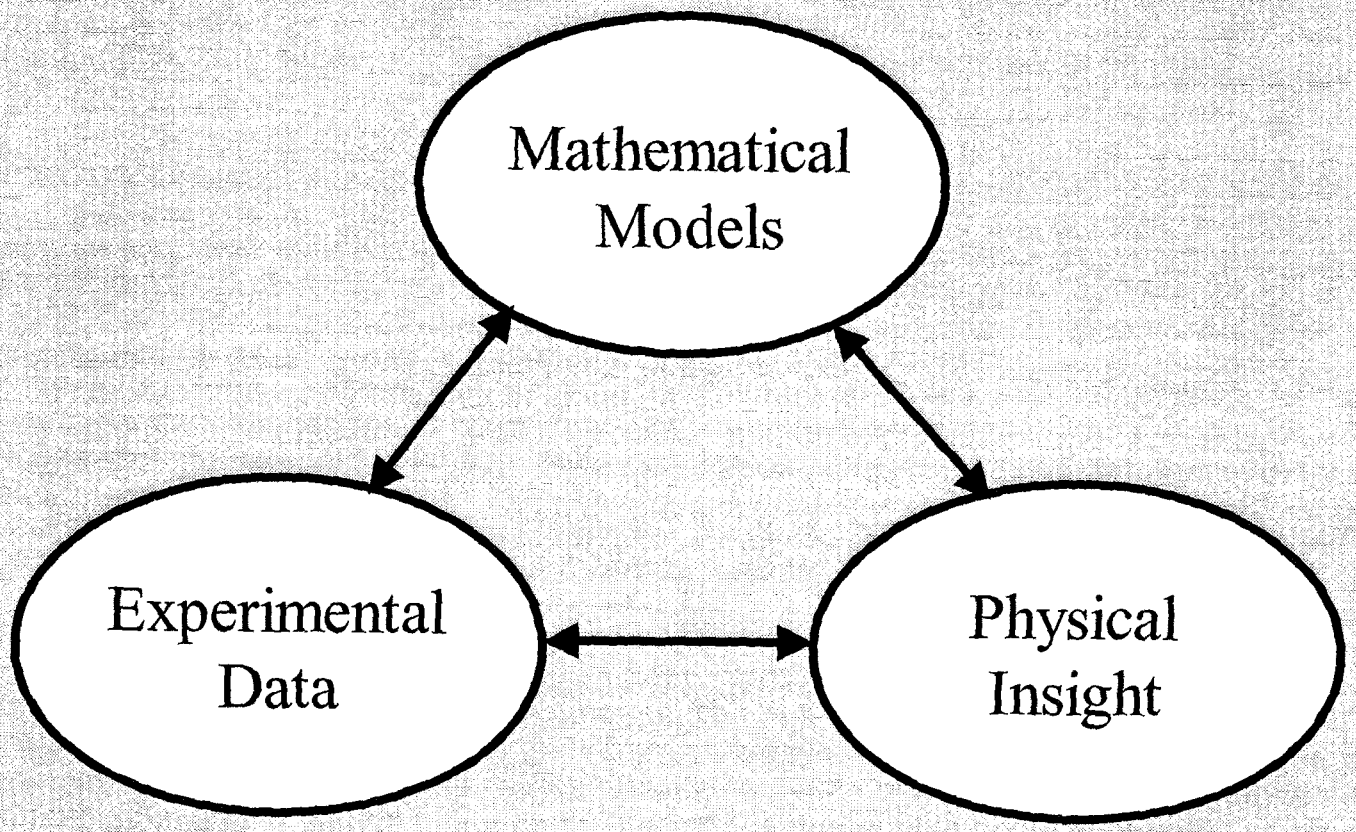

Modeling Effort

- Electrochemical Deposition of Nickel Hydroxide
  - Deposition rates of thin films
  - Impregnation of porous electrodes
- Experimental Characterization of Nickel Hydroxide
  - Diffusion coefficients of protons
  - Self-discharge rates (*i.e.,* oxygen-evolution kinetics)
  - Hysteresis between charge and discharge
  - Capacity loss on cycling

Modeling Effort

- Mathematical Modeling of Ni/H_2 Batteries
- Experimental Verification of the Ni/H_2 Battery Model
- Mathematical Modeling Li -Ion Batteries
- Experimental Verification of the Li -Ion Battery Model
- Integrated Power System Models for Satellites
- Experimental Verification of Integrated -Systems Model

Schematic of Ni/H_2 Battery

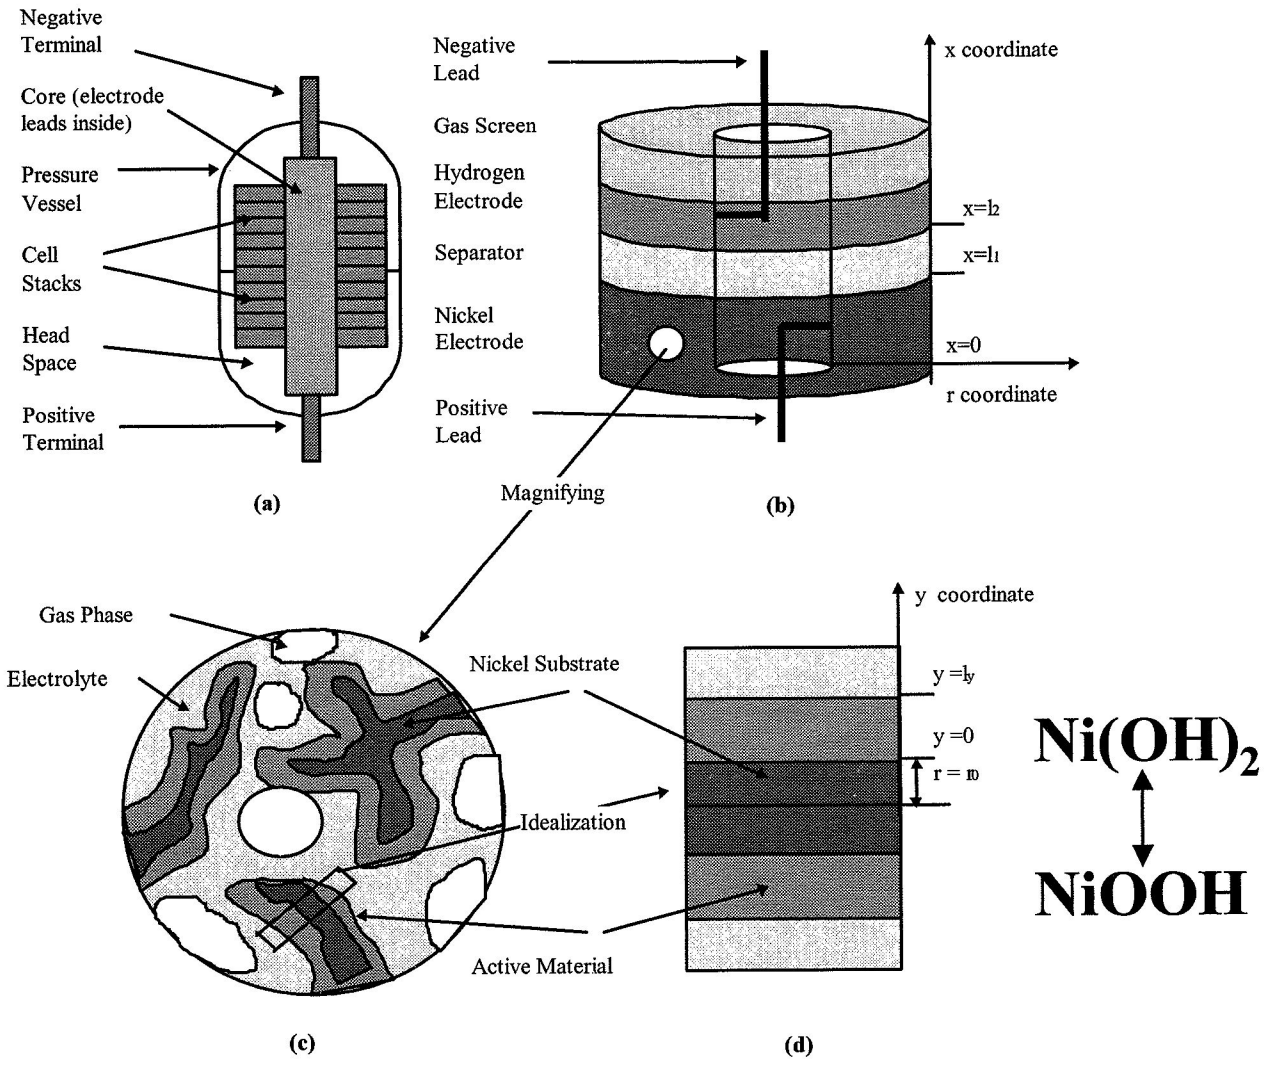

Proton Diffusion Coefficient

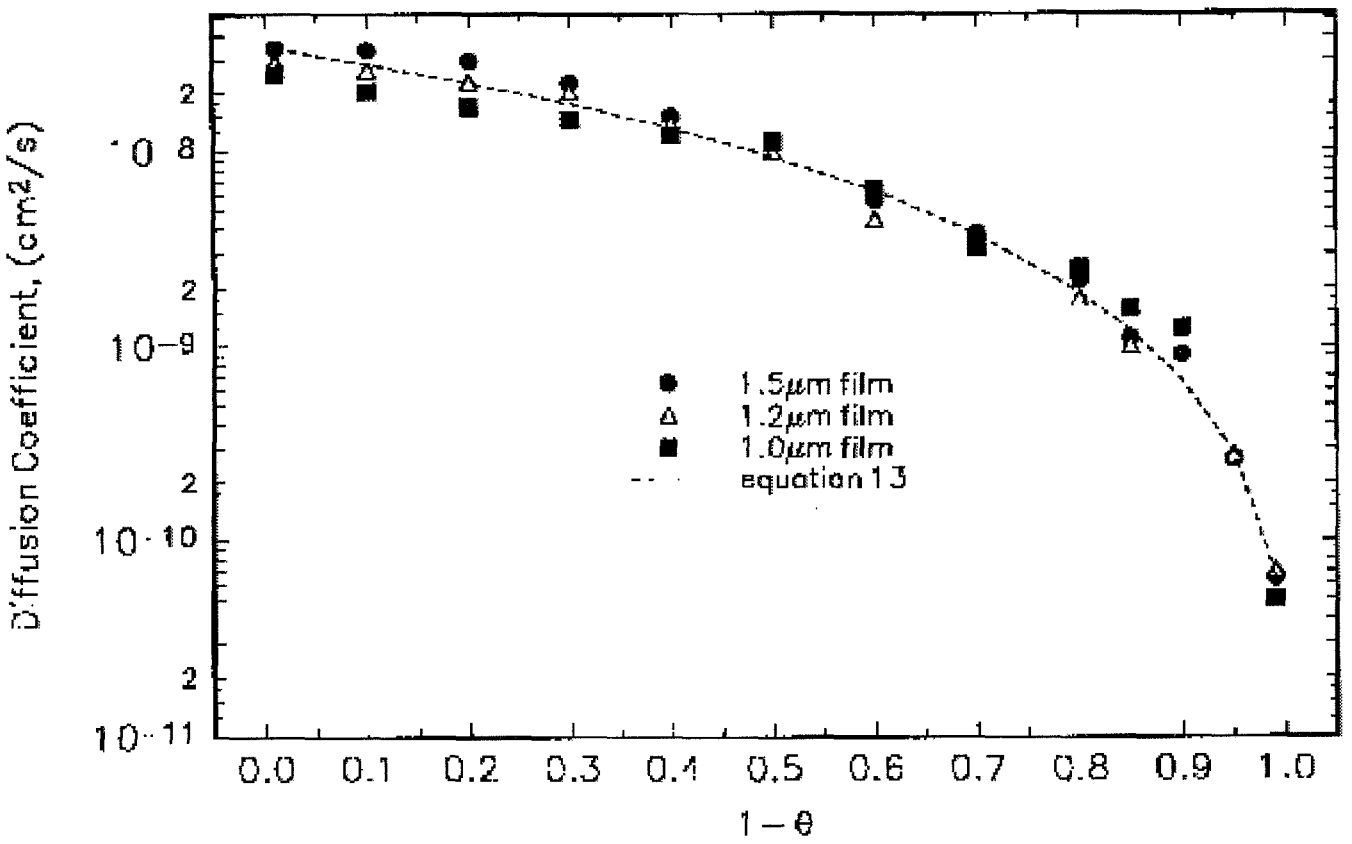

S. Motupally, C. C. Streinz, and J. W. Weidner, *J. Electrochem. Soc.*, **142**, 1401-1408 (1995).

Utilization of the NiOOH

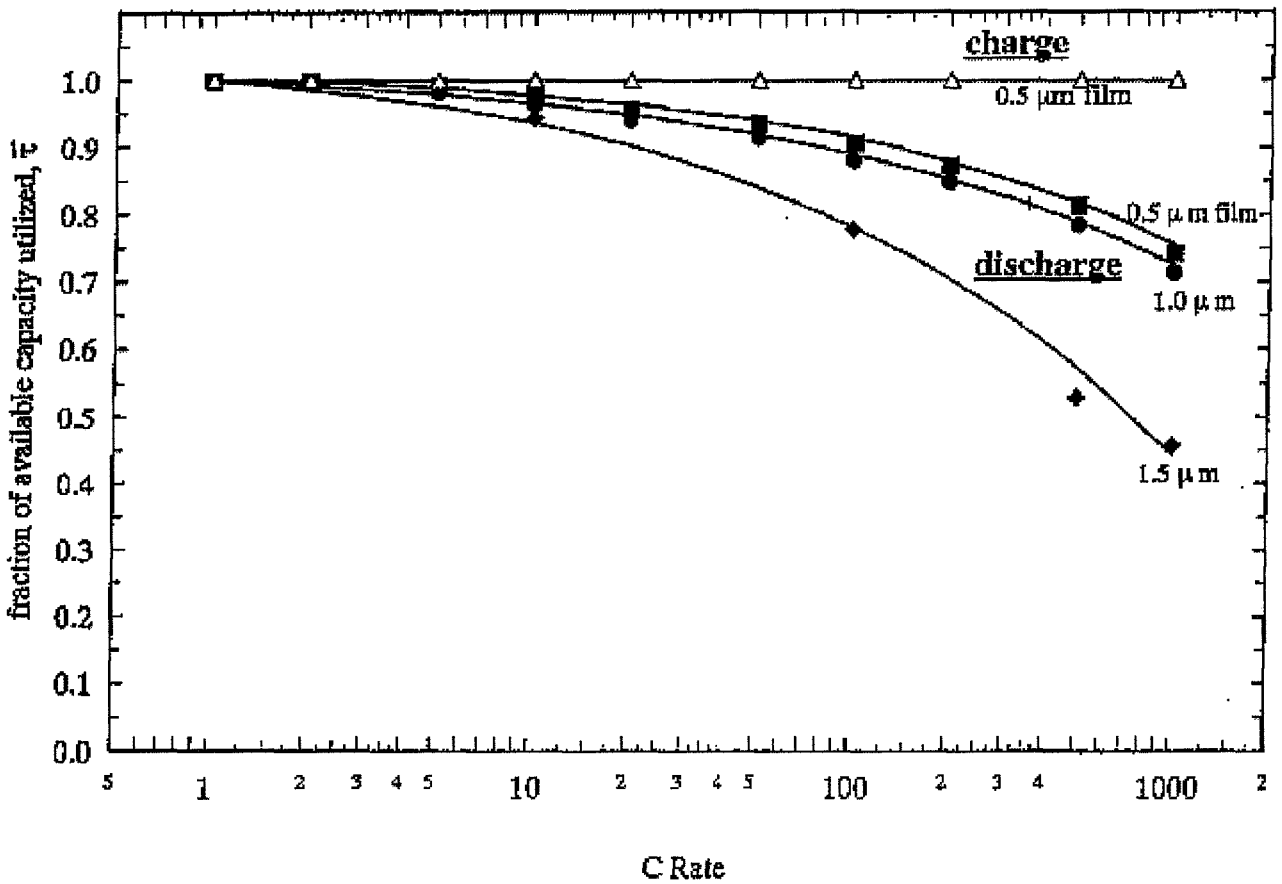

S. Motupally, C. C. Streinz, and J. W. Weidner, *J. Electrochem. Soc.*, **145**, 29-34 (1998).

Utilization of the NiOOH

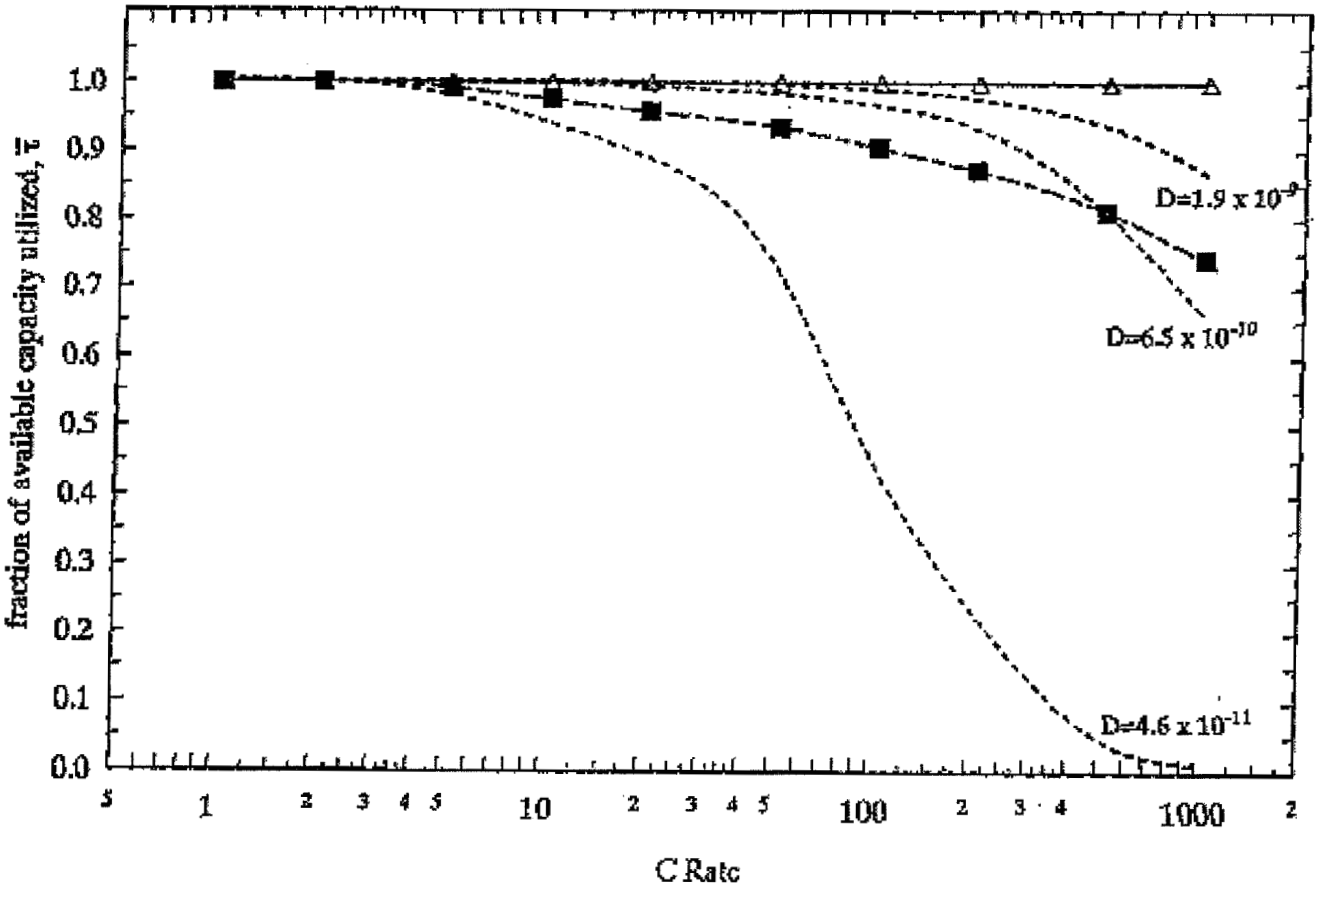

S. Motupally, C. C. Streinz, and J. W. Weidner, *J. Electrochem. Soc.*, **145**, 29-34 (1998).

Hysteresis in the Nickel Electrode

Constant Current *vs.* Constant Potential Experiments

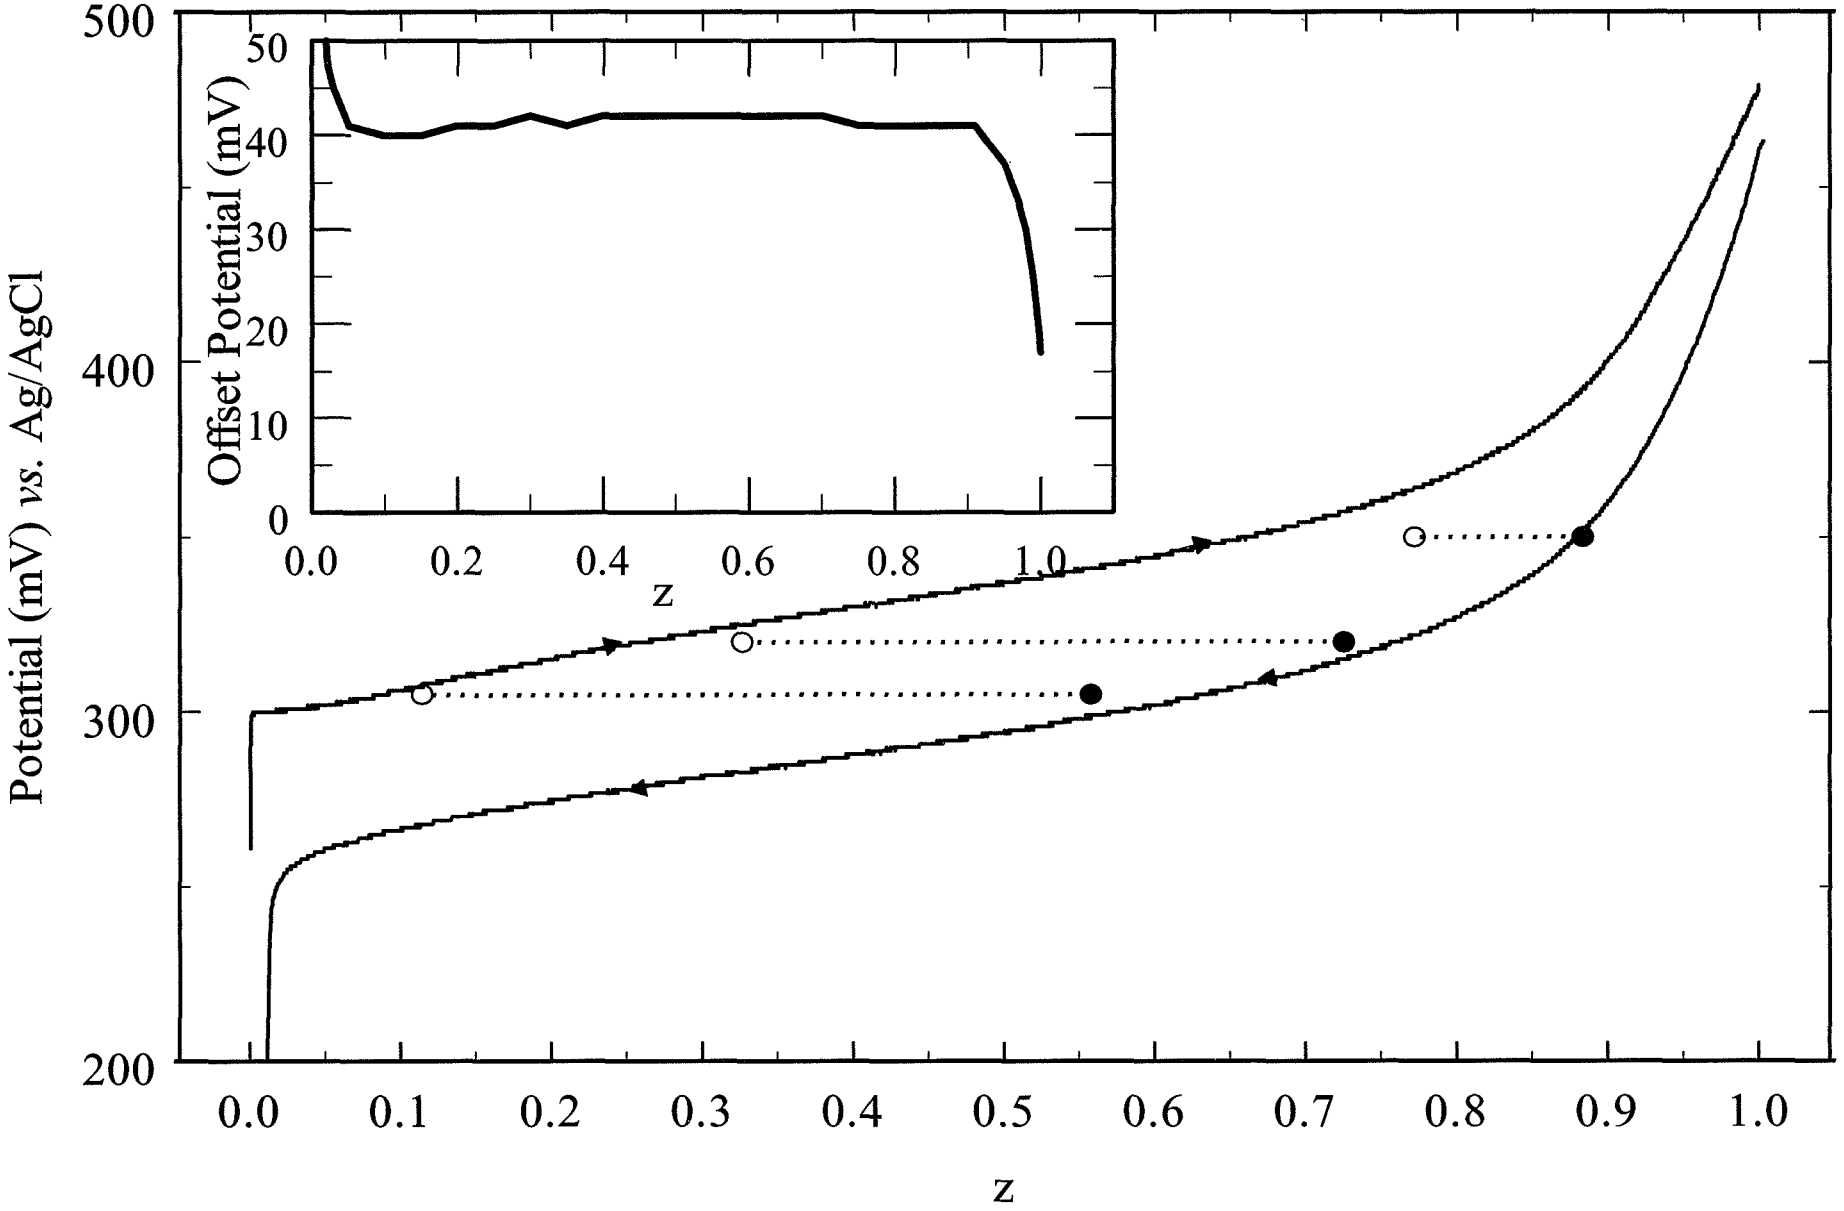

Boundary and Scanning Curves During Proton Intercalation/Extraction

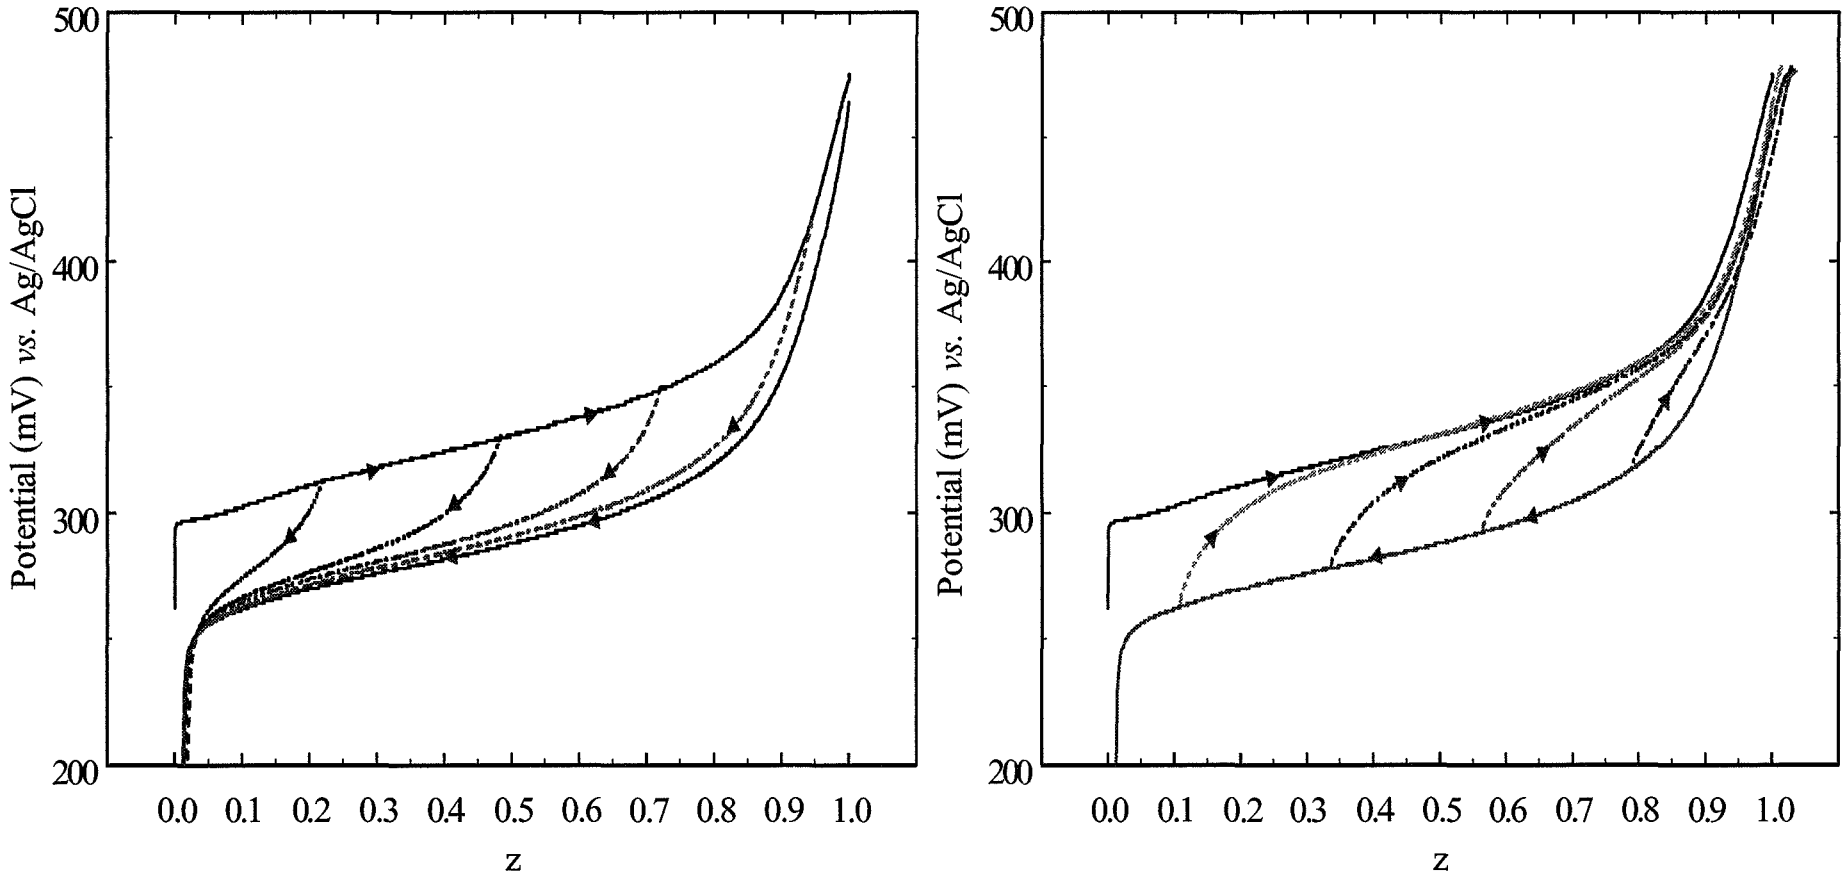

"Wiping-out" Property of Systems Exhibiting Hysteresis

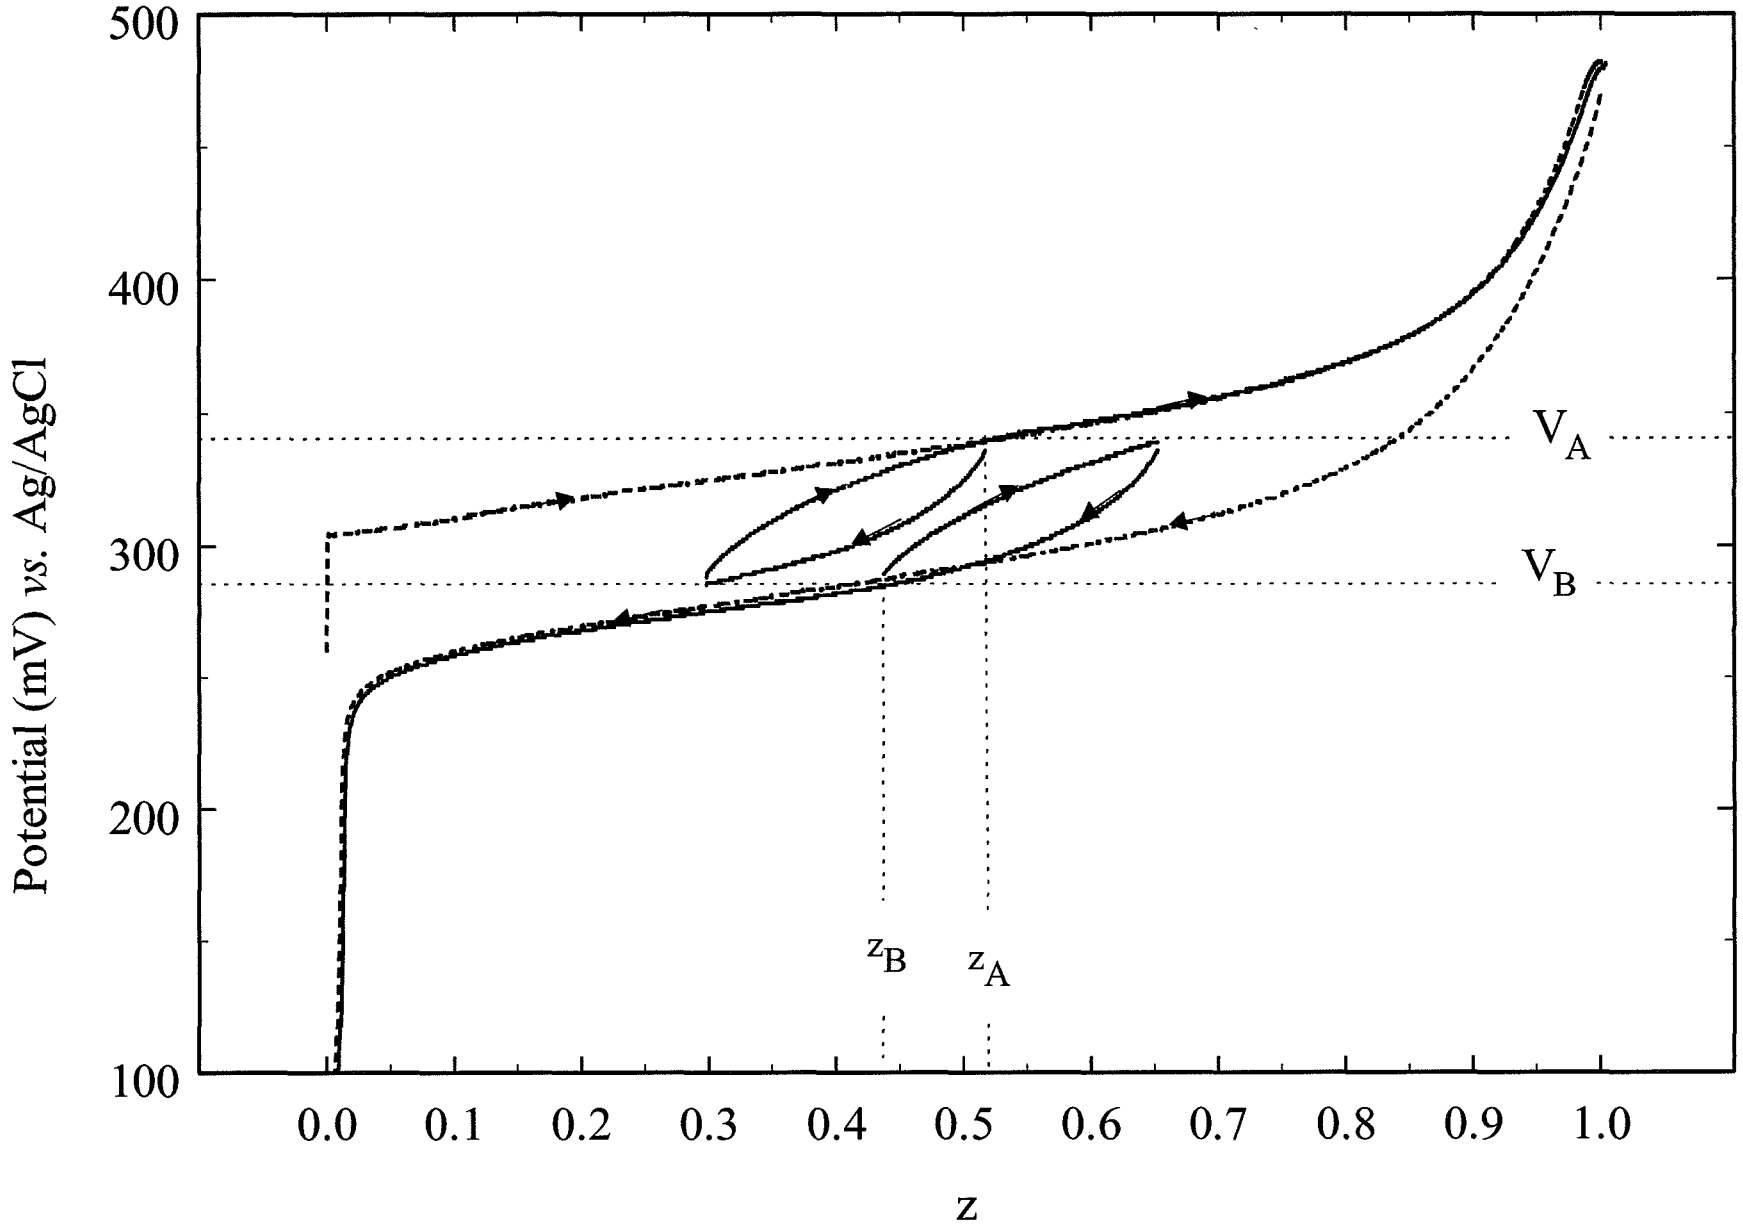

The History-Dependent Path of the Ni Electrode

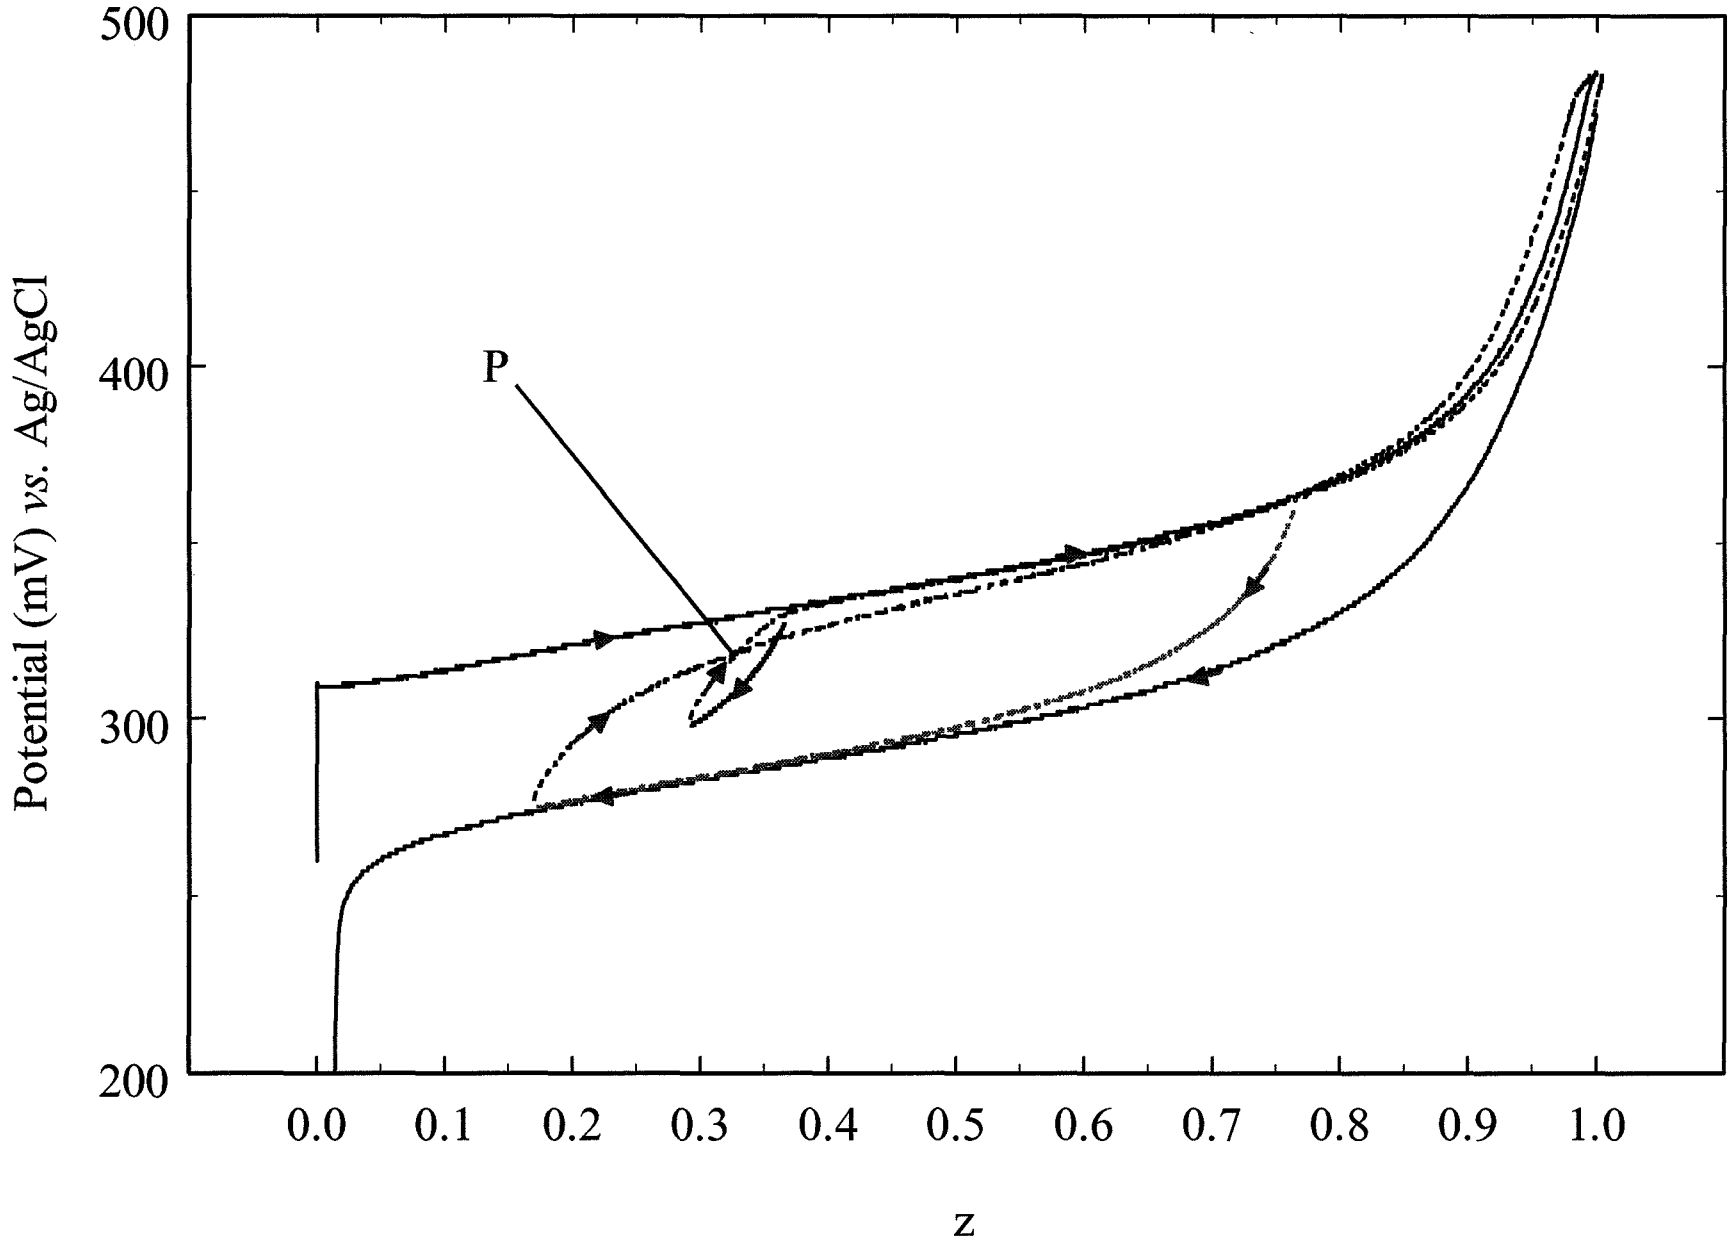

Internal Hysteresis Loops in The Ni Electrode

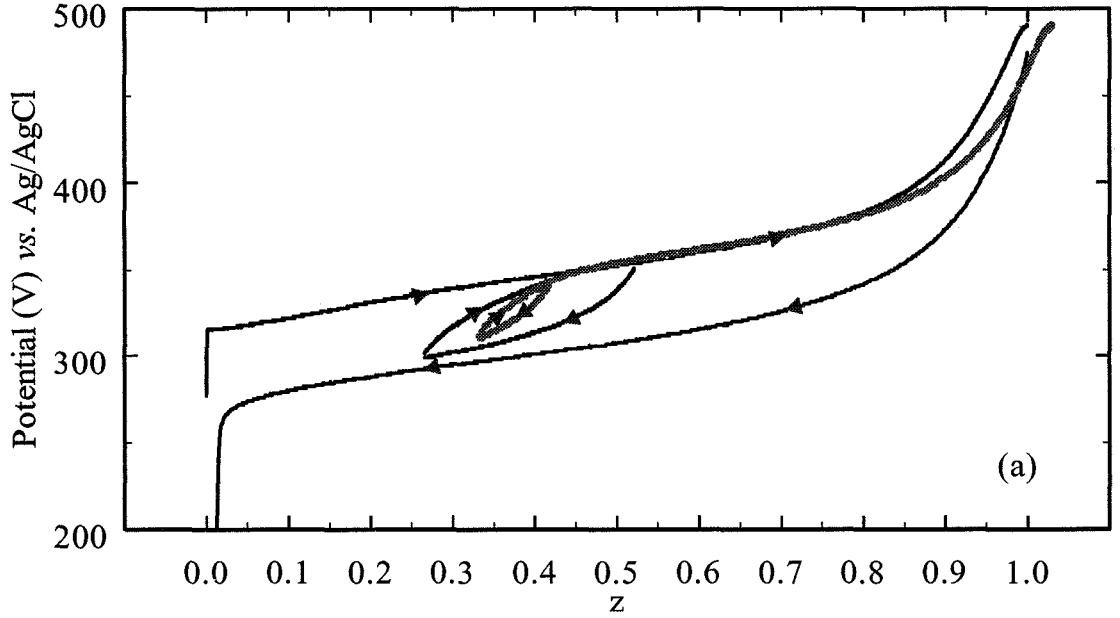

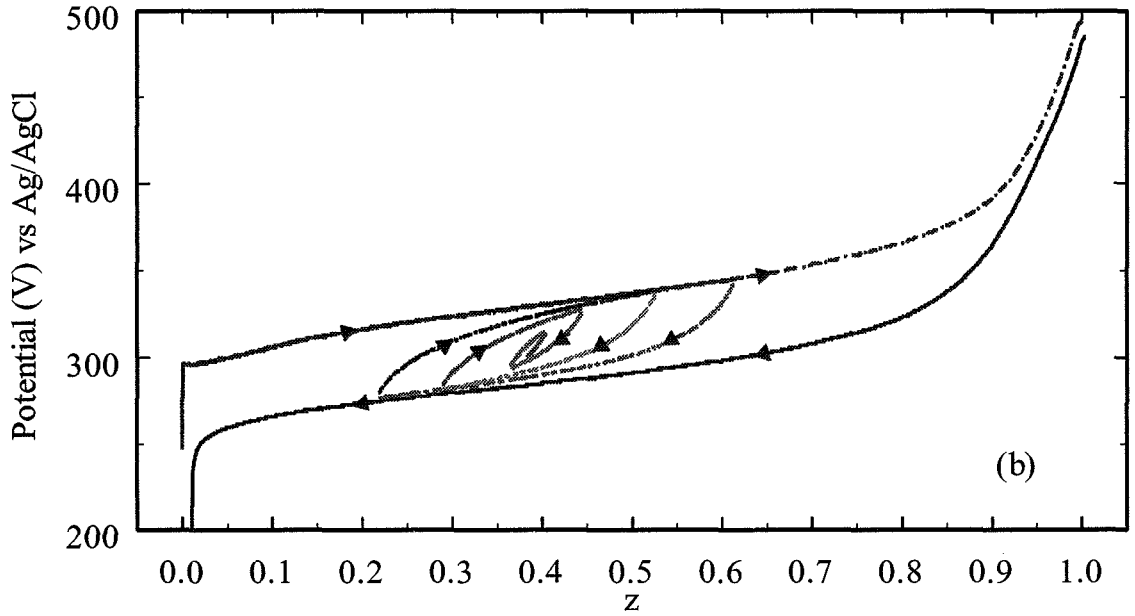

Path of the System During Continuous Cycling Over Small Z

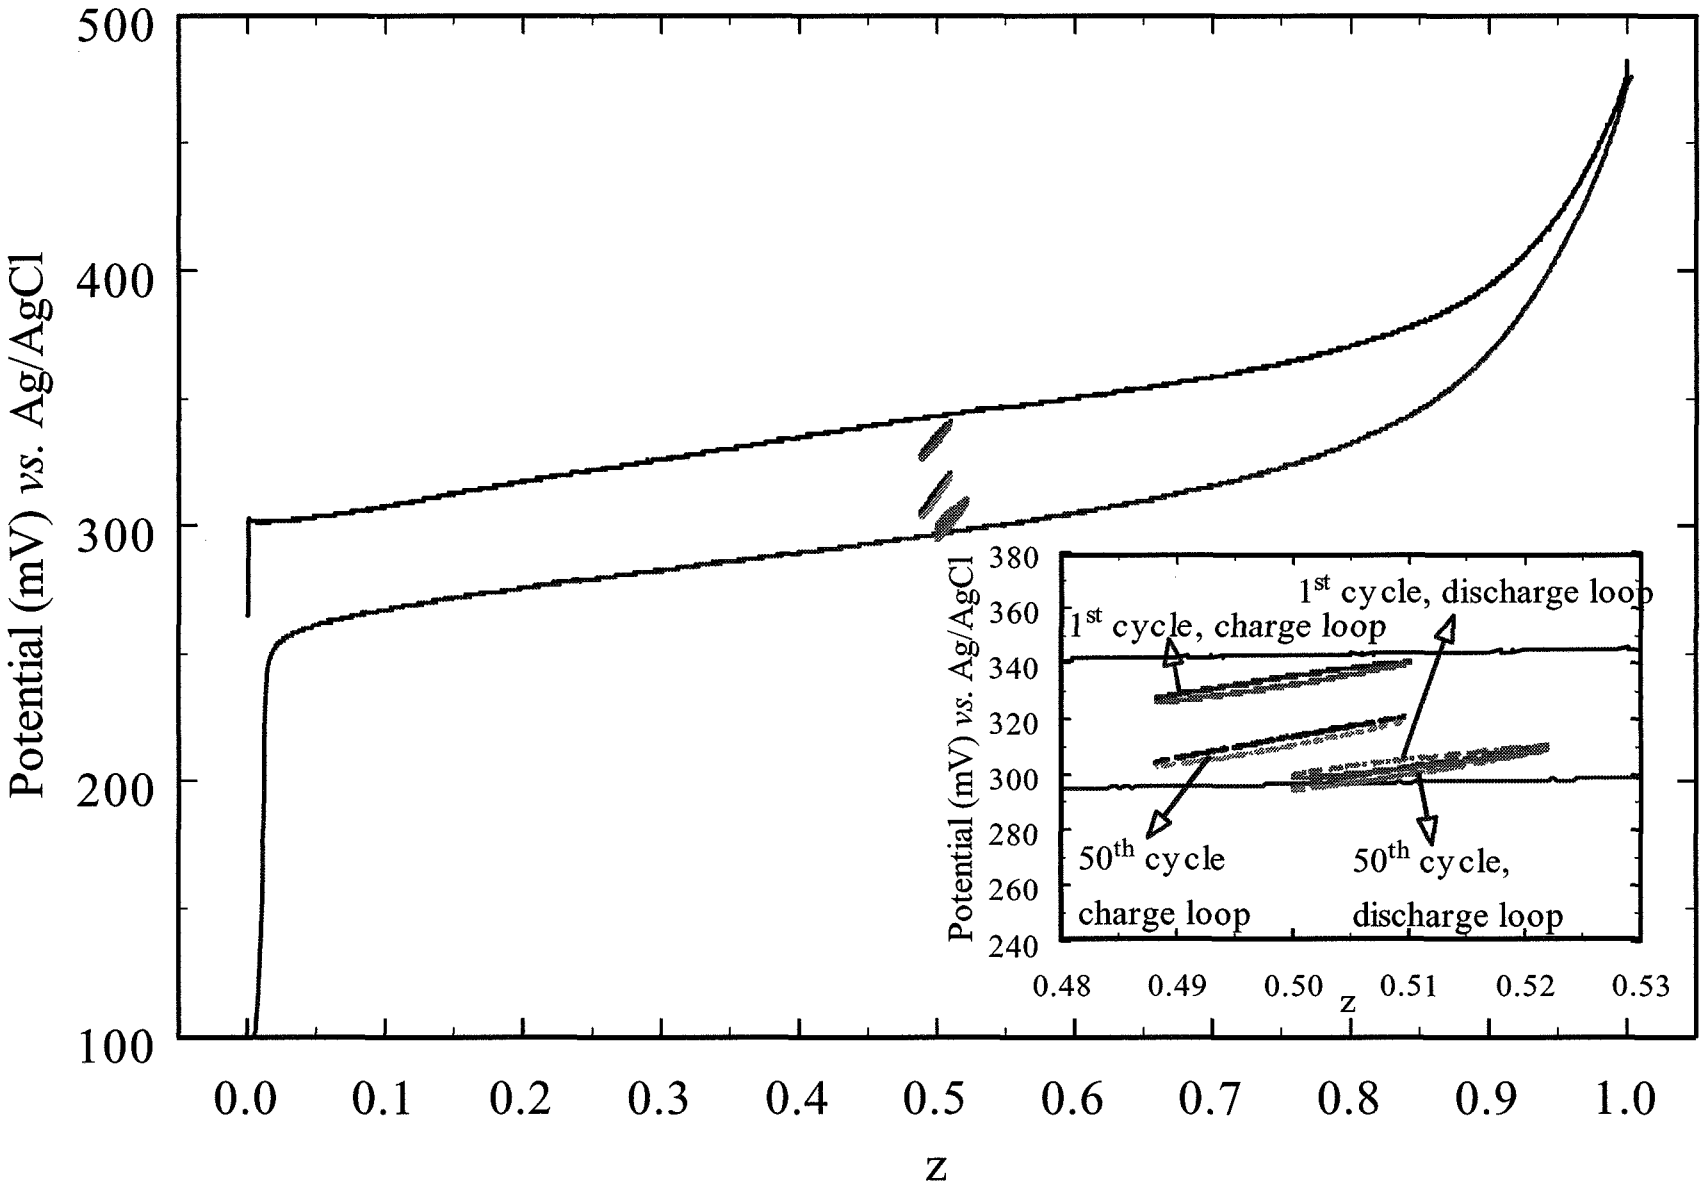

Crystal Structures for Nickel Hydroxide

ABBCCA Structure: NiOOH

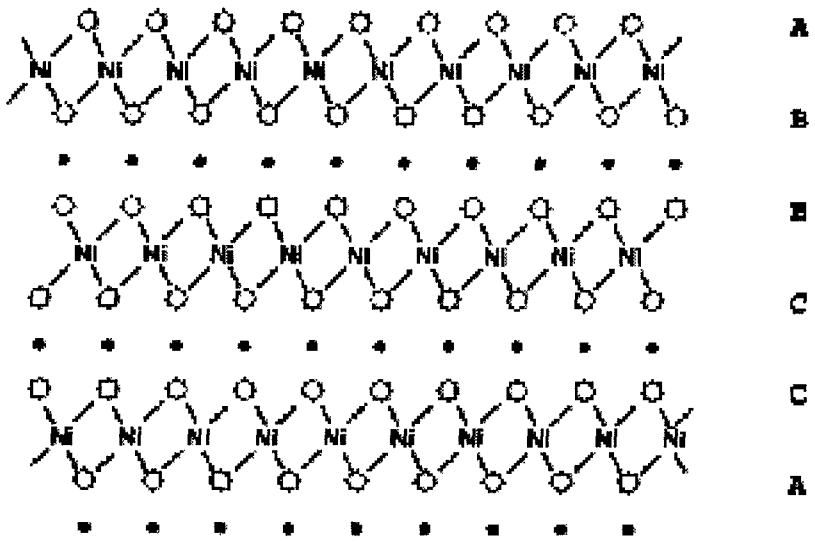

ABAB Structure: $Ni(OH)_2$

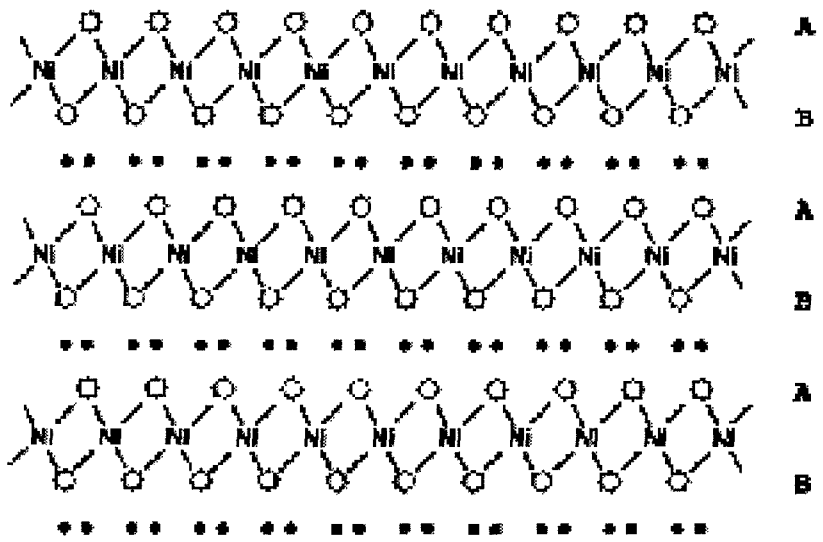

Bode Diagram

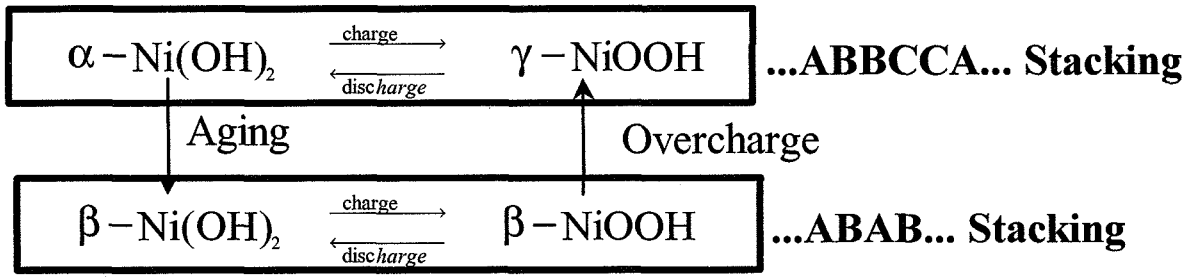

Modified Bode Diagram

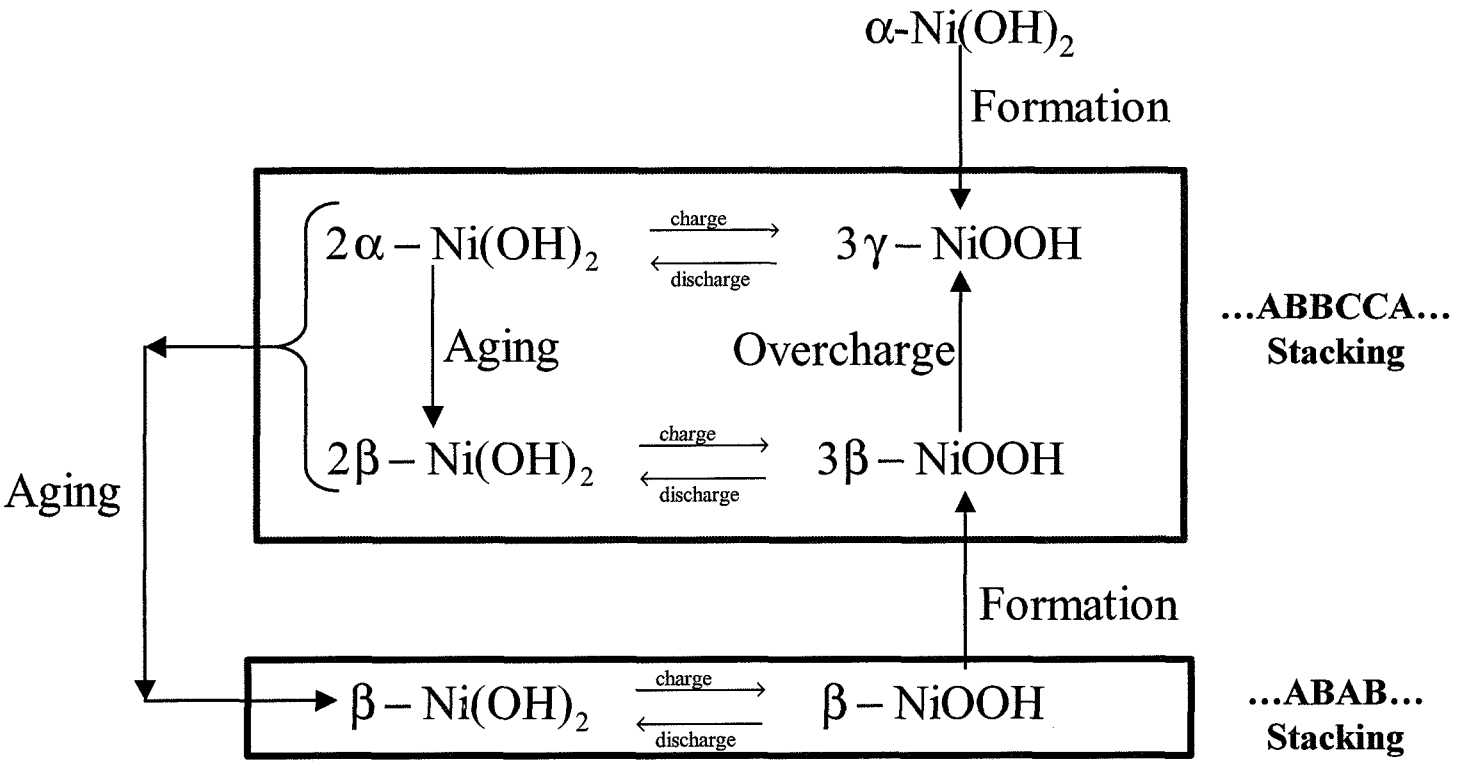

Defect Representation of the Nickel Hydroxide Electrode

$$\boxed{\left[Ni_{1-x}\,\square_{y}\,\square_{i}\,H_{x-y}\right]OOH_{2-z}\cdot X_{w}H_{2}O}$$

$$x = \frac{\text{number of Ni vacancies}}{\text{total number of Ni lattice sites}}$$

$$y = \frac{\text{number of Ni vacancies occupied by } K^{+}}{\text{total number of Ni lattice sites}}$$

$$n = \frac{\text{number of } H^{+}}{\text{number of Ni vacancies not occupied by } K^{+}}$$

$$X_{w} = \frac{\text{number of water molecules}}{\text{total number of Ni lattice sites}}$$

$$2 - z = \frac{\text{number of interlamellar protons}}{\text{total number of Ni lattice sites}}$$

Nickel Hydroxide Redox Reaction

$$\left[\mathbf{Ni}\ \ (\mathbf{K})_{\frac{y_1}{(1-x_1)}}(\mathbf{n_1H})_{\frac{x_1-y_1}{1-x_1}}\right]\mathbf{O}_{\frac{2}{1-x_1}}\mathbf{H}_{\frac{2}{1-x_1}}\cdot \mathbf{X_{w_1}H_2O}+\lambda_1\mathbf{OH^-}+\lambda_2\mathbf{K^+}$$

$$\underset{\text{discharge}}{\overset{\text{charge}}{\rightleftharpoons}}\left[\mathbf{Ni}\ \ (\mathbf{K})_{\frac{y_2}{(1-x_2)}}(\mathbf{n_2H})_{\frac{x_2-y_2}{1-x_2}}\right]\mathbf{O}_{\frac{2}{1-x_2}}\mathbf{H}_{\frac{1}{1-x_2}}\cdot \mathbf{X_{w_2}H_2O}+\lambda_3\mathbf{H_2O}+\lambda_4\mathbf{e^-}$$

$$\lambda_1=\left[\frac{n_1(x_1-y_1)-2}{(1-x_1)}-\frac{n_2(x_2-y_2)-3}{(1-x_2)}\right]\quad \lambda_3=\left[\frac{n_1(x_1-y_1)}{(1-x_1)}-\frac{n_2(x_2-y_2)-1}{(1-x_2)}\right]+X_{w_1}-X_{w_2}$$

$$\lambda_2=\left[\frac{y_2}{(1-x_2)}-\frac{y_1}{(1-x_1)}\right]\qquad \lambda_4=\left[\frac{3-y_2-n_2(x_2-y_2)}{(1-x_2)}-\frac{2-y_1-n_1(x_1-y_1)}{(1-x_1)}\right]$$

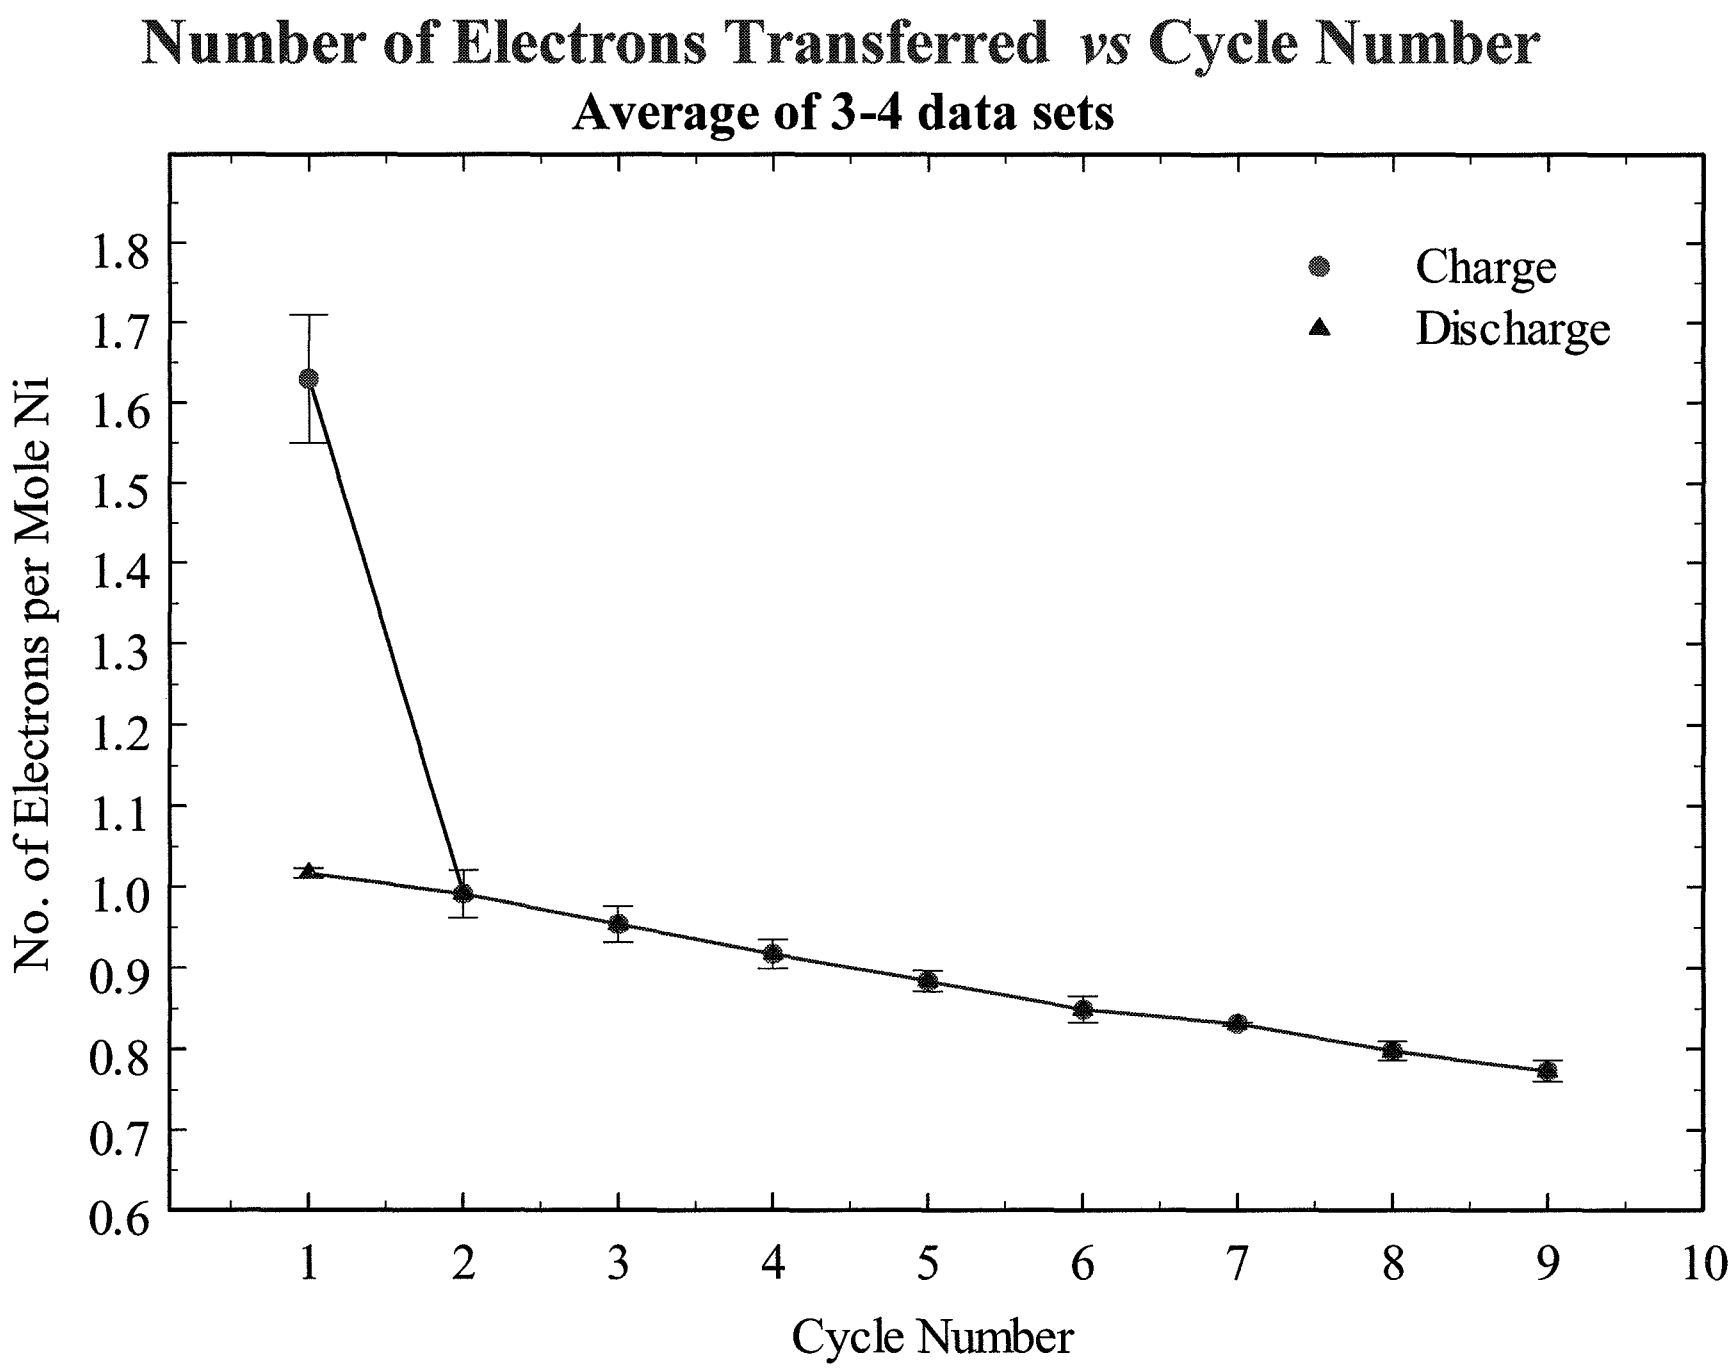
Number of Electrons Transferred vs Cycle Number
Average of 3-4 data sets
Charge
Discharge
No. of Electrons per Mole Ni
1.8
1.7
1.6
1.5
1.4
1.3
1.2
1.1
1.0
0.9
0.8
0.7
0.6
1
2
3
4
5
6
7
8
9
10
Cycle Number

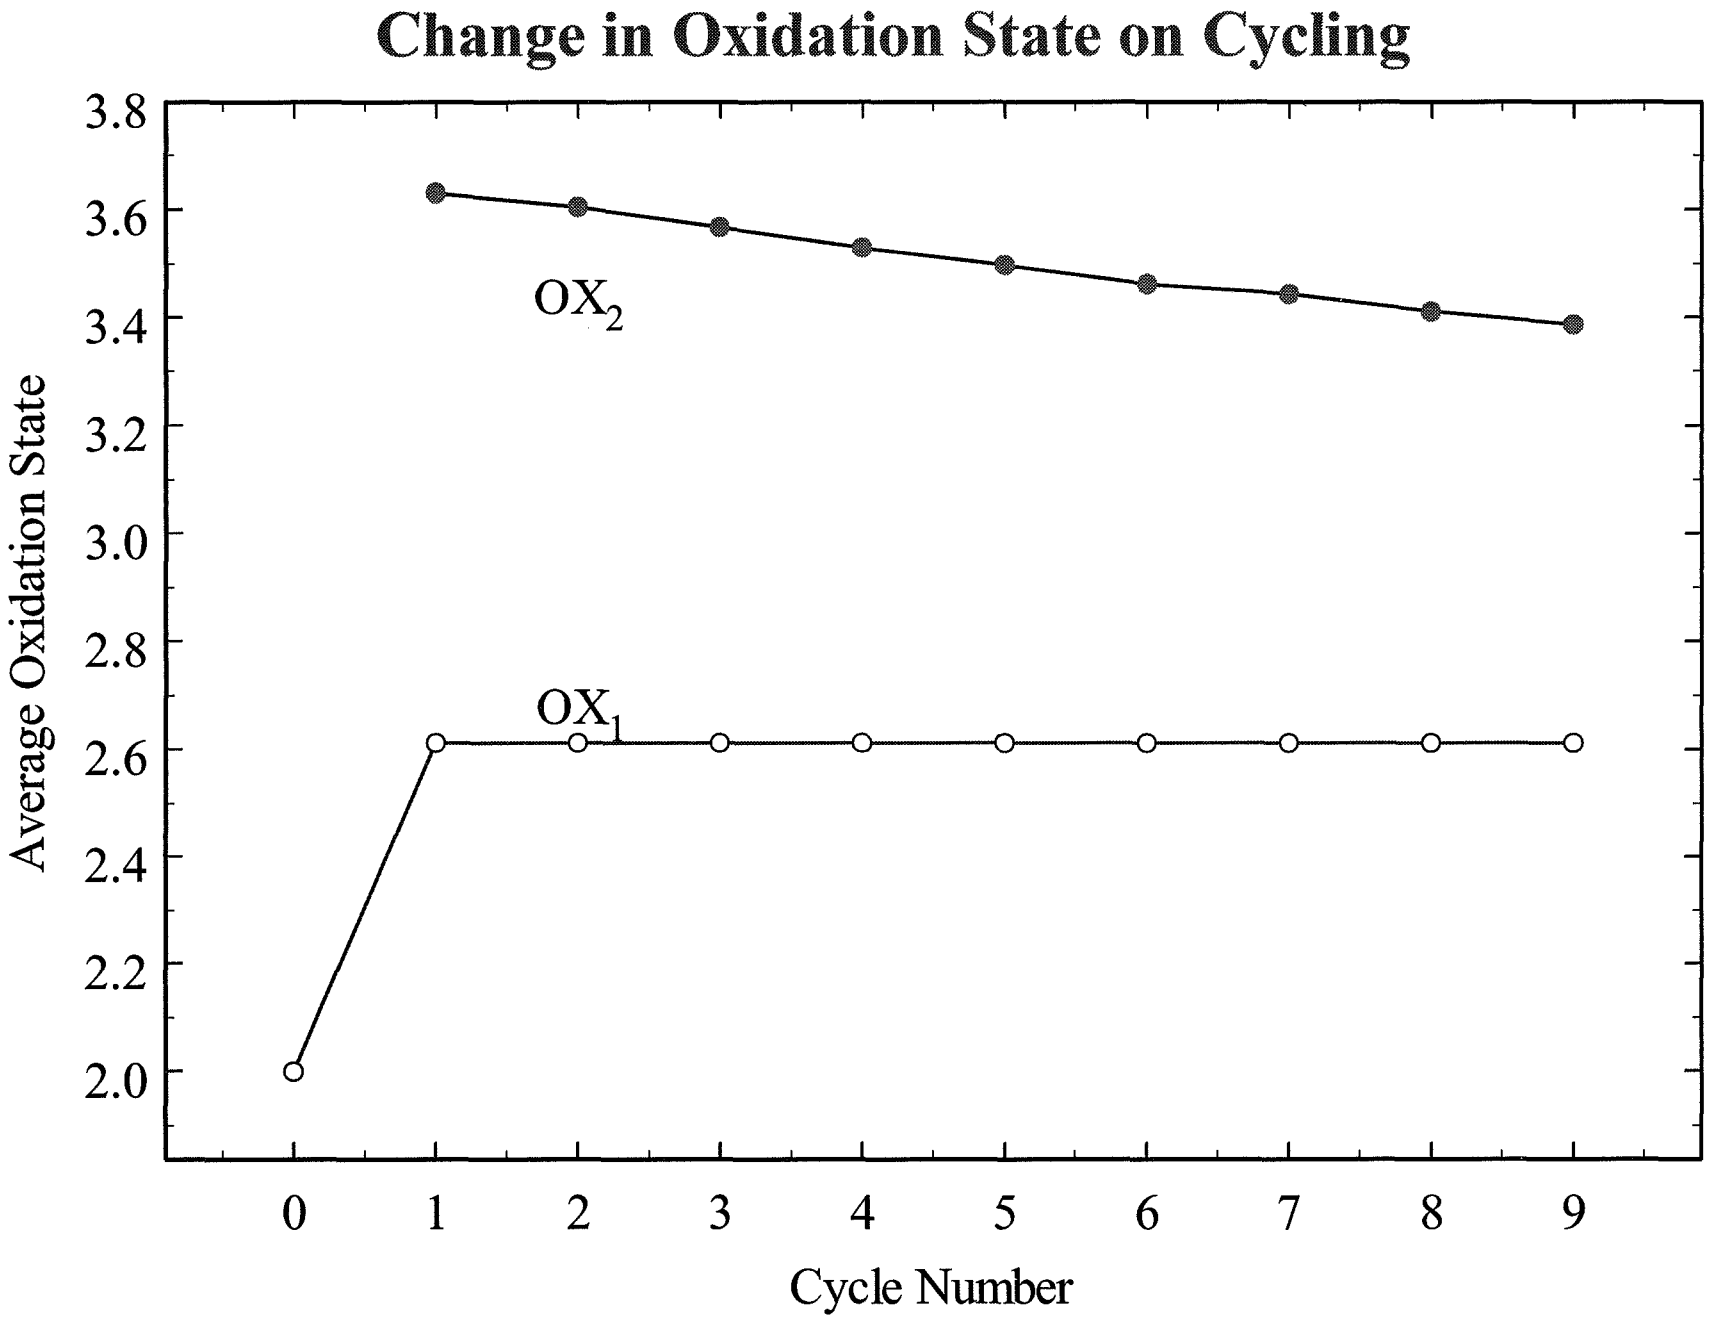
Change in Oxidation State on Cycling
Average Oxidation State
3.8
3.6
3.4
3.2
3.0
2.8
2.6
2.4
2.2
2.0
OX2
OX1
0
1
2
3
4
5
6
7
8
9
Cycle Number

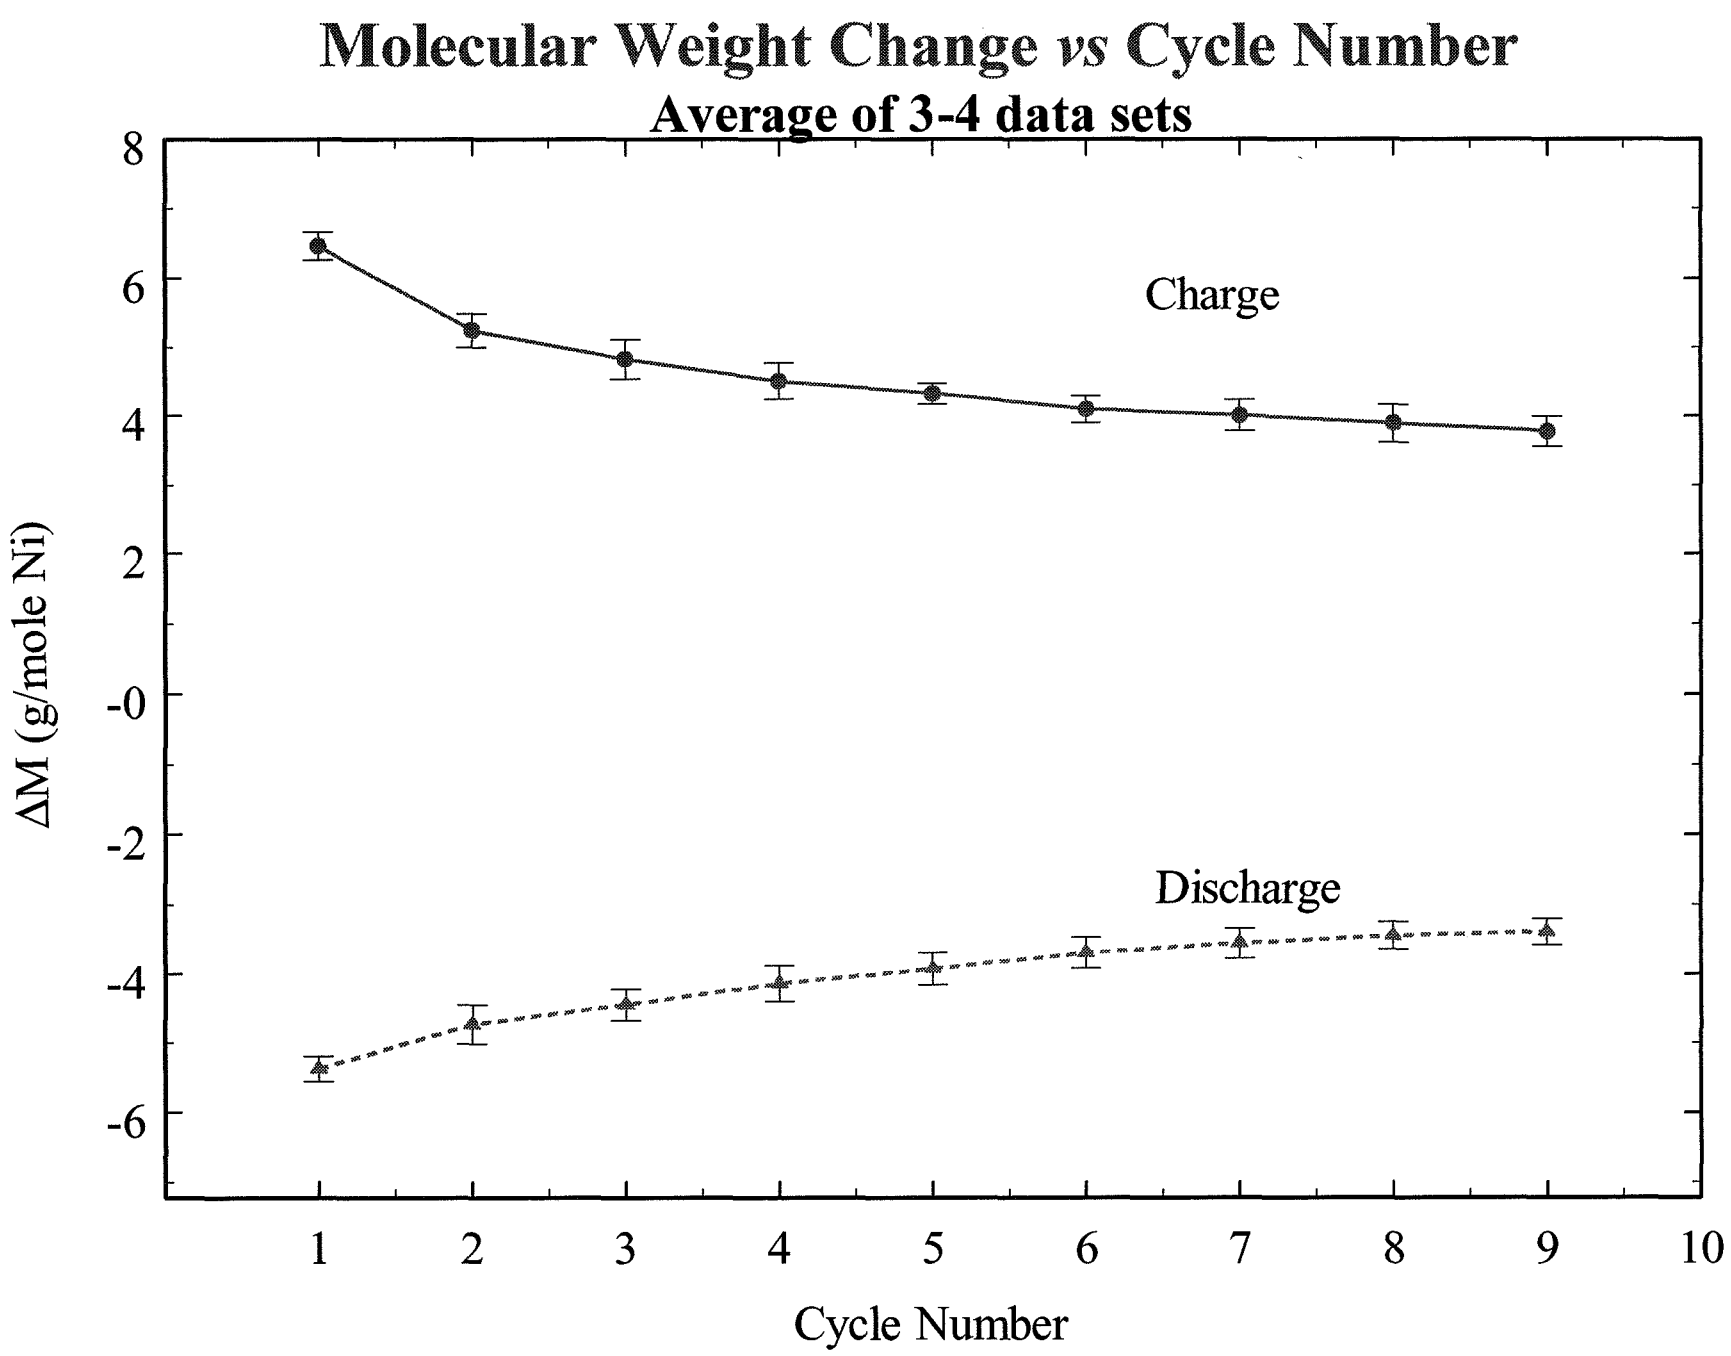
Molecular Weight Change vs Cycle Number
Average of 3-4 data sets
Charge
Discharge
ΔM (g/mole Ni)
Cycle Number
8
6
4
2
-0
-2
-4
-6
1
2
3
4
5
6
7
8
9
10

Change in Defect Parameters on Cycling

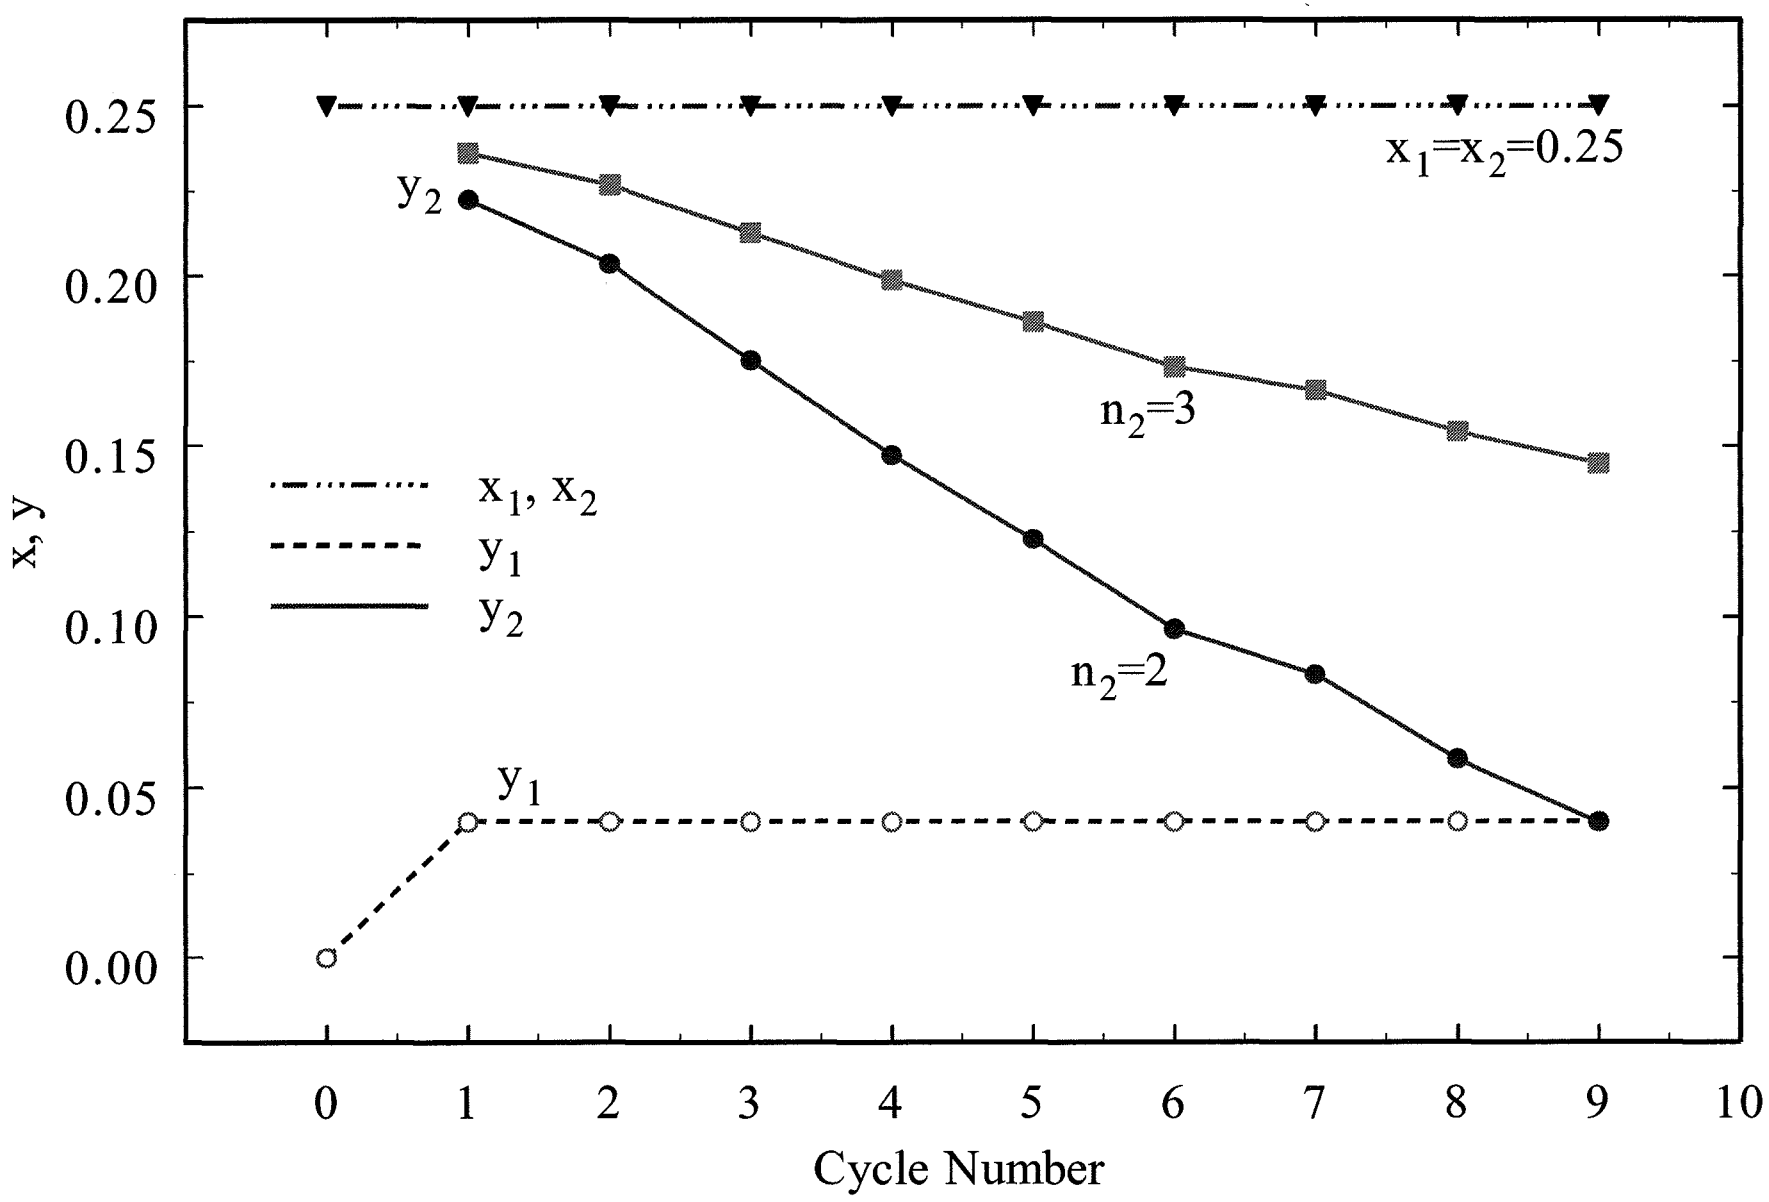

Redox Reactions In the Nickel Electrode as Described by the Defect Model

$x_1=x_2=y_2=0.25$, $n_1=0$ and $y_1=0$

$$2\alpha - \left[Ni^{2.67}(V_{Ni})_{0.33}\right]O_{2.67}H_{2.67} \underset{\text{discharge}}{\overset{\text{charge}}{\rightleftarrows}} 3\gamma - \left[Ni^{3.67}(K)_{0.33}\right]O_{2.67}H_{1.33}$$

$$+1.33OH^- + 0.33K^+ \qquad\qquad +1.33\ H_2O + 1\ e^-$$

$x_1=x_2=0.11$, $n_1=0$, $y_1=y_2=0$ and $n_2=1$

$$2\beta - \left[Ni^{2.25}(V_{Ni})_{0.12}\right]O_{2.25}H_{2.25} \underset{\text{discharge}}{\overset{\text{charge}}{\rightleftarrows}} 3\beta - \left[Ni^{3.25}(H)_{0.12}\right]O_{2.25}H_{1.12}$$

$$+OH^- \qquad\qquad +H_2O + 1e^-$$

$x_1=x_2=y_2=0.25$, $n_1=2$ and $y_1=0$

$$\alpha - \left[Ni^{2.0}(2H)_{0.33}\right]O_{2.67}H_{2.67} \xrightarrow{\text{Formation}} 3\gamma - \left[Ni^{3.67}(K)_{0.33}\right]O_{2.67}H_{1.33}$$

$$+2OH^- + 0.33K^+ \qquad\qquad +2\ H_2O + 1.67\ e^-$$

Simulated Charge/Discharge of a Ni-H_2 Cell

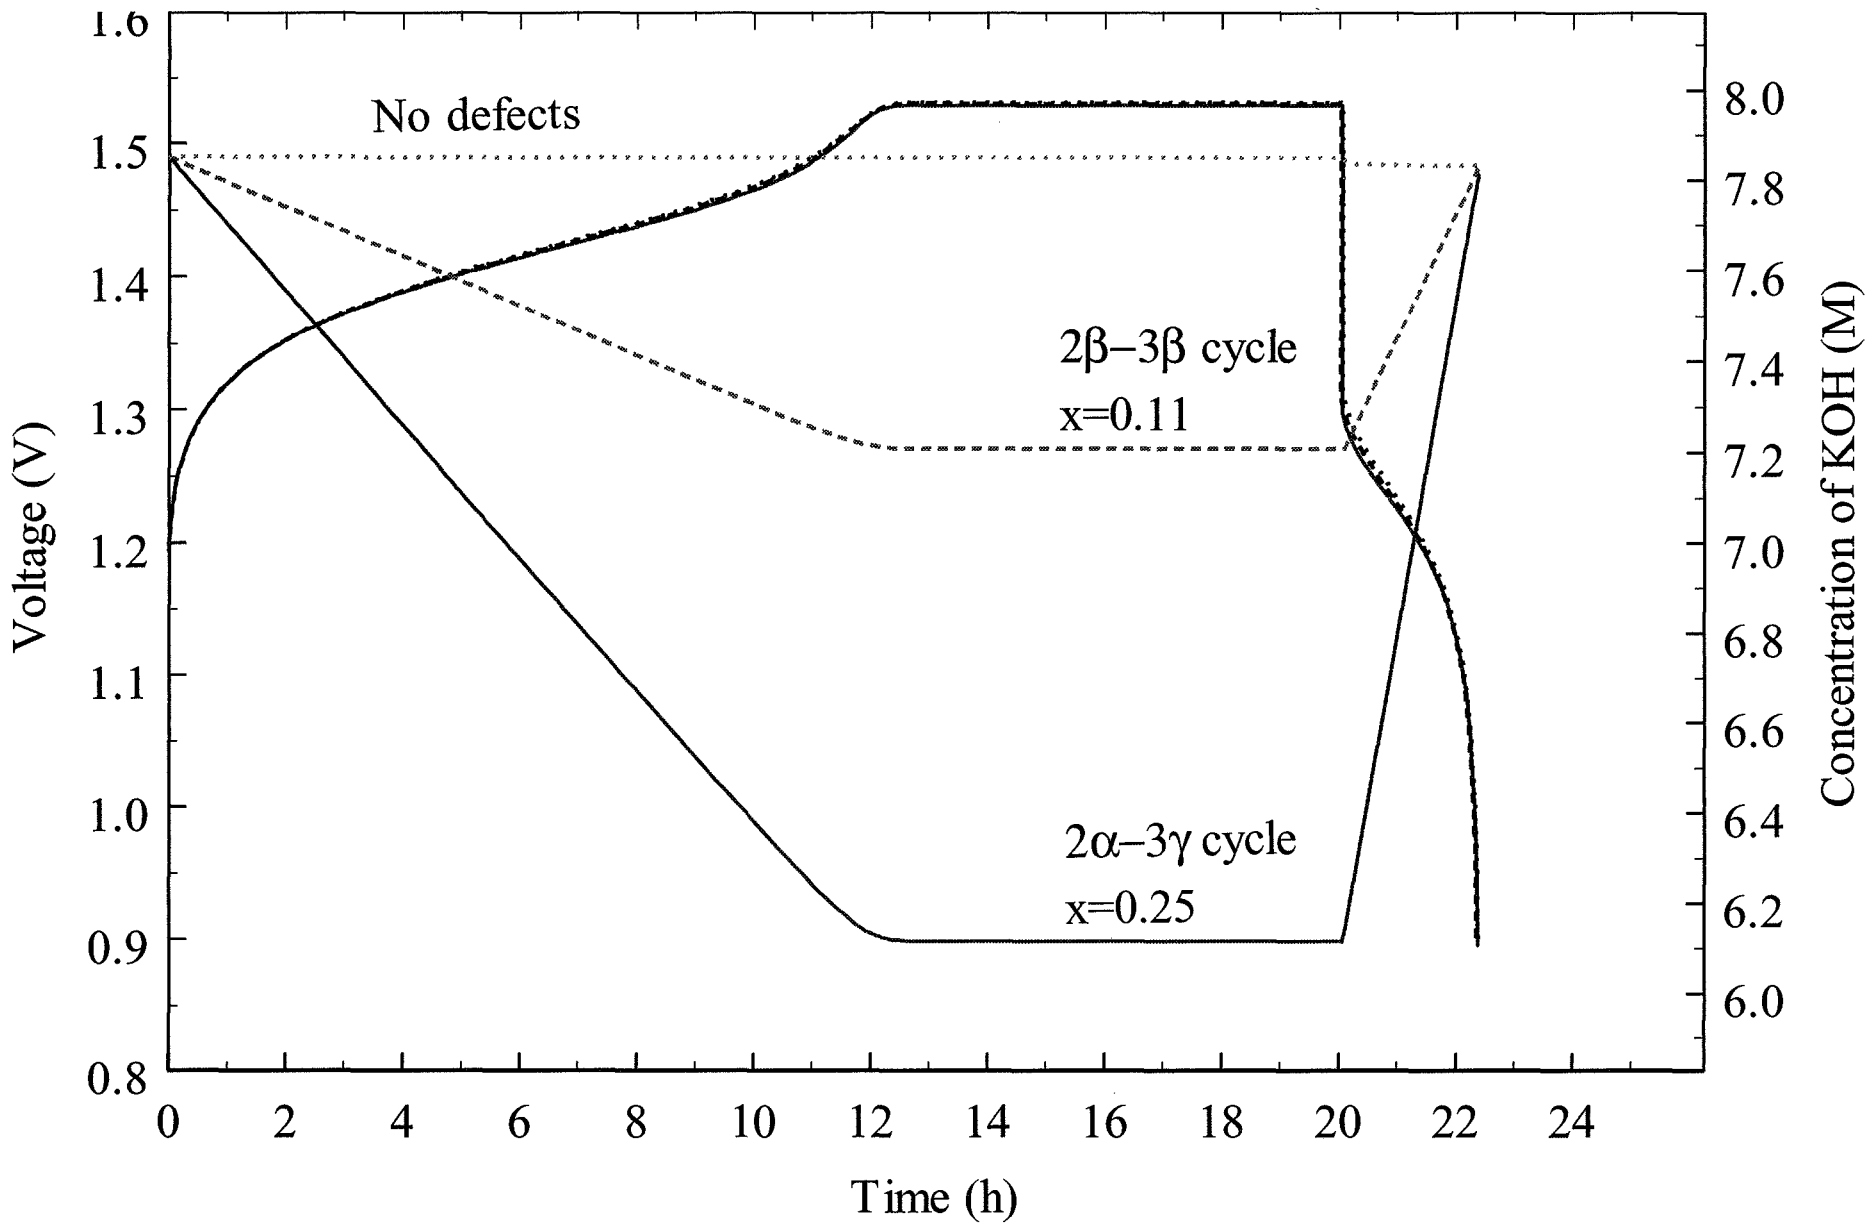

Simulated Charge/Discharge of a Ni-H_2 Cell

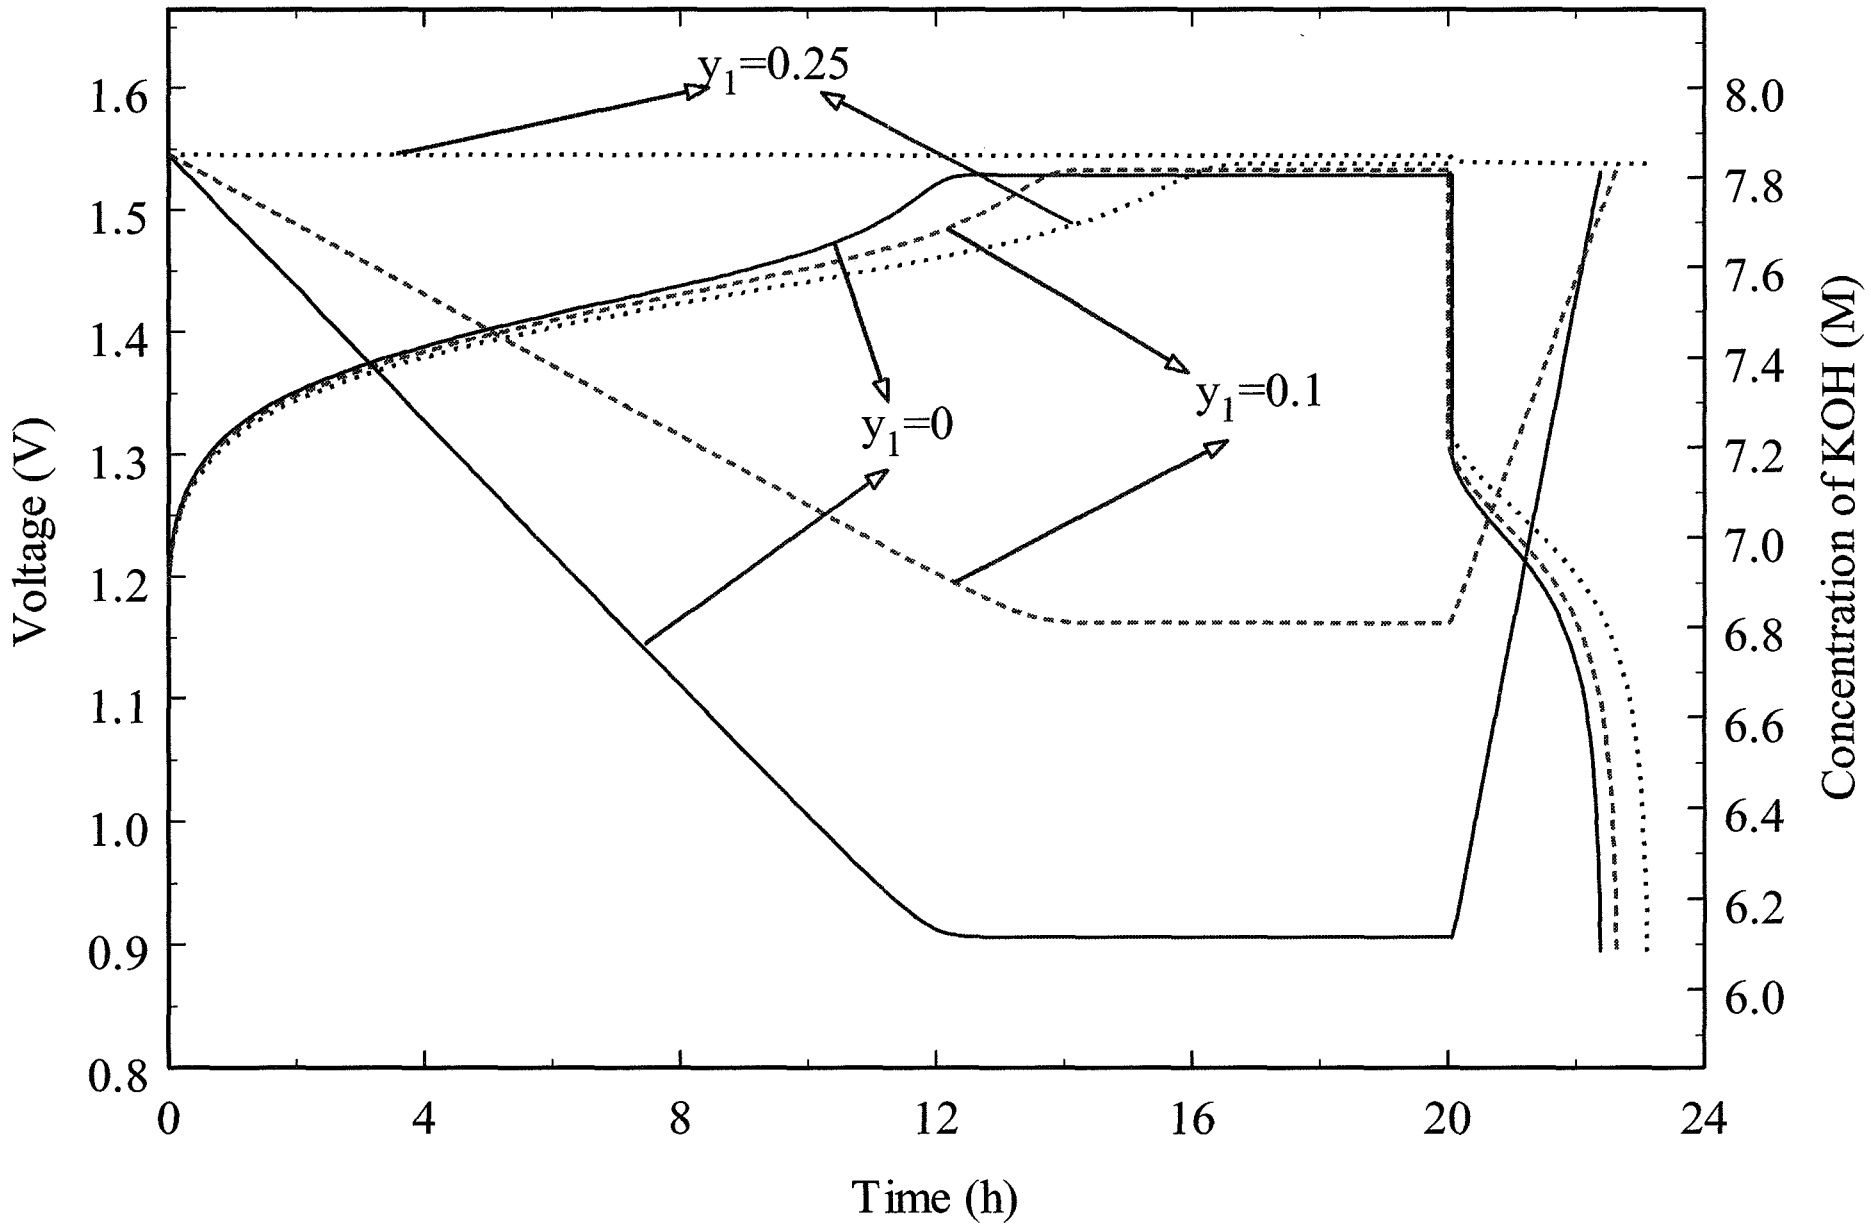

Simulated Capacity and KOH Concentration on Cycling

y_2=0.25→0.11

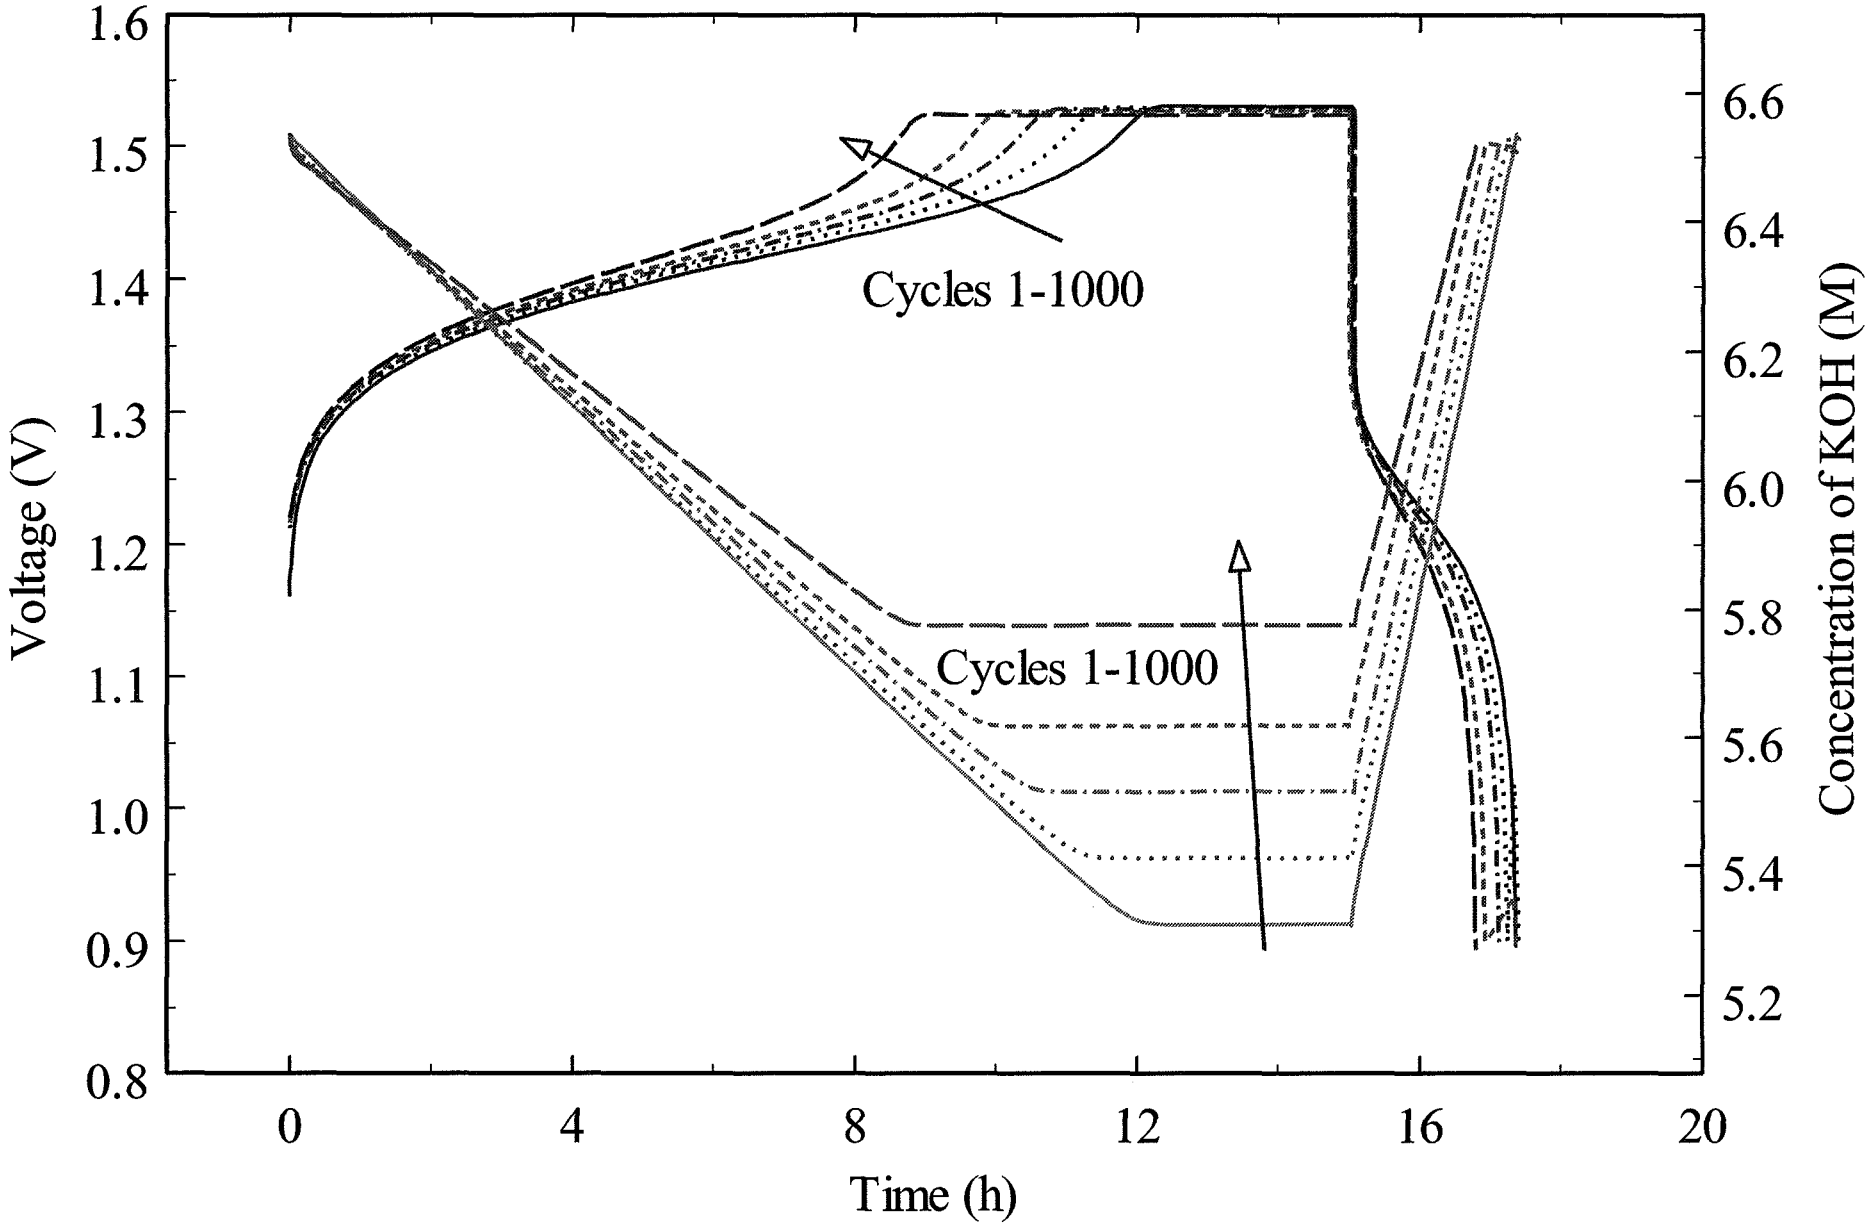

Comparison of Model Predicted Cell Potential with TRW Data

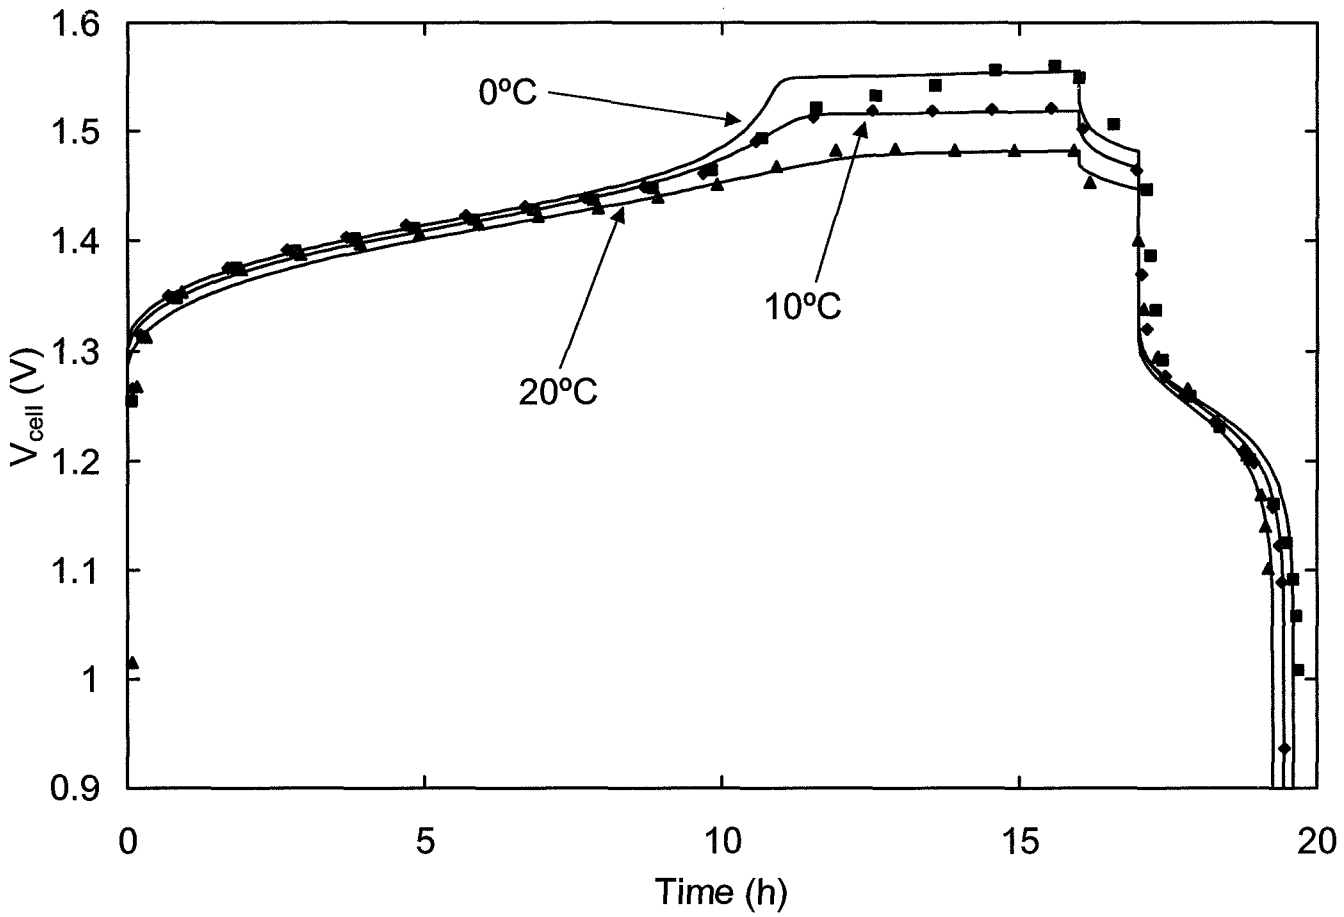

B. Wu and R. E. White, *J. Electrochem. Soc.*, in press (2000).

Comparison of Model Predicted Cell Temperature with TRW Data

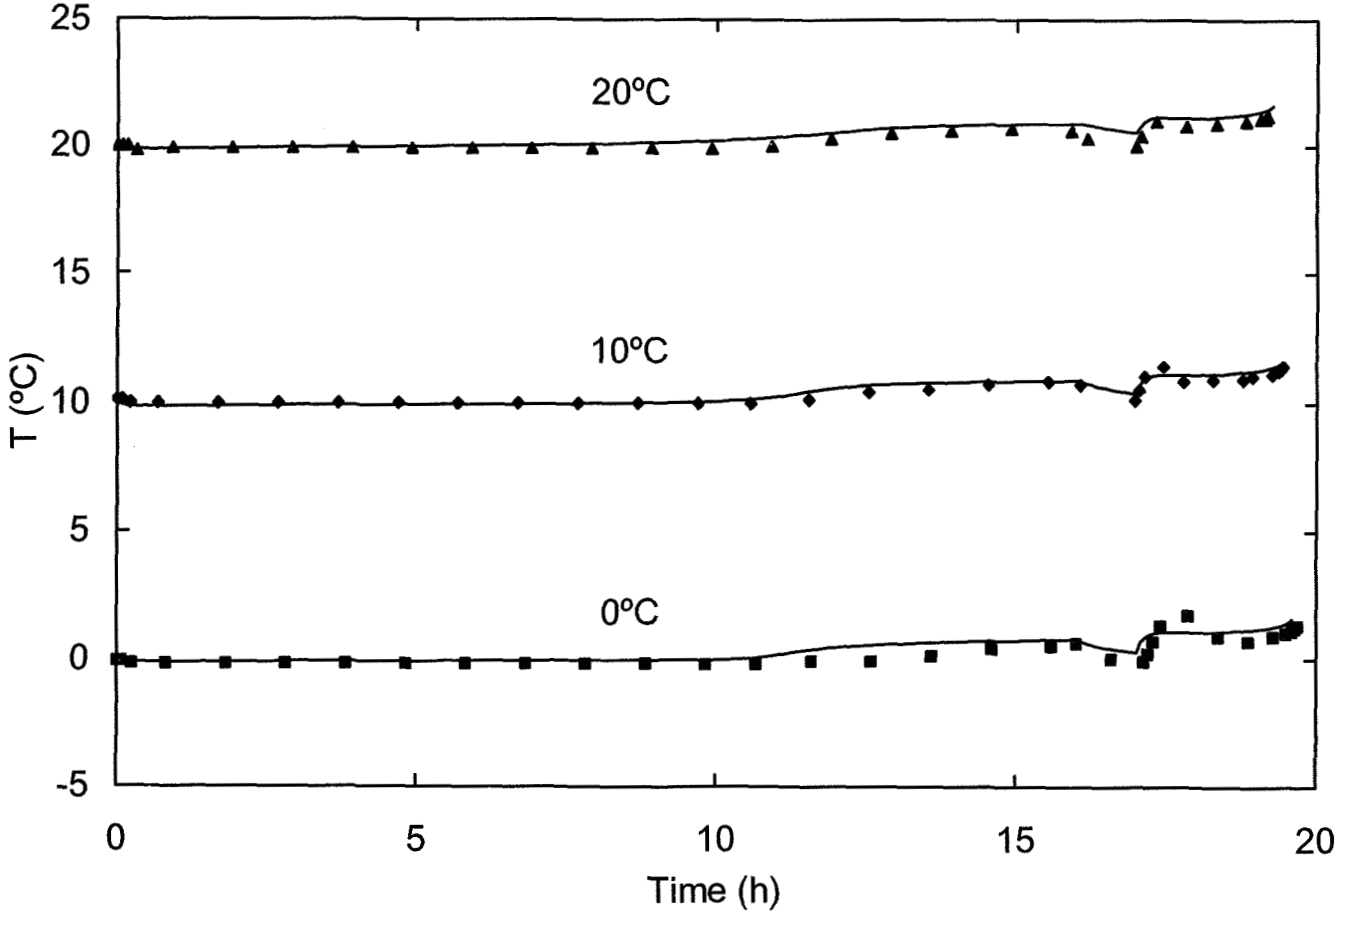

B. Wu and R. E. White, *J. Electrochem. Soc.*, in press (2000).

Comparison of Model Predicted Cell Pressure with TRW Data

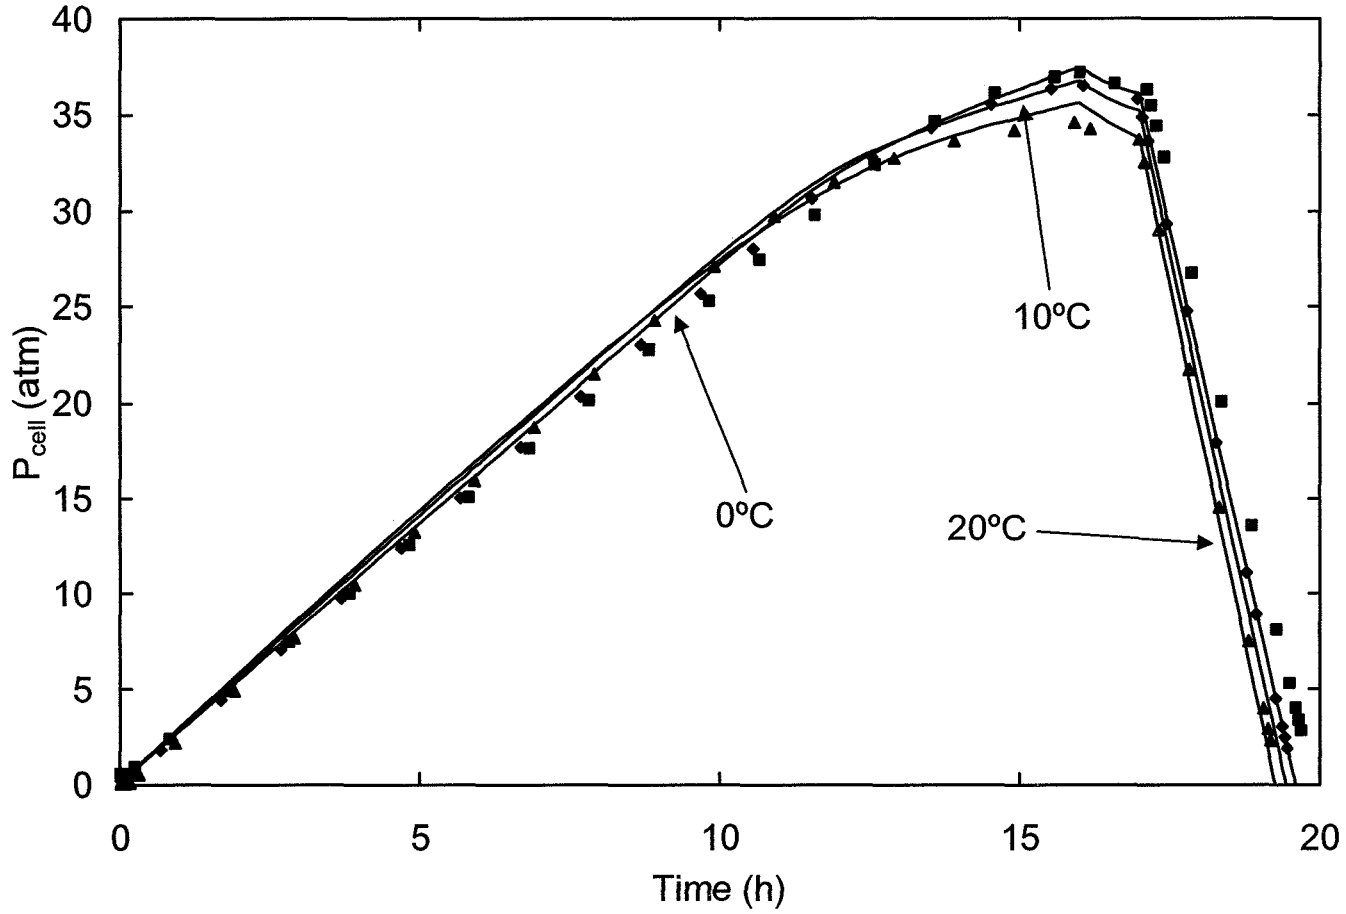

B. Wu and R. E. White, *J. Electrochem. Soc.*, in press (2000).

Experimental & Simulated Discharge Curves for a Li-Ion Cell with 1.25 M Initial Salt Concentration

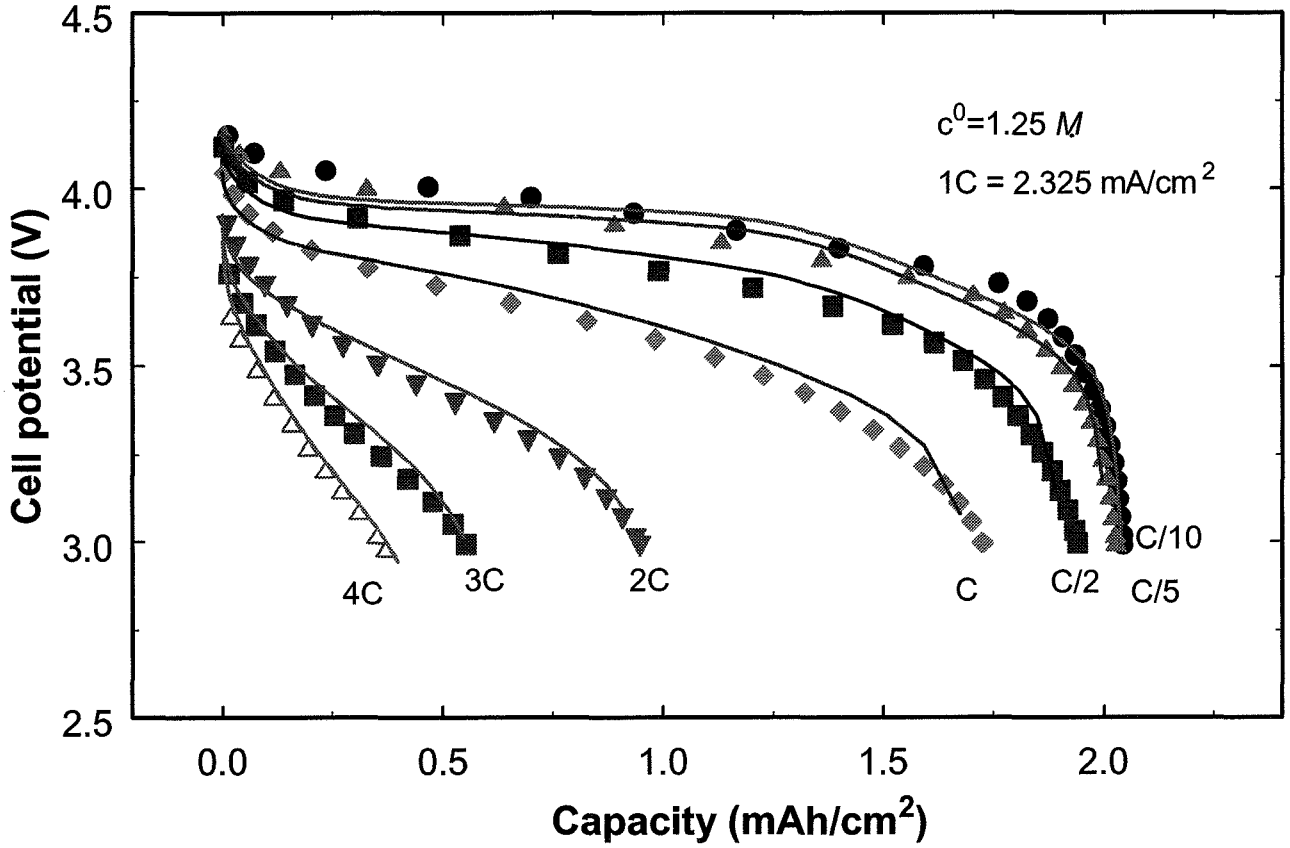

P. Arora, M. Doyle, A. S. Gozdz, R. E. White, and J. Newman, *J. Power Sources.*, **88**, 219-231 (2000).

Experimental & Simulated Discharge Curves for a Li-Ion Cell with 0.5 M Initial Salt Concentration

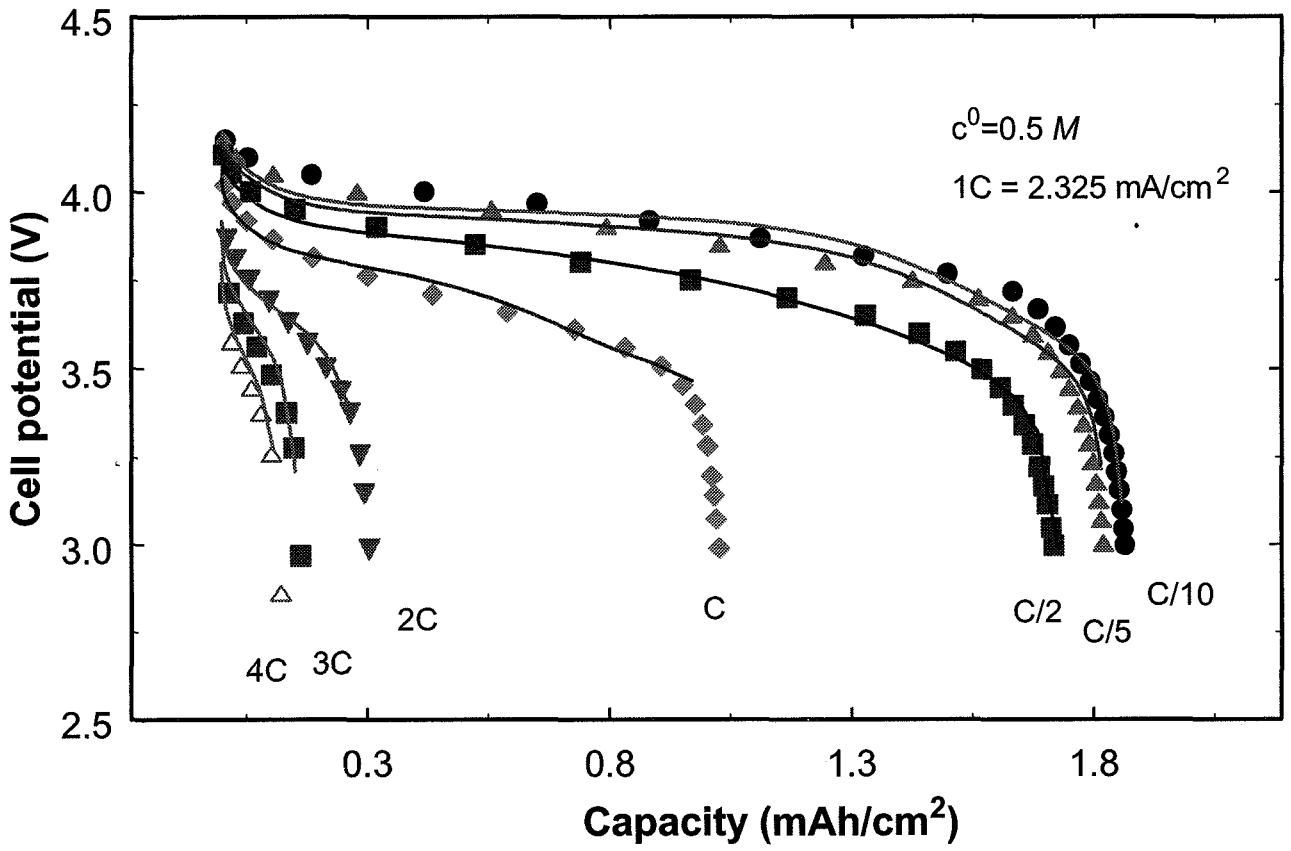

P. Arora, M. Doyle, A. S. Gozdz, R. E. White, and J. Newman, *J. Power Sources.*, **88**, 219-231 (2000).

Experimental & Simulated Discharge Curves for a Li-Ion Cell with 0.25 M Initial Salt Concentration

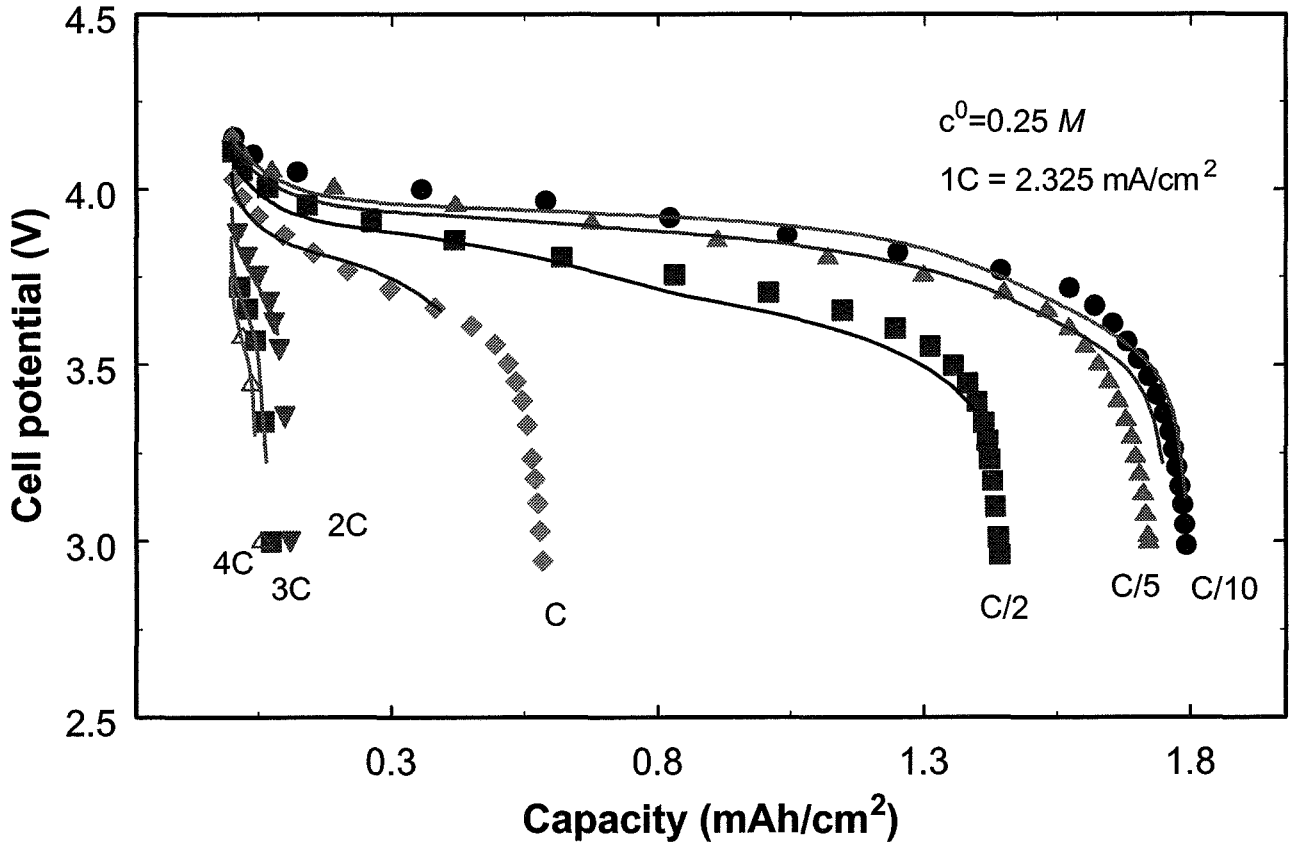

P. Arora, M. Doyle, A. S. Gozdz, R. E. White, and J. Newman, *J. Power Sources.*, **88**, 219-231 (2000).

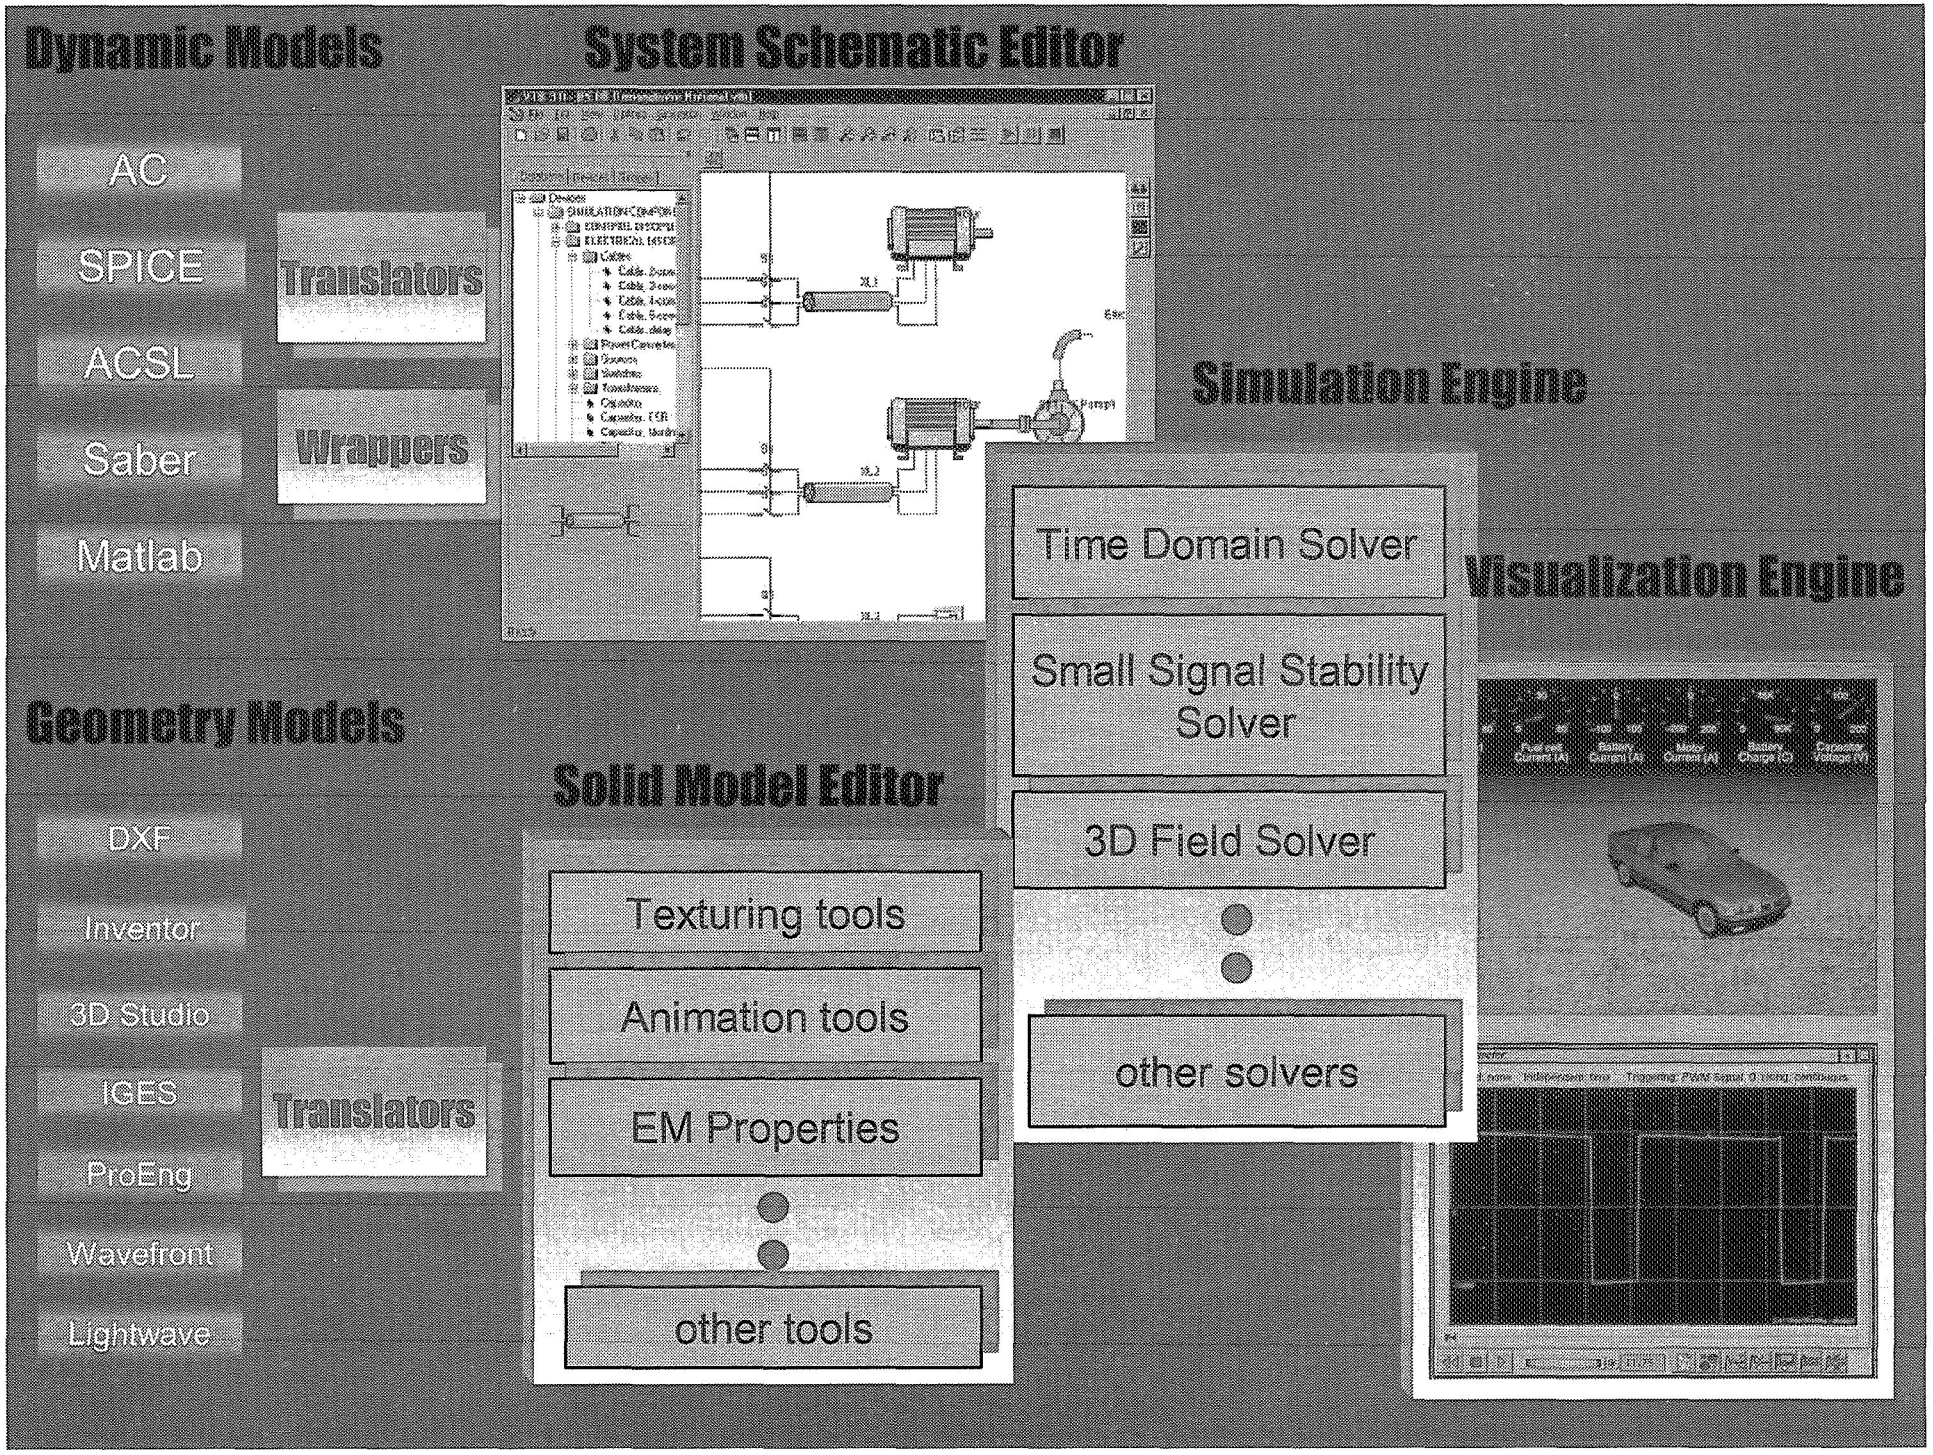
Dynamic Models
System Schematic Editor
AC
SPICE
ACSL
Saber
Matlab
Translators
Wrappers
Simulation Engine
Time Domain Solver
Small Signal Stability Solver
3D Field Solver
other solvers
Visualization Engine
Geometry Models
Solid Model Editor
DXF
Inventor
3D Studio
IGES
ProEng
Wavefront
Lightwave
Translators
Texturing tools
Animation tools
EM Properties
other tools

Project Objectives

"Investigate the optimal design of hybrid power systems for use in mobile systems."

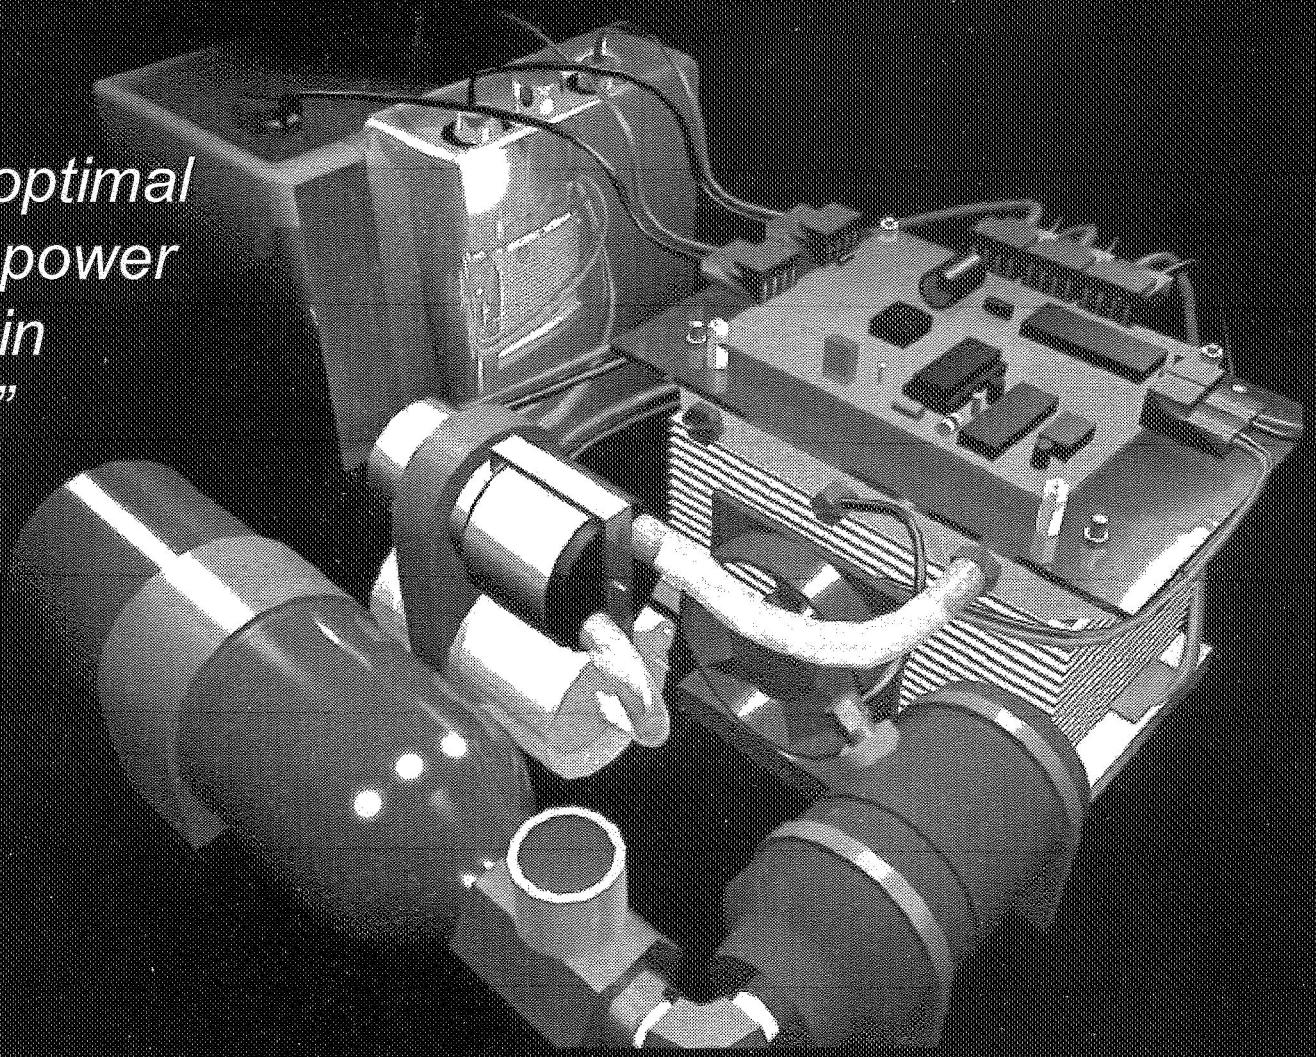

VTB supports analysis at the system level

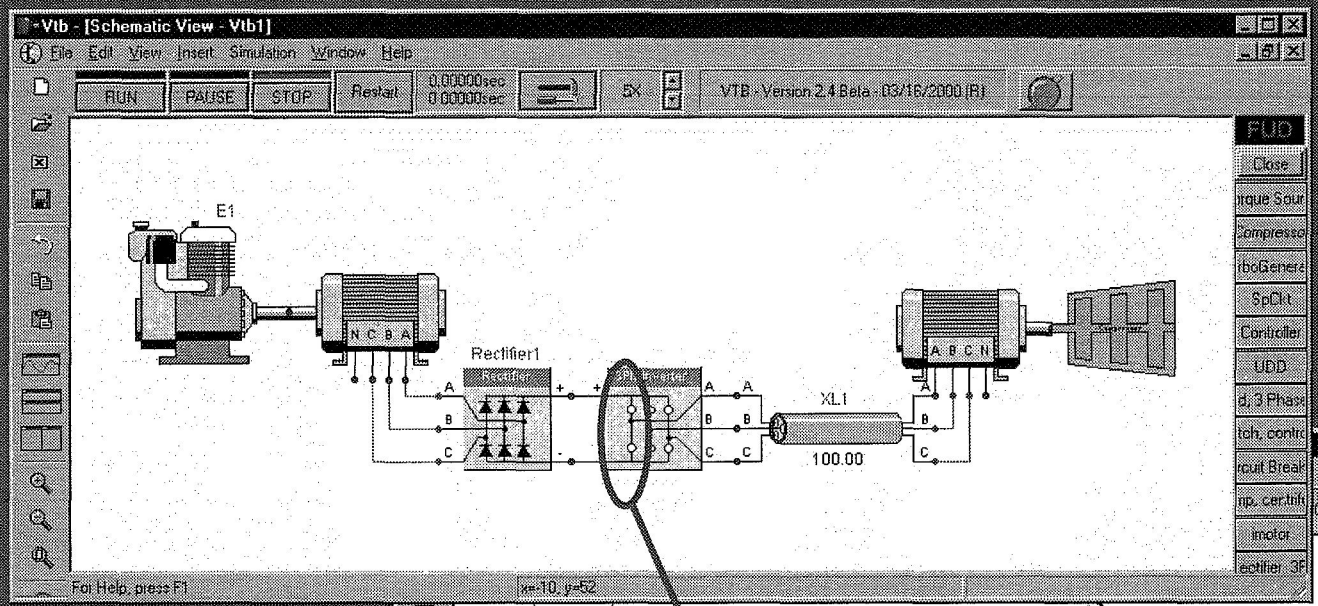

And at a detail level

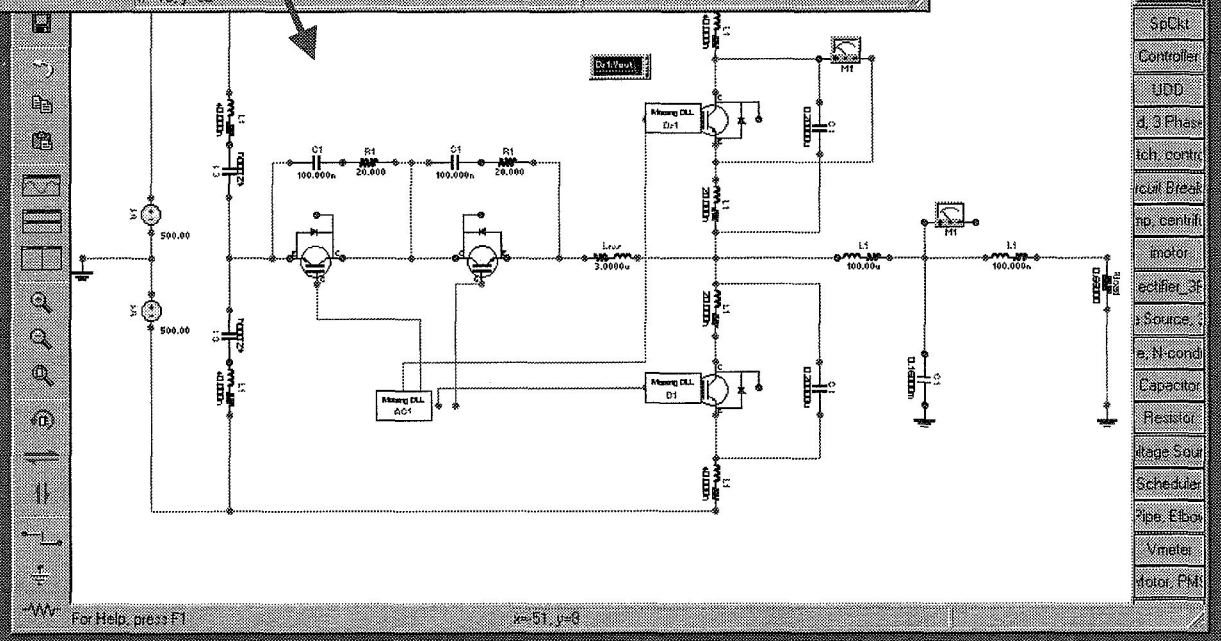

The VTB is a highly interactive environment for collaborative design and virtual prototyping of advanced power systems.

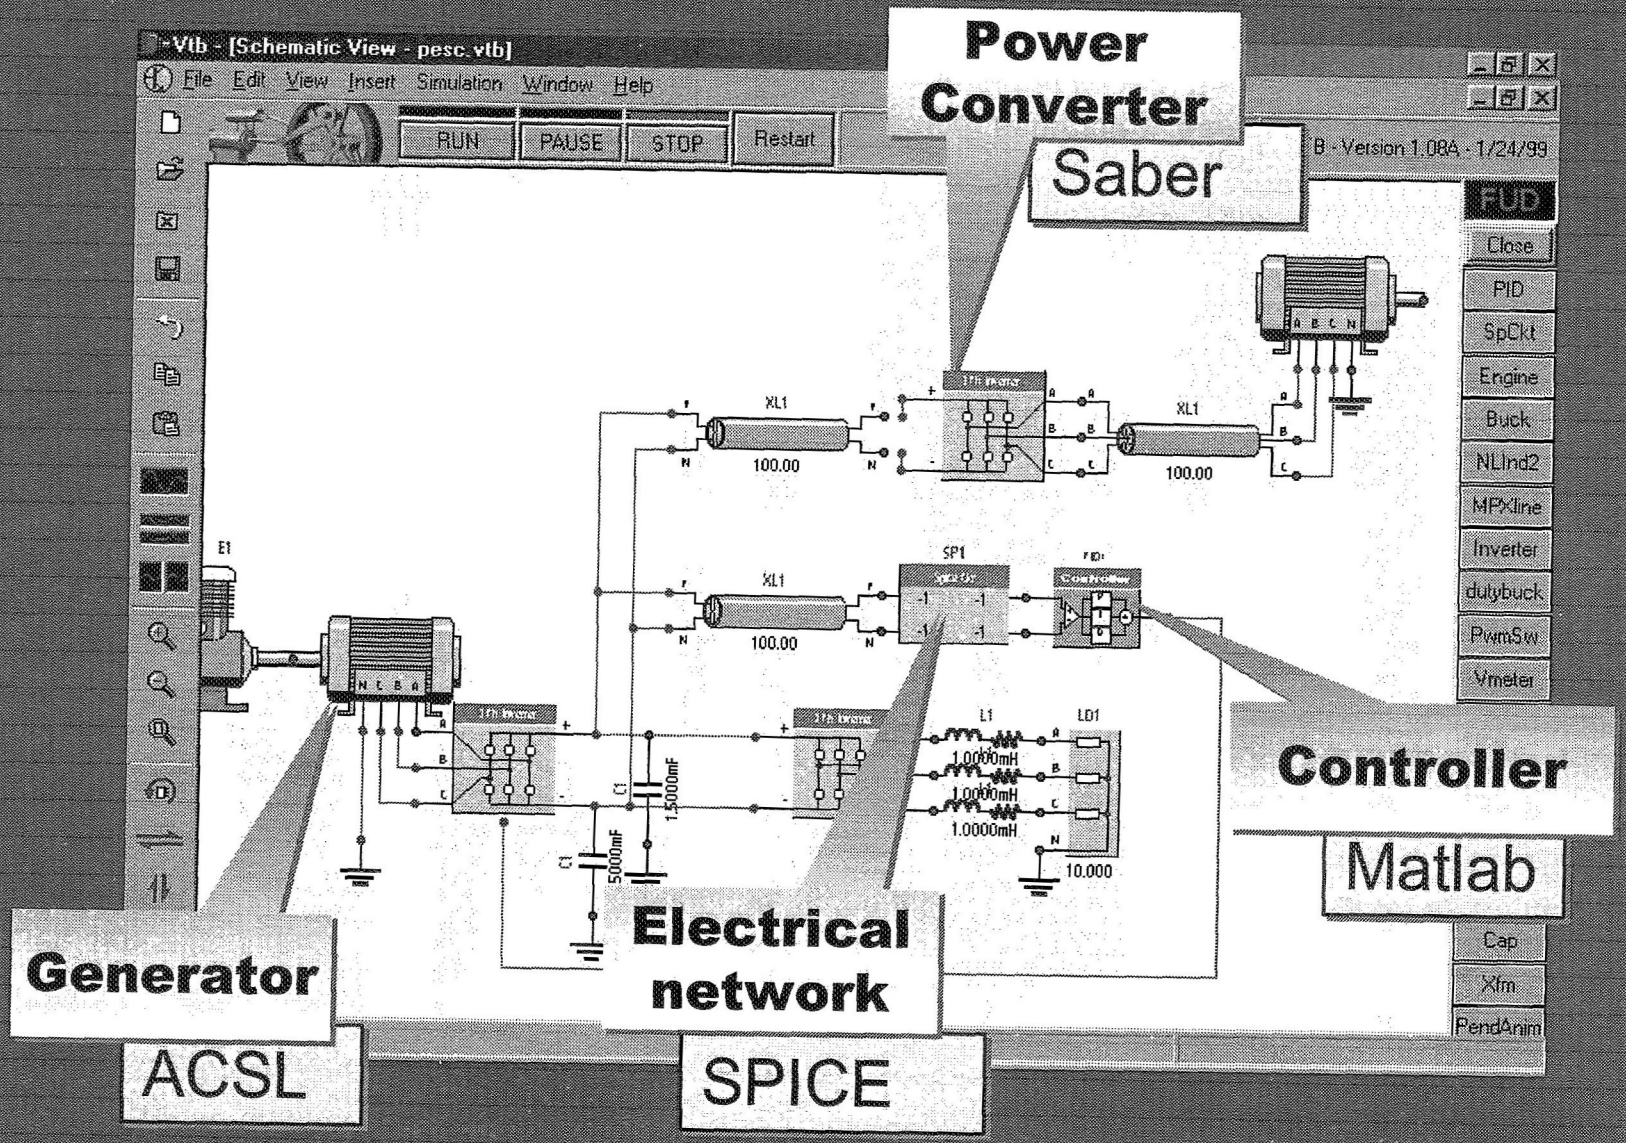

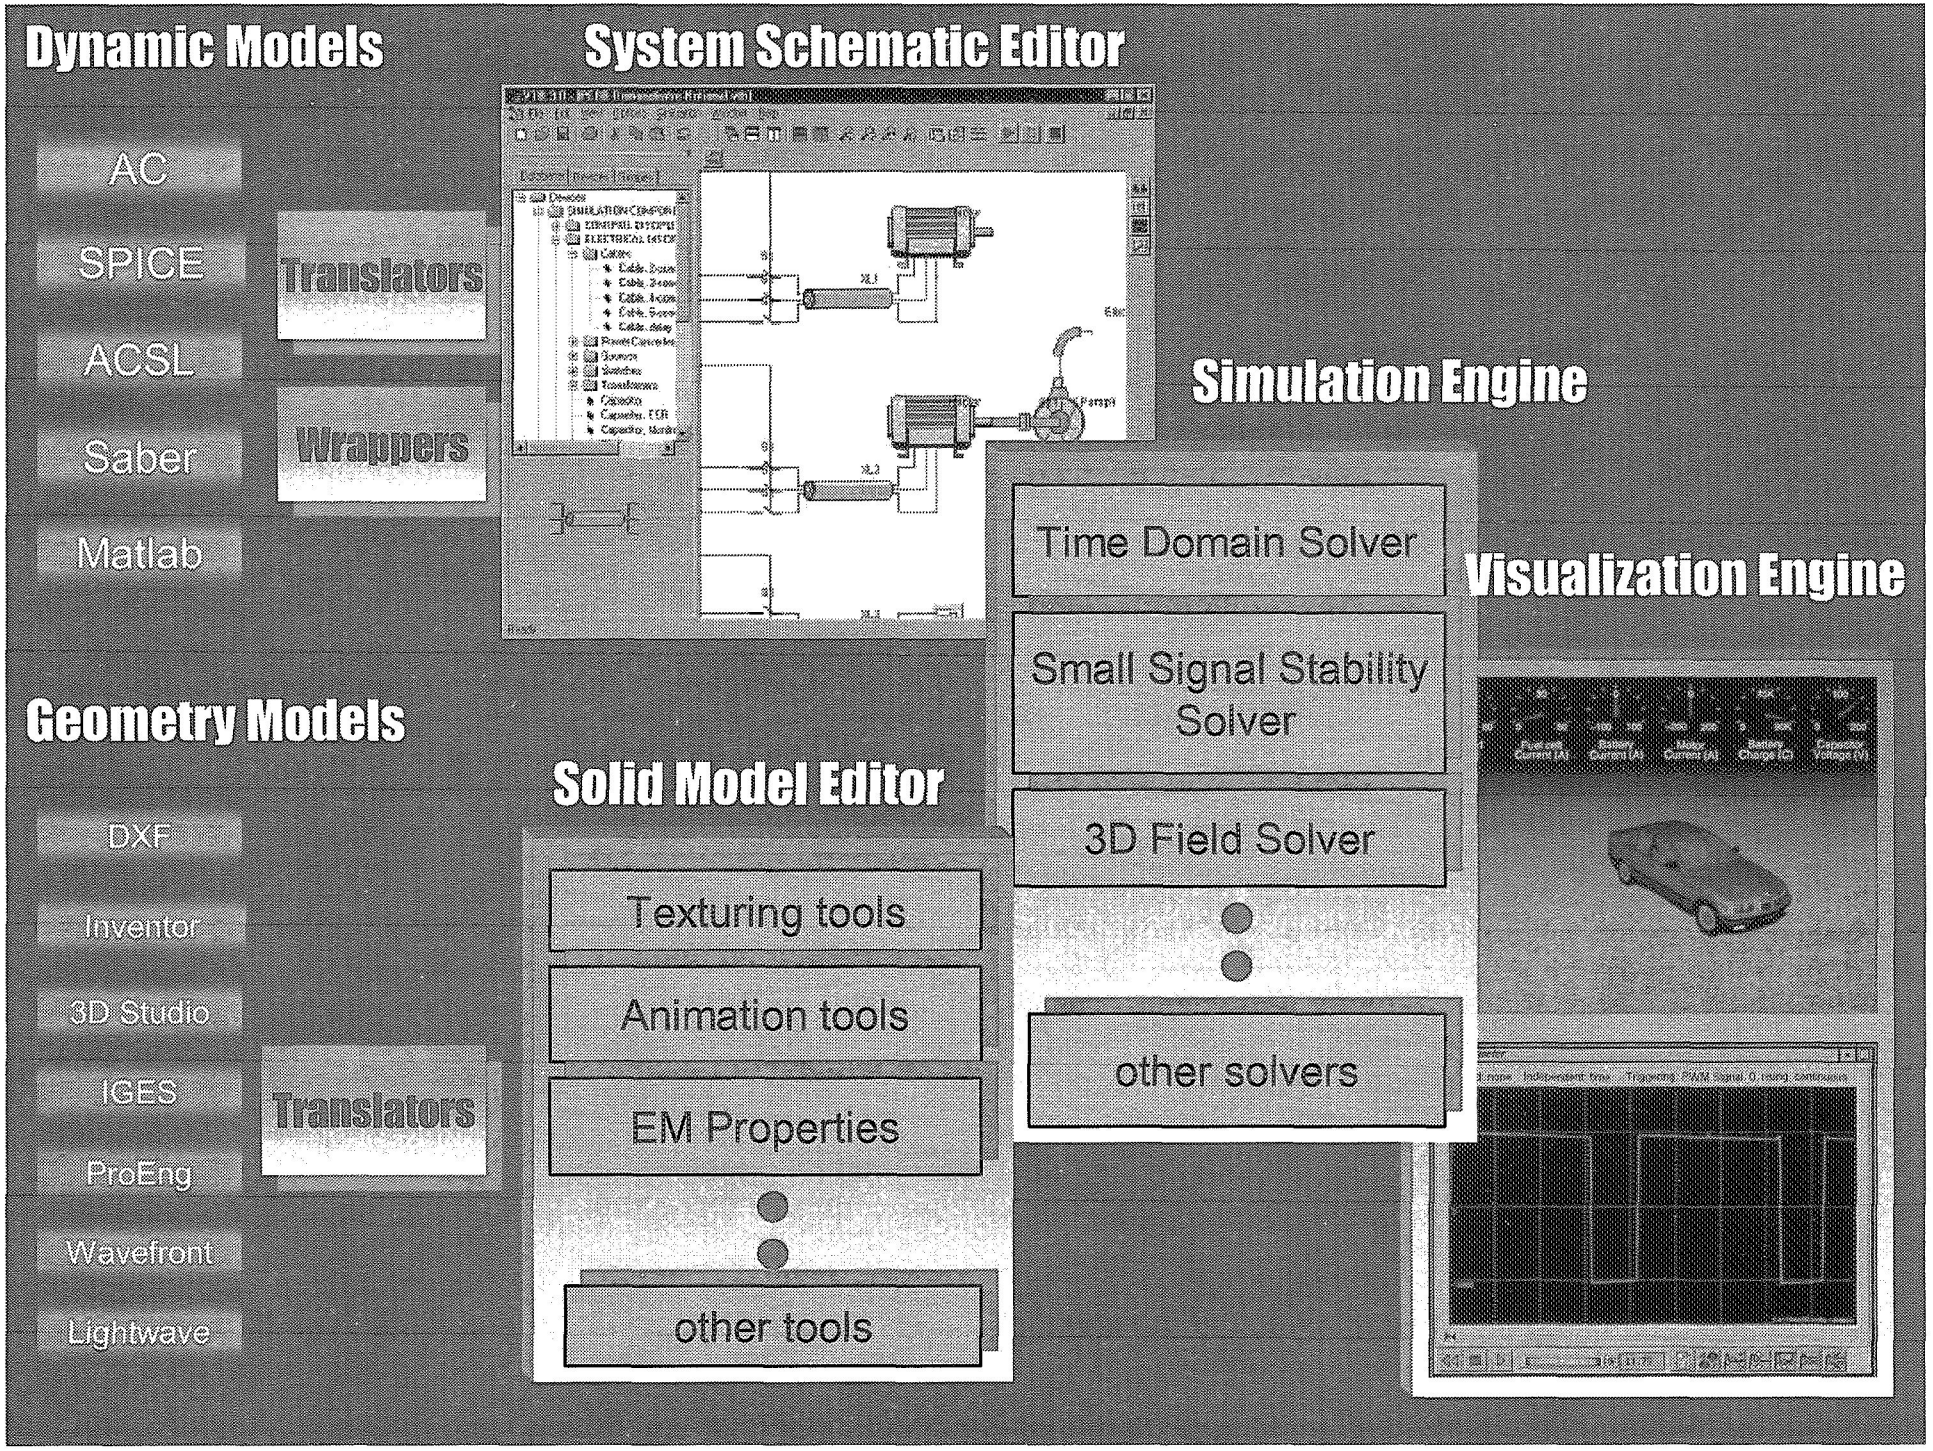
Dynamic Models
AC
SPICE
ACSL
Saber
Matlab
Translators
Wrappers
System Schematic Editor
Simulation Engine
Time Domain Solver
Small Signal Stability Solver
3D Field Solver
other solvers
Visualization Engine
Geometry Models
DXF
Inventor
3D Studio
IGES
ProEng
Wavefront
Lightwave
Translators
Solid Model Editor
Texturing tools
Animation tools
EM Properties
other tools

VTB facilitates interdisciplinary and distributed team work (and eliminates stovepipe work threading) by capturing and amplifying user knowledge at every step

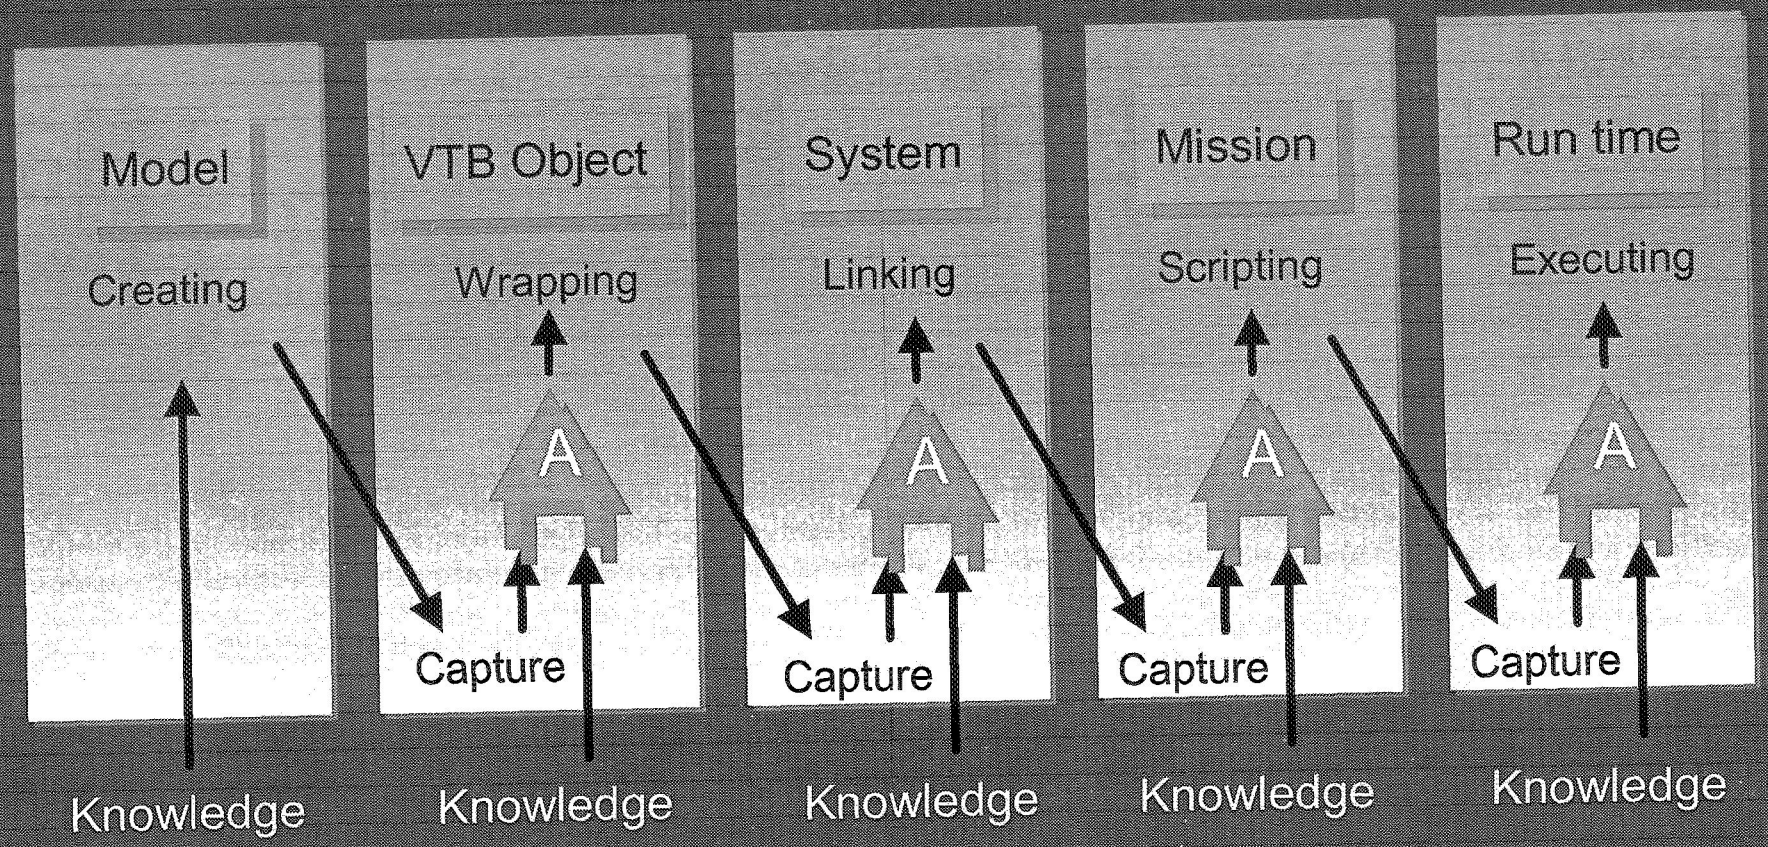

Collaborators

- Pankaj Arora
- Bahne Cornilsen
- Roger A. Dougal
- Marc Doyle
- Antoni S. Gozdz
- Sathya Motupally
- John Newman
- Venkat Srinivasan
- Christopher Streinz
- John W. Van Zee
- John W. Weidner
- Ralph E. White
- Bin Wu

57/CP/IN/44

2001117725

538014

10 p.s

Thermal and Cycle-Life Behavior of Commercial Li-ion and Li-Polymer Cells

Albert H. Zimmerman and M. V. Quinzio
Electronics and Photonics Laboratory
The Aerospace Corporation
El Segundo, California 20245

Abstract

Accelerated and real-time LEO cycle-life test data will be presented for a range of commercial Li-ion and Li-polymer (gel type) cells indicating the ranges of performance that can be obtained, and the performance screening tests that must be done to assure long life. The data show large performance variability between cells, as well as a highly variable degradation signature during non-cycling periods within the life tests. High-resolution Dynamic Calorimetry data will be presented showing the complex series of reactions occurring within these Li cells as they are cycled. Data will also be presented for cells being tested using an Adaptive Charge Control Algorithm (ACCA) that continuously adapts itself to changes in cell performance, operation, or environment to both find and maintain the optimum recharge over life. The ACCA has been used to prevent all unneeded overcharge for Li cells, NiCd cells and NiH_2 cells. While this is important for all these cell types, it is most critical for Li-ion cells, which are not designed with electrochemical tolerance for overcharge.

Introduction

The development of lithium-ion battery cells that are capable of long cycle-life for commercial applications has tempted satellite power-system engineers for years with the promise of smaller and lower weight battery systems. However, the accumulation of the performance history and databases necessary to assure high reliability over long-term space missions as well as the needed optimization of lithium-ion power systems, have made the anticipated transition to lithium-ion batteries in satellite systems quite slow. One of the leading satellite types expected to advantageously utilize lithium-ion technology is nanosatellites and picosatellites. These satellites are very small, typically in the 100g to 10 kg range. Because of their small size, very compact and lightweight batteries offer compelling advantages. Because of their relatively low cost and generally limited life requirements (1-3 years in low earth orbit is typical), commercial lithium-ion battery technology provides a promising power system option for these classes of satellites.

Here we will present performance data and thermal characteristics of selected commercial lithium-ion battery cells to illustrate some of the key advantages of these batteries for small satellites, as well as some of the issues that must be handled to reliably integrate these batteries into a successful power system.

Cycle-Life Measurements

The cycle life of a lithium-ion battery must be adequate to support worst-case mission needs with sufficient margin to assure high reliability when cell performance

variability is considered. One issue that has been noted for lithium-ion battery cells is that cycle life performance can be highly variable, depending on the details of how cells are built and how they are tested. It should be pointed out that this experience matches that obtained early in the use of nickel cadmium and nickel hydrogen cells, where large variability in performance taught many lessons related to cell design and charge management practices. Given this situation, it is key to the use of lithium-ion batteries that appropriate test and screening regimens be developed to assure that all cells selected for satellite use will perform well with the anticipated charge control system. To this end we have developed an accelerated cycling test that will rapidly indicate the cycle-life capability of lithium-ion battery cells.

A key difficulty in assessing the cycle-life capability of lithium-ion cells is the strong coupling between cycle life and both charge-management and operational temperature. This kind of coupling is not really surprising, since it has also been found to be the rule for other kinds of battery cells, most notably nickel cadmium and nickel hydrogen. As for these other types of battery cells, databases must be developed that show precisely how temperature and different charge management variations affect cycle-life. To help gather such data we have developed a simple accelerated life test protocol that is based on a simple doubling of the cycle-times normally associated with low-earth-orbits. This test employs a 45-minute cycle consisting of 15 minutes for discharge and 30 minutes for recharge, and operates the cells at 20% depth-of-discharge (DOD). Recharge is at a C/2 rate, with a constant voltage limit of 4.0 or 4.1 volts, and test temperature is 20 deg C. Thus, this test applies the currents normally anticipated at 40% DOD in a standard 90-minute LEO cycle. The test is therefore very sensitive to the increases in resistance that have often been seen to accompany or forewarn premature cell degradation, while allowing a x2 acceleration factor in cycle numbers. Whether this acceleration factor of 2 applies to standard LEO orbital usage remains to be debated, and ultimately will be established based on the test data.

This accelerated life test has been applied to a range of commercial Li-ion cells to determine anticipated performance. Figure 1 shows the relative cycle life performance of two types of SONY 18650 cells. Cell type A was acquired in 1994 and remained stored in the laboratory until 1999, when the cells were put on test. Cell type B was acquired in 1999 and immediately put on test. These two types of cells reflect the changes in cell design over a 5-year period for SONY. It should be noted that the type B cells had at least a 10% greater beginning-of-life capacity relative to the type A cells. These cells are being tested at a 1.5 Ah nameplate capacity and recharge is to a 4.1-volt limit.

There are several noteworthy results in Figure 1. First, after about 16,000 cycles of testing, it has become clear that both the type A and the type B cells are capable of a very long cycle life. Extrapolation of the observed degradation slopes yields a cycle life in excess of 50,000 for all these cells. The other noteworthy result is that the degradation rate for the newer type B cells is about twice that of the older Type A cells, in spite of the greater capacity in the newer cells. This was expected, and is at least partially a result of the utilization of a graphitic carbon in the anodes of the newer cell design, thus providing higher voltage and capacity at the cost of more rapid degradation of the highly ordered graphite structure. These results, however, clearly demonstrate that it is important to routinely screen the performance of each lot of commercial cells acquired for space use so that such changes in design or performance will be detected prior to flight.

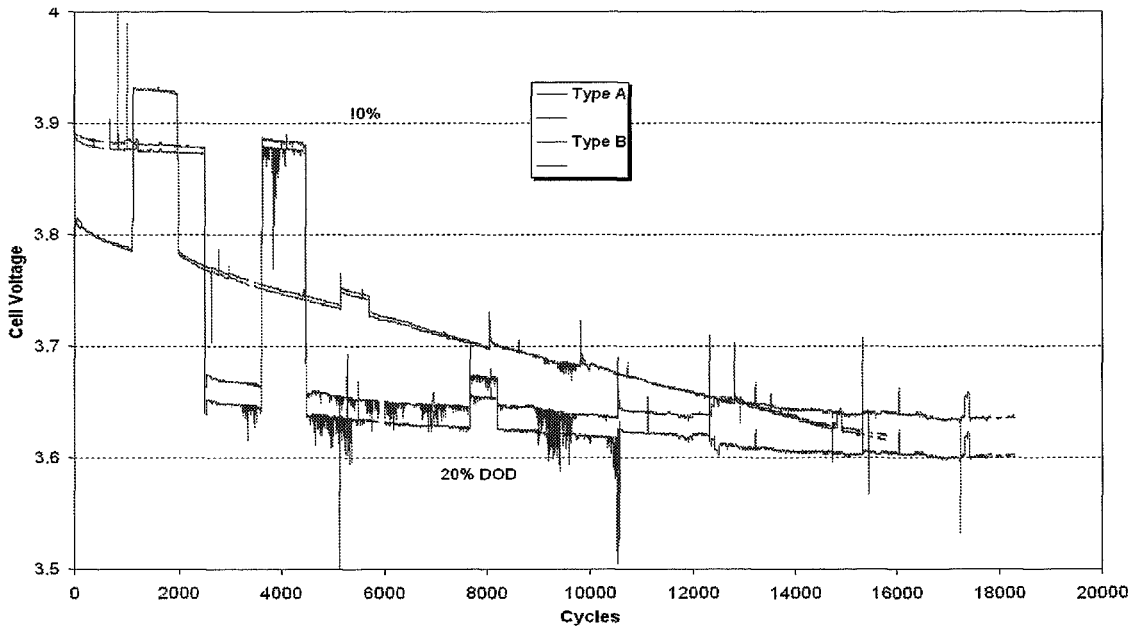

Figure 1. Comparison of Accelerated Cycling Performance for Type A and Type B SONY 18650 Cells.

The need for cell screening can be made dramatically clear by the results in Figure 2, which shows the relative performance obtained for cells from two different lots of cells that were built about 2 months apart. These are lithium-polymer cells, which are of significant interest in nanosatellites because they can be sandwiched into the satellite

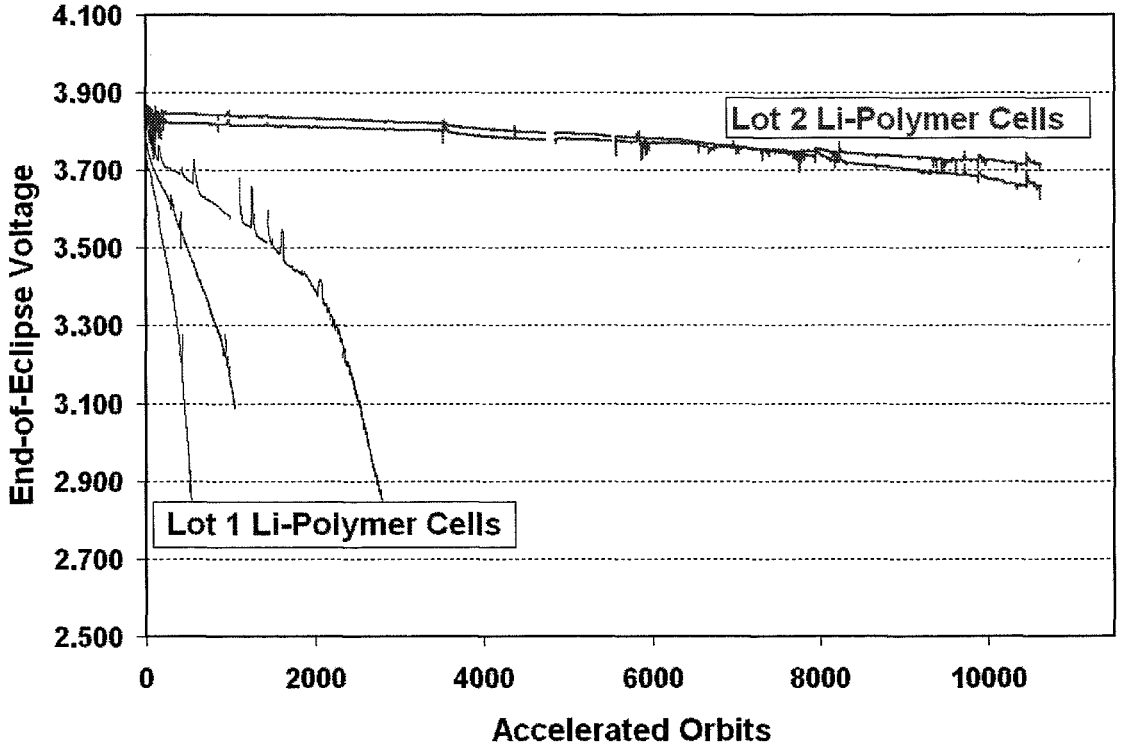

Figure 2. Relative Accelerated Test Performance of Two Lots of Li-Polymer Cells.

structure much more easily than the cylindrical 18650 cells. As noted in Figure 2, cells from the first lot operated only 1000 to 3000 cycles before failing, while cells from the second lot operated 15,000 cycles.

The issue of optimum charge control for lithium-ion cells is an area that has not been fully resolved. As indicated in Figure 1, simple recharge to 4.1 volts each cycle, then allowing the current to taper at the 4.1-volt limit can be very effective. However, the optimum recharge voltage level may not always be 4.1 volts. It may vary with the cell design, temperature, electrode degradation over life, recharge rates, or a variety of other parameters. One indication that this is indeed the case is shown in Figure 3, where the performance of four 1.5 Ah lithium polymer cells from the same build lot is indicated. Two of these cells were cycled with a 4.1-volt recharge limit and the other two were cycled with a 4.0-volt limit. The cells cycled to 4.1 volts started out with a much higher discharge voltage, however they did settle in on a more rapidly dropping voltage as cycling progressed. The cells cycled to 4.1 volts also developed a downwards curve to their end-of-discharge voltage that ultimately made them fail long before the cells that were only being recharged to 4.0 volts. It is noteworthy that the cells cycled to 4.0 volts have degraded with a slow linear slope to the end-of-discharge voltage, thus not displaying any tendency to develop a curving down drop-off.

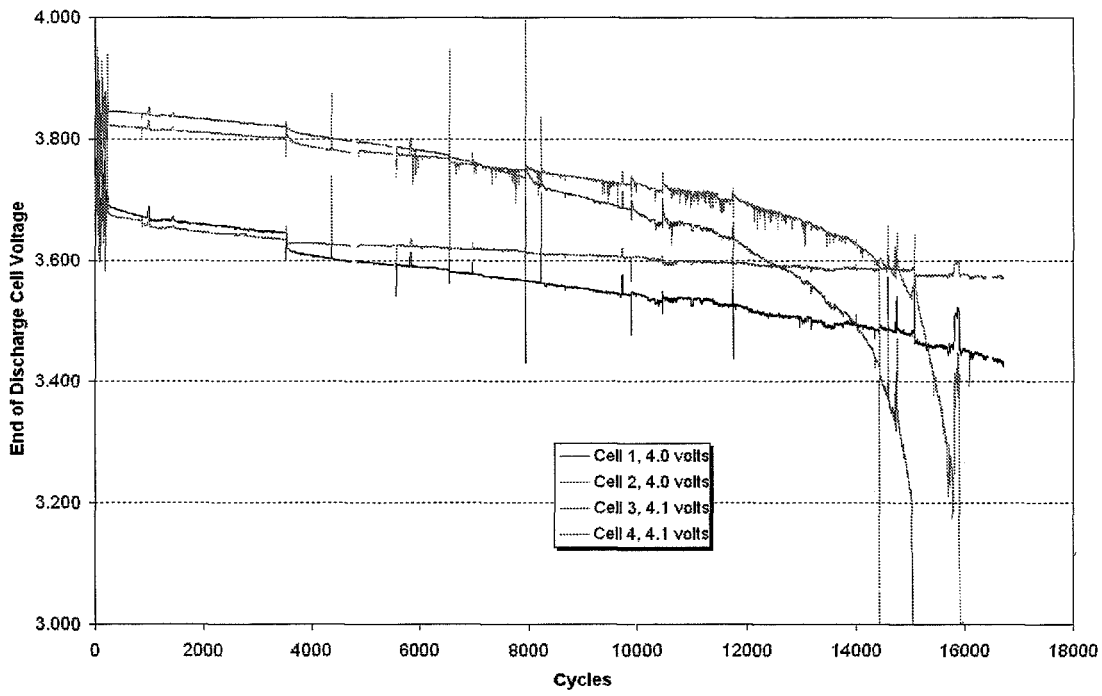

Figure 3. Relative Performance of Lithium-Polymer Cells Charged to Different Voltage Limits.

The results in Figure 3 can be interpreted to suggest a different failure mode coming into play when these cells were cycled to 4.1 volts, which was not the main degradation mode at a recharge limit of 4.0 volts. One suggestion is that the rapid and curving drop-off in end-of-discharge voltage is due to capacity loss, which was significantly accelerated by recharge to the higher voltage. This rapid and curving drop-

off is superimposed on a more linear drop-off that is due to increases in the impedance of the electrodes and electrolyte as the cells are cycled. For the cells cycled to 4.0 volts, the increasing impedance of the cells appears to be the dominant degradation mode, explaining why no tendency has yet been seen for the end-of-discharge voltage to curve downwards. These results clearly suggest that limiting the added degradation mode at the higher voltages for these cells can significantly increase their expected performance life and reliability in a satellite power system, at the cost of some lesser performance at beginning of life.

The data in Figure 3 also show another potential issue with lithium ion cells. At about cycle 3500, a two-week test shutdown occurred due to the failure of some test equipment. During these two weeks the cells were left in the fully charged state (either at 4.0 or 4.1 volts). When the cycling resumed, all the cells adopted an increased degradation rate, except one of the cells being charged to 4.0 volts. In addition several of the cells displayed a step decrease in the end-of-discharge voltage in response to simply standing open circuited for two weeks in the fully charged state. Both the variability in how this stand period impacted the cells, as well as the performance loss itself are a significant concern. These results indicate that cells should be maintained at a less than fully charged state during known periods where no cycling or very shallow cycling is required. This is a charge management capability that must be built into the satellite power system, since in many low-earth-orbits there are sometimes periods of up to several weeks when no battery cycling is required.

The accelerated testing that has been done on a wide range of lithium-ion and lithium polymer cells suggests that the initial downward slope in the end-of-discharge voltage is a good relative indication of degradation rate and ultimate cycle life. If we examine the slope over the first 2500 cycles of test, those cells that failed most rapidly always had a higher slope. While simple extrapolation of slopes to a failure point could be deceiving due to the accelerating drop-off for some cells, in all cases these cells had a higher early slope than did cells that did not exhibit downwards curvature towards end-of-life. Thus, we propose a 2500-cycle accelerated screening test be performed on a sampling of commercial cells from each lot intended for use in satellites. While this test can be performed at any temperature, we recommend 20 deg C as a good standard temperature. The charge voltage limit for this test should be based on that anticipated in the power system, but based on our data a 4.0-volt limit is recommended.

Dynamic Calorimetry Results

The heat generation from lithium-ion cells is important both for designing a thermal control system that can adequately handle the end-of-life thermal environment, and for observing the electrochemical processes within an operating cell. The voltage of a lithium-ion cell typically does not clearly show steps and plateaus corresponding to the changing processes in the cell. However, the thermal behavior of a cell is capable of separating quite subtle changes in the cell reaction processes. Heat generation from lithium cells was measured here using dynamic calorimetry. This technique provides accurate heat generation rates or rapidly changing systems, and thus is applicable during high rate charge or discharge. Heat generation is sensed by the response of tiny thermistors attached to the sides of a cell. The cell is immersed in a fluid bath that is held at a constant temperature (to ± 0.0002 deg C), and heat generation is determined from the

response of the thermistors which respond to the small region of the cell wall to which they are attached. Typical maximum thermal excursions for these thermistors are about 0.1 deg C for 1.5 Ah lithium-ion cells. This heat measurement system is calibrated by balancing electrical and thermal energy over a complete stabilized charge/discharge cycle, and typically has a thermal time constant of only several seconds.

Figure 4 shows a typical charge and discharge voltage, which has a number of subtle inflections during recharge and discharge, but no clear indication of changing electrochemistry as the cell is cycled. Figure 5 shows how the heat generation from a 1.5 Ah lithium-polymer cell varies during charge and discharge at 20 deg C, and compares

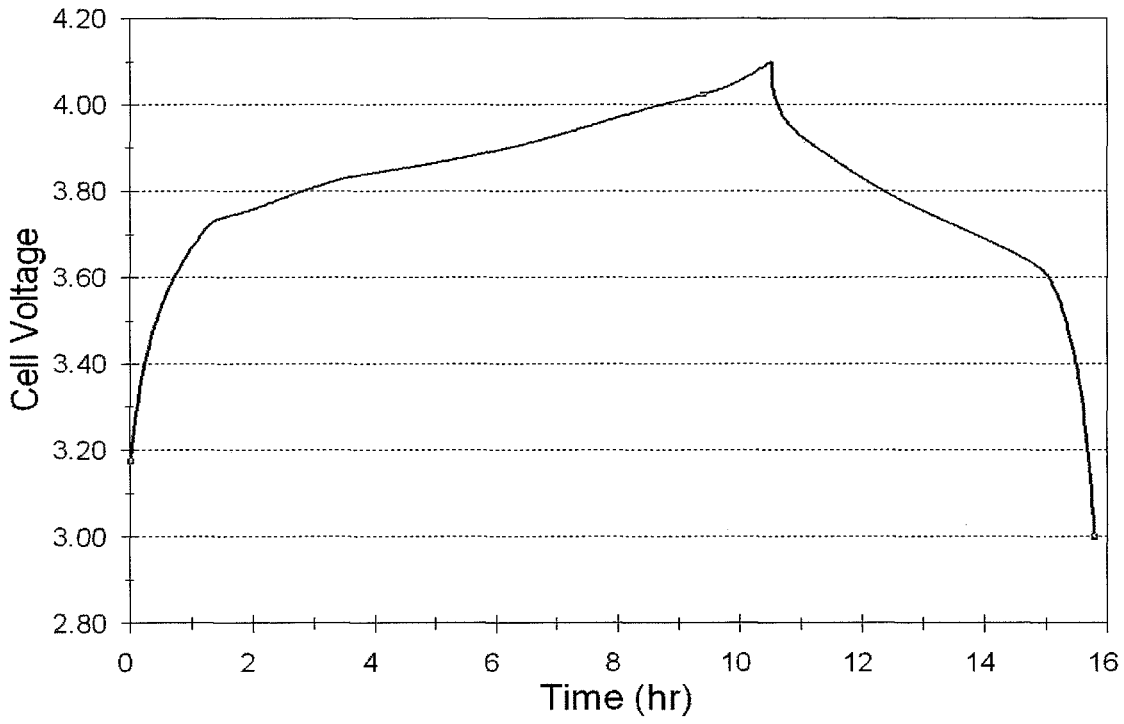

Figure 4. Typical Charge and Discharge Voltage for a Lithium-Polymer Cell.

the heat generation to the voltage profile. There are clearly a number of step changes in the heat production by this cell as it goes through several endothermic processes at the start of recharge, followed by several exothermic processes. All of these processes appear to be fully reversible, i.e. they appear during discharge as well as during recharge with the exception of the exothermic spike seen at the start of recharge. This exothermic spike is always seen for this particular type of cell, suggesting that some reactive material has been formed during recharge that is initially discharged. While this raises some concern regarding cycle life for this cell design, cells that are on test appear to be capable of about a 20,000 cycle life at 20% DOD.

The thermoneutral voltage of the cell may be determined during charge and discharge from the heat generation data. The thermoneutral voltage is the voltage at which no heat is generated during charge or discharge. Figure 6 indicates the thermoneutral voltage along with the cell voltage for a 1.5 Ah lithium-polymer cell. There are clearly a number of staging processes taking place during intercalation as the

cell charges and discharges, and which correspond to the changes in heat generation seen in Figure 5.

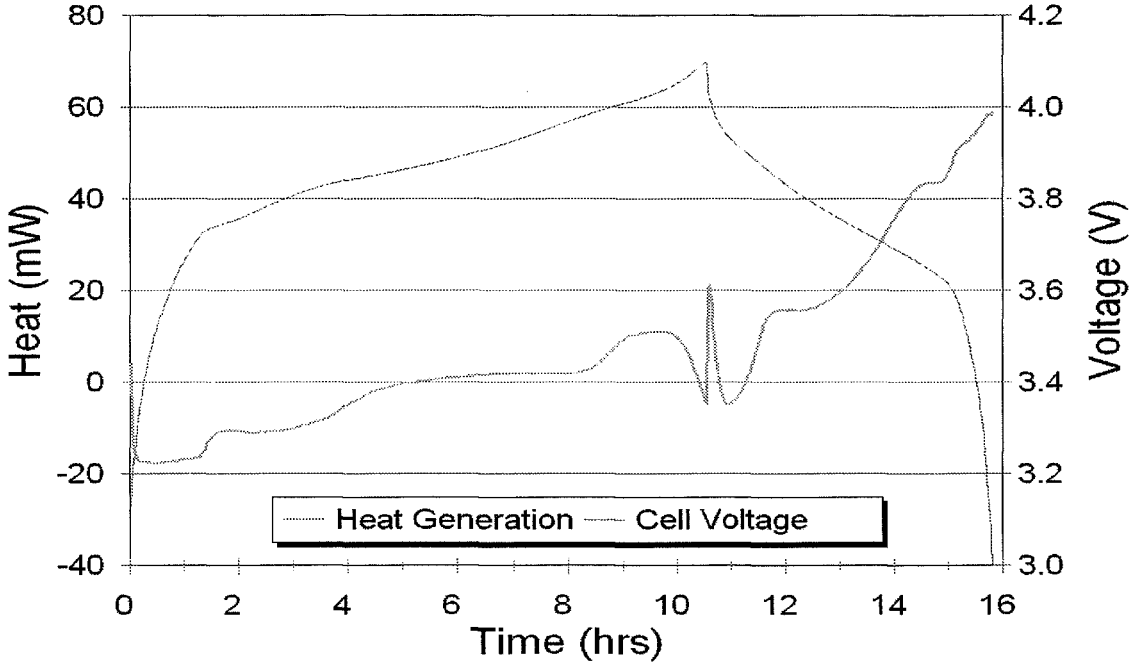

Figure 5. Lithium-Polymer Cell Heat Production during Charge and Discharge.

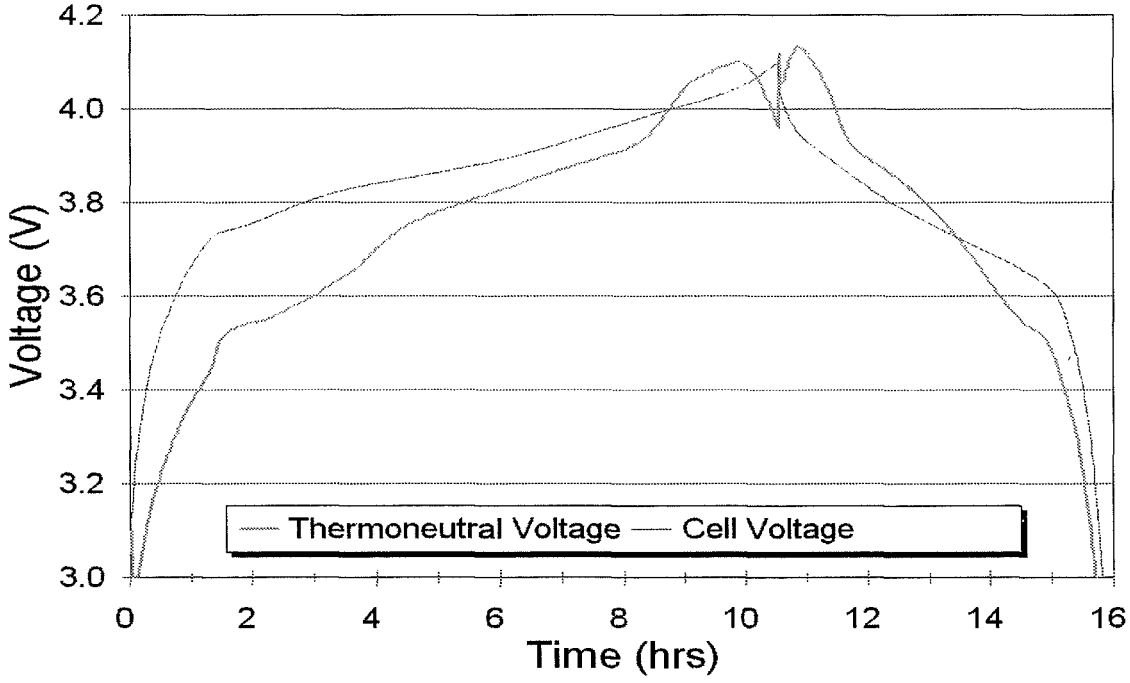

Figure 6. Lithium Polymer Cell Voltage and Thermoneutral Potential during Charge and Discharge.

Adaptive Charge Control Algorithm

The long-term performance of most rechargeable batteries is degraded by unnecessary overcharge. While nickel cadmium and nickel hydrogen cells can tolerate overcharge, any overcharge that is not needed to maintain the state-of-charge does indeed tend to diminish cycle life. Lithium-ion cells have no internal mechanism to allow them to tolerate overcharge, thus any overcharge not needed to keep them charged adequately should be avoided if long cycle life is required. We have developed an adaptive charge control algorithm that applies recharge based on keeping track of recharge ratio, and which continuously adjusts the applied recharge ratio to prevent any overcharge that is not needed to maintain the state of charge. This algorithm automatically adjusts for inaccuracies in the recharge ratio measurement, for temperature variations, electrode or cell degradation, as well as current or DOD changes. In this way this algorithm seeks to prevent any unneeded overcharge over cycle life, which should optimize the cycle life from a given lithium-ion cell design.

Figure 7 indicates a test of this algorithm on a pair of NiCd cells. The algorithm required about 550 cycles to adapt itself to the needs of a NiCd cell, settling out with a recharge ratio of about 101% in this 20% DOD test. Figure 8 indicates another test of this algorithm for a 0.75 Ah commercial lithium-ion cell pair operated in a thermal vacuum environment that simulated low-earth orbit operation at 20% DOD. These cells operated for over 2200 cycles with little evidence of significant degradation. The dithering of the voltages in Figure 8 is due to the continuous adjustments in the cell recharge as the adaptive algorithm verifies that it is maintaining the optimum recharge conditions. Figure 9 shows a similar simulated low-earth orbit test of two 1.5 Ah lithium-polymer cells in a nanosatellite mass simulator operated in a thermal vacuum chamber. In Figure 9 we again see the dithering as the algorithm continuously adjusts the amount of recharge applied to the cells, which is controlled on an independent cell basis. These two cells do show some evidence of degradation after about 3000 cycles, which is recognized by the gradual decrease in the average end-of-discharge voltage and increase in the end-of-charge voltage. In this test the end of life will occur when the average end of discharge voltage reaches 3.0 volts and the peak recharge voltage reaches 4.1 volts.

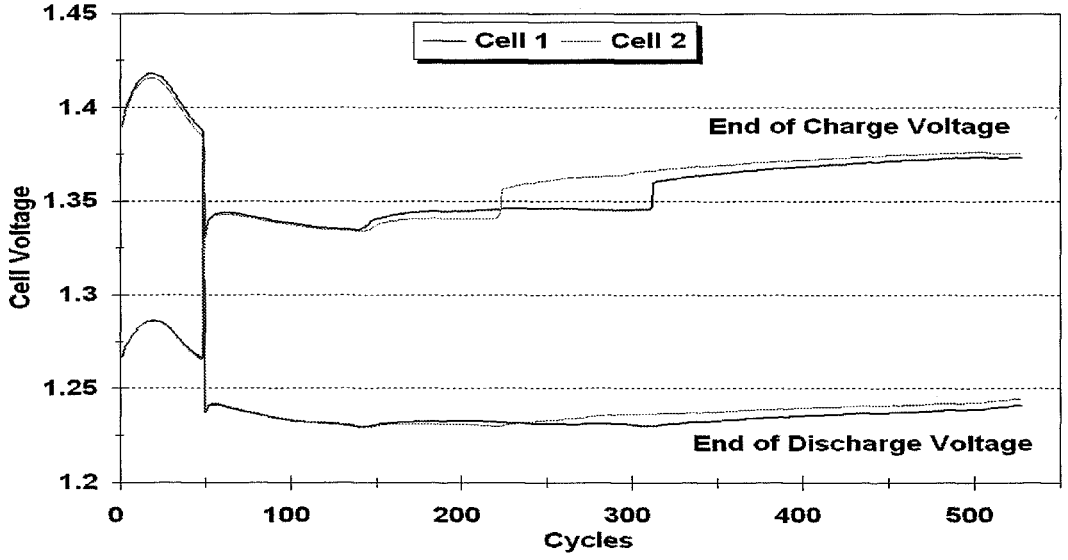

Figure 7. Adaptive Charge Control Test for 2 NiCd Cells.

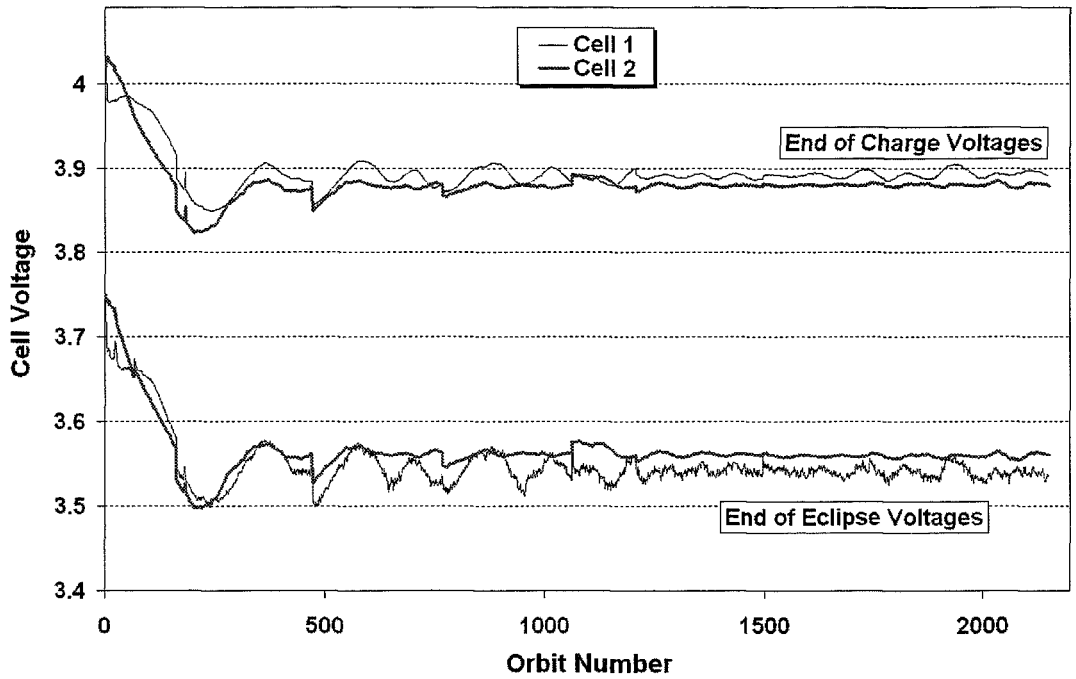

Figure 8. Adaptive Charge Control Test for Two Lithium-ion Cells.

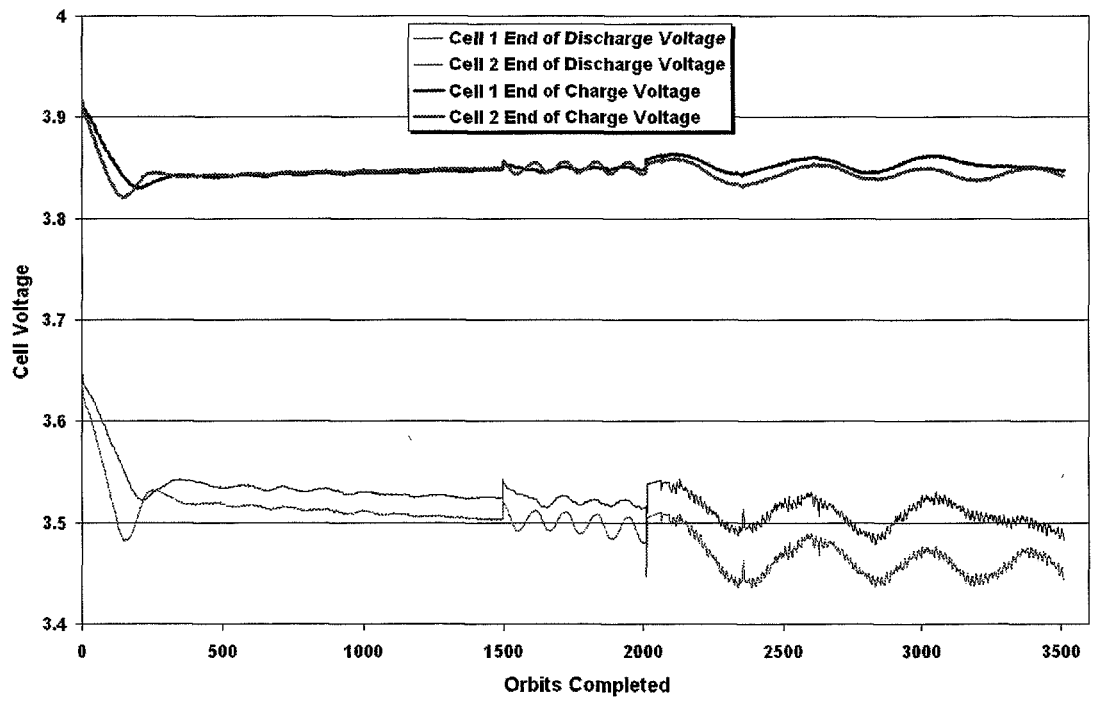

Figure 9. Adaptive Charge Control Test for Two Lithium-polymer Cells.

The Adaptive Charge Control Algorithm method for the charge management of lithium ion batteries can offer a minimum stress cycling regime that will change in response to changes in the cell electrodes, resistance, or environment to maintain

minimum stress. This approach is capable of actually optimizing the cycle life of a lithium-ion battery. Additional testing of this algorithm with spacecraft type lithium-ion cells is expected to begin shortly.

Conclusions

An accelerated cycling test has been developed that can screen lithium-ion test cells from a given lot in 2-3 months of test time, and is based on the degradation seen in cell voltages over the first 2500 cycles. Evidence has also been seen suggesting that some lithium-ion cells do not respond well to periods of stand in a highly charged state. Calorimetry measurements on a wide range of lithium-ion and lithium polymer cells invariably show a rich chemistry of staging processes as lithium ions undergo stepwise intercalation into the electrodes. Calorimetry can also provide an extremely sensitive method for detecting changes in cell design or chemistry over time, as well as verifying the thermal design of a satellite for a given type of cell at end of life.

An Adaptive Charge Control Algorithm has been discussed that is capable of automatically adapting to the charge needs of a battery cell so as to maintain an optimized recharge protocol for minimizing stress due to cycling. Data have been presented demonstrating the functioning of this algorithm for NiCd, lithium-ion, and lithium-polymer batteries.

LOCKHEED MARTIN

Li-ion Battery Cell Balancing Requirements

NASA Aerospace Battery Workshop
Huntsville, Alabama
November 14, 2000

Mark J. Isaacson and Vincent L. Teofilo
Lockheed Martin Space Systems
Sunnyvale, CA 94089
mark.isaacson@lmco.com

20011774
53801
35pr
38/cp/11/44

Outline

- *Advanced Technology Program (ATP)*
- *LI-ion Battery Management Requirements and Strategies*
- *Li-ion Battery Management Architectures*
- *Li-ion Cell Balancing Requirements for Portable Electronics Applications*
- *Summary*

ATP Program Structure

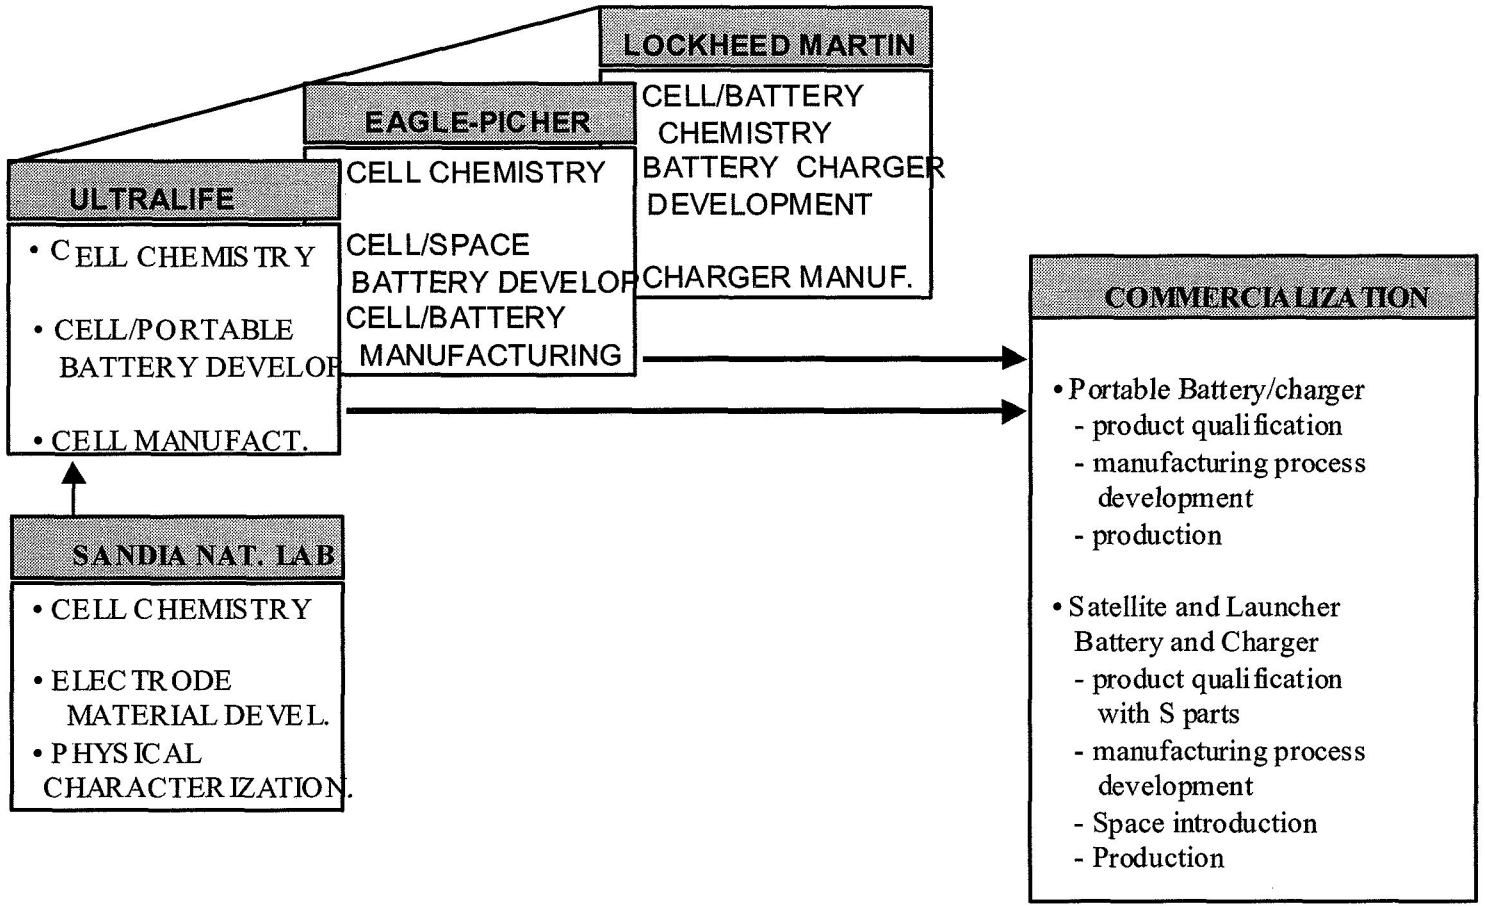

Li-Ion Batteries

- High Energy Density and Specific Energy
- Long Cycle Life.
- Established Manufacturing Infrastructure for portable electronics.
- Battery/cell manufacturers developing Li-ion for satellite application.
- Sensitive to over-charge and over-discharge.

⇒ Battery Management Electronics for Portable Electronics and Aerospace applications?

ATP Testing

- *ATP Program Testing*
  - *LMSS focus is on cell characterization for evaluating charge balancing requirements*
- *Ultralife (UBI) Cells*
  - *700 mAmp-hour (nominal)*
  - *made on production line*
  - *graphitic anode*
  - *$LiNi_{1-x}Co_xO2$ cathode*
  - *polymer-gel electrolyte*
- *A note on statistics*
  - *test sample size must be sufficiently large to reach definitive conclusions*
  - *only a few cells have been tested here to provide direction*
  - *UBI will supply additional data*

Li-ion Battery Management Strategies

- Battery Level Voltage Monitoring
- Cell Level Voltage Monitoring
- Dissipative Cell Level Voltage Management
- Non-Dissipative Cell Level Voltage Management

Battery Level Voltage Monitoring

- Battery voltage is monitored.
- Cell voltages are not measured.
- Switched from Constant Current to Constant Voltage charge when Maximum *Battery* Voltage is reached.
- Battery voltage is maintained within specified limits.
- Cells voltages may exceed specified limits (I.e. be over-charged or over-discharged.) depending on cell-to-cell variations.
- Simple, inexpensive.

Cell Level Voltage Monitoring

- Cell voltages are monitored.
- Switched from Constant Current to Constant Voltage charge when first cell reaches Maximum *Cell* Voltage.
- Cell voltages are all maintained within specified limits.
- Cell state-of-charge is not actively managed.
- Battery capacity limited by lowest cell capacity.
- Minimum level of voltage management in commercial portable electronics.

Dissipative Cell Level Voltage Management

- Voltages of individual cells are monitored.
- State-of-charge of individual cells is actively managed by bypassing current around cells through a dissipative element such as a resistor.
- Voltage of all cells are maintained within specified limits.
- Operates only during charge.
- Battery capacity is limited by that of lowest capacity cell but all cells can be charged to maximum capacity.

Non-Dissipative Cell Level Voltage Management

- Voltages of individual cells are monitored.
- State-of-charge of individual cells is *managed* by transferring energy from cell to cell via a "nondissipative" element such as a capacitor.
- Voltage of all cells are maintained within specified limits.
- Can operates during both charge and discharge.
- Battery capacity is not limited by lowest capacity cell.

Li-ion Battery Charge Control Architectures

- Dissipative
  - Resistive Equalization
  - Analog Shunt Equalization
- Non-dissipative
  - Switched Capacitor Equalization
  - Resonant Equalization

Resistive Equalization

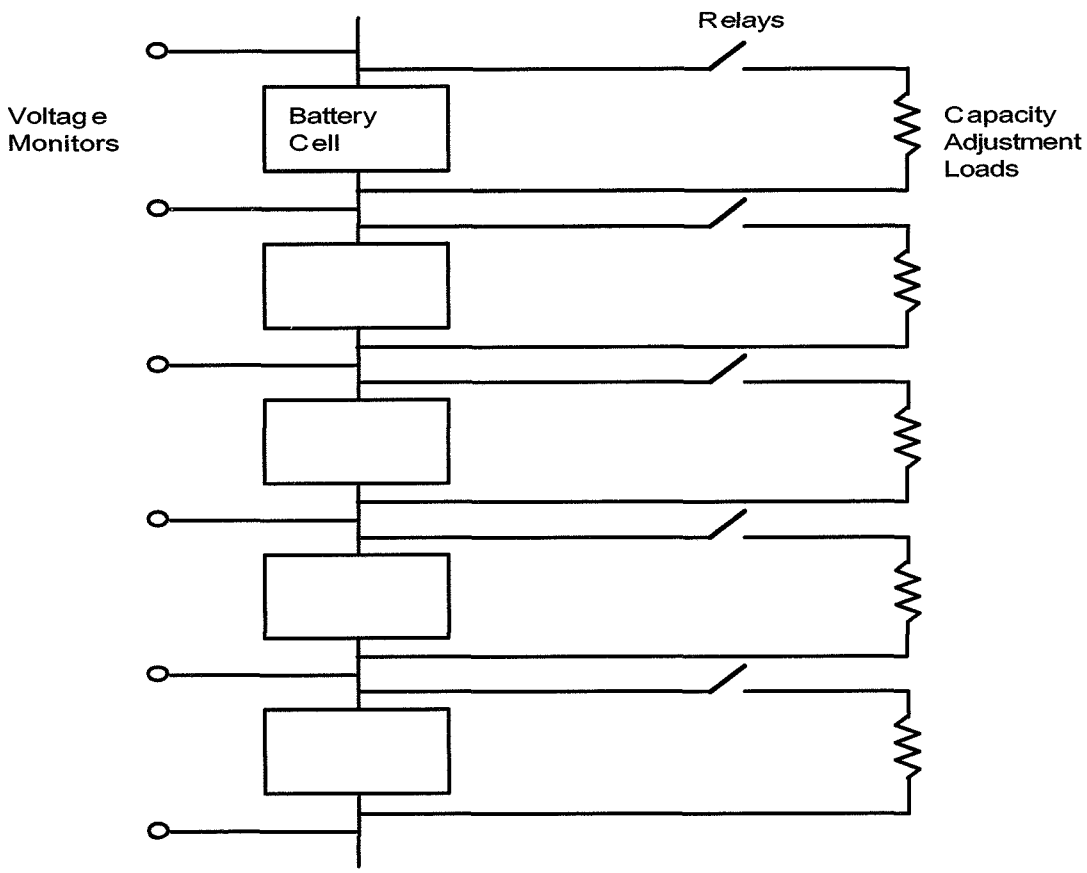

Analog Shunt Equalization

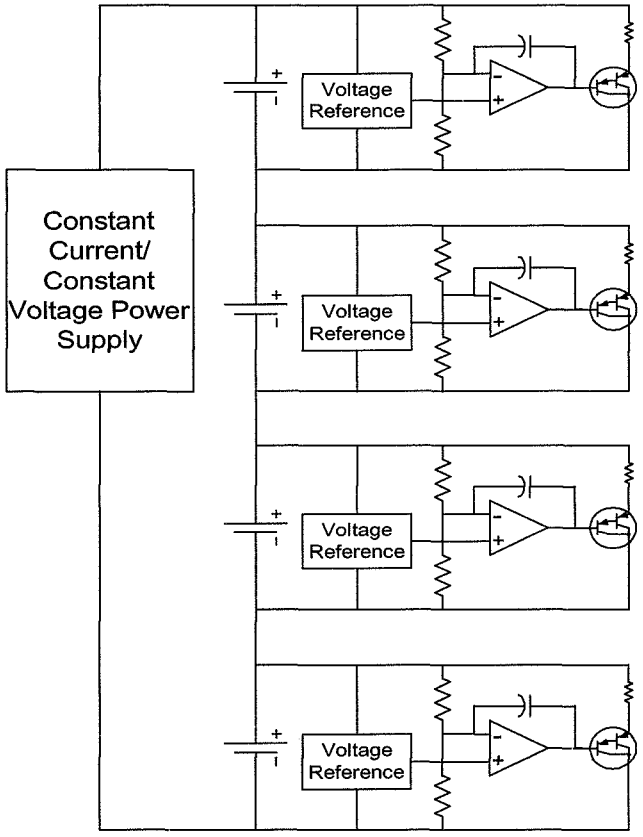

Switched Capacitor Equalization

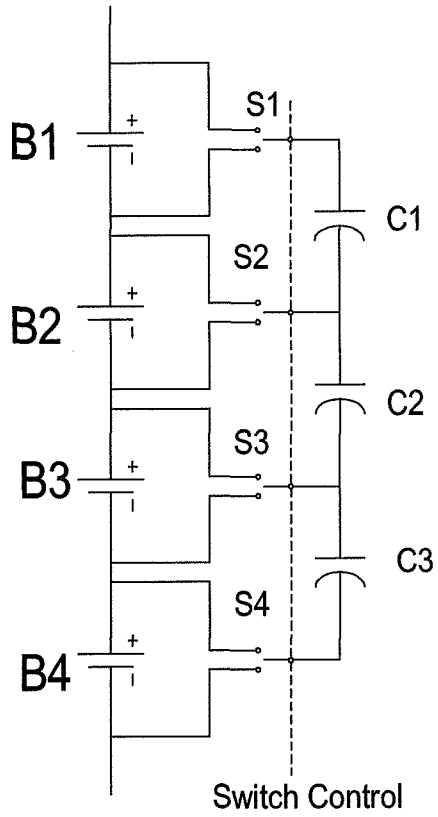

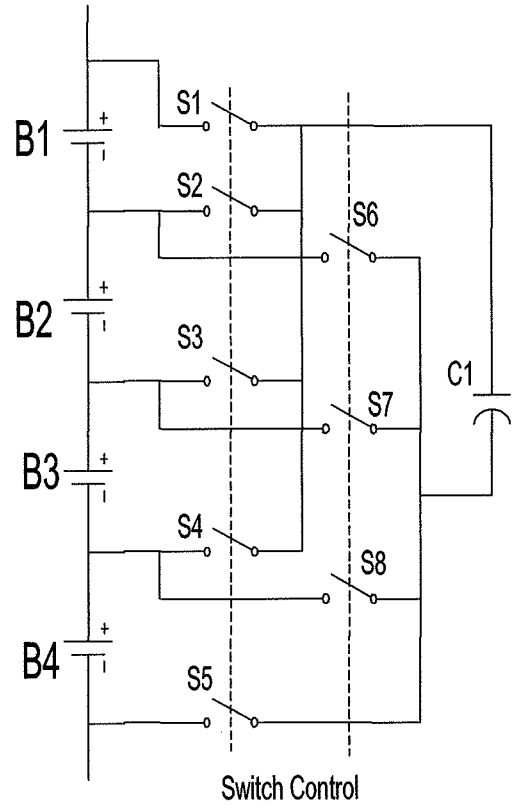

Resonant Equalization

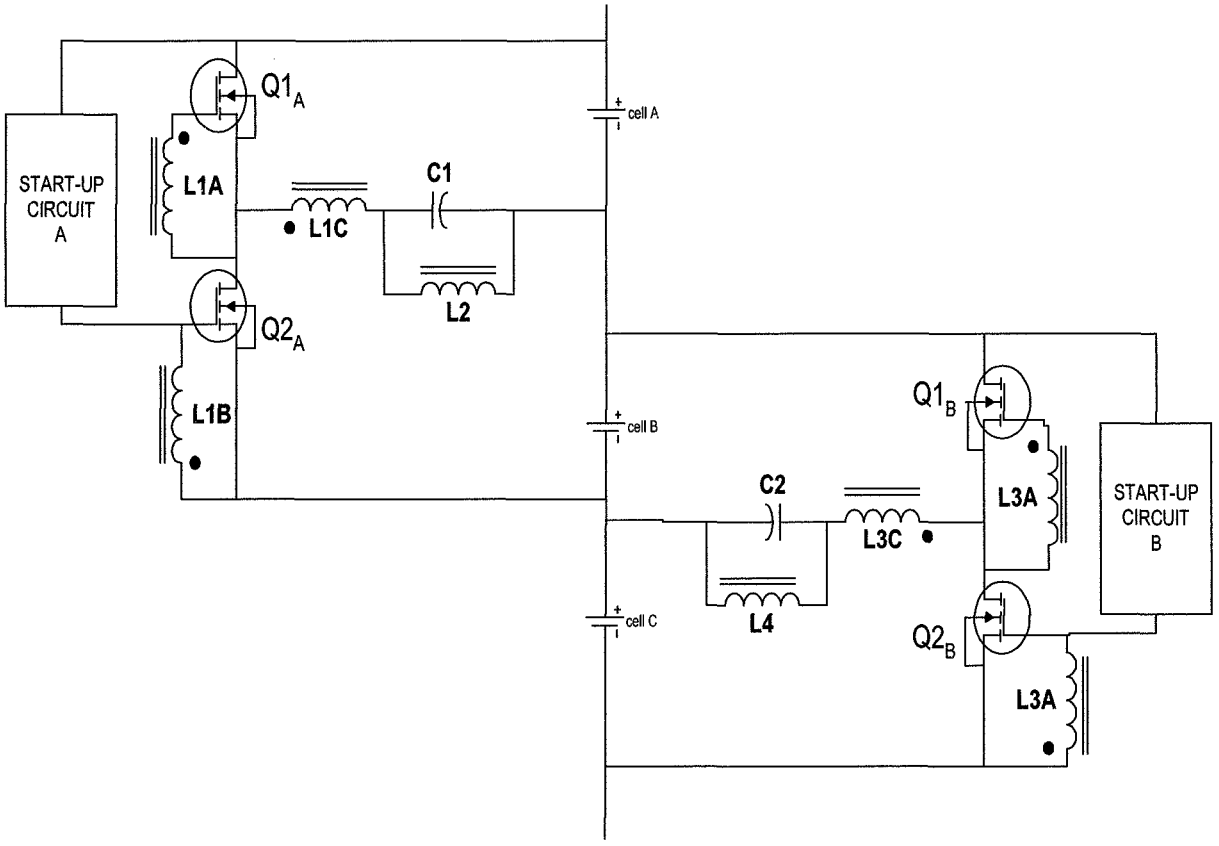

Portable Li-Ion Battery Management System Implementation

LOCKHEED MARTIN

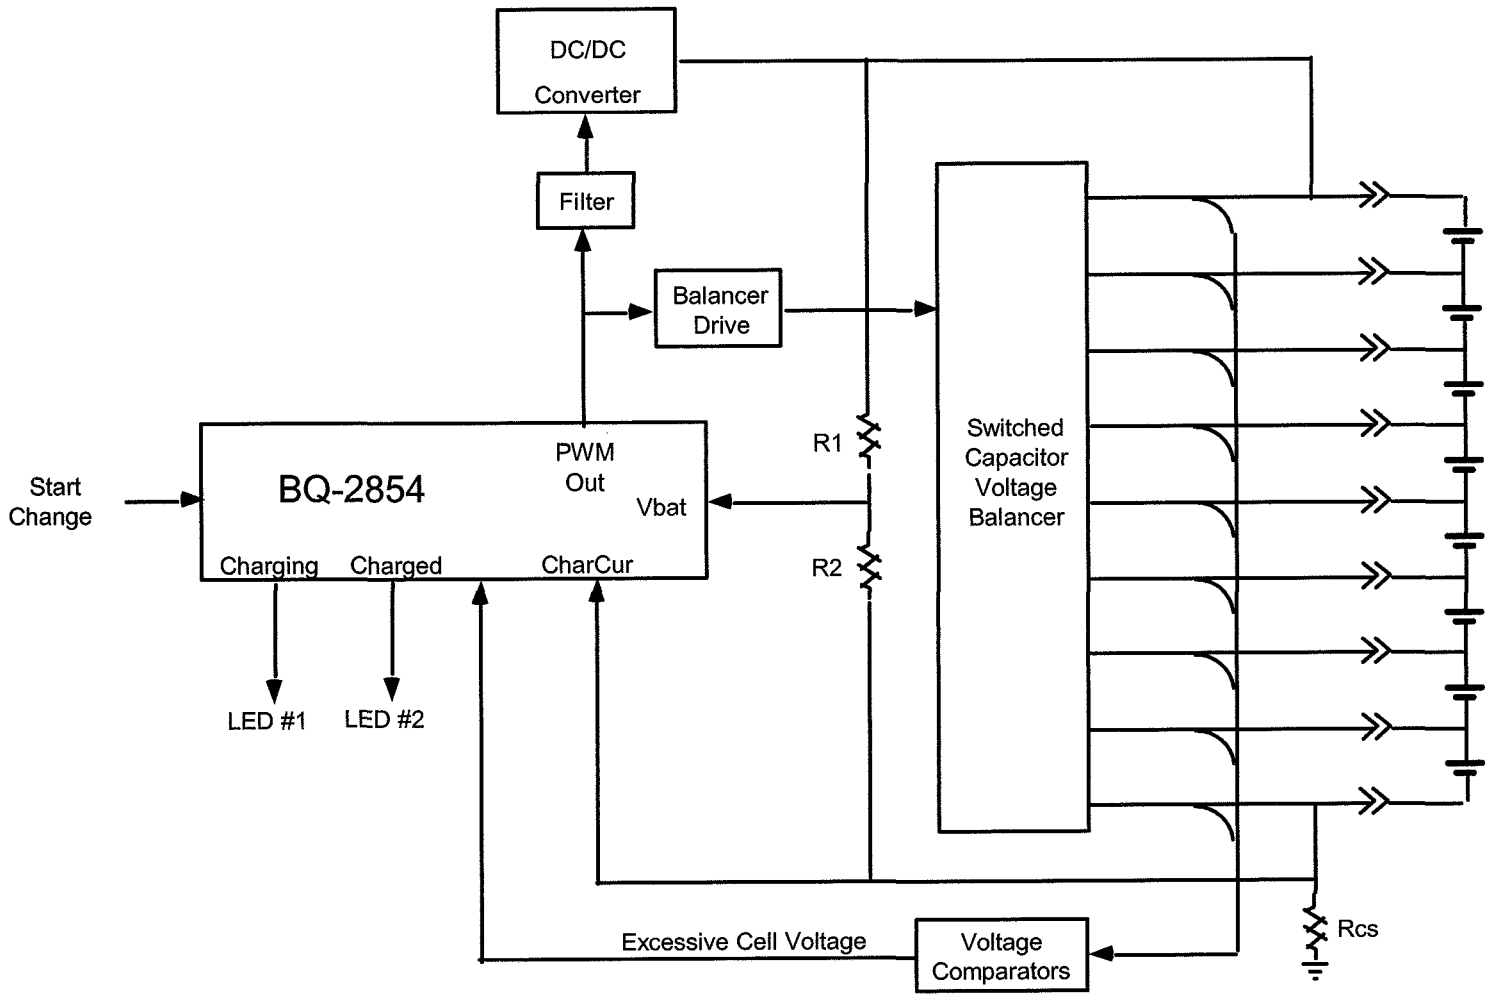

Space Battery Management System Implementation

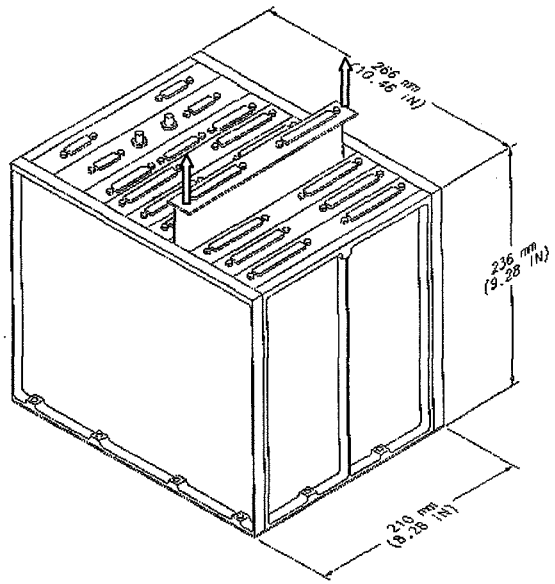

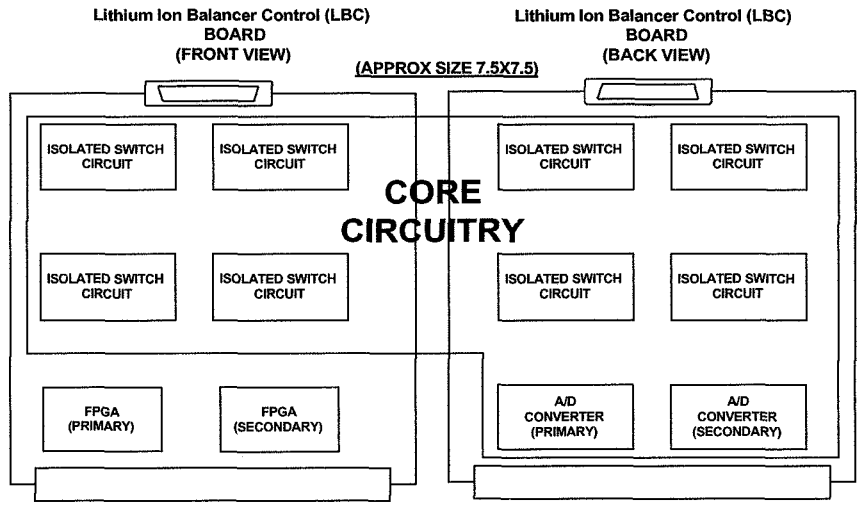

Desirable Features of Portable Electronics Batteries

- ***Maximum Discharge Run Time***
- ***Minimum Charge Time***
- ***Increased Cycle Life***

⇒ ***Application requirements for portable electronics differ from those of Aerospace***

Testing Sequence

- *Beginning-of-Life (BOL) Tests*
  - *capacity characterization*
  - *DC resistance*
  - *self-discharge balance*
- *Cycling*
- *End-of-Life (EOL) Tests*
  - *capacity characterization*
  - *DC resistance*
  - *self-discharge balance*

BOL Capacity Characterization

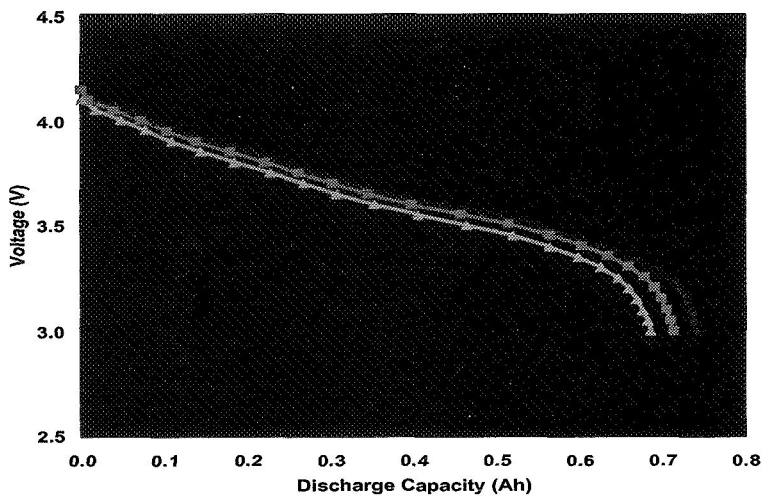

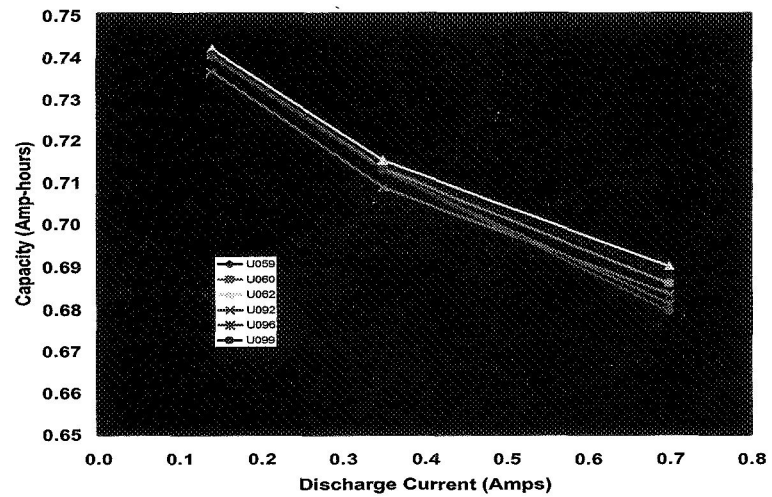

Table 2 Beginning-of-Life Cell Discharge Capacities			
Cell	**Discharge Capacity (Amp-hours)**		
	0.14 Amps	**0.35 Amps**	**0.7 Amps**
U59	0.7411	0.7136	0.6879
U60	0.7405	0.7132	0.6857
U62	0.7419	0.7150	0.6898
U92	0.7366	0.7086	0.6833
U96	0.7402	0.7127	0.6810
U99	0.7406	0.7127	0.6792
Statistics (All Cells)			
Mean, Ah	0.7402	0.7126	0.6845
SD, Ah	0.0018	0.0022	0.0041
SE, %	0.2484	0.3018	0.5948
Statistics (w/o Cell U92)			
Mean, Ah	0.7409	0.7134	0.6847
SD, Ah	0.0007	0.0010	0.0045
SE, %	0.0898	0.1332	0.6580

Test Description

- C, C/2, C/5 discharges
- 20°C
- 4.15 V max, 3.0 V min

Test Results

- Tight capacity distribution. (Similar to Japanese manufacturers.)
- Wider capacity distribution at high discharge rates
- Cell U092 developed electrolyte leak because of improper handling

BOL DC Resistance Test Procedure

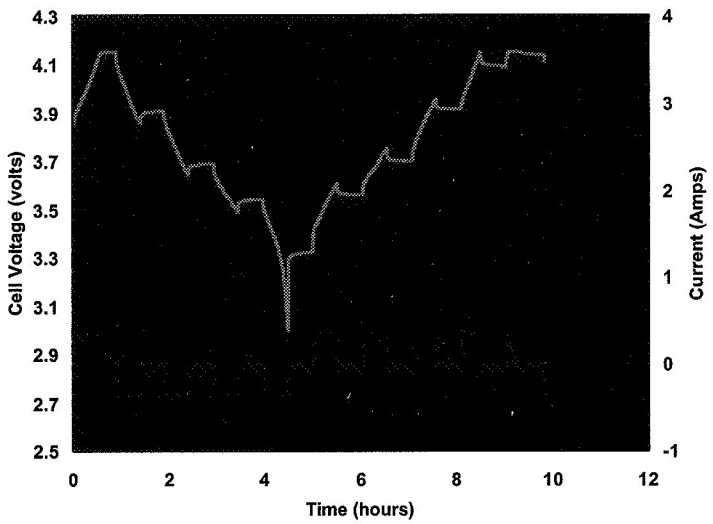

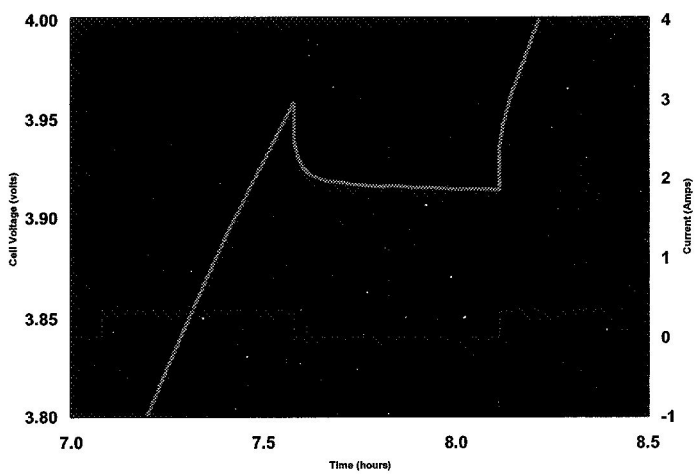

Test Description

- Charge and discharge at 350 mA (C/2).
- 30-minute OC at 75%, 50%, 25%, and 0% SOC on discharge and 25%, 50%, 75% and 10% SOC on charge.
- Polarization divided into two components, $?_{5s}$ and $?_{30m}$ based on AC impedance tests.
- $?_{5s}$ is dominated by faradaic resistance and ESR.
- $?_{30m}$ is dominated by concentration polarization.

BOL DC Resistance Test Results

Table 3 Beginning-of-Life Cell Polarization			
Cell	**Cell Polarization (mV) (All values are negative but the sign has been omitted.)**		
	?$_{5s}$	?$_{30m}$	Total Polarization
U59	24.8	30.2	55.0
U60	24.8	30.3	55.1
U62	25.1	31.4	56.5
U96	26.4	34.3	60.7
U99	23.9	36.6	60.5
Statistics (excluding Cell U92)			
Mean, mV	25.1	34.1	59.2
SD, mV	1.3	2.6	2.4
SE, %	5.0	7.6	4.0

Test Description

- Cell polarization 50-60 mV.
- Standard deviation (1-3 mV) and standard error (5-10%) are small.

Equilibrium Voltages for Cells in Series with Unequal Self Discharge Rates

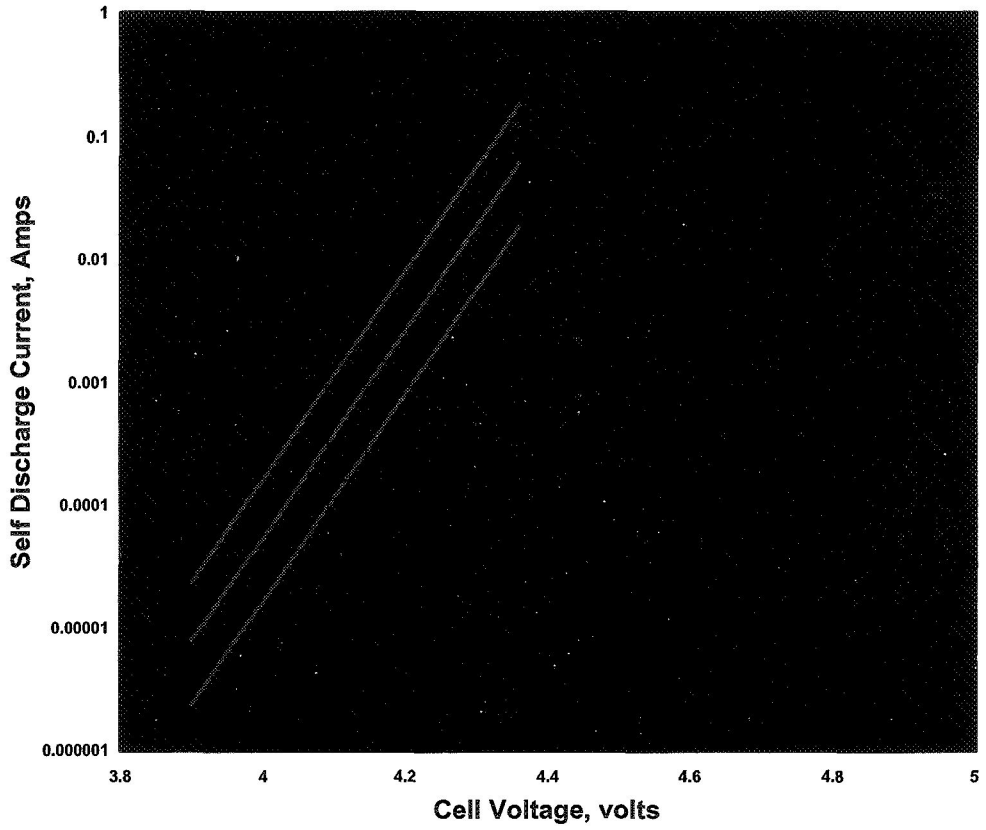

BOL Self Discharge Balancing Results

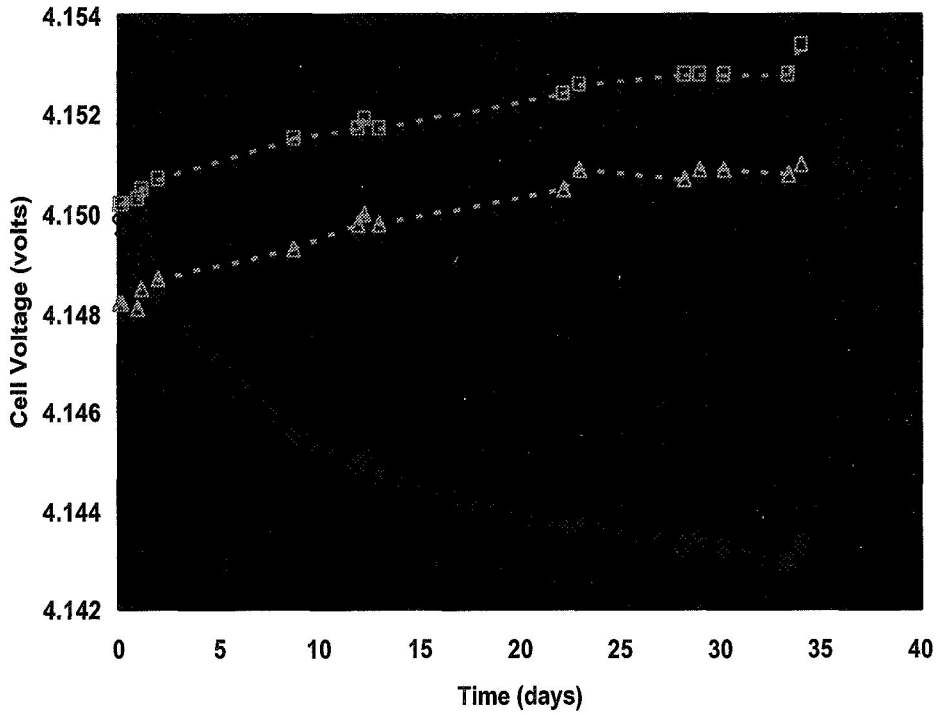

Test Results

- EOL voltage dispersion less than BOL voltage dispersion.
- Consistent with decrease in self discharge as cells age because of increase in internal resistance of cells.

Cell Cycling

- Three cells (U059, U062, U096) placed on cycle test
  - Test Regimen (100% DOD)
    - Constant current charge at C/2 to 4.15 V.
    - Constant voltage charge at 4.15 V to C/20.
    - Constant current discharge at C.
  - Test regimen similar to that used for portable electronics
- All cells cycles for an equal time
- Cells with lower capacity completed more cycles than those with a higher capacity
- Capacity characterization, DC resistance and self-discharge balance experiment repeated at end of cycle test to obtain end-of-life data (EOL)
- Cell-to-cell interactions in batteries?

Comparison of EOL and BOL Discharge Capacities

Table 2 Beginning-of-Life Cell Discharge Capacities			
Cell	**Discharge Capacity (Amp-hours)**		
	0.14 Amps	**0.35 Amps**	**0.7 Amps**
U59	0.7411	0.7136	0.6879
U60	0.7405	0.7132	0.6857
U62	0.7419	0.7150	0.6898
U92	0.7366	0.7086	0.6833
U96	0.7402	0.7127	0.6810
U99	0.7406	0.7127	0.6792
Statistics (All Cells)			
Mean, Ah	0.7402	0.7126	0.6845
SD, Ah	0.0018	0.0022	0.0041
SE, %	0.2484	0.3018	0.5948
Statistics (w/o Cell U92)			
Mean, Ah	0.7409	0.7134	0.6847
SD, Ah	0.0007	0.0010	0.0045
SE, %	0.0898	0.1332	0.6580

Table 1 End-of-Life Cell Discharge Capacities			
Cell	**Discharge Capacity (Amp-hours)**		
	0.14 Amps	**0.35 Amps**	**0.7 Amps**
U59	0.6063	(1)	0.574
U60	-	-	-
U62	0.5794	0.6049	0.5695
U92	-	-	--
U96	0.616	0.5856	0.5538
U99	-	-	-
Statistics			
Mean, Ah	0.6006	0.5953	0.5658
SD, Ah	0.0190	0.0136	0.0106
SE, %	3.1573	2.2927	1.8744

Test Results

- Cell capacities decrease as cells age.
- Cell capacity distribution increases as cells age.
- Capacity distribution is still relatively tight at EOL as well as at BOL.
- No evidence of need for balancing electronics.

Comparison of EOL and BOL DC Resistance Data

Table 4 Beginning-of-Life Cell Polarization			
Cell	**Cell Polarization (mV)** **(All values are negative but the sign has been omitted.)**		
	?$_{5s}$	?$_{30m}$	Total Polarization
U59	24.8	30.2	55.0
U60	24.8	30.3	55.1
U62	25.1	31.4	56.5
U96	26.4	34.3	60.7
U99	23.9	36.6	60.5
Statistics (excluding Cell U92)			
Mean, mV	25.1	34.1	59.2
SD, mV	1.3	2.6	2.4
SE, %	5.0	7.6	4.0

Table 3 End of Life Cell Polarization			
Cell	**Cell Polarization (mV)** **(All values are negative but the sign has been omitted.)**		
	?$_{5s}$	?$_{30m}$	Total Polarization
U59	33.0	77.9	110.9
U62	31.7	79.4	111.1
U96	35.7	87.0	122.7
Statistics			
Mean, mV	33.5	81.4	114.9
SD, mV	2.0	4.9	6.8
SE, %	6.1	6.0	5.9

Test Results

- Cell internal resistances increase as cells age.
- Cell internal resistance distribution increases as cells age.
- Internal resistance distribution is still relatively tight at EOL.
- No evidence of need for balancing electronics.

Comparison of EOL and BOL Self Discharge Balancing Data

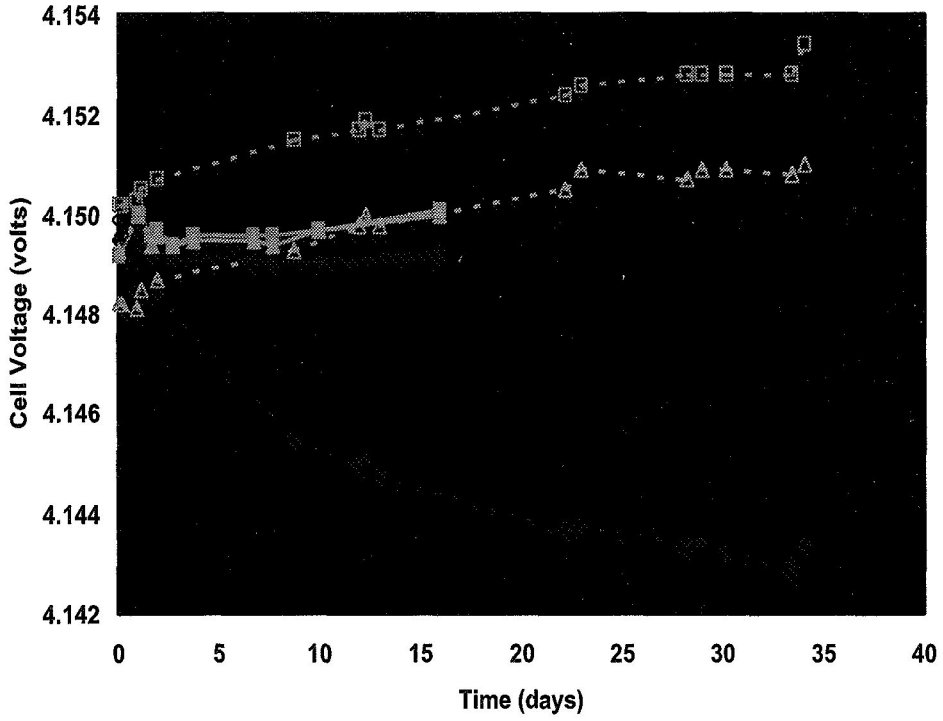

Test Results

- EOL voltage dispersion less than BOL voltage dispersion.
- Consistent with decrease in self discharge as cells age because of increase in internal resistance of cells.
- No evidence of need for balancing electronics.

"Monte Carlo" Calculations

- Generate (with computer) 150 cells
  - standard deviations from experimental capacity characterization
  - random number generator
  - normal capacity distribution as weighting function
- Randomly assemble 50 three-cell batteries
  - No matching
  - Three cells in series is a typical configuration for lap tops
- Calculate Discharge Energy for Unbalanced batteries
  - assume discharge energy is limited by cell with lowest discharge energy
  - battery discharge energy is three time discharge energy of "weakest" cell
- Calculate Discharge Energy for Nondissipatively Balanced Battery
  - assume 100% efficiency or perfect balancing
  - battery discharge energy is sum of discharge energy of three cells
- Determine difference in discharge energy between balanced and unbalanced batteries

Histogram of Capacity Differences Distribution between Unbalanced and Non-Dissipatively Balanced Batteries containing Cells with Different Self Discharge Rates

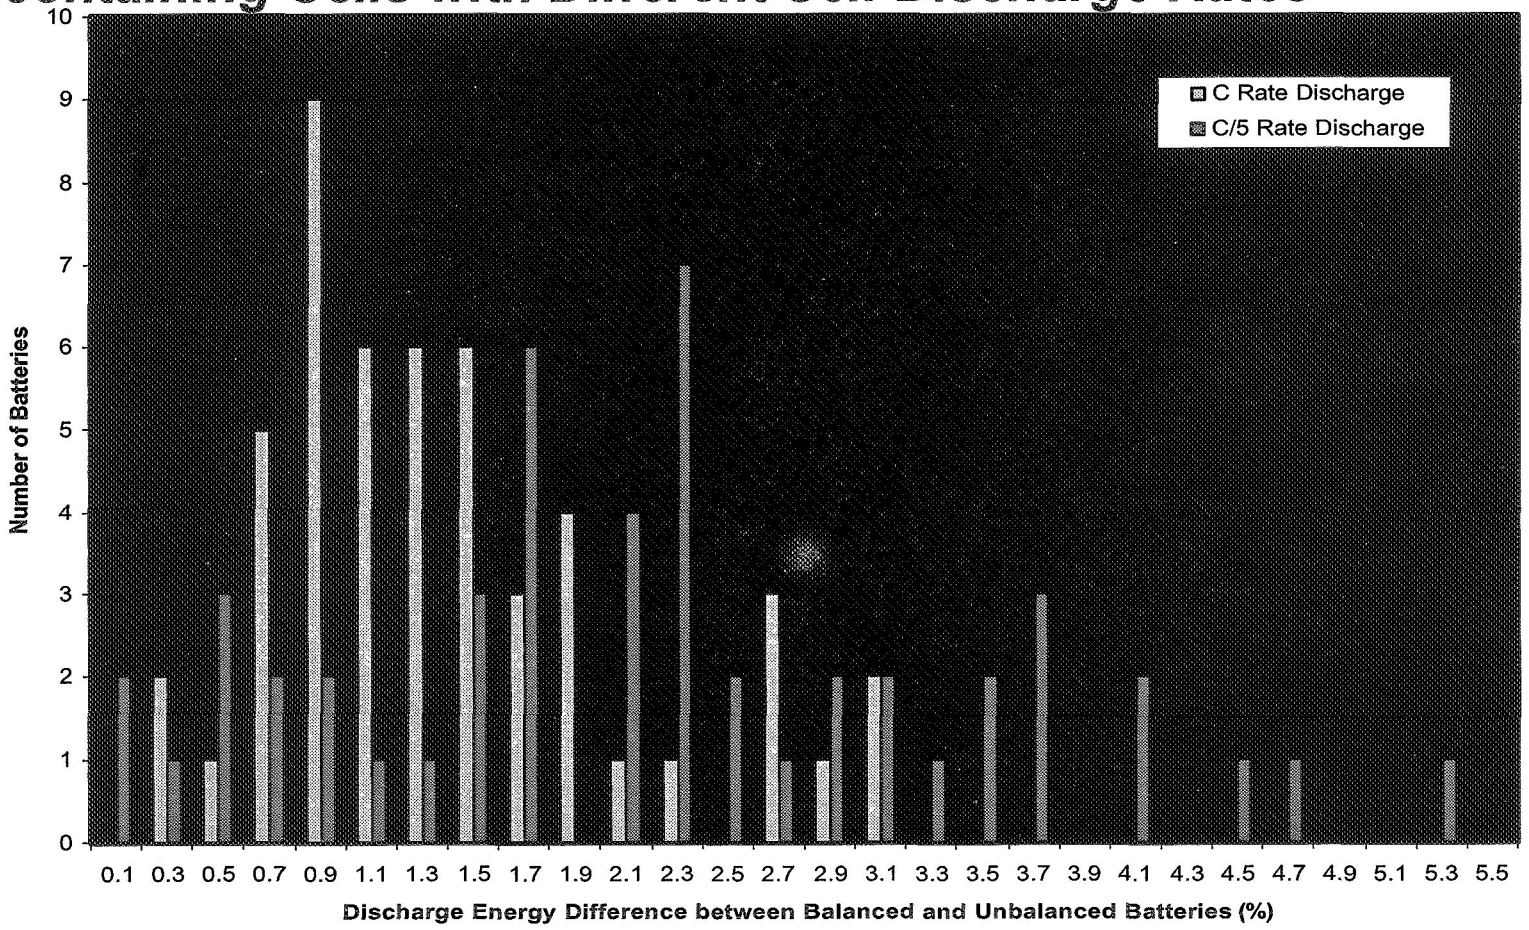

Monte Carlo Calculations of Capacity Difference Distribution between Unbalanced and Non-Dissipatively Balanced Batteries containing Cells with Different Self Discharge Rates

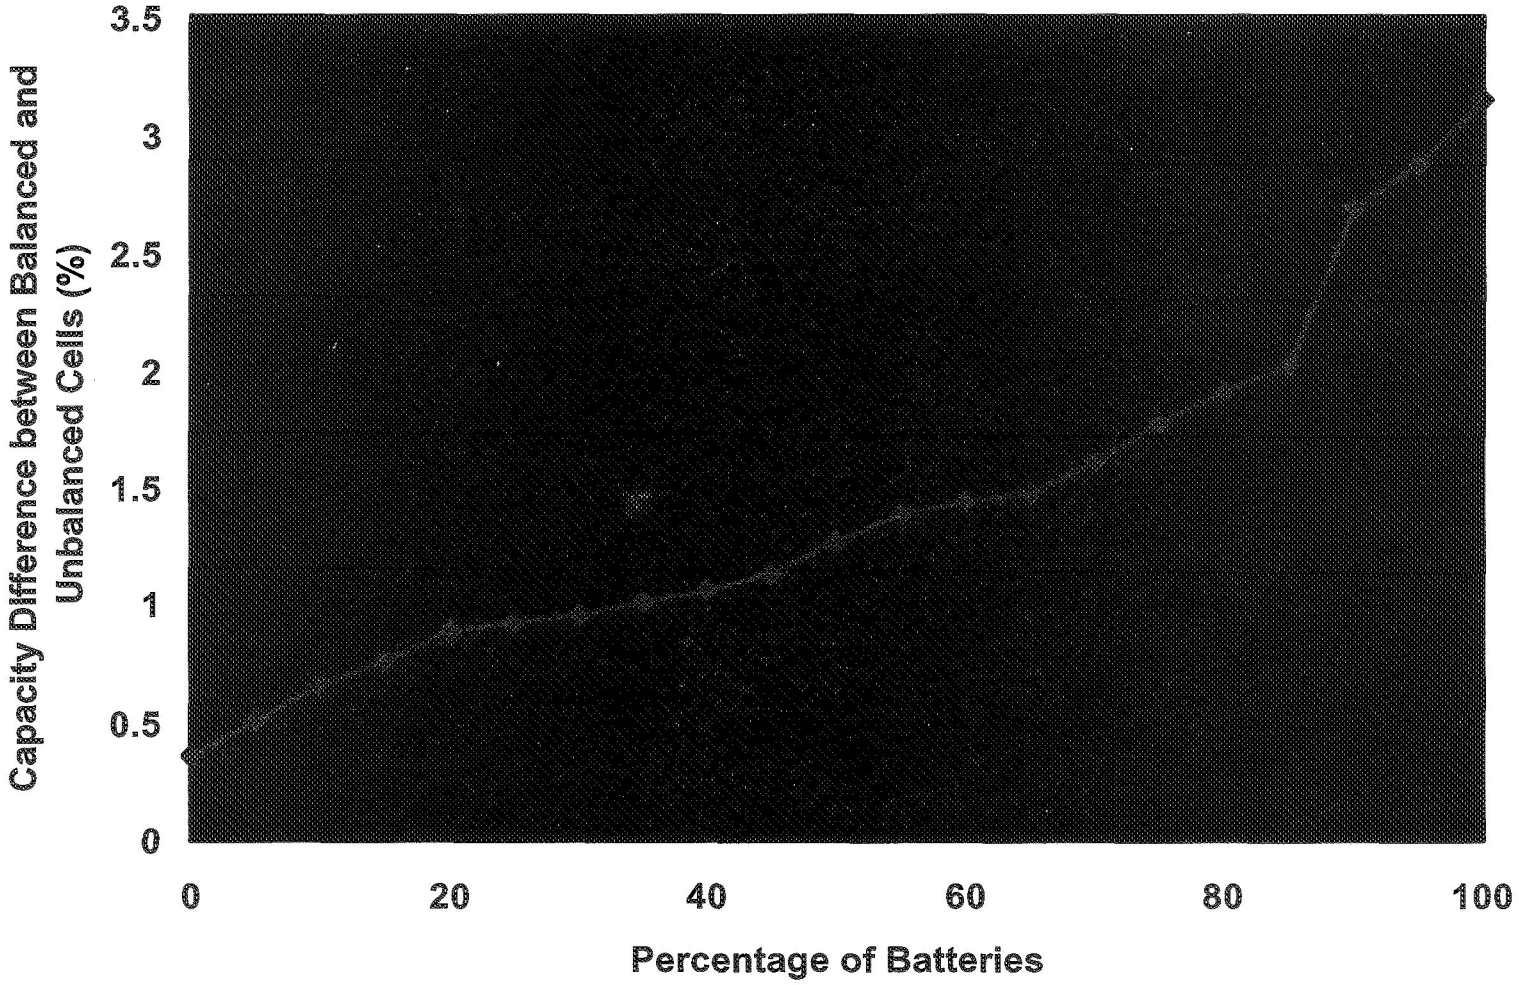

Available Discharge Energy Calculations for Unbalanced, Dissipative Balancing and

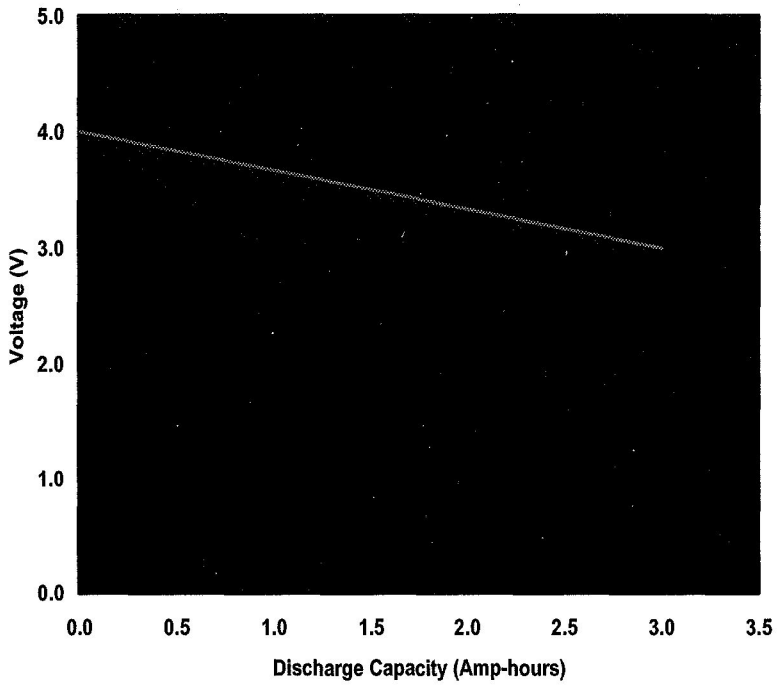

Assumptions

- **Battery with two cells in series**
- **Cell 1 Capacity: 1 Ah**
- **Cell 2 Capacity: 3 Ah**

Energy Calculations

- **Unbalanced (Worst Case)**

E = (3.17V)(3Ah)+(3.5V)(1Ah)= 6.67Wh

- **Dissipative Balancing (Best Case)**

E = (3.83V)(1Ah)+(3.5V)(1Ah)= 7.33Wh

- **Non-Dissipative Balancing**

E = (3.5V)(3Ah)+(3.5V)(1Ah)= 14 Wh

Monte Carlo Calculations for Effect of Balancing Method on Battery Yield for Batteries containing Cells with Different Discharge Capacities

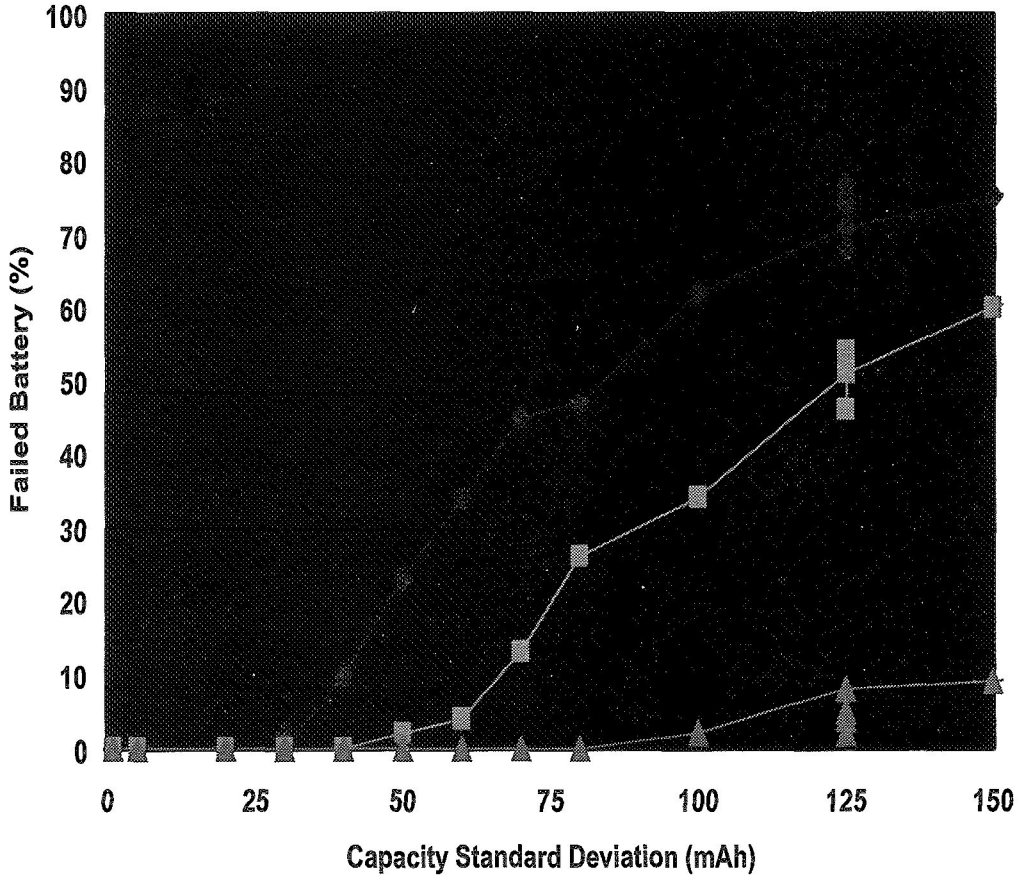

Input Data

- Nominal Capacity: 700 mAh
- Nominal Discharge Energy: 2520 Wh
- Failure Criteria: 2016 Wh/cell or 6048 Wh/battery (80% of BOL energy)
- Average EOL Discharge Energy: 2142 Wh/cell. 85% of BOL energy yielding 5% average margin.

Summary

- *LI-ion Battery Management Requirements, Strategies and Architectures Reviewed.*
- *UBI Li-ion cell testing under way to quantify Charge Balancing Requirements.*
- *No evidence for Need for Cell Balancing for UBI Cells for Portable Commercial Electronics.*
- *Conclusions for UBI portable electronics cells not necessarily applicable to other applications and other cell types.*

Acknowledgement

This work was supported by the Department of Commerce under Advanced Technology Program Award No. 70NANB8H4073, Project No. 98-03.

SAFT

TRW

Characterization and Simulated LEO Cycling of SAFT Lithium Ion Cells

Chuck Lurie and Philip Johnson
TRW Space and Electronics Group
Redondo Beach, California 90278

Robert J. Staniewicz
SAFT America, Inc., SAFT R & D Center
Cockeysville, MD 21030

The 2000 NASA Aerospace Battery Workshop
Holiday Inn -- Research Park
Huntsville, Alabama
November 14 - 16, 2000

20011771 39
538022
24p

Scope

- This presentation summarizes test results, to date, obtained with SAFT MP commercial cells and prototype space cells.
- These tests are part of an ongoing program at TRW to evaluate lithium ion cells for space application.
- To facilitate development of a coherent data base, all cells in the program are subjected to similar test regimes:
  - Characterization
    - = Charge acceptance as a function of CVL and temperature
    - = Cell resistance as a function of SOC and temperature
  - Cycling
    - = LEO: 25% DOD, 15°C and 25°C, or
    - = GEO: 70% DOD, 15°C and 25°C

Test Plan

Characterization: Charge Acceptance, Cell Resistance

- Charge Acceptance: determined as a function of CVL and temperature
  - Charge at C/5 to a CVL; taper charge until current is < C/100
  - Discharge at C/5 to 3.0 volts
- Cell Resistance: determined as a function of SOC, during charge and discharge
  - Impose 10% current pulses during C/5 charge and discharge
  - determine cell resistance as dV/dI
- All characterizations were performed at 15°C and 25°C

Test Plan

Simulated Leo Cycling

- Depth of Discharge: 25% (basis: capacity at 25ºC to a CVL of 4.0 volts and taper charge until the current is < C/100
- Orbit: 100 minutes with 36 minute eclipse periods
- Charge regime: 0.5C to CVL; taper until eclipse discharge
- Charge management: Individual cell control
- Discharge: 0.42C (36 minutes)

Test Setup

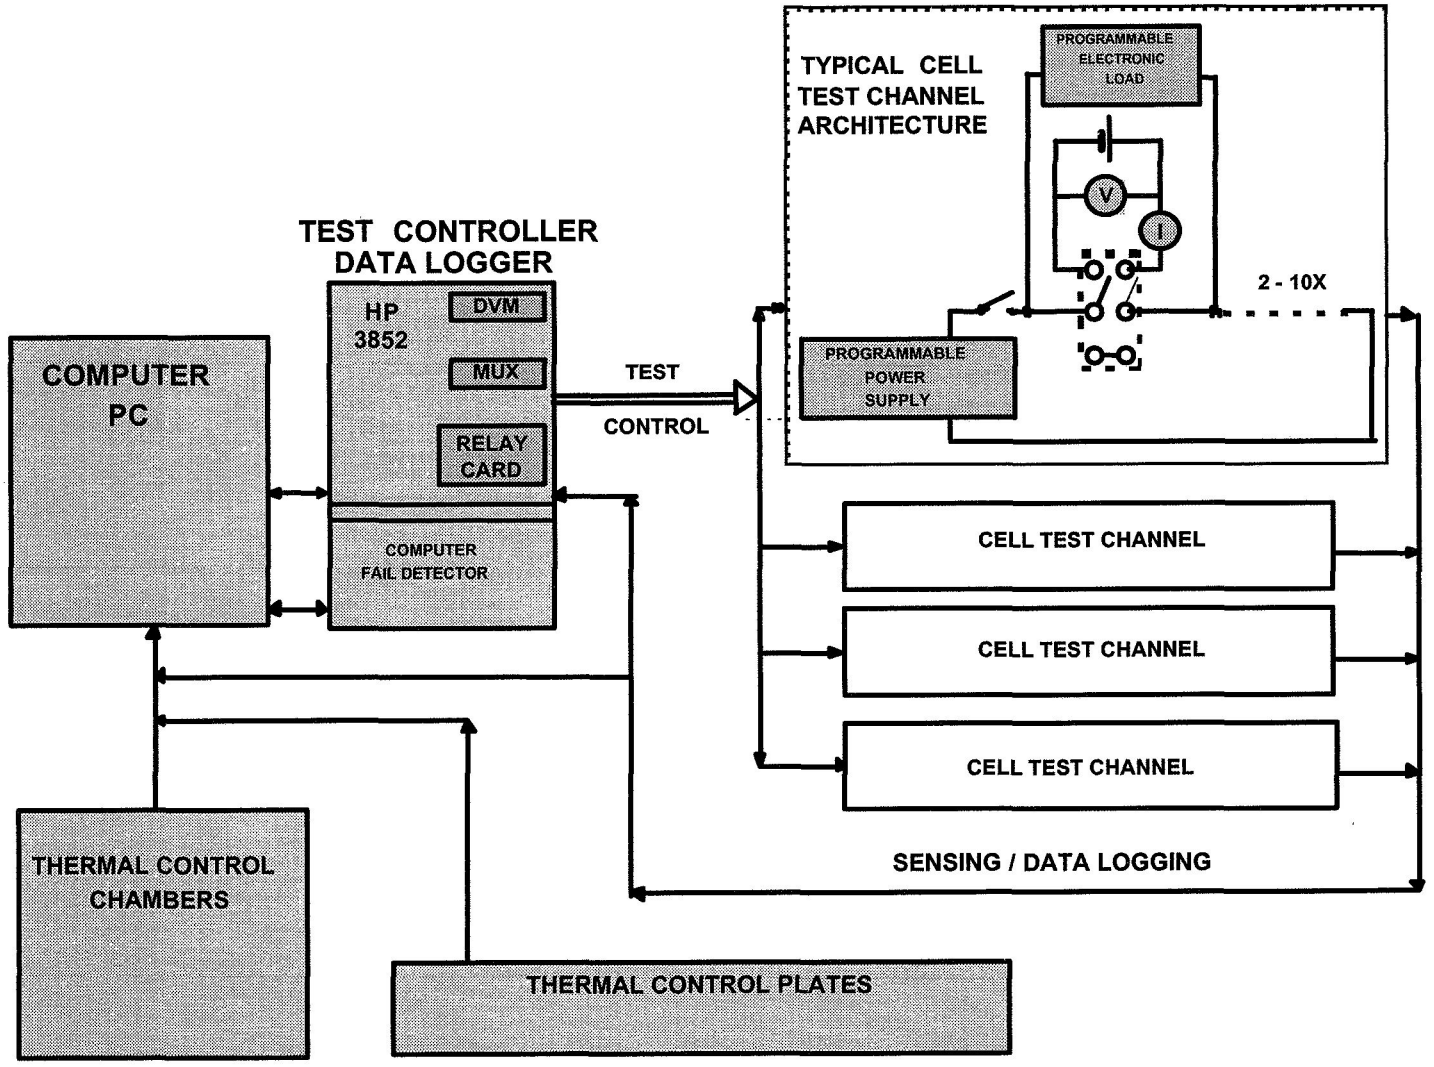
TYPICAL CELL
TEST CHANNEL
ARCHITECTURE
PROGRAMMABLE
ELECTRONIC
LOAD
V
I
2 - 10X
PROGRAMMABLE
POWER
SUPPLY
TEST CONTROLLER
DATA LOGGER
HP
3852
DVM
MUX
RELAY
CARD
COMPUTER
FAIL DETECTOR
COMPUTER
PC
TEST
CONTROL
CELL TEST CHANNEL
CELL TEST CHANNEL
CELL TEST CHANNEL
SENSING / DATA LOGGING
THERMAL CONTROL
CHAMBERS
THERMAL CONTROL PLATES

Test Facility

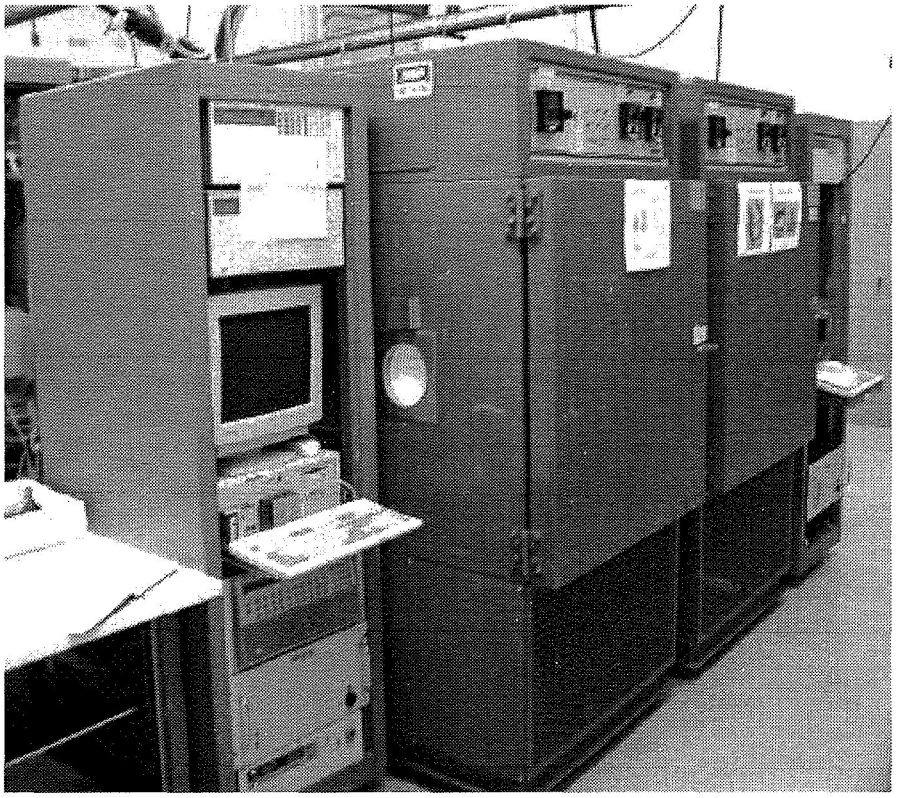

- Accommodates lithium ion cell characteristics
  - Charge/discharge mgmt
  - Safety
- Autonomous test control and data logging
- Individual cell, cell pack, or battery control for all test articles
- Fail safe capability for test anomalies

Test Articles

MP Cell

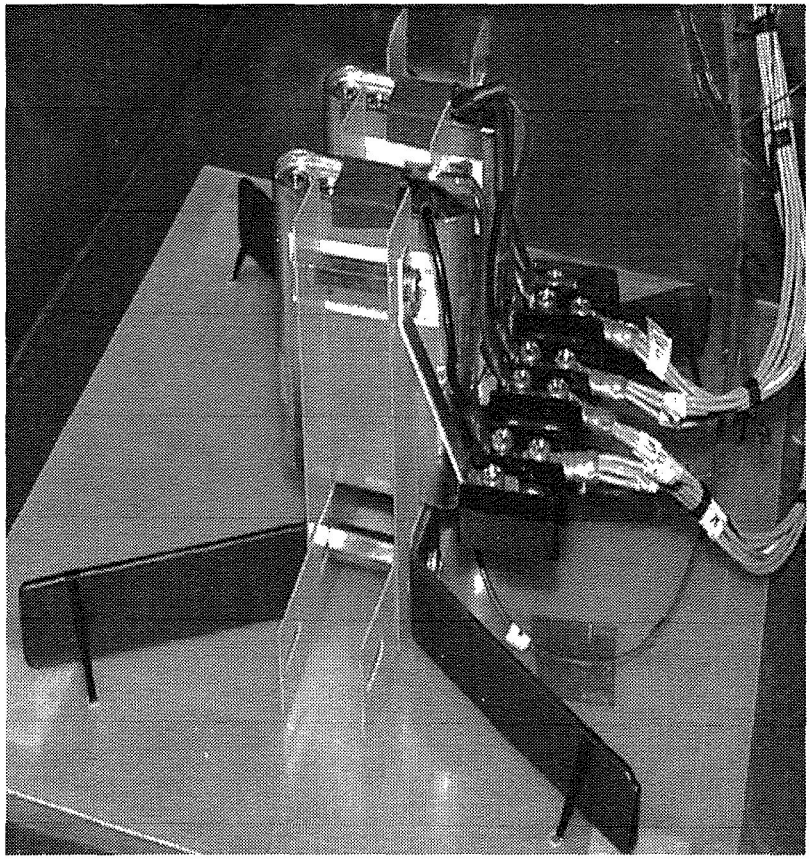

Prototype Cell

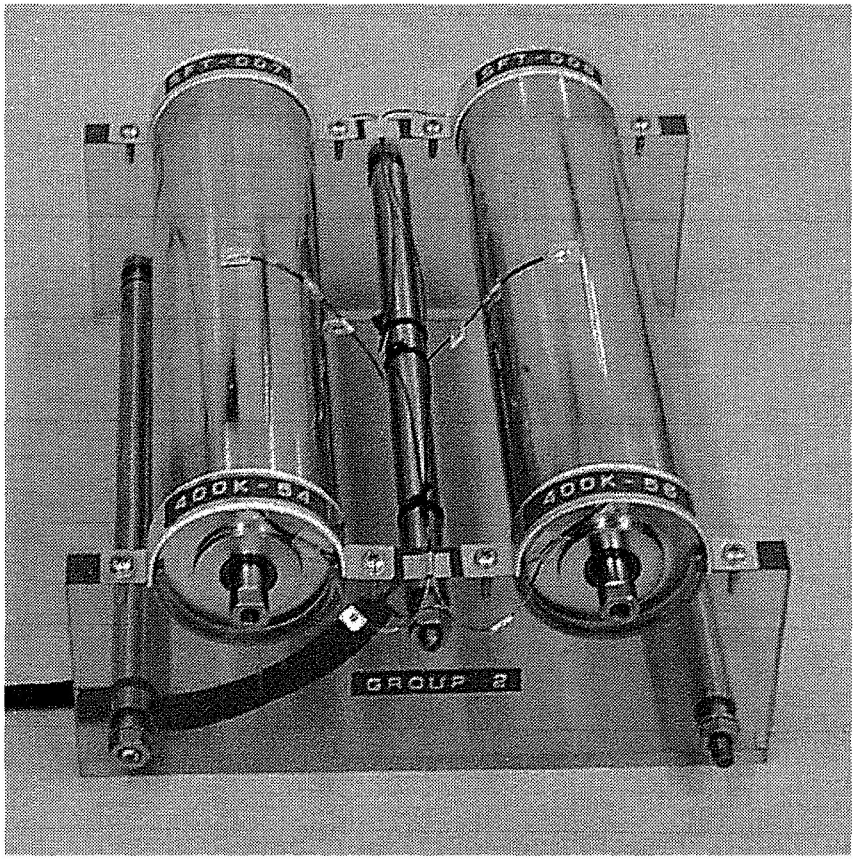

MP Cell Description

- Nomenclature: SAFT Li-Ion Prototype -- MP 176065
- Nominal Cell Capacity: 4.3 Ah
- Positive Electrode: $LiCoO_2$, PVDF binder
- Negative Electrode: Synthetic graphite, Non-fluorinated polymer binder
- Electrolyte: EC-DEC-DMC + VC additive
- Separator: PE/PP multilayer
- Stack: Wound prismatic
- Container: Stainless steel can, negative polarity
- Place of Manufacture: France

PROTOTYPE Cell Description

- Nomenclature: SAFT 400K Space Cell
- Nominal Cell Capacity: 42 Ah, 150 Wh
- Positive Electrode: $LiNiO_2$, PVDF binder
- Negative Electrode: Synthetic graphite, non-PVDF binder
- Electrolyte: 1M $LiPF_6$ PC/EC/3DMC
- Separator: PE/PP multilayer
- Stack: Wound cylindrical
- Container: Stainless steel can, negative polarity
- Place of Manufacture: USA

Test Results
(MP and Prototype Cells)

- Characterization
  - Charge acceptance
  - Cell resistance
- LEO Cycling
  - Typical 25% DOD cycle
  - EODV as a function of cycling at 25ºC
  - EODV as a function of cycling at 15ºC
  - Reserve capacity

MP Cell Characterization

Charge Acceptance as a Function of CVL at 25°C

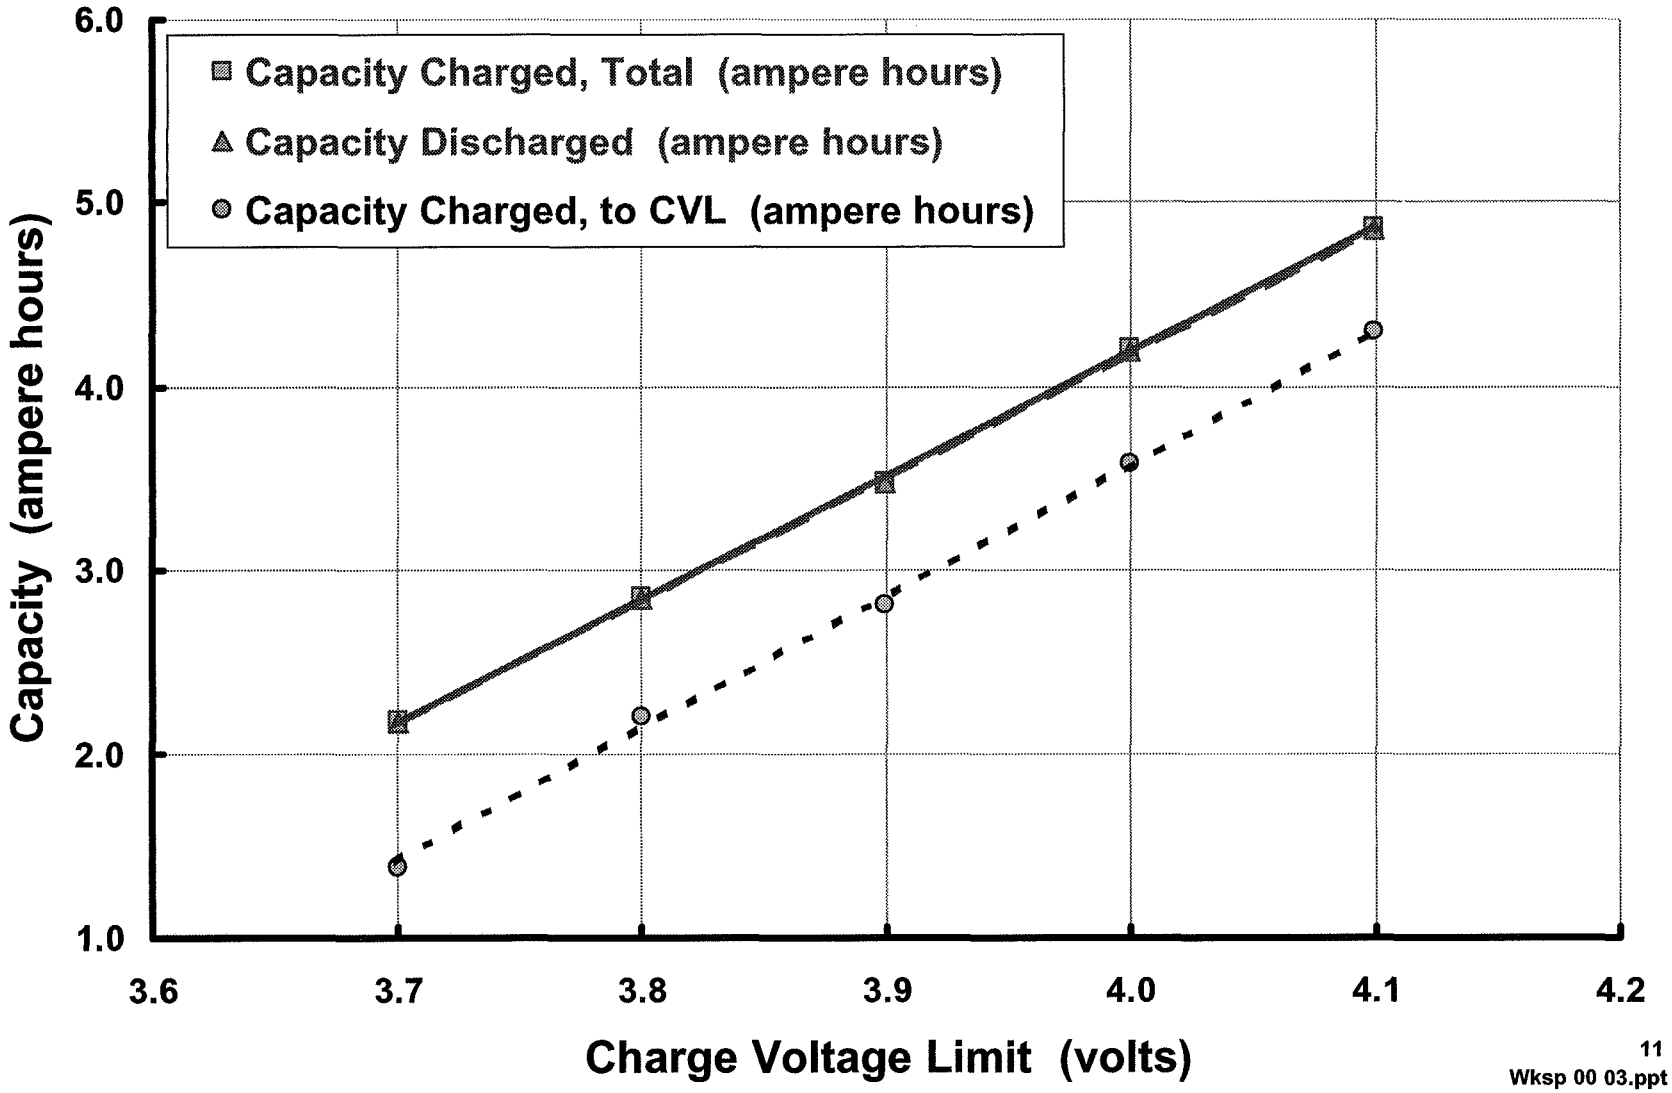

MP Cell Characterization

Cell Resistance as a Function of State of Charge at 25°C

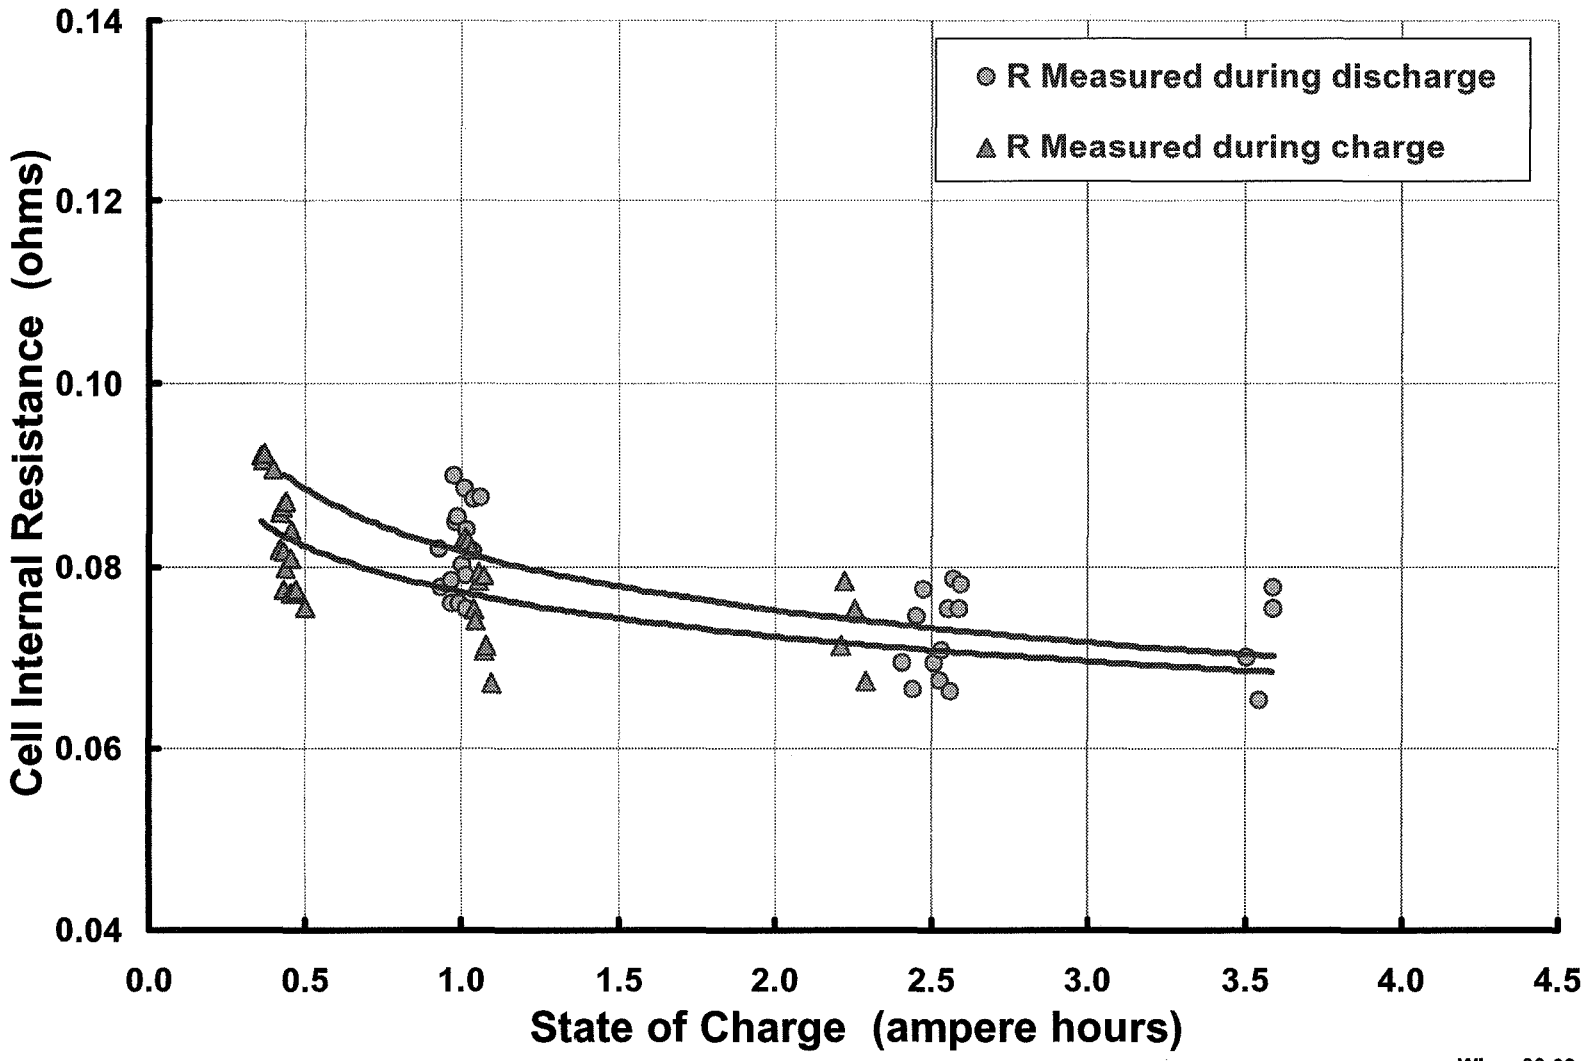

MP Cell LEO Cycling

Typical 25% DOD LEO Cycle (25°C)

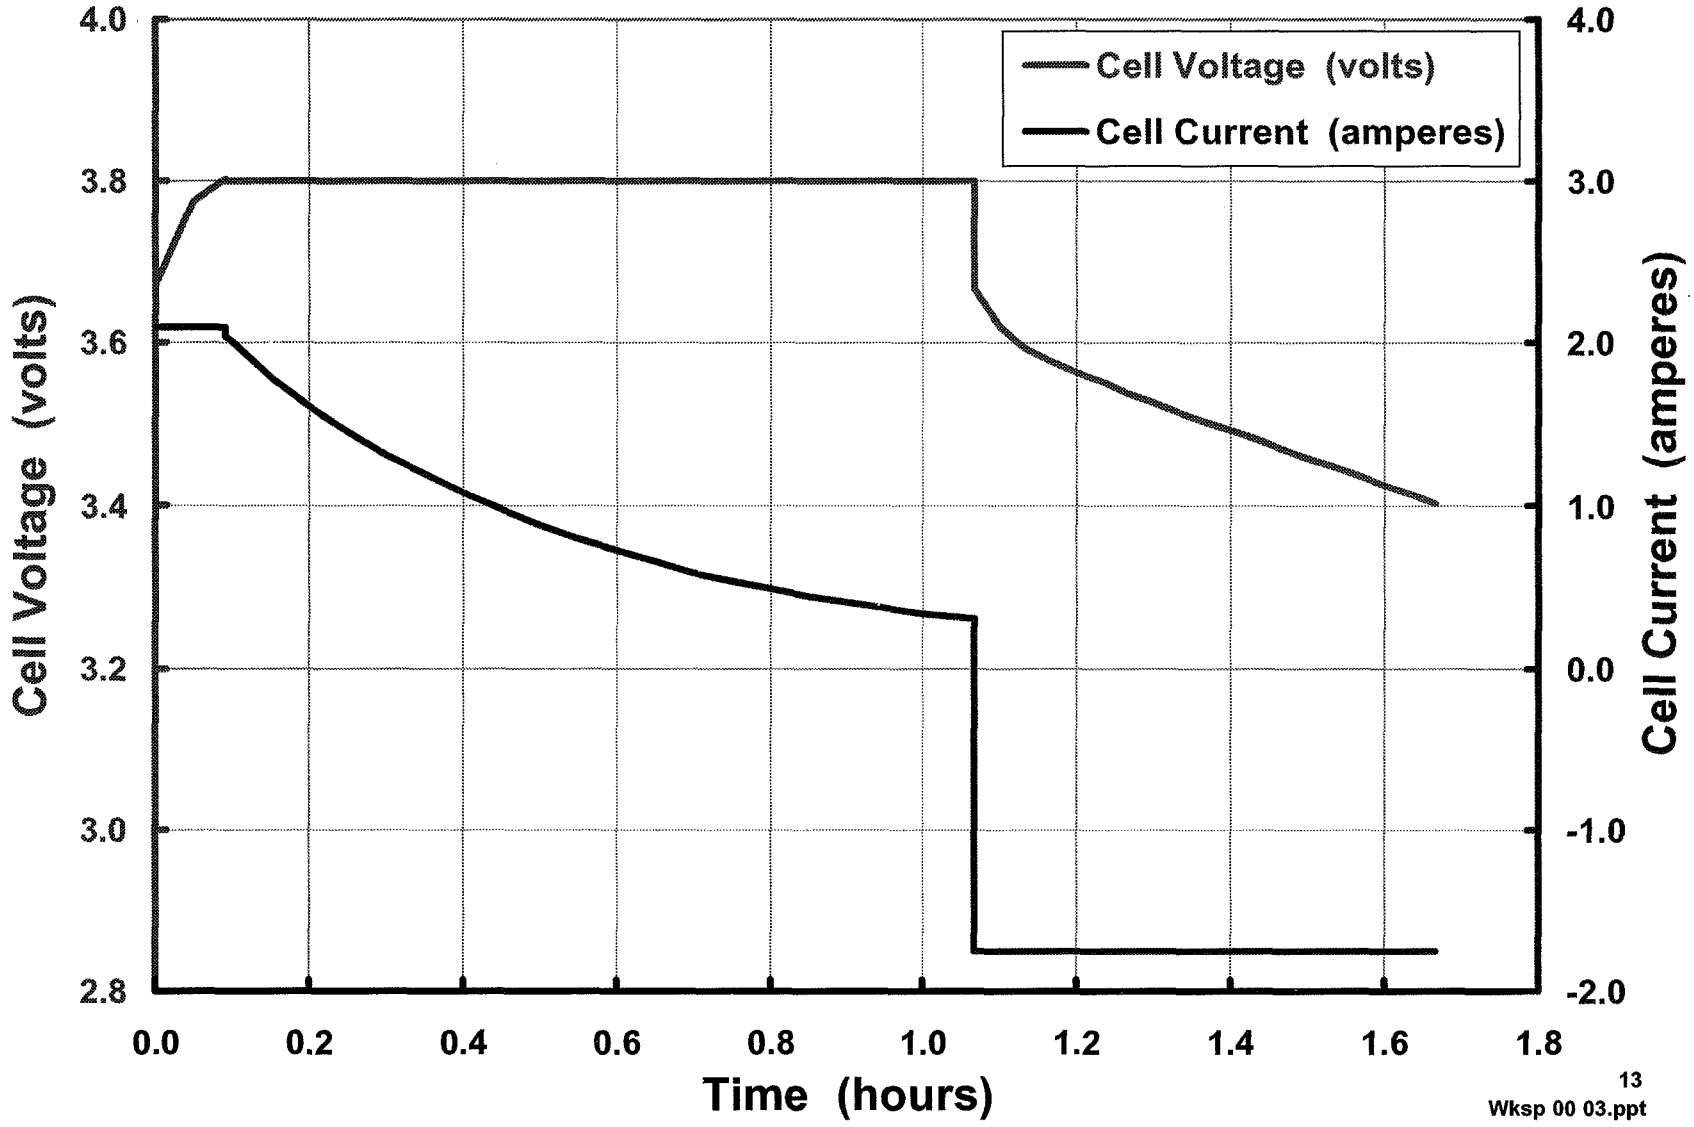

MP Cell LEO Cycling

EODV as a function of cycling at 25ºC

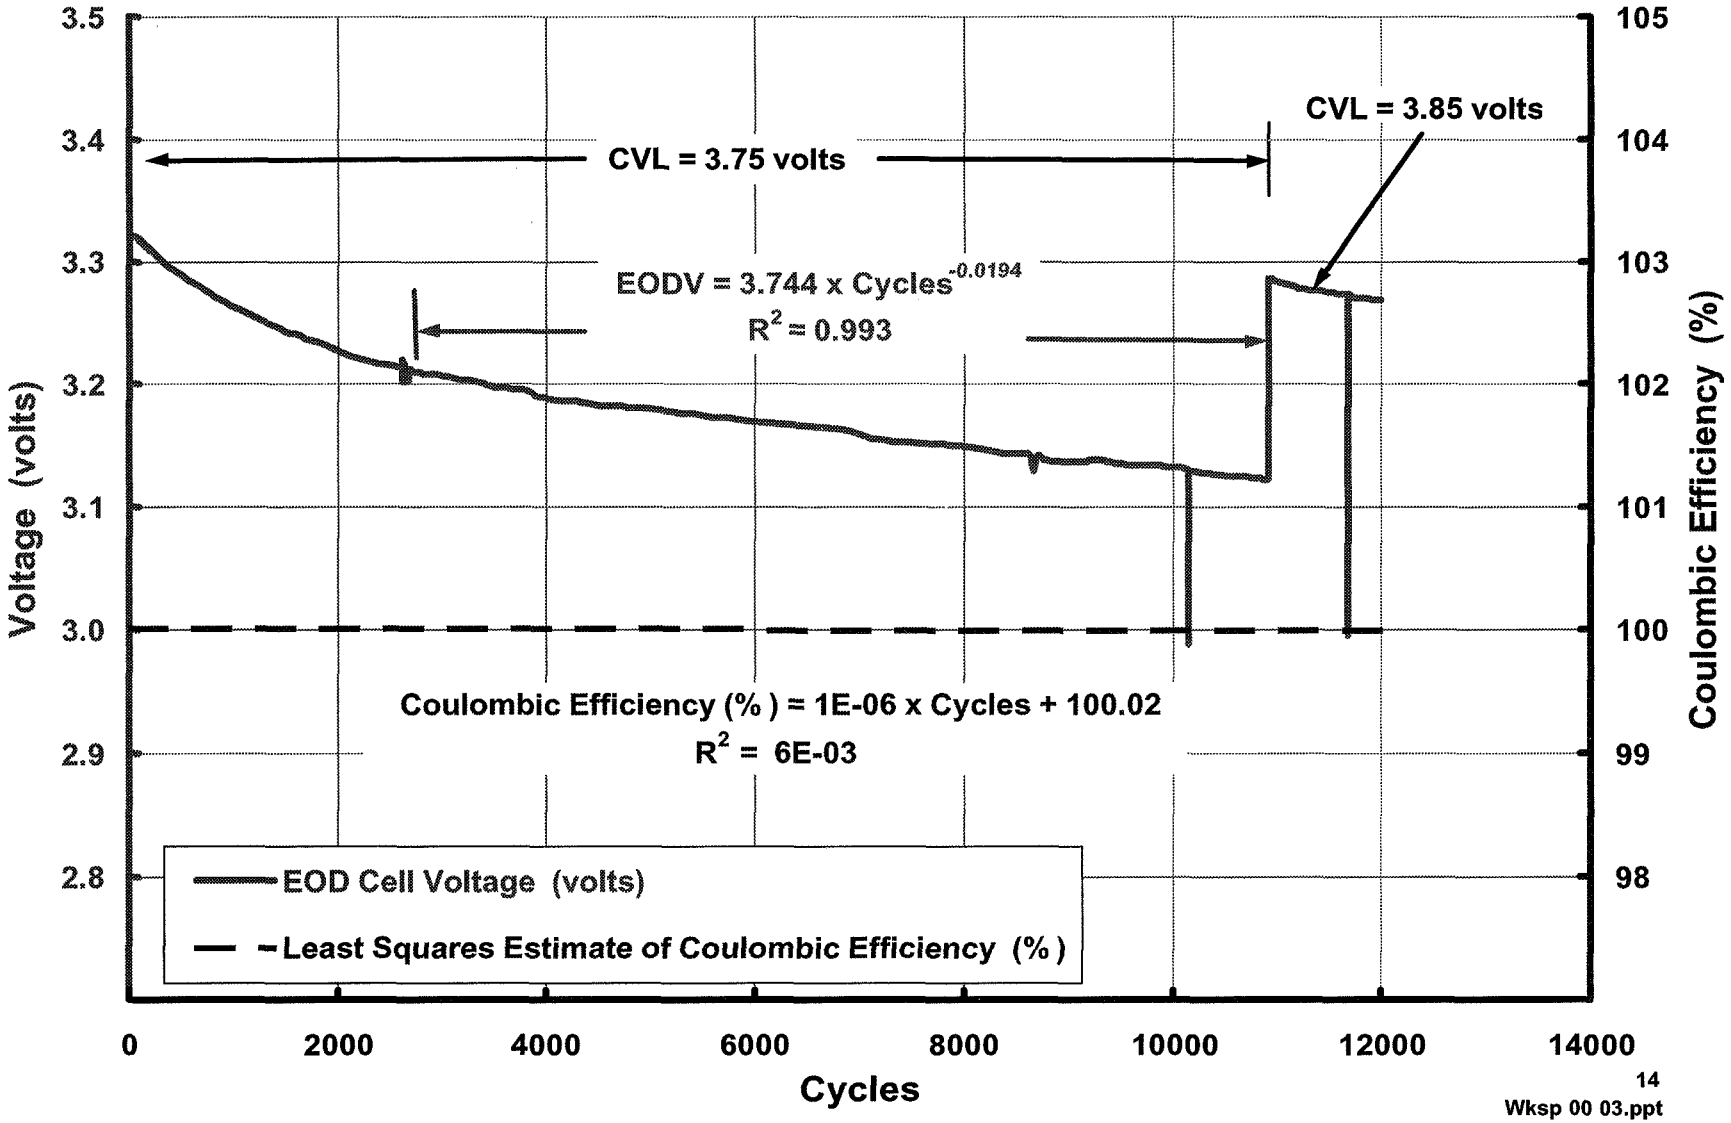

MP Cell LEO Cycling

EODV as a function of cycling at 15ºC

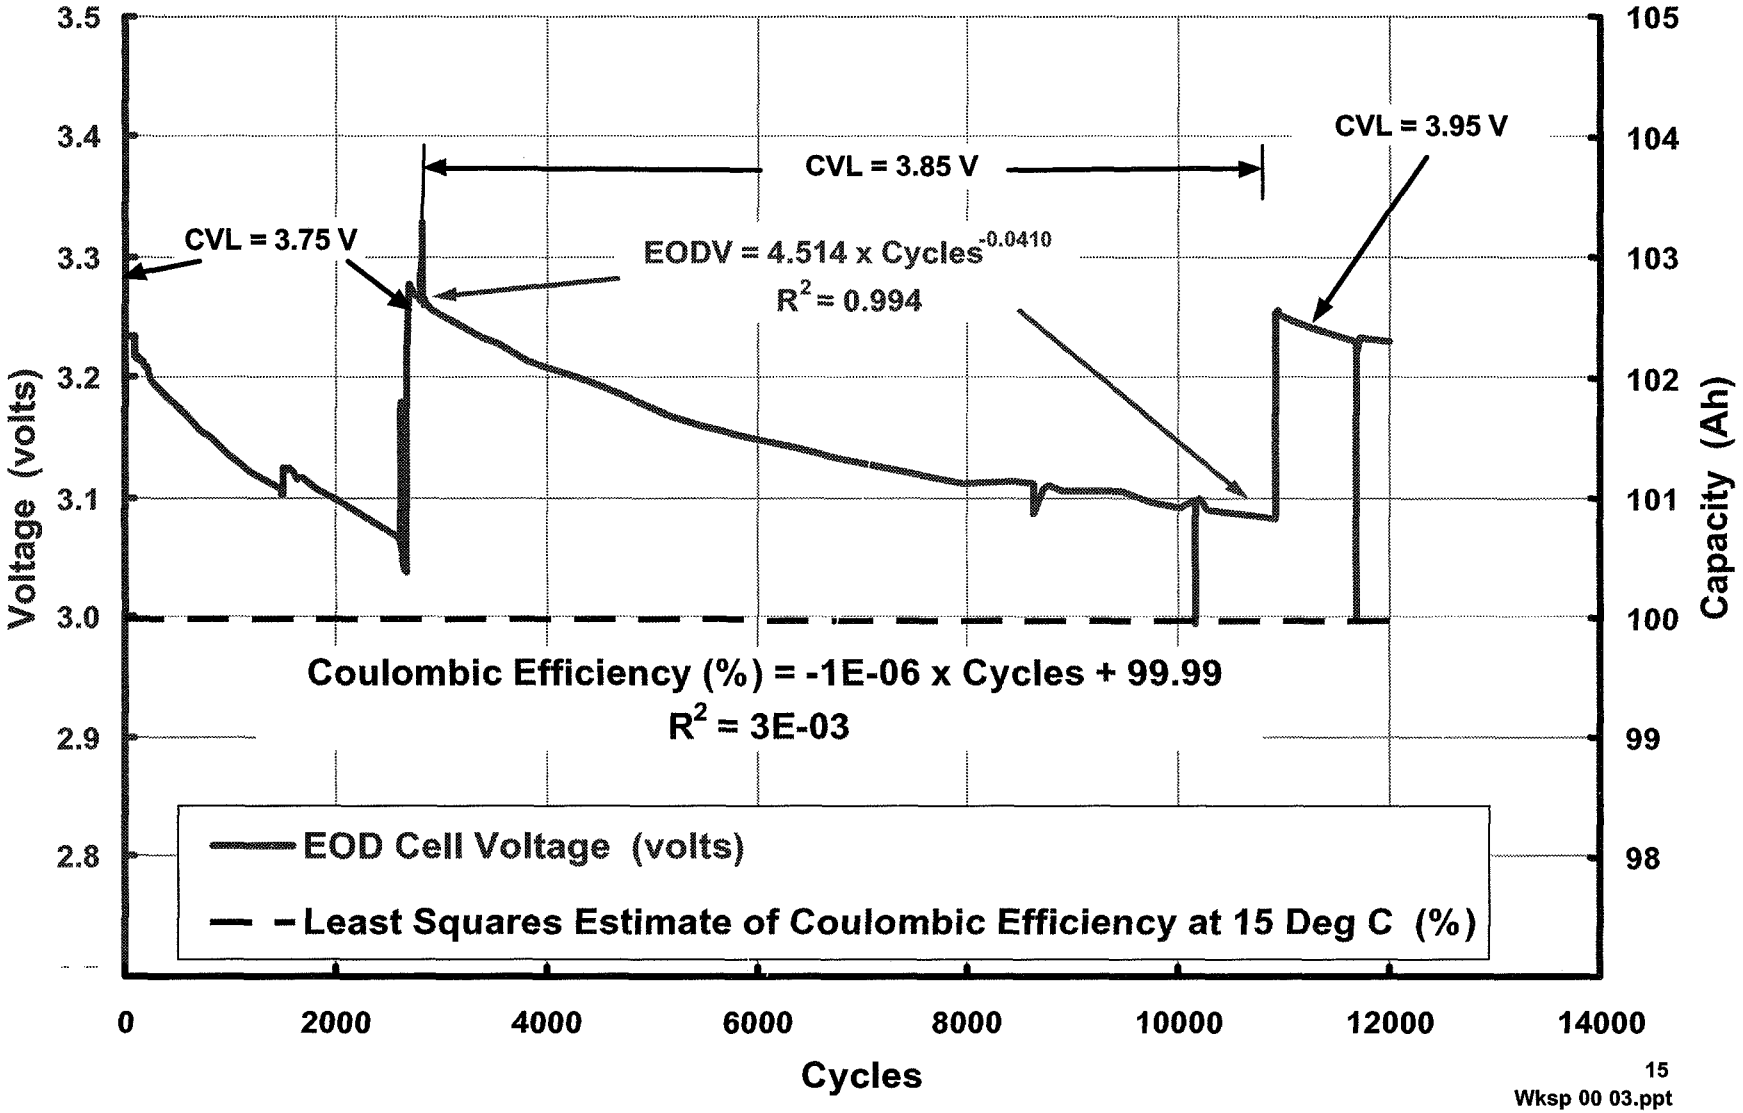

MP Cell LEO Cycling

Reserve Capacity Estimate (25 Deg C)

		Capacity (Ah) -- Charge: 3.75V CVL + taper			
Time (Years)	Temp (Deg C)	Discharge to 3.0V	Discharge to 25% of BOL 4.0V CVL capacity	Reserve	Loss
BOL	25	2.54	1.07	1.47	
2.0	25	1.35	1.07	0.28	1.19

Capacity (Reserve), 3.75V CVL (Ah) = Capacity (LEO to 3.0V) - Capacity (25% DOD)

Capacity (Loss), 3.75V CVL (Ah) = Capacity (BOL) - Capacity (Time "t")

Reserve Capacity Estimate

Definition of Terms

- Capacity (Reserve), 3.75V CVL (Ah): The capacity remaining, to a 3.0V cutoff, following a 25% DOD discharge, during simulated LEO cydhg.
- Capacity (LEO to 3.0V): Capacity to a 3.0V cutoff, following a simulated LEO charge to a 3.75V CVL and taper charge.
- Capacity (BOL): BOL capacity to a 3.0V cutoff, following charge, at C/5, to a specified CVL and taper charge until the current is <C/100.
- Capacity (25% DOD): 25% of the BOL capacity.
- Capacity (Loss): The difference between capacity at BOL and time "t", determined with comparable charge/discharge parameters..
- Capacity (Time "t"): The capacity observed at a time "t", to a 3.0V cutoff, following a simulated LEO cycle charge to a 3.75V CVL and taper

Prototype Cell Characterization

Charge Acceptance as a Function of CVL and Temperature

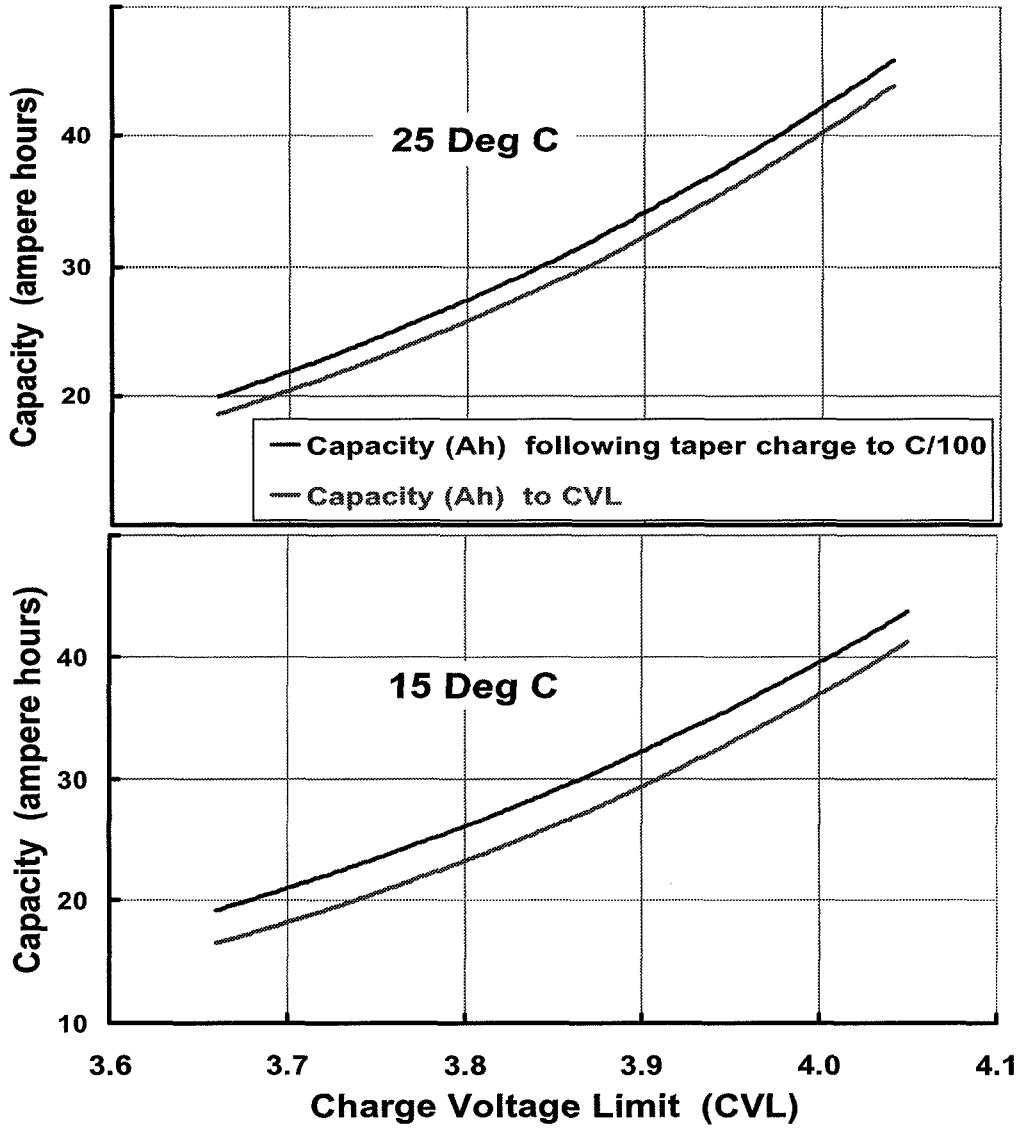

Prototype Cell Characterization

Cell Resistance as a Function of State of Charge and Temperature

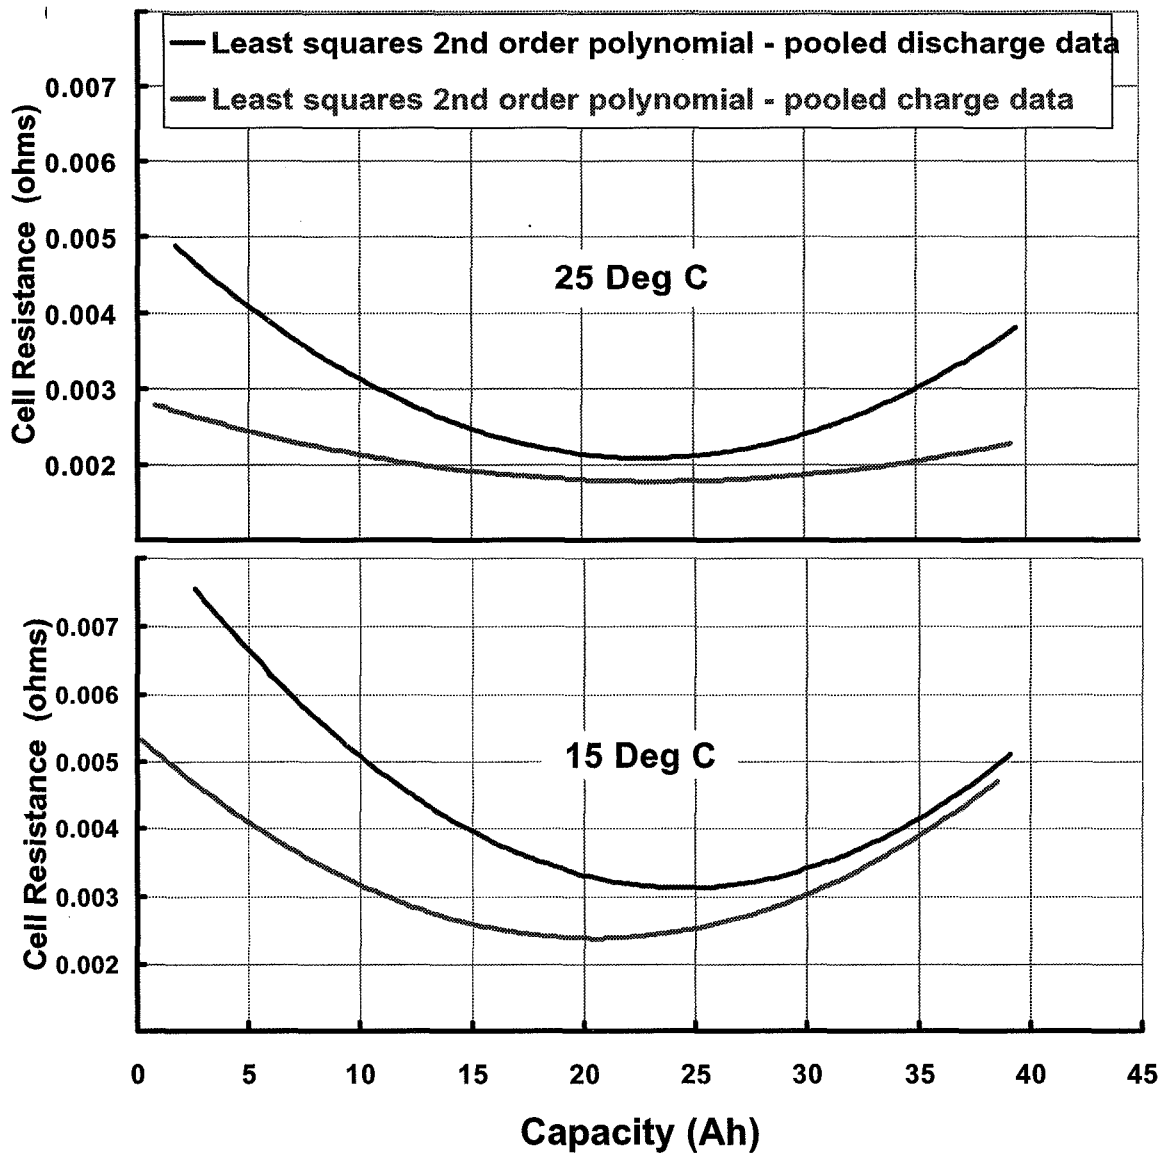

Prototype Cell LEO Cycling

Typical 25% DOD LEO Cycle (25ºC)

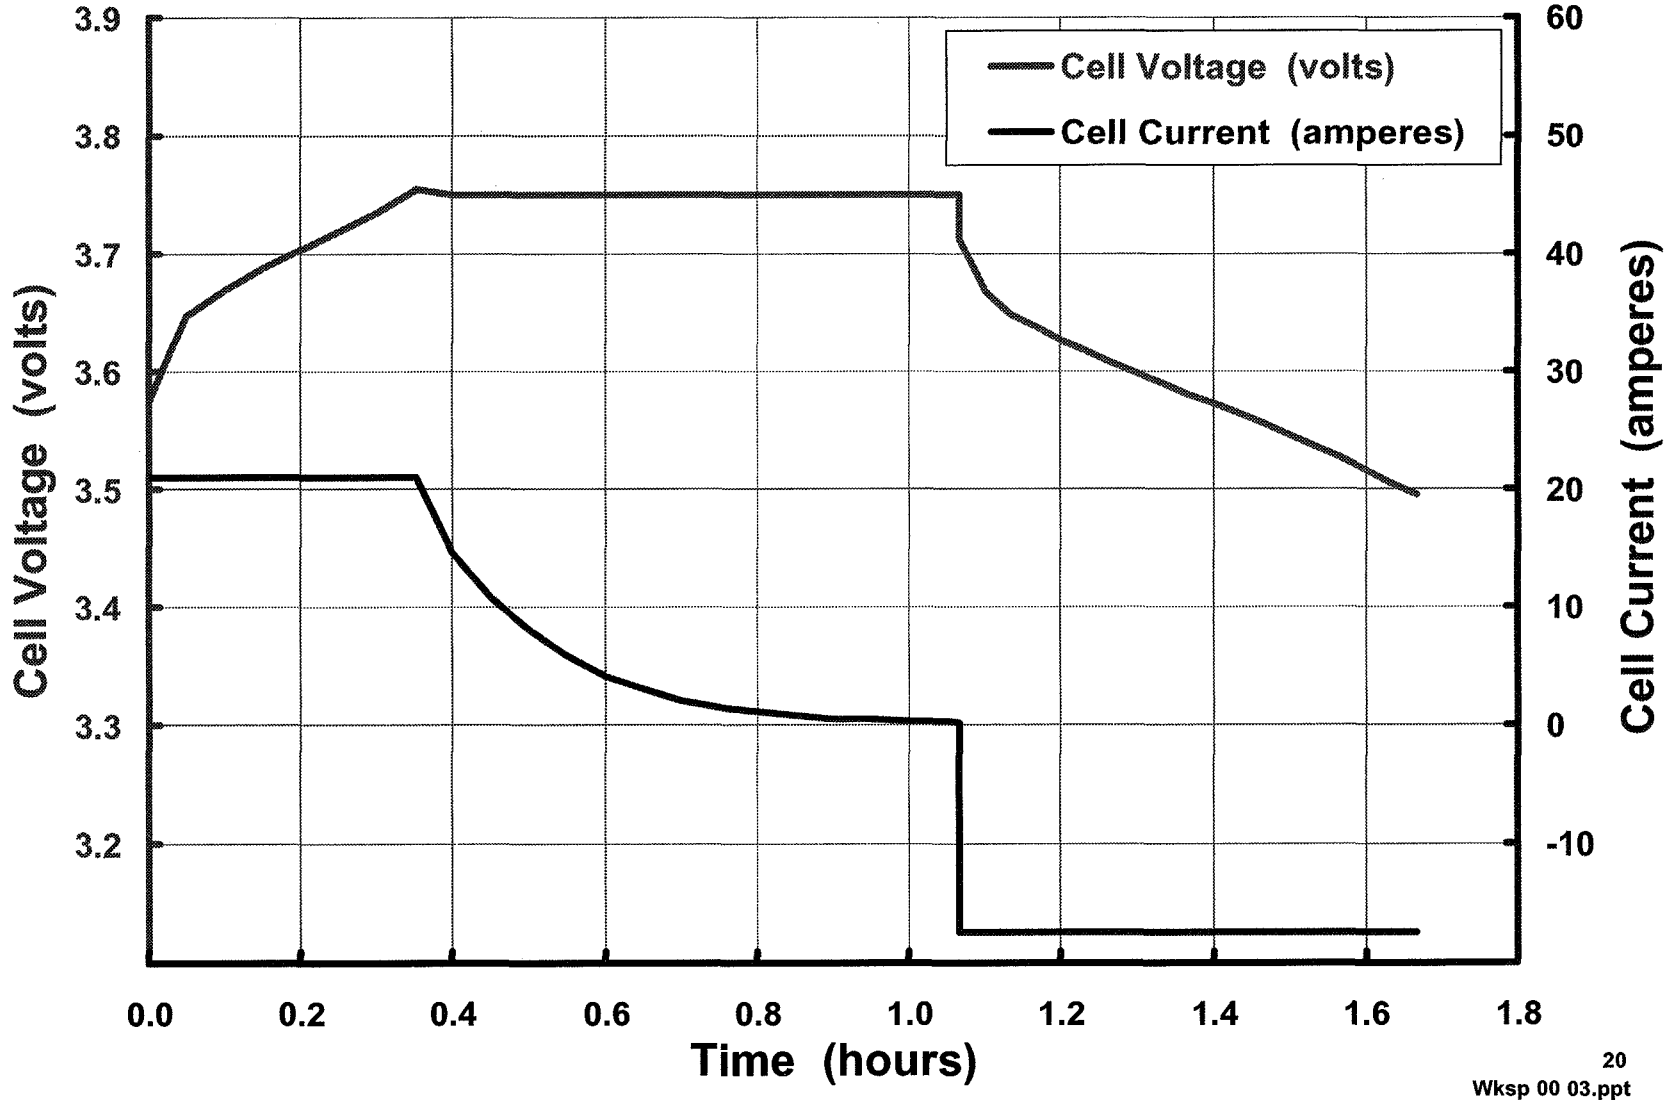

Prototype Cell LEO Cycling

EODV as a Function of cycling at 25ºC

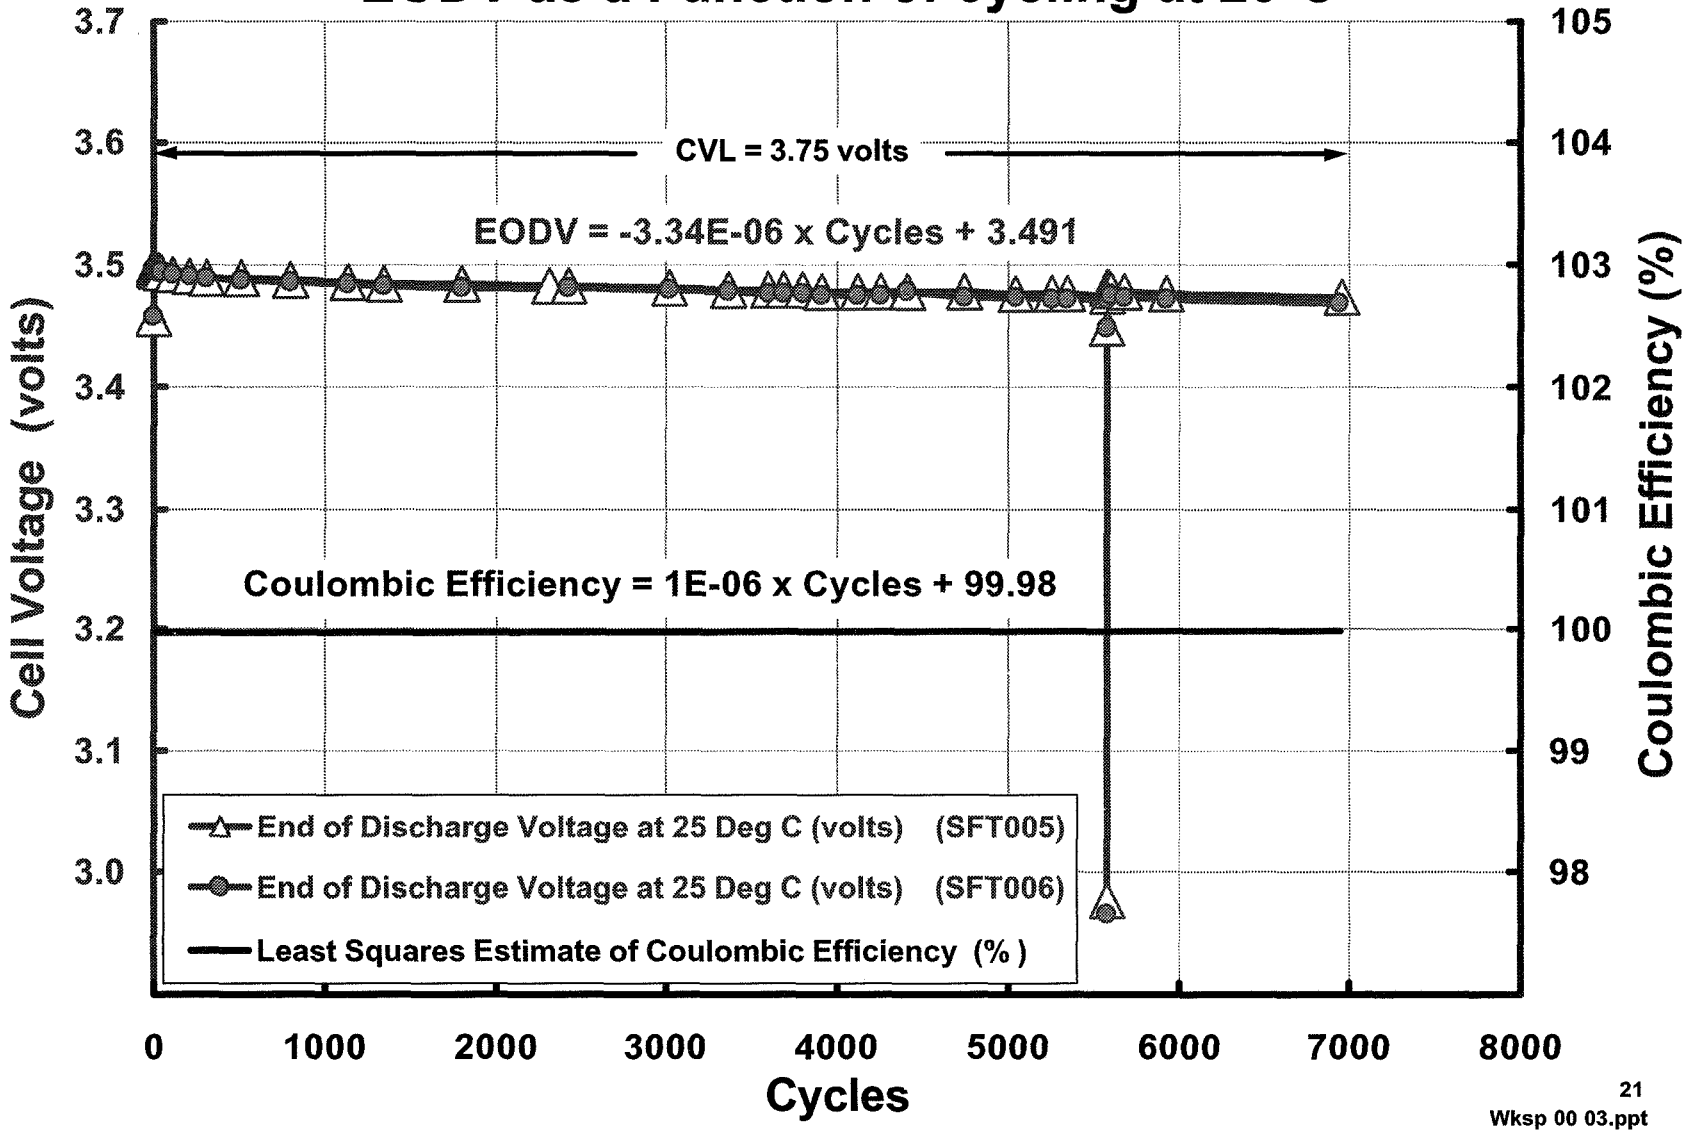

Prototype Cell LEO Cycling

EODV as a Function of cycling at 15ºC

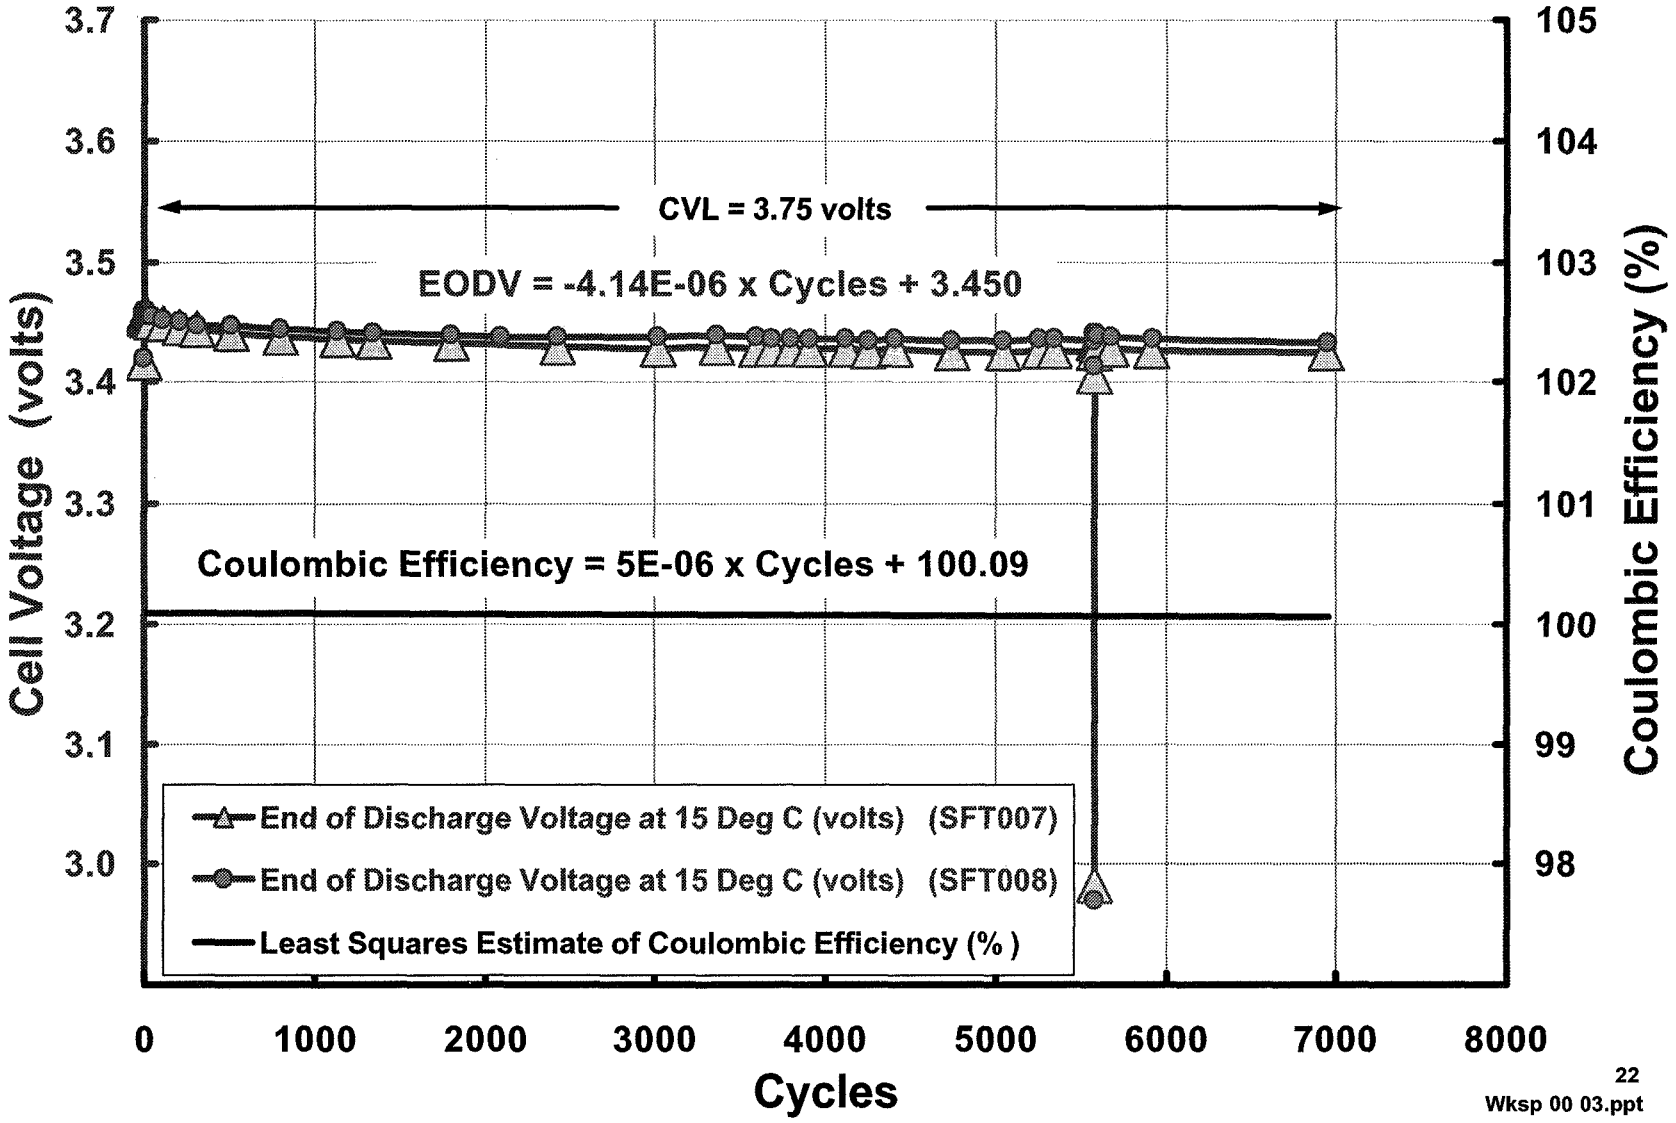

Prototype Cell LEO Cycling

Reserve Capacity Estimate

		Capacity (Ah) -- Charge: 3.75V CVL + taper			
Time (Months)	Temp (Deg C)	Discharge to 3.0V	Discharge to 25% of BOL 4.0V CVL capacity	Reserve	Loss
BOL	25	24.5	10.5	13.9	
13 Months	25	23.8	10.5	13.3	0.7
BOL	15	23.4	10.5	12.9	
13 Months	15	21.4	10.5	10.9	2.0

Capacity (Reserve), 3.75V CVL (Ah) = Capacity (LEO to 3.0V) - Capacity (25% DOD)

Capacity (Loss), 3.75V CVL (Ah) = Capacity (BOL) - Capacity (Time "t")

Summary

- SAFT MP 176065 and 42Ah space prototype cells are on test
- Testing includes initial characterization, and simulated, real time 25% DOD LEO cycling
- Initial characterization testing is complete
- MP cells have successfully completed > 2 years of LEO cycling
- 42 Ah cells have successfully completed > 1 year of LEO cycling and the low fade observed is encouraging; results are consistent with approximately 10-year life
- No anomalies have been observed
- Testing is continuing

SAFT

GEO AND LEO LIFE TEST RESULTS ON VES140 SAFT Li-Ion

Y. Borthomieu, J.P. Planchat

Defense and Space Division

SAFT POITIERS

AGENDA

- VES140 Cell Design
- Qualification Status
- Calendar Effect Results
- Life Test Results
- Conclusions

SAFT

Lithium-Ion Advantages for Space Applicatio

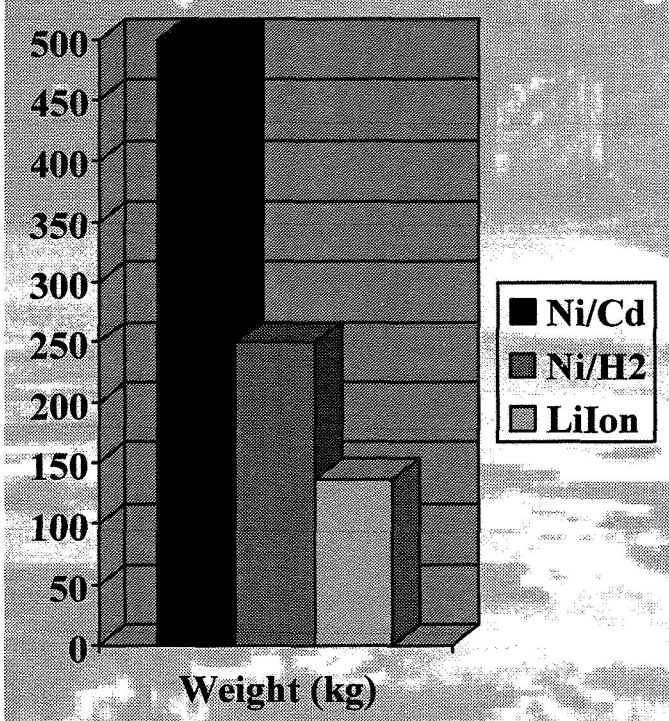

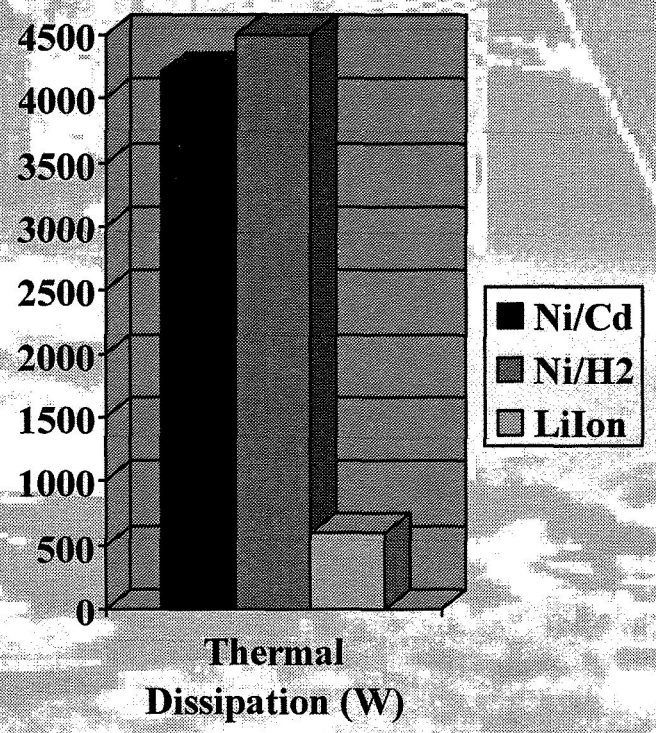

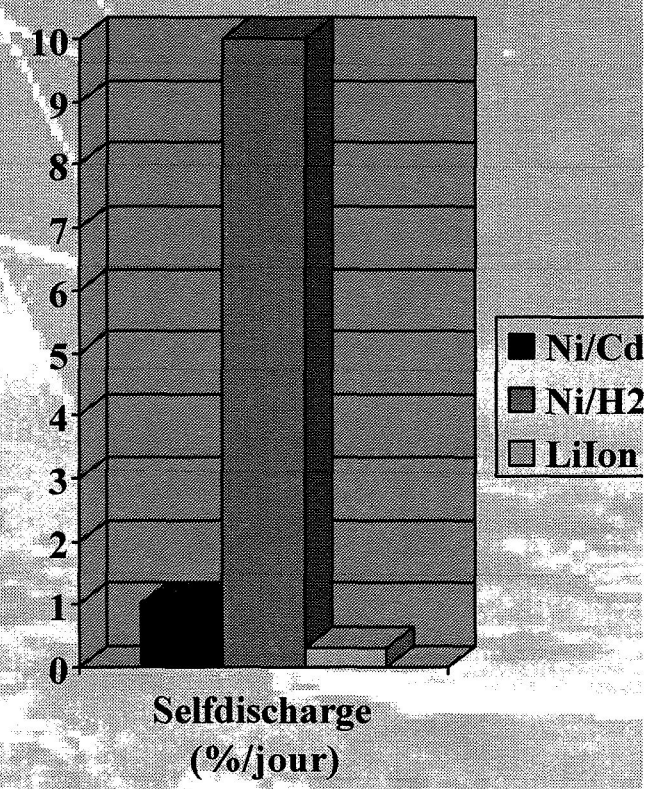

For 12 kW Battery

SAFT

Li-Ion cells in parallel

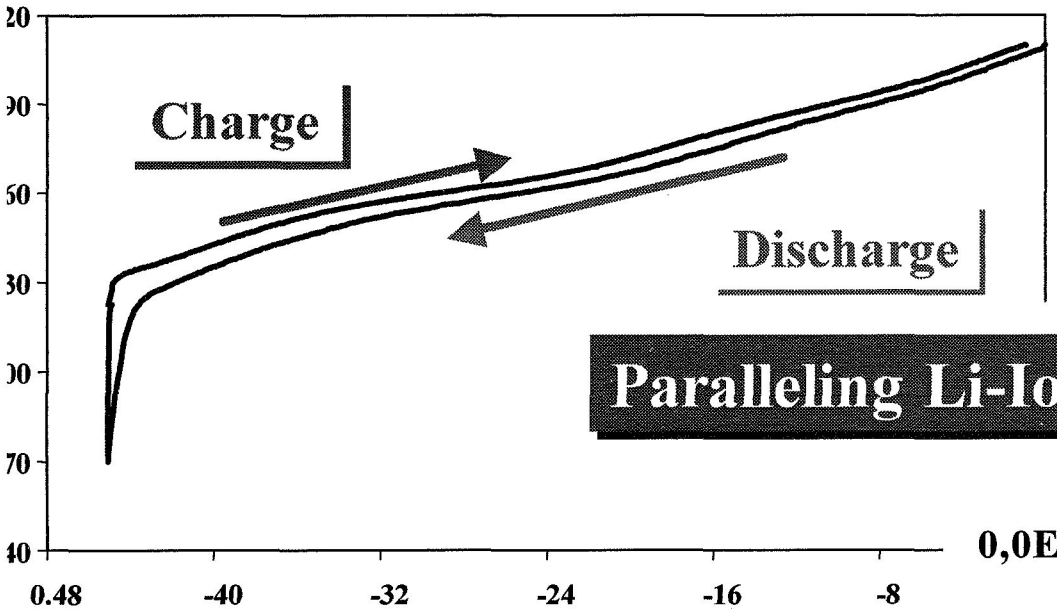

Low impact of Temperature on OC

Paralleling Li-Ion cells is OK

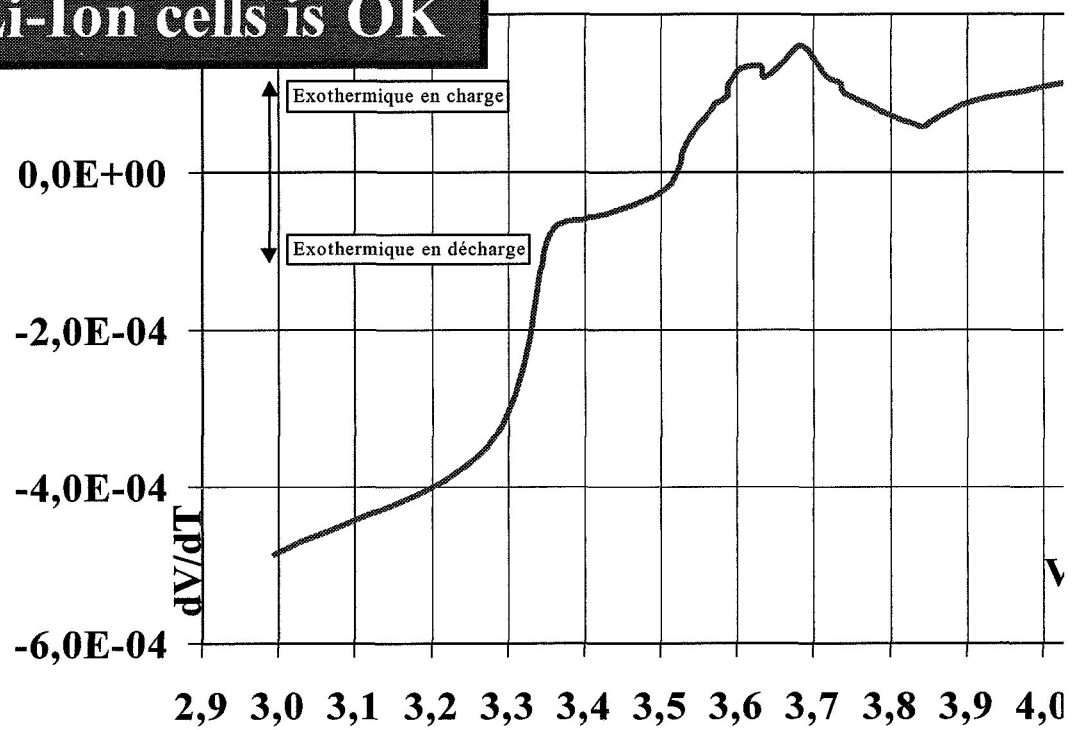

Voltages is function of intercalated Lithium ions

$Li_{0.85}Ni_{(1-Y)}M_YO_2+3C \leftrightarrow Li_{0.35}Ni_{(1-Y)}M_YO_2+0.5LiC_6$

SAFT

VES 140 S Cell design

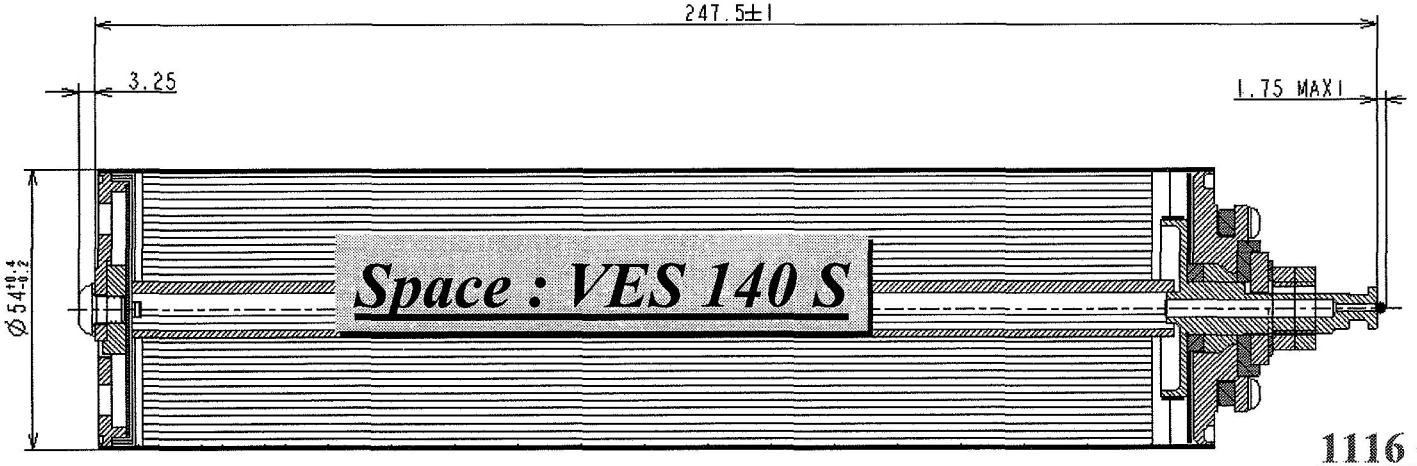

1116 +/- 25 g

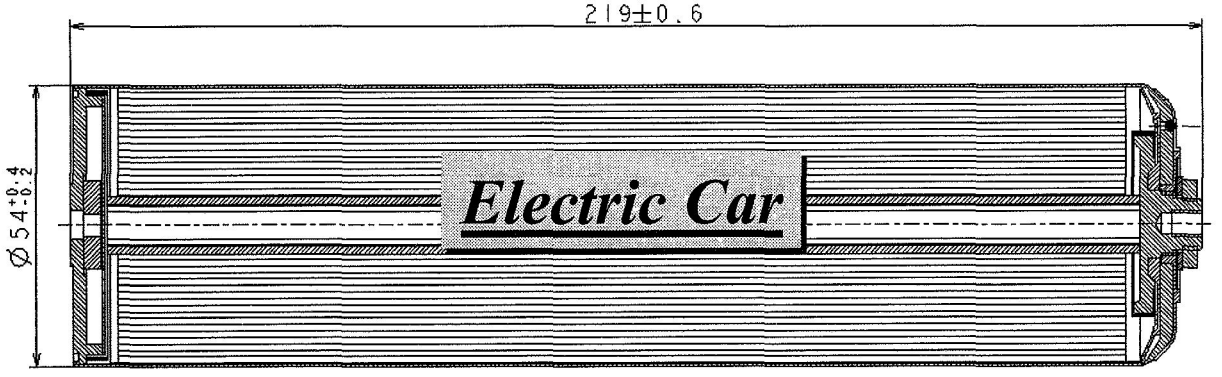

1074 +/- 25 g

SAFT

Qualification Program

- GEO real time life test
- GEO Accelerated life test
- BOL Qualification
- Calendar Test
- LEO Accelerated life test
- LEO real time life test

Qualification GEO

Qualification LEO

SAFT

Qualification

Qualification Review the 21st June 00 with CNES, ESA ASTRIUM and ASPI :

- Electrical tests
- Mechanical tests
- Abuse tests
  - « overcharge » : charge up to 4.5 V
  - « overdischarge »
  - short circuit
  - high temperature test

SAFT

Energy versus EOCV

Energy versus UEOCV; Charge 9 A, Disch 17.5 A, T = + 20 °C

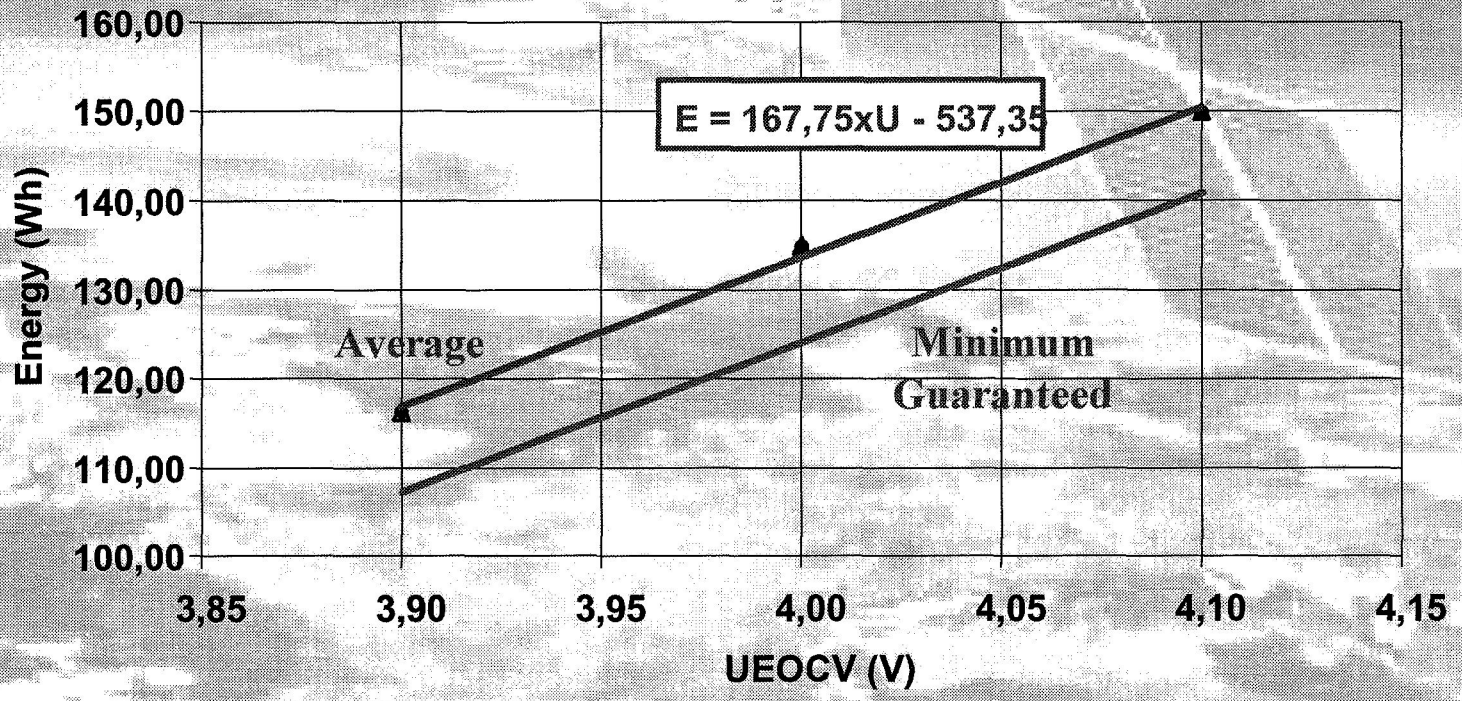

SAFT

Energy versus I discharge

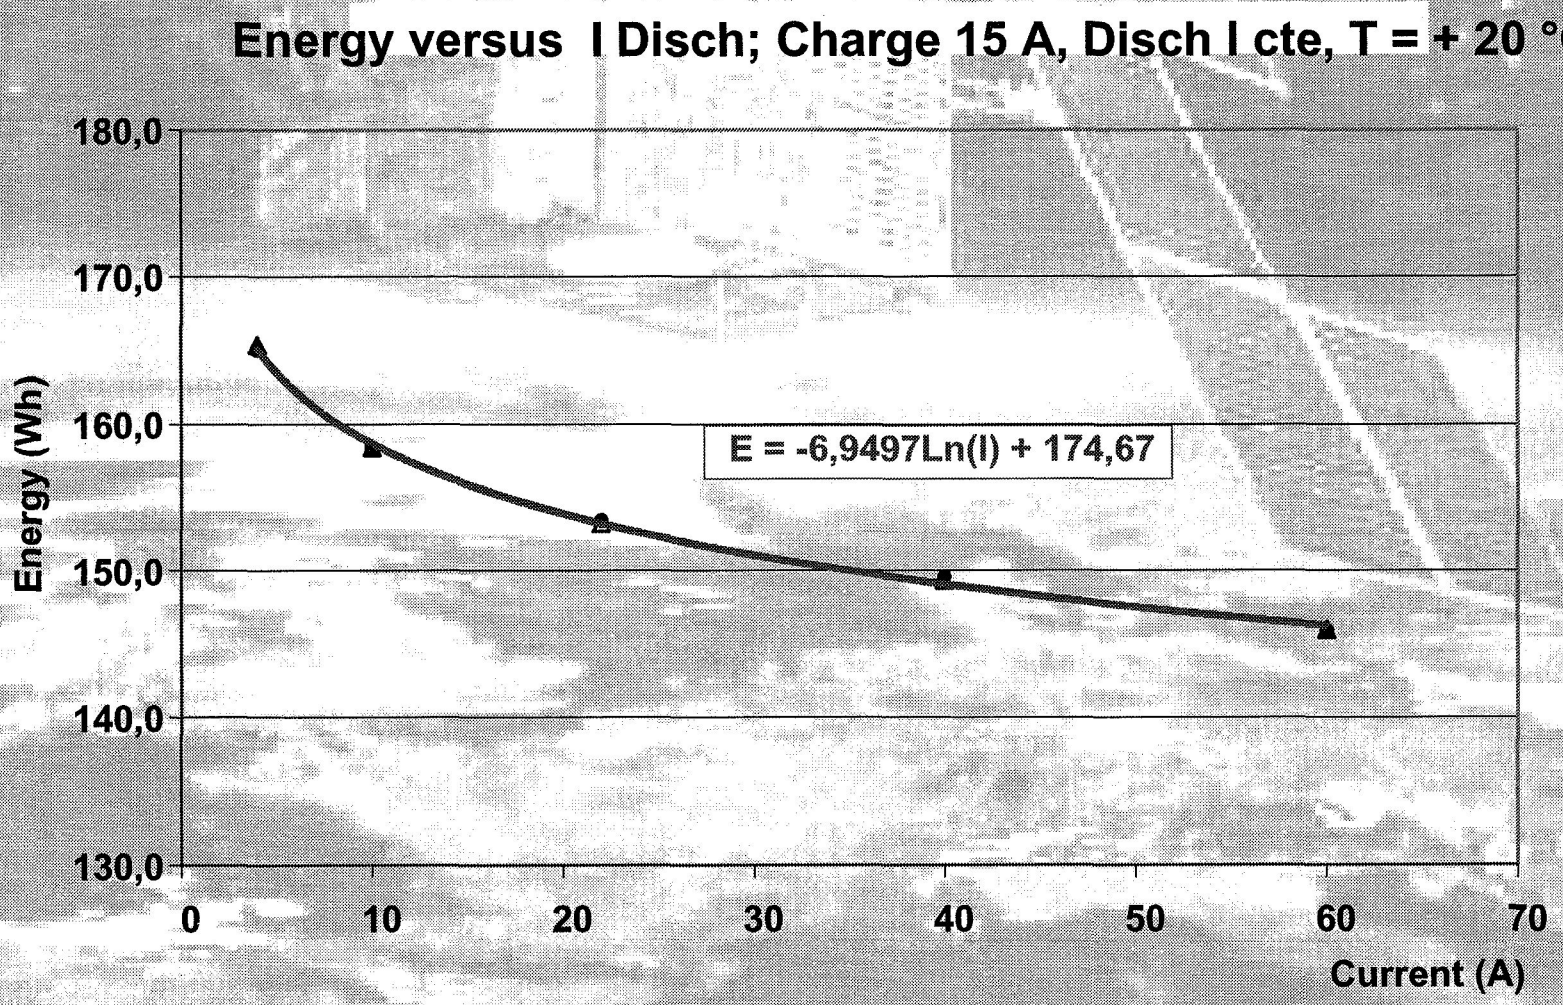

SAFT

Energy versus Power

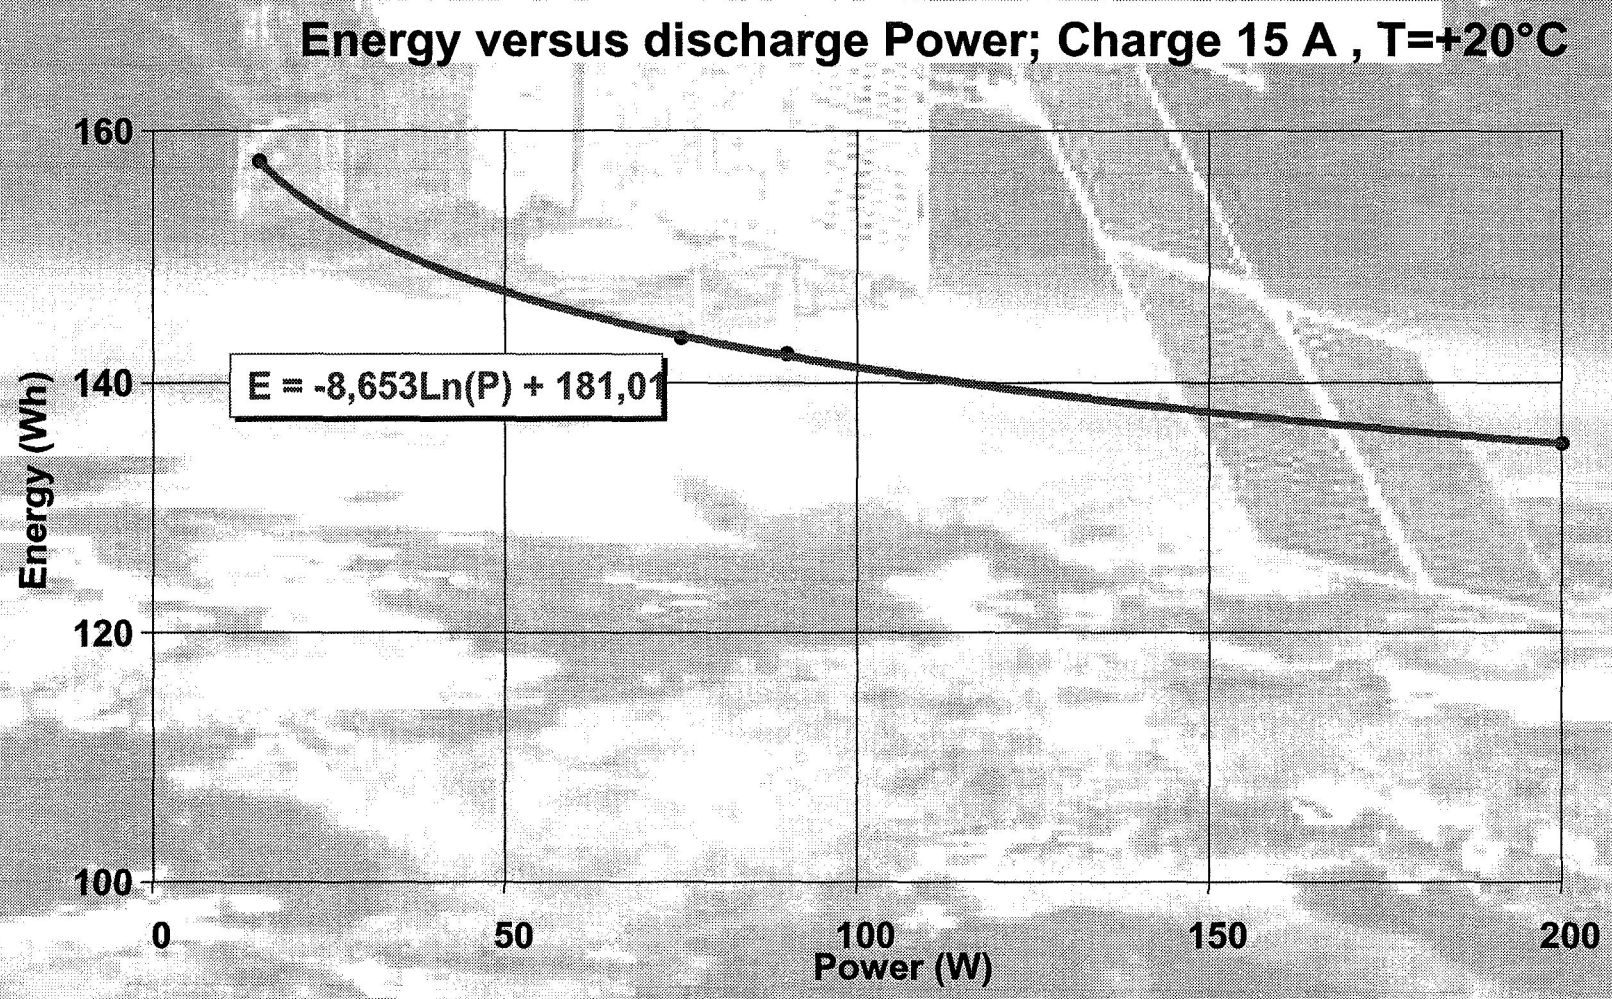

SAFT

Energy versus discharge temperature

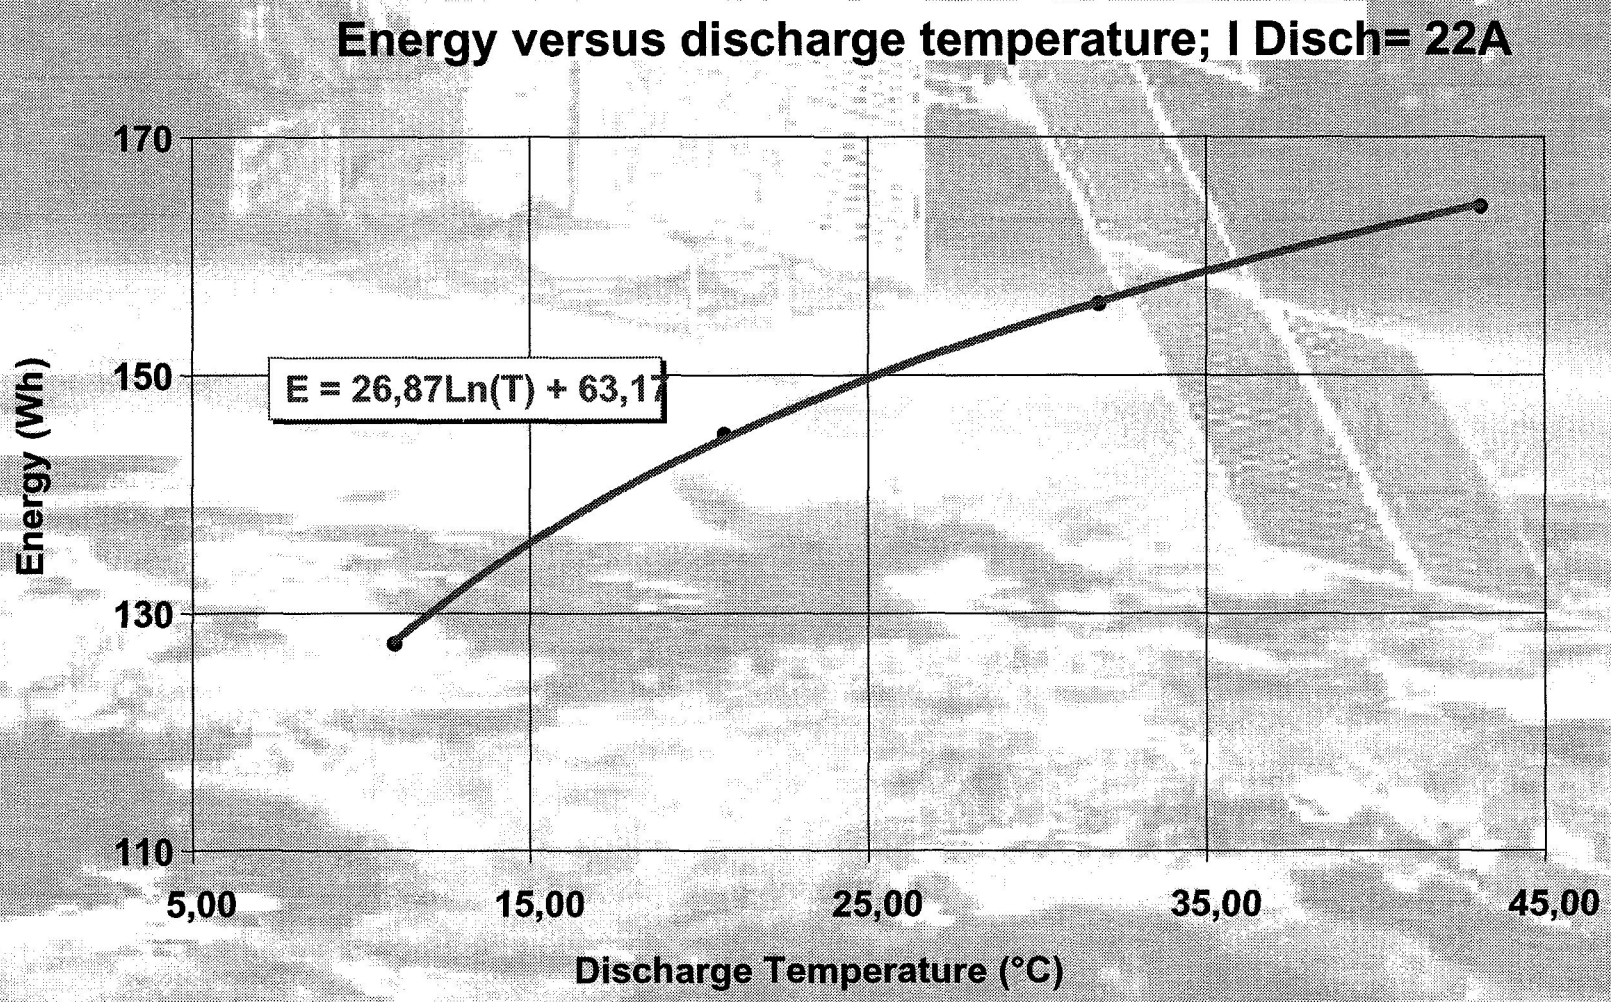

SAFT

Sine Vibrations

- Vibrations performed on 3 cells :
  - charged at 3.8 V

Sweep rate, 2 octave / min, in OX and OZ

Frequency	Level
5 to 24 Hz	± 11 mm
24 to 100 Hz	25 g

SAFT

Random Vibrations

OZ axe level (3 min):

Frequency	Level
20 to 100 Hz	+6 dB/Oct
100 to 800 Hz	0.5 g^2/Hz
800 to 1100 Hz	slope
1100 to 1500 Hz	2 g^2/Hz
1500 to 2000 Hz	-6 dB/Oct

OX & OY axe level (6 min):

Frequency	Level
20 to 100 Hz	+ 3 dB/Oct
100 to 150 Hz	0.3 g^2/Hz
150 to 200 Hz	slope
200 to 300 Hz	3 g^2/Hz
300 to 400 Hz	slope
400 to 900 Hz	0.8g^2/Hz
900 to 1000 Hz	slope
1000 to 1100 Hz	2g^2/Hz
1100 to 2000 Hz	- 9 dB/Oct

Global 44.34 gRms

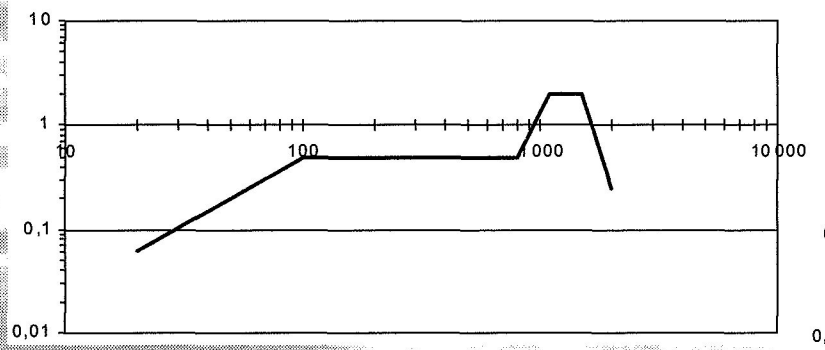

Global 45.32. gRms

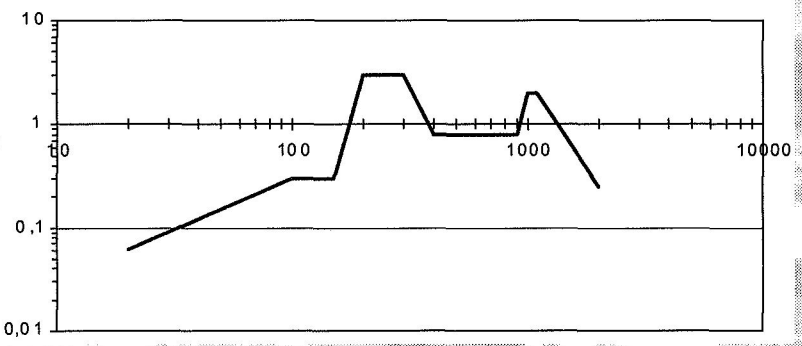

No modification on resonance frequency > 140 hz

No voltage evolution during test

No change on energy and integrity (DPA)

SAFT

Self Discharge

% available Energy versus storage time

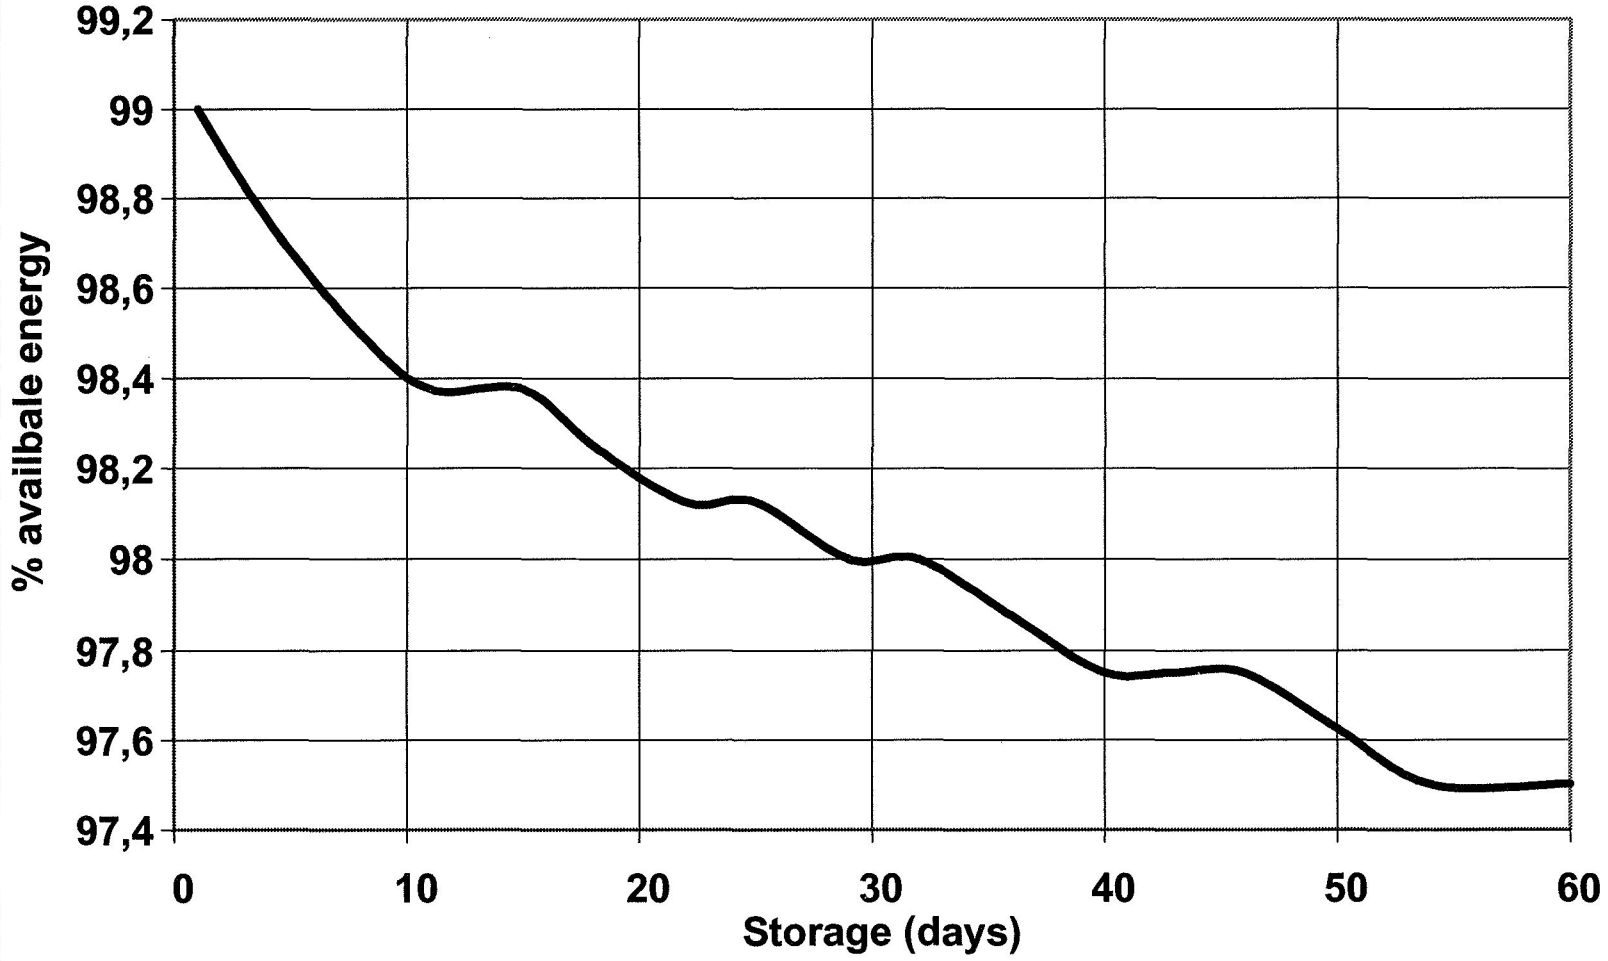

SAFT

Peak Discharge

- 150 Amps (2 secondes)

C/2 discharge

	30 min	60 min	93 min
Cell voltage UEOC = 4.0V	3.348	3.172	2.864
Cell voltage UEOC = 3.8V	3.168	2.887	

- 500 Amps (1 seconde)

	30 min	60 min	93 min
Cell voltage UEOC = 4.0V	2.784	2.593	

SAFT

Overcharge 25 amps @ 4.5 V

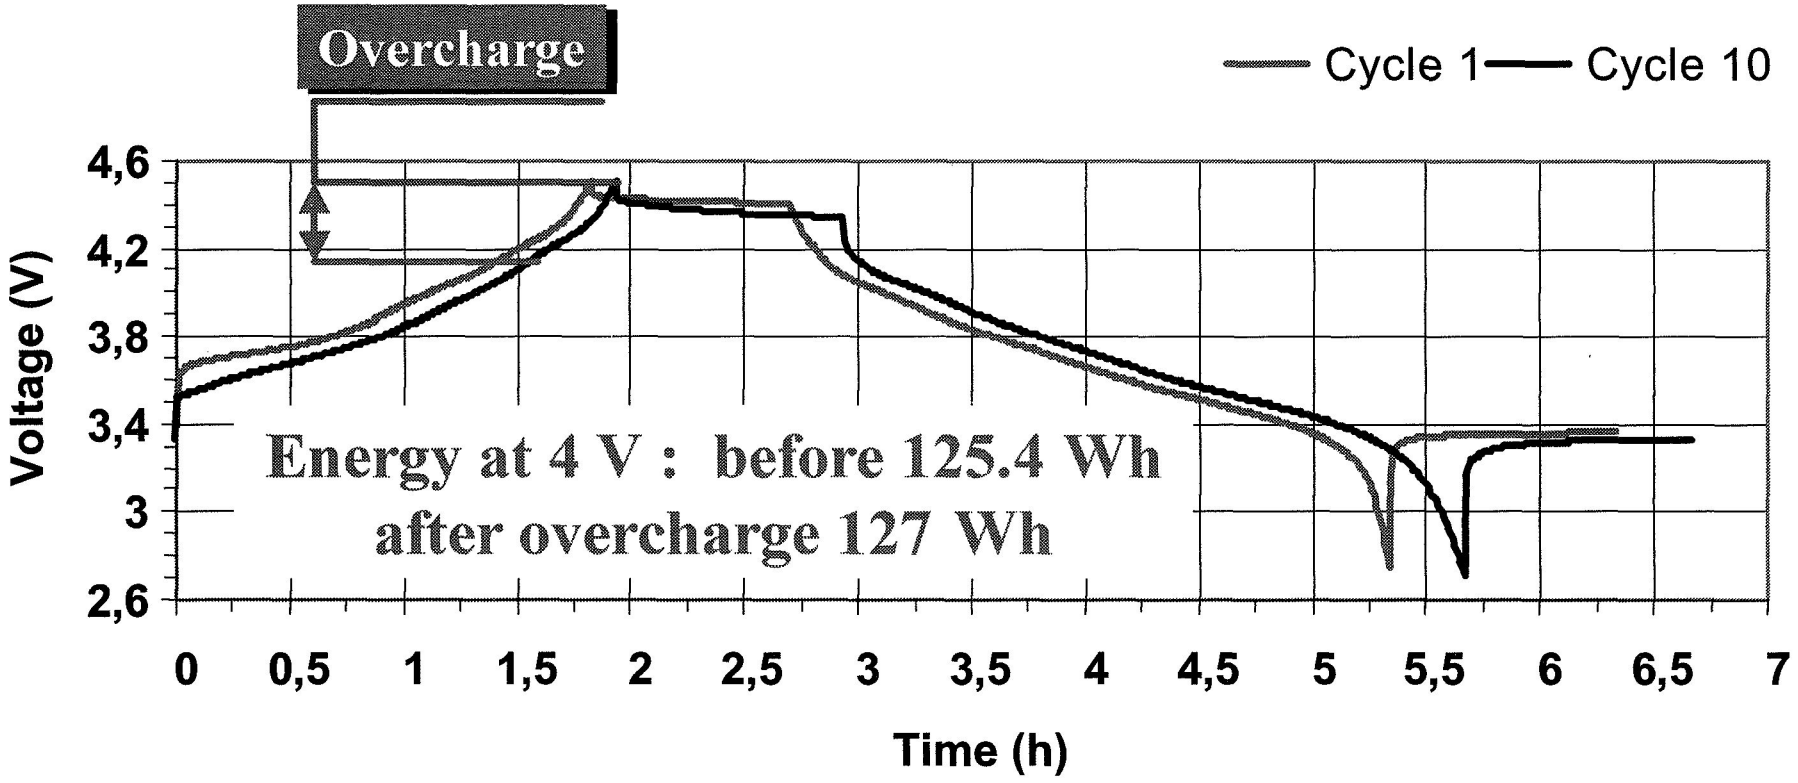

SAFT

Overdischarge

Charge 15.5A EOCV 4.0V, Discharge 20A EODV -0.8V

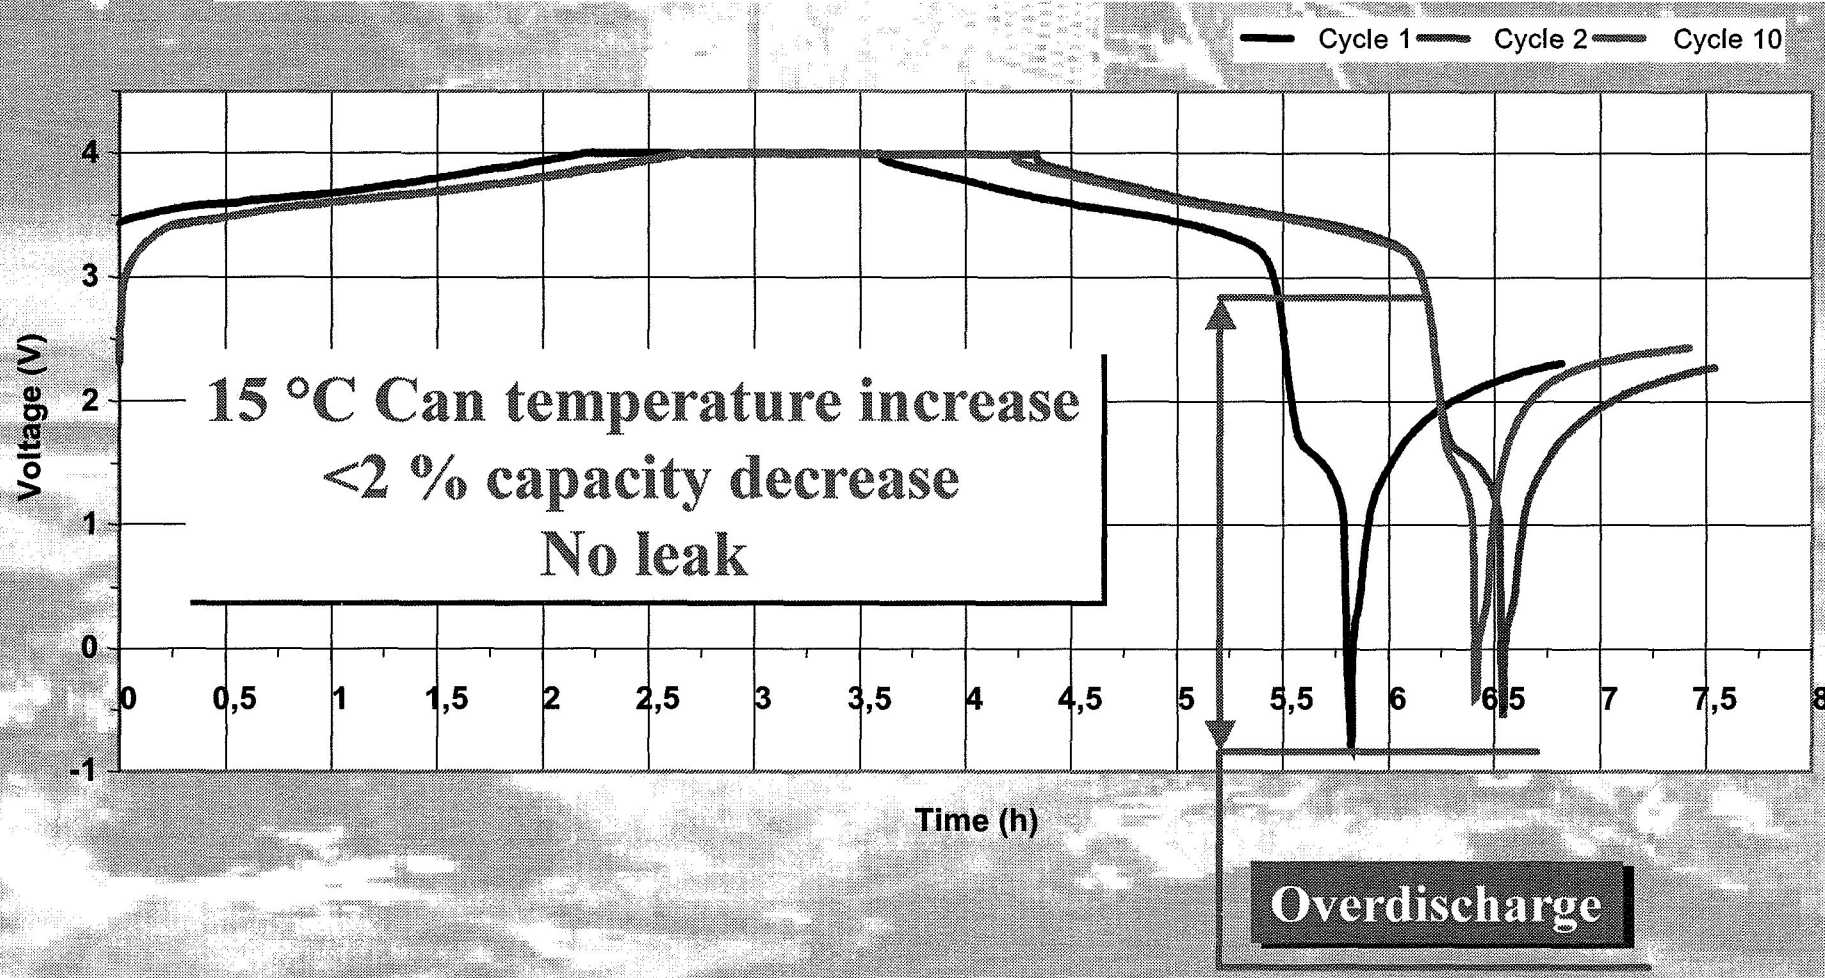

SAFT

Short circuit

SHORT-CIRCUIT R = 3 mOhms
Cell L 369, U EOC = 4,10 V

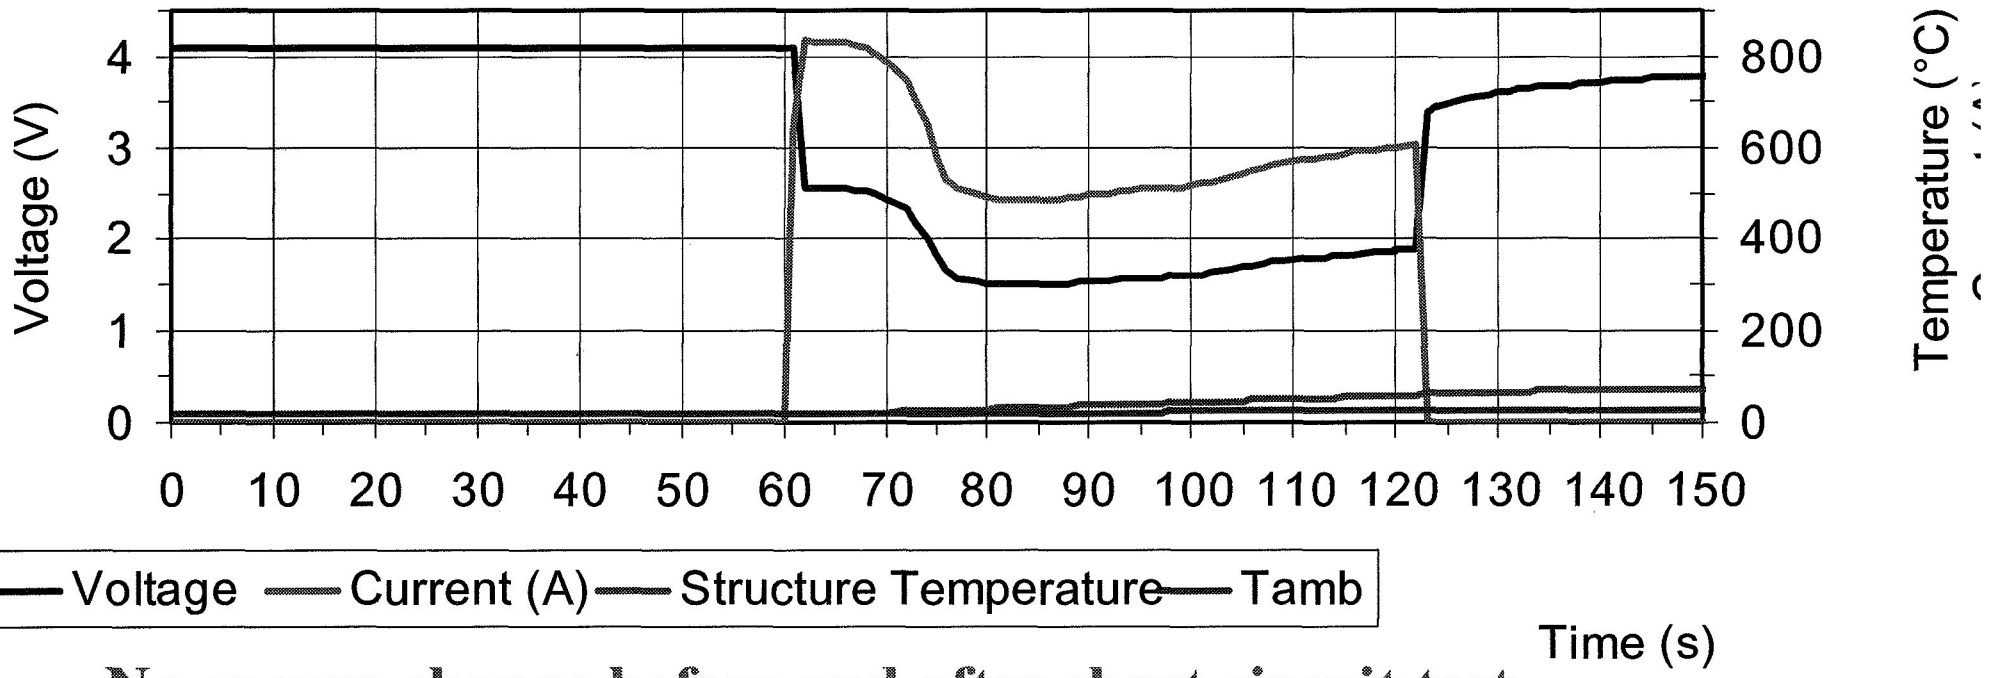

No energy change before and after short circuit test

SAFT

Radiation Test

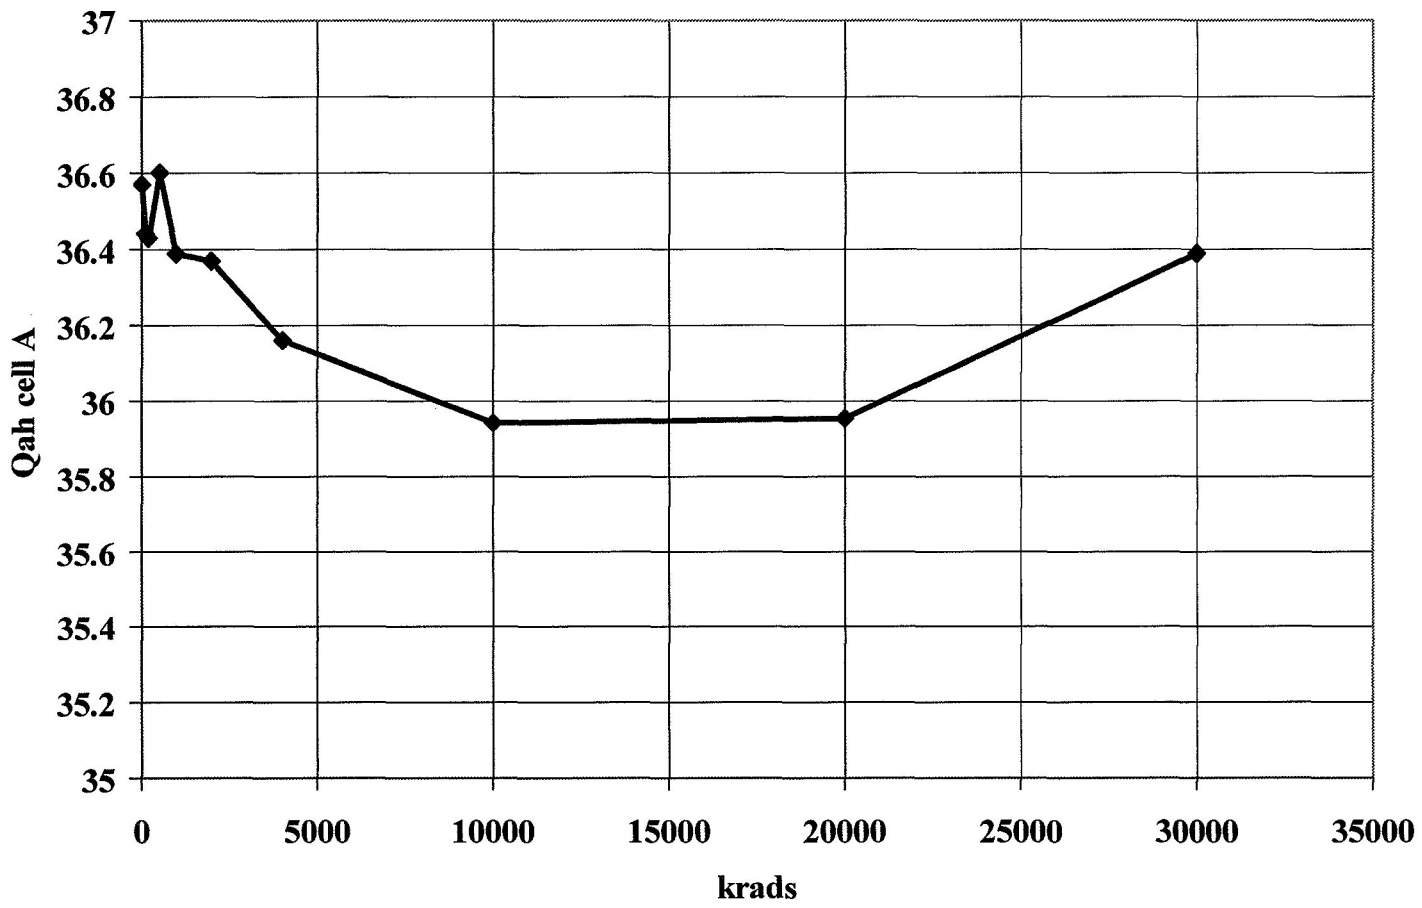

SAFT

Crush Test

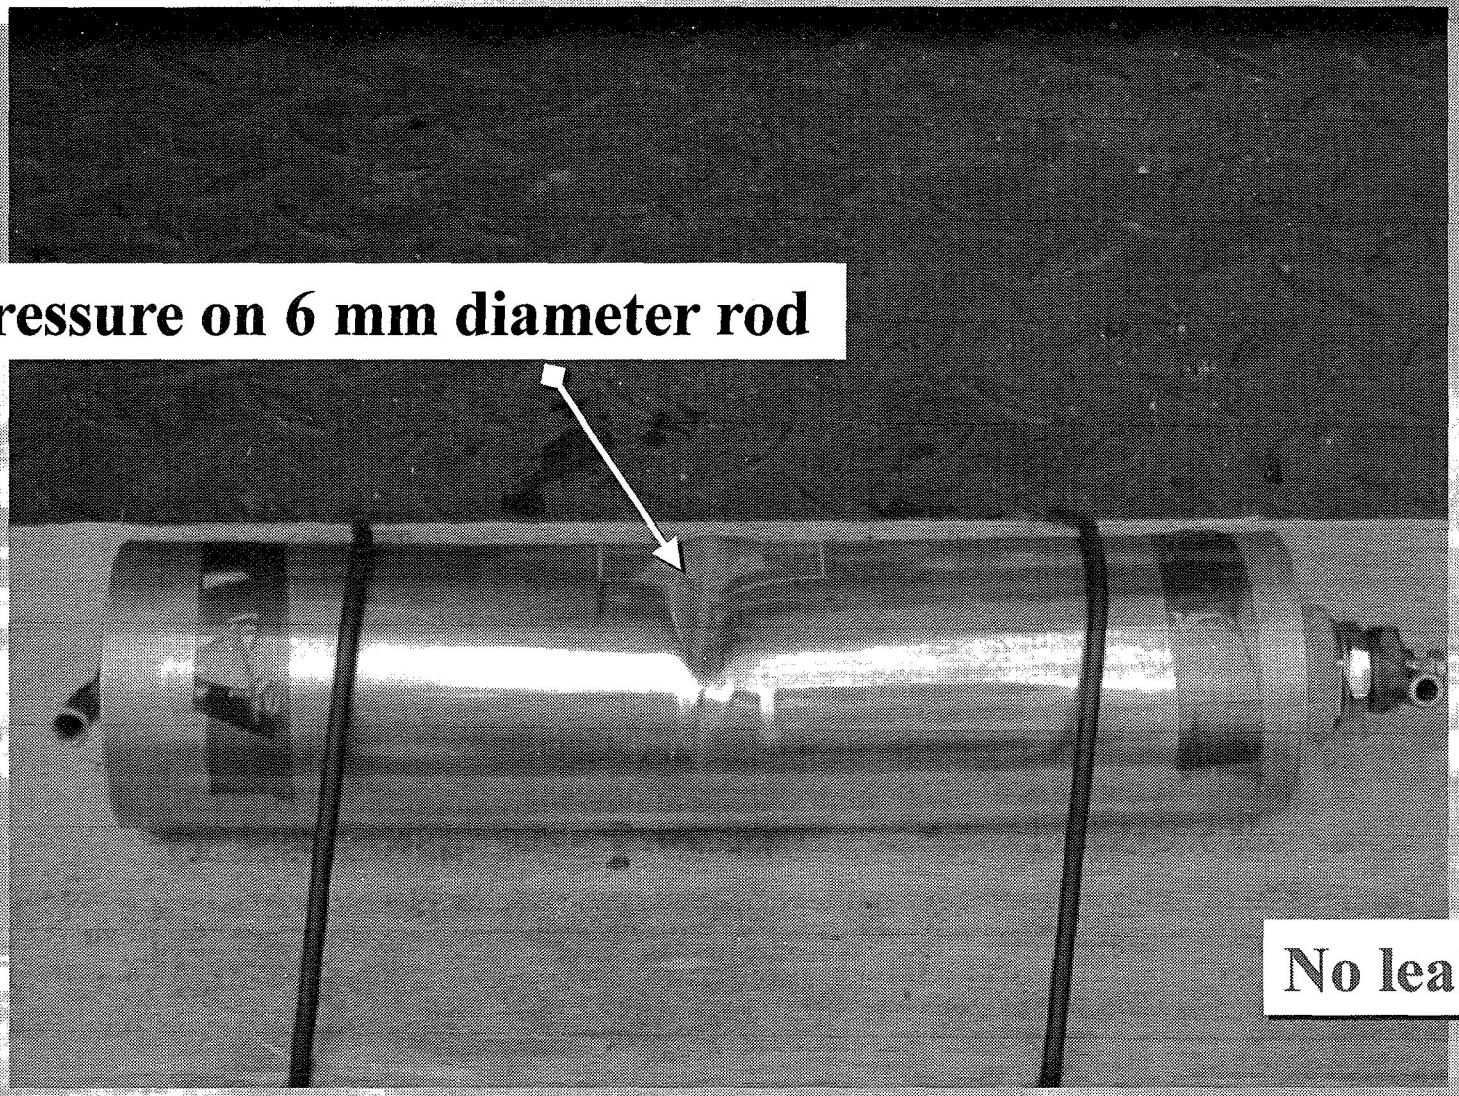

No leak, no sho

SAFT

Calendar Test Plan

Test Plan

- Storage Temperature
  From 0°C to 60°C
- EOCV
  From 3.70 V to 4.10V
- Conditions
  OCV and floating

SAFT

Nickel based alloy specificities

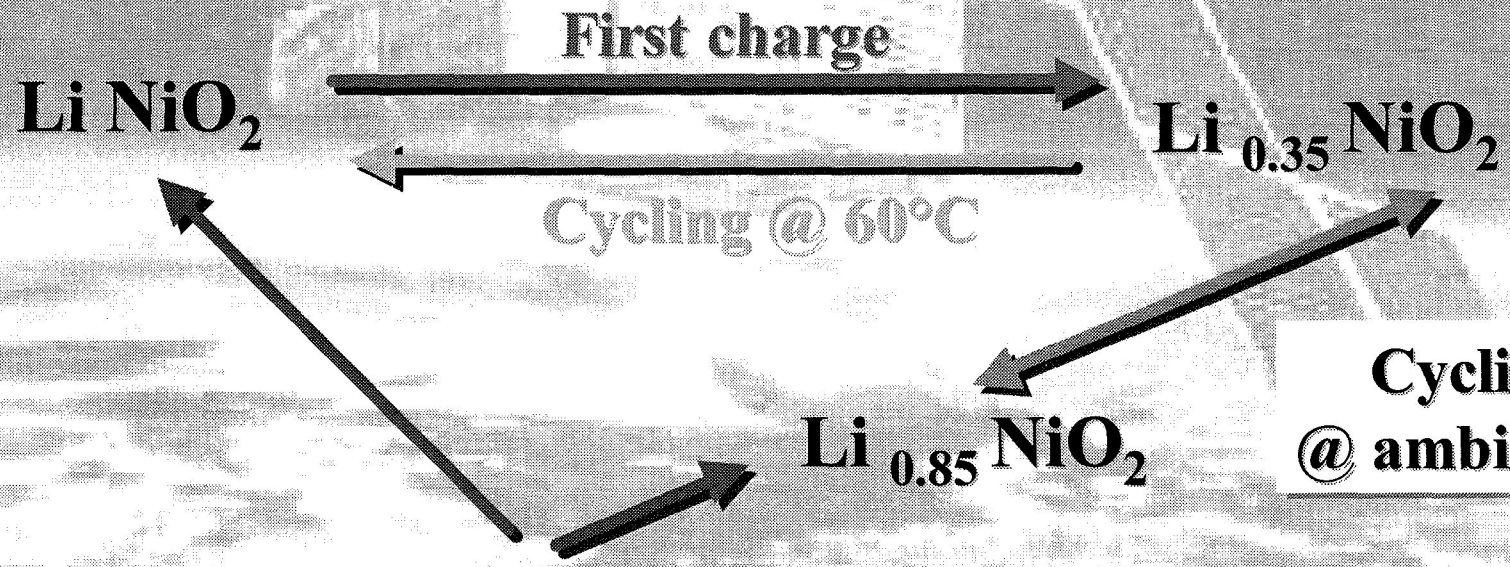

Cycling @ ambient T

Lithium reserve = 12% within negative electrode

SAFT

3.8V ,30°C, Floating

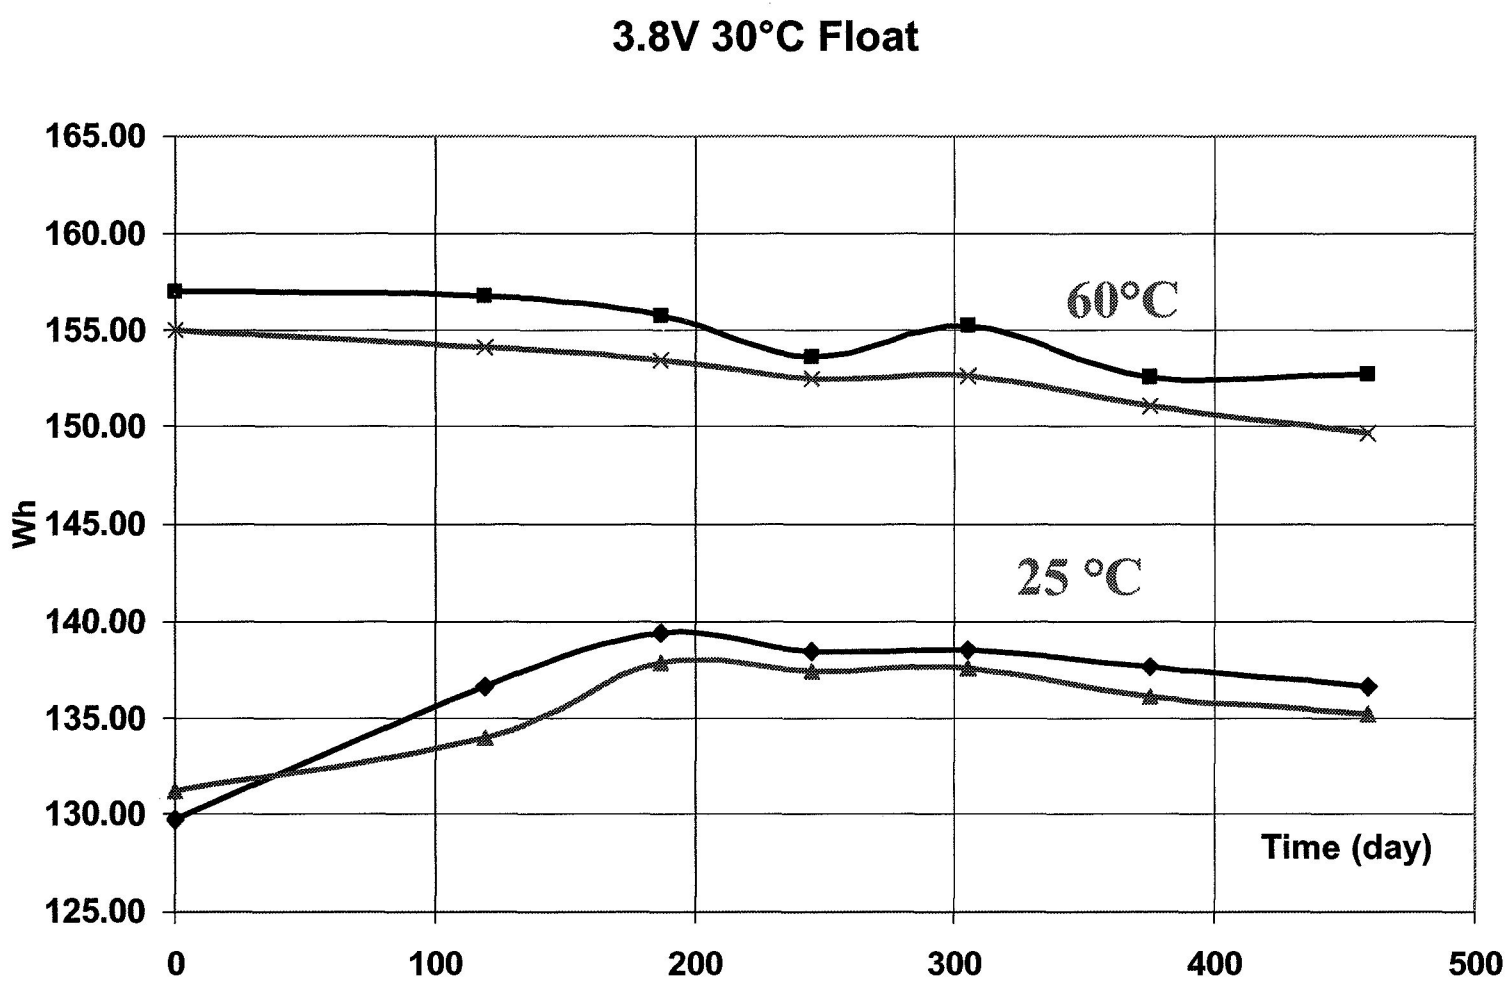

SAFT

3.70V ,10°C, OCV

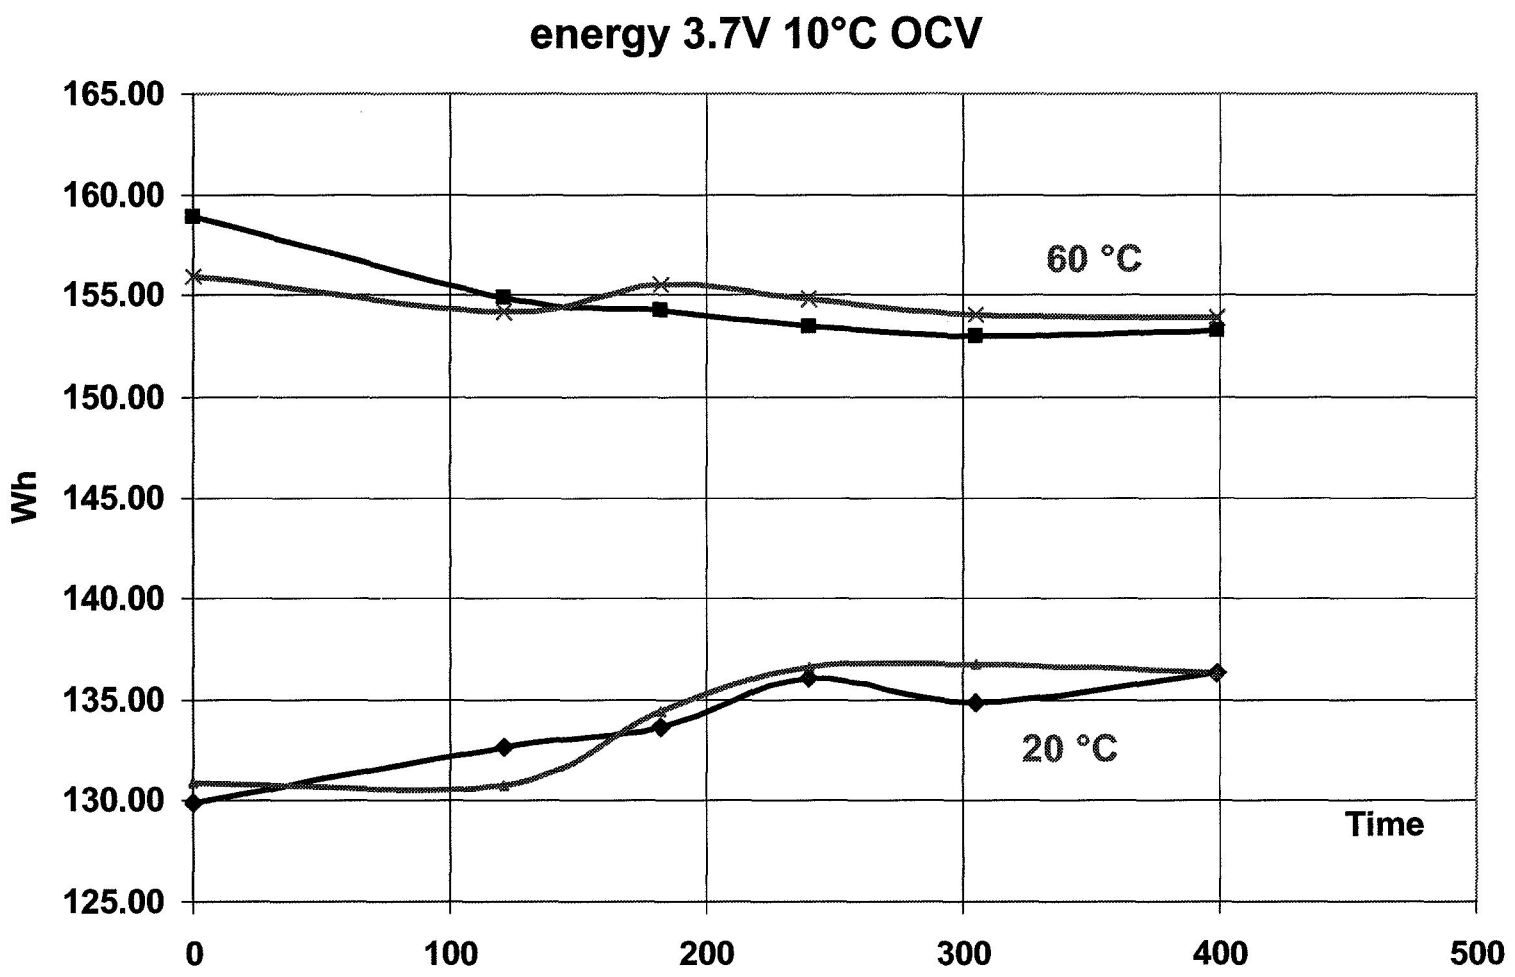

SAFT

Calendar Effect

Capacity Loss due to Calendar Effect vs Temperature

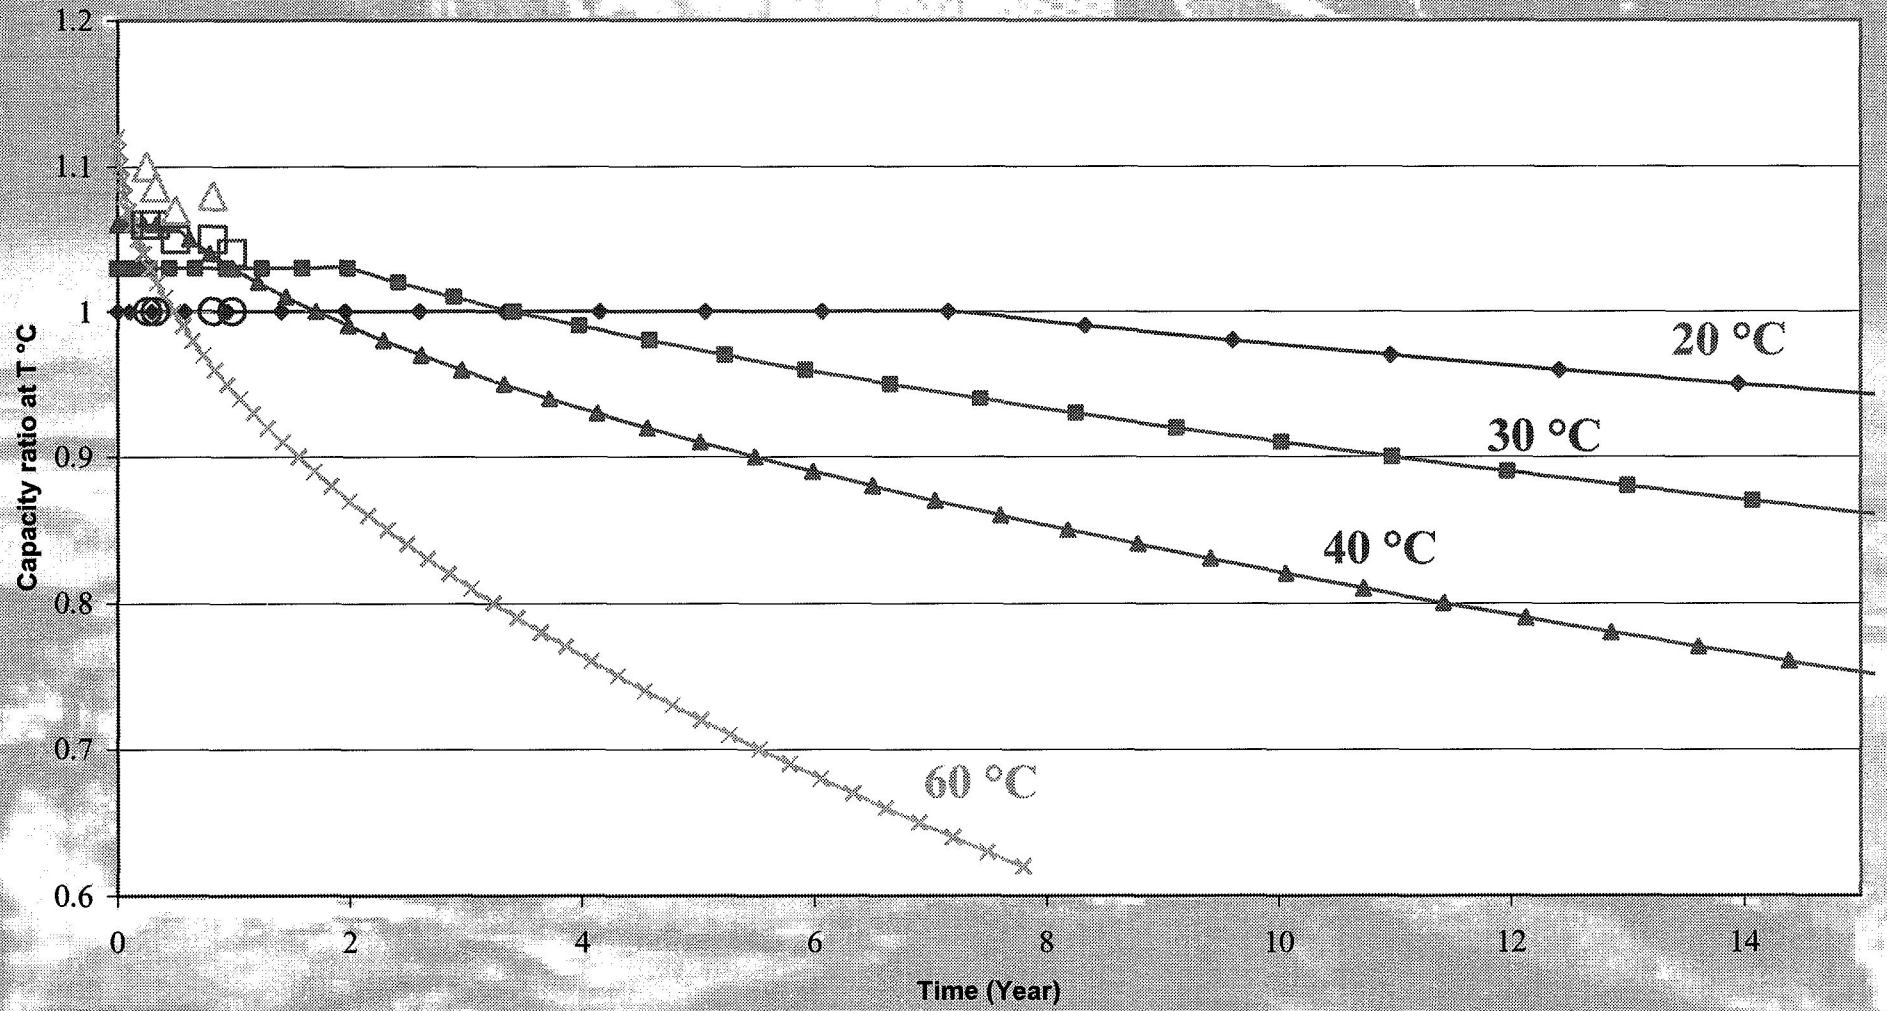

SAFT

Cycling Test

TEST CONDITIONS

- GEO Cycling
  - From 60 to 85% DOD
  - EOCV from 4.00V to 4.1V
  - Charge current from 4 to 12 Amps
  - >30 cells in test

- LEO Cycling
  - From 10 to 40% DOD
  - EOCV from 3.80V to 3.90V
  - 16 to 70 cycles per day
  - >40 cells in test

SAFT

Accelerated 80 % DOD GEO cycling

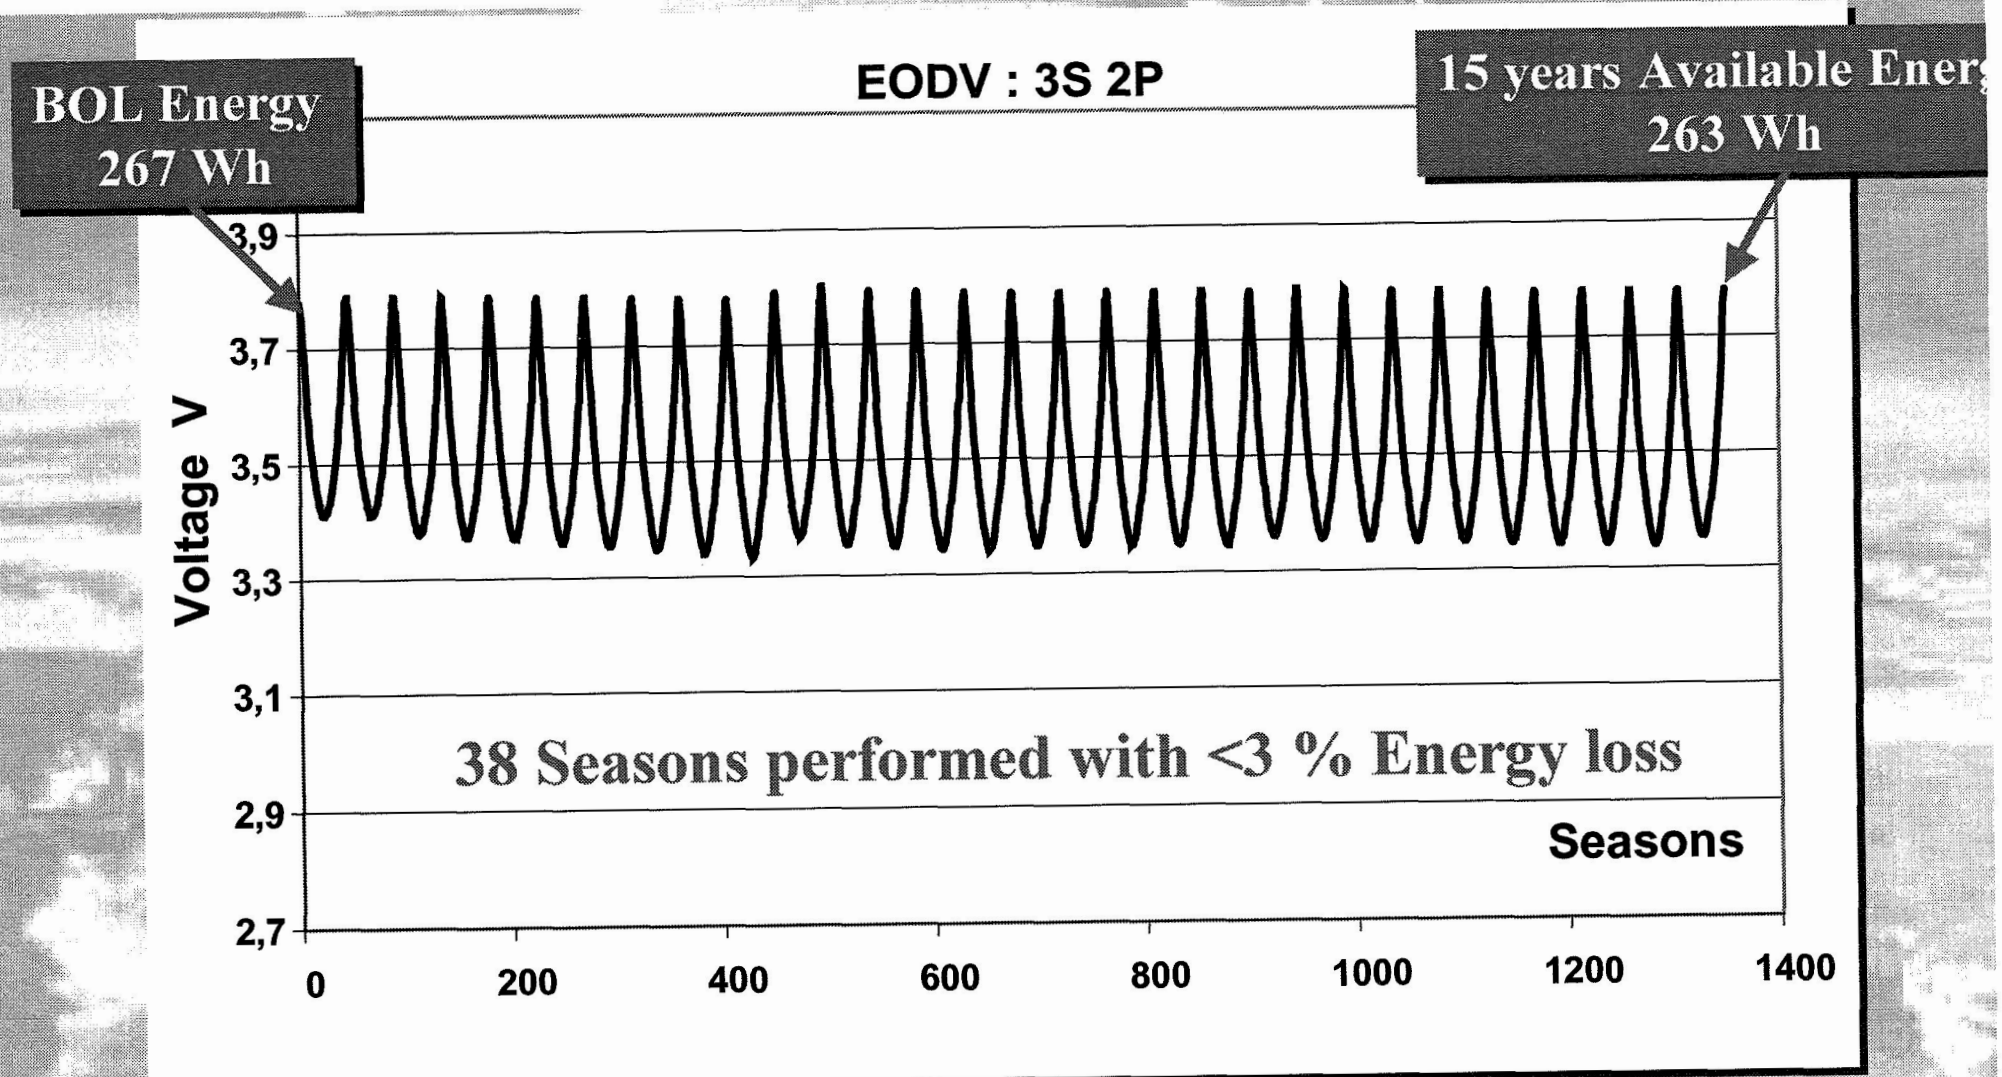

SAFT

Accelerated 85 % DOD GEO cycling

UEODV at cycle 23 and Energy versus nb seasons
3S 2P T=25 °C

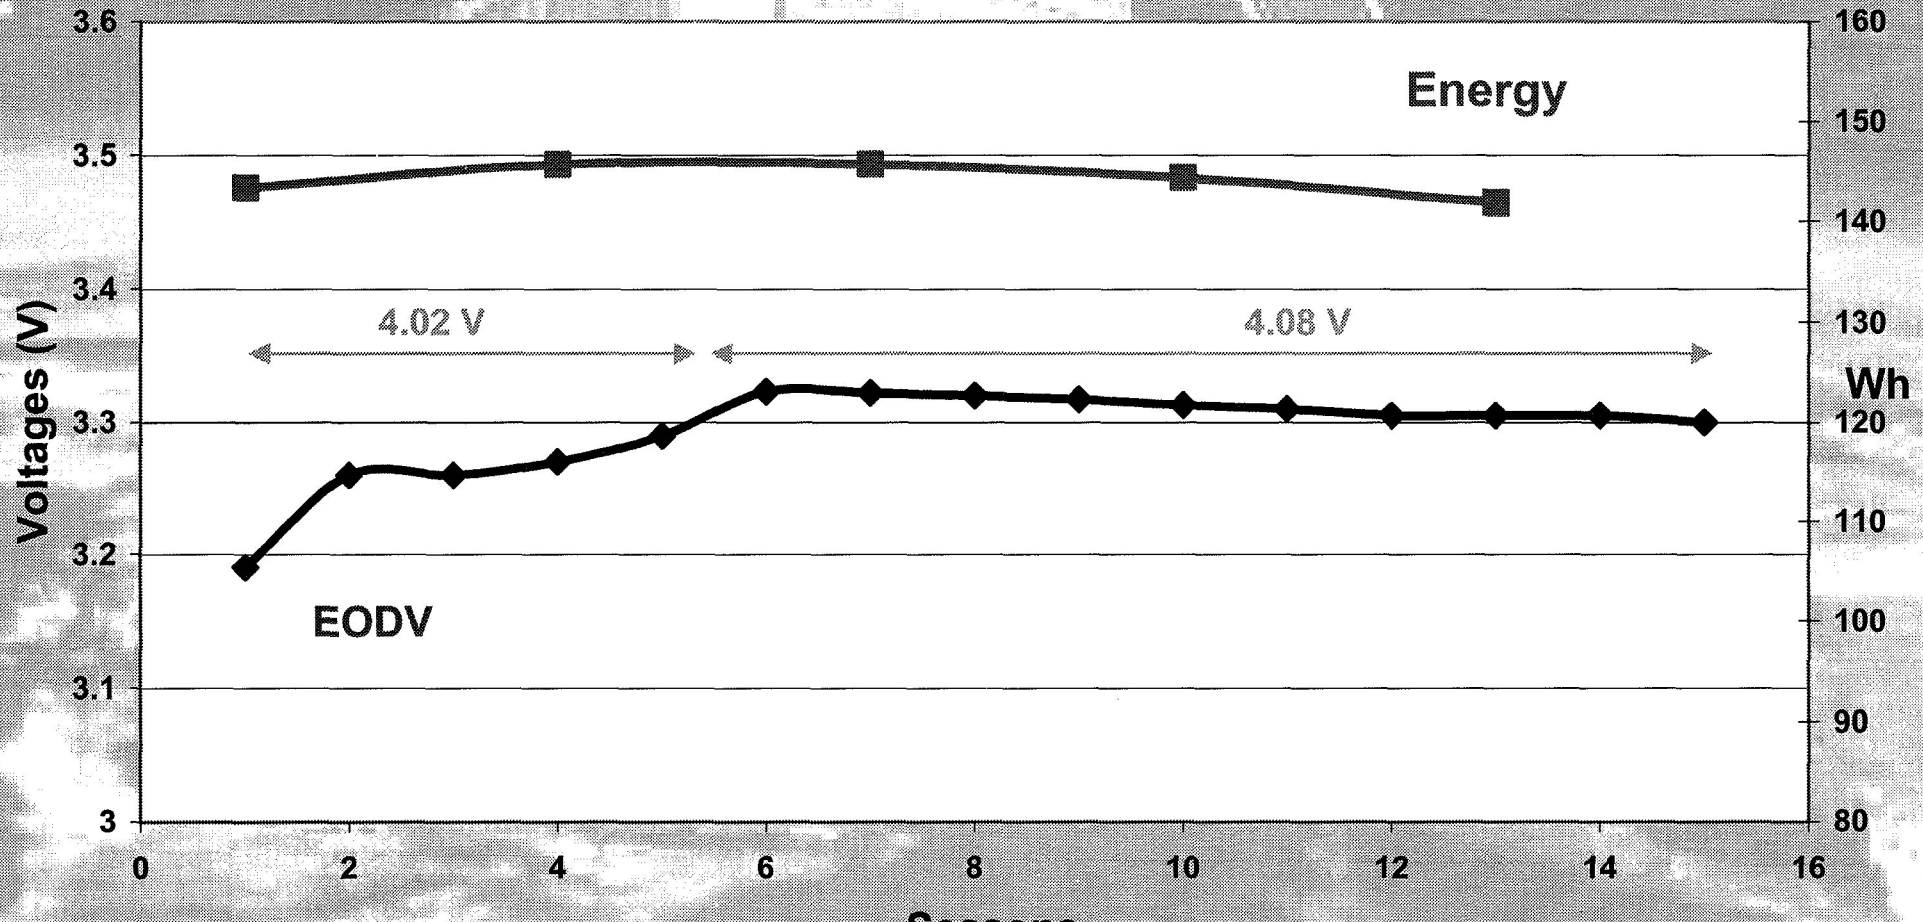

SAFT

GEO Life tests

SYNTHESIS OF GEO TESTING ON SAFT CELLS

Cell Version	Test	DOD	Nb Cells Tested	Nb Seasons Performed	Fading Measured	Fading @15 years
Prototype	Semi accelerated 2c/day +PP	40%	6 S Module	18	15%	**25%**
Prototype	Constant (charge C/5, disch : C/1.	60%	1	42 (1960 cycl	17%	**12%**
Stentor	Semi accelerated 2c/day +PP	40%	6 S Module	32	8%	**8%**
Stentor	Acceleratec	80%	2S2P Module	30	11%	**11%**
VES140 0	Acceleratec	80%	3S2P Module	36	3%	**2.5%**
VES140 0	Semi accelerate	85%	3S2P Module	18	0%	**-**
VES140 0	Acceleratec	70% 60%	2 cells 4 cells	16 (710 cycles 16 (706 cycles	1.0% 1.0%	**3.0%** **2.9%**

15 YEARS GEO FADING ENERGY <3%

SAFT

Accelerated LEO Cycling : 20 % DOD, 3.9 V

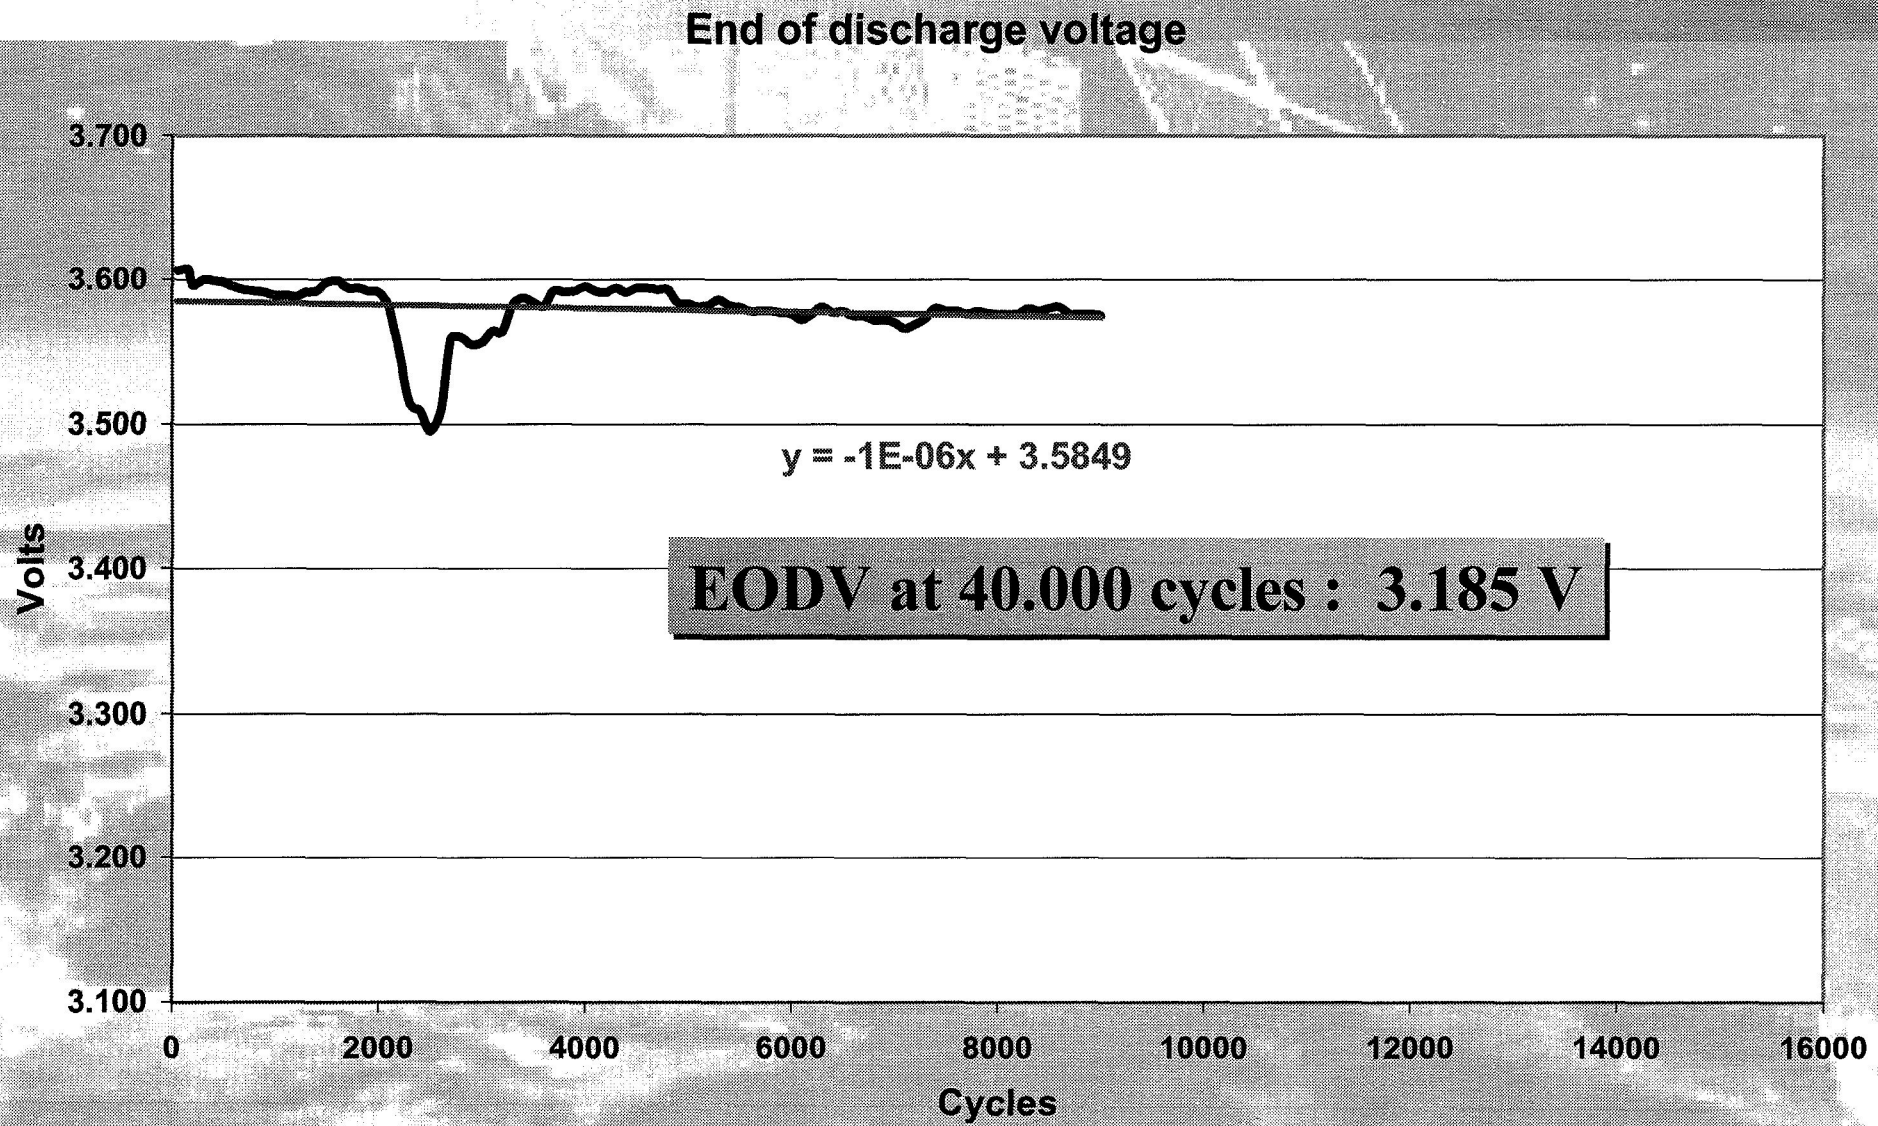

SAFT

Accelerated LEO Cycling : 20 % DOD, 3.9 V

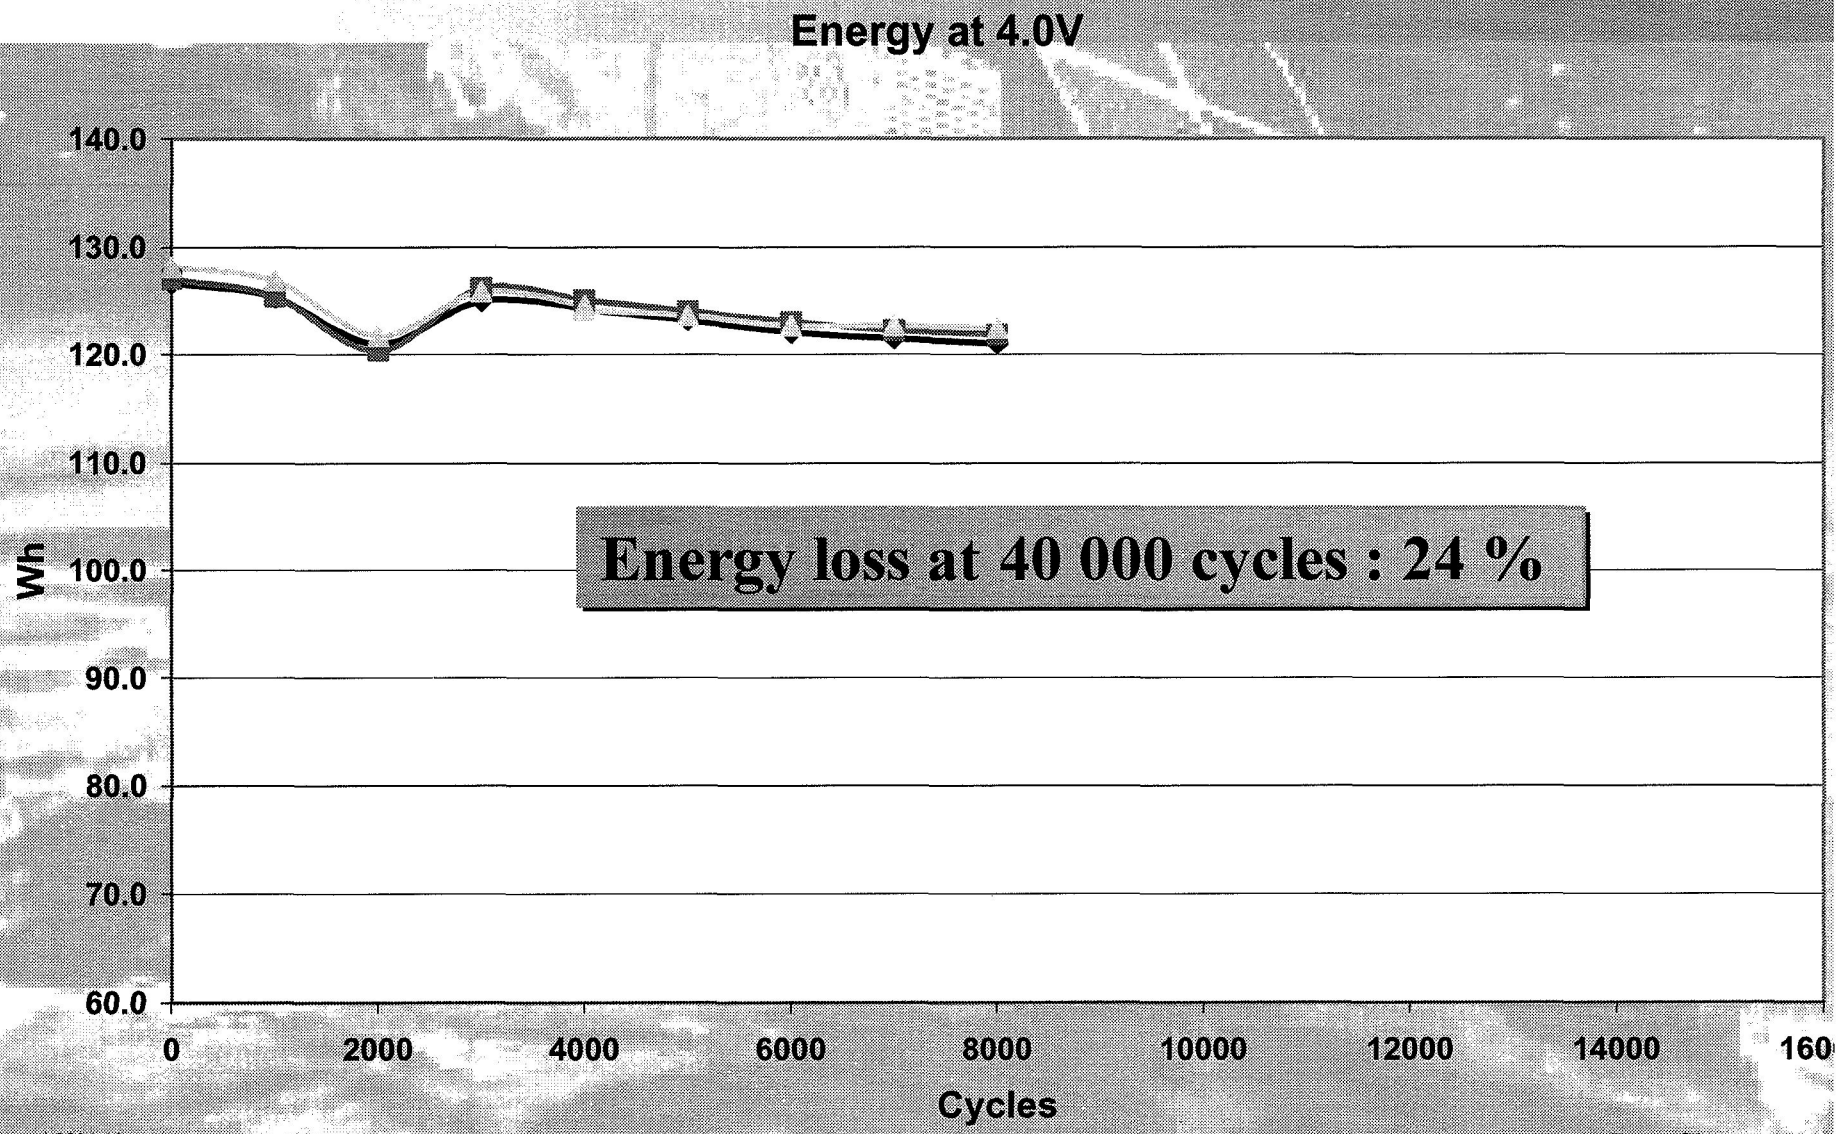

Energy loss at 40 000 cycles : 24 %

SAFT

Real LEO Cycling : 30 % DOD, 3.8 V

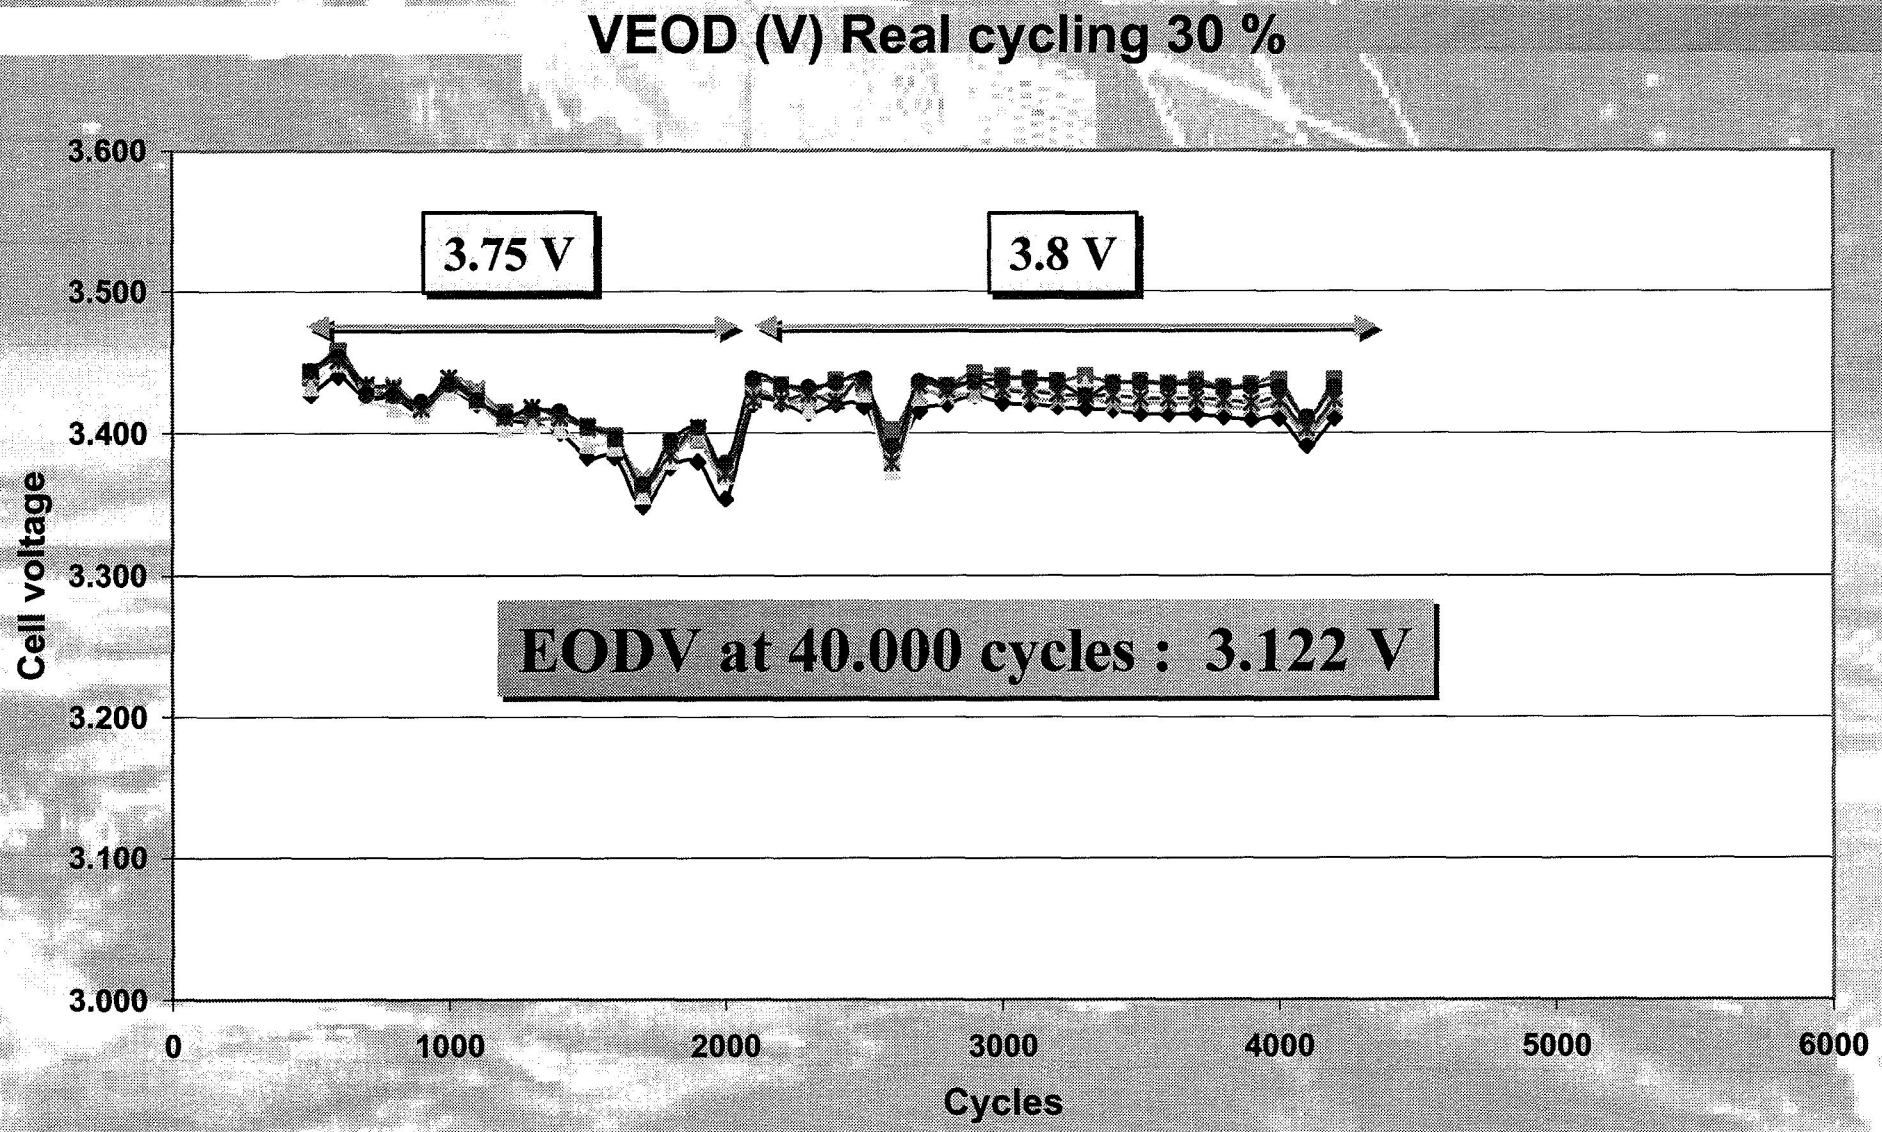

SAFT

Real LEO Cycling : 30 % DOD, 3.8 V

ENERGY @ 4.00V & 3.80V

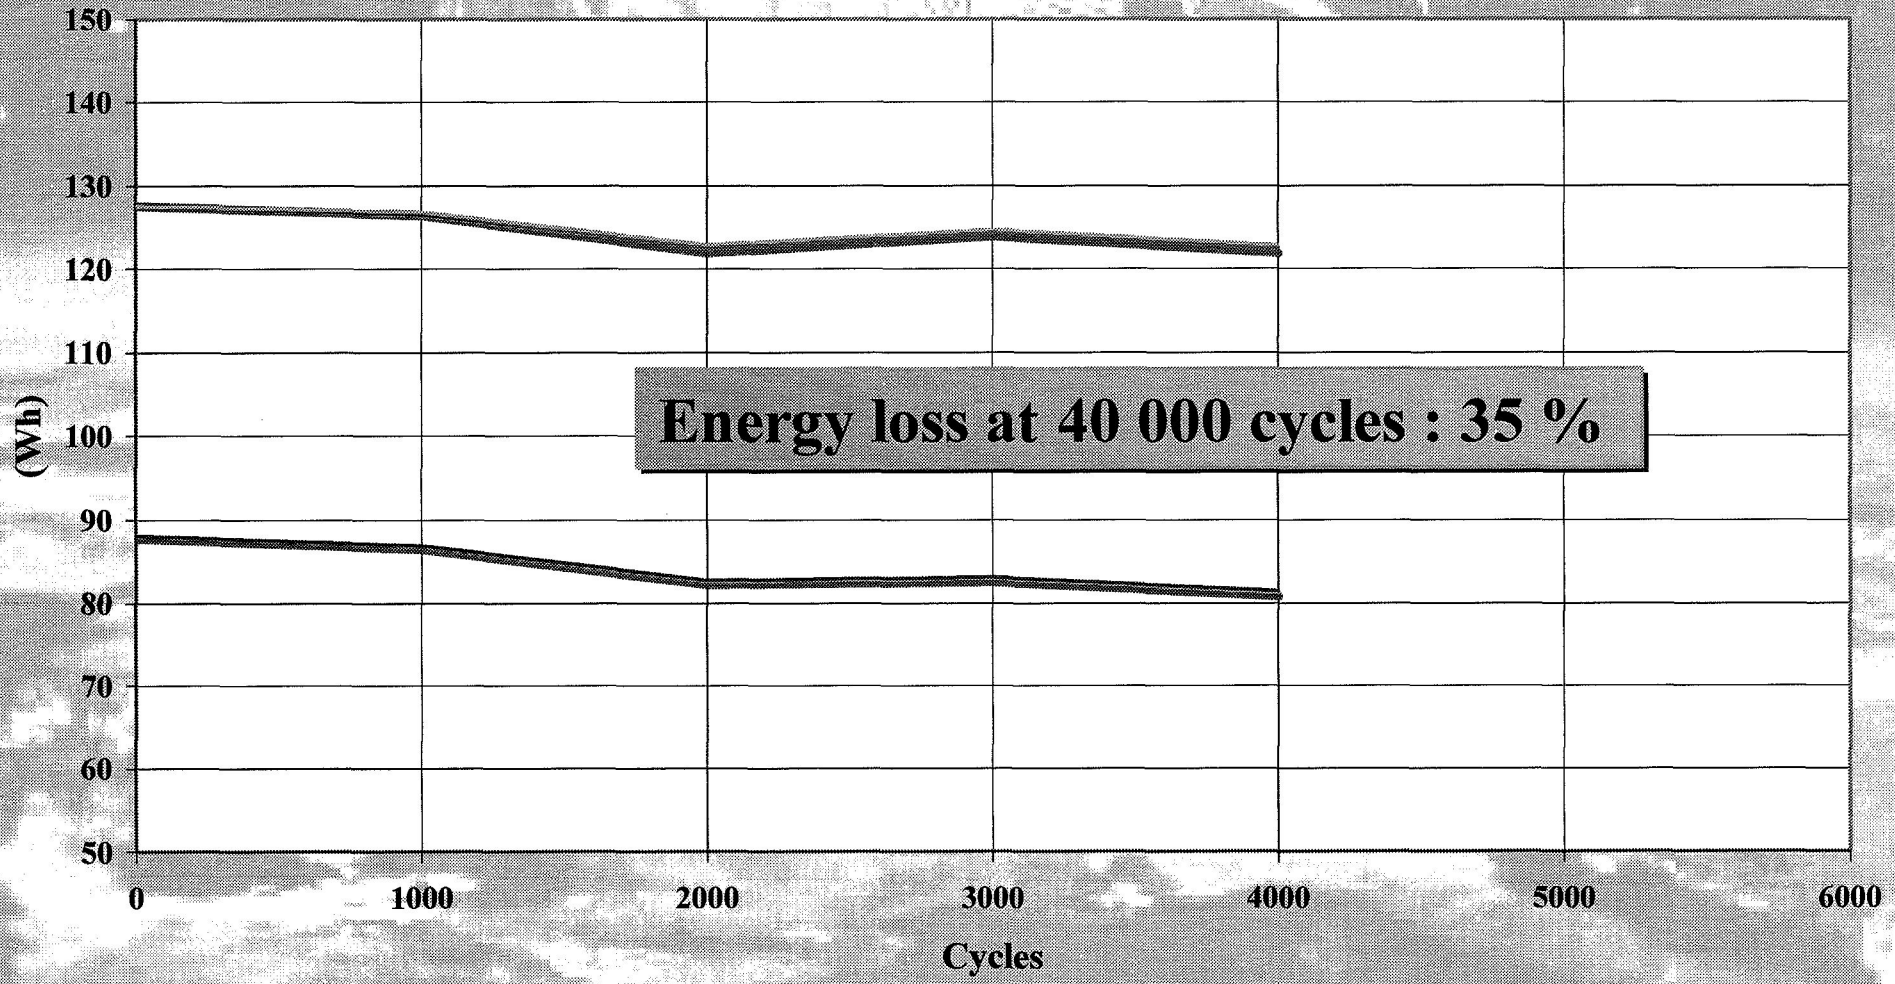

SAFT

LEO BATTERY DESIGN

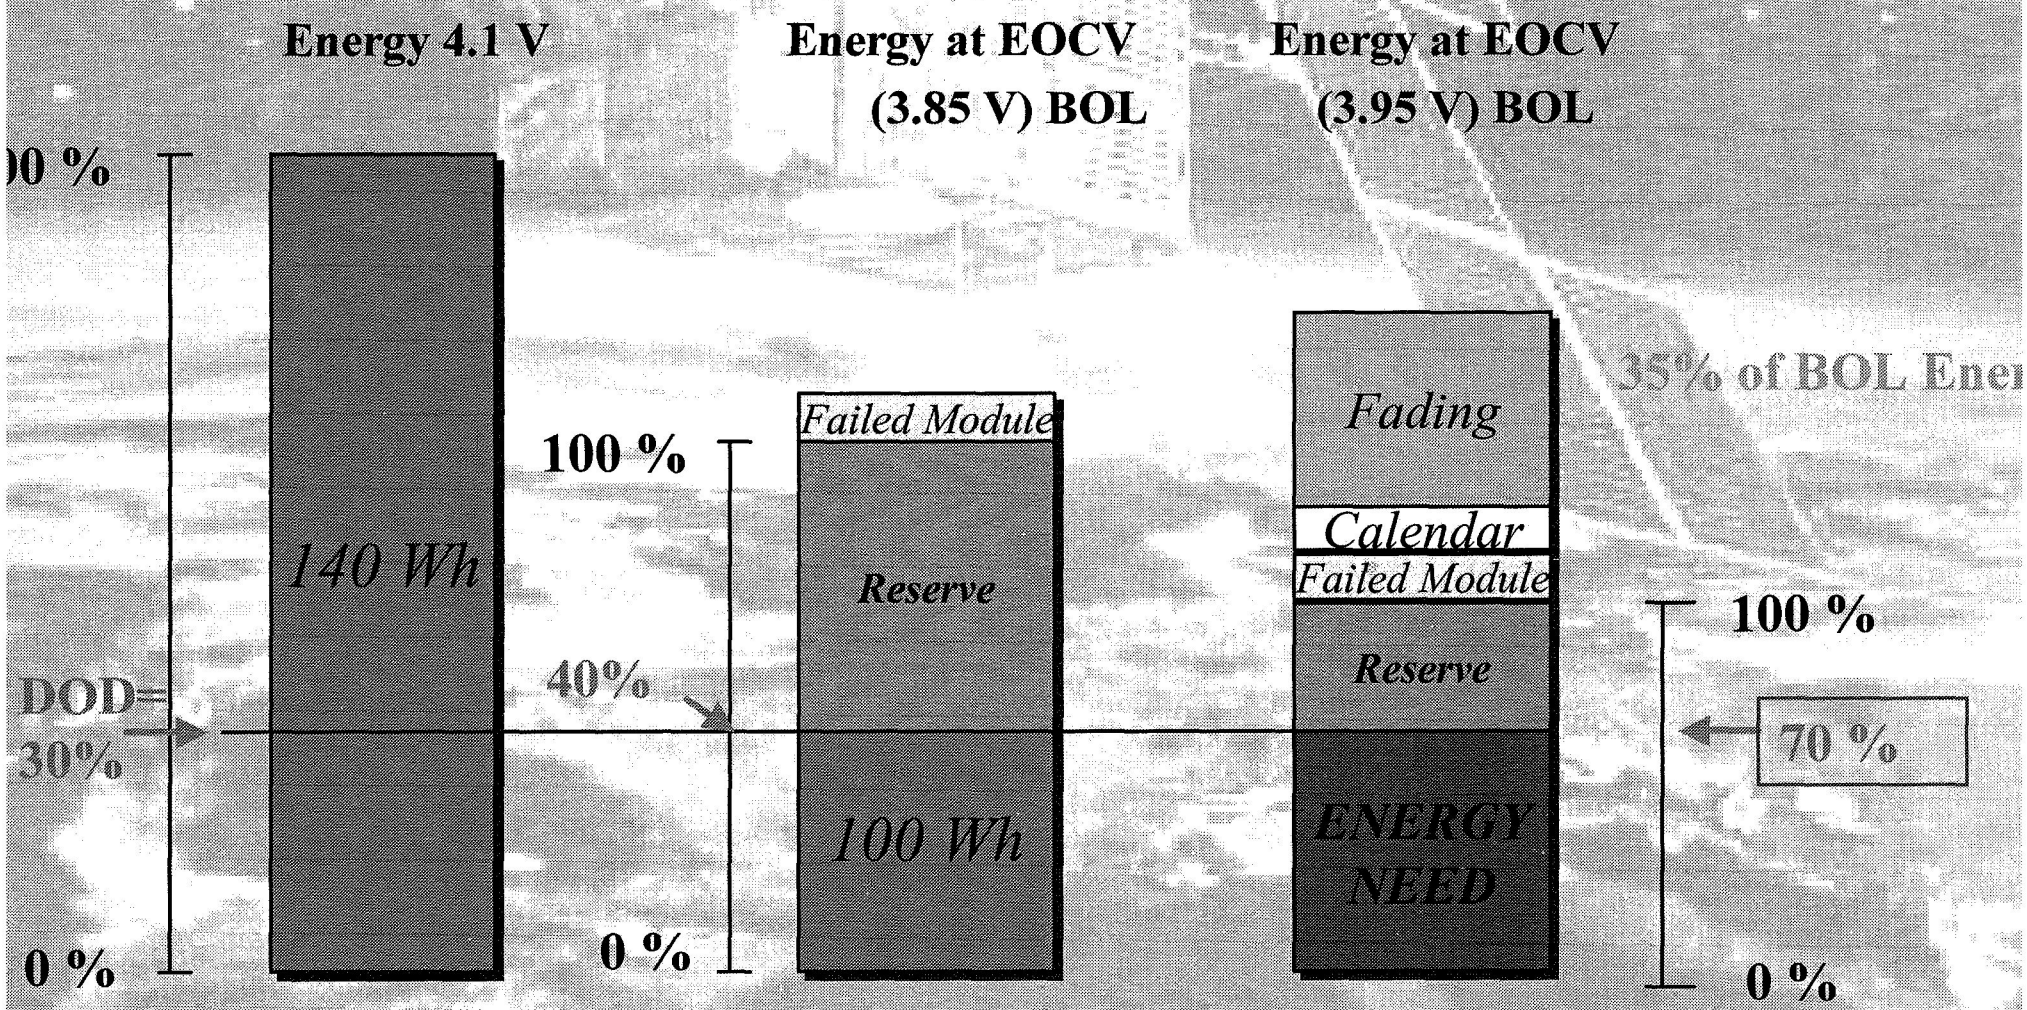

SAFT

Conclusion

- VES 140 S cell :
  - Qualified by ESA, CNES, ASTRIUM and ASPI
  - Weight <1142g
  - Dimensions : Diameter 54, length 250 mm
  - Min Guaranteed Energy>132 Wh (Average 140 Wh) @ 4.10 V

  - Calendar Effect $t=X^2.e^{(6680/T-20.24)}+X.e^{(6989/T-20.59)}$

  - Cycling law $N=1.5*10^6*e^{-0.0846*DOD}$

    18 equivalent GEO years results at 80 % DOD (< 3 % fading)

    10.000 LEO cycles at 30 % DOD

SAFT

Conclusion (Cont 'd)

- Negative Excess (Lithium) : 12%
- Self discharge < 3 mA
- Impédance <3 mOhm @ 20 et 60% DOD
- Air Transportation Autorization N° 903-99
- Actual Industrial Line Capability :32 cells per day

VES 140 S qualified for Space use
Will fly on Stentor
>18 years GEO life test 80 % DOD
>2 years LEO life test 30 % DOD

SAFT

LITHIUM ION DD CELLS
EVALUATION FOR SPACE APPLICATION

HAIYAN CROFT

BOB STANIEWICZ

SAFT R&D CENTER

Silver Lining

2001117777

538030

24 pgs

SAFT

OVERVIEW

- CHEMISTRY
- CHARACTERIZATION OF DD CELLS
- HOW ACCELERATED TESTING IS PERFORMED
- CALENDAR RESULTS
- TESTING RESULT AND PREDICTED CYCLE LIFE

SAFT

CHEMISTRY

- CHEMISTRY
  - POSITIVE MATERIAL: $LiNi_{1-x-y}Co_xM_yO_2$
  - NEGATIVE IS ADMIXTURE OF TWO GRAPHITES WITH NON-PVDF BINDER
- CAPACITY: 9.2 AH
- ENERGY DENSITY: 135 WH/KG

SAFT

HARDWARE

- STAINLESS STEEL HARDWARE
- CELL DIMENSION: CYLINDRIAL
  - CELL OD 32 MM OR 1.32 IN
  - CELL HEIGHT 122MM OR 4.8 IN
- MULTIMPLE TABS ON ELECTRODES
- CELL WEIGHT: 250 GRAMS

Discharge Rate characterization at 23°C

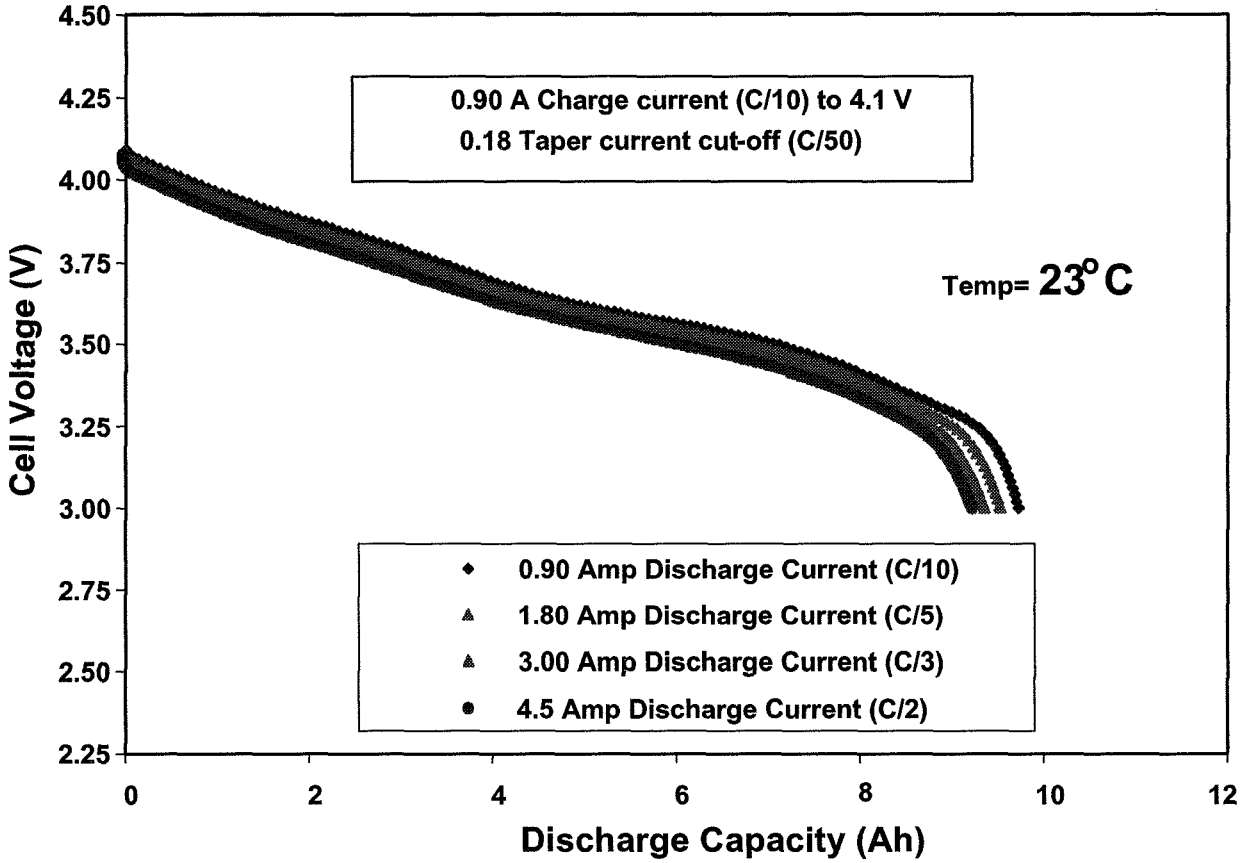

Discharge Rate characterization at -20°C

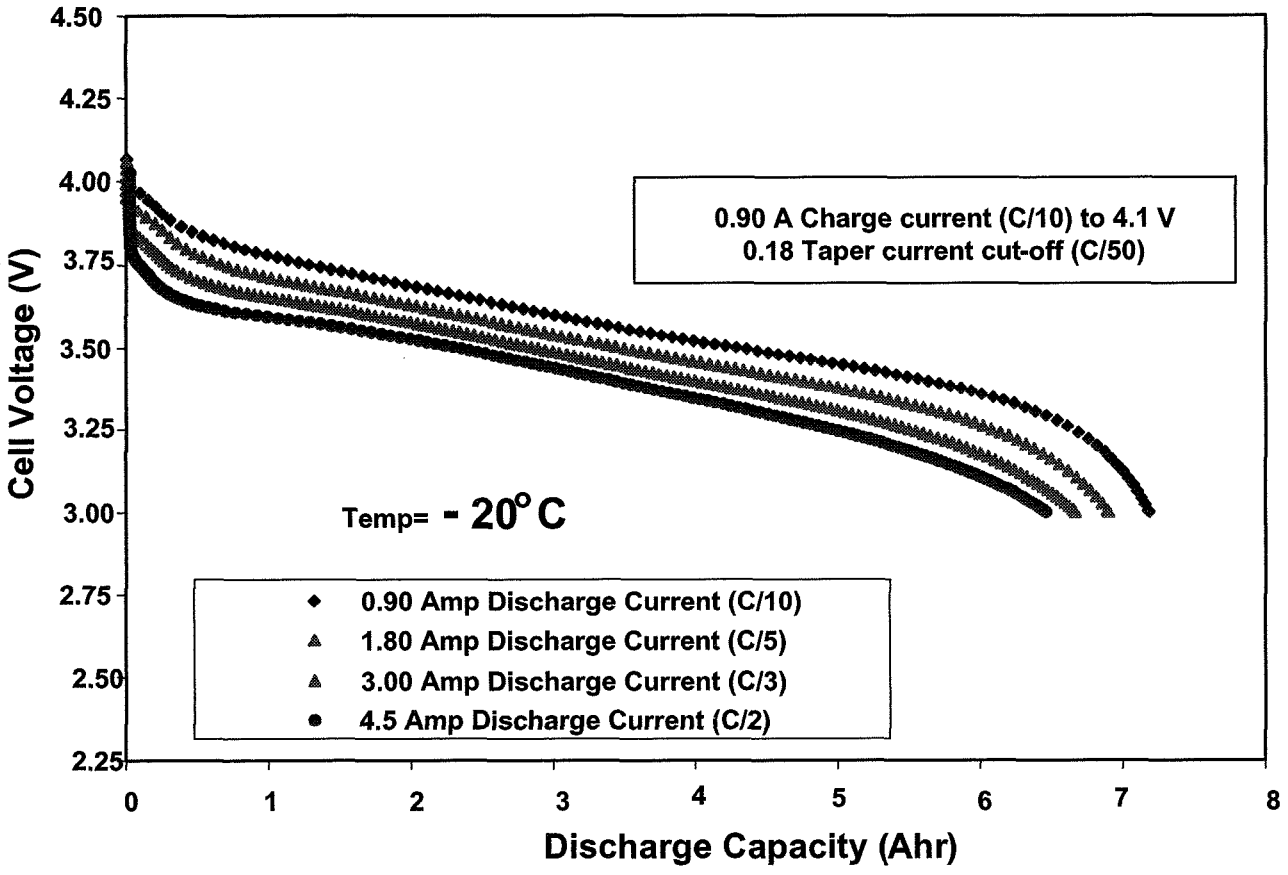

Discharge Performance at Various Temperatures

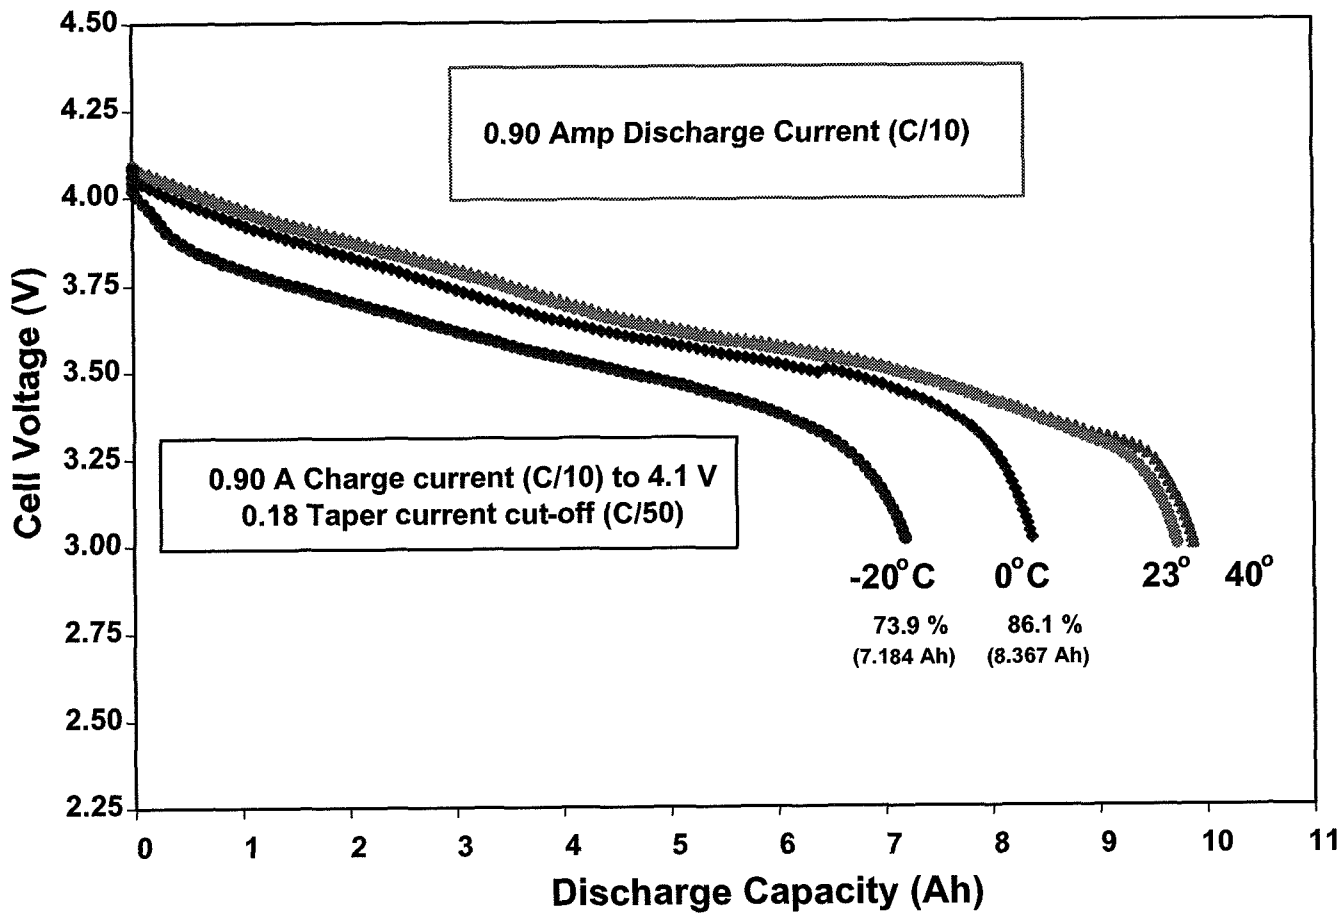

SAFT

- LEO AND GEO CYCLING DEMONSTRATING PERFORMANCES FOR PLANETARY AND INTERPLANETARY APPLICATIONS

DEPTH OF DISCHARGE	CYCLES ACHIEVED TO DATE	RESULTS
30%	10,000	PREDICTED FOR 40K CYCLES
60%	1500	

SAFT

ACCELERATED TESTING METHODS

WE JUDGED WHAT MIGHT BE REASONABLE, ACCELERATED TRADEOFFS OF TIME AND CURRENT TO ACCOMPLISH CYCLE DEMONSTRATION

GEO – ACCELERATION IS STRAIGHTFORWARD:
WE ADOPTED 1.2 HOURS FOR DISCHARGE
4.8 HOURS FOR CHARGE

THE DISCHARGE IS AT A CONSTANT DOD RATHER THAN A TRUE SEASON WITH THE WELL-KNOW PARABOLIC ECLIPSE DURATION

LEO – ACCELERATION REQUIRES A CAREFUL BALANCE OF SHORTEN TIME AND CURRENT INCREASE

	CYCLES/DAY	CURRENT (A)	TIME (M)
30% DOD	28.7	DIS 10	15.12
		CHG 5.25	35

SAFT

LEO TESTING

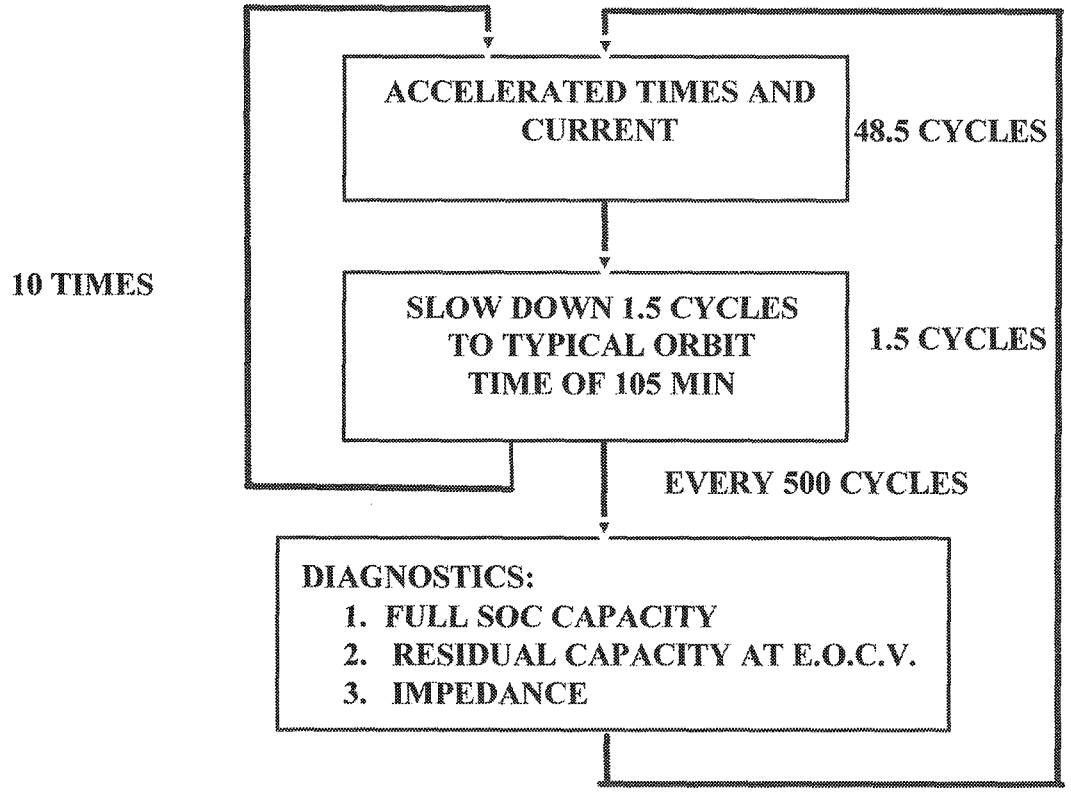

SLOWING DOWN TO REAL TIME ORBIT RATES OF 105 MIN. EVERY 50 CYCLES IS ESSENTIAL SO THAT E.O.D.V. REFLECTS TRUE ORBIT CONDITIONS

SAFT

LEO TESTING

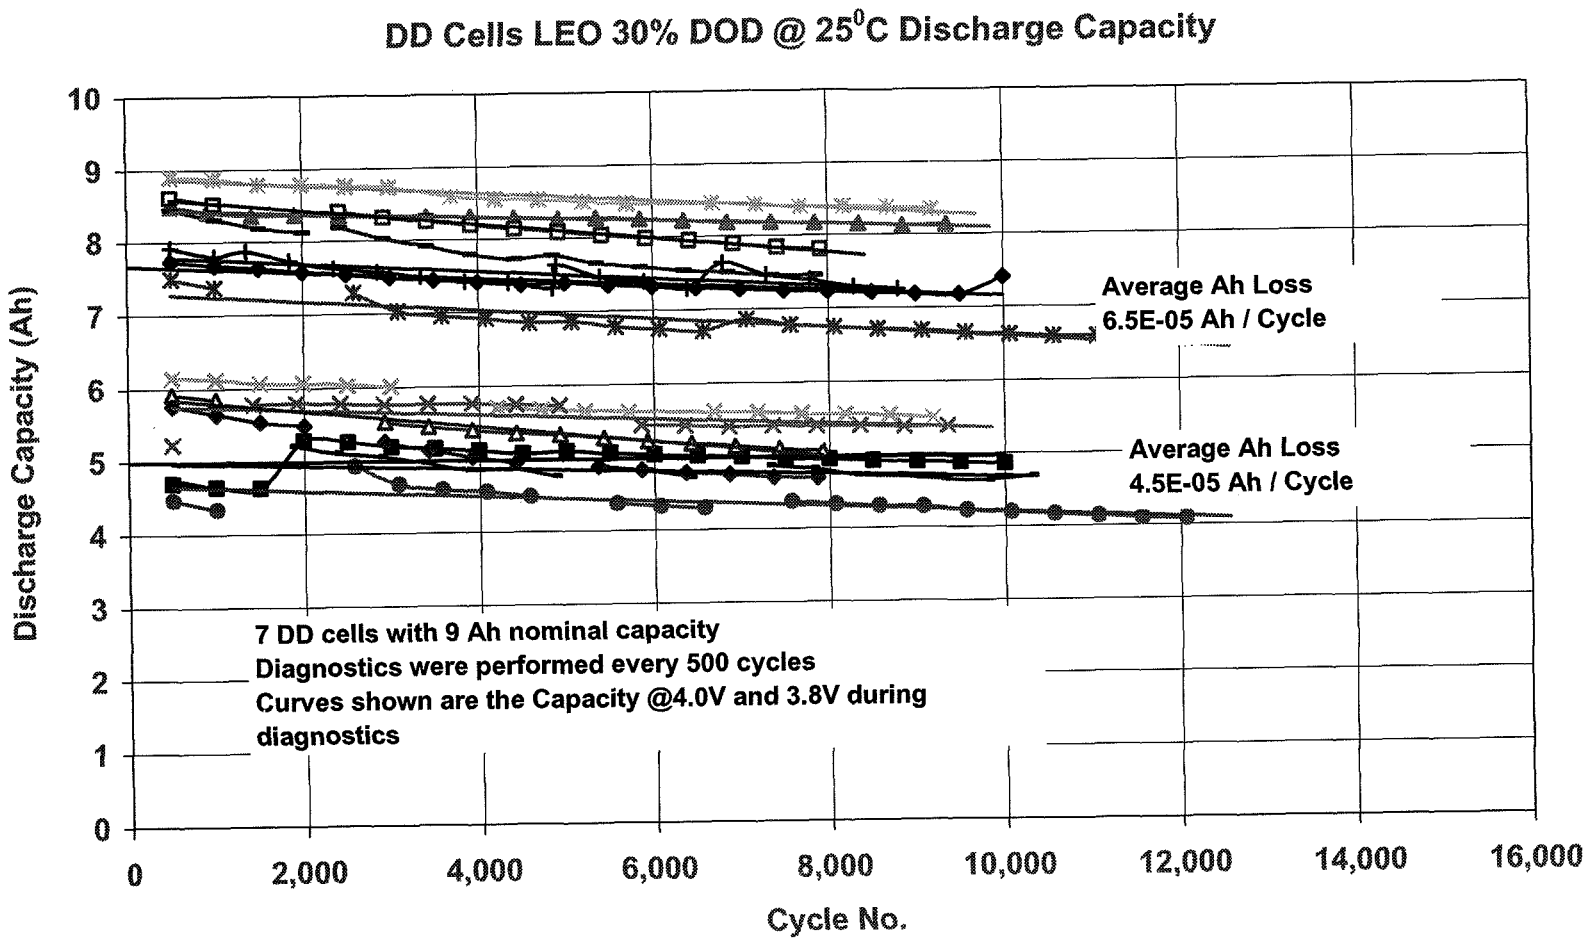

SAFT

LEO TESTING

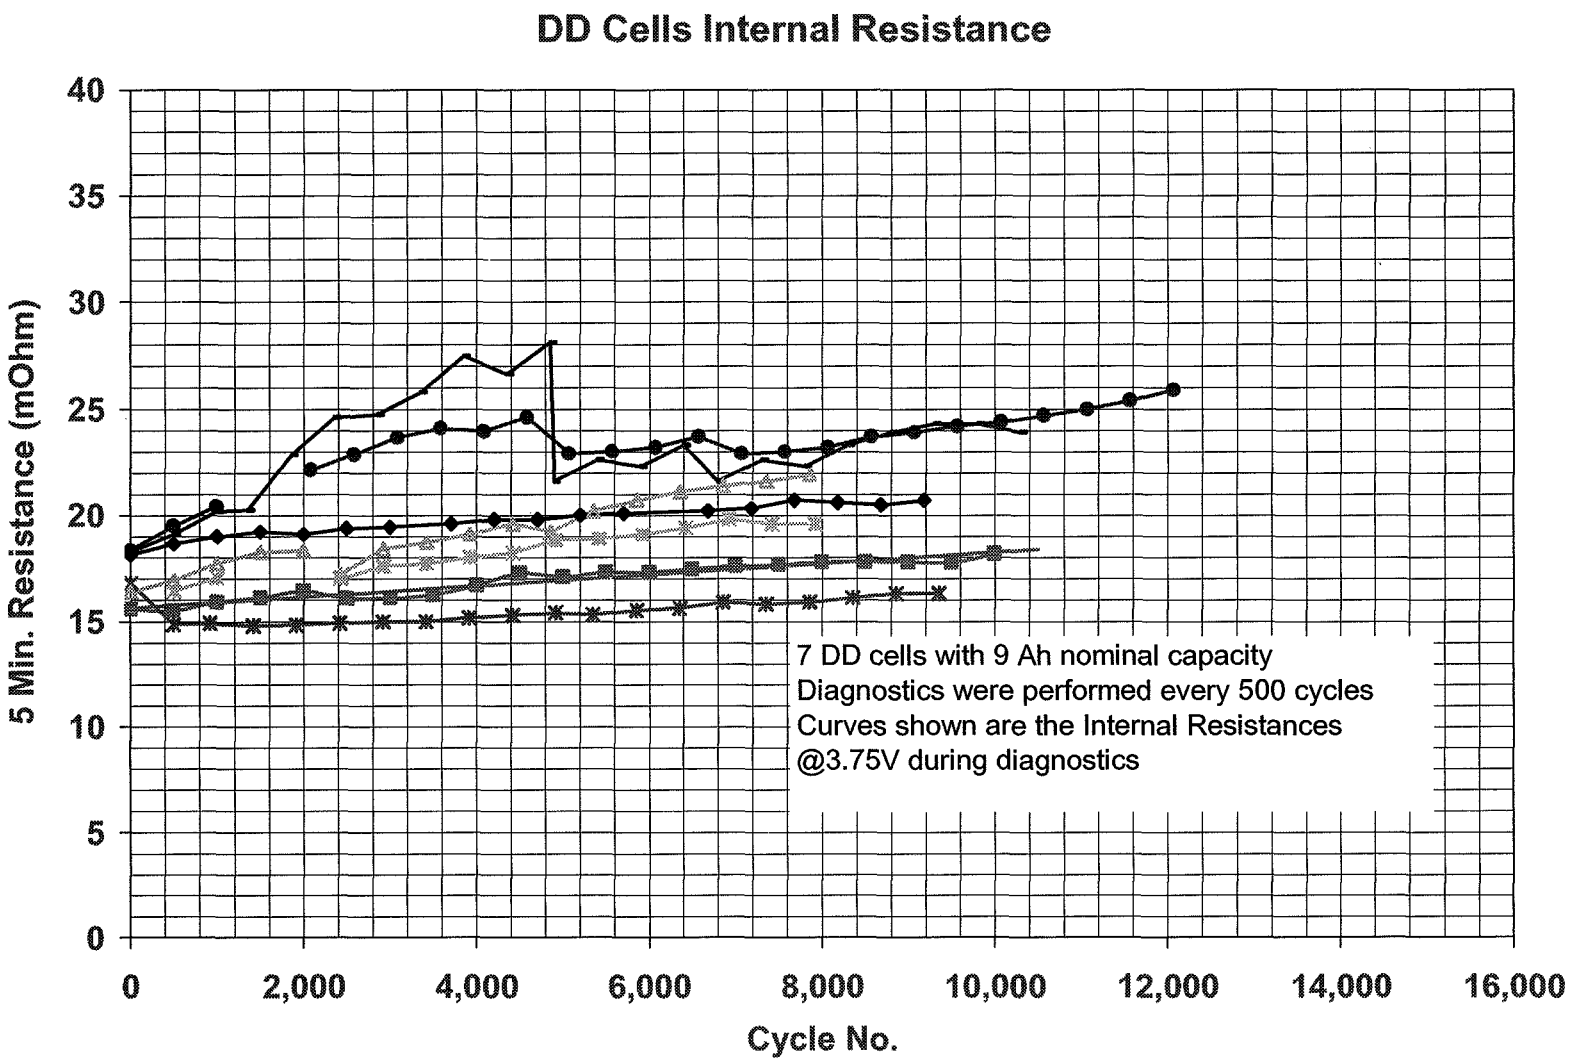

SAFT

LEO TESTING

DD cells LEO test - 30% DOD EODV @ 25C

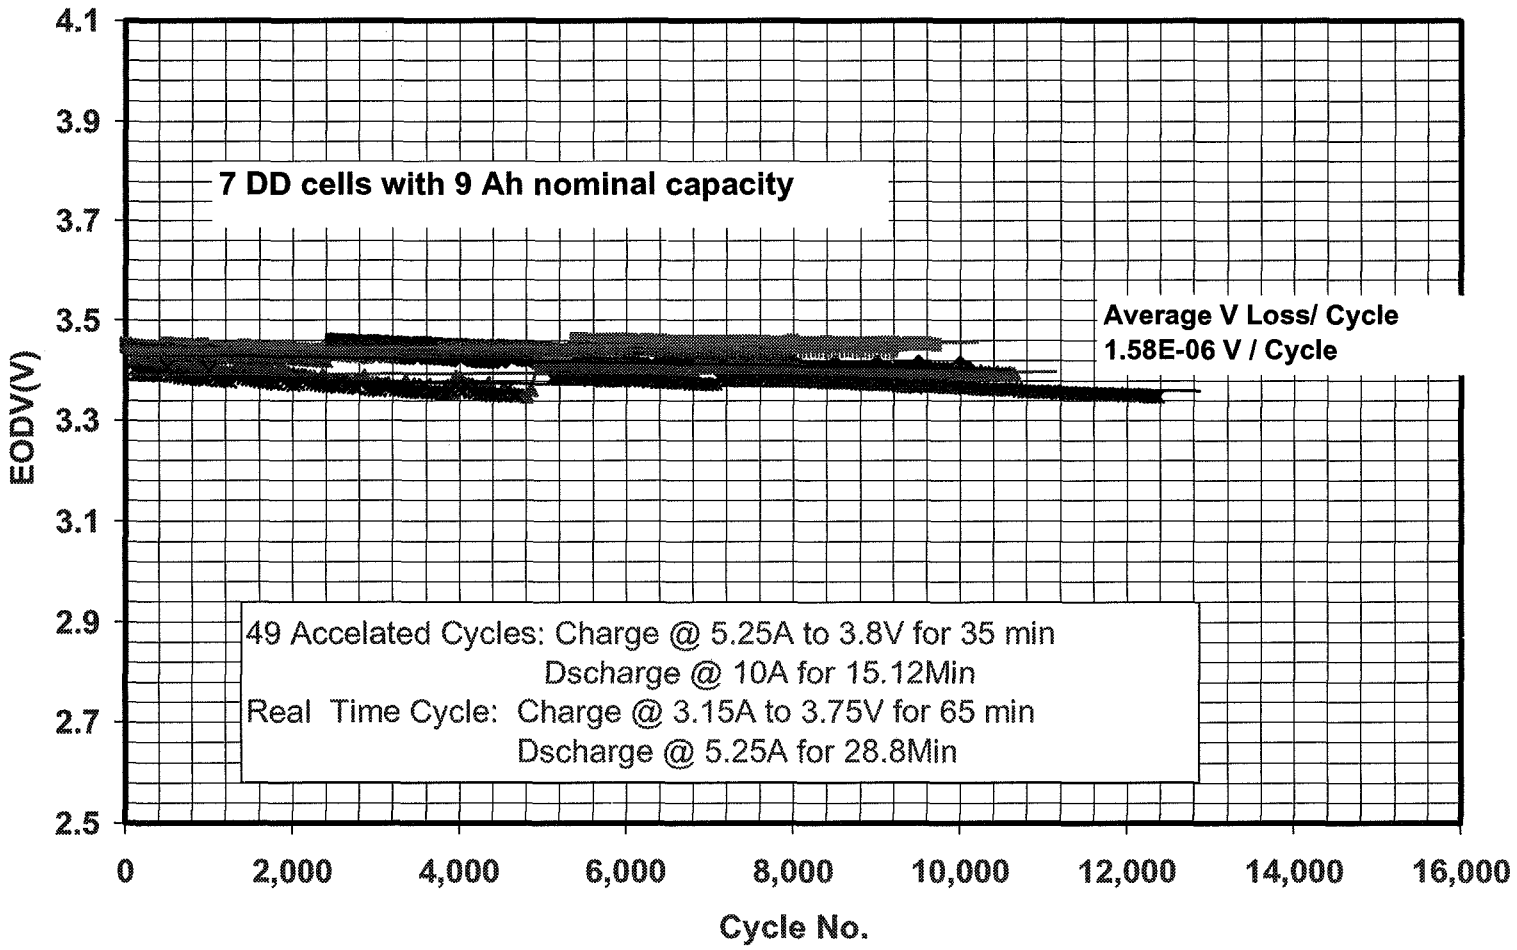

SAFT

LEO TESTING

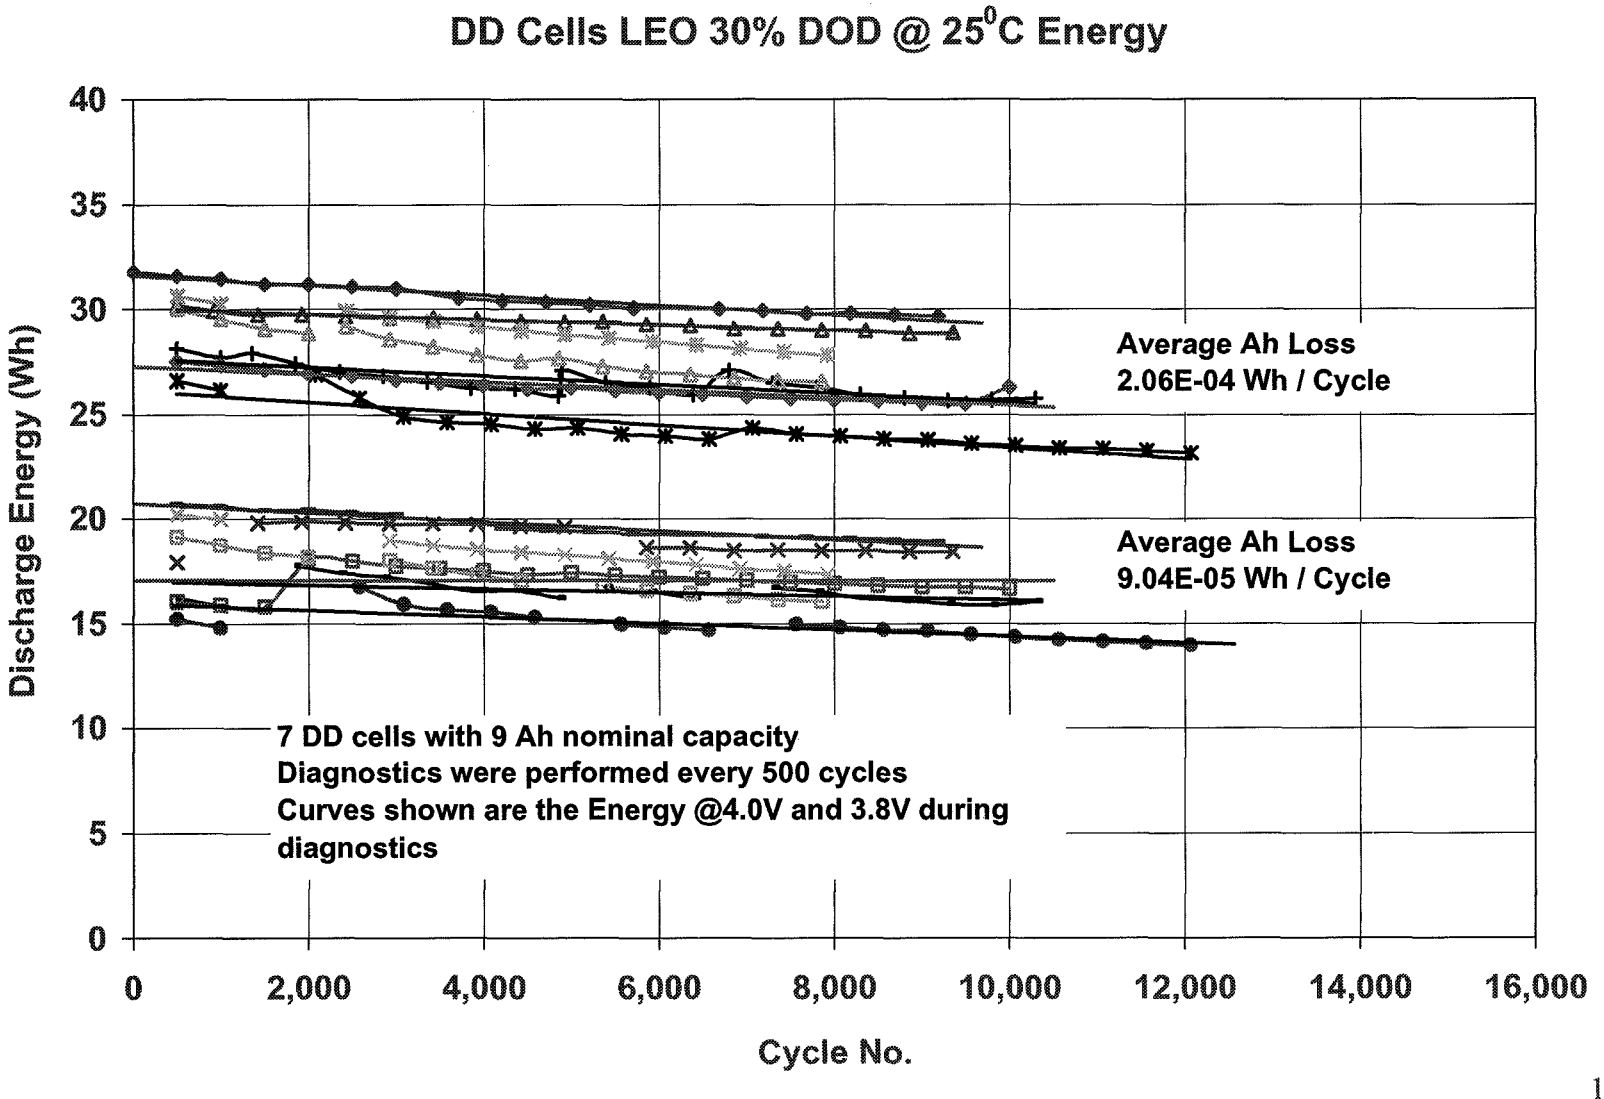

SAFT

CYCLE LIFE EXTRAPOLATION

PROTOTYPE DD CELLS (B.O.L. = 30 Wh)

Depth Of Discharge %	Cycles Achieved	Wh Fade Rate @ 4V % Per Cycle	Typical Req. For Cycles	E.O.M. Energy* Wh 25°C
30	12,000	.000206	40,000	21.8
60	1500	.0011	1,500	29.9

*NOT CORRECTED FOR CALENDAR LIFE

SAFT

GEO TESTING

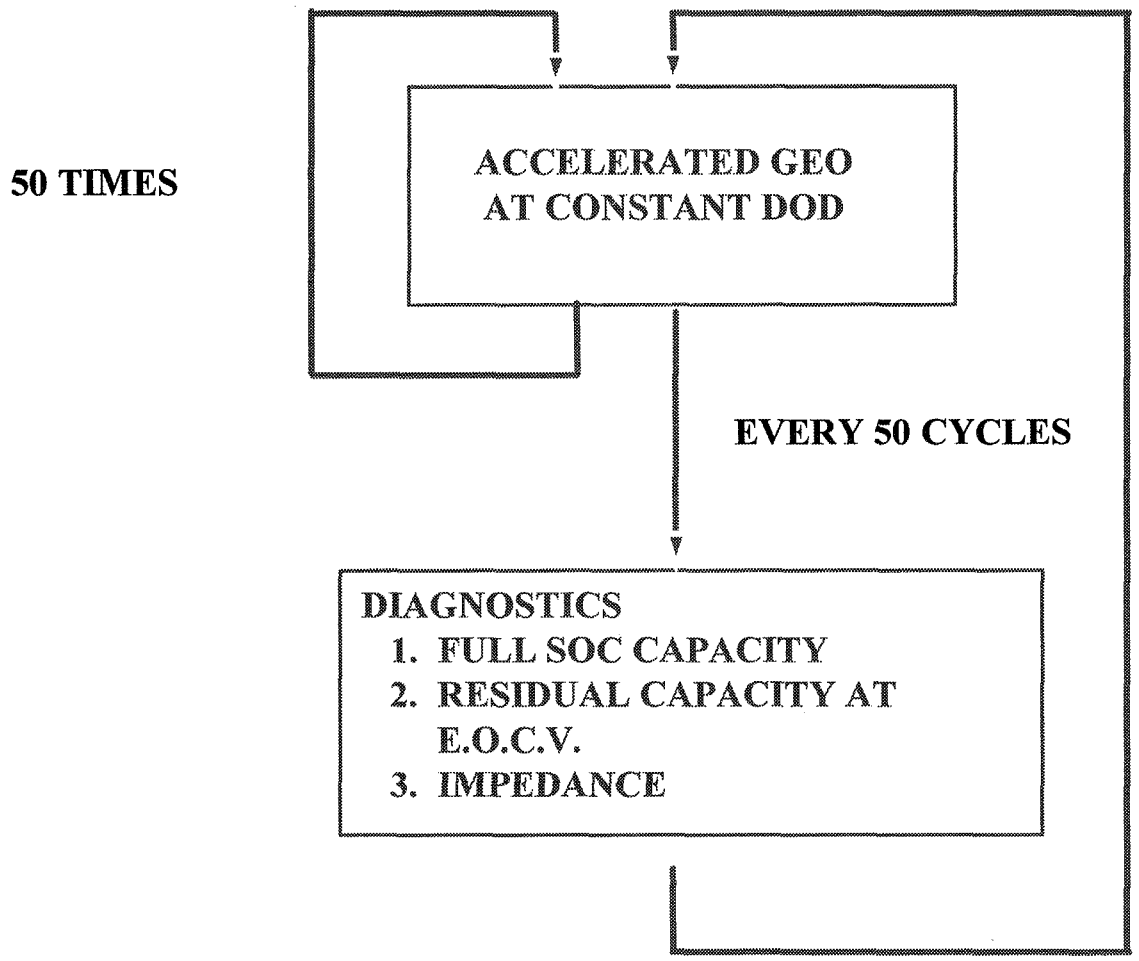

SAFT

GEO TESTING

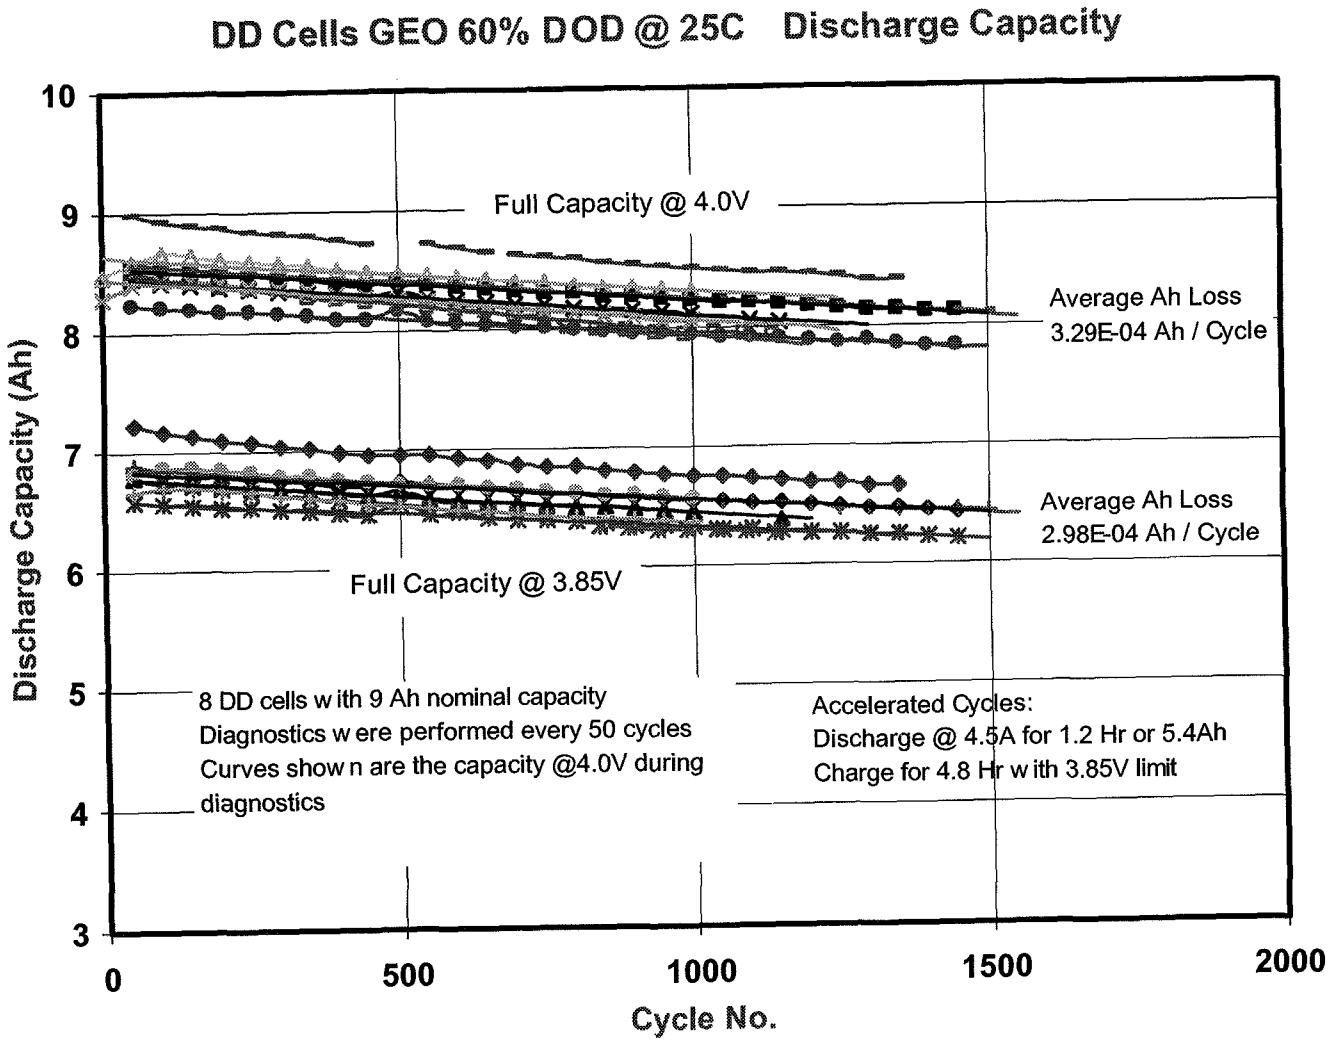

SAFT

GEO TESTING

DD Cells GEO 60% DOD @ 25C Internal Resistance

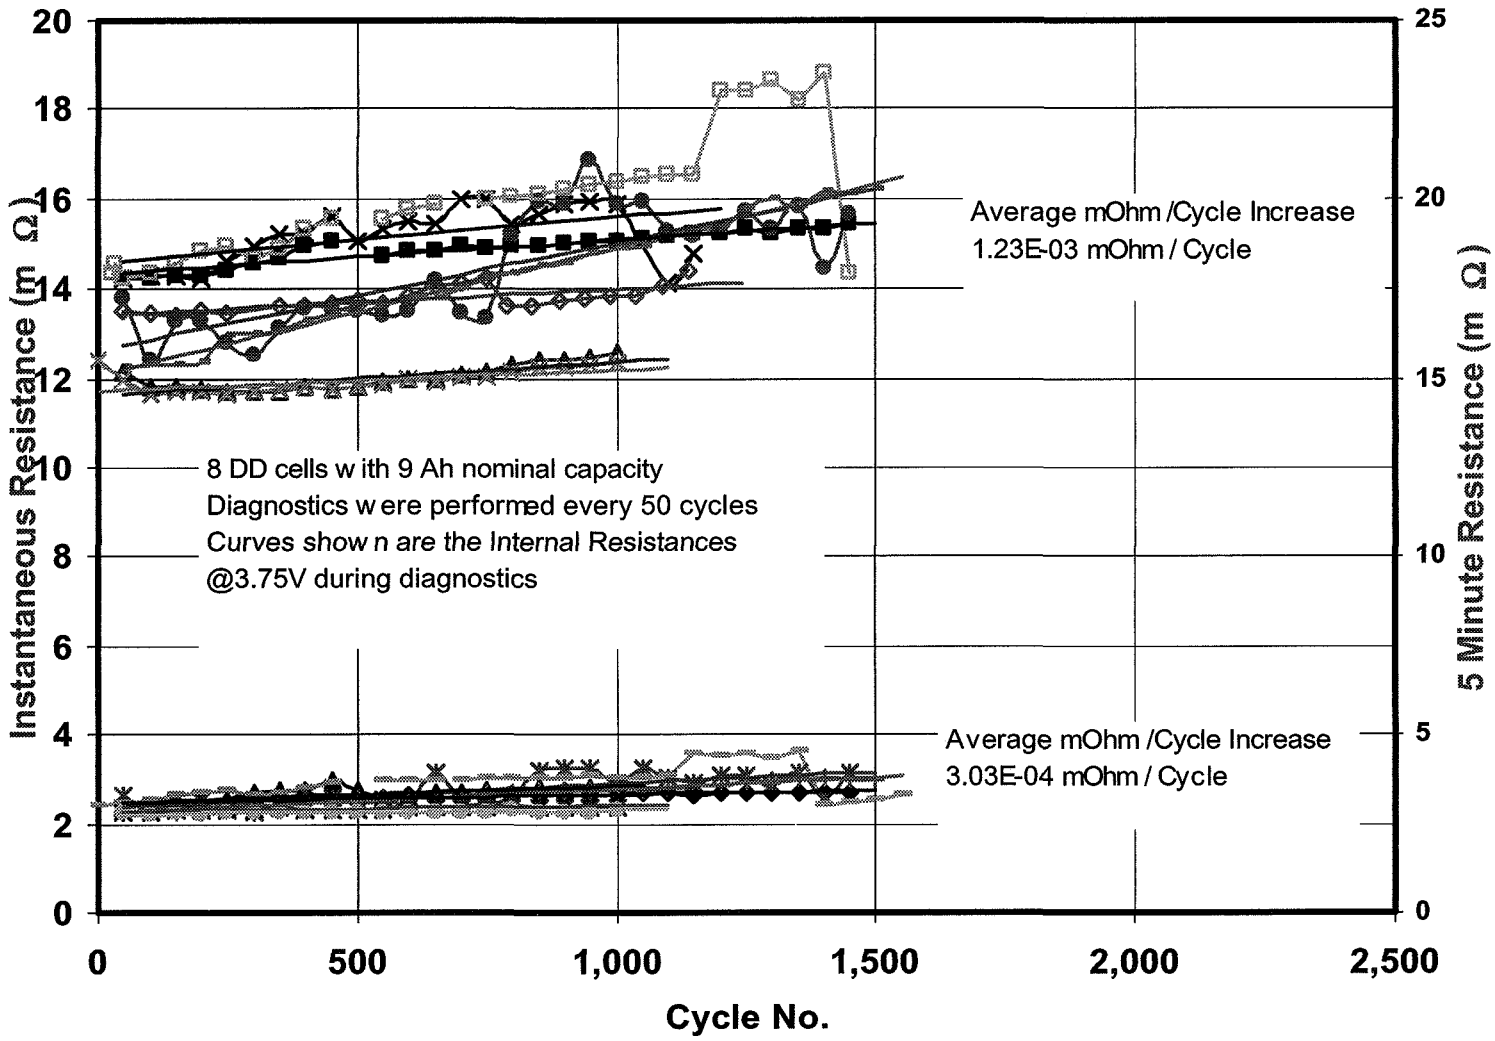

SAFT

GEO TESTING

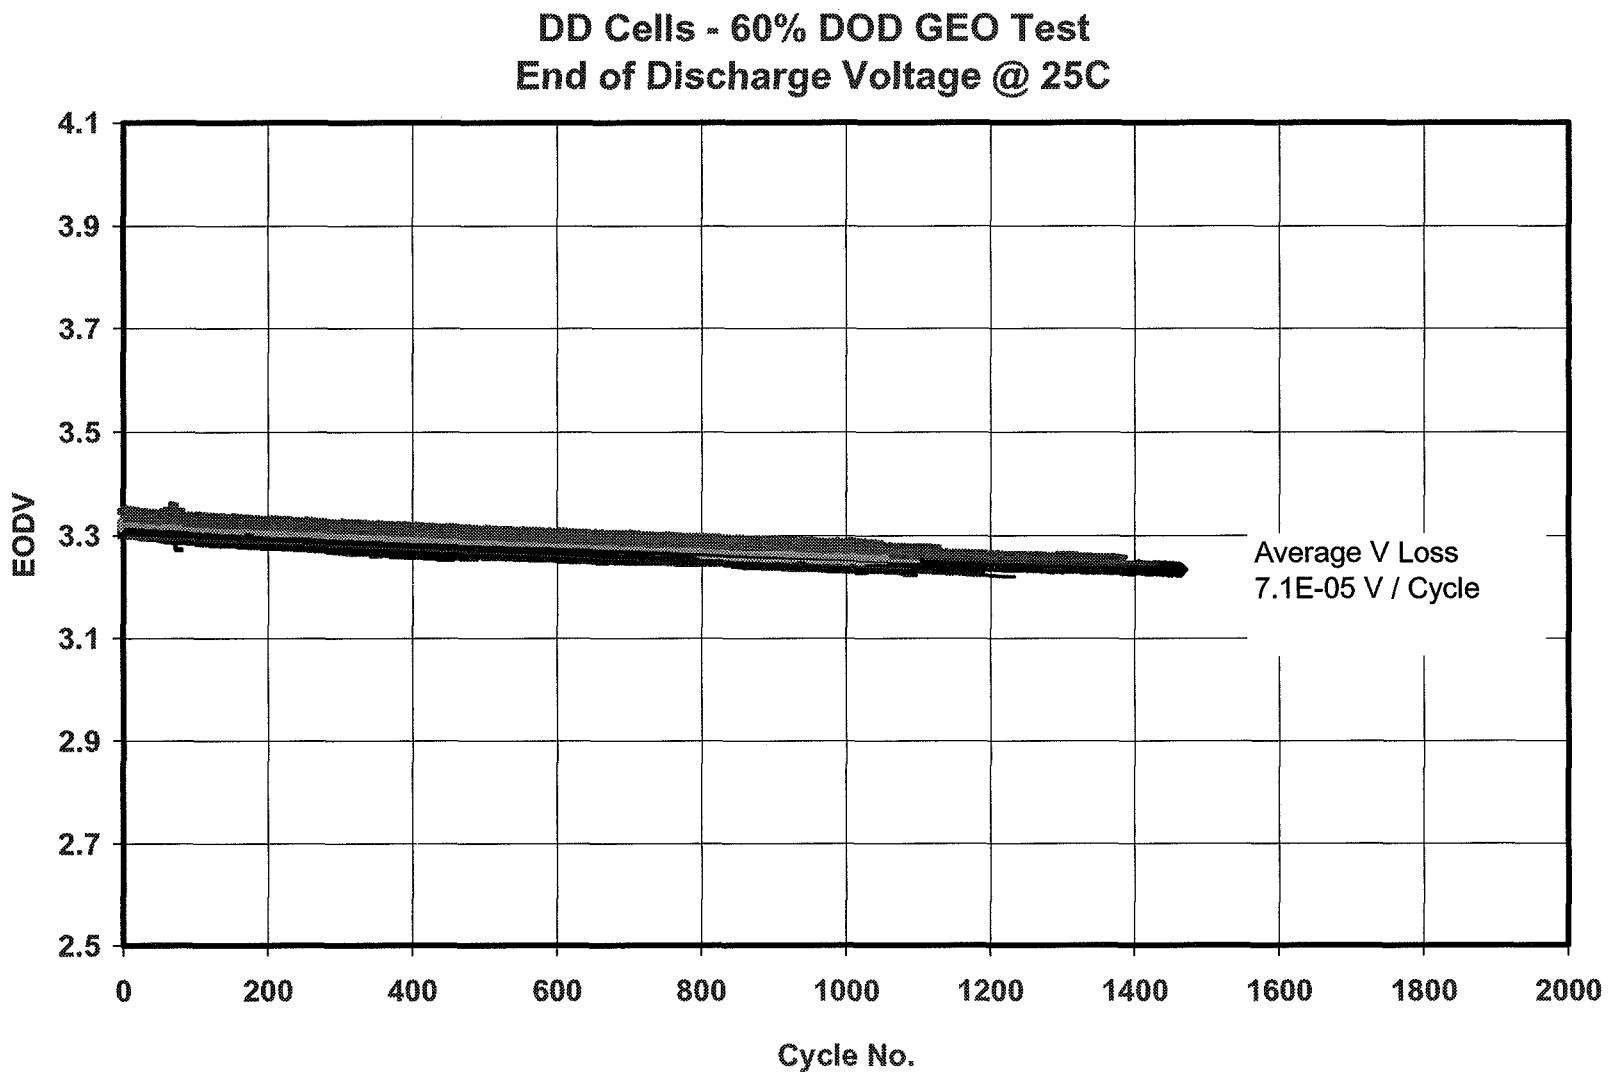

SAFT

GEO TESTING

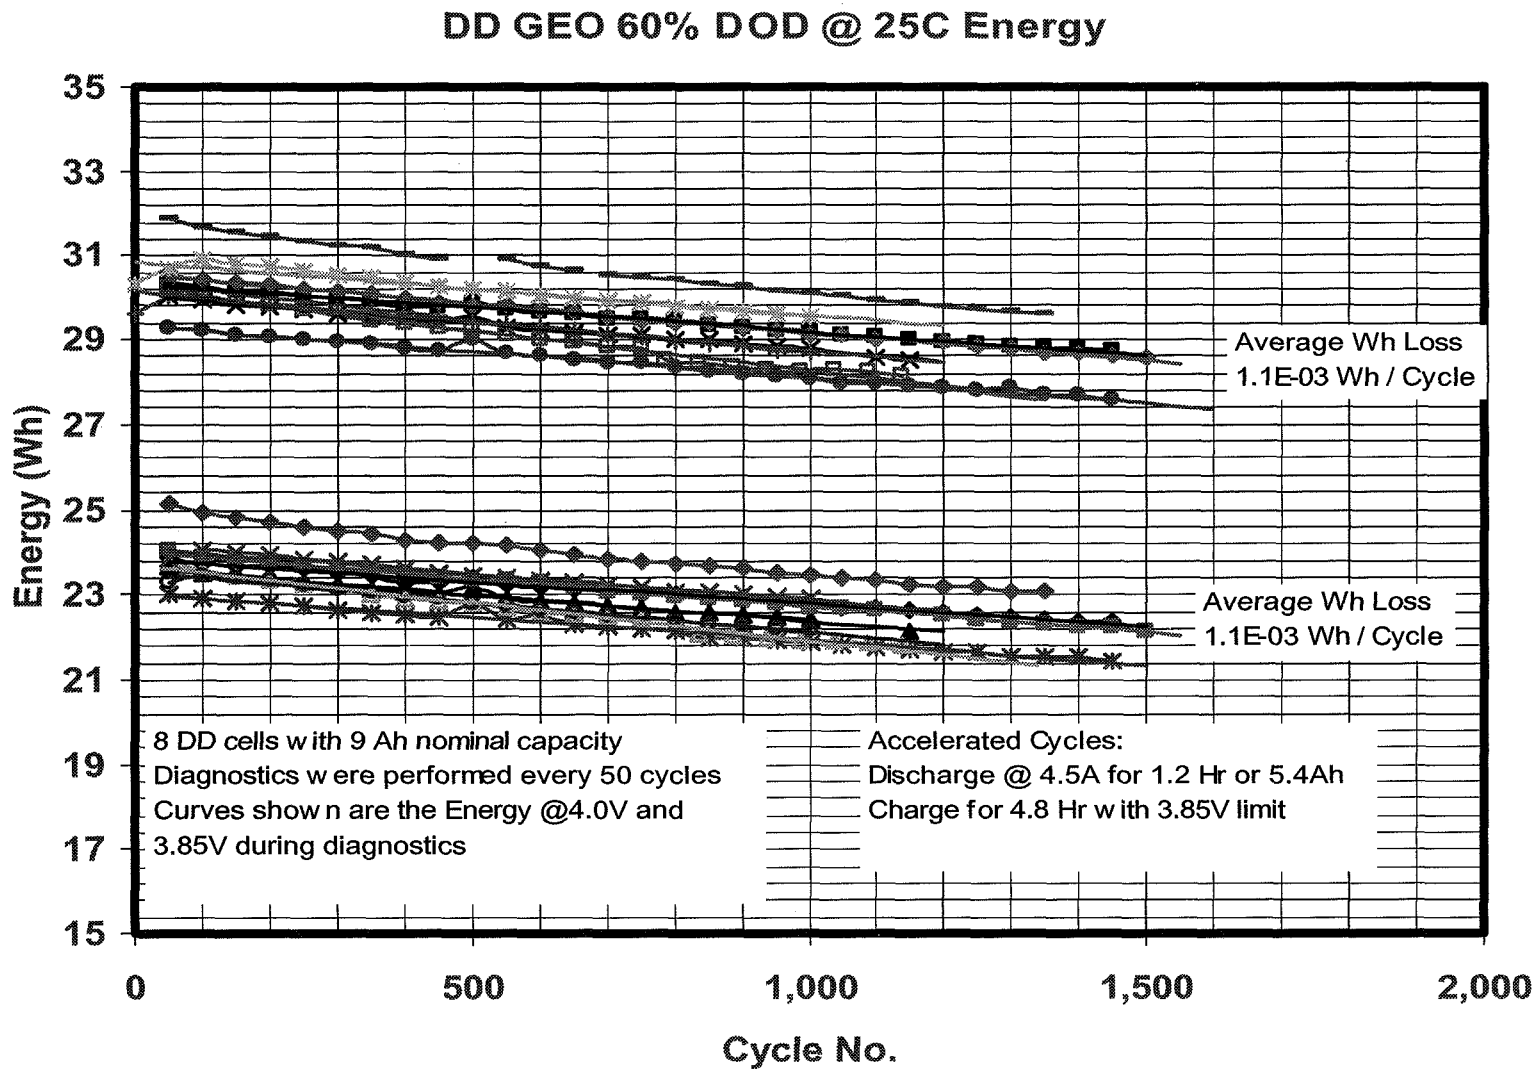

CALENDAR LIFE

Cell Fading Mechanisms

- Loss of lithium due to continuous SEI layer build up – parabolic function where fading rate decreases with time
- Degradation of active material properties – probably linear loss of capacity and impedance growth

SAFT

CALENDAR LIFE

- Capacity measurement conducted at ambient temperature
- Cells stored on open circuit at 50% SOC in 45°C and 60°C, which is reasonable since a cycling cell is on average at 50% SOC
- Diagnostic tests performed every month for impedance and capacity

Calendar Life Projection

Capacity Loss	Expected Life of the Battery Updated for 32 weeks of data and normalized for temperature							
Years	1	3	5	7	10	12	14	15
Months	12	36	60	84	120	144	168	180
15°C	2.91%	3.63%	4.35%	5.07%	6.15%	6.87%	7.59%	7.95%
25°C	3.44%	5.21%	6.99%	8.77%	11.43%	13.21%	14.98%	15.87%

Equations	
Capacity Loss-Temperature relationships	$\%Loss = 8*10^{7}*e^{-7.5734*x}$ where $x = {}^{1000}/K$ used for projecting the loss of capacity
Linear loss of capacity after the 3rd month	%Loss = A + B*(# of months) where A = 2.55% and B = 0.03% for 15°C where A = 2.55% and B = 0.074% for 25°C

SAFT

CYCLE LIFE EXTRAPOLATION

CORRECTED FOR CALENDAR LIFE (8 YEARS FOR LEO; 15 YEARS GEO)

Depth Of Discharge %	Cycles Achieved	Wh Fade Rate @ 4V % Per Cycle	Typical Req. For Cycles	E.O.L. Energy* Wh 25°C
30	12,000	.000704	40,000	21.8 - 2.6 = 19.1
60	1500	.0011	1,500	29.9- 4.49 = 25.4

CRANE CELL TESTING SUPPORT OF NASA/GODDARD SPACE FLIGHT CENTER: AN UPDATE

Mike Strawn and Jerry David
NAVSURFWARCENDIV Crane, Indiana
Gopalakrishna M. Rao
NASA Goddard Space Flight Center
Greenbelt, Maryland

Sia/Pol/Mt/Ht
2001117797
3pgs
538033

OBJECTIVE

- Verify the Quality and Reliability of aerospace battery cells and batteries for NASA flight programs
- Disseminate the data
  - to develop a Plan for in-orbit battery management
  - to Design a cell/battery for future NASA spacecraft
- Establish a cell test Data Base for rechargeable cell/batteries

PACKS

Orbit	Pack	Type	Ah	Start Date	DoD	°C	K Cycles
Stress	0021H	Super	21	10/98	50	20	10.9
Mission	0040P	Saft Ni-Cd	40	7/96	21	5	20.4
Mission	0044P	Saft Ni-Cd	40	1/99	21	5	9.0
Mission	0045P	Saft Ni-Cd	40	1/00	21	5	3.2
Mission	0052T	Super	50	3/95	14.4	10	28.9
Mission	0053T	Super	50	5/95	17	0	27.9
Mission	6151T	Super	50	6/96	25	10	22.4
Stress	6152T	Super	50	6/96	17	0	24.6
Stress	3023M	EPT-CPV	23	11/98	60	10	1.3
Stress	3023T	EPT-CPV	23	12/98	60	10	10.4
Mission	3050S	EPT	50	1/00	60	10	4.1
Mission	3050H	EPT	50	10/95	20	5	25.6
Mission	3600H	EPT	93	1/92	11	-5	42.7
Mission	3601H	EPT	93	1/92	11	-5	42.2

DISCONTINUED PACKS

Orbit	Pack	Type	Ah	Date Start/ End	DoD	°C	K Cycles
Stress	0042P	Saft Ni-Cd	40	7/97 3/00	40	20	15.1
Stress	0043P	Saft Ni-Cd	40	10/97 2/00	40	20	13.1
Mission	B300A	Super	21	3/99 2/00	pulse	5	0.5
GEO REAL	GOES 1	Saft Ni-Cd	12	10/95 7/00	60	0	Sh#10

Packs discontinued during FY00

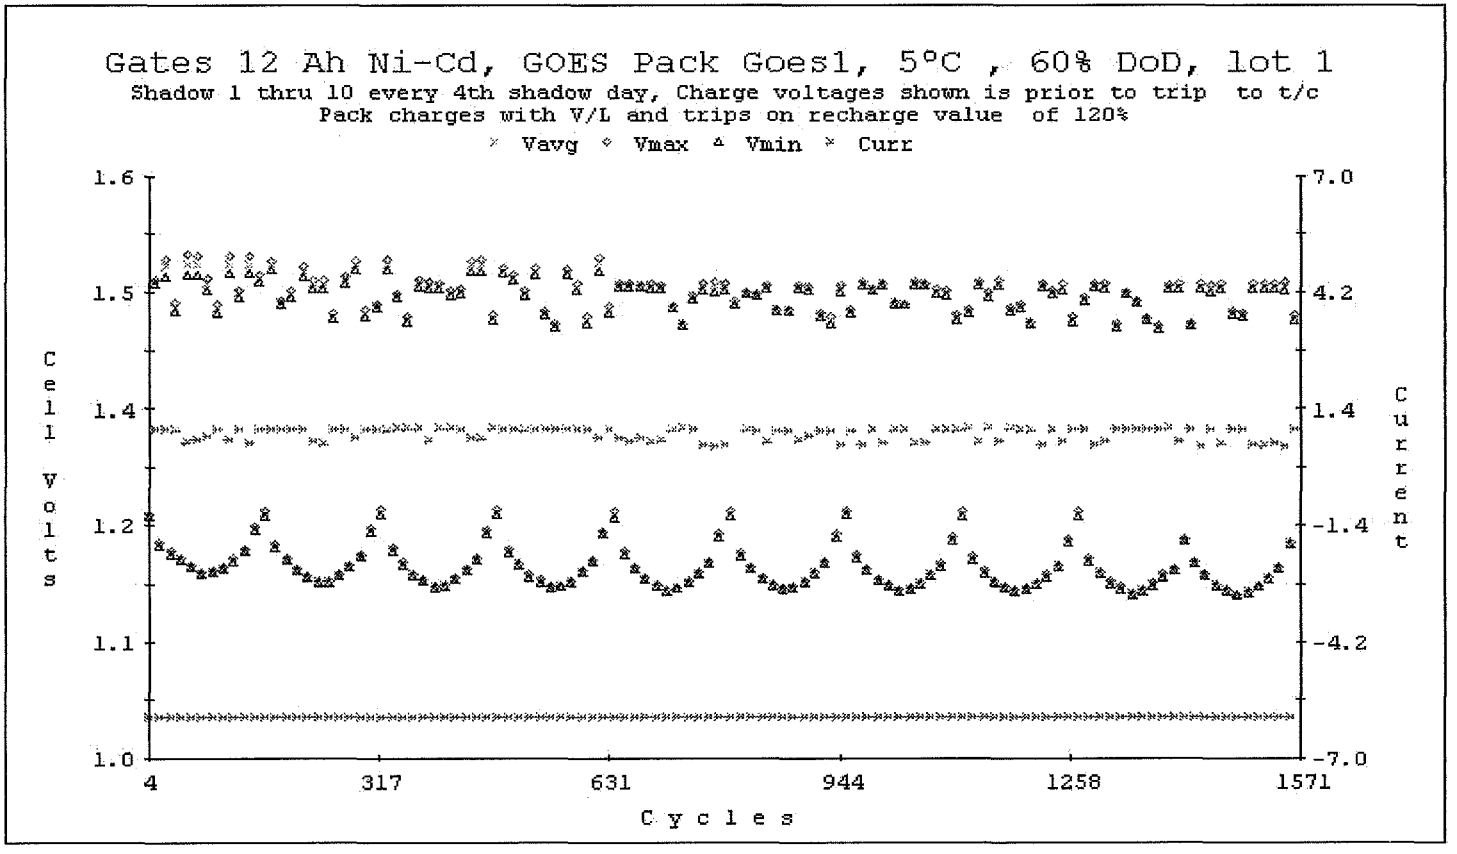
Gates 12 Ah Ni-Cd, GOES Pack Goes1, 5°C , 60% DoD, lot 1
Shadow 1 thru 10 every 4th shadow day, Charge voltages shown is prior to trip to t/c
Pack charges with V/L and trips on recharge value of 120%
Vavg Vmax Vmin Curr
1.6
1.5
1.4
1.2
1.1
1.0
Cell Volts
7.0
4.2
1.4
-1.4
-4.2
-7.0
Current
4
317
631
944
1258
1571
Cycles

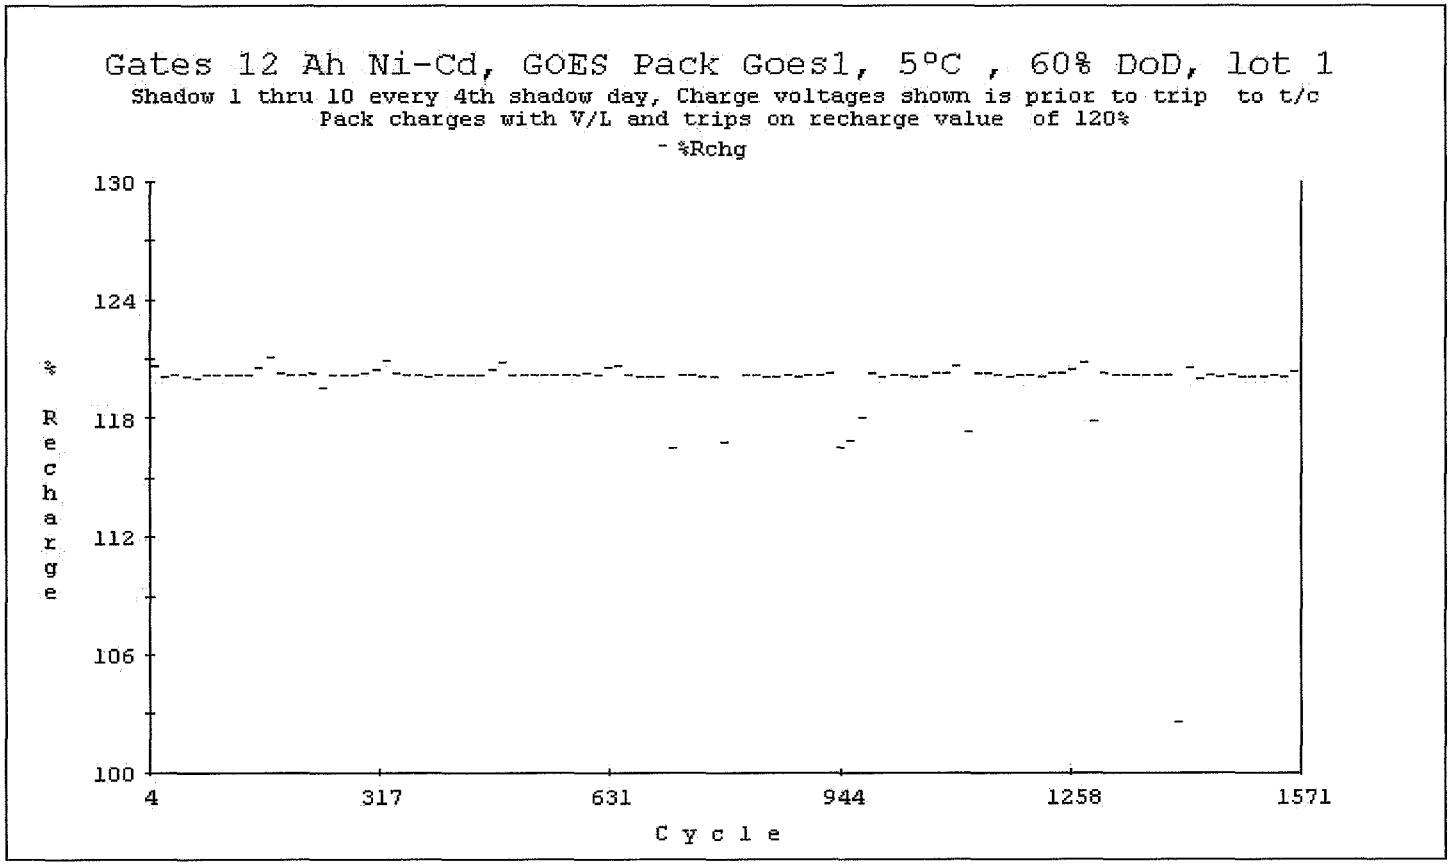
Gates 12 Ah Ni-Cd, GOES Pack Goes1, 5°C , 60% DoD, lot 1
Shadow 1 thru 10 every 4th shadow day, Charge voltages shown is prior to trip to t/c
Pack charges with V/L and trips on recharge value of 120%
- %Rchg
130
124
118
112
106
100
% Recharge
4
317
631
944
1258
1571
Cycle

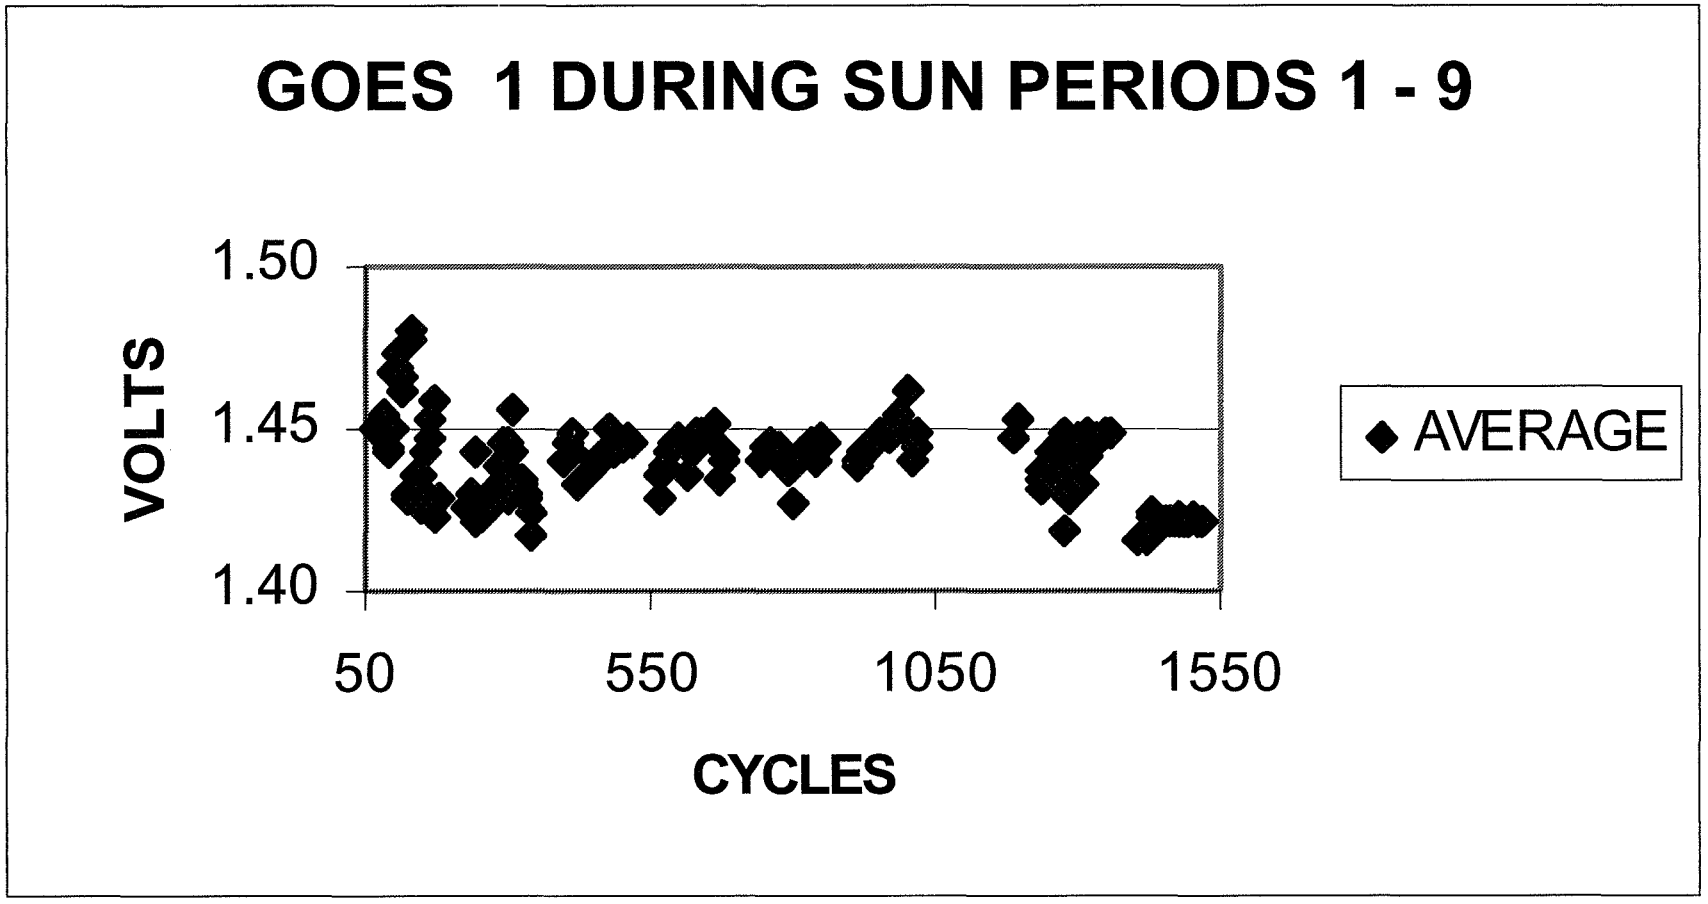
GOES 1 DURING SUN PERIODS 1 - 9
1.50
1.45
1.40
VOLTS
50
550
1050
1550
CYCLES
AVERAGE

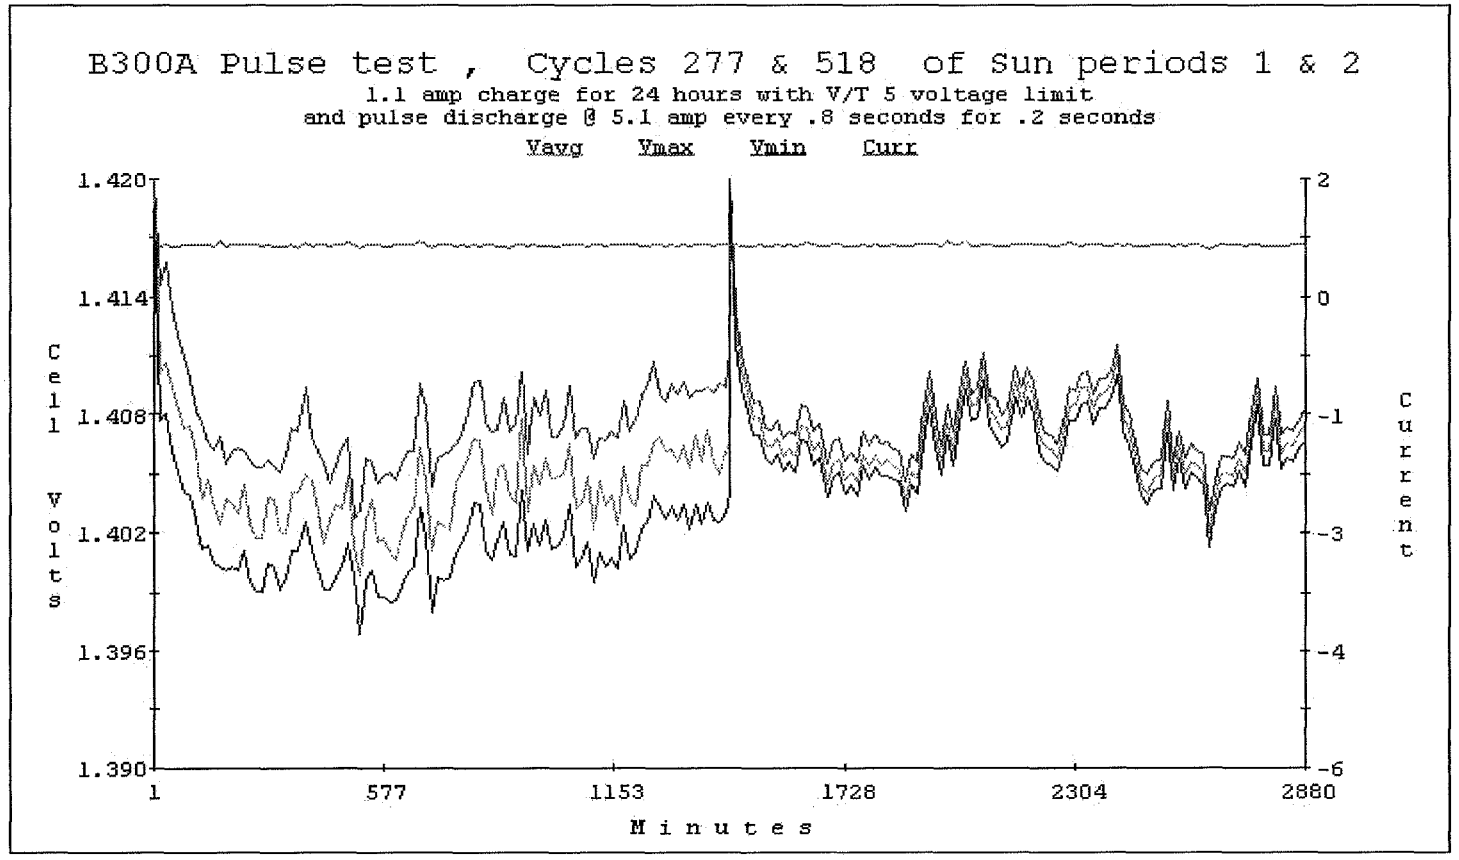
B300A Pulse test , Cycles 277 & 518 of Sun periods 1 & 2
1.1 amp charge for 24 hours with V/T 5 voltage limit
and pulse discharge @ 5.1 amp every .8 seconds for .2 seconds
Vavg
Vmax
Vmin
Curr
1.420
1.414
1.408
1.402
1.396
1.390
Cell Volts
2
0
-1
-3
-4
-6
Current
1
577
1153
1728
2304
2880
Minutes

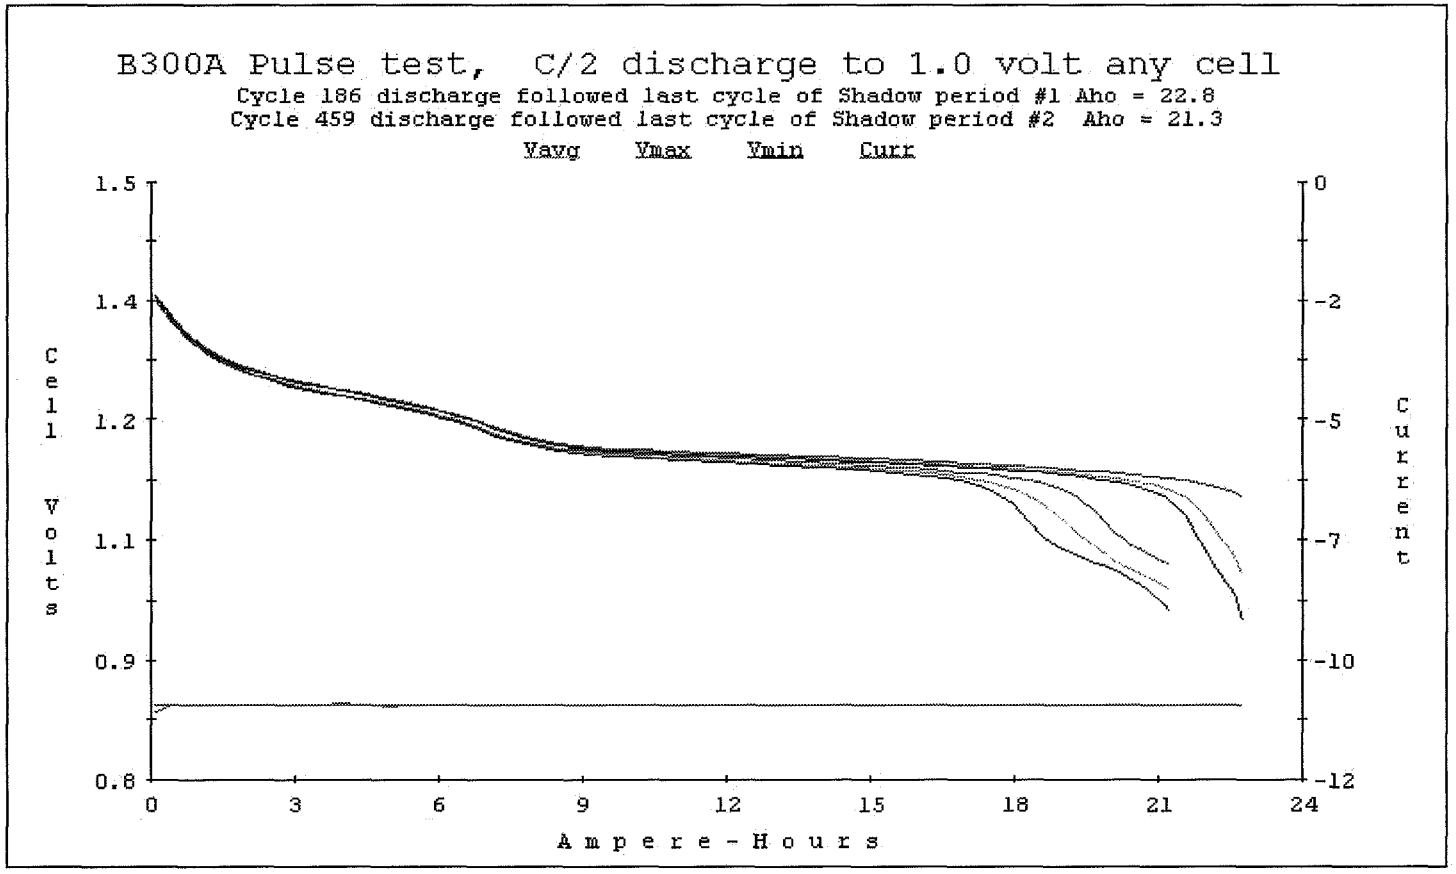
B300A Pulse test, C/2 discharge to 1.0 volt any cell
Cycle 186 discharge followed last cycle of Shadow period #1 Aho = 22.8
Cycle 459 discharge followed last cycle of Shadow period #2 Aho = 21.3
Vavg Vmax Vmin Curr
Cell Volts
1.5
1.4
1.2
1.1
0.9
0.8
0
-2
-5
-7
-10
-12
Current
0 3 6 9 12 15 18 21 24
Ampere-Hours

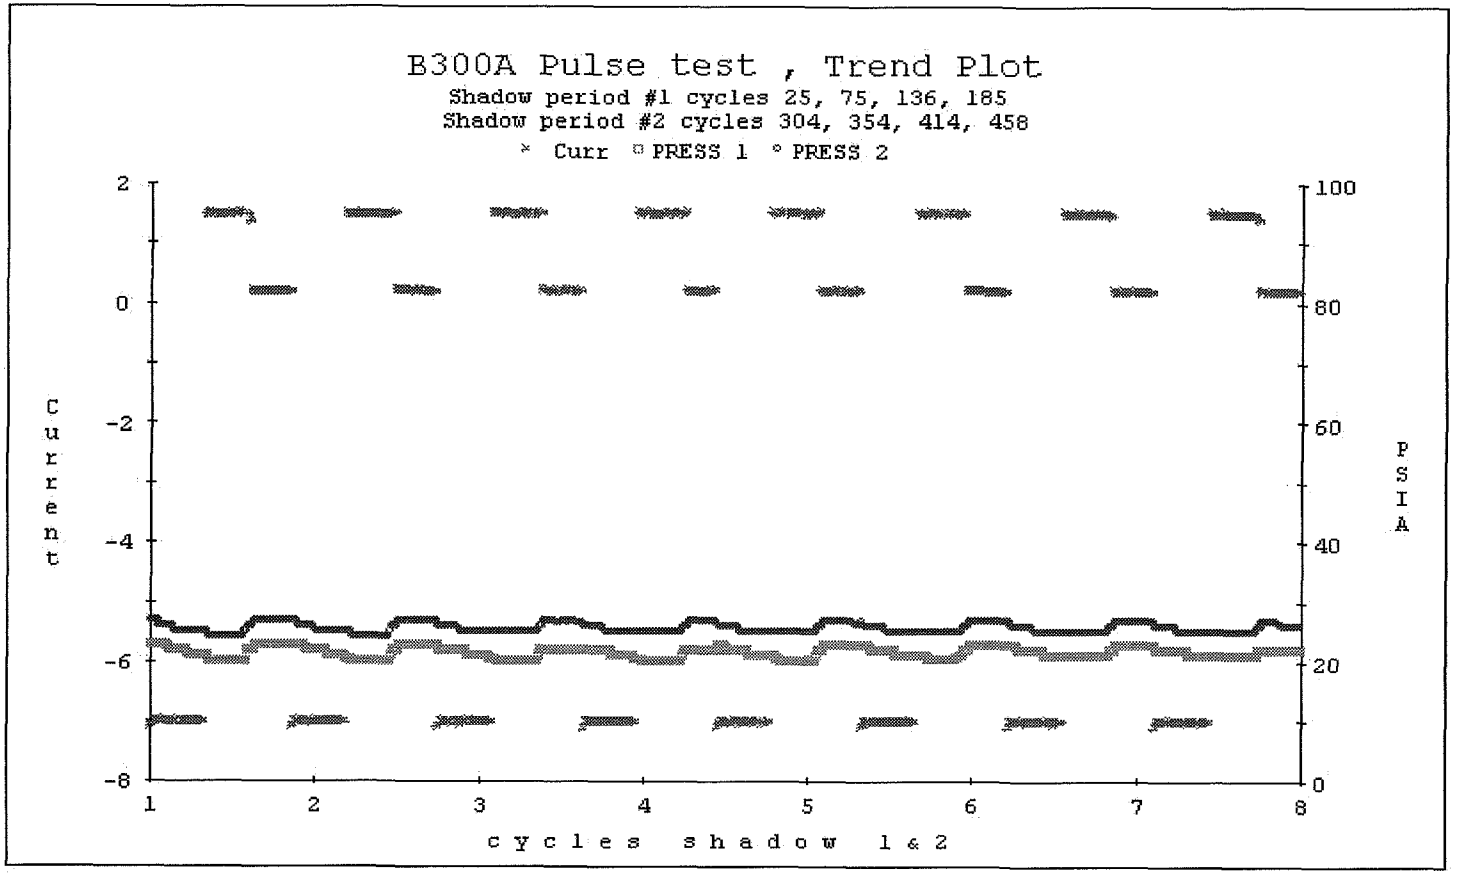
B300A Pulse test , Trend Plot
Shadow period #1 cycles 25, 75, 136, 185
Shadow period #2 cycles 304, 354, 414, 458
Curr PRESS 1 PRESS 2
Current
PSIA
2
0
-2
-4
-6
-8
100
80
60
40
20
0
1
2
3
4
5
6
7
8
cycles shadow 1 & 2

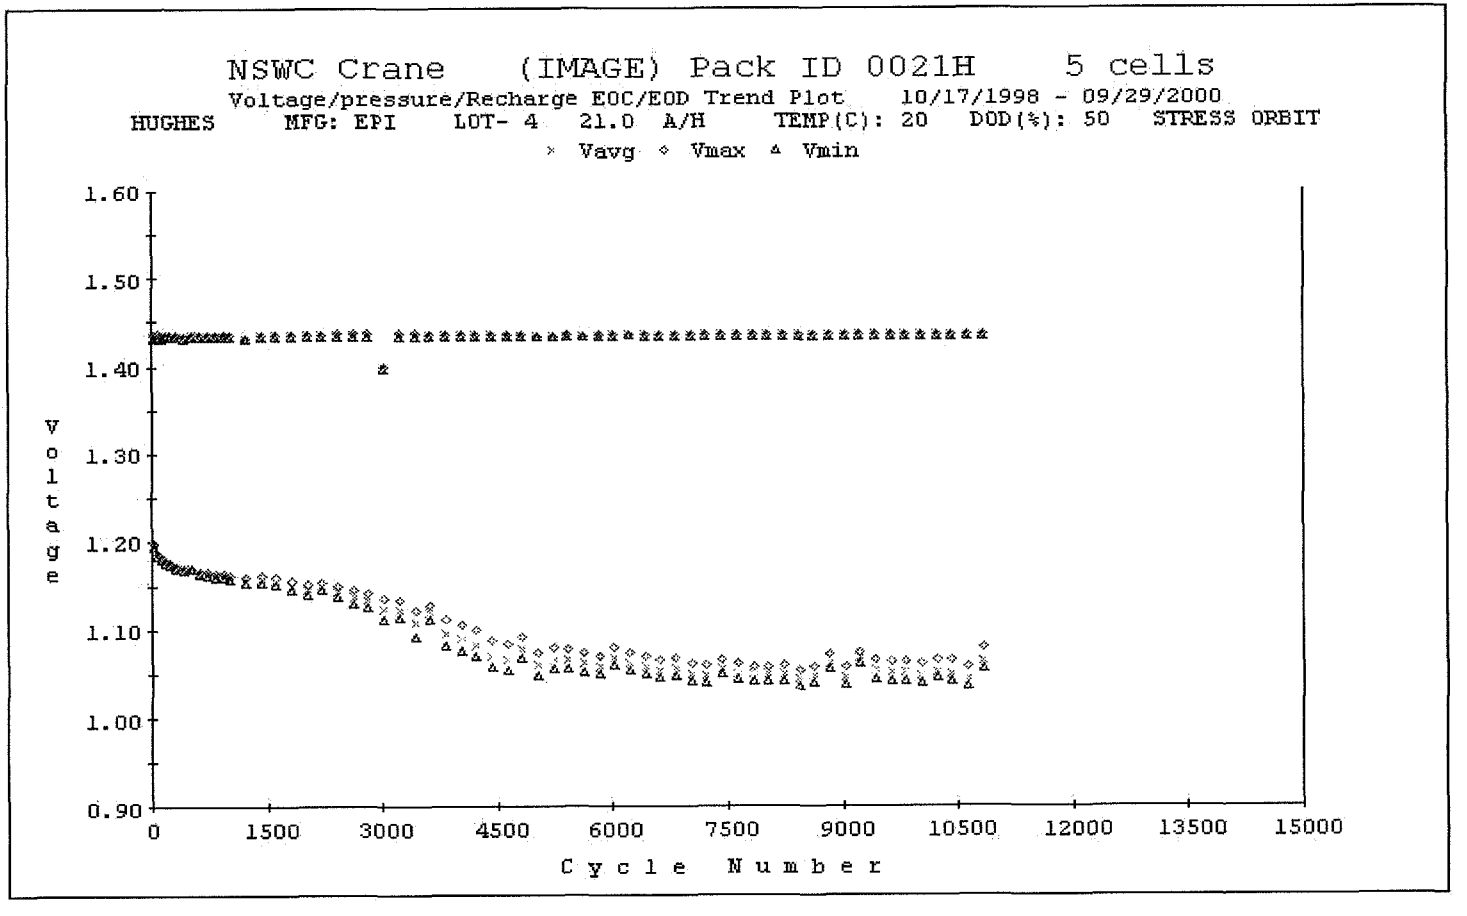
NSWC Crane (IMAGE) Pack ID 0021H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 10/17/1998 - 09/29/2000
HUGHES MFG: EPI LOT- 4 21.0 A/H TEMP(C): 20 DOD(%): 50 STRESS ORBIT
× Vavg ◇ Vmax △ Vmin
Voltage
1.60
1.50
1.40
1.30
1.20
1.10
1.00
0.90
0
1500
3000
4500
6000
7500
9000
10500
12000
13500
15000
Cycle Number

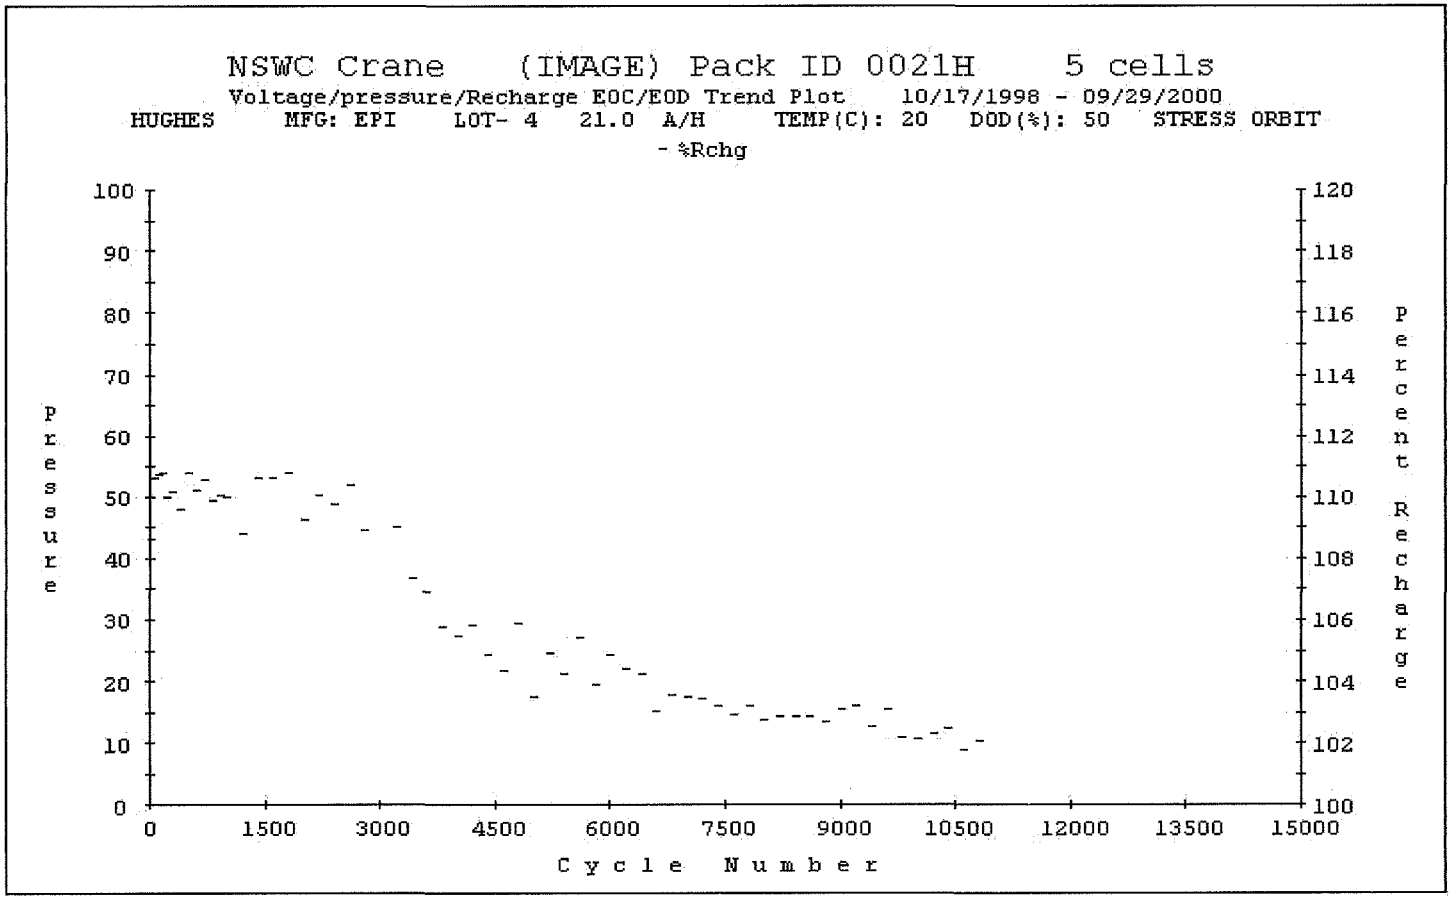
NSWC Crane (IMAGE) Pack ID 0021H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 10/17/1998 - 09/29/2000
HUGHES MFG: EPI LOT- 4 21.0 A/H TEMP(C): 20 DOD(%): 50 STRESS ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
1500
3000
4500
6000
7500
9000
10500
12000
13500
15000

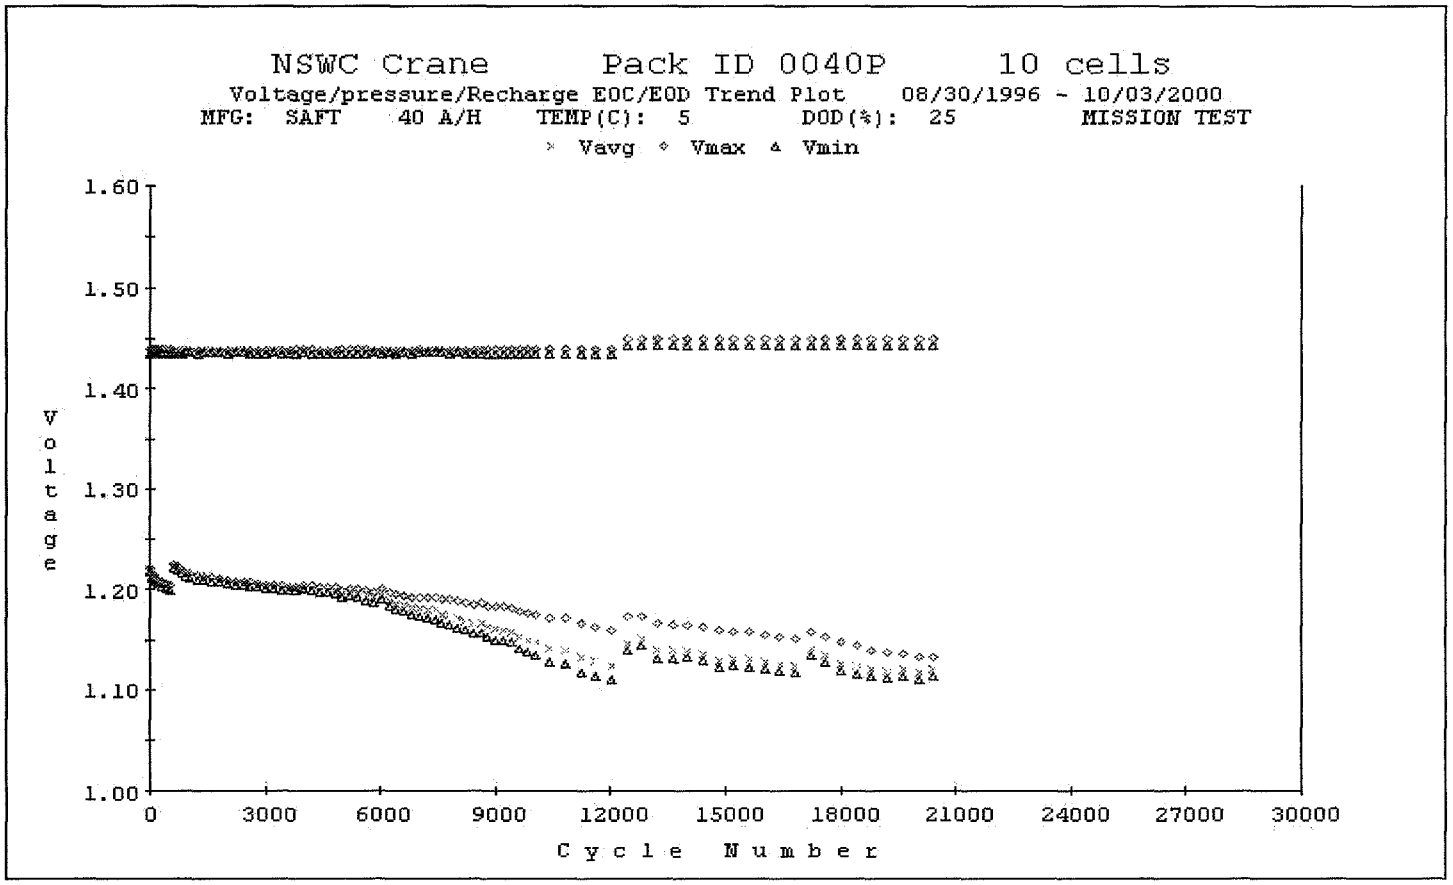
NSWC Crane Pack ID 0040P 10 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 08/30/1996 - 10/03/2000
MFG: SAFT 40 A/H TEMP(C): 5 DOD(%): 25 MISSION TEST
Vavg Vmax Vmin
Voltage
1.60
1.50
1.40
1.30
1.20
1.10
1.00
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

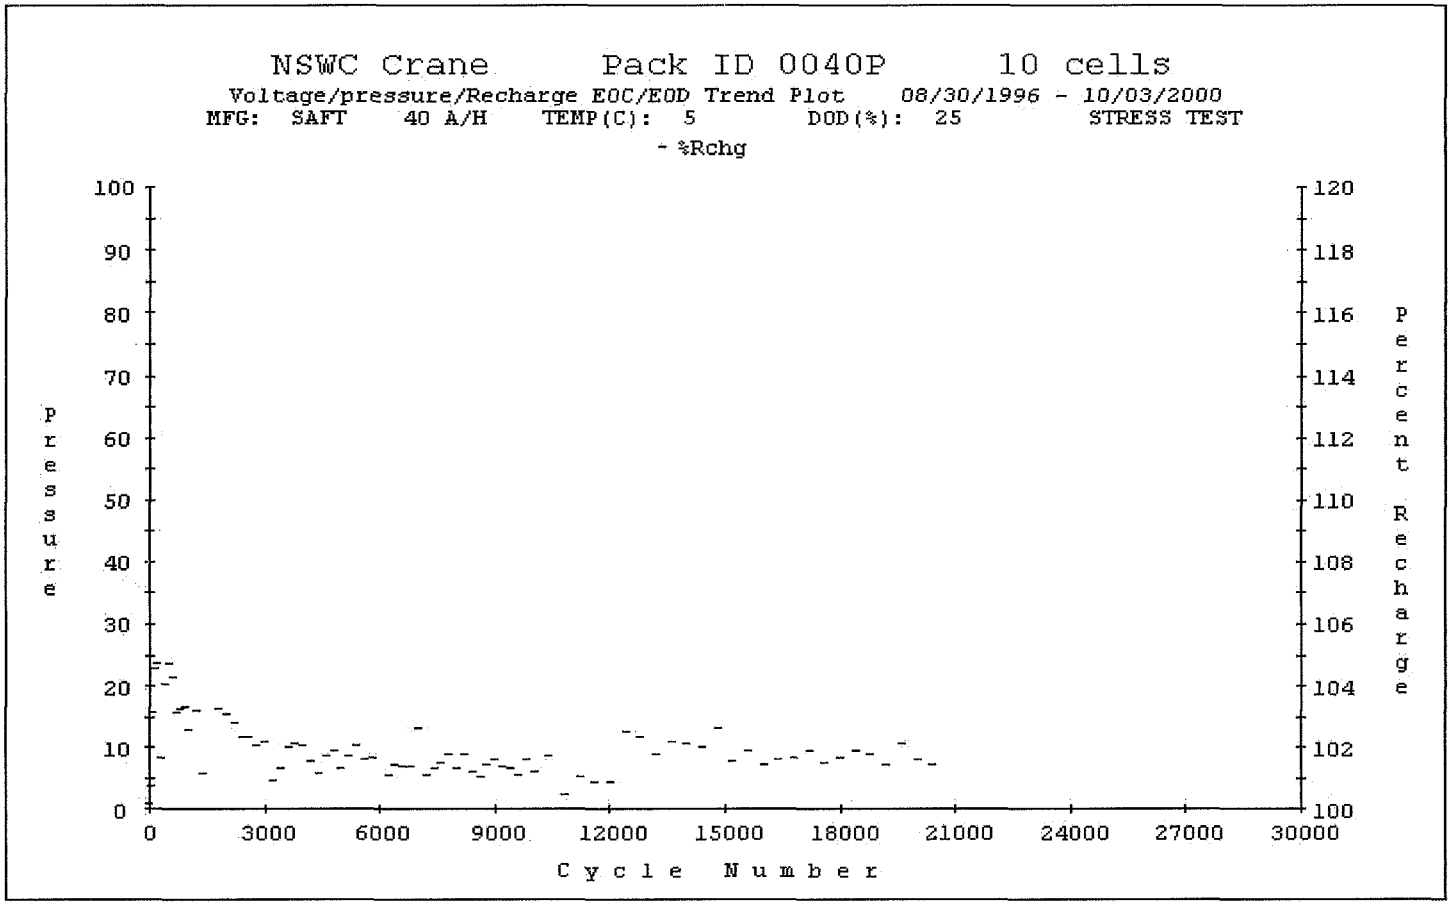
NSWC Crane Pack ID 0040P 10 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 08/30/1996 - 10/03/2000
MFG: SAFT 40 A/H TEMP(C): 5 DOD(%): 25 STRESS TEST
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

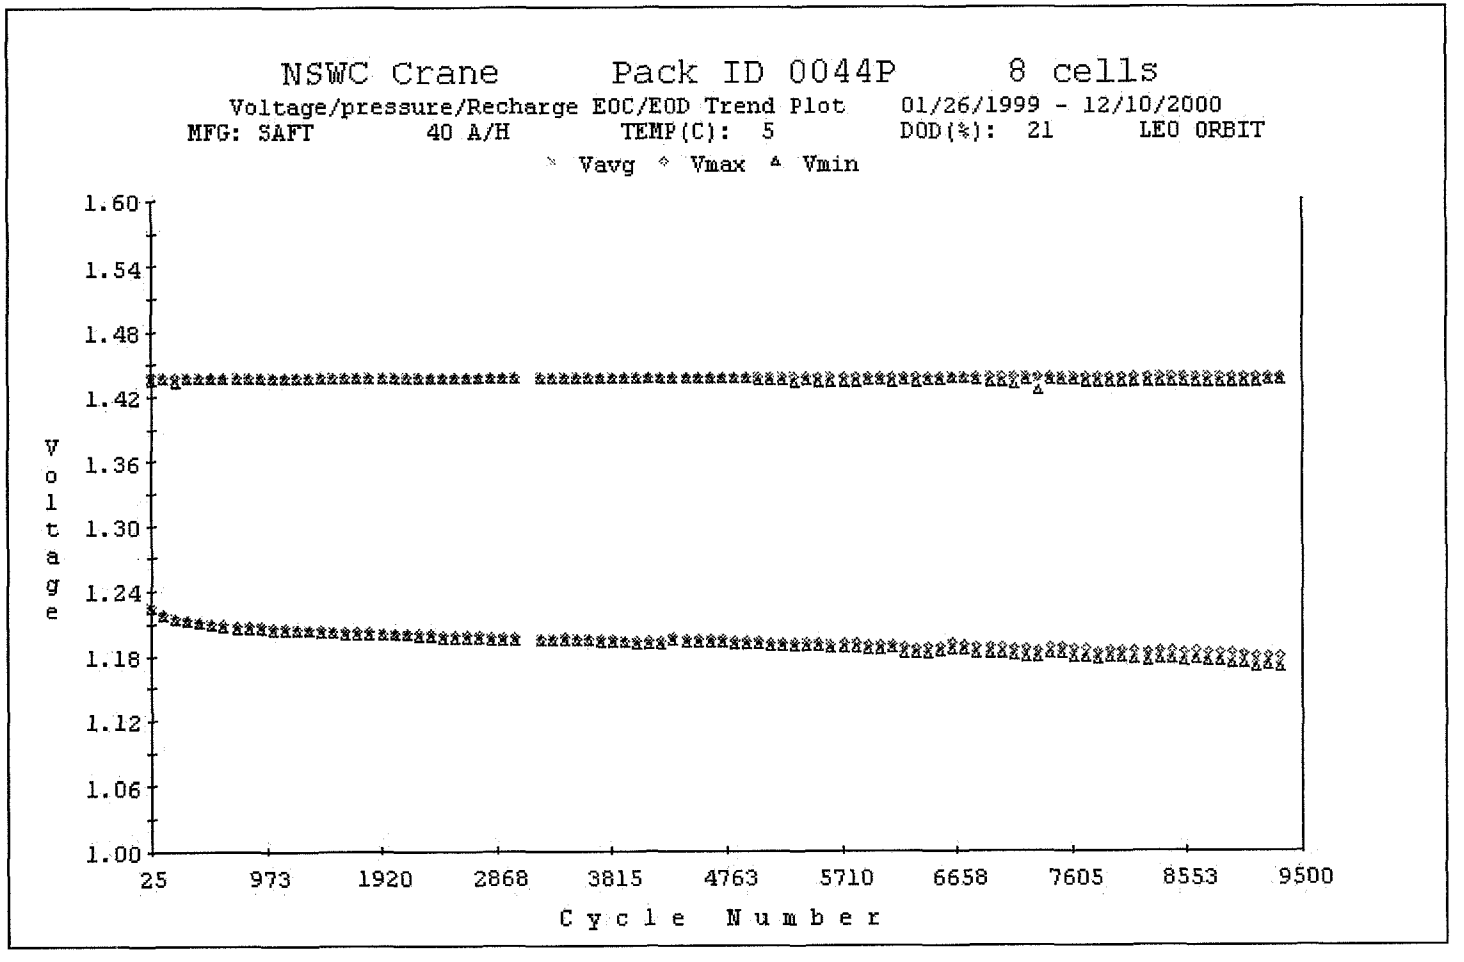
NSWC Crane Pack ID 0044P 8 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 01/26/1999 - 12/10/2000
MFG: SAFT 40 A/H TEMP(C): 5 DOD(%): 21 LEO ORBIT
Vavg Vmax Vmin
1.60
1.54
1.48
1.42
1.36
1.30
1.24
1.18
1.12
1.06
1.00
Voltage
25
973
1920
2868
3815
4763
5710
6658
7605
8553
9500
Cycle Number

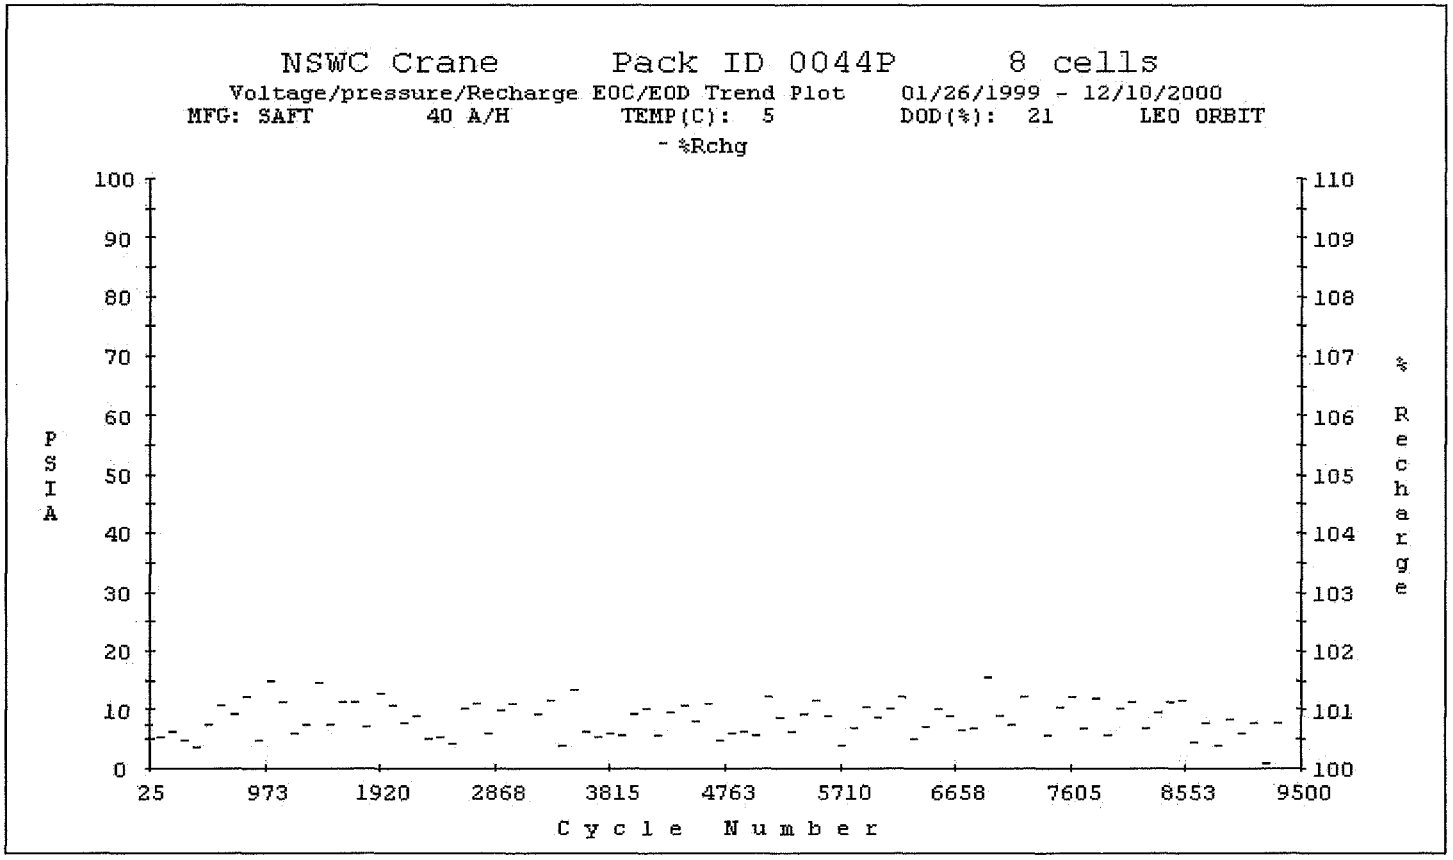
NSWC Crane Pack ID 0044P 8 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 01/26/1999 - 12/10/2000
MFG: SAFT 40 A/H TEMP(C): 5 DOD(%): 21 LEO ORBIT
- %Rchg
PSIA
% Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
101
102
103
104
105
106
107
108
109
110
25
973
1920
2868
3815
4763
5710
6658
7605
8553
9500

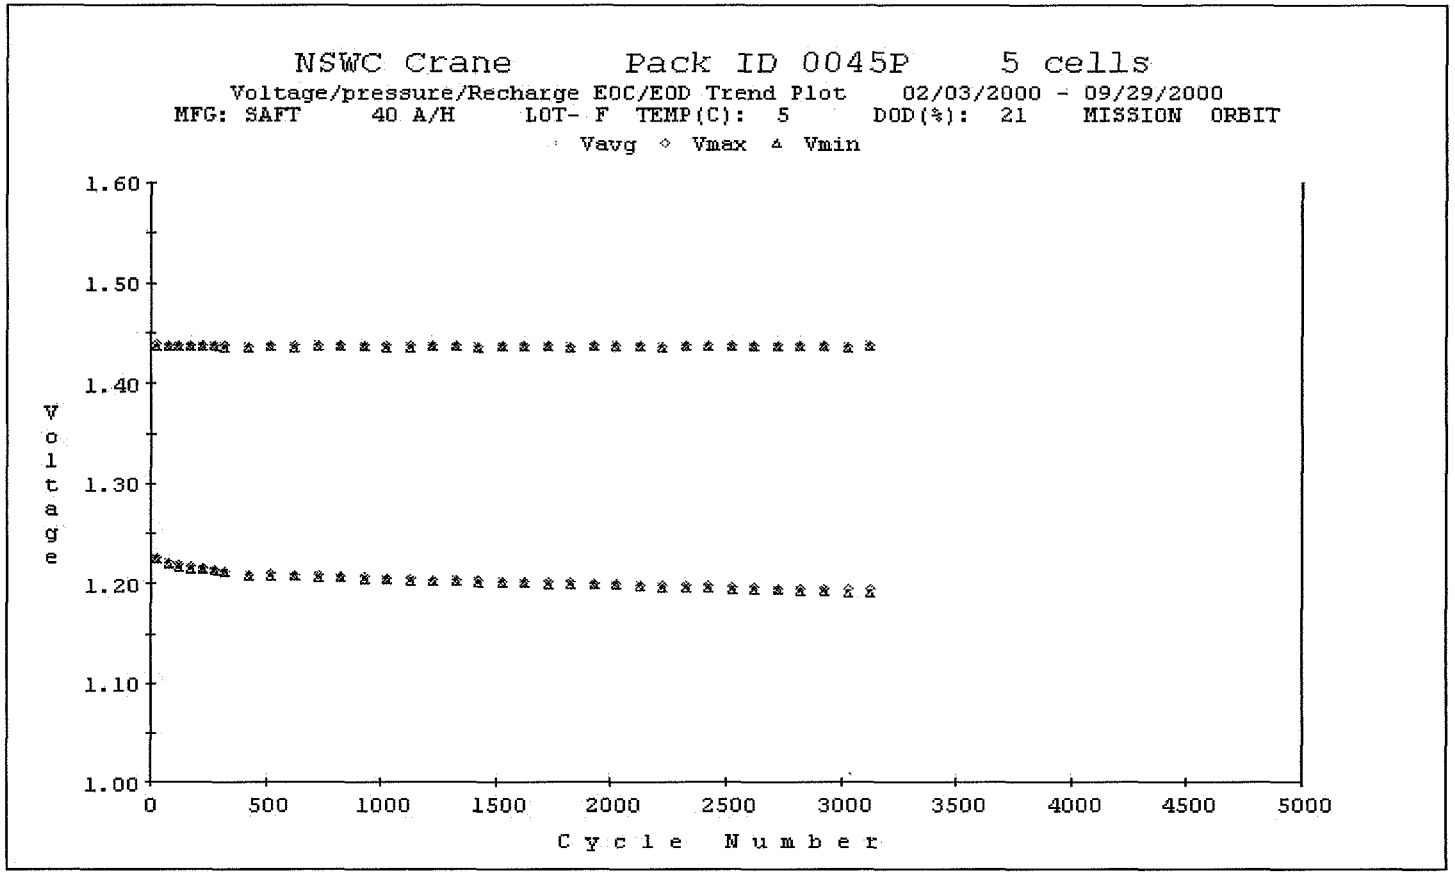
NSWC Crane Pack ID 0045P 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 02/03/2000 - 09/29/2000
MFG: SAFT 40 A/H LOT- F TEMP(C): 5 DOD(%): 21 MISSION ORBIT
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
500
1000
1500
2000
2500
3000
3500
4000
4500
5000
Cycle Number

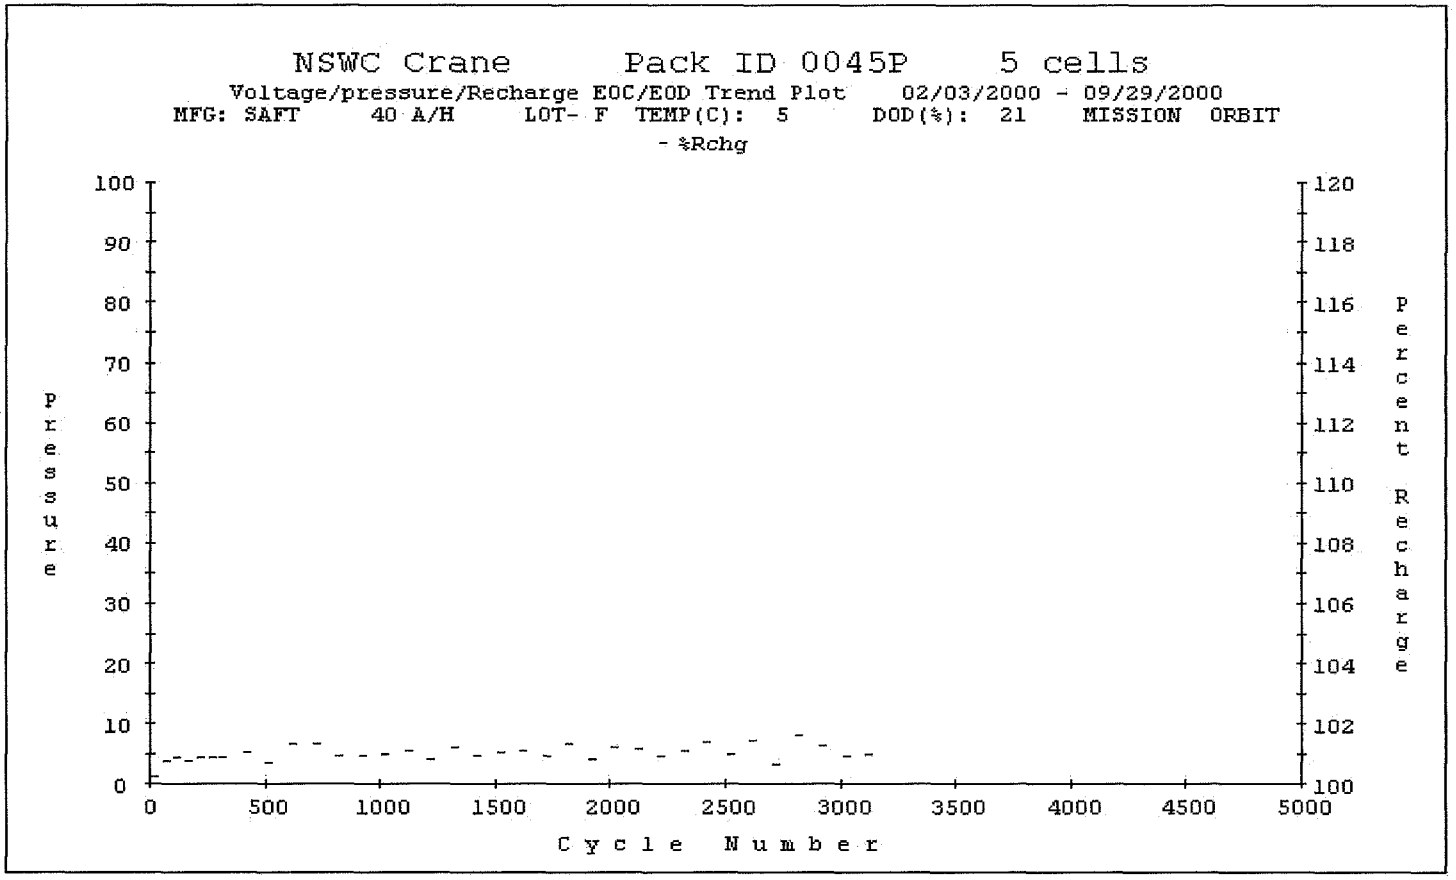
NSWC Crane Pack ID 0045P 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 02/03/2000 - 09/29/2000
MFG: SAFT 40 A/H LOT- F TEMP(C): 5 DOD(%): 21 MISSION ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
500
1000
1500
2000
2500
3000
3500
4000
4500
5000

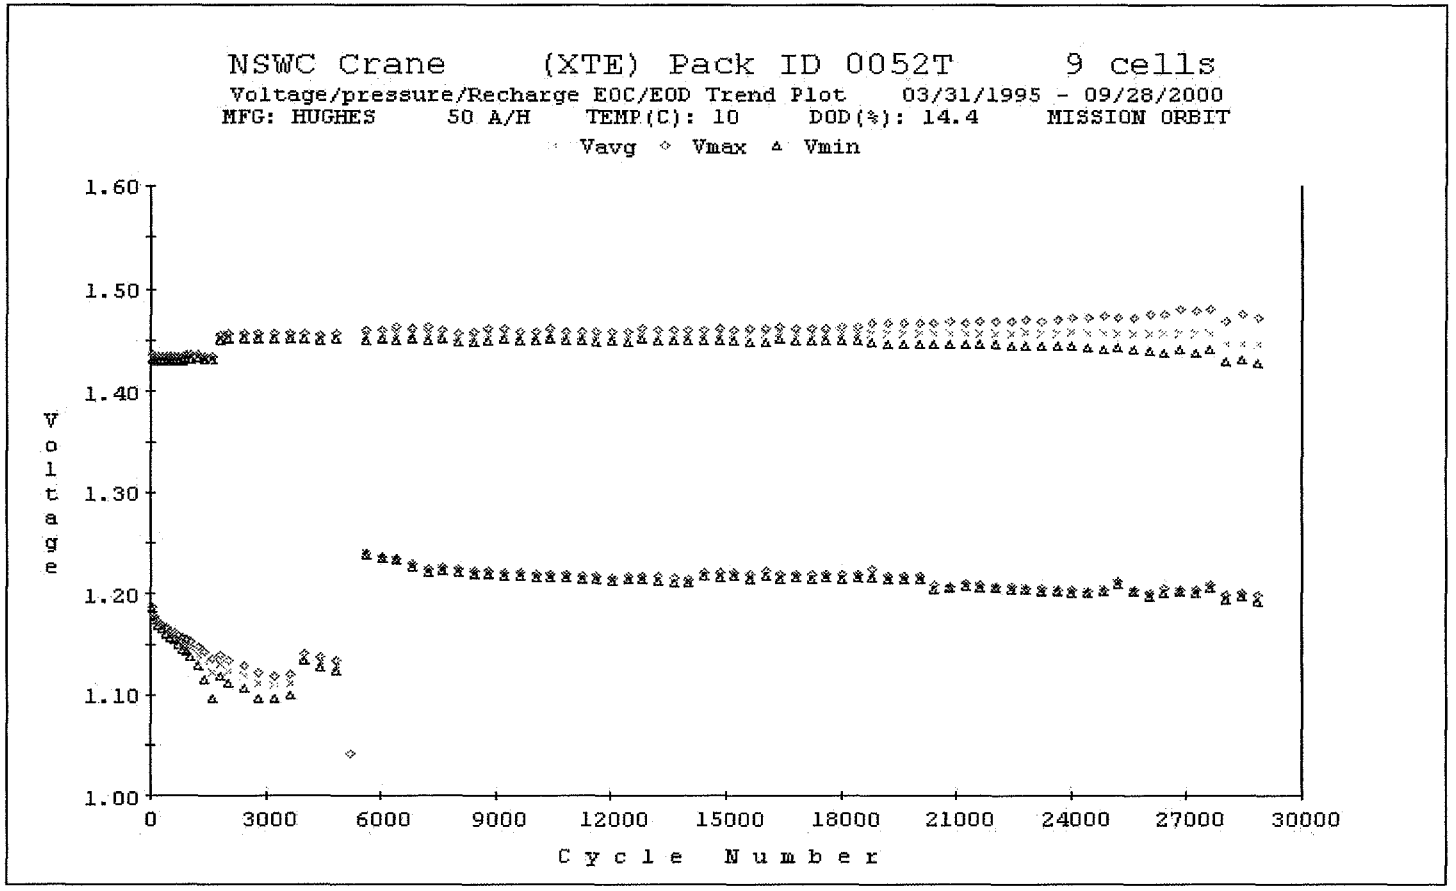
NSWC Crane (XTE) Pack ID 0052T 9 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 03/31/1995 - 09/28/2000
MFG: HUGHES 50 A/H TEMP(C): 10 DOD(%): 14.4 MISSION ORBIT
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

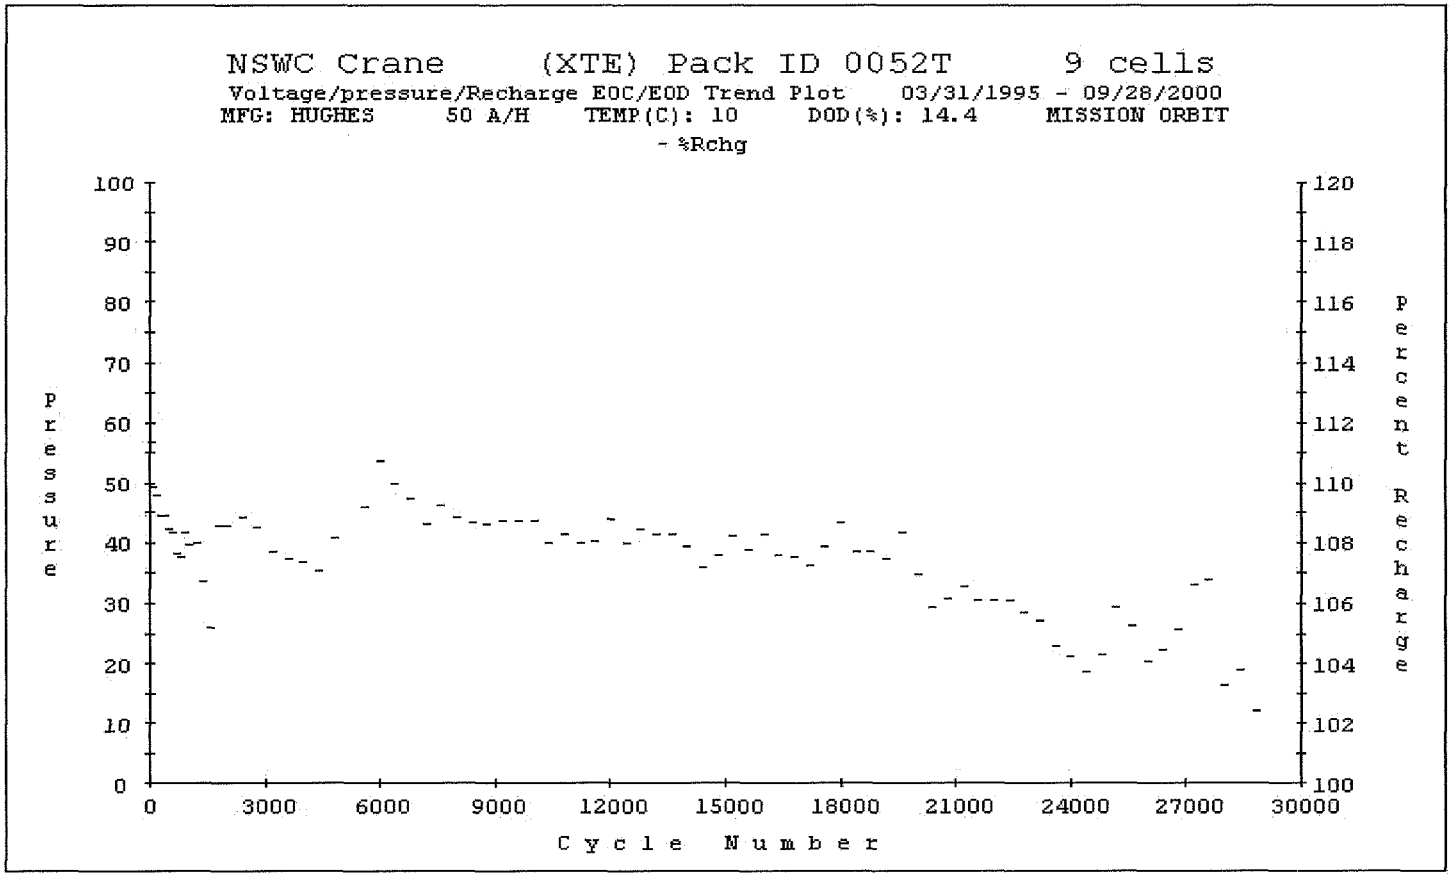
NSWC Crane (XTE) Pack ID 0052T 9 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 03/31/1995 - 09/28/2000
MFG: HUGHES 50 A/H TEMP(C): 10 DOD(%): 14.4 MISSION ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

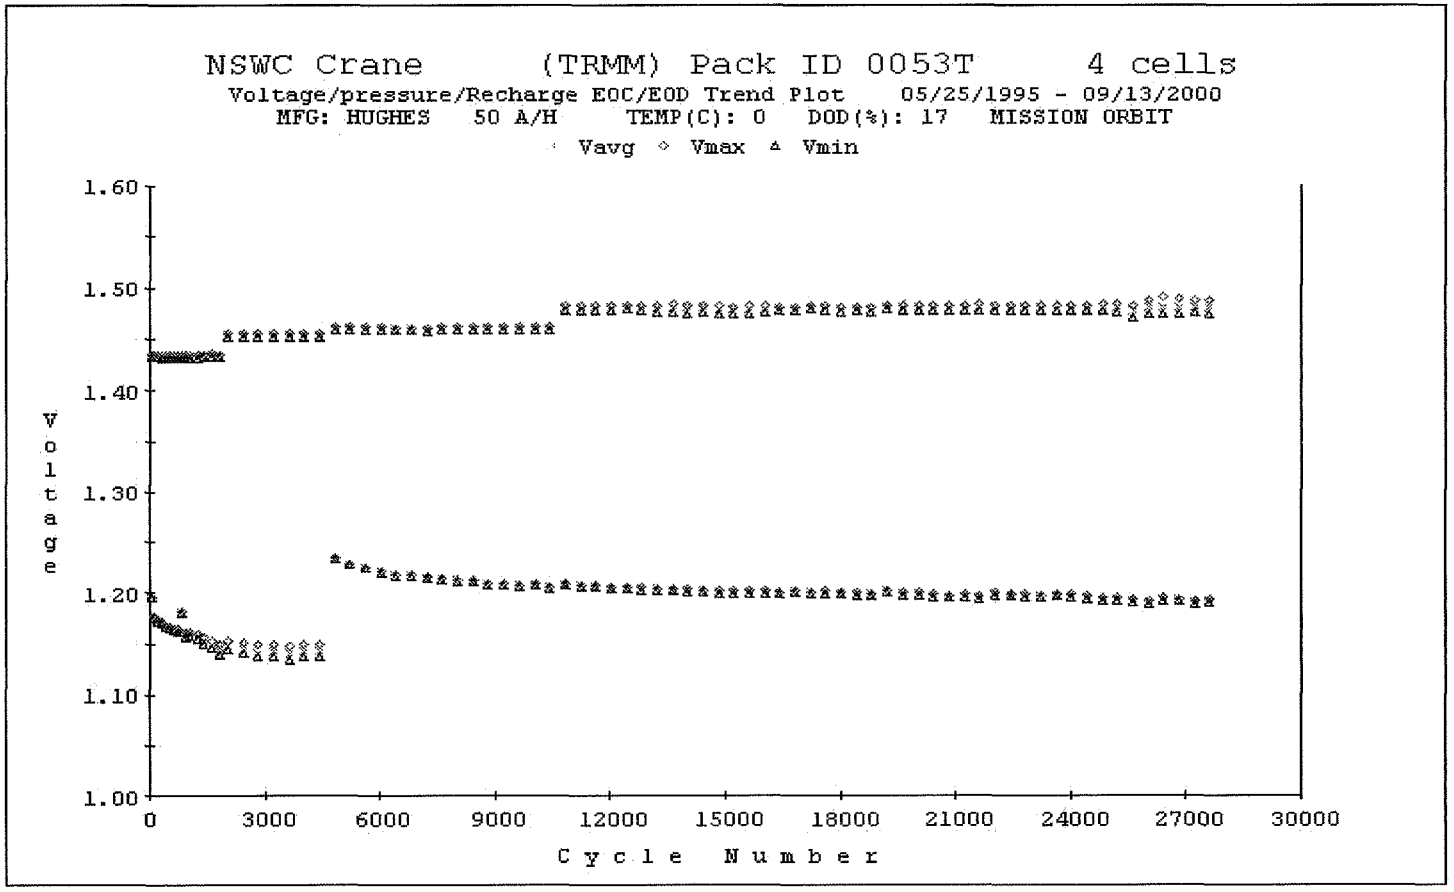
NSWC Crane (TRMM) Pack ID 0053T 4 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 05/25/1995 - 09/13/2000
MFG: HUGHES 50 A/H TEMP(C): 0 DOD(%): 17 MISSION ORBIT
Vavg Vmax Vmin
Voltage
1.60
1.50
1.40
1.30
1.20
1.10
1.00
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

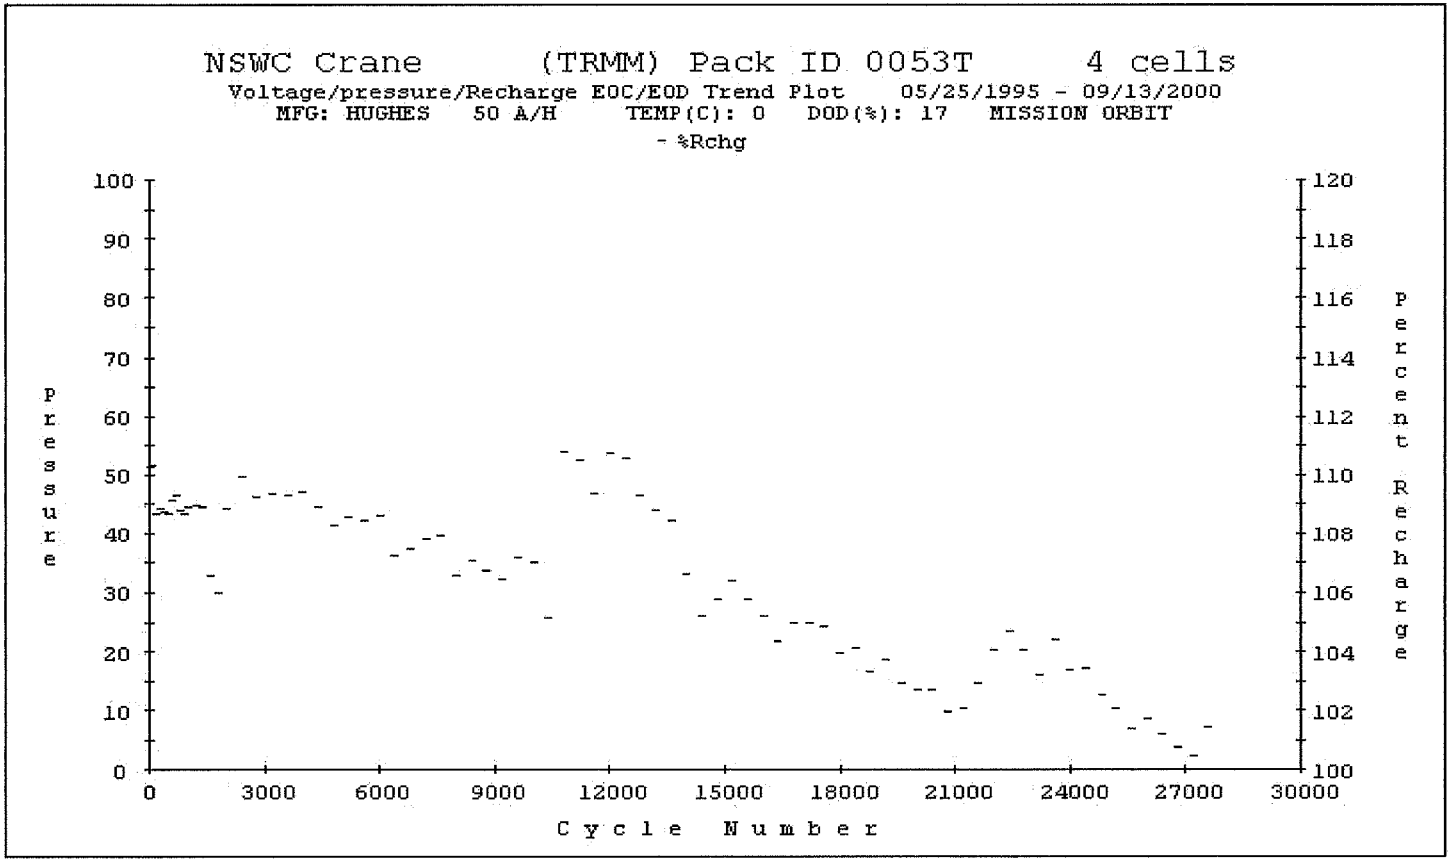
NSWC Crane (TRMM) Pack ID 0053T 4 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 05/25/1995 - 09/13/2000
MFG: HUGHES 50 A/H TEMP(C): 0 DOD(%): 17 MISSION ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

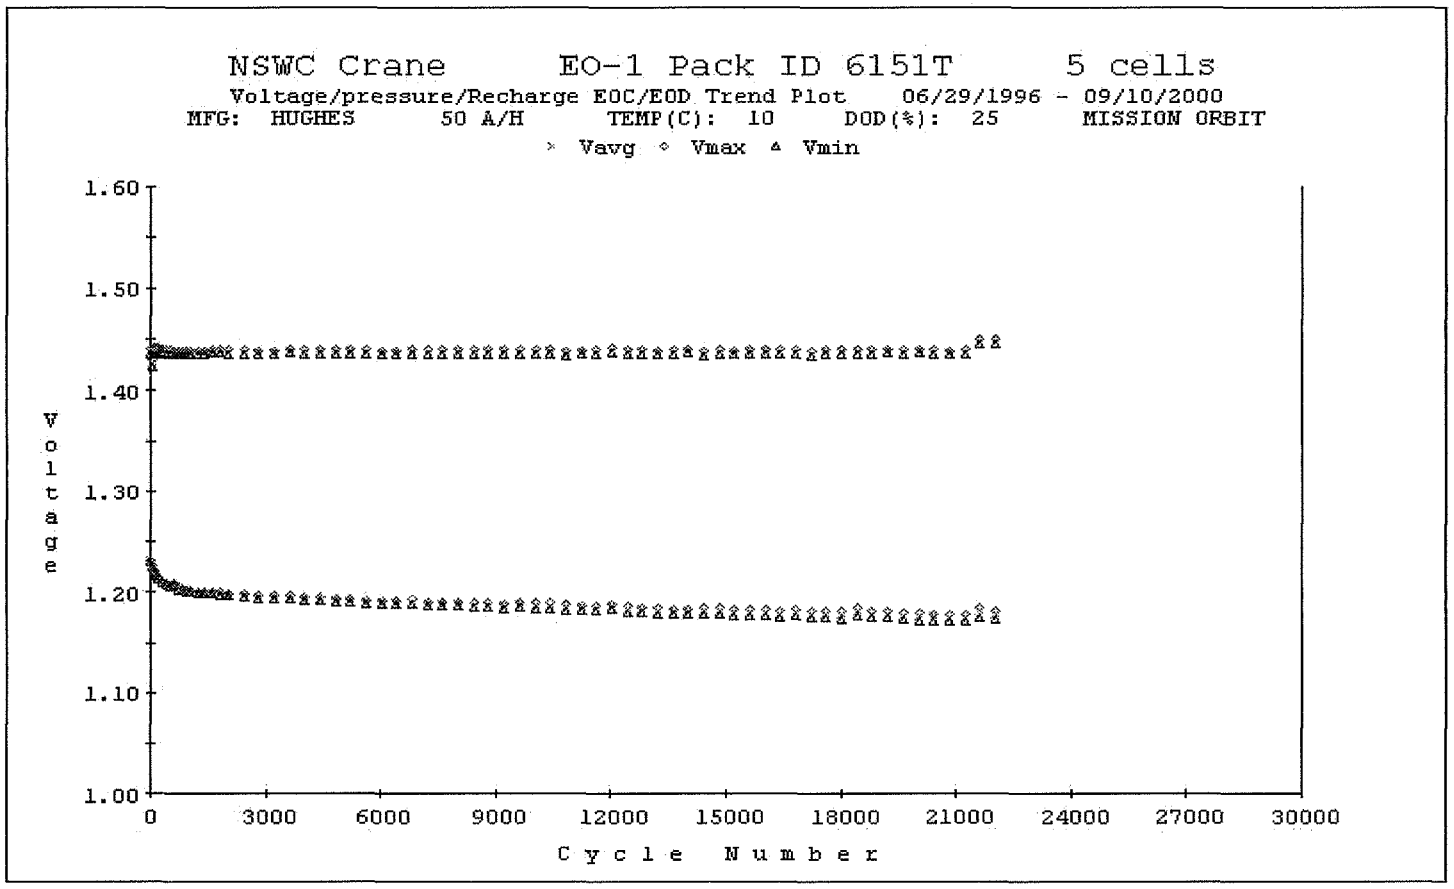
NSWC Crane EO-1 Pack ID 6151T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/29/1996 - 09/10/2000
MFG: HUGHES 50 A/H TEMP(C): 10 DOD(%): 25 MISSION ORBIT
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

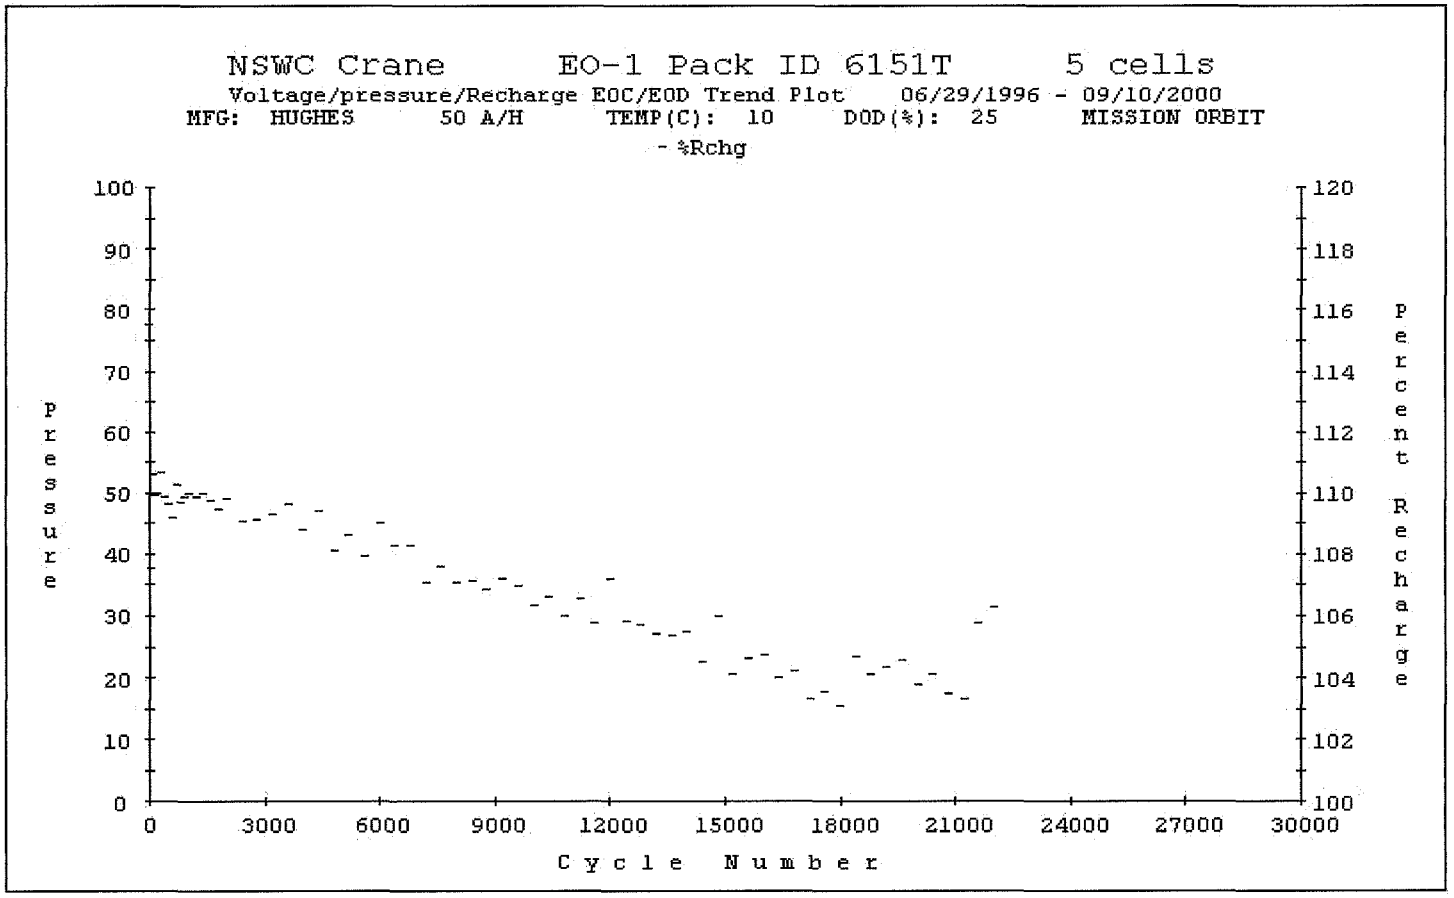
NSWC Crane EO-1 Pack ID 6151T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/29/1996 - 09/10/2000
MFG: HUGHES 50 A/H TEMP(C): 10 DOD(%): 25 MISSION ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

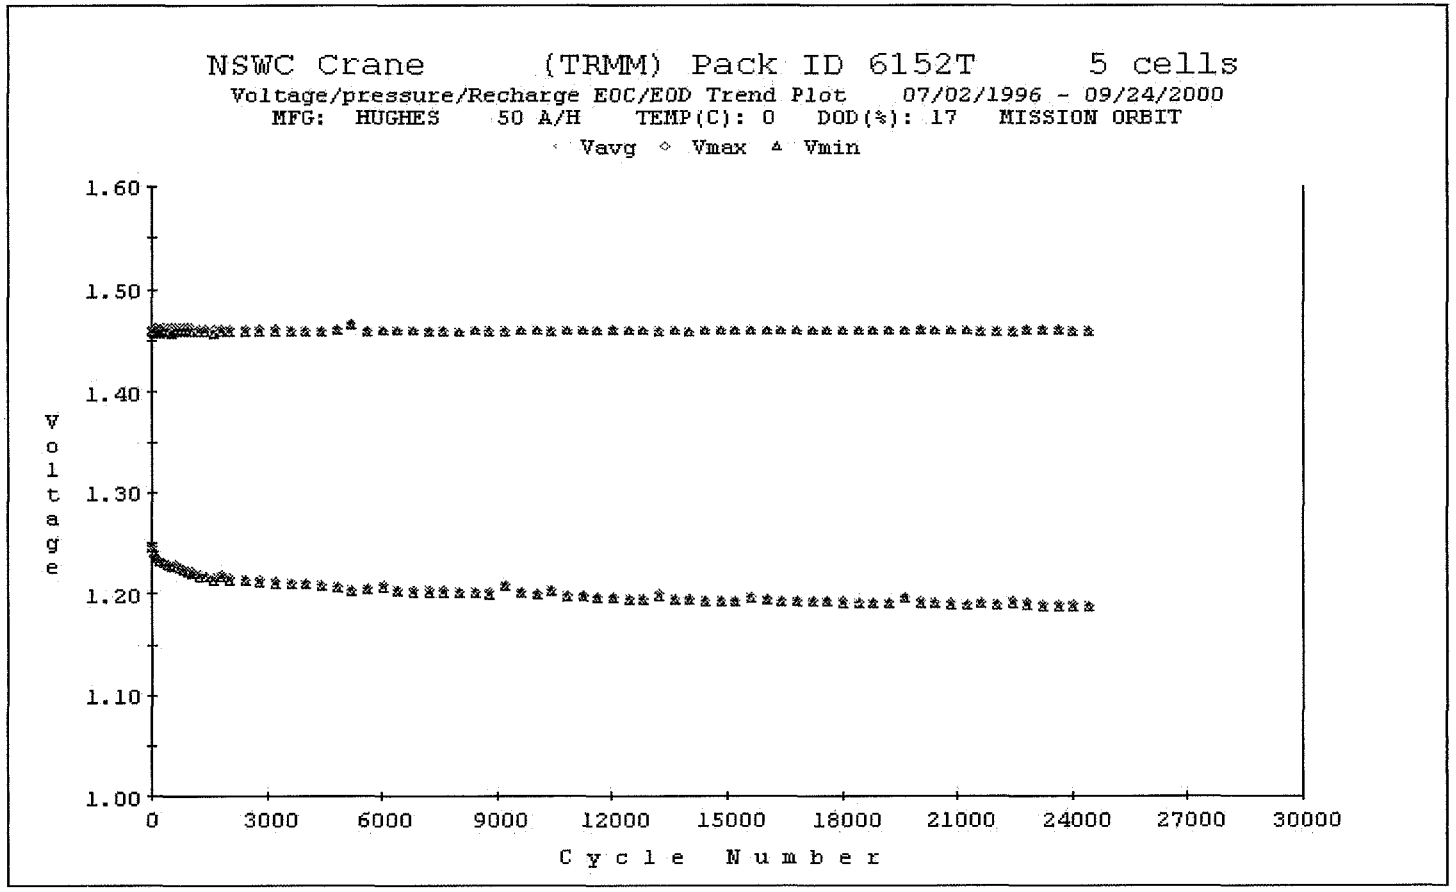
NSWC Crane (TRMM) Pack ID 6152T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 07/02/1996 - 09/24/2000
MFG: HUGHES 50 A/H TEMP(C): 0 DOD(%): 17 MISSION ORBIT
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

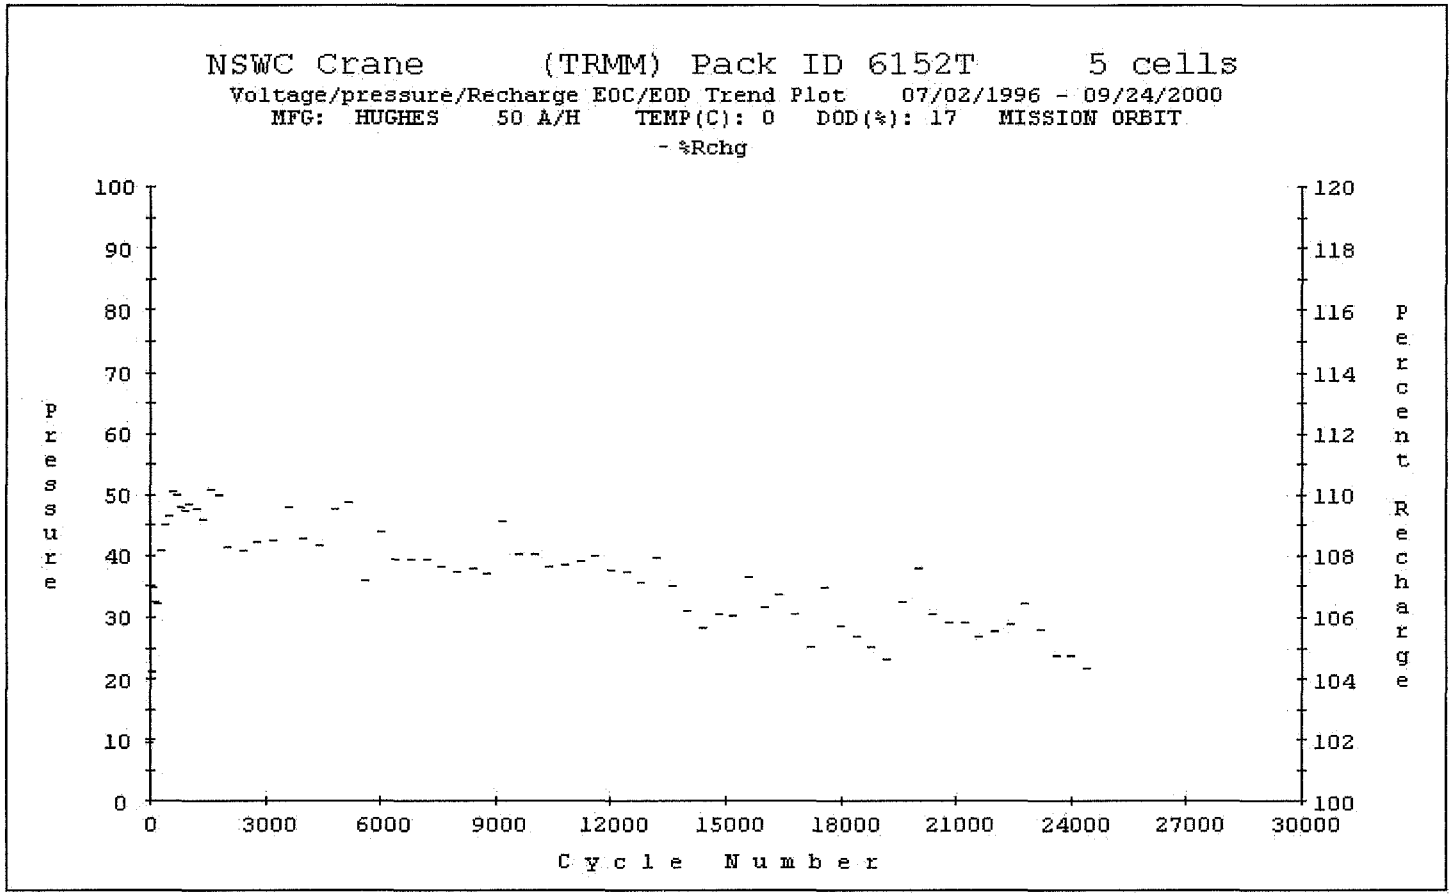
NSWC Crane (TRMM) Pack ID 6152T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 07/02/1996 - 09/24/2000
MFG: HUGHES 50 A/H TEMP(C): 0 DOD(%): 17 MISSION ORBIT
- %Rchg
Pressure
Percent Recharge
Cycle Number
0
10
20
30
40
50
60
70
80
90
100
100
102
104
106
108
110
112
114
116
118
120
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

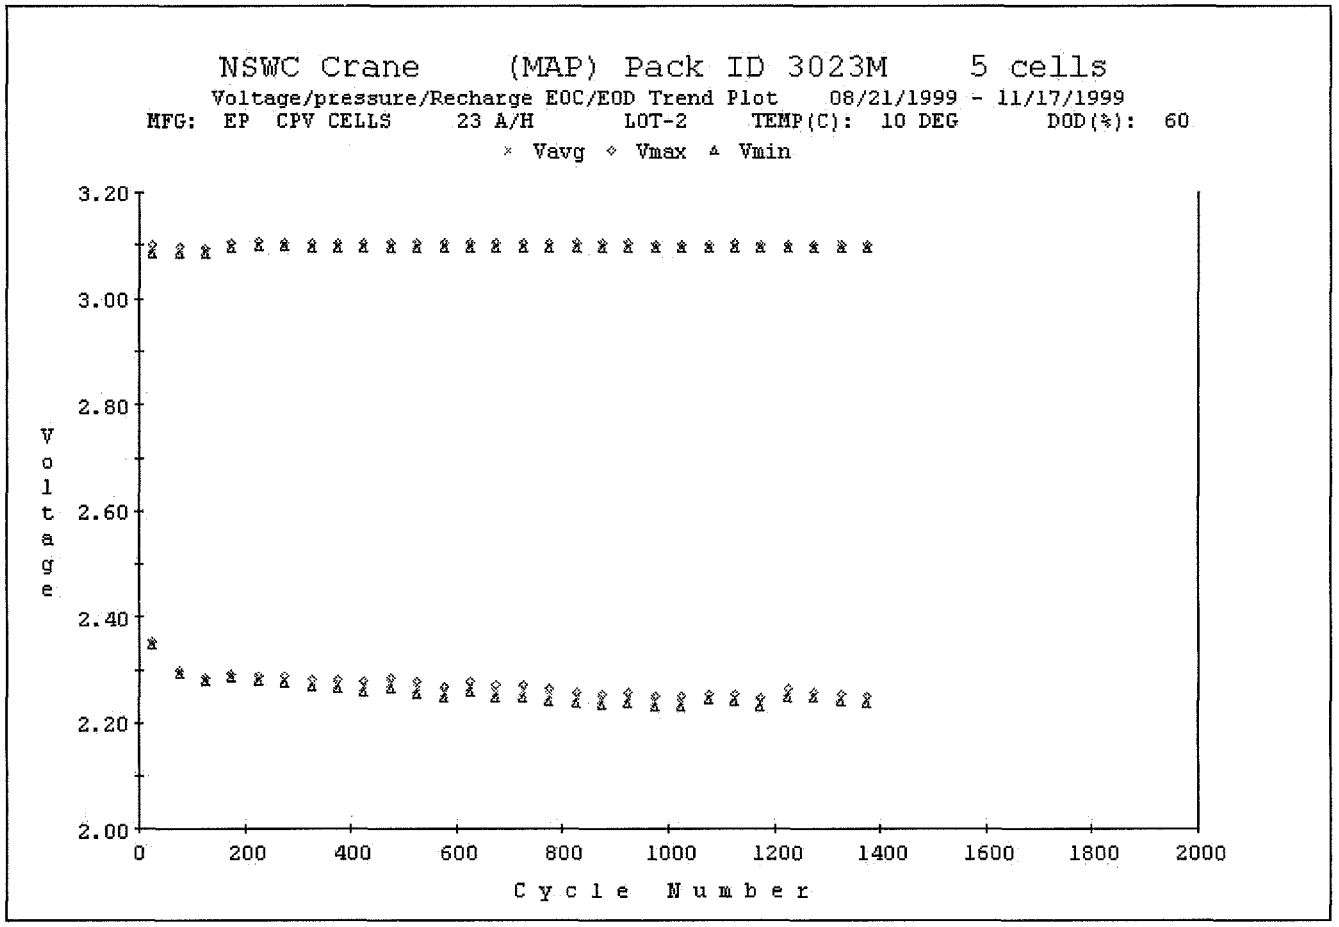
NSWC Crane (MAP) Pack ID 3023M 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 08/21/1999 - 11/17/1999
MFG: EP CPV CELLS 23 A/H LOT-2 TEMP(C): 10 DEG DOD(%): 60
× Vavg ◇ Vmax △ Vmin
Voltage
3.20
3.00
2.80
2.60
2.40
2.20
2.00
0
200
400
600
800
1000
1200
1400
1600
1800
2000
Cycle Number

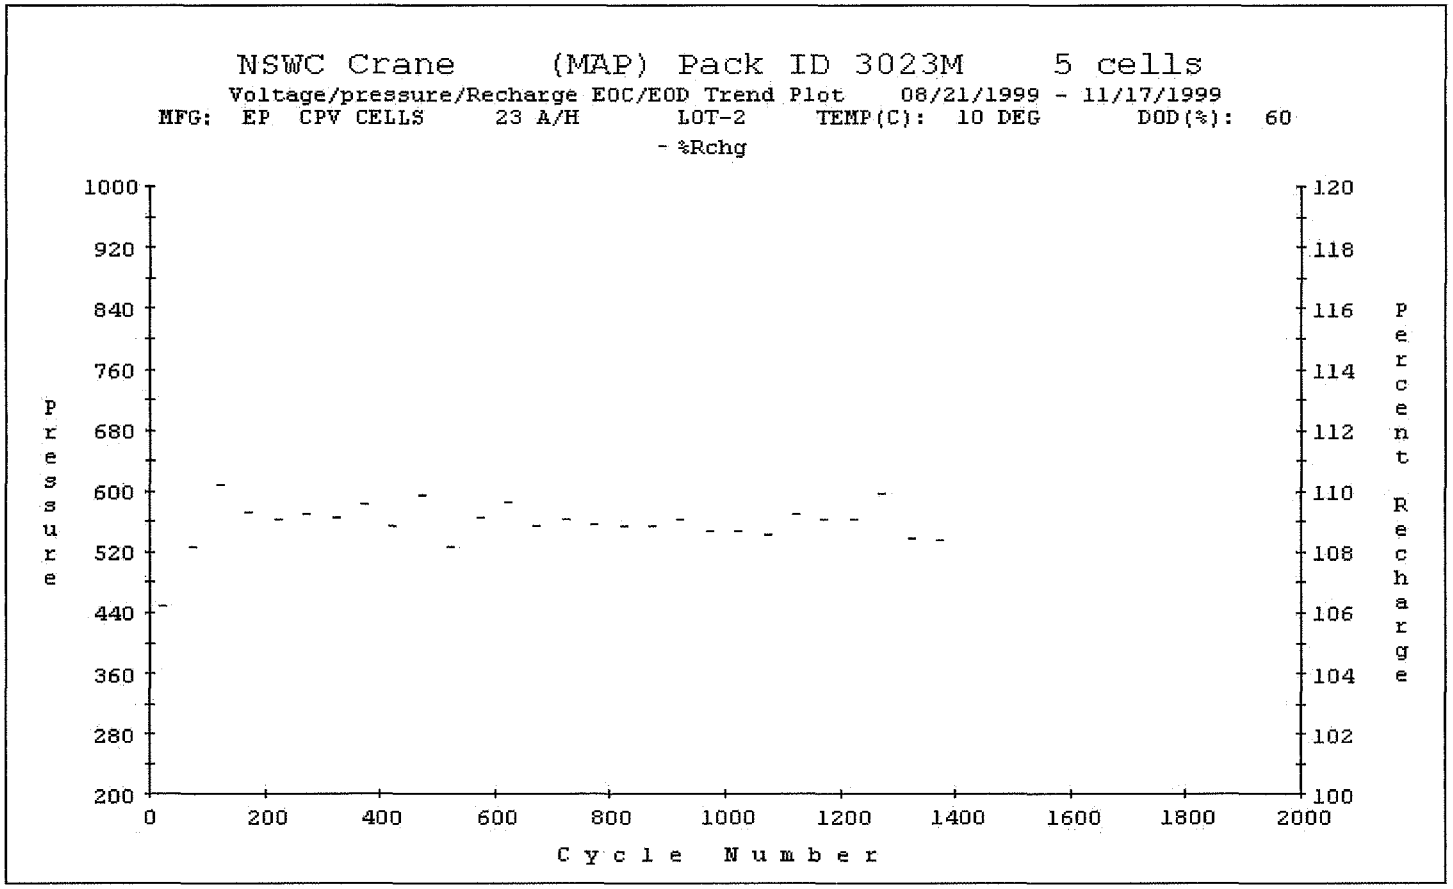
NSWC Crane (MAP) Pack ID 3023M 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 08/21/1999 - 11/17/1999
MFG: EP CPV CELLS 23 A/H LOT-2 TEMP(C): 10 DEG DOD(%): 60
- %Rchg
Pressure
1000
920
840
760
680
600
520
440
360
280
200
Percent Recharge
120
118
116
114
112
110
108
106
104
102
100
0
200
400
600
800
1000
1200
1400
1600
1800
2000
Cycle Number

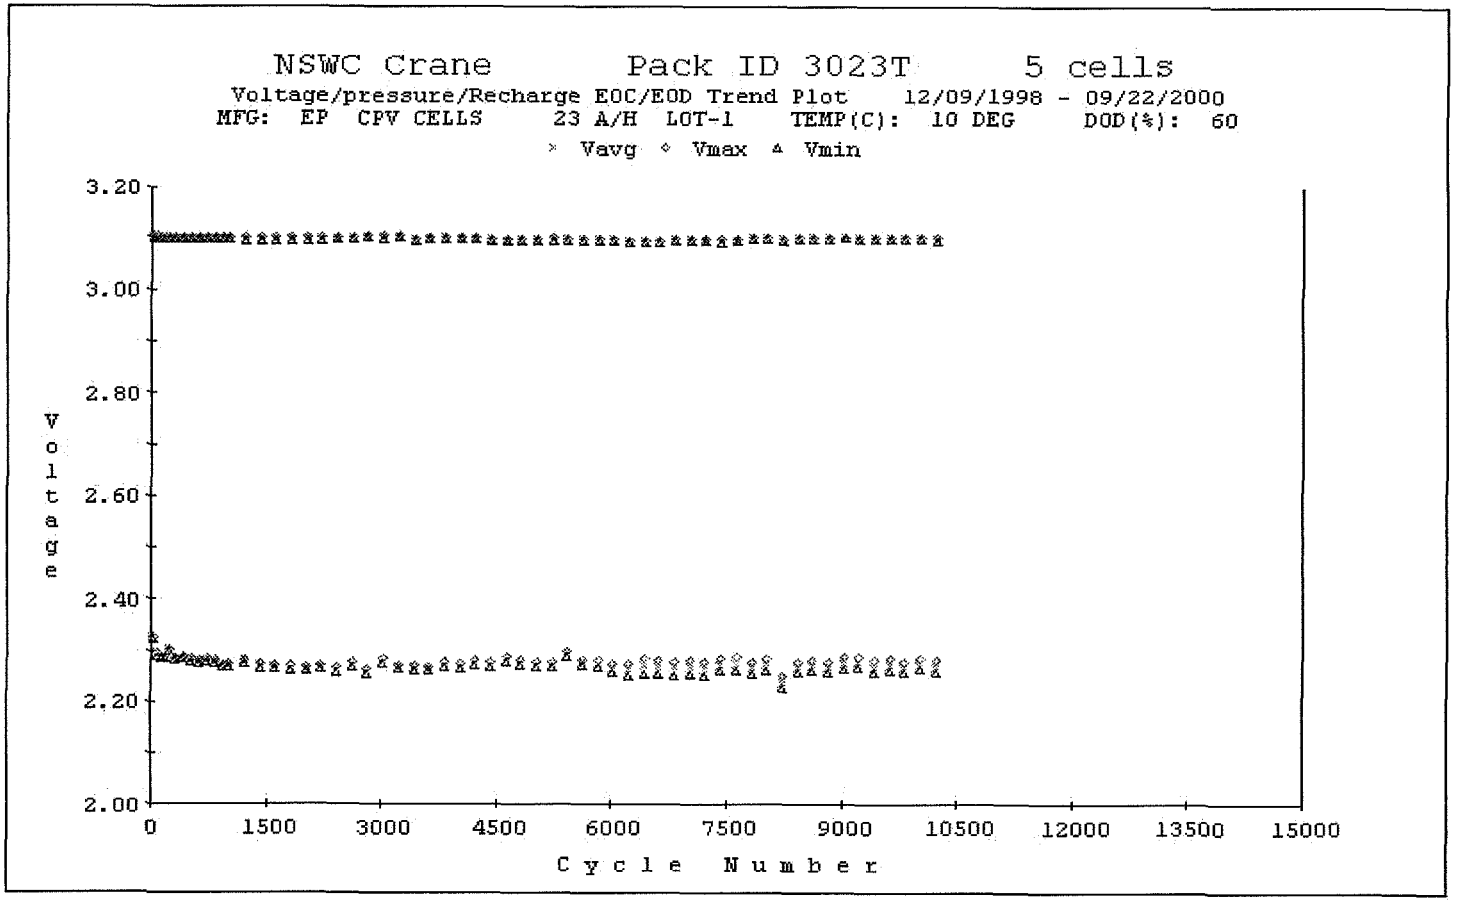
NSWC Crane Pack ID 3023T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 12/09/1998 - 09/22/2000
MFG: EP CPV CELLS 23 A/H LOT-1 TEMP(C): 10 DEG DOD(%): 60
Vavg Vmax Vmin
3.20
3.00
2.80
2.60
2.40
2.20
2.00
Voltage
0
1500
3000
4500
6000
7500
9000
10500
12000
13500
15000
Cycle Number

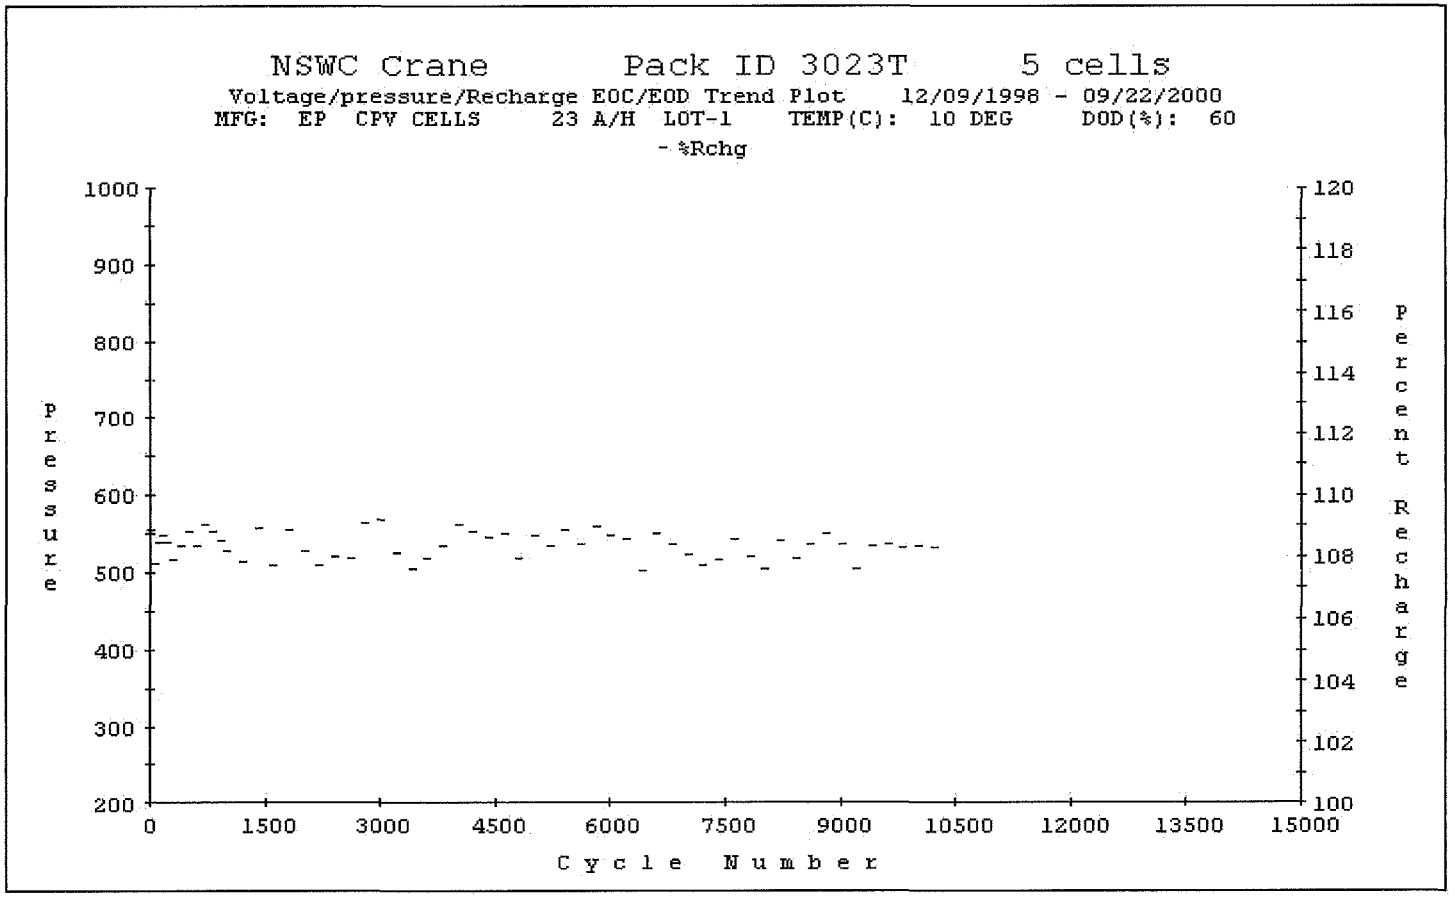
NSWC Crane Pack ID 3023T 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 12/09/1998 - 09/22/2000
MFG: EP CPV CELLS 23 A/H LOT-1 TEMP(C): 10 DEG DOD(%): 60
- %Rchg
Pressure
1000
900
800
700
600
500
400
300
200
Percent Recharge
120
118
116
114
112
110
108
106
104
102
100
0
1500
3000
4500
6000
7500
9000
10500
12000
13500
15000
Cycle Number

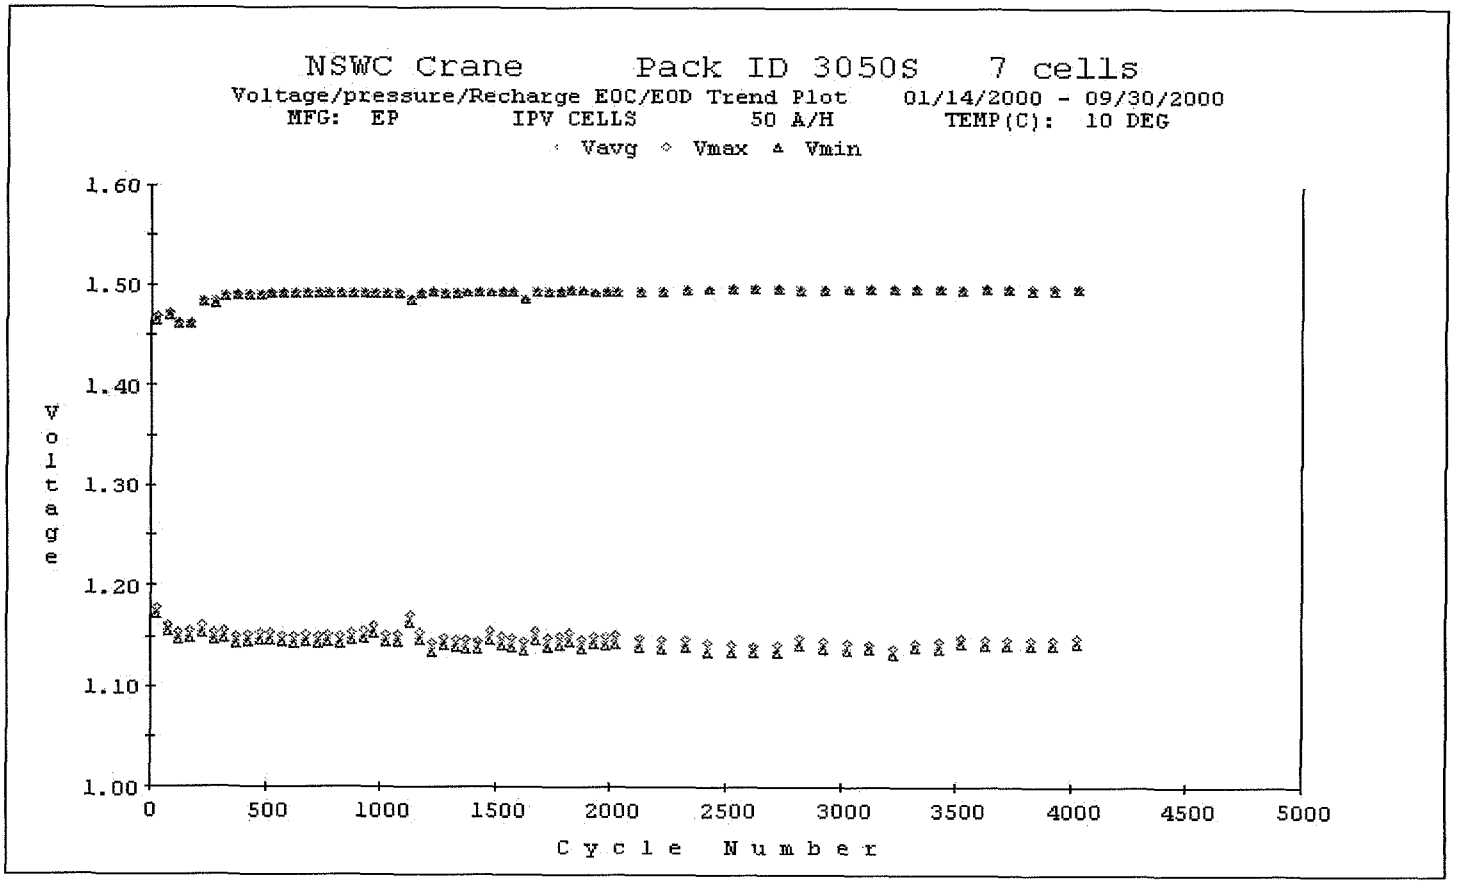
NSWC Crane Pack ID 3050S 7 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 01/14/2000 - 09/30/2000
MFG: EP IPV CELLS 50 A/H TEMP(C): 10 DEG
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
500
1000
1500
2000
2500
3000
3500
4000
4500
5000
Cycle Number

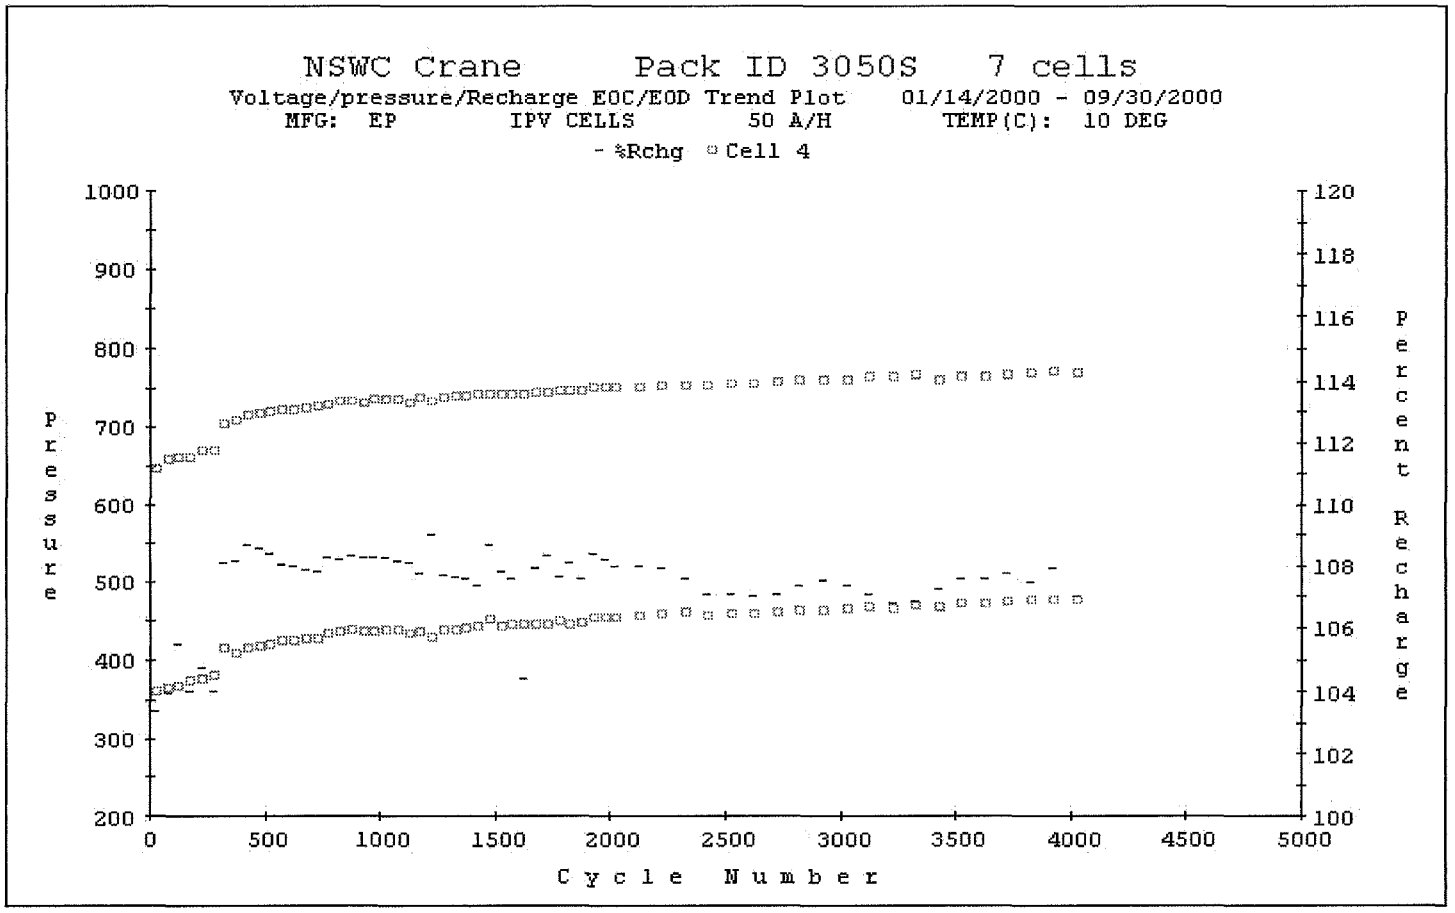
NSWC Crane Pack ID 3050S 7 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 01/14/2000 - 09/30/2000
MFG: EP IPV CELLS 50 A/H TEMP(C): 10 DEG
- %Rchg Cell 4
Pressure
Percent Recharge
Cycle Number
1000
900
800
700
600
500
400
300
200
120
118
116
114
112
110
108
106
104
102
100
0
500
1000
1500
2000
2500
3000
3500
4000
4500
5000

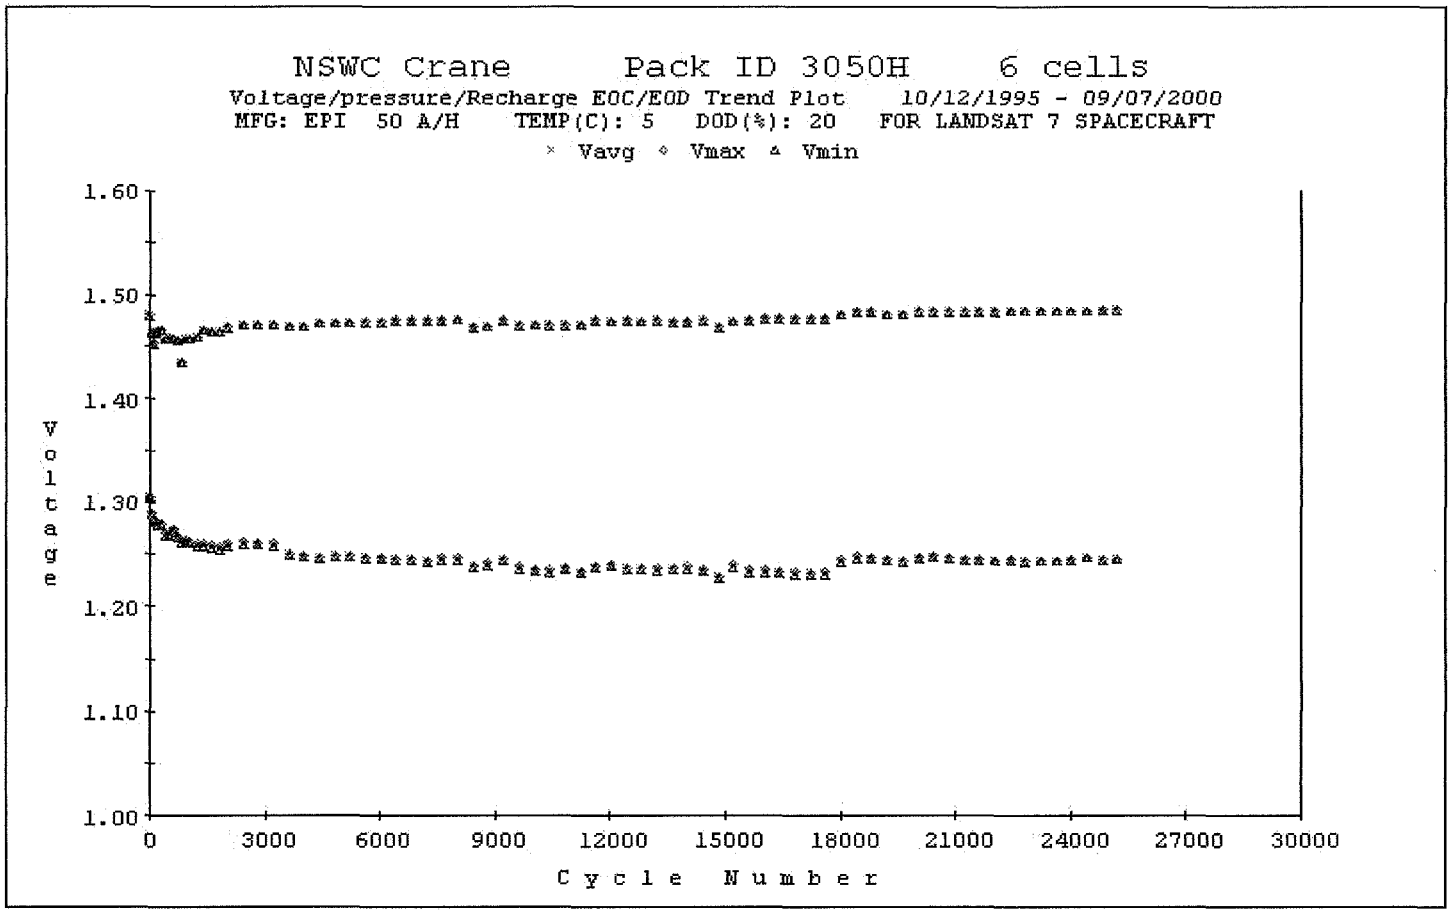
NSWC Crane Pack ID 3050H 6 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 10/12/1995 - 09/07/2000
MFG: EPI 50 A/H TEMP(C): 5 DOD(%): 20 FOR LANDSAT 7 SPACECRAFT
× Vavg ◇ Vmax △ Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000
Cycle Number

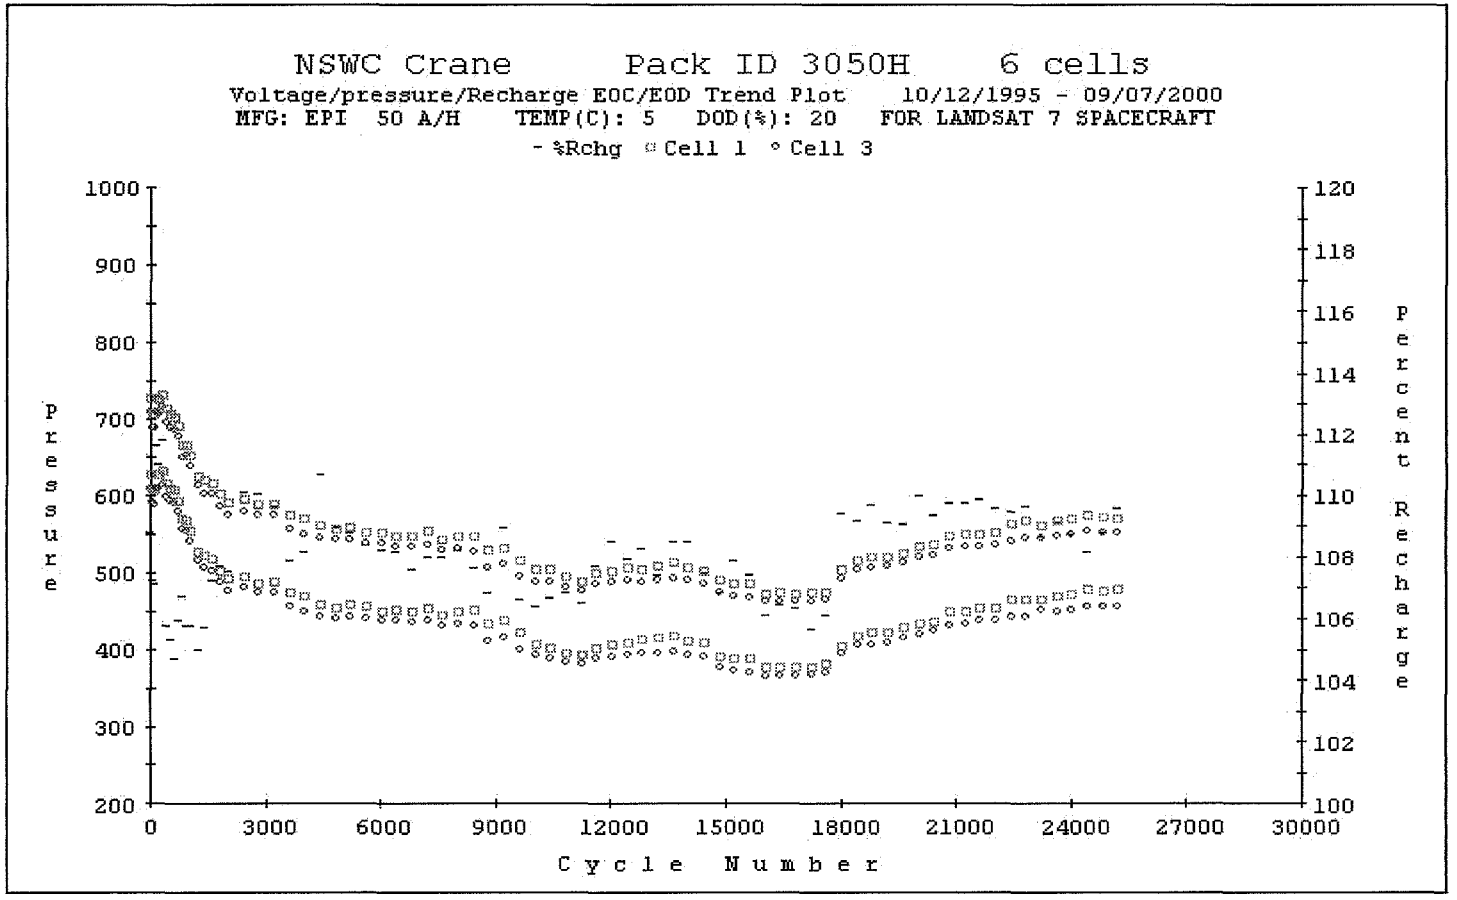
NSWC Crane Pack ID 3050H 6 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 10/12/1995 - 09/07/2000
MFG: EPI 50 A/H TEMP(C): 5 DOD(%): 20 FOR LANDSAT 7 SPACECRAFT
- %Rchg Cell 1 Cell 3
Pressure
Percent Recharge
Cycle Number
1000
900
800
700
600
500
400
300
200
120
118
116
114
112
110
108
106
104
102
100
0
3000
6000
9000
12000
15000
18000
21000
24000
27000
30000

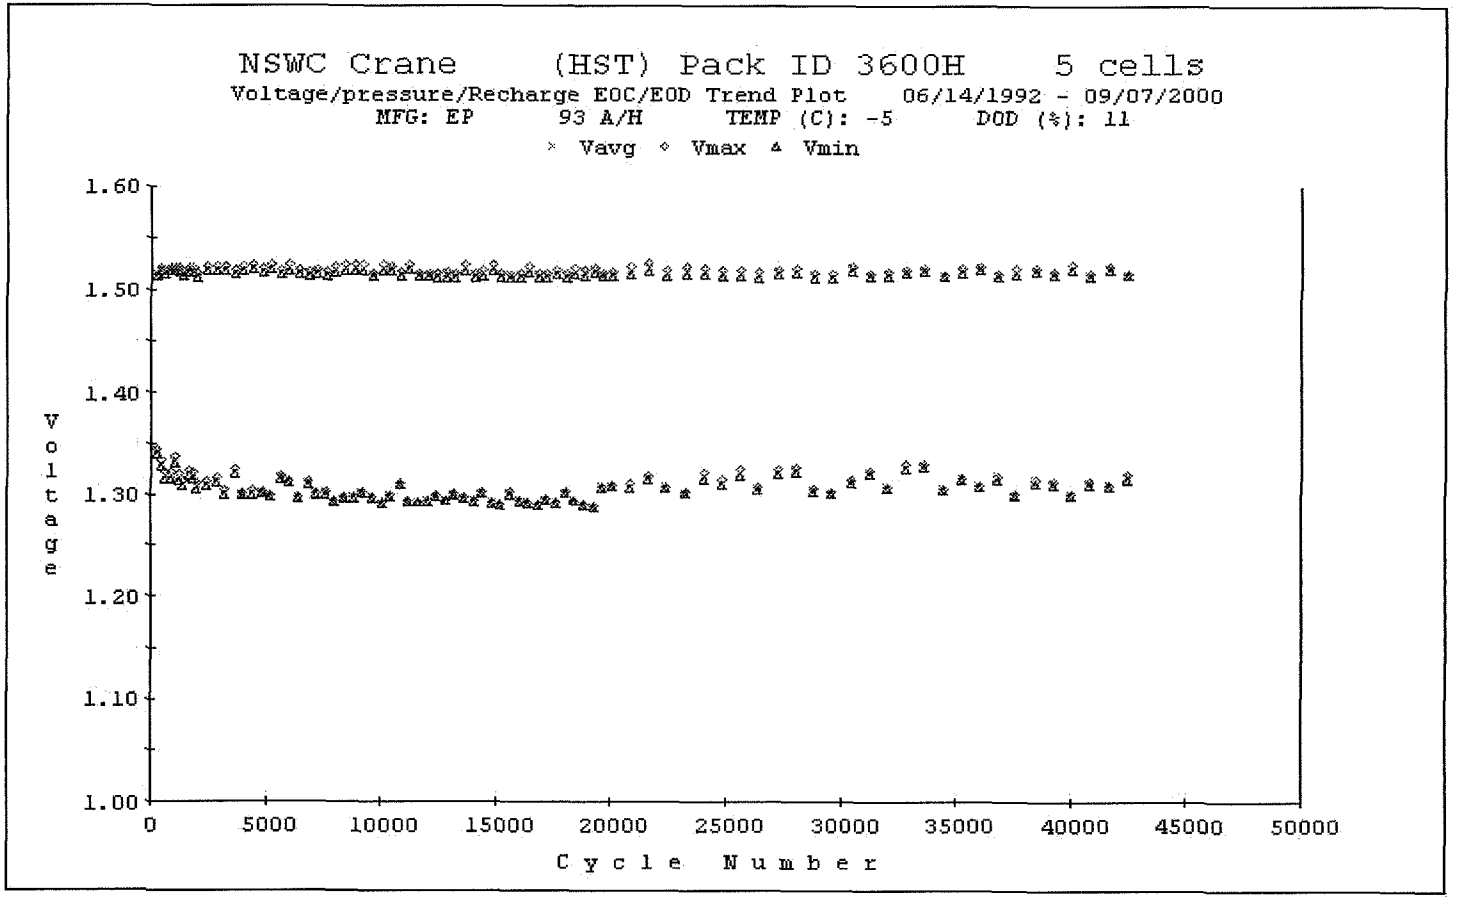
NSWC Crane (HST) Pack ID 3600H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/14/1992 - 09/07/2000
MFG: EP 93 A/H TEMP (C): -5 DOD (%): 11
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
5000
10000
15000
20000
25000
30000
35000
40000
45000
50000
Cycle Number

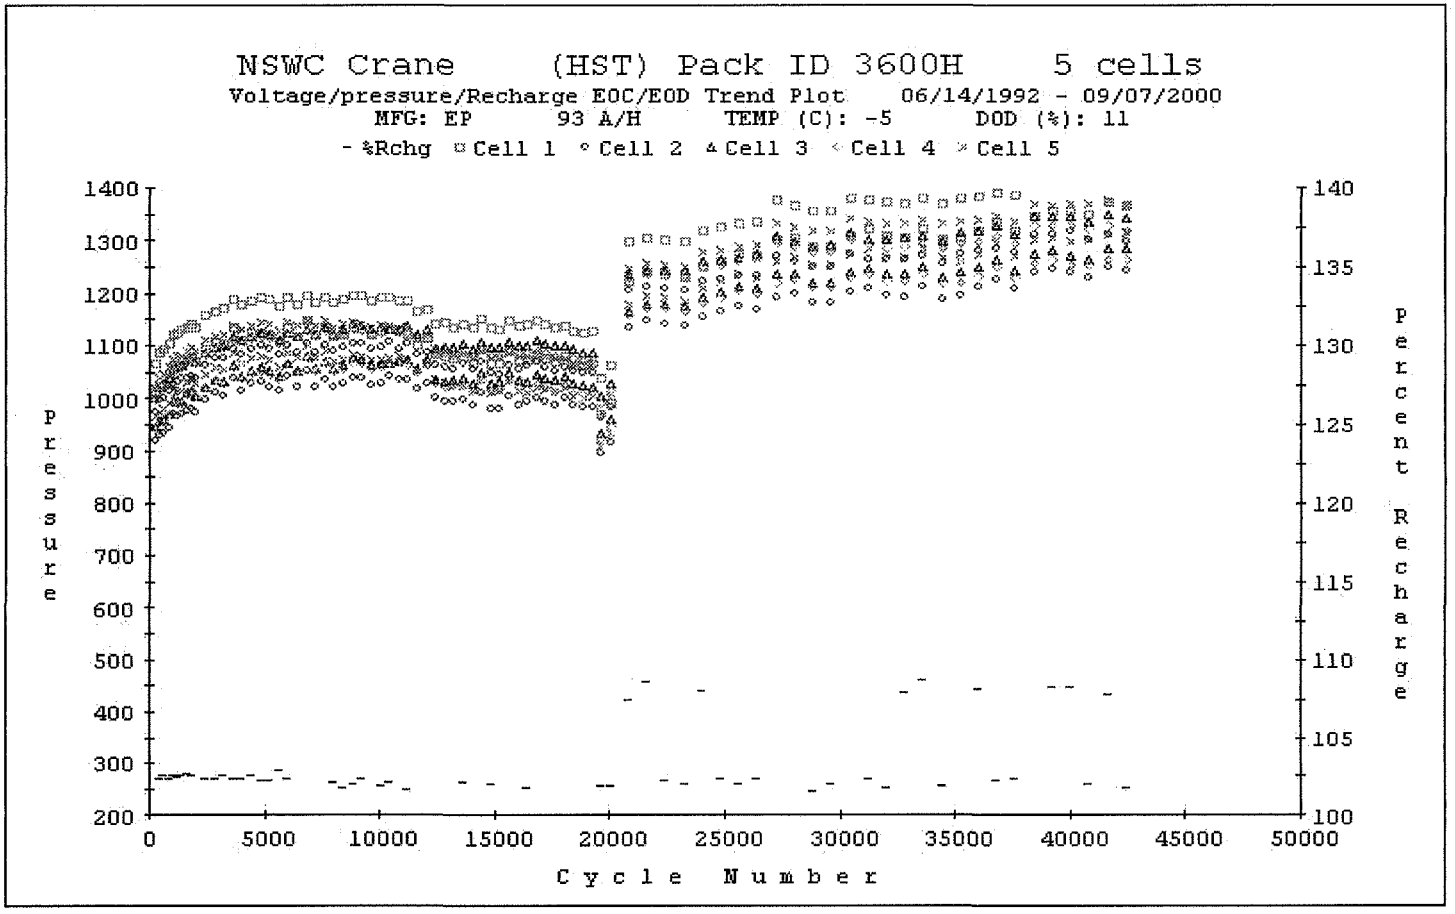
NSWC Crane (HST) Pack ID 3600H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/14/1992 - 09/07/2000
MFG: EP 93 A/H TEMP (C): -5 DOD (%): 11
- %Rchg Cell 1 Cell 2 Cell 3 Cell 4 Cell 5
Pressure
Percent Recharge
Cycle Number
1400
1300
1200
1100
1000
900
800
700
600
500
400
300
200
140
135
130
125
120
115
110
105
100
0
5000
10000
15000
20000
25000
30000
35000
40000
45000
50000

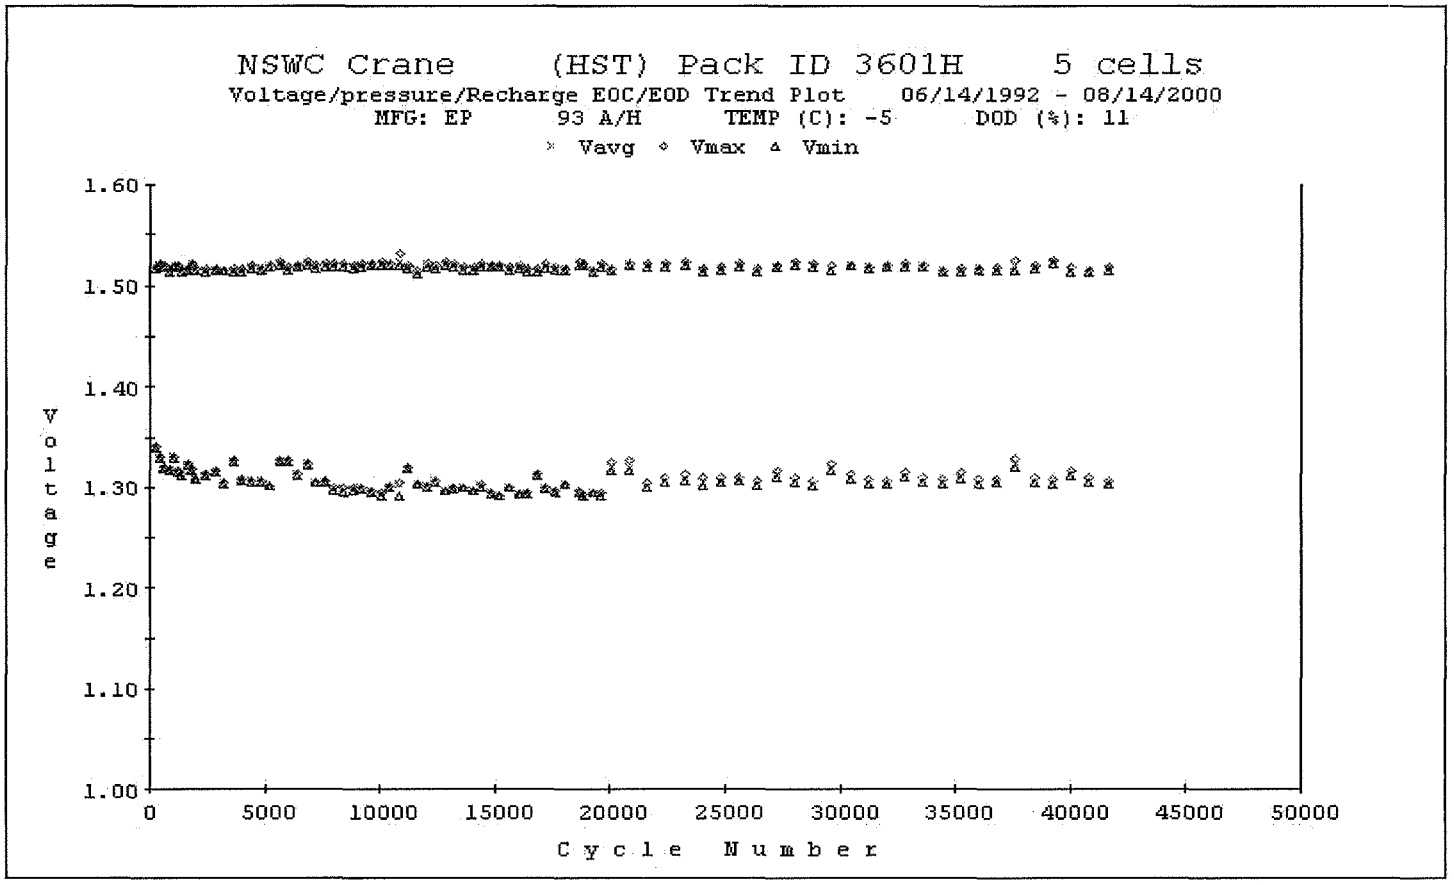
NSWC Crane (HST) Pack ID 3601H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/14/1992 - 08/14/2000
MFG: EP 93 A/H TEMP (C): -5 DOD (%): 11
Vavg Vmax Vmin
1.60
1.50
1.40
1.30
1.20
1.10
1.00
Voltage
0
5000
10000
15000
20000
25000
30000
35000
40000
45000
50000
Cycle Number

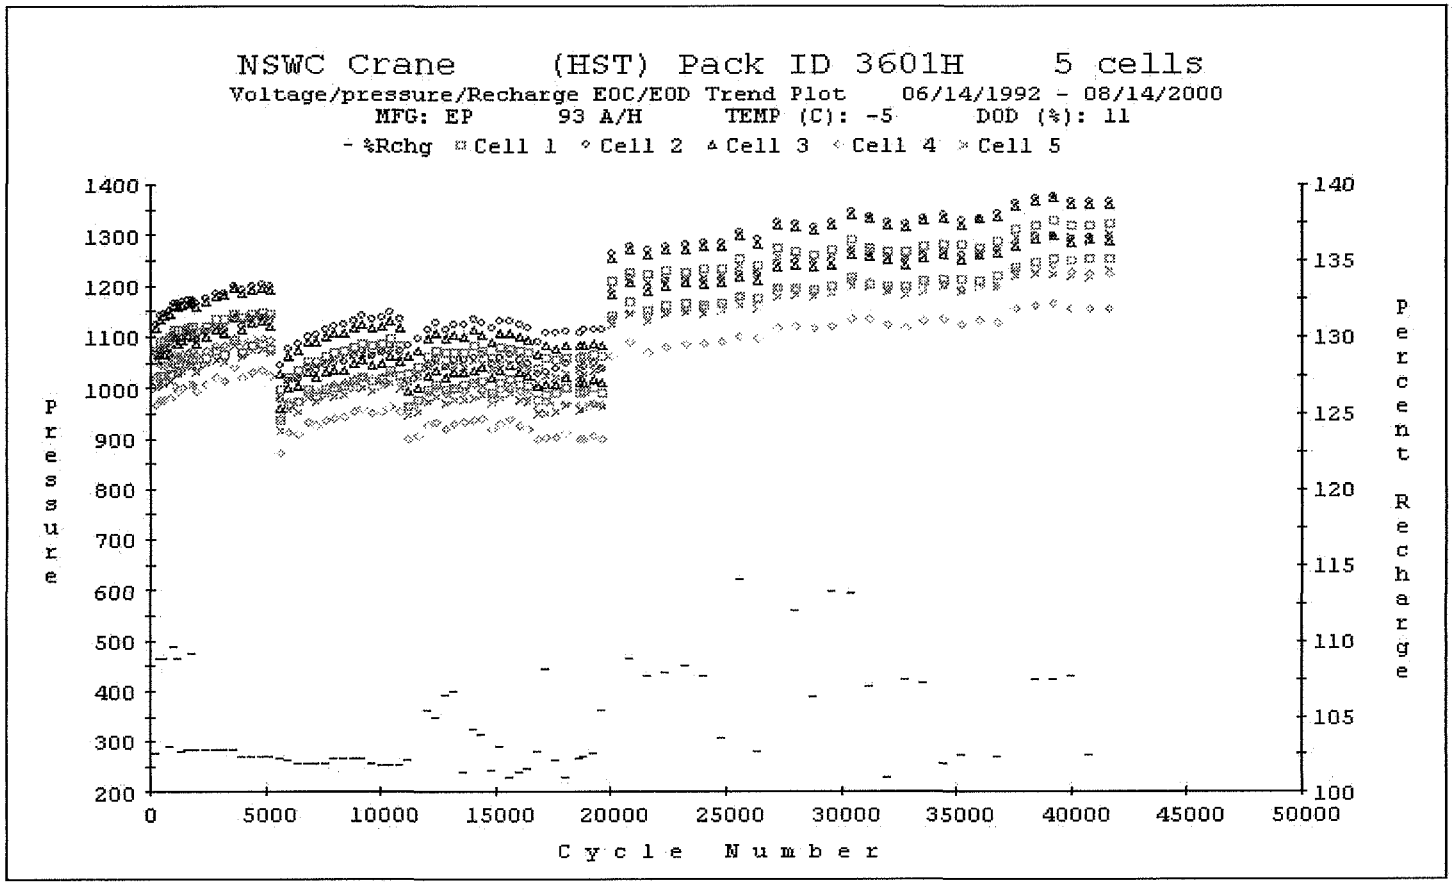
NSWC Crane (HST) Pack ID 3601H 5 cells
Voltage/pressure/Recharge EOC/EOD Trend Plot 06/14/1992 - 08/14/2000
MFG: EP 93 A/H TEMP (C): -5 DOD (%): 11
%Rchg Cell 1 Cell 2 Cell 3 Cell 4 Cell 5
Pressure
Percent Recharge
Cycle Number
1400
1300
1200
1100
1000
900
800
700
600
500
400
300
200
140
135
130
125
120
115
110
105
100
0
5000
10000
15000
20000
25000
30000
35000
40000
45000
50000

SUMMARY

- Quality EPT Ni-H2, EPT Super NiCd and SAFT NiCd cells have been demonstrated for Aerospace applications
- The data has been provided to NASA Centers and other Agencies for their use and application
  - Developed plan and used in NASA in-orbit battery management.
- Database on rechargeable cell/batteries is now available for customer use.

EAGLE PICHER
Eagle-Picher Technologies, LLC



Large Capacity Single Pressure Vessel (SPV) Battery Development

Jeff Dermott

Jack Brill

Eagle-Picher Technologies, LLC

Joplin, Missouri

513/ep 1/N 1/44

20011178 09
2093
538036

EAGLE PICHER
Eagle-Picher Technologies, LLC



Single Pressure Vessel (SPV) Background

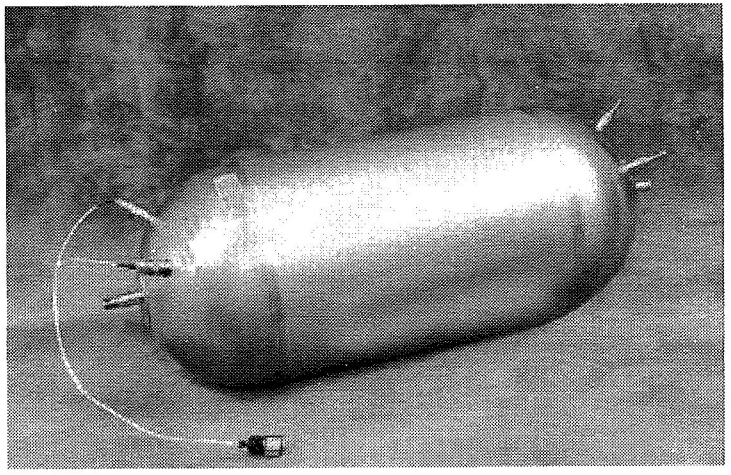

- Originally Developed for the Iridium® Program
- 104 Batteries Produced
- 92 Batteries Launched
- Flights Included Batteries Having Capacities of 50 Ah and 60 Ah
  - Iridium®, Ikonos, STEX
  - 50 Ah --- 24 Flights
  - 60 Ah --- 68 Flights

EAGLE PICHER
Eagle-Picher Technologies, LLC

Single Pressure Vessel (SPV) Battery Characteristics

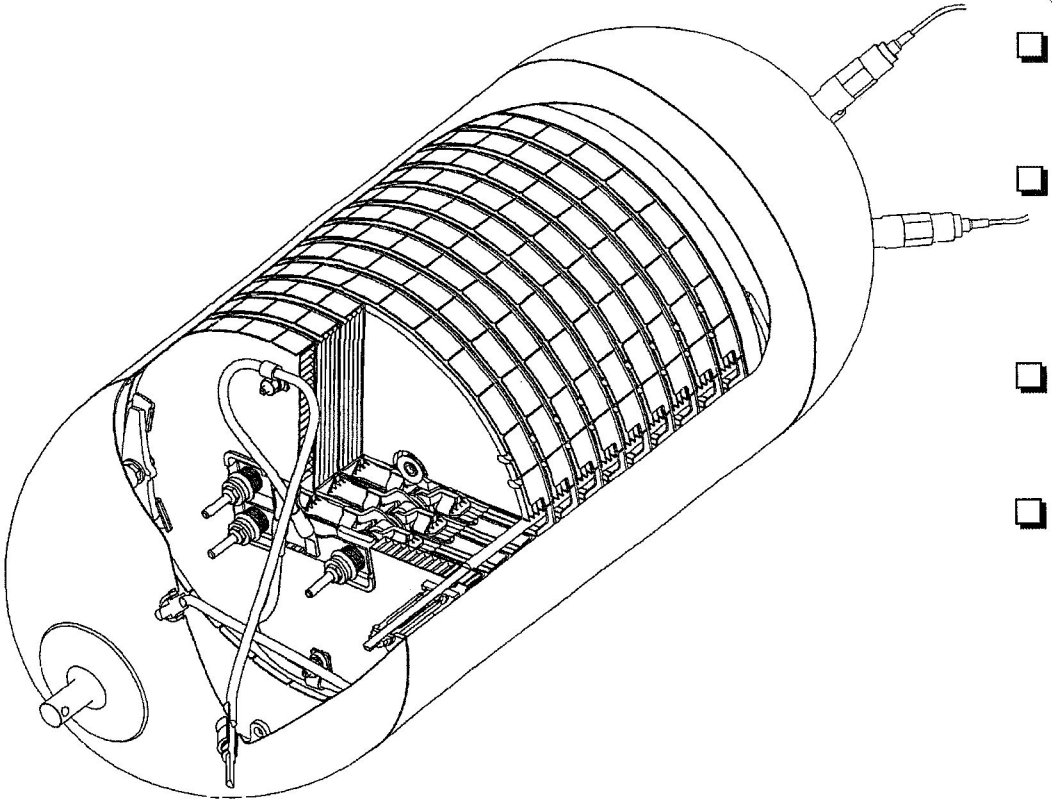

- All Cells in One Pressure Vessel
- Pressure Monitored by Two Transducers for Redundancy
- Heat Conducted by Ni-coated Al Plates
- Cell Terminals Connected by Mechanical Pressure

EAGLE PICHER
Eagle-Picher Technologies, LLC

SPV Design Heritage

- Qualified Batteries In the 10 inch Diameter Pressure Vessel:
  - 30 Ah --- SAR 10107
    - Length 19.44 inches
    - MEOP 400 psig
    - Weight 43 lbs
  - 50 Ah --- SAR 10065
    - Length 24.7 inches
    - MEOP 500 psig
    - Weight 67 lbs
  - 60 Ah --- SAR 10081
    - Length 25.2 inches
    - MEOP 640 psig
    - Weight 80 lbs

EAGLE PICHER
Eagle-Picher Technologies, LLC



Designs in Development

- Two Battery Designs in Development with 13 inch Diameter Pressure Vessels
- Scaled From the 10 Inch Designs
- Lessons Learned From 10 Inch SPV Applied to 13 Inch Diameter Battery Designs
- Cell Terminal/ECS Seal Design Modified Due to the Need for a Larger Current Conductor

EAGLE PICHER
Eagle-Picher Technologies, LLC



SPV Design Comparison

Modules Per Cell	Resulting 10" Design Capacity (AH)	Resulting 13" Design Capacity (AH)
3	30	N/E
4	40	80
5	50	100
6	60	120

- **30 Ah, 50 Ah, & 60 Ah 10" Battery Designs Proven by Flight Heritage.**
- **80 Ah & 120 Ah 13" Battery Designs Are Currently in Development.**

EAGLE PICHER
Eagle-Picher Technologies, LLC

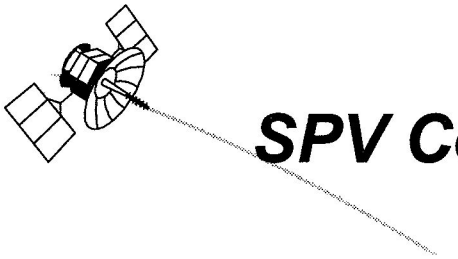

SPV Cell Design

- Same Cell Design As Was Used in 10" Design
- Dual Layer Electrolyte Containment System
- Microporous Vent Allows Gas to Flow, but Not Liquid

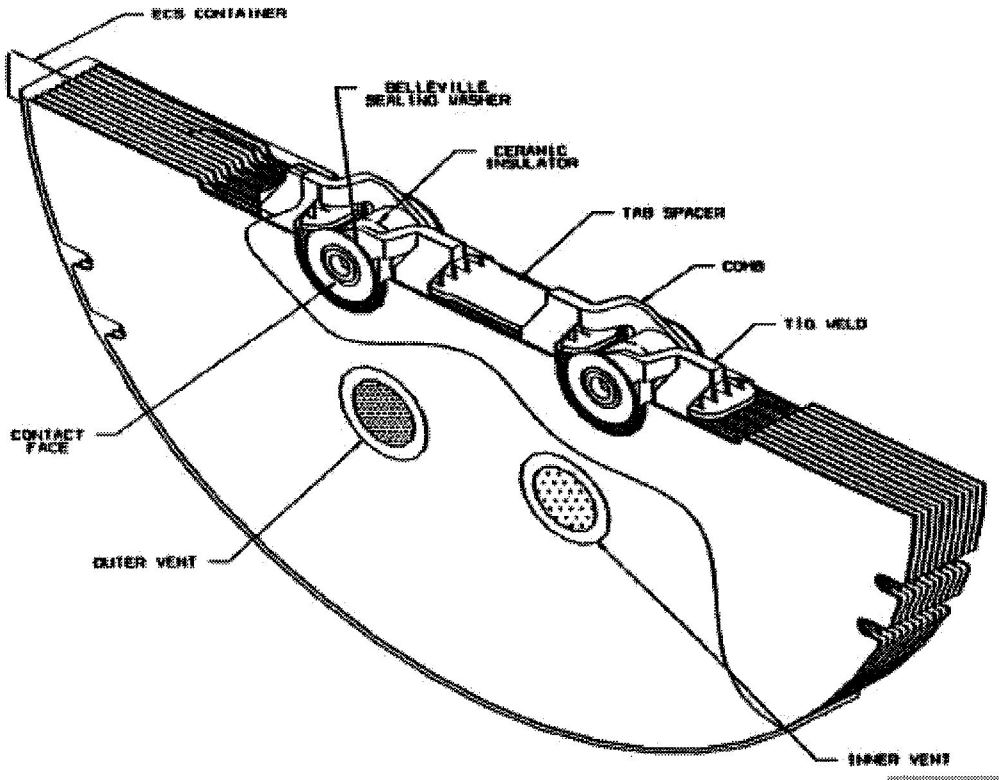

EAGLE PICHER
Eagle-Picher Technologies, LLC

SPV Module features

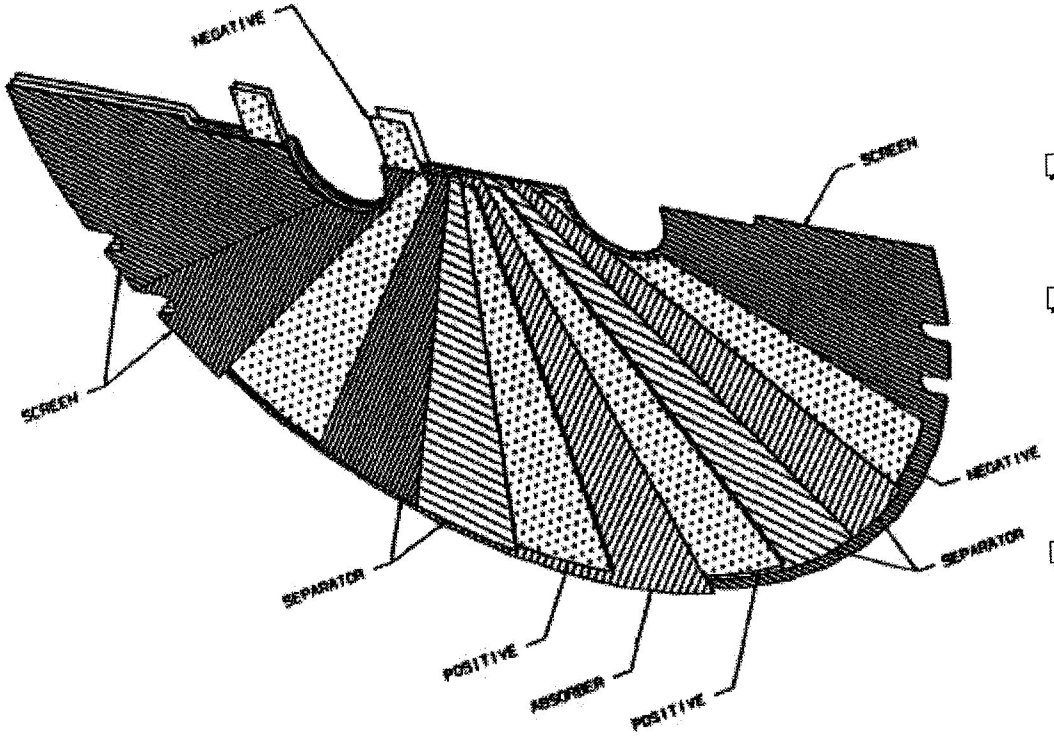

- "Half-Moon" Module Shape Identical to 10" Design
- Nickel Plaque Identical to Original 10" Design
- Two Tabs Per Electrode for Low Impedance and Redundancy
- Absorber Functions As an Electrolyte Reservoir

EAGLE PICHER
Eagle-Picher Technologies, LLC

SPV Pressure Vessel Characteristics

- Pressure Vessel Manufactured From Inconel 718 by the Same Processes Used in the 10" Design
- Boss and Trunion Welds Are LASER Welds
- Girth Weld Is LASER Weld by In-house System
- Pressure Vessel Qualified With Cycle-burst Sample in Same Manner As 10" Designs

EAGLE PICHER
Eagle-Picher Technologies, LLC

13" Battery Design Improvements

- Most Changes to SPV Design Are Necessary to Incorporate the Larger Electrode Size or Higher Current Rates.
- ECS-Comb Seal Redesign Completed and Verified Through Development Test
- Benefits of ECS-Comb Seal Redesign
  - Fewer Parts Necessary to Seal Simplifies Comb Seal
  - ECS Hermetically Sealed and Tested Prior to Battery Stack
  - Restacking Battery Will Not Automatically Require a Rebagging of Cells
  - Allows Larger Surface Area for Intercell Electrical Connections
  - Fewer Electrical Tie Rods Reduces Mass Associated With Electrical Connections

EAGLE PICHER
Eagle-Picher Technologies, LLC



SPV Battery Performance Similarities

- Battery Impedance Similar to That of the 10" Design (<35 mΩ) – Measured 21 mΩ
- Charge Retention Efficiency Is Same As 10" Design (85-90%) – Measured 87.5%
- Hydrogen Leak Rate Same as Level Experienced in 10"design (< 5 X 10^{-6} cc/sec)

EAGLE PICHER
Eagle-Picher Technologies, LLC

80 AH SPV Battery Design Summary

❑ Battery Type	SAR 10121
❑ Nominal Voltage (volts)	27.7
❑ Rated Capacity (Ah)	80
❑ Actual Capacity (Ah)	90.6
❑ Specific Energy (WHr/kg)	55.3
❑ Energy Density (WHr/liter)	70.9
❑ Weight (lb)	100
❑ Diameter (inches)	13.06
❑ Length (inches)	26.4
❑ MEOP (psig)	540

EAGLE PICHER
Eagle-Picher Technologies, LLC



C/10 Charge for SAR 10121

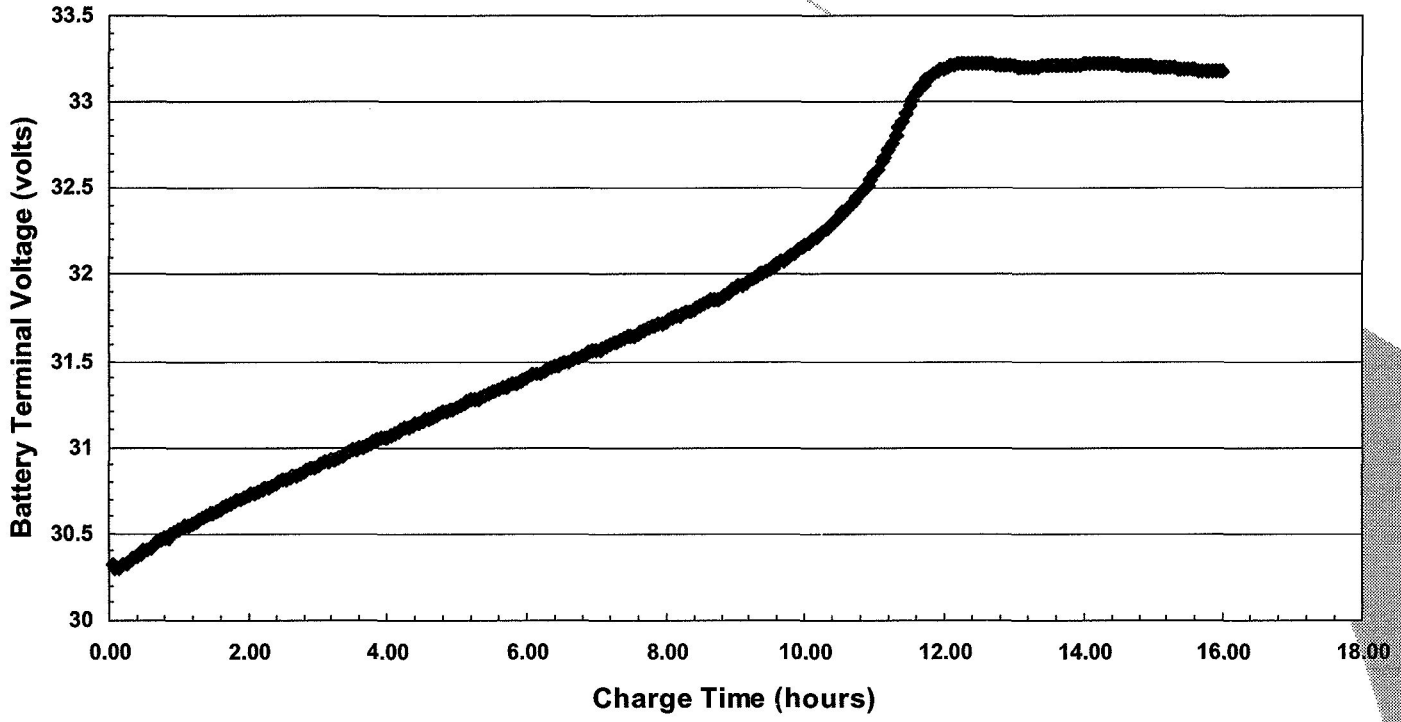

EAGLE PICHER
Eagle-Picher Technologies, LLC



C/2 Discharge for SAR 10121

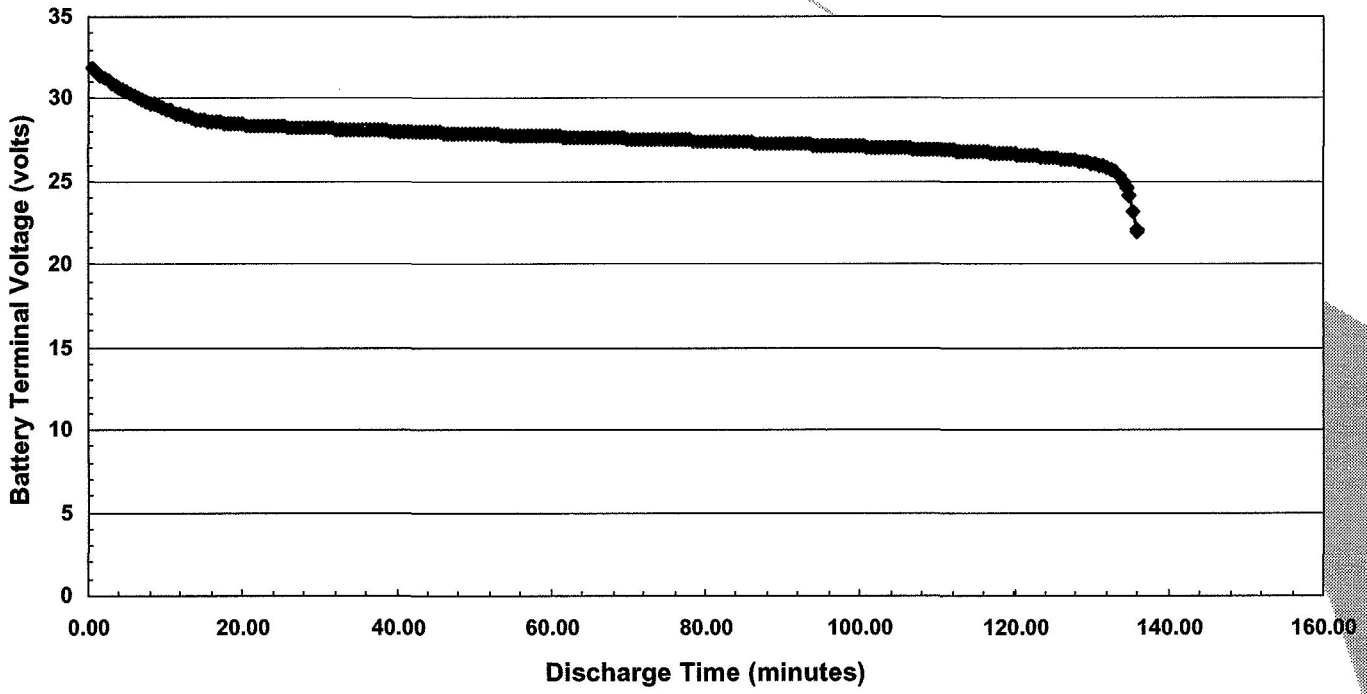

EAGLE PICHER
Eagle-Picher Technologies, LLC



C/2 Discharge for SAR 10121 After 72 Hr OCV

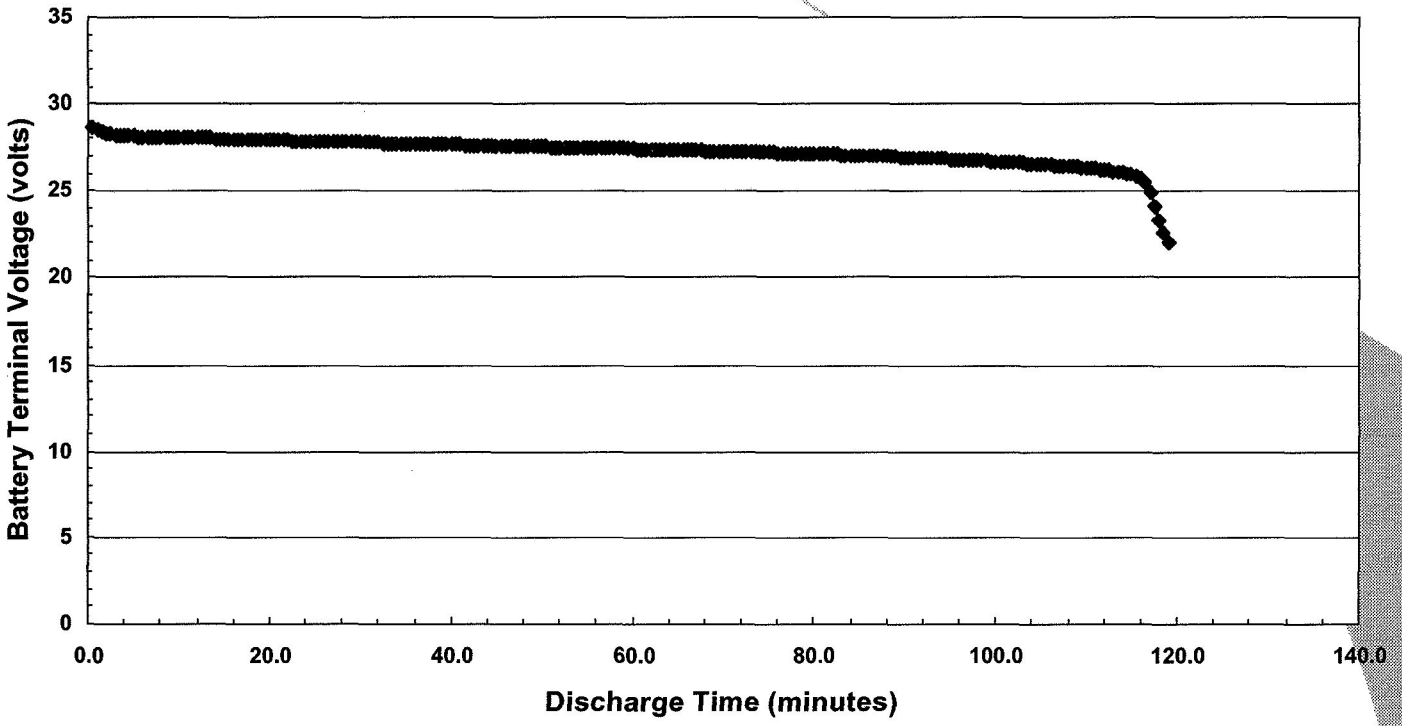

EAGLE PICHER
Eagle-Picher Technologies, LLC



Step Charge for SAR 10121

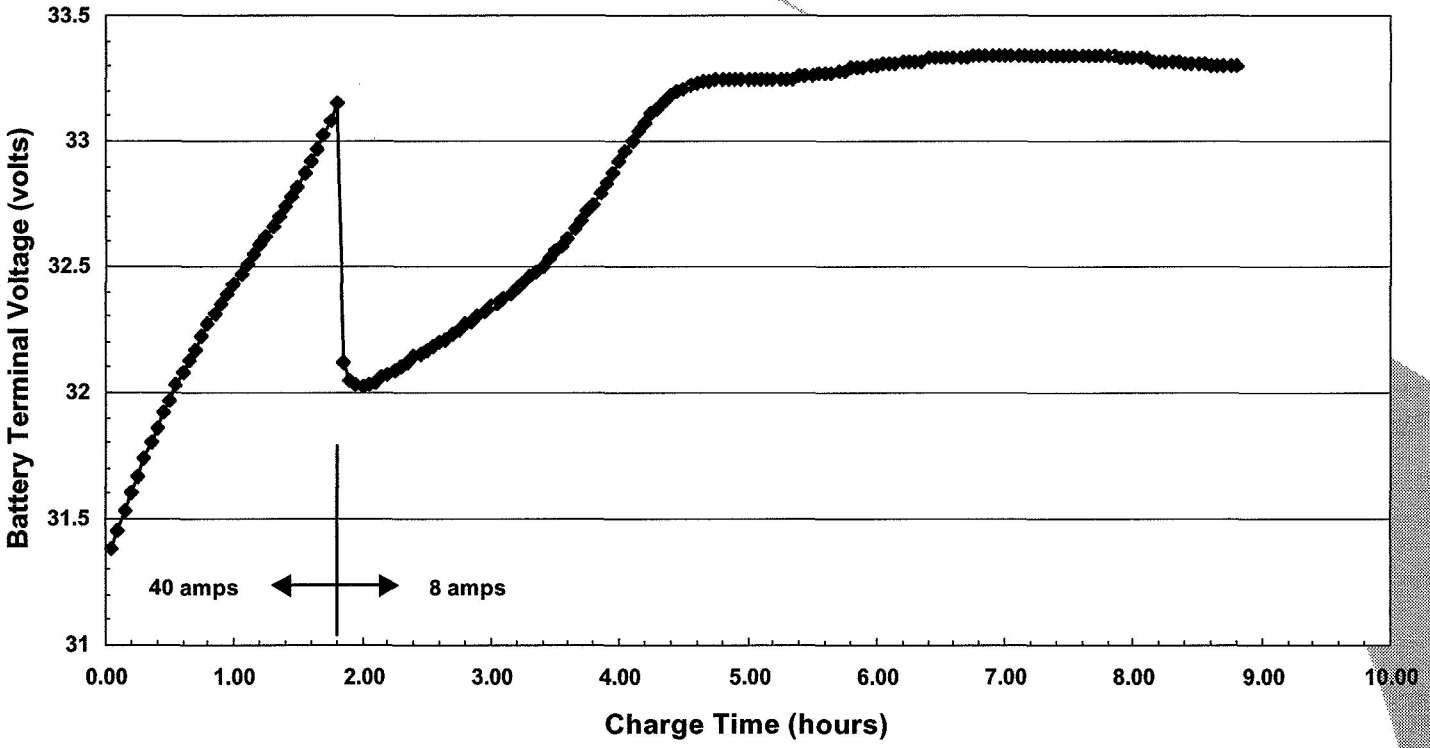

EAGLE PICHER
Eagle-Picher Technologies, LLC



Discharge with 160 amp Pulse SAR 10121

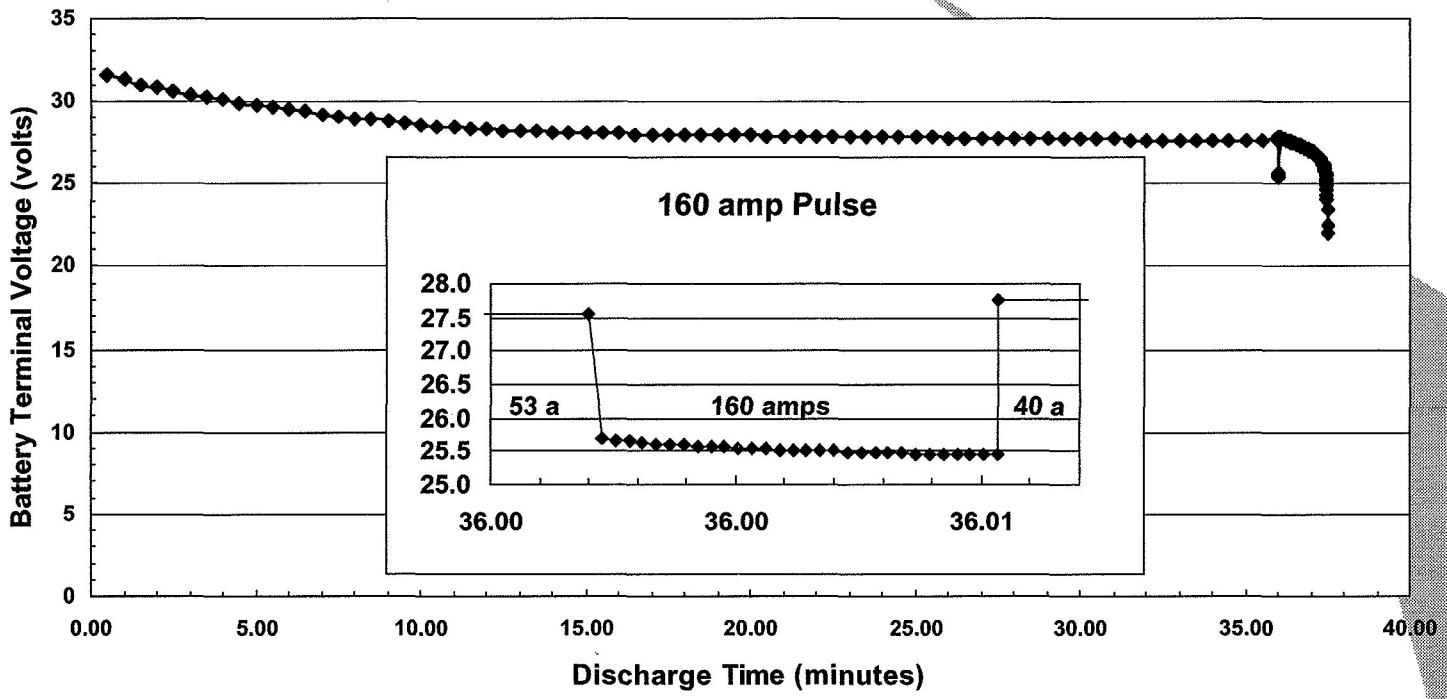

EAGLE PICHER
Eagle-Picher Technologies, LLC



120 AH SPV Battery Proposed Design Summary

❑ Battery Type	SAR 10125
❑ Nominal Voltage (volts)	27.7
❑ Rated Capacity (Ah)	120
❑ Actual Capacity (Ah)	132
❑ Specific Energy (WHr/kg)	53.7
❑ Energy Density (WHr/liter)	64.3
❑ Weight (lb)	150
❑ Diameter (inches)	13.06
❑ Length (inches)	36.2
❑ MEOP (psig)	540

EAGLE PICHER
Eagle-Picher Technologies, LLC

Planned 13" Battery Design Qualification Tests

- Pressure Vessel Qualification (Cycle & Burst Sample)
- Random Vibration to 12.9 Grms
- Sinusoidal Vibration to 10.5 G
- Pyrotechnic Shock
- Electrical Testing
  - Standard Capacity @ -10°C to 30°C
  - LEO Operational Profile
  - GEO Operational Profile
  - Charge/Discharge Rates (pulse)
  - Charge Retention @ 10°C
  - Impedance
  - Insulation Resistance

EAGLE PICHER
Eagle-Picher Technologies, LLC

Summary

- Two Battery Designs Are Being Developed in the 13 Inch Diameter
- Both Designs Utilize the Basic Technology Qualified and Flown on the Iridium® Program
- 80 Ah Design Is Being Completed for Qualification Test with Planned Completion of March 2001
- 120 Ah Design Will Be Completed by November 2001

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Conclusions

- Proper handling of Ni-H_2 cells/batteries in storage, during I&T, and at launch site is very important to preserve the useful energy and to extend the mission life
- Cell reversal test is not a prudent test to verify or quantify the nickel pre-charge in Ni-H_2 cells/batteries
- The second plateau is due to the formation of Ni^{+3} that is electrochemically inactive
- Gas analysis of the cell, and Chemical analysis of the positive plate are confirmatory tests to determine the nature of pre-charge in Ni-H_2 cells

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Effect of Handling, Storage and Cycling on Ni-H_2 Cells: Second Plateau Phenomenon

Hari Vaidyanathan

Lockheed Martin Global Telecommunications

And

Gopalakrishna M. Rao

NASA/Goddard Space Flight Center

2000 NASA Aerospace Battery Workshop

Huntsville, Alabama

November 14-16, 2000

5H/CP/1M/14

15 p.s 2001117816

S2085-1

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Background

- The discharge voltage profile for some Ni-H_2 cells exhibits a second plateau at about 0.8V
- The capacity at a lower voltage plateau results in loss of useful energy
- The proportion of capacity in the second plateau varies with handling, storage, use and cycling

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Criteria for Cell Selection

- Cells received after ATP from the Vendor
- Cells stored cold in discharged open-circuit conditions
- Cells stored dry/cold and activated in later years
  - Room temperature exposure
- Cells removed from a workhorse battery
  - Room temperature exposure
  - Intermittent charging
  - Extensive use
  - Cell reversal

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Cell History

CELL I.D.	HISTORY
TERRA - 50 AH	
2-044	STORED AT LOW TEMP
1-005	STORED AT LOW TEMP
2-117	WORKHORSE BATTERY
2-146	WORKHORSE BATTERY
3-160	17317 LEO CYCLES (40%DOD AND 10°C)
3-205	STORED AT LOW TEMP
2-097	WORKHORSE BATTERY
2-048	WORKHORSE BATTERY
2-061	WORKHORSE BATTERY/500 LEO CYCLES (40%DOD AND 10°C)
HST - 93 AH	
10-515	ATP
10-511	DRY STORED (2 YRS), STORED UNCONTROLLED (1 YEAR) AFTER ATP
10-512	DRY STORED (2 YRS), STORED UNCONTROLLED (1 YEAR) AFTER ATP
11-754	DRY STORED (2 YRS), STORED UNCONTROLLED (1 YEAR) AFTER ATP
AQUA and AURA 160 AH	
1-041	ATP
2-102	ATP, SEAL REWORK, ATP

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

C/2 RATE DISCHARGE PROFILES AT10°C

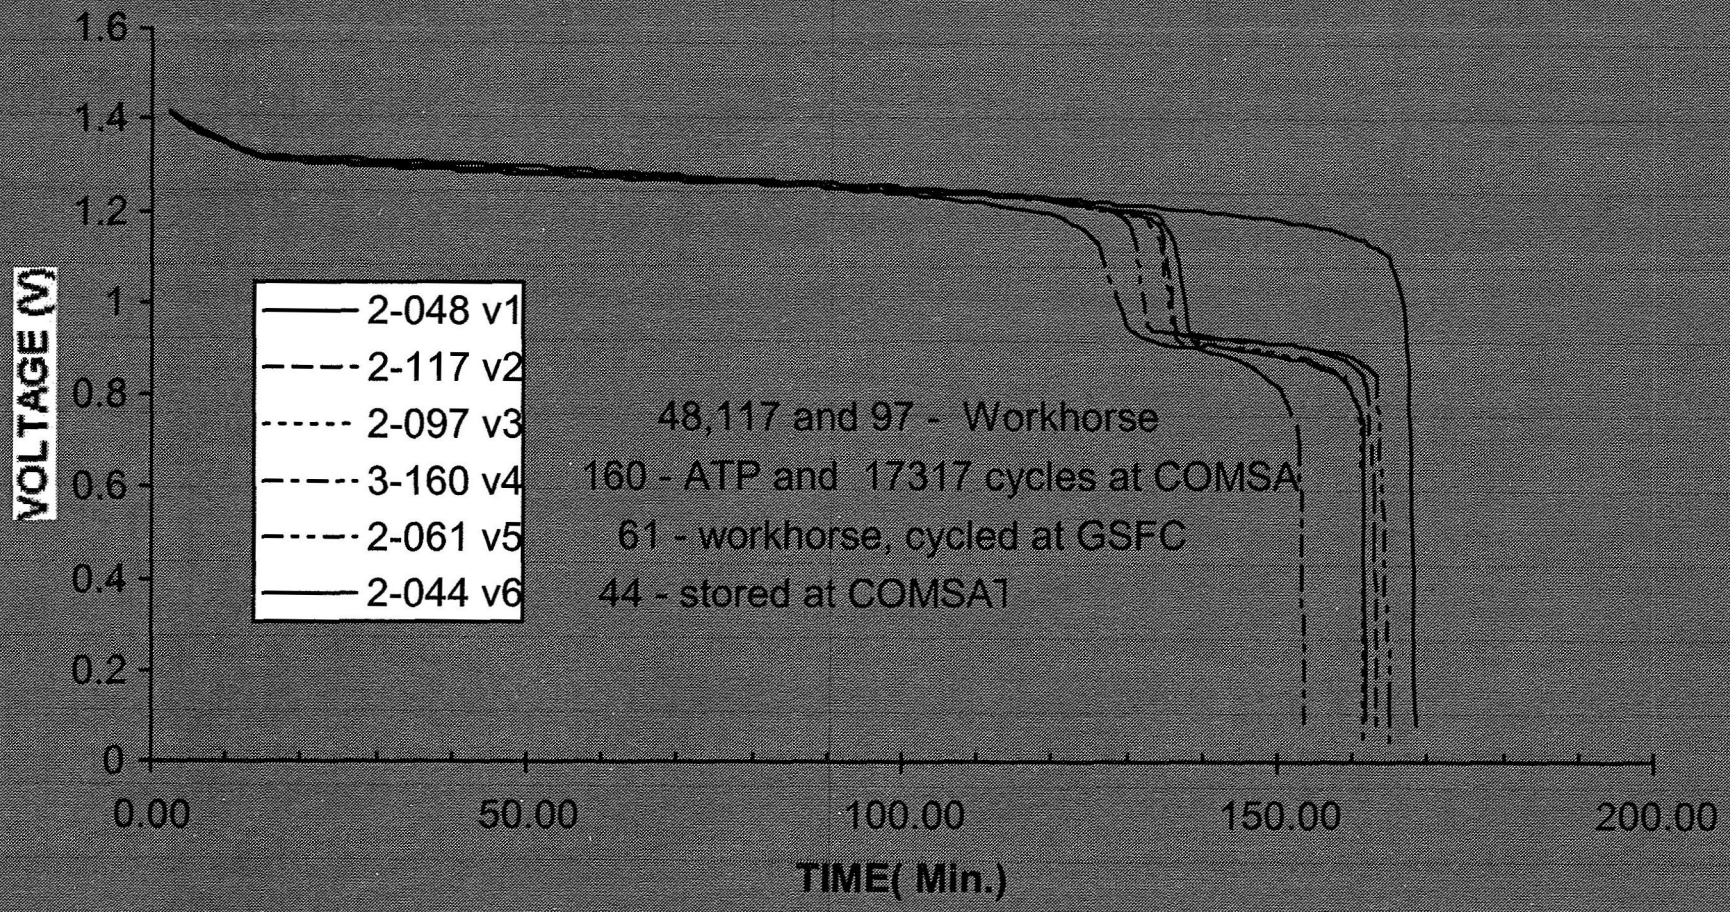

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Second Plateau Capacity at C/2 Discharge

CELL I.D.	HISTORY	Capacity 1V	AH,10°C 0.1V	SECOND PLATEAU CAPACITY, %
	50 AH, TERRA			
2-044	Stored at low temp.	68.9	69.7	1.1
1-005	Stored at low temp.	63.6	64.3	1
2-117	Workhorse battery	56	63.8	12.2
2-146	Workhorse battery	62.5	63.9	2.2
3-160	17317 LEO cycles	53.4	64.5	17.2
3-205	Stored at low temp.	63.7	64.2	0.78
2-097	Workhorse battery	55.2	67.5	18.1
2-048	Workhorse battery	56	67.7	17.3
2-061	Workhorse battery, 500 LEO cycles	54.4	68.9	21
	93 AH, HST			
10-515	ATP	84.2	88.7	5
10-511	Dry storgae, Uncontrolled storage after ATP	93.4	98.3	5
10-512	Dry storgae, Uncontrolled storage after ATP	93	99.3	5.9
11-754	Dry storgae, Uncontrolled storage after ATP	91.8	97.5	5.8
	160 AH, AQUA and AURA			
1-041	ATP	184.7	185.1	0.3
2-102	ATP, Seal rework, ATP	192.2	192.9	0.2

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

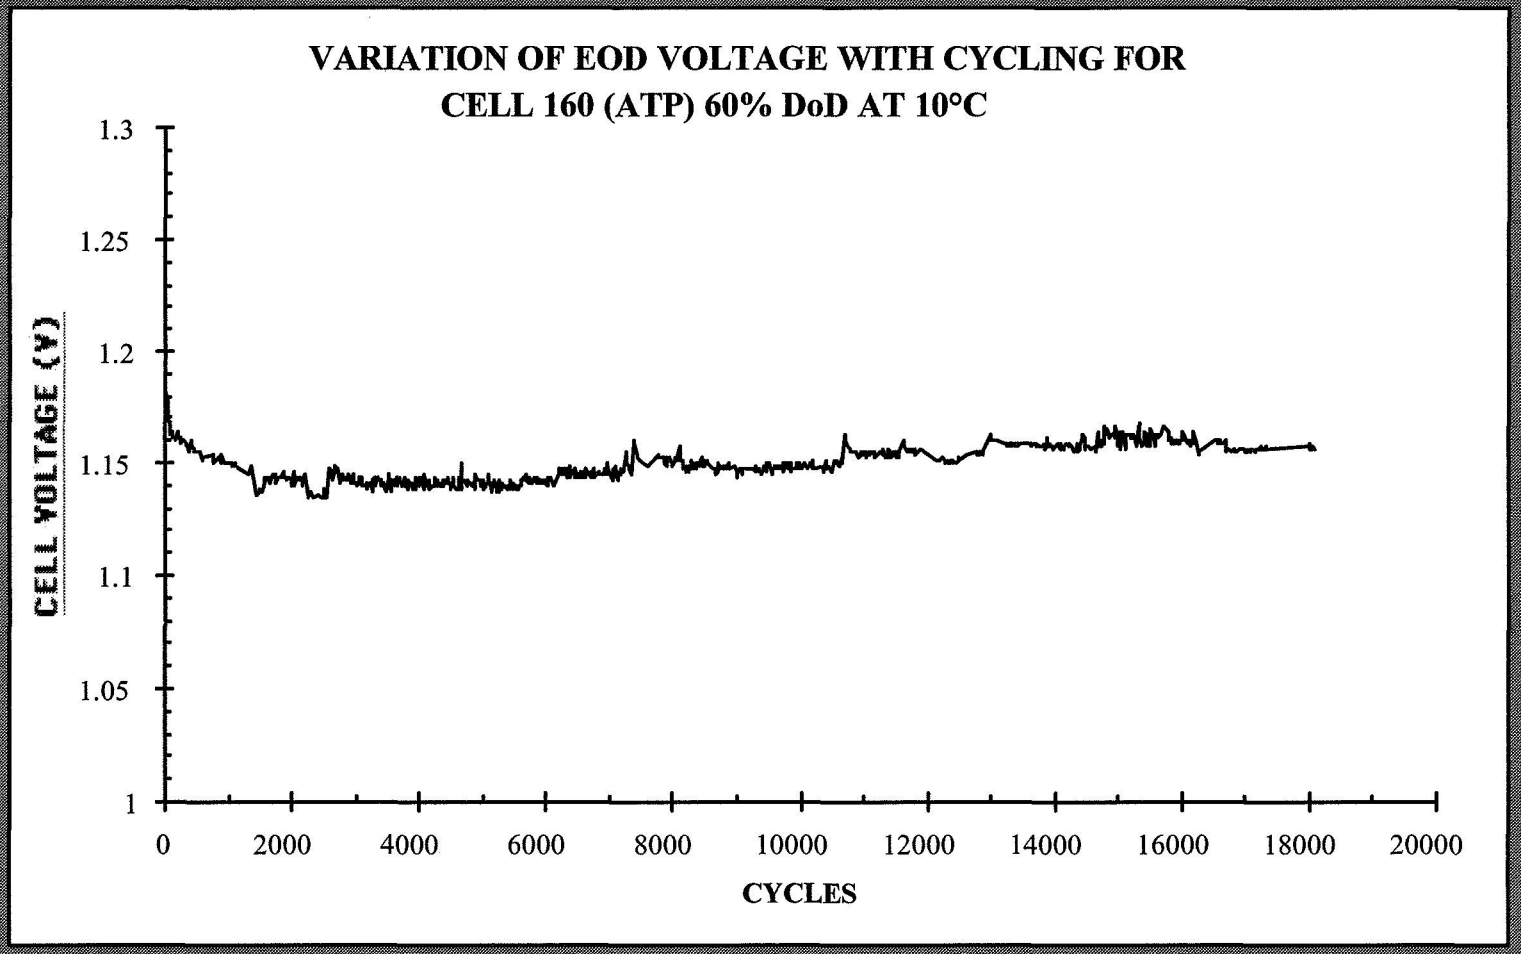

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VARIATION OF END OF DISCHARGE VOLTAGE FOR CELL 048 AT 60% DoD AT 10°C (Workhorse Battery - TERRA)

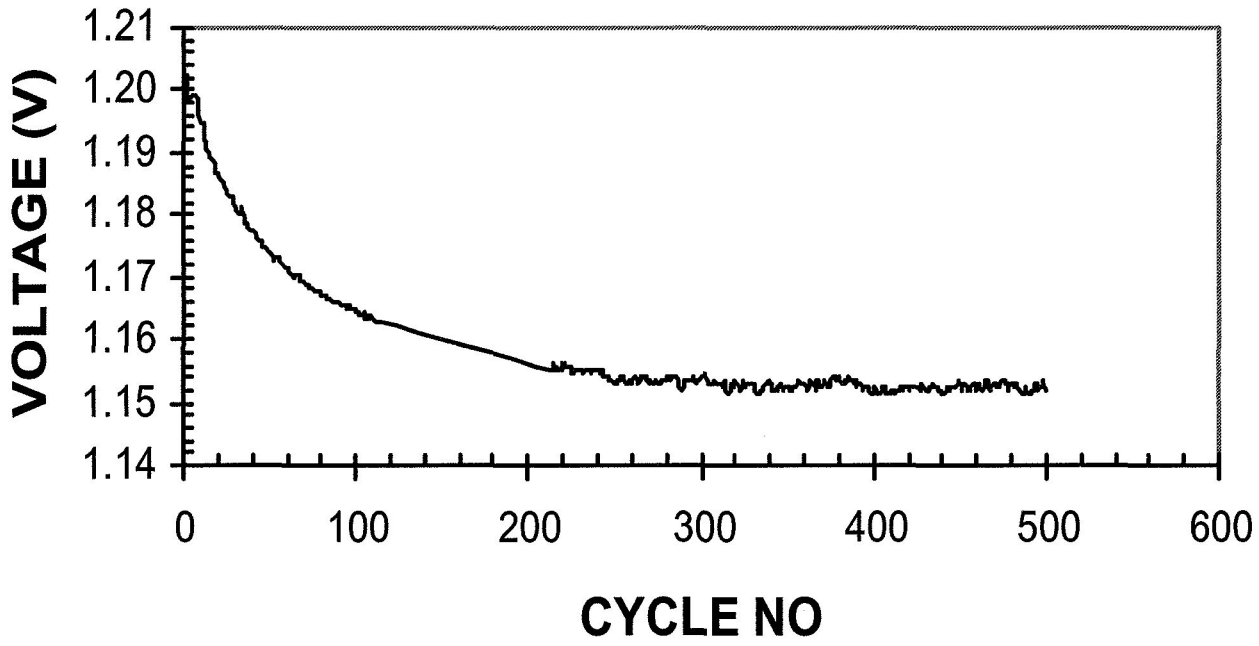

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

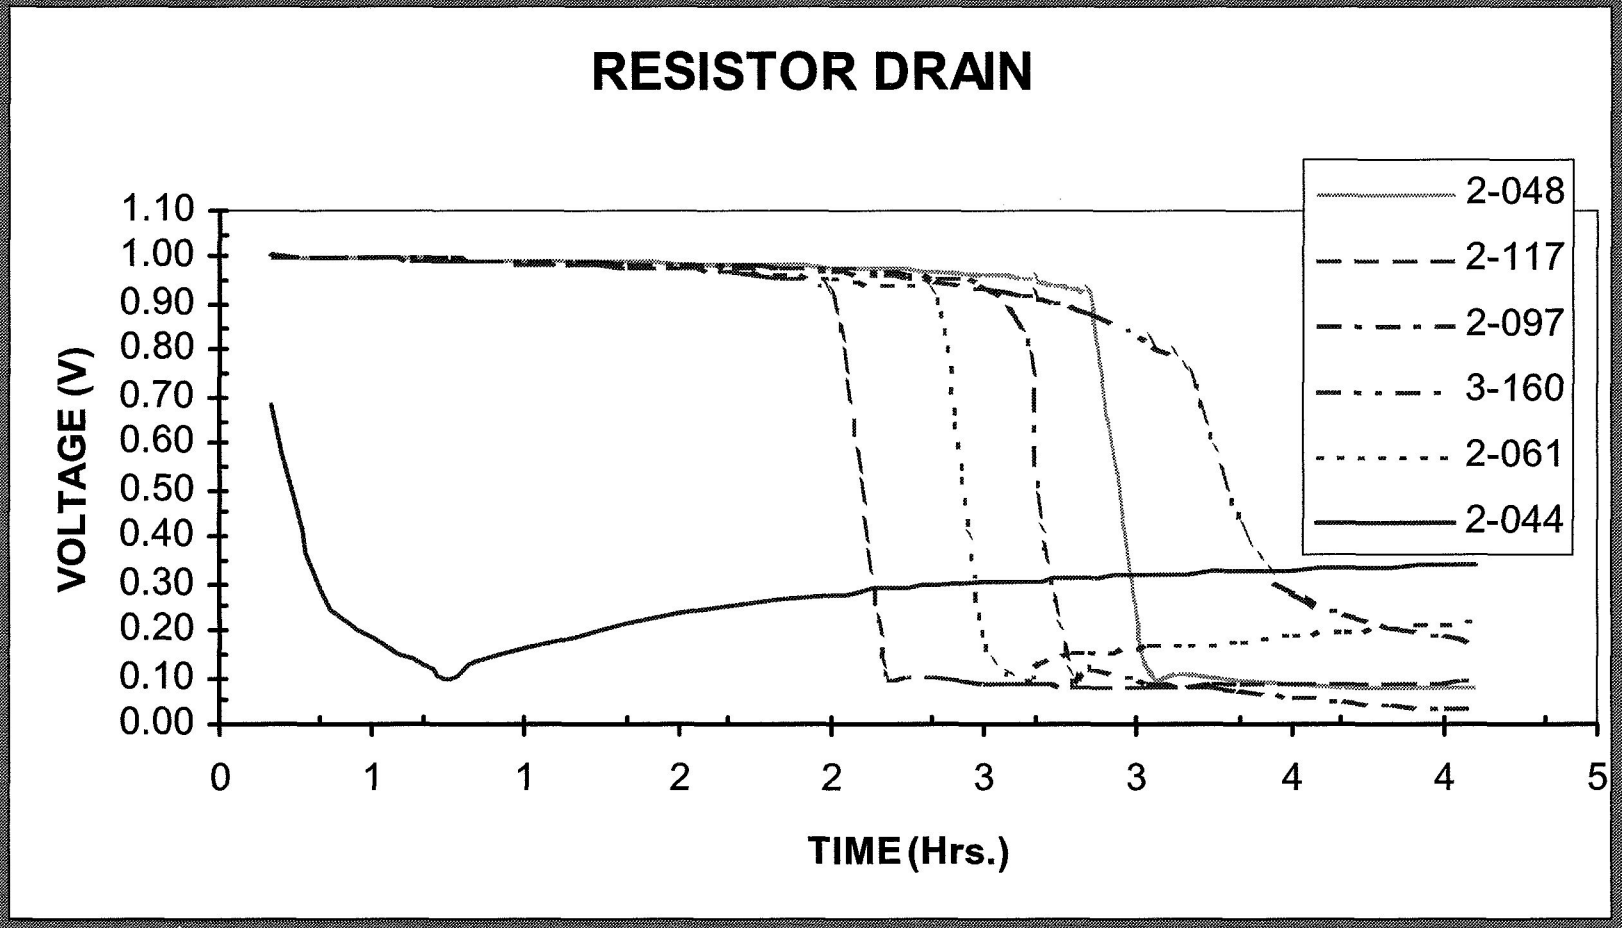

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Cell Reversal Test Condition

- Temperature = 20°C
- Charge at C/10 for 16 hrs followed by two discharges at C/2 to 1V and at C/20 to 0.01V and then resistive drain to 0.005V
- Reversal discharge at C/40 for 5 minutes

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

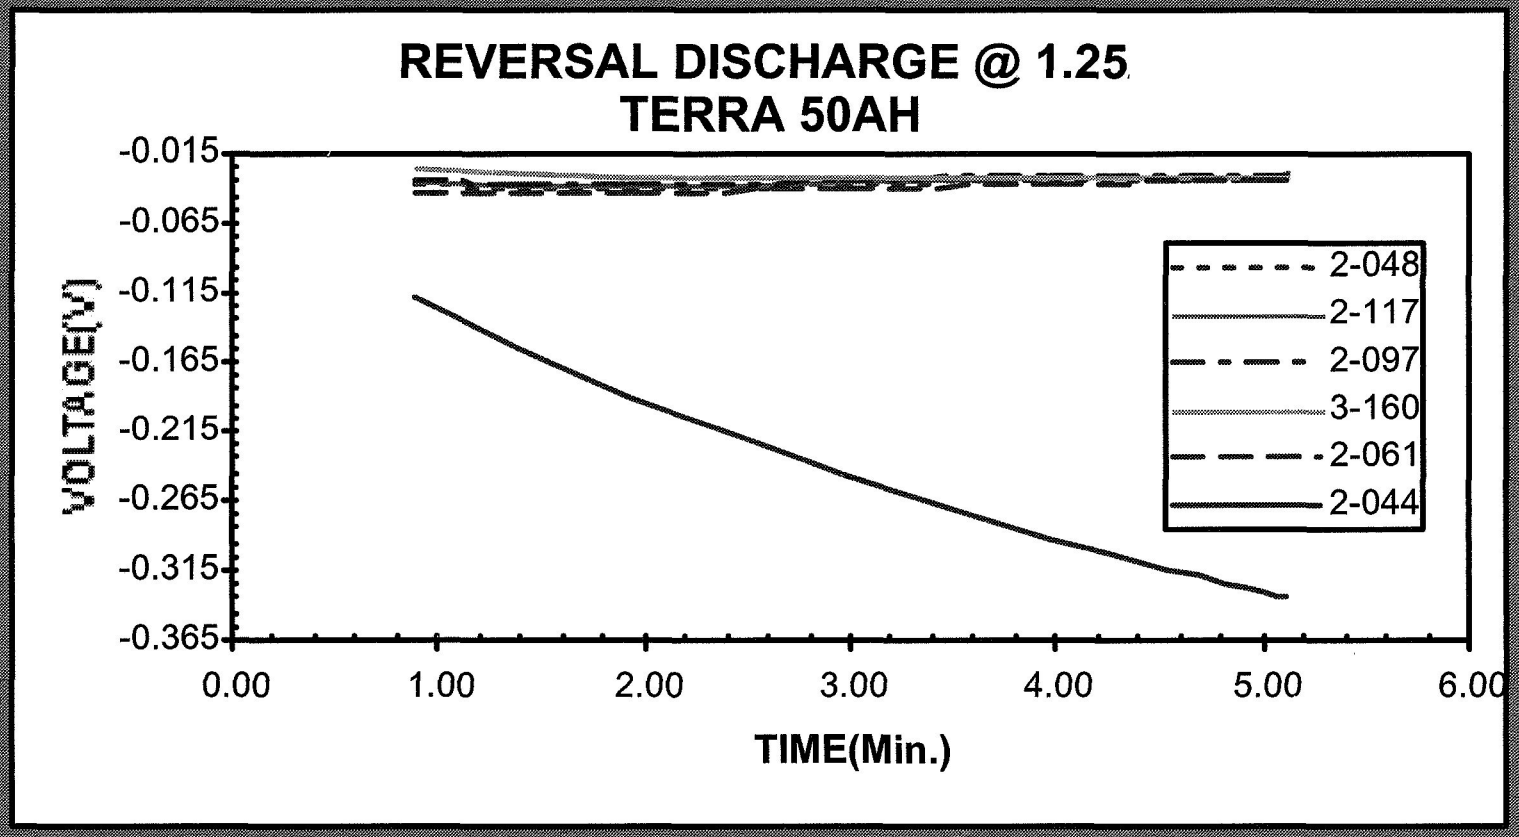

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

GAS ANALYSIS

CELL I.D.	GAS CONTENT
50 AH TERRA cell(2-044), stored at low temp.	No gas present
50 AH TERRA (2-061), workhorse, 500 cycles	vacuum
50 AH TERRA (2-097), workhorse	No gas present
50 AH TERRA (2-117), work horse	H2 less than 100mL
50 Ah TERRA (3-160), ATP, 173 17 cycles	H2 3700 mL
50 AH TERRA (2-146), workhorse	vacuum
50 AH TERRA (3-205), stored at low temp.	vacuum
93 AH HST (11-754), stored uncontrolled 1 year	vacuum
93 AH HST (10-511), stored uncontrolled 1 year	vacuum
93 AH HST (10-512), stored uncontrolled 1 year	vacuum
93 AH HST (10-515), stored uncontrolled 1 year	vacuum
160 AH AQUA (1-041), ATP	vacuum
160 AH AURA (2-102), ATP, seal rework, ATP	vacuum

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

NICKEL PRECHARGE

CELL ID	AH	ELECTRICAL	CHEMICAL	TOTAL	TOTAL, %
50 AH TERRA (2-044)	58.9	0.3	8.0	8.3	16.5
50 AH TERRA (2-117)	49.1	0.0	14.6	14.6	29.2
50 AH TERRA (3-160)	47.5	0.0	9.1	9.1	18.1
50 AH TERRA (2-146)	58.7	0.7	1.3	4.5	8.9
50AH TERRA (3-205)	57.3	1.0	8.7	9.7	19.4
93 AH HST (10-511)	89.3	0	7.9	7.9	8.8
93 AH HST (10-515)	78.6	1.4	12.8	13.2	14.7
160 AH AQUA Cell (1-41)	150	8	19.3	27.3	18.2
160 AH AURA Cell (2-102)	165	8.7	16.3	25	15.1

* Based on measured 20°C Capacity

Summary

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

- Cell stored at low temperature did not exhibit a second plateau in the discharge profile
- Second plateau occurs in cells that are subjected to excessive use, high temperature exposure, intermittent charging, cell reversal, and cycling
- Cells exhibiting second plateau also have a large residual capacity at a lower voltage of about 0.8 V and a voltage plateau at 1V during resistive drain
- Gas analysis indicated the presence of large quantity of hydrogen in the cycled cell and relatively small quantity of hydrogen in ONLY one of the cells that exhibited second plateau
- Chemical analysis indicated the presence of Ni^{+3} in discharged positive plates

EAGLE PICHER
Technologies, LLC

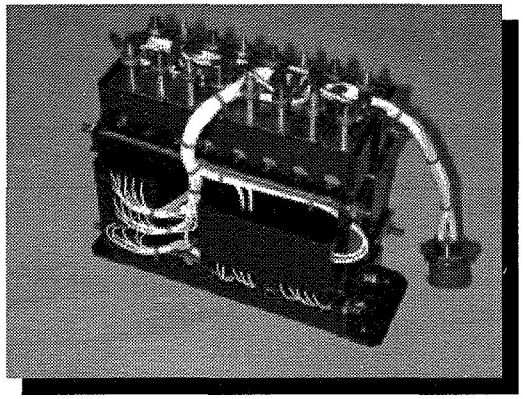

Progress Toward a Li-ion Spacecraft Battery

CHAD KELLY & JAMES DeGRUSON

15 NOVEMBER 2000

NASA AEROSPACE BATTERY WORKSHOP

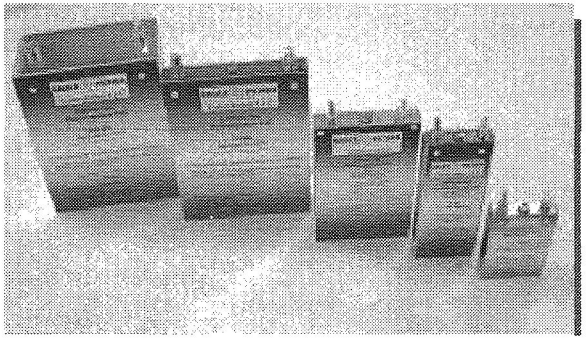

EAGLE PICHER Technologies, LLC

PROGRESS Late 99'

✦**Specific Energy**

- 100 Wh/Kg in 1999

✦**Energy Density**

- 300 Wh/L in 1999

✦**Impedance (SLC-16002)**

- 3.5 milliohms in 1999

✦**Temperature Capability**

- 10% @ C/5 @ -30°C in 1999

✦**Cycle Life**

✦**LEO 25% from 100%SOC**

- 2700 completed 1999

✦**GEO Battery**

- 36 Abb. GEO in 1999

✦**Rate Capability**

- C Max in 1999

EAGLE PICHER Technologies, LLC

PROGRESS
Late 99' and 2000'

✦**Specific Energy**

- 100 Wh/Kg in 1999
- >150 Wh/Kg in 2000

✦**Energy Density**

- 300 Wh/L in 1999
- >380 Wh/L in 2000

✦**Impedance (SLC-16002)**

- 3.5 milliohms in 1999
- 1.4 milliohms in 2000

✦**Temperature Capability**

- 10% @ C/5 @ -30°C in 1999
- >75% @ 0.6C -30°C in 2000

✦**Cycle Life**

✦**LEO 25% from 100%SOC**

- 2700 completed 1999
- 13000 projected 2000

✦**GEO Battery**

- 36 Abb. GEO in 1999
- 101 Abb. GEO in 2000
- >808 Battery Cycles W/o Electronics

✦**Rate Capability**

- C Max in 1999
- 3.3C Tested in 2000

EAGLE PICHER Technologies, LLC

Characteristics of the SLC-16002 Cell Design

	98/99'
Size	3"x7.15"x0.94"
Mass	840g
Ah	20Ah@10A 24Ah BOL
Wh/Kg	>100Wh/Kg
Rate Capability	20A Max 12Ah Delivered

EAGLE PICHER Technologies, LLC

Characteristics of the SLC-16002 Cell Design

	98/99'	2000'
Size	3"x7.15"x0.94"	3"x7.15"x0.94"
Mass	840g	815g
Ah	20Ah@10A 24Ah BOL	35Ah@35A 38Ah BOL
Wh/Kg	>100Wh/Kg	>150Wh/Kg
Rate Capability	20A Max 12Ah Delivered	117A Tested 12Ah Delivered

EAGLE PICHER Technologies, LLC

PROGRESS SINCE INCEPTION OF USG CONTRACT

LEO Cycle Life Demonstration (25% DOD)
Real Time Data (16 cycles/ Day)

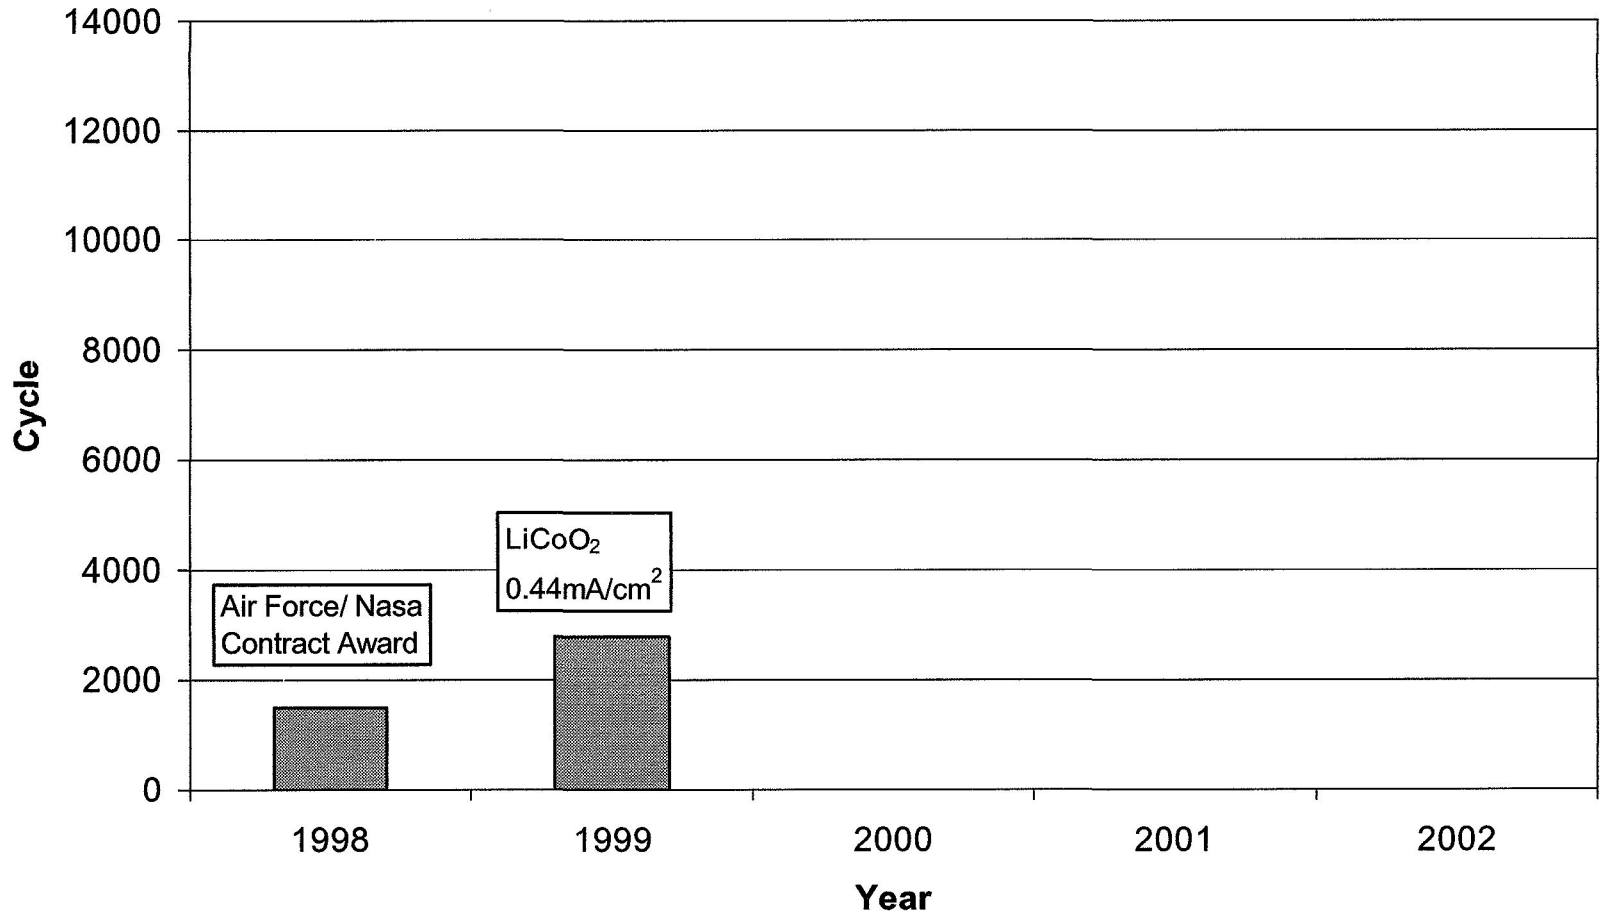

EAGLE PICHER Technologies, LLC

PROGRESS SINCE INCEPTION OF USG CONTRACT

LEO Cycle Life Demonstration (25% DOD)
Real Time Data (16 cycles/ Day)

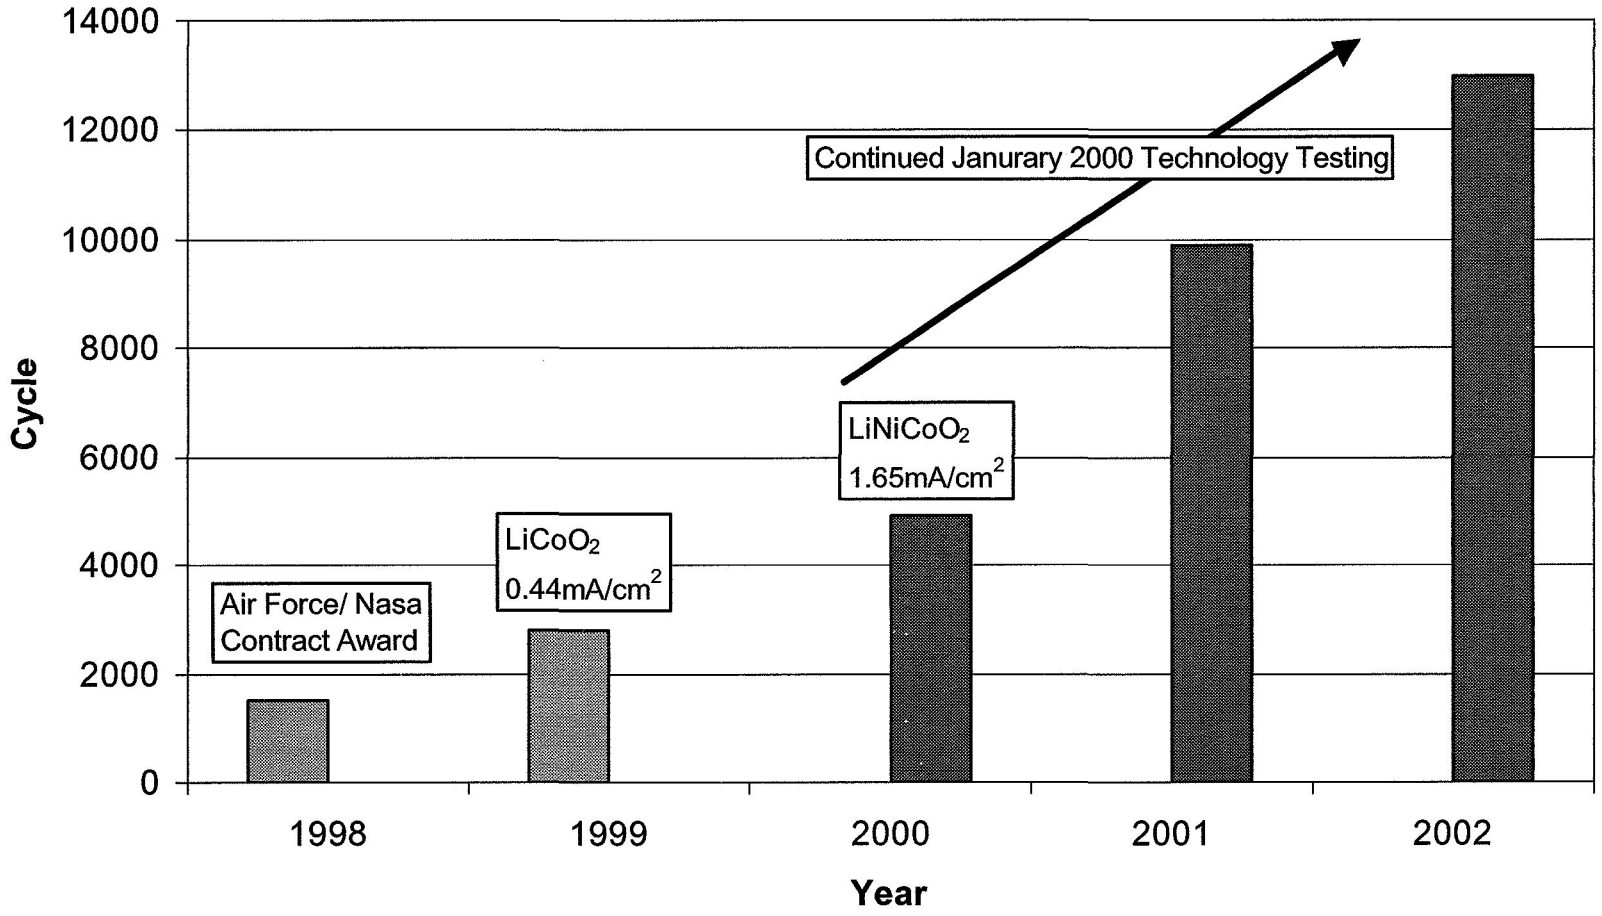

EAGLE PICHER Technologies, LLC

PROGRESS SINCE INCEPTION OF CONTRACT

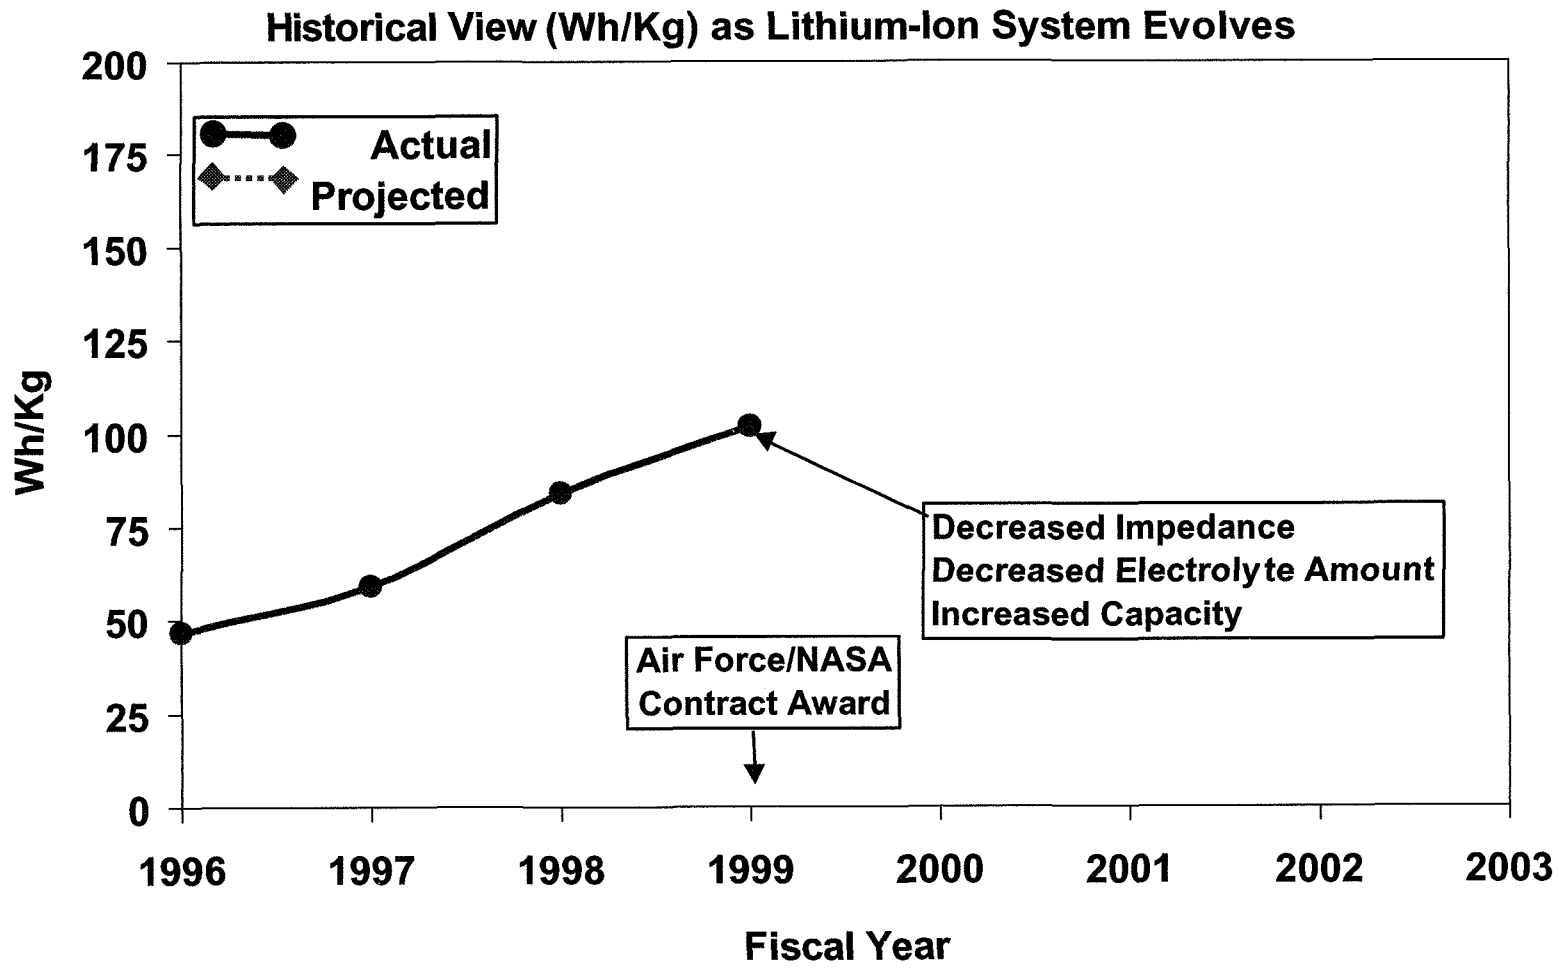

EAGLE PICHER Technologies, LLC

PROGRESS SINCE INCEPTION OF CONTRACT

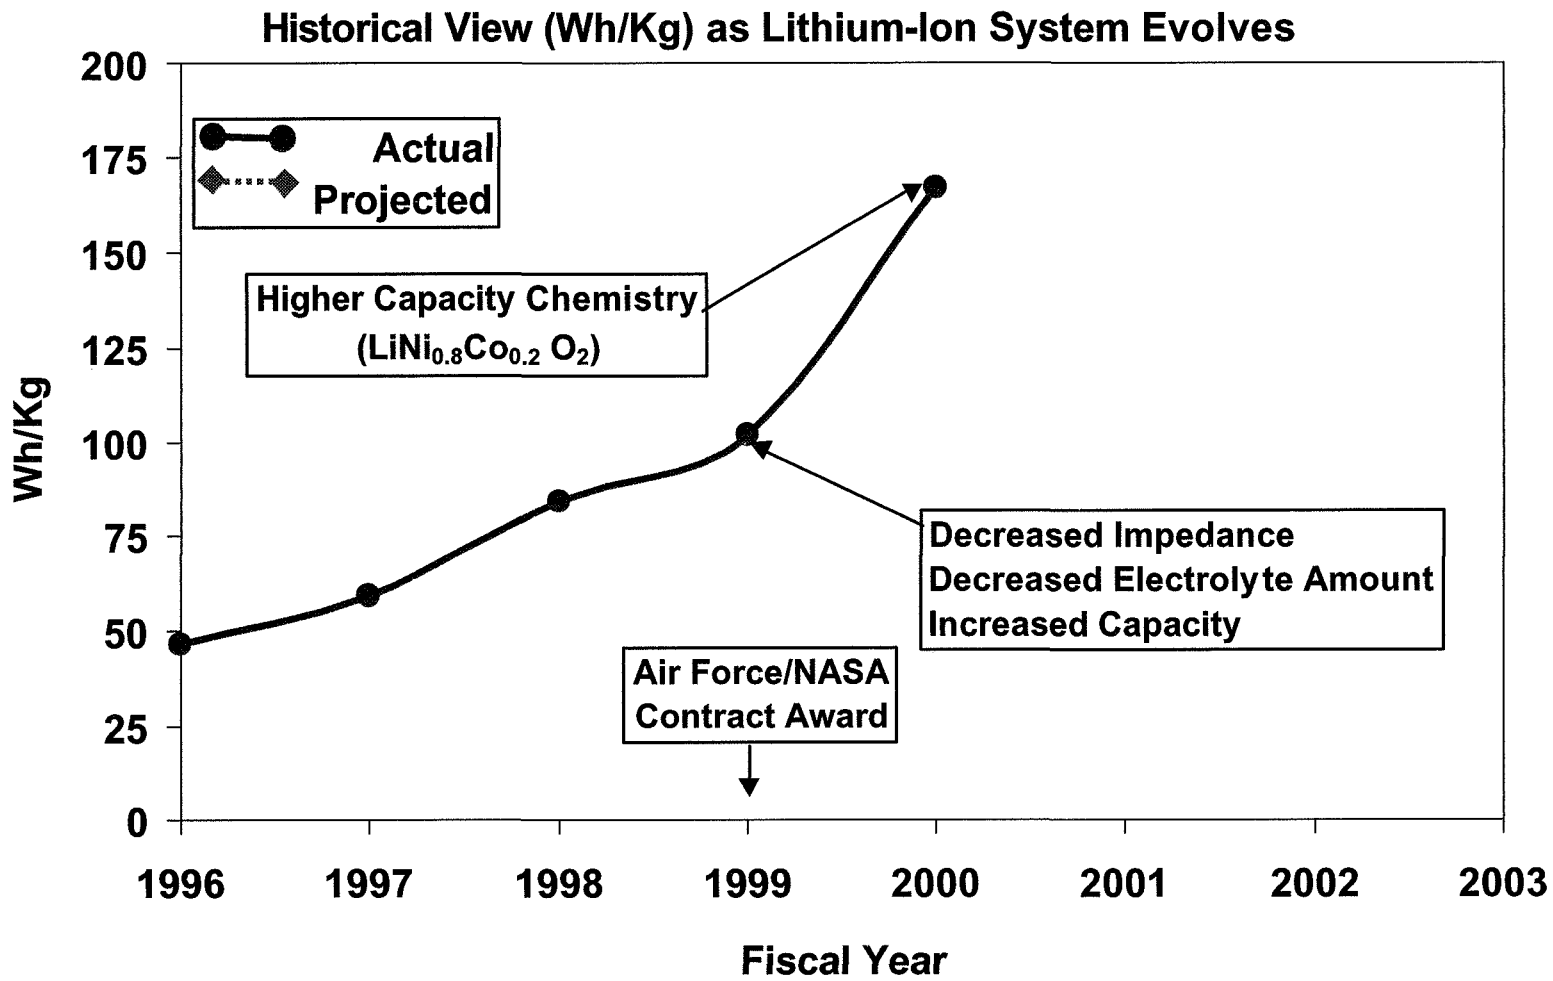

EAGLE PICHER Technologies, LLC

PROGRESS SINCE INCEPTION OF CONTRACT

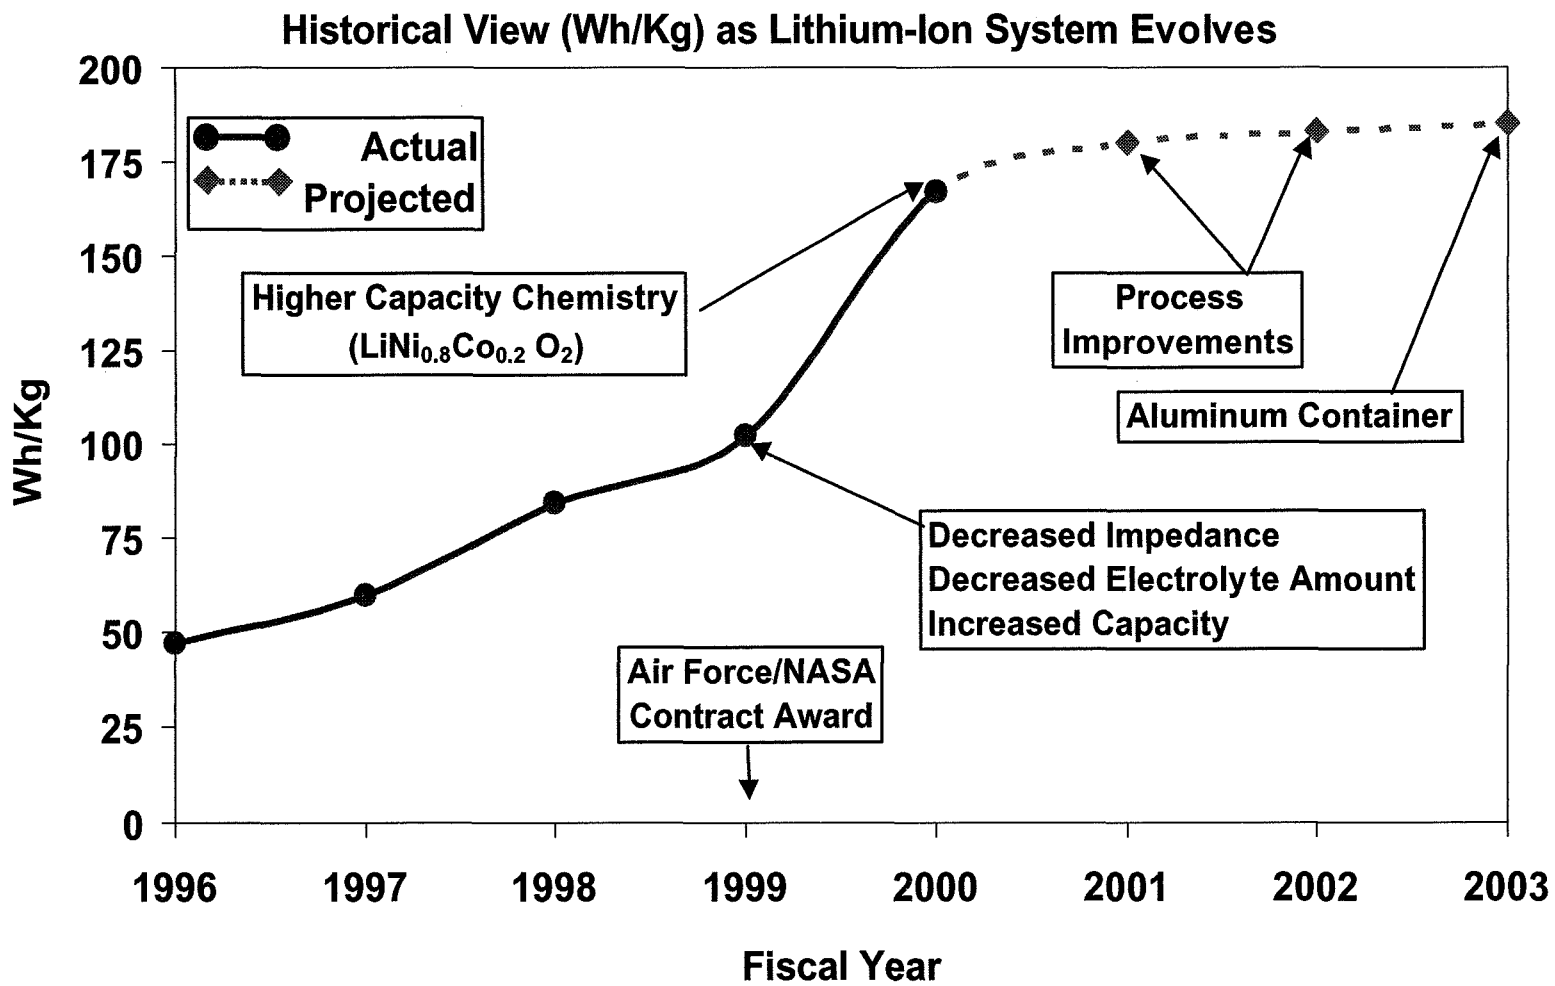

EAGLE PICHER
Technologies, LLC

CELL EVALUATION

Rate/Temperature Tests

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **PURPOSE: DETERMINE DISCHARGE CHARACTERISTICS OF "NEW" CHEMISTRY**
  - **CHARGE RATE EFFECTS**
  - **DISCHARGE RATE EFFECTS**
  - **TEMPERATURE EFFECTS**
    - CELL DISCHARGE CAPACITY (AHRS)
    - CELL DISCHARGE ENERGY (WHRS)
    - CELL ENERGY DENSITY (WHRS/KG)

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **PURPOSE: DETERMINE DISCHARGE CHARACTERISTICS OF "NEW" CHEMISTRY**
  - **CHARGE RATE EFFECTS**
  - **DISCHARGE RATE EFFECTS**
  - **TEMPERATURE EFFECTS**
    - CELL DISCHARGE CAPACITY (AHRS)
    - CELL DISCHARGE ENERGY (WHRS)
    - CELL ENERGY DENSITY (WHRS/KG)
  - **TEST RATES EXPRESSED IN mA/cm^2 OF CATHODE SURFACE AREA**
    - ALLOWS RESULTS TO BE "SCALED" FOR OTHER PRISMATIC CELL DESIGNS

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **PURPOSE: DETERMINE DISCHARGE CHARACTERISTICS OF "NEW" CHEMISTRY**
  - **CHARGE RATE EFFECTS**
  - **DISCHARGE RATE EFFECTS**
  - **TEMPERATURE EFFECTS**
    - CELL DISCHARGE CAPACITY (AHRS)
    - CELL DISCHARGE ENERGY (WHRS)
    - CELL ENERGY DENSITY (WHRS/KG)
  - **TEST RATES EXPRESSED IN mA/cm² OF CATHODE SURFACE AREA**
    - ALLOWS RESULTS TO BE "SCALED" FOR OTHER PRISMATIC CELL DESIGNS

- **STANDARD SLC-16002 (35 AHR NAMEPLATE) CELL DESIGN CHOSEN AS TEST VEHICLE**

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL CHARGE VOLTAGE @ 23°C

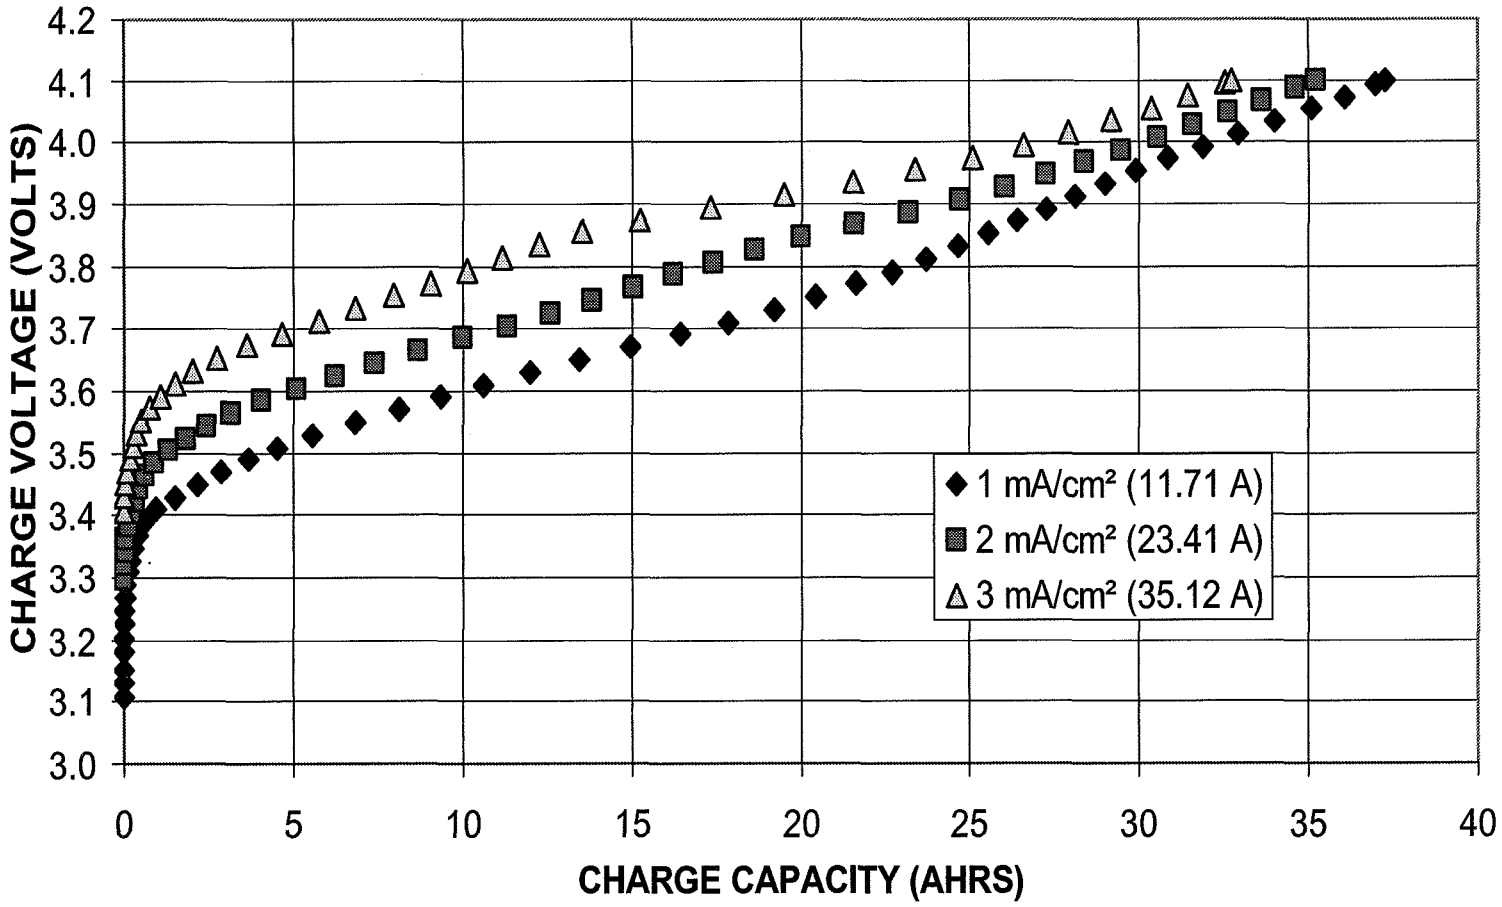

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL CHARGE VOLTAGE @ 23°C

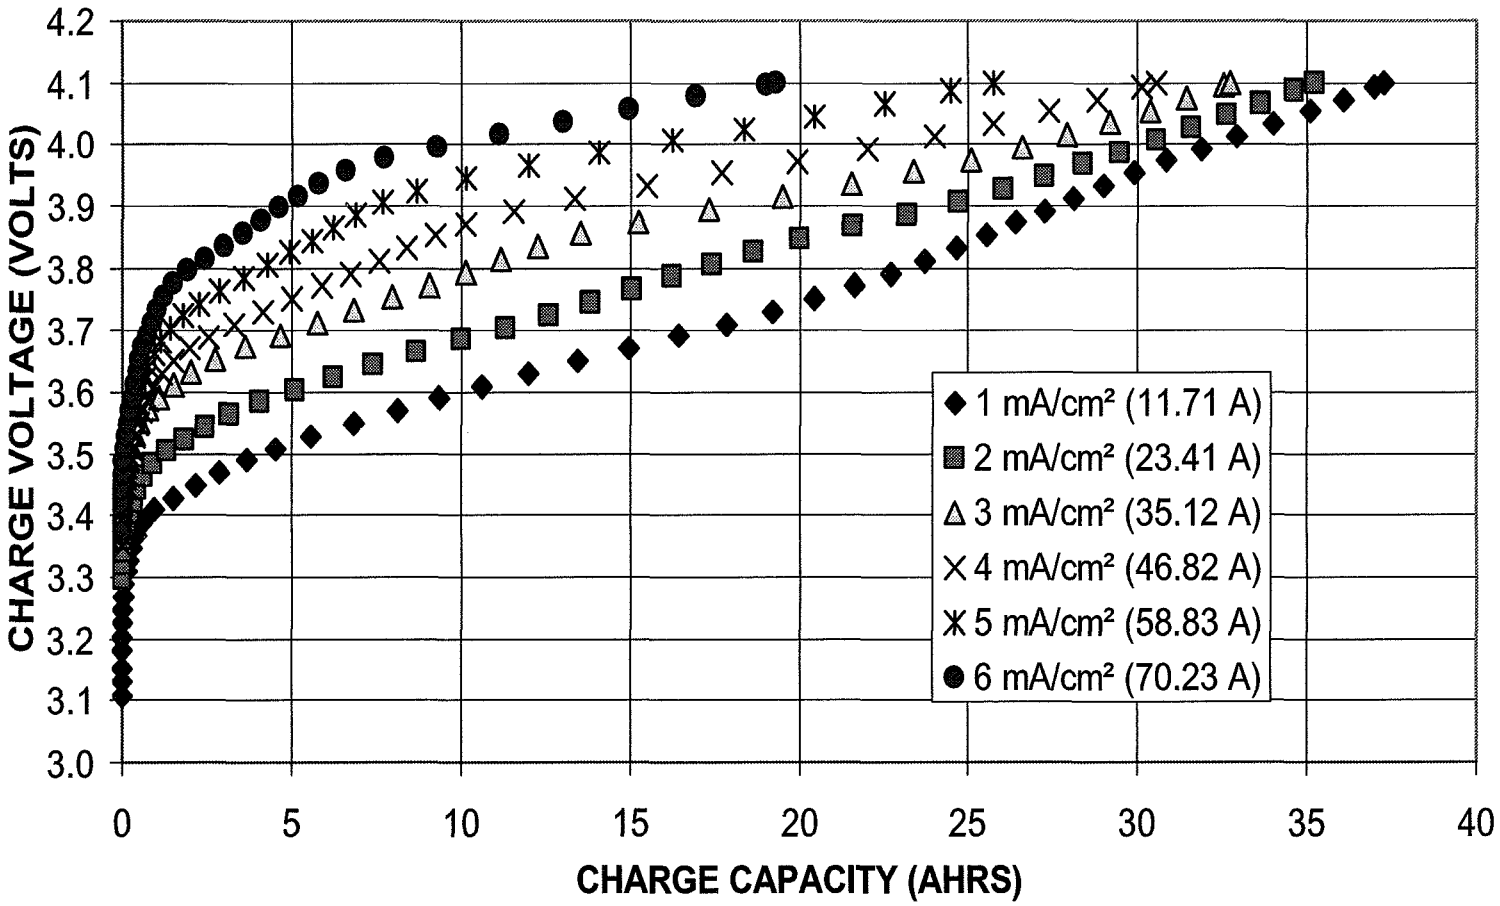

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **CHARACTERIZE STANDARD SLC-16002 (35 AHR NAMEPLATE) CELL DESIGN**
  - **AMBIENT TEMPERATURE (23°C) CHARGE VS:**
    - 70°C DISCHARGE
    - 60°C DISCHARGE
    - 50°C DISCHARGE
    - 40°C DISCHARGE
    - 23°C DISCHARGE
    - 10°C DISCHARGE
    - 0°C DISCHARGE
    - -10°C DISCHARGE

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **CHARACTERIZE STANDARD SLC-16002 (35 AHR NAMEPLATE) CELL DESIGN**
  - **AMBIENT TEMPERATURE (23°C) CHARGE VS:**
    - 70°C DISCHARGE
    - 60°C DISCHARGE
    - 50°C DISCHARGE
    - 40°C DISCHARGE
    - 23°C DISCHARGE
    - 10°C DISCHARGE
    - 0°C DISCHARGE
    - -10°C DISCHARGE
  - **SAME TEMPERATURE CHARGE & DISCHARGE**
    - 23°C
    - 10°C
    - 0°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **CHARACTERIZE STANDARD SLC-16002 (35 AHR NAMEPLATE) CELL DESIGN**
  - **AMBIENT TEMPERATURE (23°C) CHARGE VS:**
    - 70°C DISCHARGE
    - 60°C DISCHARGE
    - 50°C DISCHARGE
    - 40°C DISCHARGE
    - 23°C DISCHARGE
    - 10°C DISCHARGE
    - 0°C DISCHARGE
    - -10°C DISCHARGE
  - **SAME TEMPERATURE CHARGE & DISCHARGE**
    - 23°C
    - 10°C
    - 0°C
  - **DISCHARGE RATES FROM 1 mA/cm² (C/3 AMPS) thru 10 mA/cm² (3.3C AMPS)**

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ TEST PROFILE

- **CHARGE CELL AT 2.34 AMPS (0.2 mA/cm²) TO 4.1 VOLTS**
- **DISCHARGE CELL PER THE FOLLOWING STEP RATE SEQUENCE:**
  - 117.06 AMPS (10 mA/cm²)
  - 105.35 AMPS (9 mA/cm²)
  - 93.65 AMPS (8 mA/cm²)
  - 81.94 AMPS (7 mA/cm²)
  - 70.23 AMPS (6 mA/cm²)
  - 58.53 AMPS (5 mA/cm²)
  - 46.82 AMPS (4 mA/cm²)
  - 35.12 AMPS (3 mA/cm2)
  - 23.41 AMPS (2 mA/cm²)
  - 11.71 AMPS (1 mA/cm²)

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ TEST PROFILE

- **CHARGE CELL AT 2.34 AMPS (0.2 mA/cm²) TO 4.1 VOLTS**
- **DISCHARGE CELL PER THE FOLLOWING STEP RATE SEQUENCE:**
  - 117.06 AMPS (10 mA/cm²)
  - 105.35 AMPS (9 mA/cm²)
  - 93.65 AMPS (8 mA/cm²)
  - 81.94 AMPS (7 mA/cm²)
  - 70.23 AMPS (6 mA/cm²)
  - 58.53 AMPS (5 mA/cm²)
  - 46.82 AMPS (4 mA/cm²)
  - 35.12 AMPS (3 mA/cm2)
  - 23.41 AMPS (2 mA/cm²)
  - 11.71 AMPS (1 mA/cm²)
- **ALL DISCHARGE STEPS TO 3.0 VOLT CUT-OFF**
- **15 MINUTE OPEN CIRCUIT BETWEEN DISCHARGE STEPS FOR VOLTAGE RECOVERY & TEMPERATURE RESTABILIZATION**
- **TOTAL CAPACITY IS CUMULATIVE AS RATE STEPS DOWN**

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

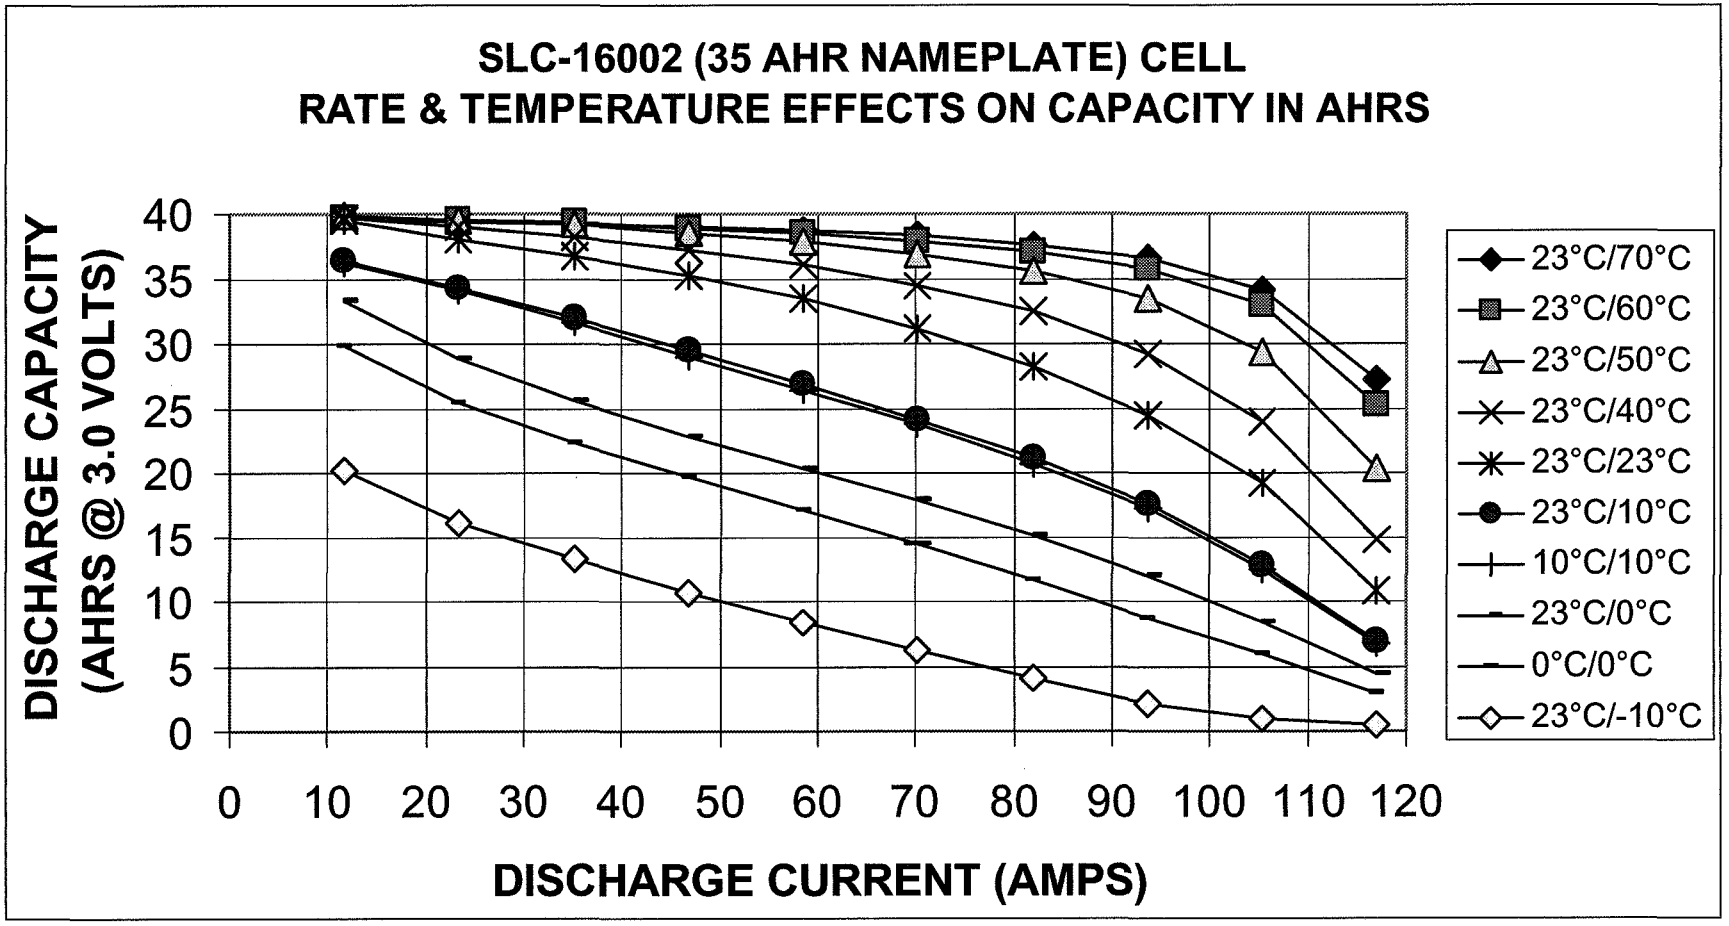

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY**
  - **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 32 SECOND PULSE @ -10°C
      - 54% OF NAMEPLATE CAPACITY @ 23°C
      - 97% OF NAMEPLATE CAPACITY @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY

- **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**

  - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 32 SECOND PULSE @ -10°C
    - 54% OF NAMEPLATE CAPACITY @ 23°C
    - 97% OF NAMEPLATE CAPACITY @ 70°C

  - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 18% OF NAMEPLATE CAPACITY @ -10°C
    - 89% OF NAMEPLATE CAPACITY @ 23°C
    - 109% OF NAMEPLATE CAPACITY @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY

- **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**

  - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 32 SECOND PULSE @ -10°C
    - 54% OF NAMEPLATE CAPACITY @ 23°C
    - 97% OF NAMEPLATE CAPACITY @ 70°C

  - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 18% OF NAMEPLATE CAPACITY @ -10°C
    - 89% OF NAMEPLATE CAPACITY @ 23°C
    - 109% OF NAMEPLATE CAPACITY @ 70°C

  - **C AMPS (3 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 38% OF NAMEPLATE CAPACITY @ -10°C
    - 105% OF NAMEPLATE CAPACITY @ 23°C
    - 112% OF NAMEPLATE CAPACITY @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 17% OF NAMEPLATE CAPACITY @ 0°C
      - 36% OF NAMEPLATE CAPACITY @ 10°C
      - 54% OF NAMEPLATE CAPACITY @ 23°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 17% OF NAMEPLATE CAPACITY @ 0°C
      - 36% OF NAMEPLATE CAPACITY @ 10°C
      - 54% OF NAMEPLATE CAPACITY @ 23°C
    - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 41% OF NAMEPLATE CAPACITY @ 0°C
      - 67% OF NAMEPLATE CAPACITY @ 10°C
      - 89% OF NAMEPLATE CAPACITY @ 23°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **SIGNIFICANT CELL CAPACITY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 17% OF NAMEPLATE CAPACITY @ 0°C
      - 36% OF NAMEPLATE CAPACITY @ 10°C
      - 54% OF NAMEPLATE CAPACITY @ 23°C
    - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 41% OF NAMEPLATE CAPACITY @ 0°C
      - 67% OF NAMEPLATE CAPACITY @ 10°C
      - 89% OF NAMEPLATE CAPACITY @ 23°C
    - **C AMPS (3 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 64% OF NAMEPLATE CAPACITY @ 0°C
      - 90% OF NAMEPLATE CAPACITY @ 10°C
      - 105% OF NAMEPLATE CAPACITY @ 23°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

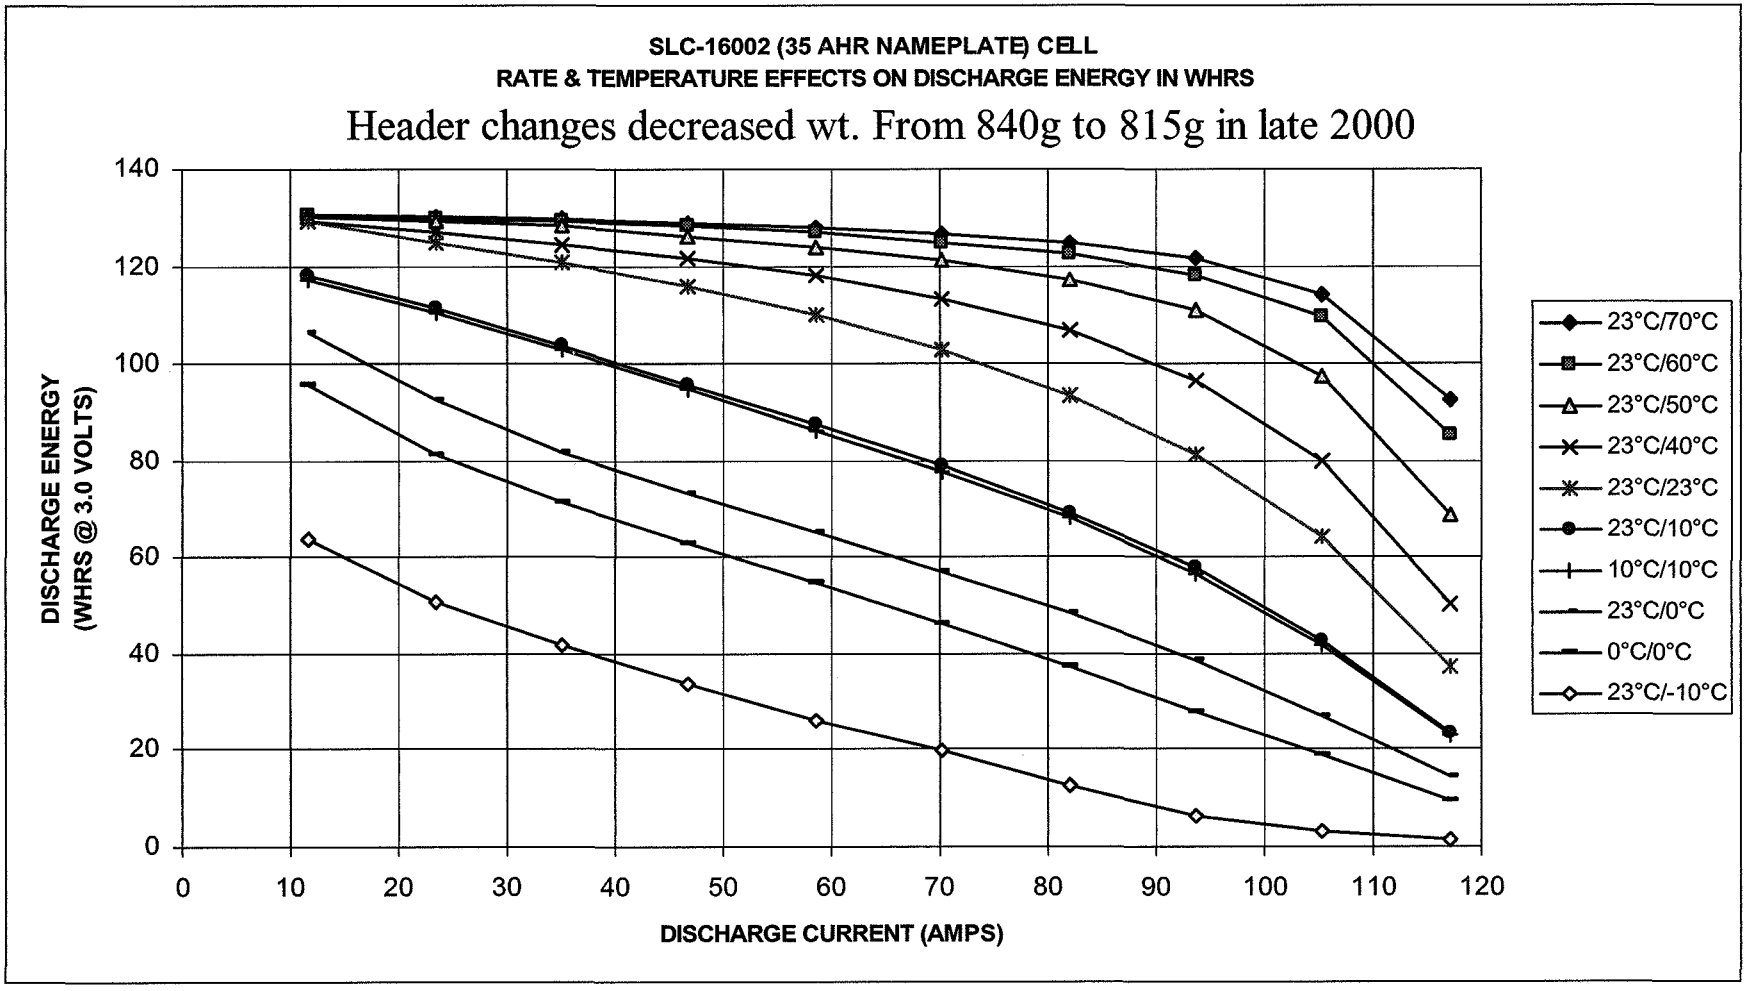

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- **AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY**
  - **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 3.25 WHRS @ -10°C
      - 64.38 WHRS @ 23°C
      - 113.96 WHRS @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY

- **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**
  - ➤ **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 3.25 WHRS @ -10°C
    - 64.38 WHRS @ 23°C
    - 113.96 WHRS @ 70°C
  - ➤ **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 19.64 WHRS @ -10°C
    - 102.80 WHRS @ 23°C
    - 126.75 WHRS @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

✦ AMBIENT TEMPERATURE (23°C) CHARGE TEST SUMMARY

- **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**

  - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 3.25 WHRS @ -10°C
    - 64.38 WHRS @ 23°C
    - 113.96 WHRS @ 70°C

  - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 19.64 WHRS @ -10°C
    - 102.80 WHRS @ 23°C
    - 126.75 WHRS @ 70°C

  - **C AMPS (3 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
    - 41.72 WHRS @ -10°C
    - 120.57 WHRS @ 23°C
    - 129.58 WHRS @ 70°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 18.67 WHRS @ 0°C
      - 41.57 WHRS @ 10°C
      - 64.38 WHRS @ 23°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 18.67 WHRS @ 0°C
      - 41.57 WHRS @ 10°C
      - 64.38 WHRS @ 23°C
    - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 46.40 WHRS @ 0°C
      - 77.54 WHRS @ 10°C
      - 102.80 WHRS @ 23°C

EAGLE PICHER Technologies, LLC

SLC-16002 (35 AHR NAMEPLATE) CELL TESTS

- ***SAME TEMPERATURE*** **CHARGE/DISCHARGE TEST SUMMARY**
  - **CELL DISCHARGE ENERGY AVAILABLE AT ELEVATED DISCHARGE RATES**
    - **3C AMPS (9 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 18.67 WHRS @ 0°C
      - 41.57 WHRS @ 10°C
      - 64.38 WHRS @ 23°C
    - **2C AMPS (6 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 46.40 WHRS @ 0°C
      - 77.54 WHRS @ 10°C
      - 102.80 WHRS @ 23°C
    - **C AMPS (3 mA/cm²) DISCHARGE RATE TO 3.0 VOLT CUT-OFF**
      - 71.50 WHRS @ 0°C
      - 102.55 WHRS @ 10°C
      - 120.57 WHRS @ 23°C

EAGLE PICHER
Technologies, LLC

LEO/GEO Tests

EAGLE PICHER Technologies, LLC

Utilization Levels for EPT Li-ion

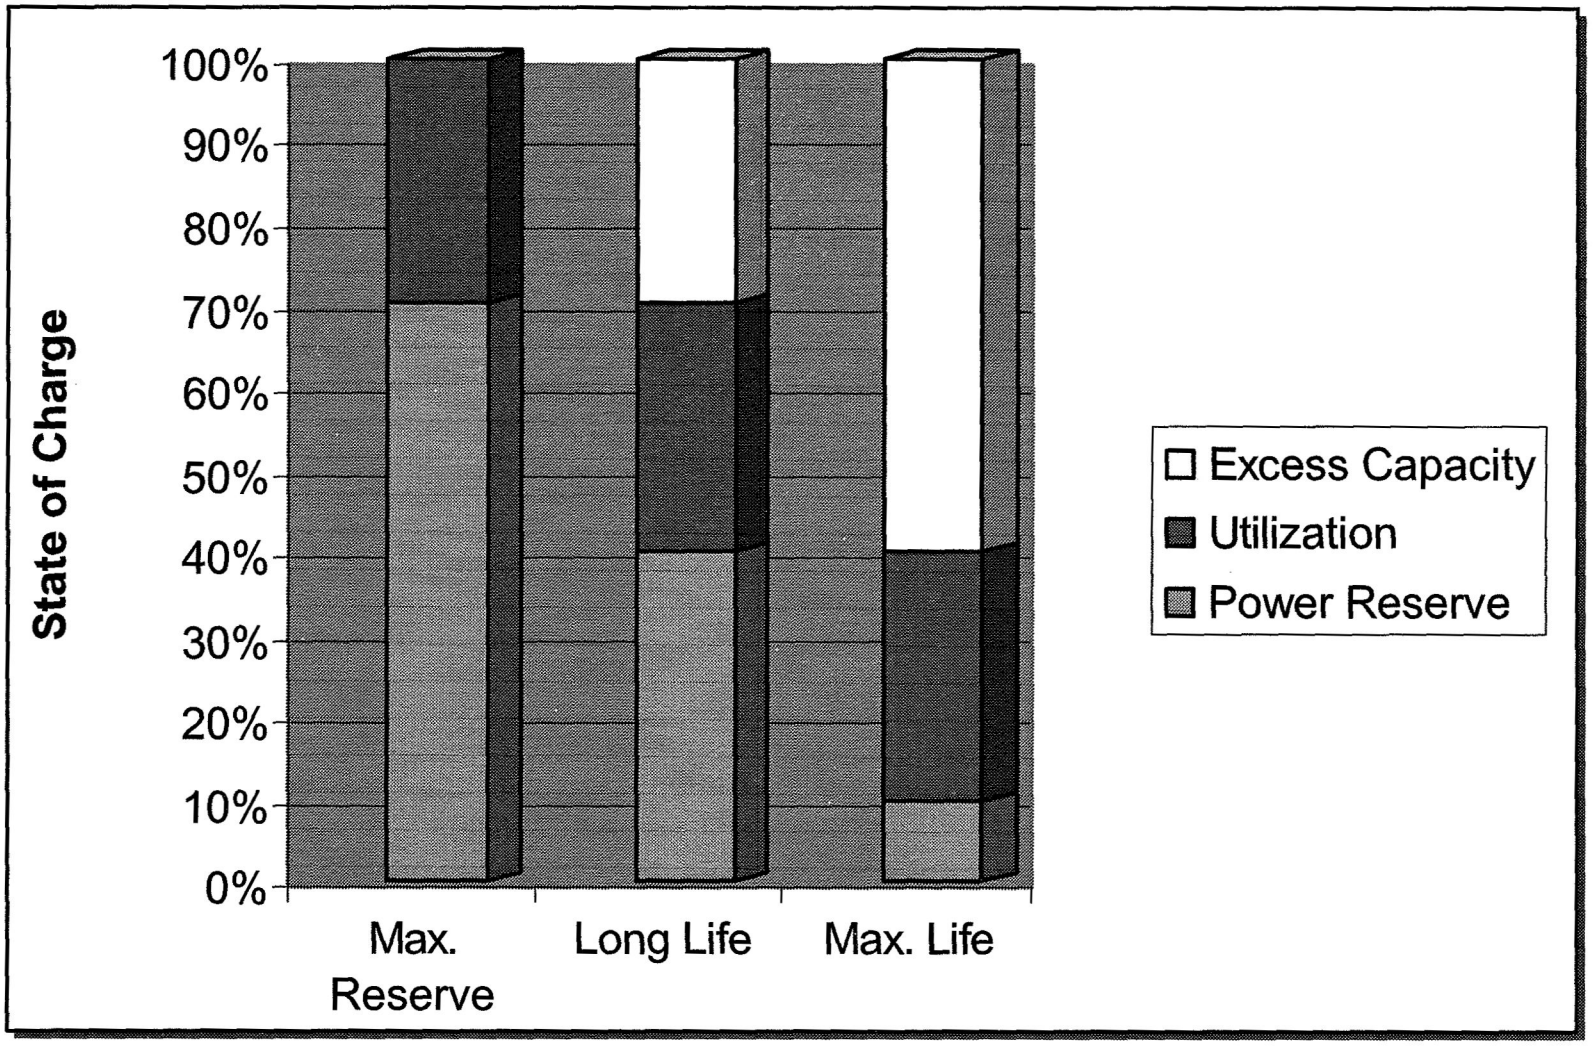

EAGLE PICHER Technologies, LLC

LEO Testing

- 25% DOD
- 100% SOC

- C/4 Charge
- C/2 Discharge

EAGLE PICHER Technologies, LLC

LEO Testing

- 25% DOD
- 100% SOC

- C/4 Charge
- C/2 Discharge

- 4850 Cycles Accumulated

- Projected to 13000 Cycles

EAGLE PICHER Technologies, LLC

Completed an Projected Cycle Life

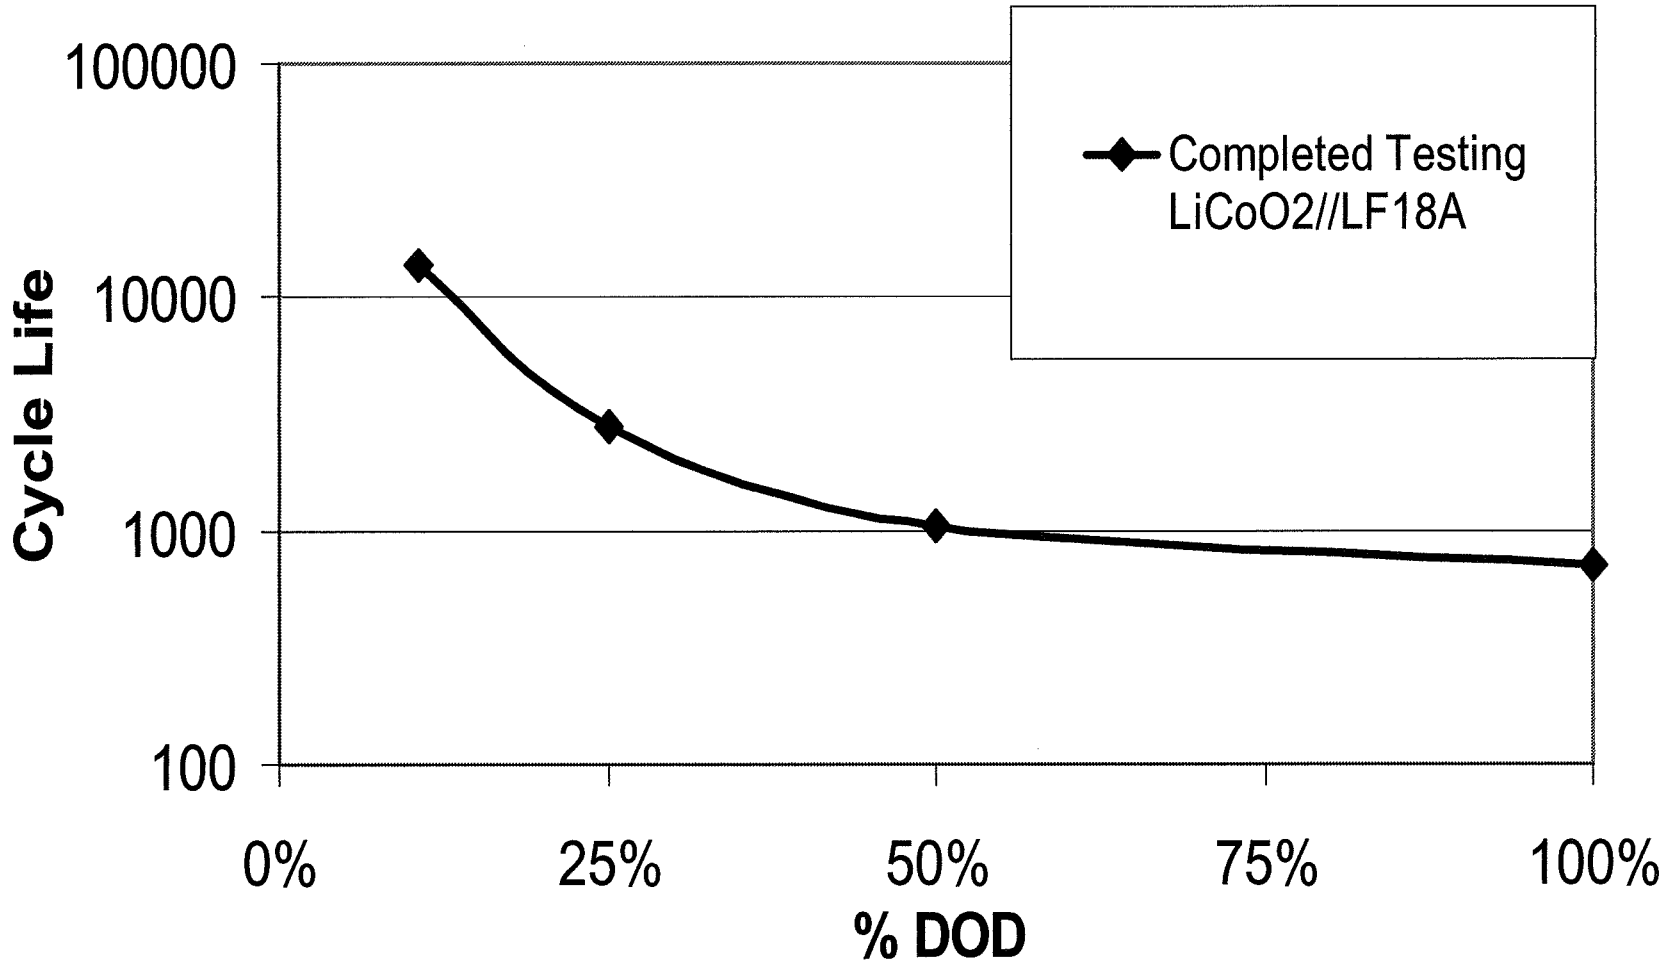

EAGLE PICHER Technologies, LLC

Completed an Projected Cycle Life

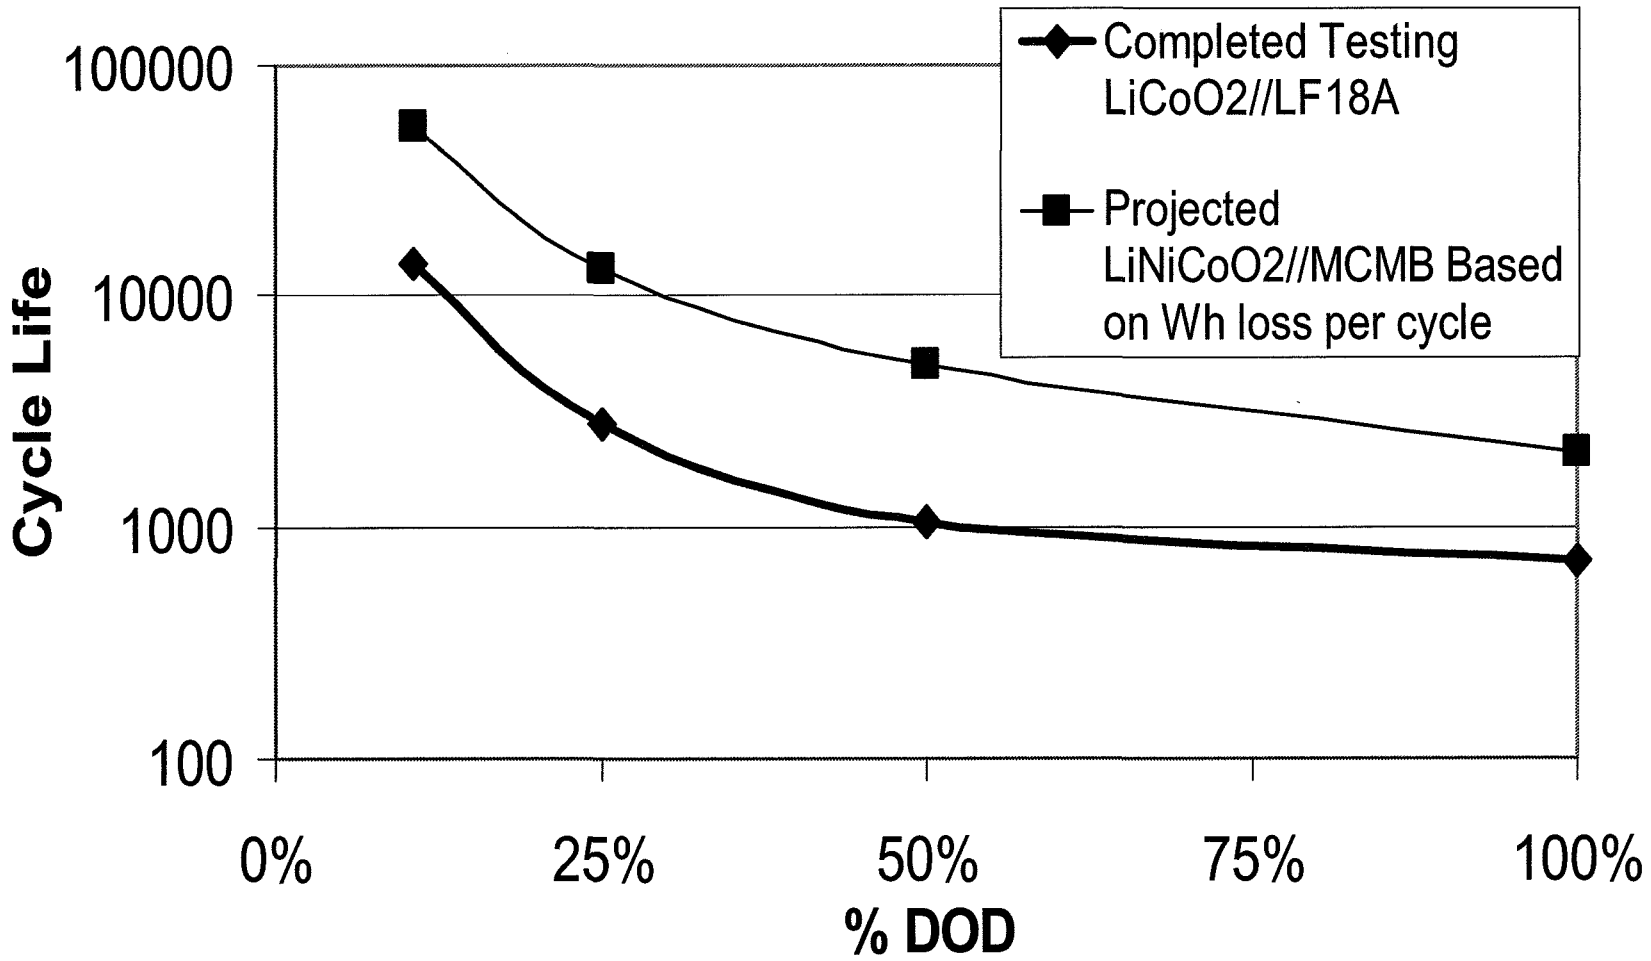

EAGLE PICHER Technologies, LLC

IRAD GEO Battery Development

- Battery Design
- Thermal Characteristics
- Battery Life Data

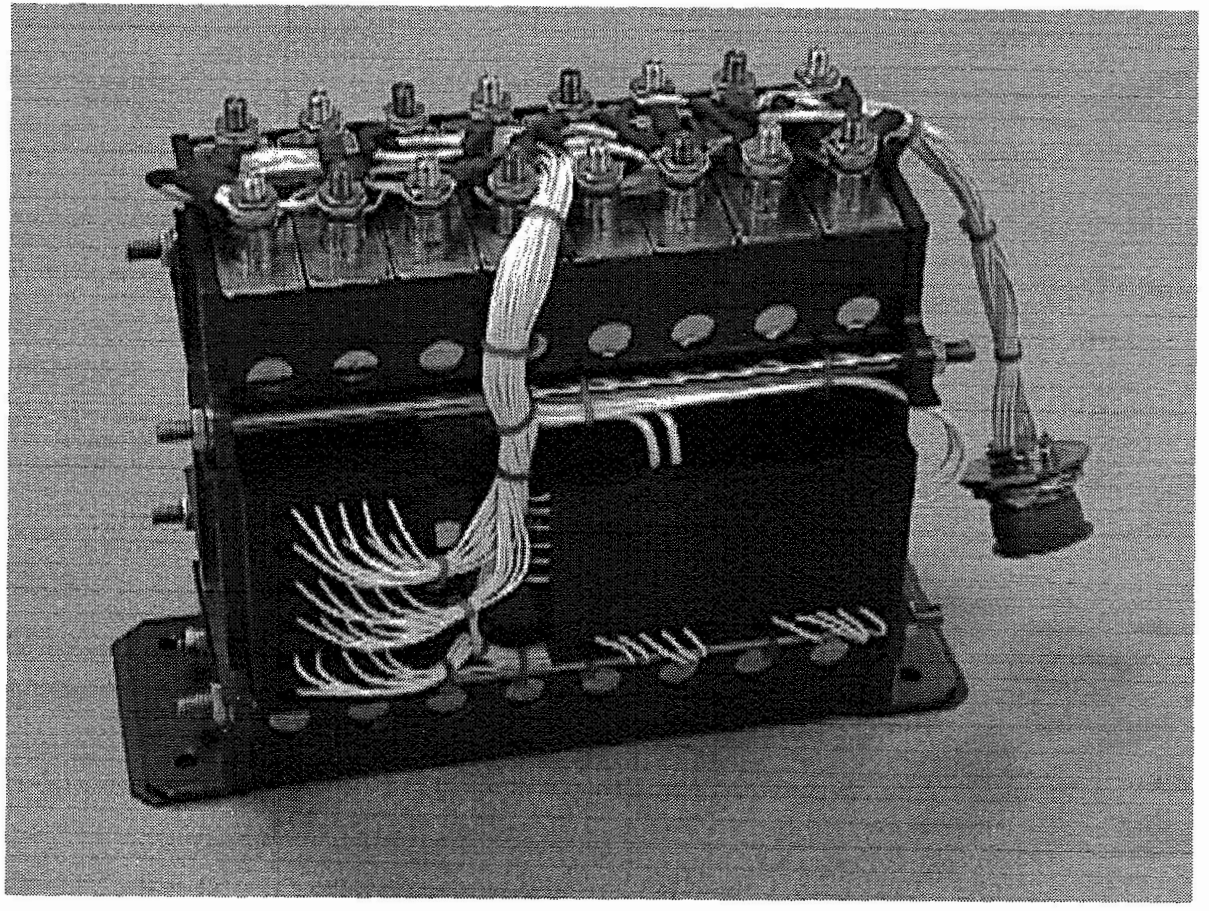

EAGLE PICHER Technologies, LLC

Battery Structure & Design

- **SLB-16001 battery**
- **Comprised of eight SLC-16002 cells**
- **Structural & thermal hardware includes:**
  - Aluminum alloys
  - RTV's
  - Thermal transfer enhancement materials
  - High strength fastening systems
  - Electrically neutral architecture

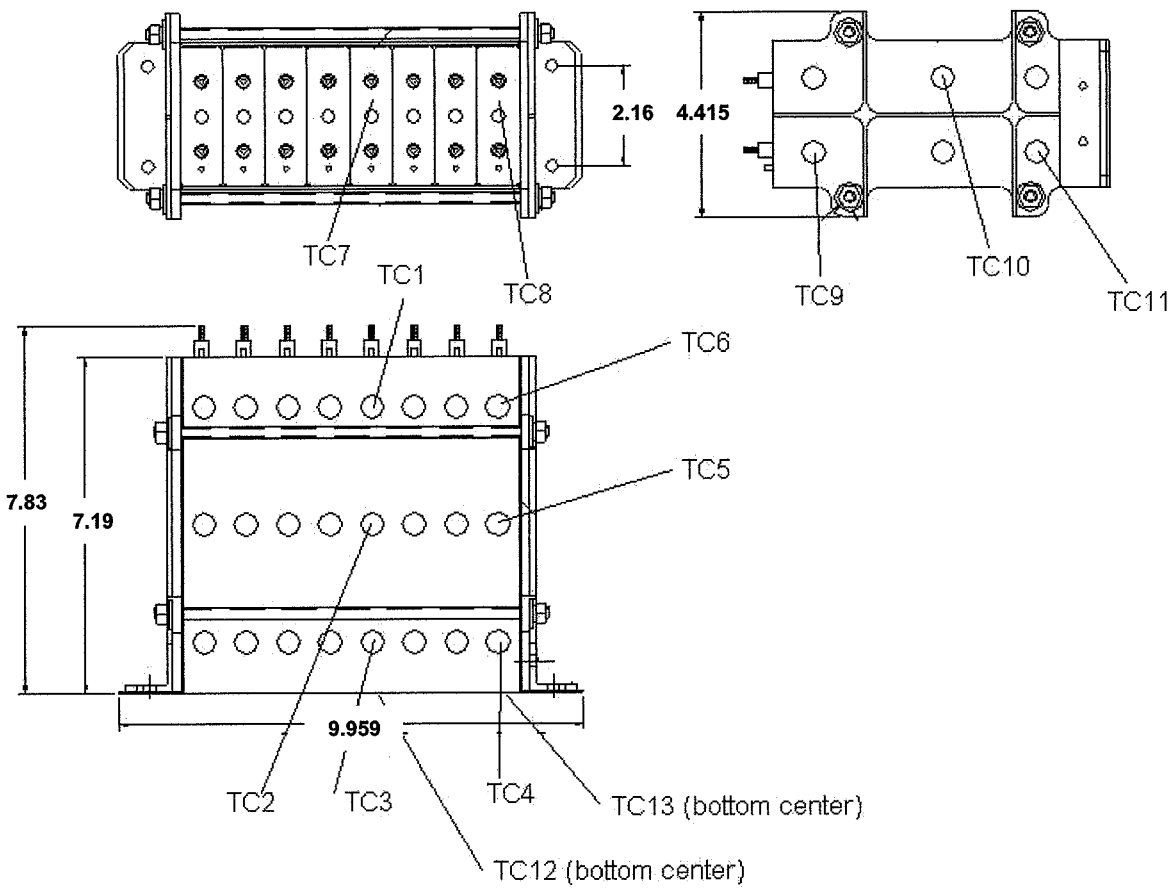

EAGLE PICHER Technologies, LLC

Series String Battery Testing

- **Abbreviated GEO Season for initial series battery testing**
  - 7.5%DOD
  - 15%DOD
  - 30%DOD
  - 60%DOD
  - 30%DOD
  - 15%DOD
  - 7.5%DOD
- **30 minute rest between cycles**

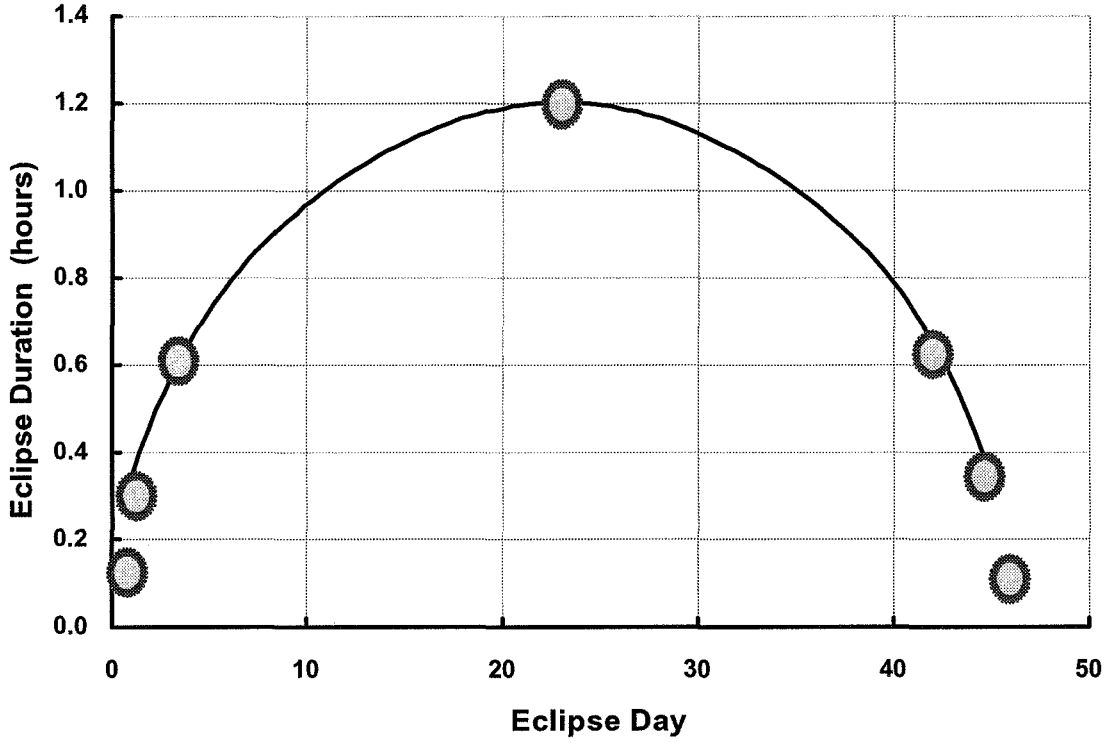

EAGLE PICHER Technologies, LLC

Thermal Characteristics of Battery

- Low variance in DT leads to longer life
- High rate and High Cycle Life applications Higher Importance
- 2°C maximum temperature variance throughout entire battery during full cycle

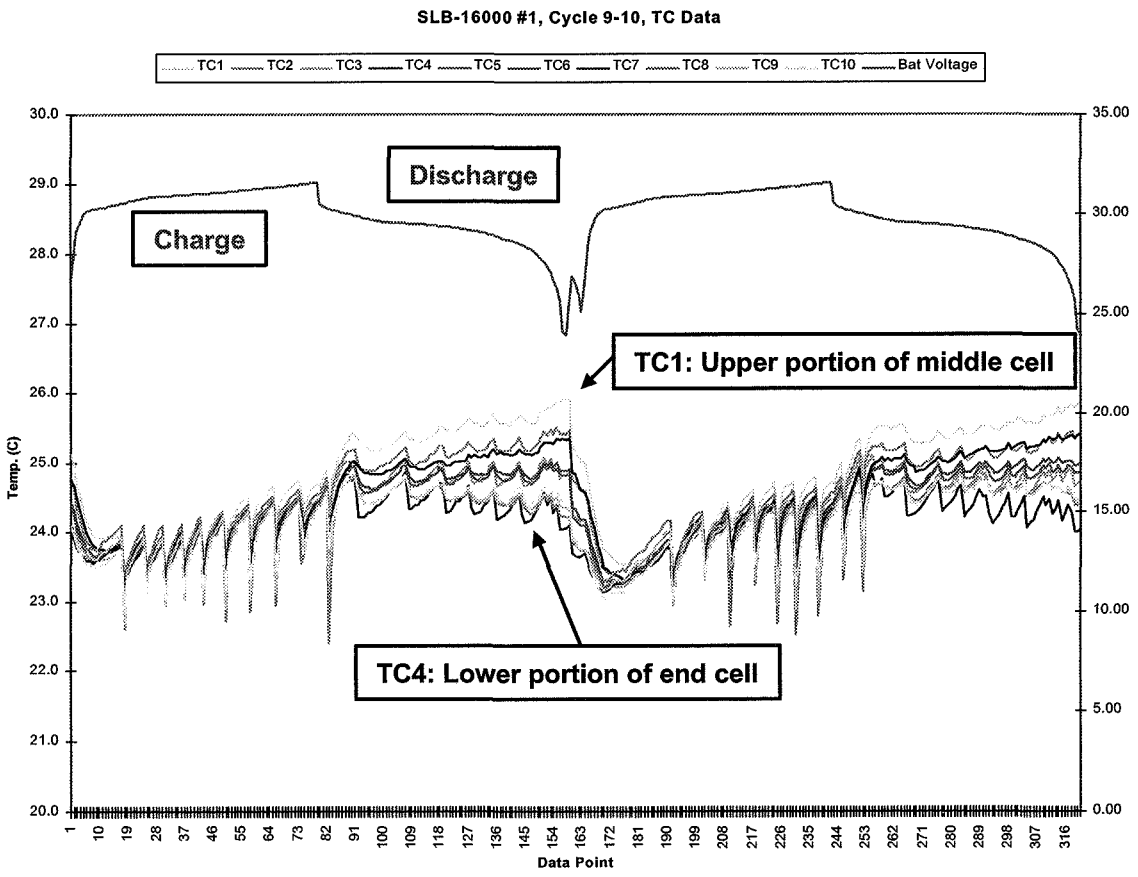

EAGLE PICHER Technologies, LLC

End of Discharge Voltage 60% DOD Operation

- Historical data has shown End of discharge voltage linear until approximately 3.2 volts/cell

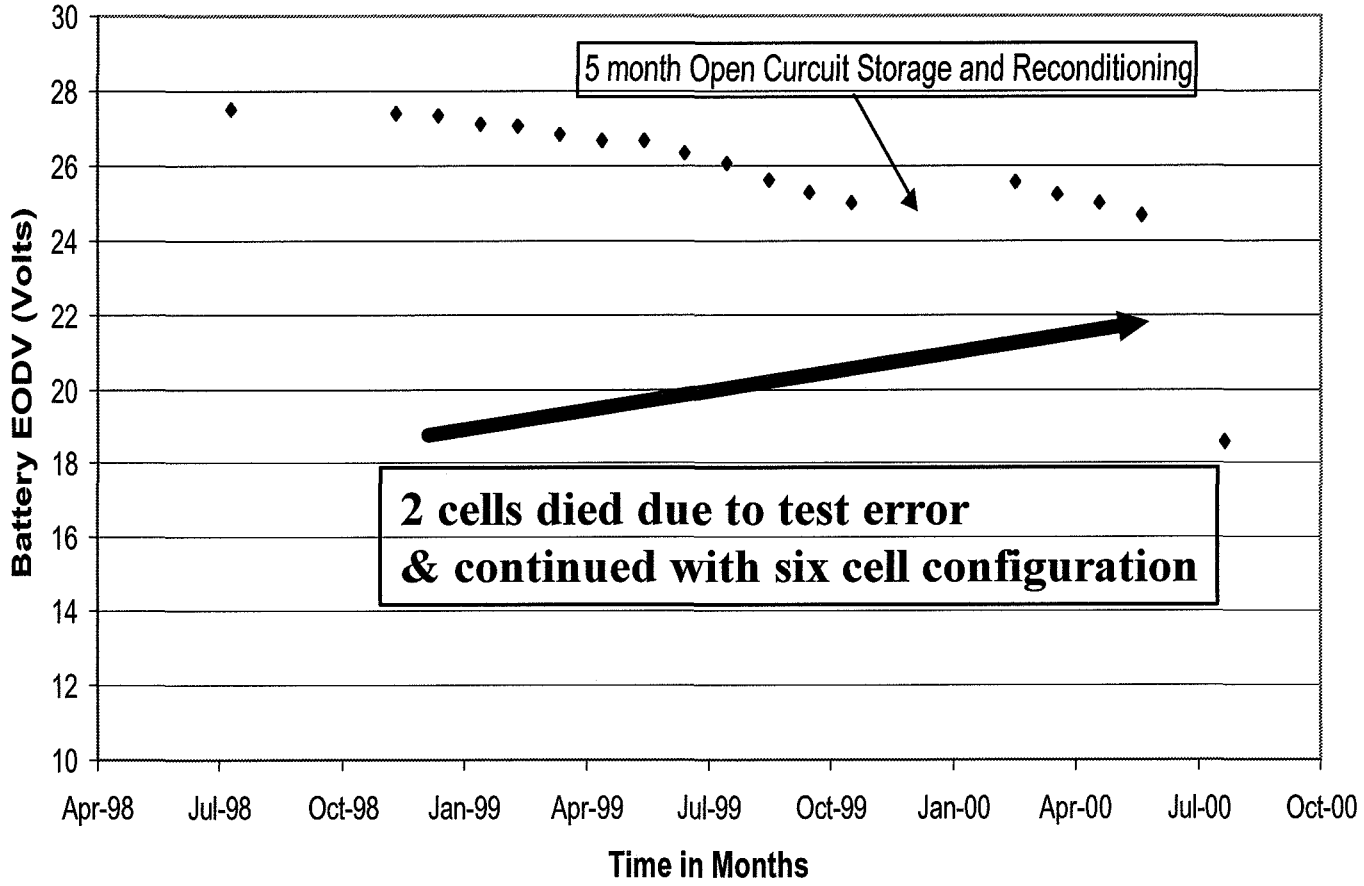

EAGLE PICHER Technologies, LLC

End of Discharge Voltage 60% DOD Operation

- **Historical data has shown End of discharge voltage linear until approximately 3.2 volts/cell**
- **Results**
  - 101 Abb. GEO Seasons (>808 Cycles w/o electronics)
  - Represents 18 seasons in GEO
  - 9 years in orbit

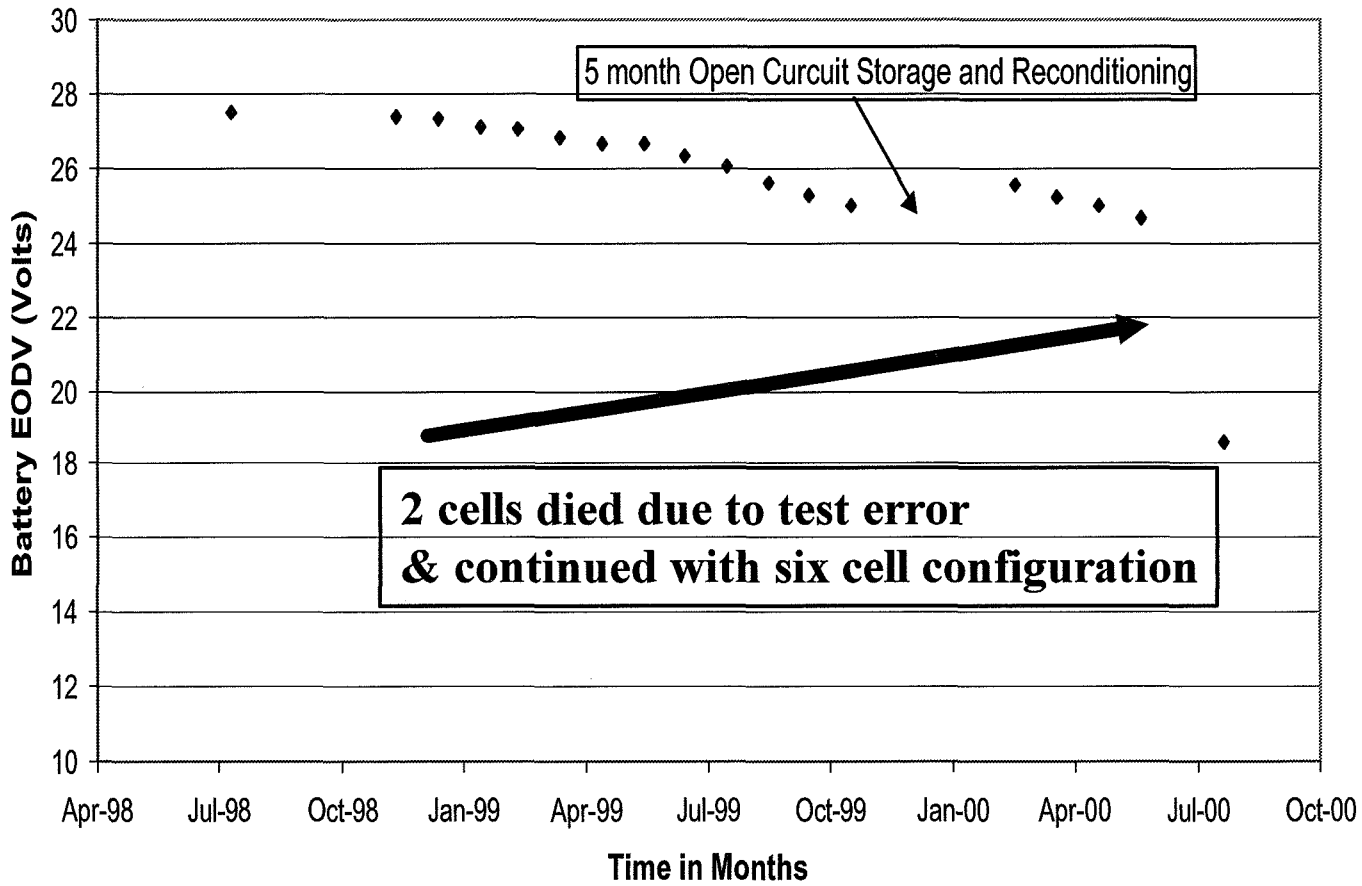

EAGLE PICHER Technologies, LLC

Conclusions

- Chemistry changes have shown significant increases in
  - Energy Density/ Specific Energy
  - Rate / Temperature Capability
  - Life

EAGLE PICHER Technologies, LLC

Conclusions

- ✦Chemistry changes have shown significant increases in
  - ✦Energy Density/ Specific Energy
  - ✦Rate / Temperature Capability
  - ✦Life

- ✦GEO Battery Cycled over 2.5 years w/o individual cell control or bypass electronics

EAGLE PICHER Technologies, LLC

Conclusions

- ✦Chemistry changes have shown significant increases in
  - ✦Energy Density/ Specific Energy
  - ✦Rate / Temperature Capability
  - ✦Life

- ✦GEO Battery Cycled over 2.5 years w/o individual cell control or bypass electronics
- ✦Acceptable performance demonstrated during safety testing (Jim DeGruson 0830 Thursday)

Characterization of Electrolytes by Computer Modeling

Brandy Moore,
Richard Whiteley,
James Currie and
Kevin Johnson

Pacific University
Forest Grove, Oregon

S15/CP/M/Hyd
2001117820
26 Apr 528042

Background of Lithium Battery Technology

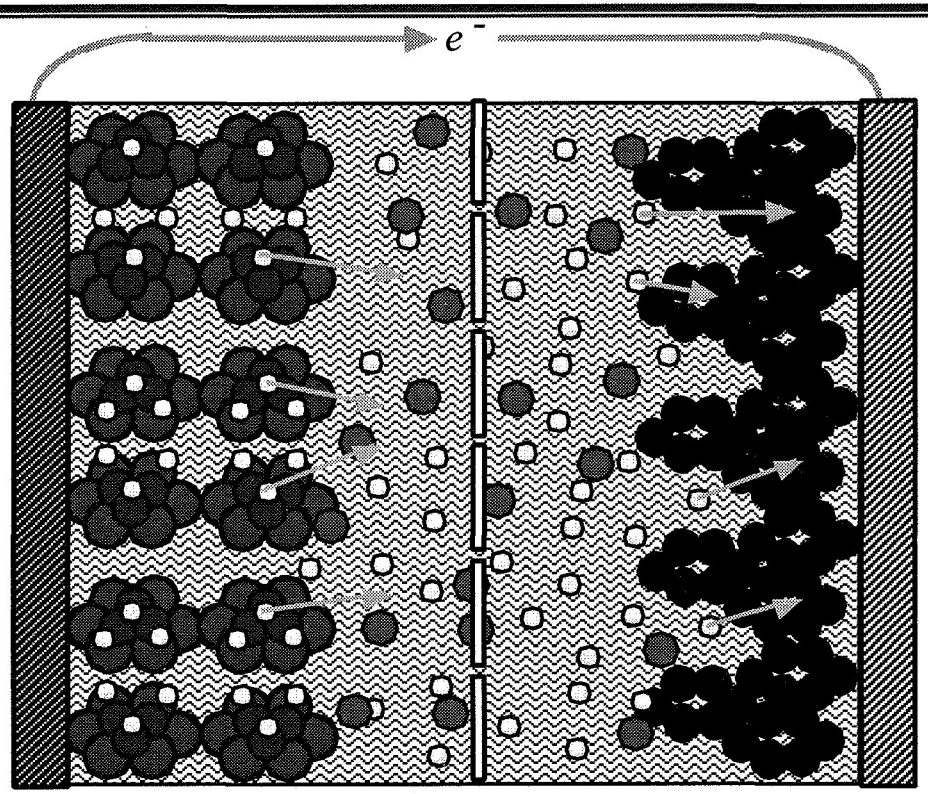

$$LiNiO_2 \longrightarrow xLi^+ + Li_{1-x}NiO_2 + xe^-$$

$$C_6 + yLi^+ + ye^- \longrightarrow Li_yC_6$$

Electrolyte Requirements

- The Ideal Solvent
  - Large liquid range
  - Low viscosity
  - Ability to solvate ions
  - Minimal toxicity
  - Large working voltage

Status Quo for Solvents

						
M.P.	**4.6°C**	**-43**	**+39**	**-49**	**-43**	**-109**
B.P.	**91°C**	**126**	**248**	**240**	**203**	**66**
Viscosity	**0.59cP**	**0.75**	**1.86 ***	**2.5**	**1.75**	**0.48**
Dielectric Constant e	**3.12**	**2.82**	**89.6 ***	**64.4**	**39**	**7.75**
****Solution Conductivity**	**11.00 mS/cm**	**5.00**	**6.97**	**5.28**	**10.62**	**12.87**

* At 40°C

** 1 M LiAsF

The Problem

- The electrolyte (solvent) can be reduced in lieu of Li^+ ion reduction / intercalation.
- This causes significant, irreversible capacity loss on the first charge cycle.
- It can also lead to considerably more capacity loss over long periods.
- The S.E.I. or P.E.I. that forms with electrolyte decomposition mitigates further decomposition of the electrolyte, but this S.E .I. or P.E.I. also inhibits charge transfer at the anode and this li mits the *power* of the Li Ion cell.

How the SEI works

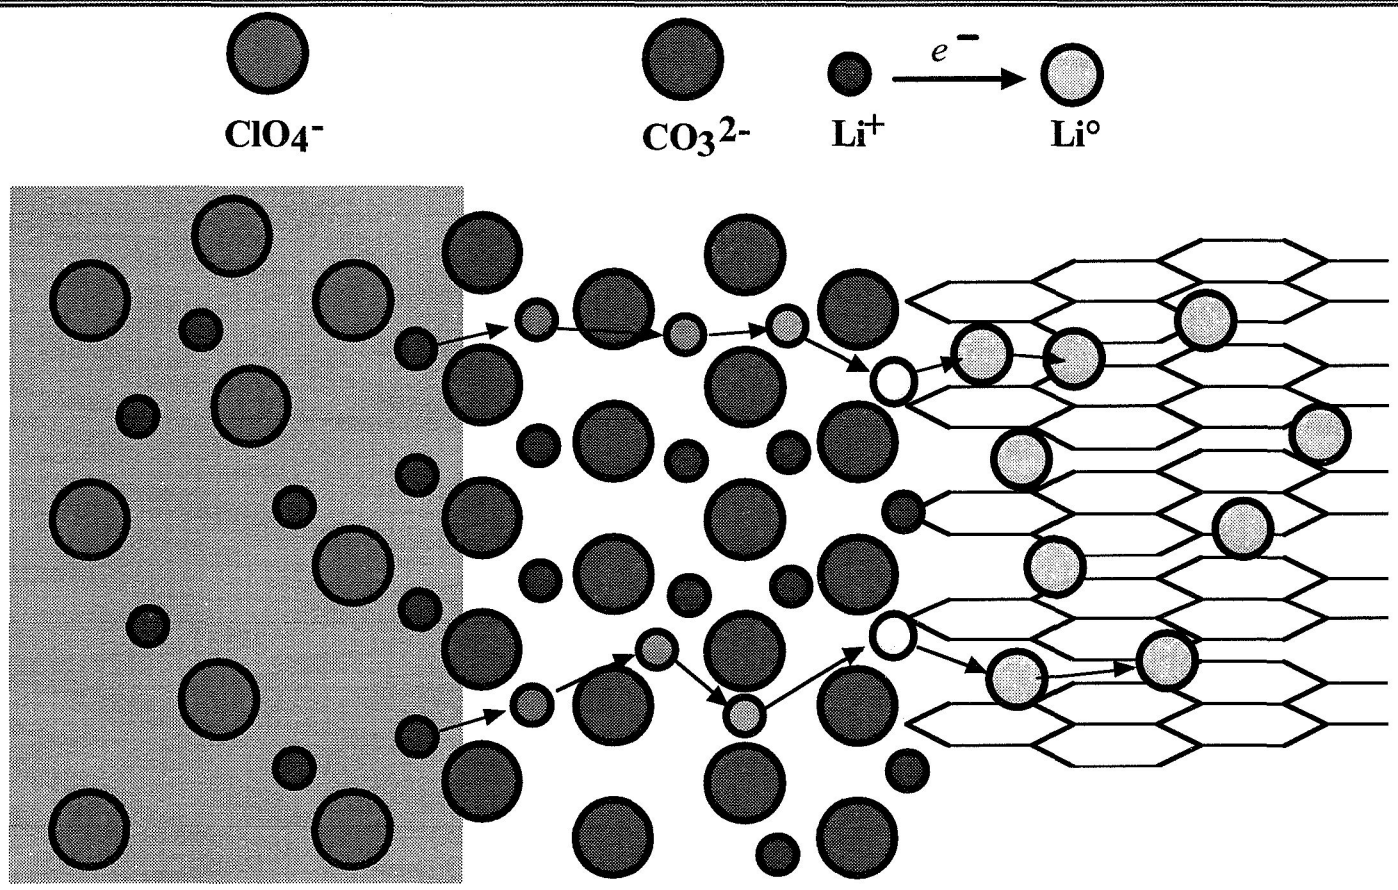

Questions

- Can the behavior of electrolyte solvent be predicted through computer modeling?
  - What *molecular* properties of a solvent make it susceptible to electrochemical degradation?
  - What properties of a solvent make it form a S.E.I. or P.E.I.?
  - Can a solvent be designed that will not be oxidized or reduced under charge or discharge conditions?
  - If not, can a solvent be designed that will form a thin, robust S.E.I.?

Generally Accepted Behavior of Alkyl Carbonates

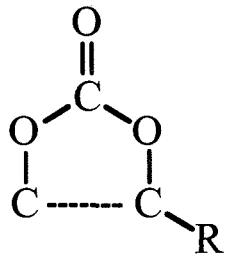

- They strongly coordinate Li^+ ions, probably 4:1[1,2]
- There is an electron transfer to the electrolyte well anodic of Li^+ ion reduction[3]
- Subsequent electron transfers are likely[4,5]
- *After* the reduction process, these Alkyl Carbonates decompose to: [4,6,7] polymerization products, $CH_2{=}CHR_{(g)}$, $CO_{2(g)}$, $(CHROCO_2Li)_{2(s)}$, and $Li_2CO_{3(s)}$
- Chloroethylene Carbonate *also* easily loses Cl^- [8]

Free Energy Map 1

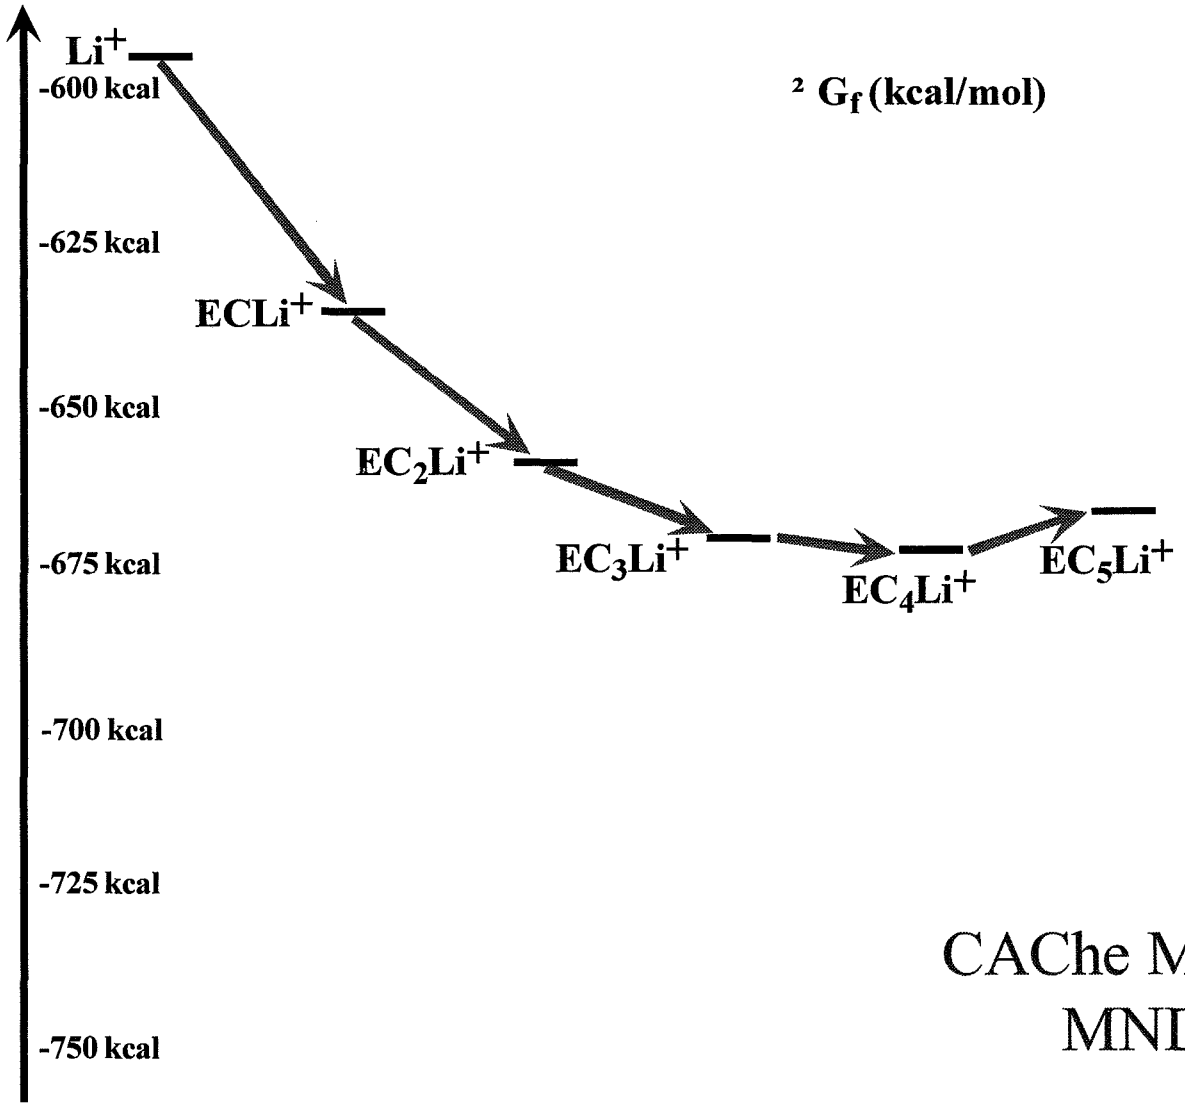

CAChe MOPAC
MNDO

Li^+ Ion Solvation

$$Li^+ + nS \longrightarrow LiS_n^+$$

Solvent	Ave. n	$\alpha_{LiS_{n(mode)}^+}$	$^2G^\circ$ form. kcal/mole
	3.97	0.97	-78
	3.98	0.98	-87
	4.00	1.00	-72
	4.00	1.00	-71
	5.92	0.93	-140

Free Energy Map 2

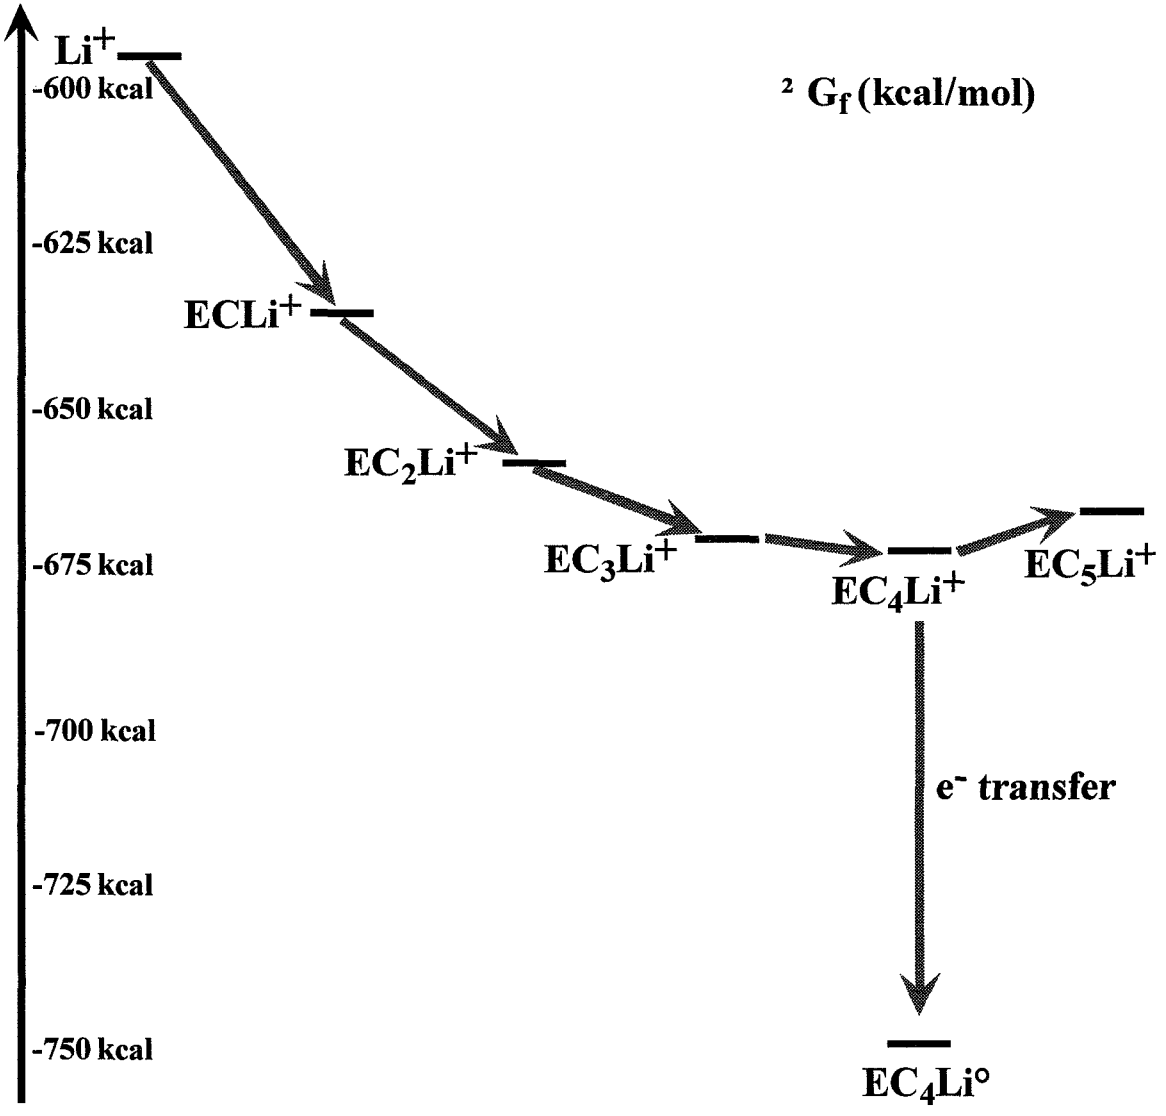

First Reduction Process

$$S + e^- \longrightarrow S^- \qquad LiS_4^+ + e^- \longrightarrow LiS_n^0$$

Solvent	E.A. (S) (eV)	$^2G^\circ_{red}$ (kcal/mole)	E.A. (LiS_4^+)	$^2G^\circ_{red}$
	-0.97	-1.5	1.9	-77
	-1.02	-1.1	1.8	-70
	0.30	-12.5	2.7	-88
	-0.68	-9.3	2.3	-80

Free Energy Map 3

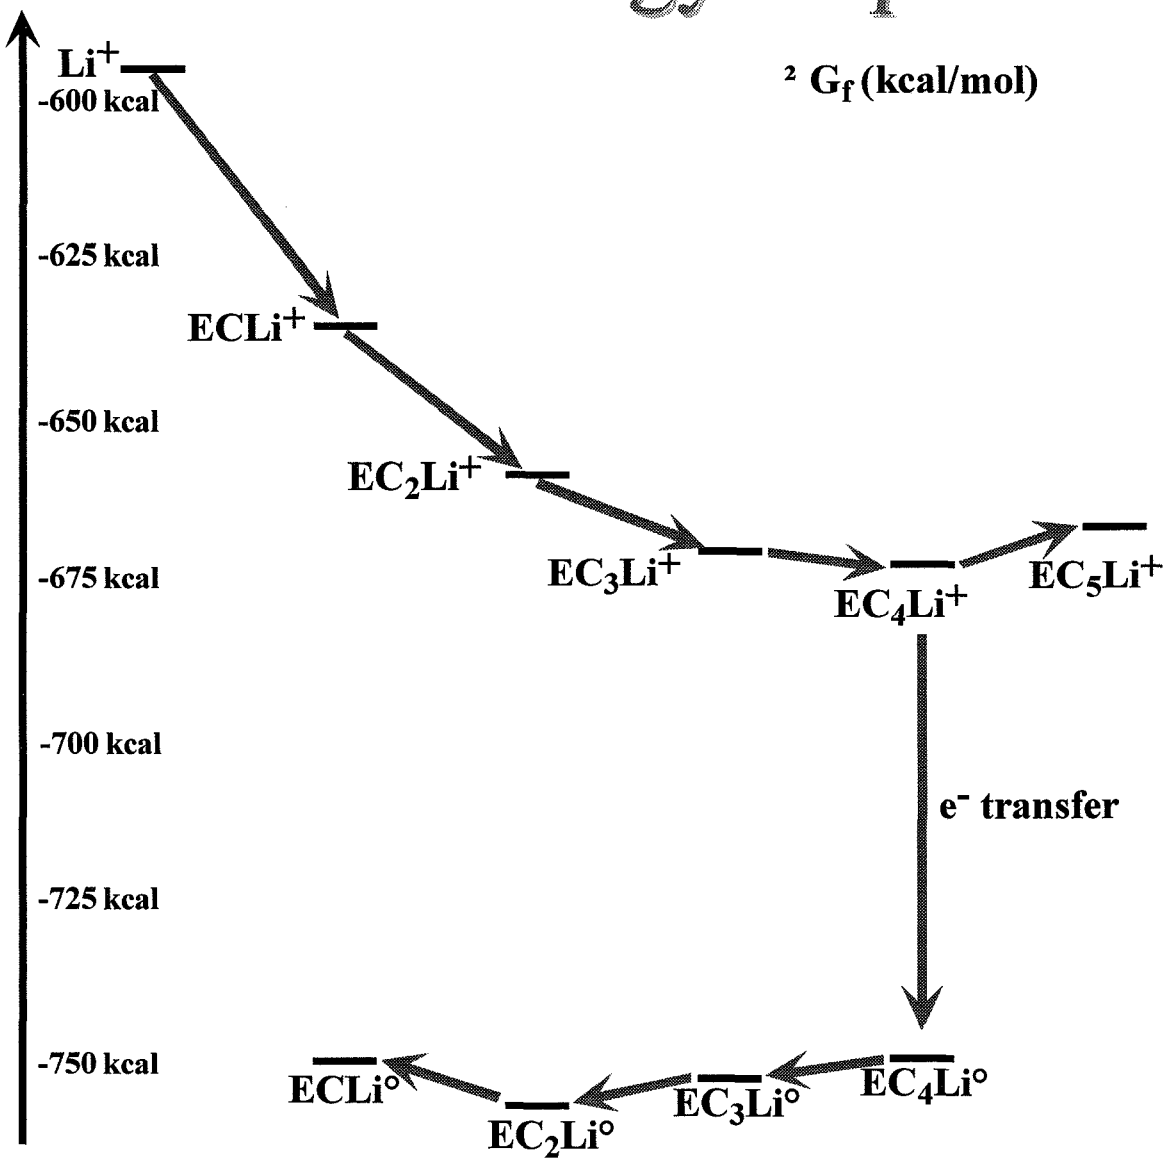

Free Energy Map 4

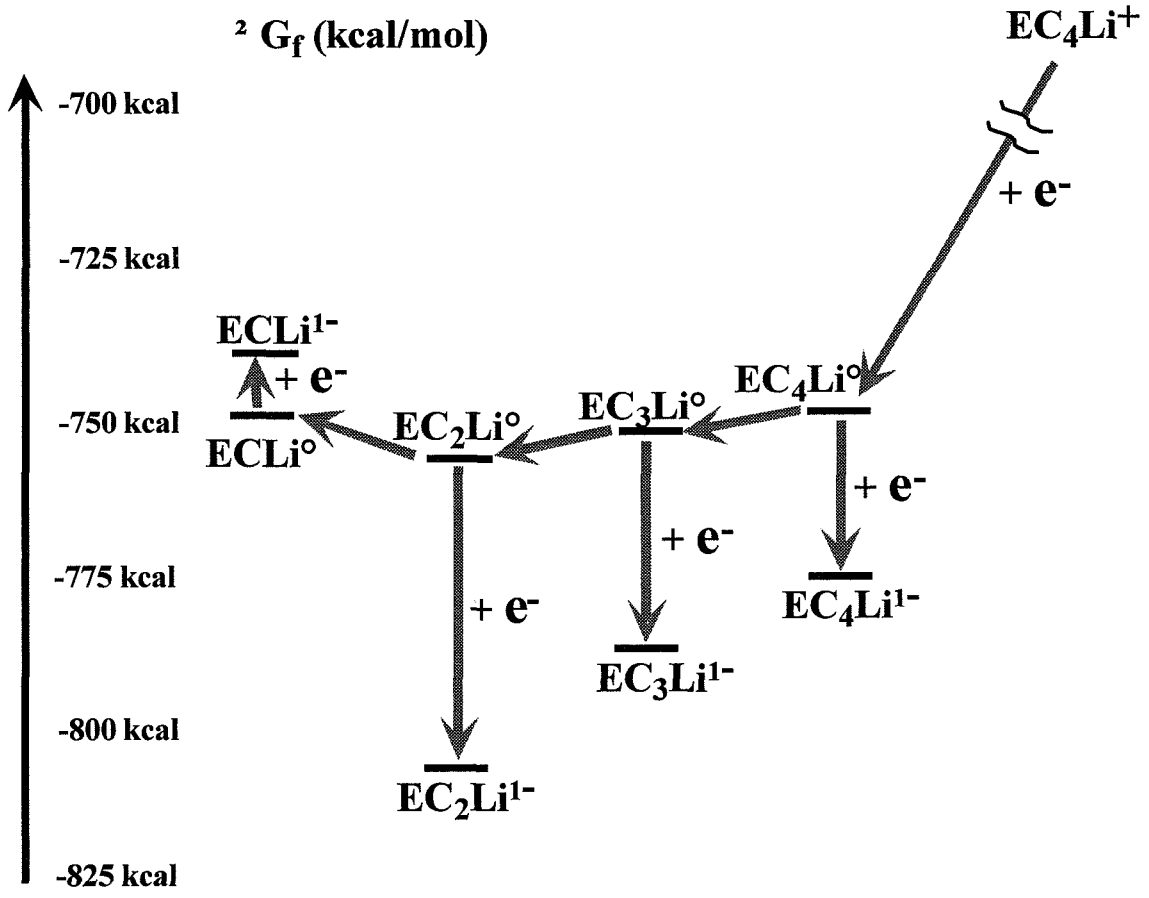

Charge Distribution

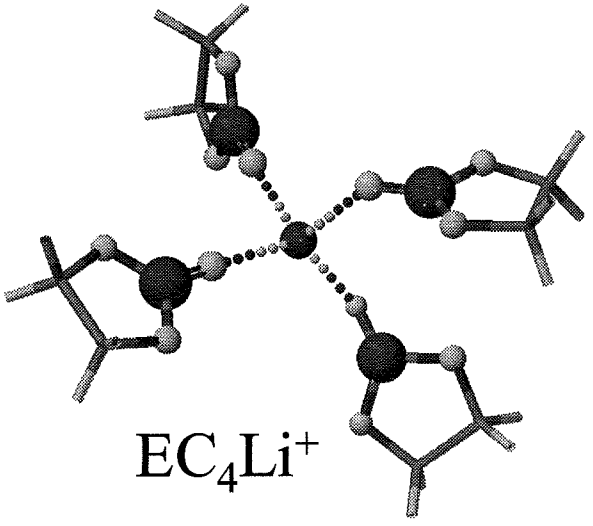

EC_4Li^+

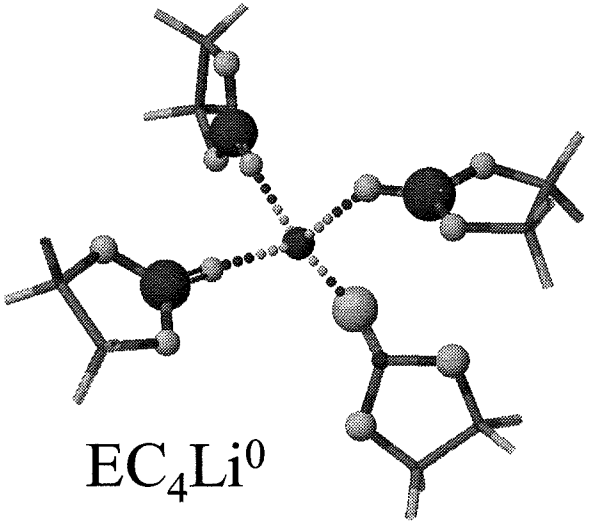

EC_4Li^0

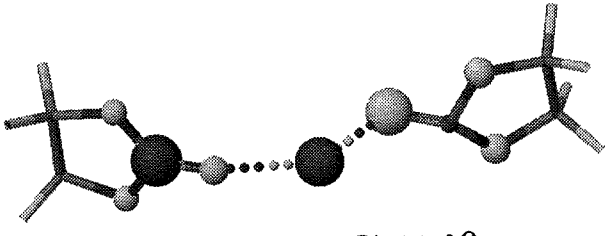

EC_2Li^0

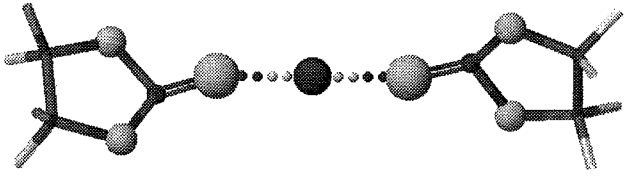

EC_2Li^{1-}

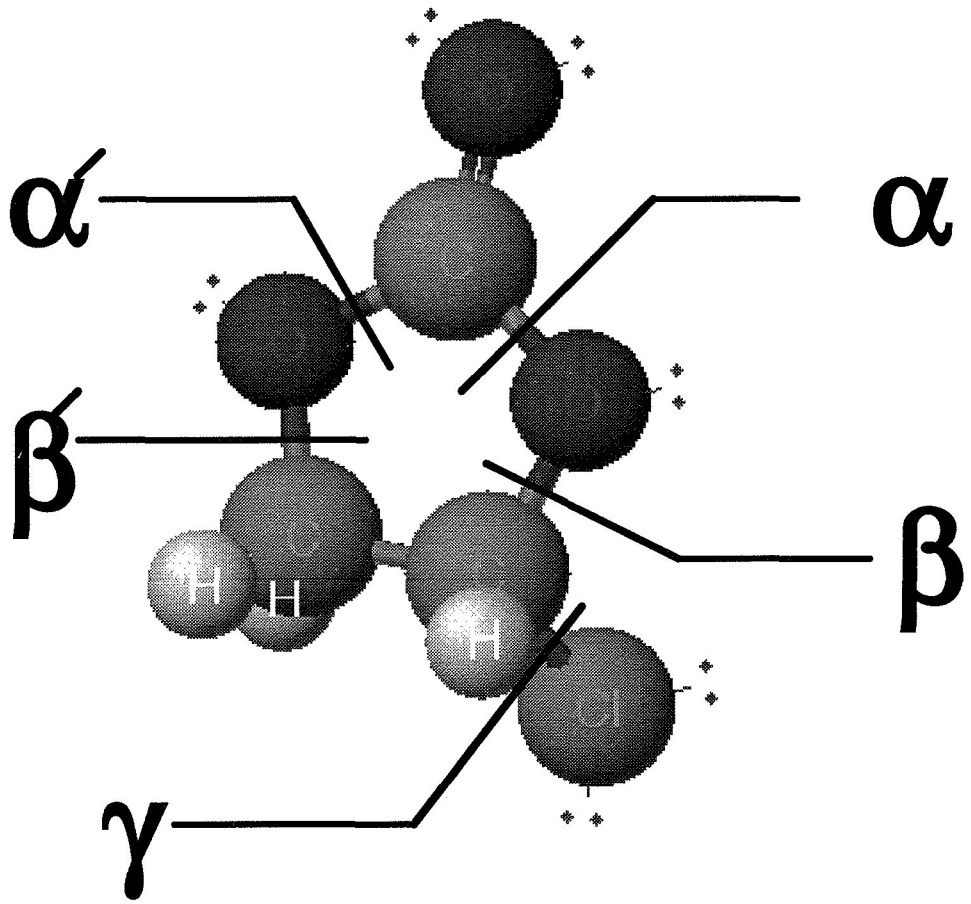
α′
α
β′
β
γ
H
H
H
Cl

?H Normalized Reaction Pathway

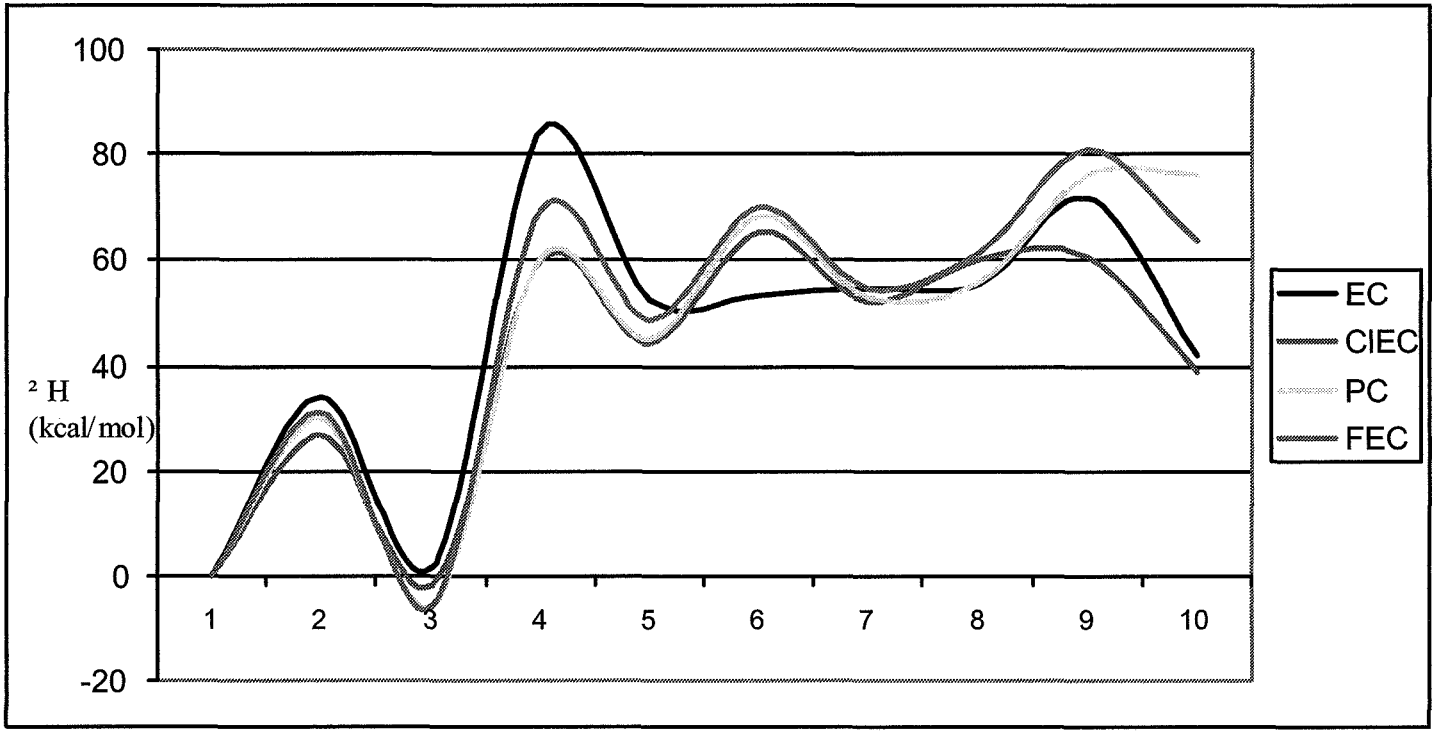

1 doubly reduced w/ 2 solvent molec

2 breaking beta bond (transition state)

3 broken beta bond (opt)

4 addition of 3rd electron

5 optimized structure w/ 3e-

6 breaking other beta bond (transition state)

7 optimized, carbonate formed

8 CH_2=CH-R lost

9 losing solvent molecule (transition state)

10 isolated lithium carbonate

?G Normalized Reaction Pathway

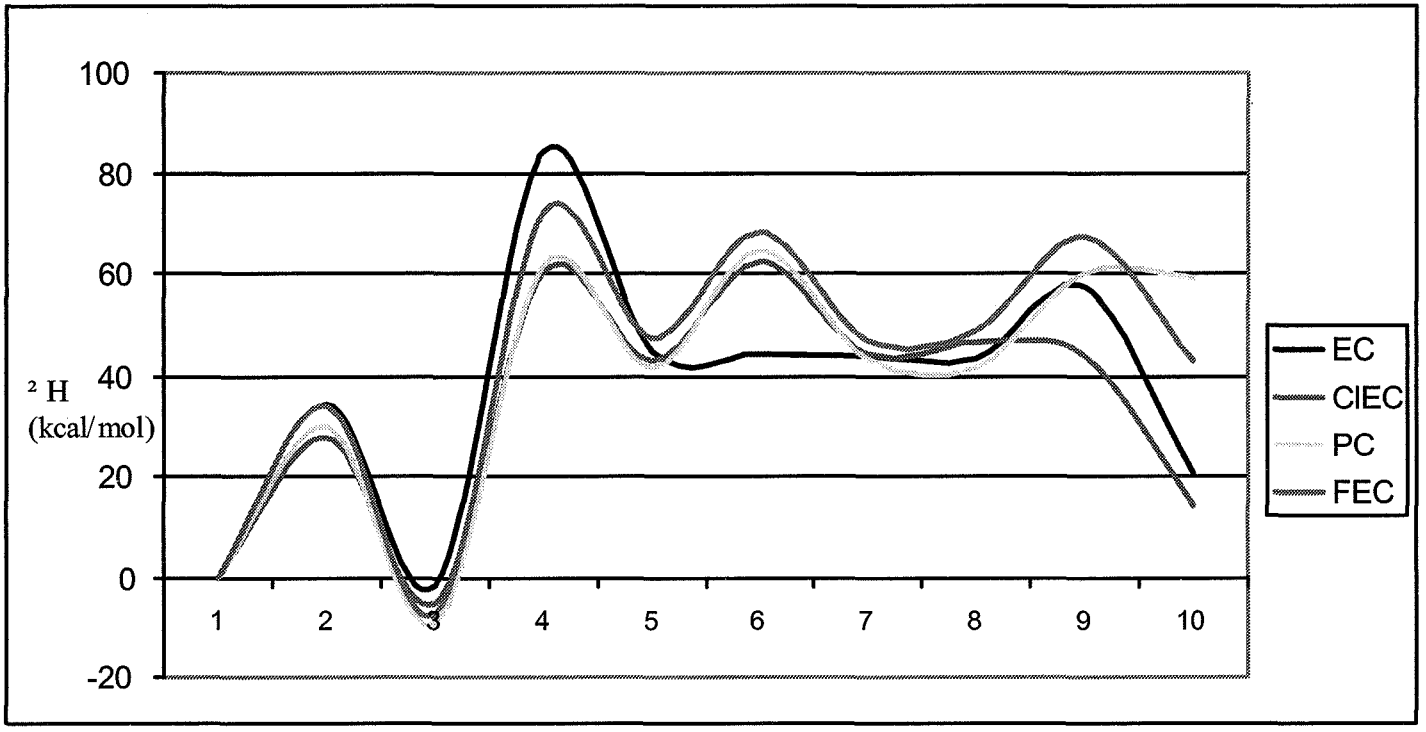

1 doubly reduced w/ 2 solvent molec

2 breaking beta bond (transition state)

3 broken beta bond (opt)

4 addition of 3rd electron

5 optimized structure w/ 3e-

6 breaking other beta bond (transition state)

7 optimized, carbonate formed

8 CH_2=CH-R lost

9 losing solvent molecule (transition state)

10 isolated lithium carbonate

ClEC Reactions Pathways

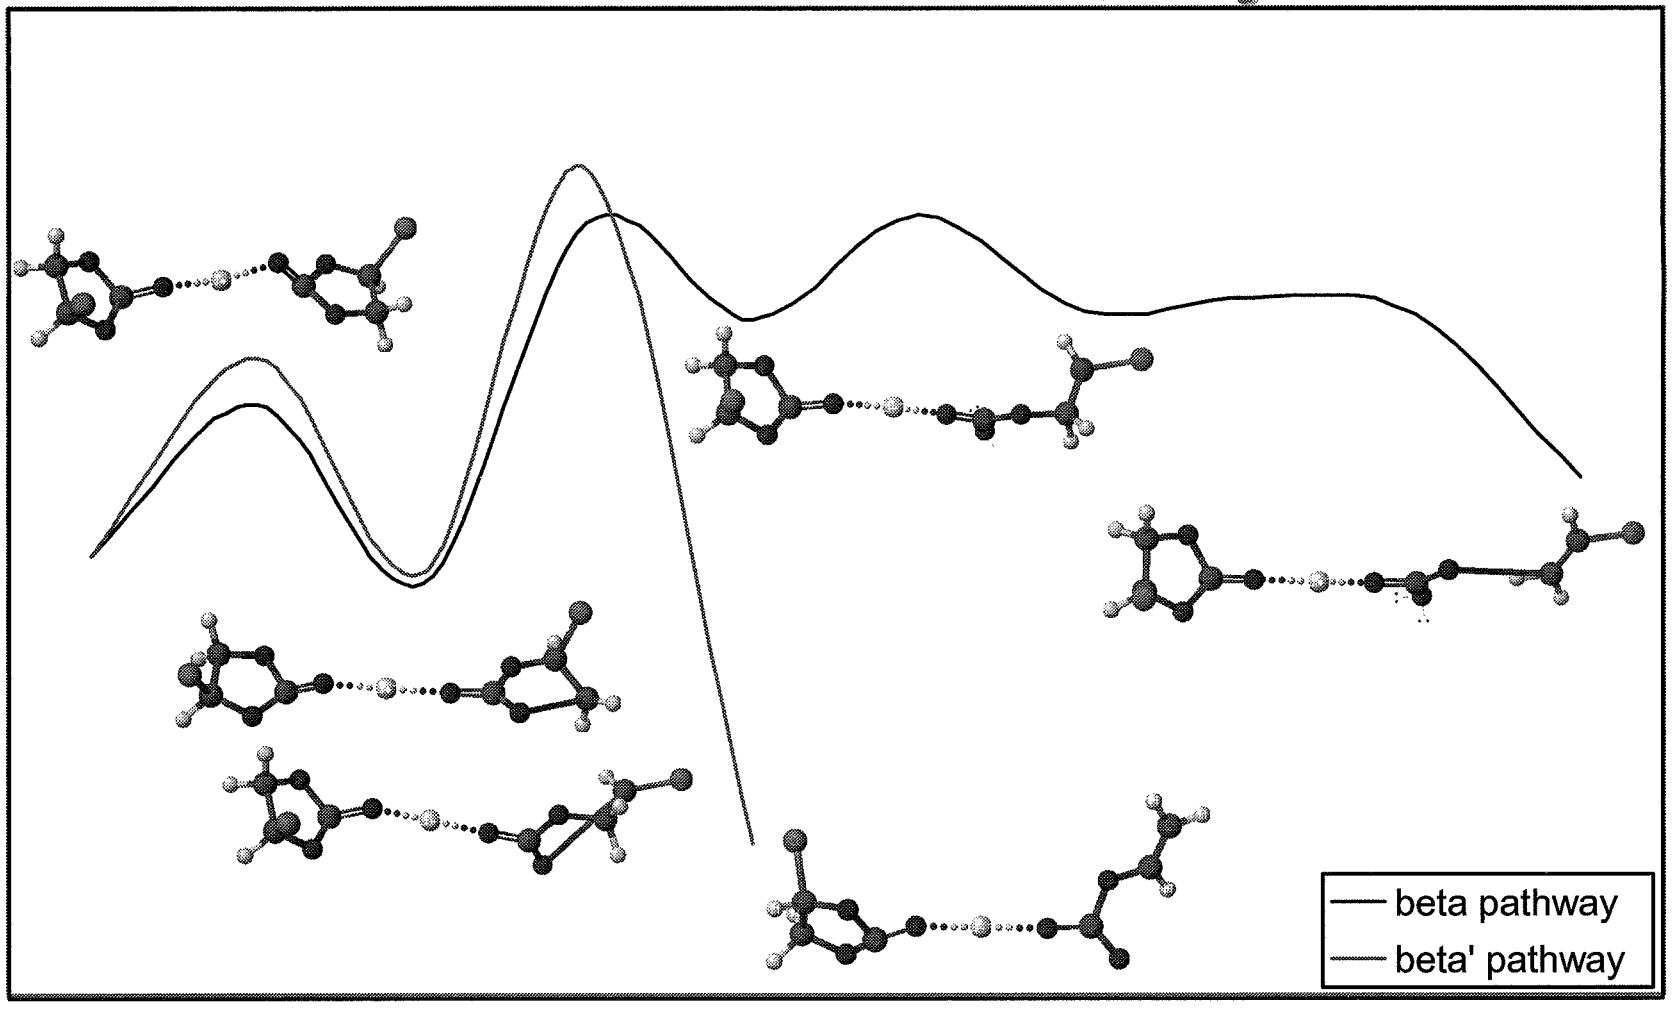

ClEC Reactions Pathways

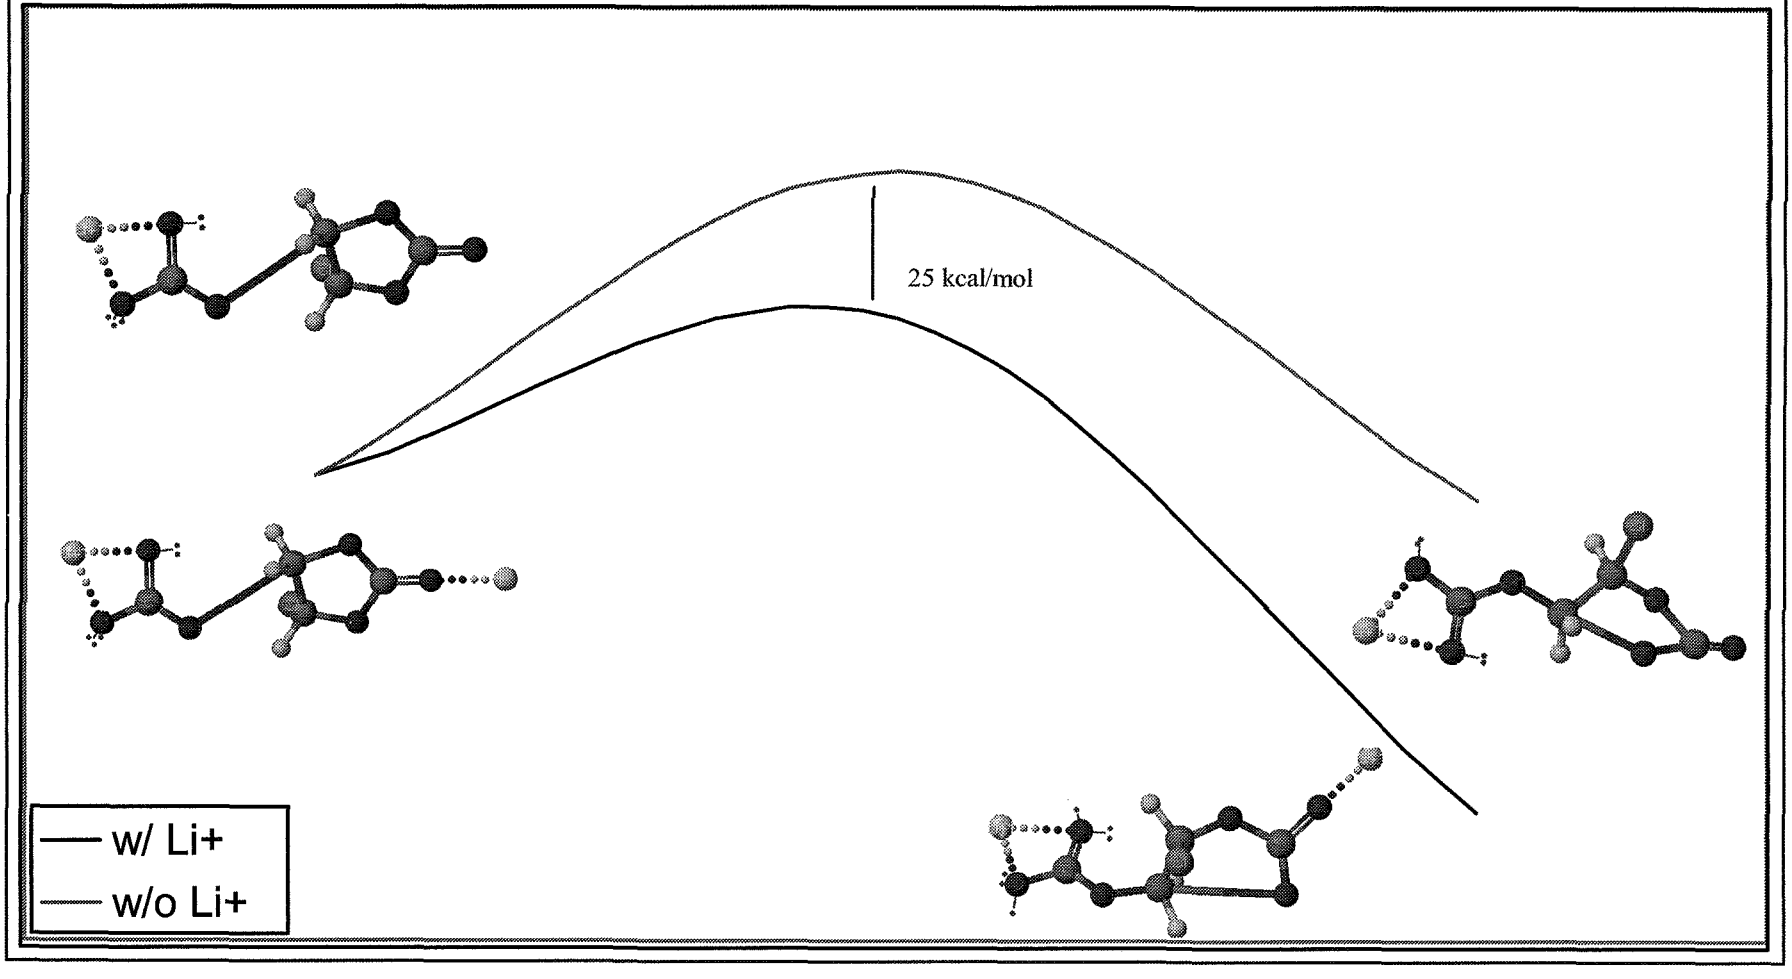

Future Work

- Further analysis of the pathways obtained from this research using *ab initio* calculations and updated parameters in MOPAC.
- Investigate oxidation processes.
- Design and characterize new solvents based on this work.

References

1. R. Blint, *J. Electrochem. Soc.*, **142**, 696-702 (1995).
2. S. Hyodo and K. Okabayashi, *Electrochim. Acta,* 34, 1551-1556 (1989).
3. S. Mori, H. Asahina, H. Suzuki, A. Yonei, and K. Yokoto, *J. Power Sources*, 68, 59-64 (1997).
4. D. Aurbach, Y. Ein-Ely and A. Zaban, *J. Electrochem. Soc.*, 141, L1-3 (1994).
5. D. Aurbach, A. Zaban, A. Schechter, Y. Ein-Eli, E. Zinigrad and B. Markovsky, *ibid,* 142, 2873-2889 (1995).
6. D. Aurbach, M. Daroux, P. Faguy and E. Yeager, *ibid*, 134, 1611-1619 (1987).
7. D. Aurbach and M. Moskovich, *ibid.*, 145, 2629-2639 (1998).
8. Z.X. Shu, R.S. McMillan, J.J. Murray and I.J. Davidson, *ibid*, 143, 2230-2235 (1996).

Acknowledgements

- Murdock Charitable Trust
- Pacific University

The Lithium Ion Cell

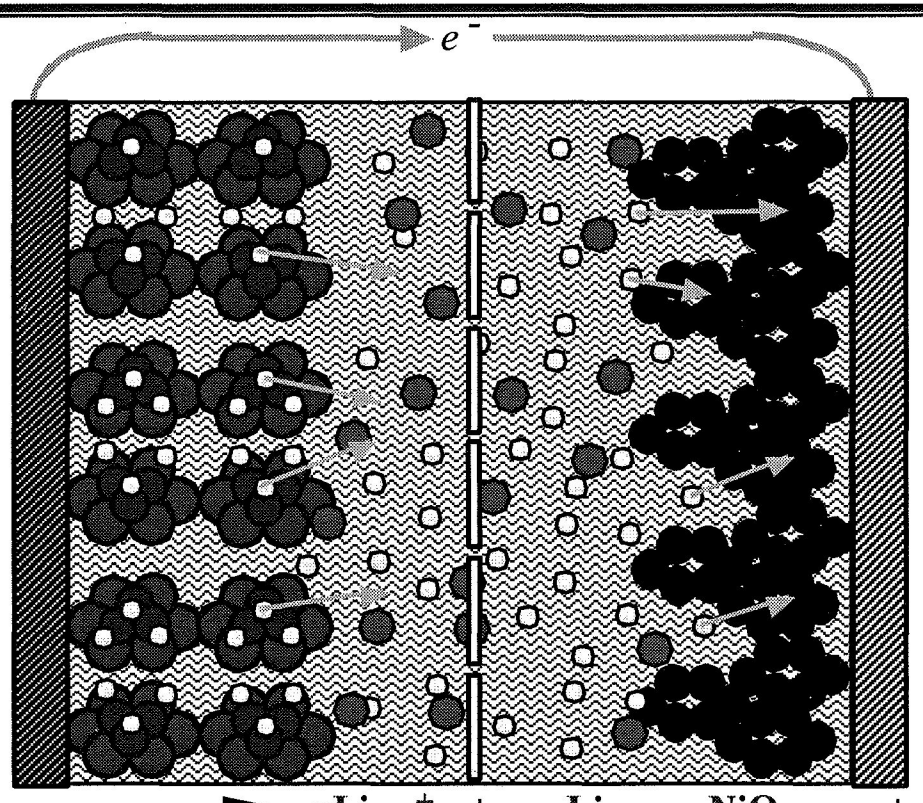

$$LiNiO_2 \longrightarrow xLi^+ + Li_{1-x}NiO_2 + xe^-$$

$$C_6 + yLi^+ + ye^- \longrightarrow Li_yC_6$$

Carbonate Reaction Pathways

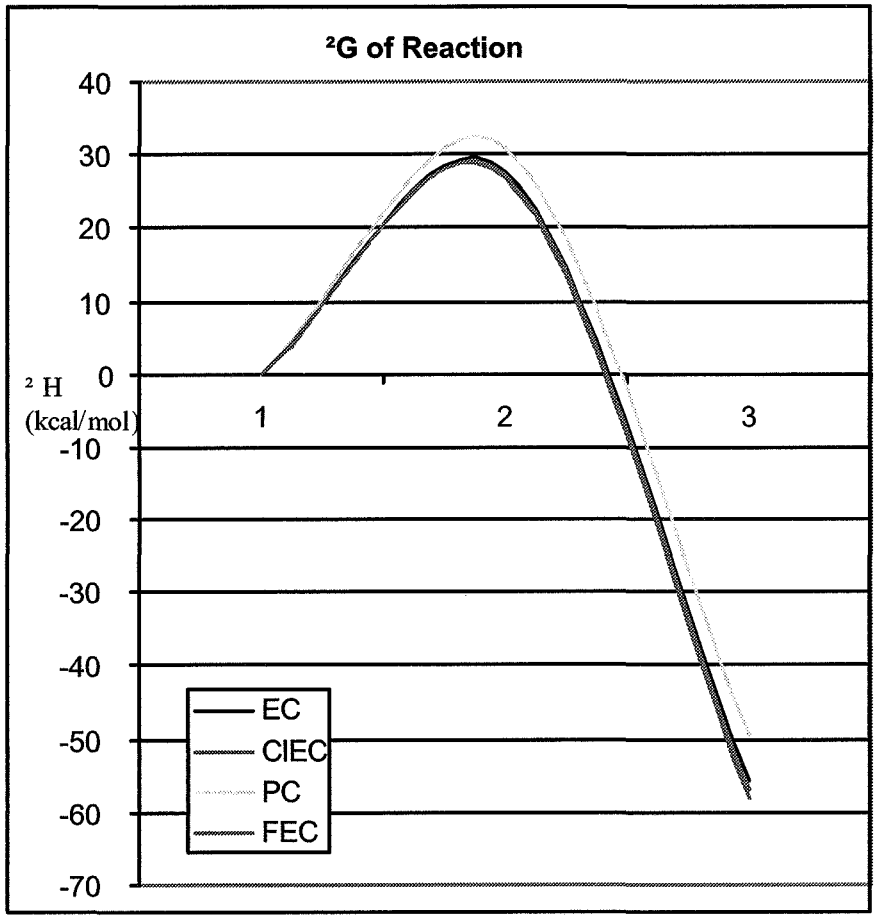

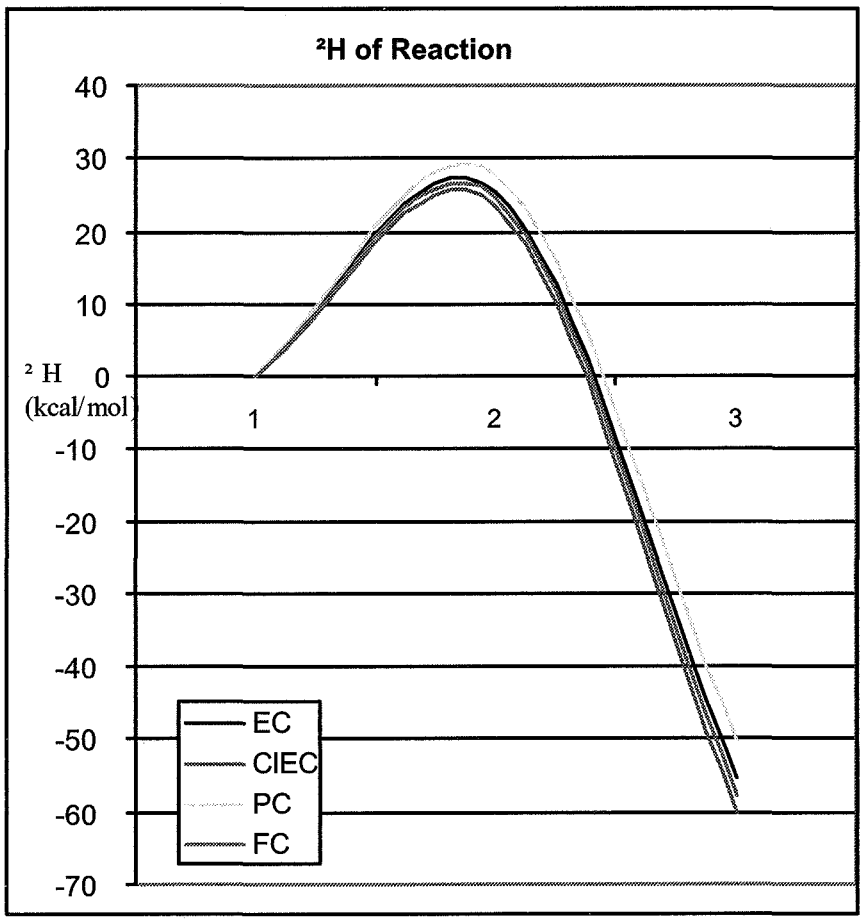

517 / CP / IN / 44 2001118395 538080

Large Lithium Ion Batteries for Aerospace and Aircraft Applications

Gregg C. Bruce and Lynn Marcoux
Eagle-Picher Energy Products
1155 West 15th Street, North Vancouver BC
Canada V7P 1M7

ABSTRACT

Eagle-Picher Energy Products (EPEP) has been manufacturing and testing large lithium ion cells (up to 100-Ah) for several years. Recently, work has focused on testing of different chemistries at variable temperatures and designing and fabricating 100-Ah cylindrical cells. For the aircraft application the largest concern is irreversible capacity loss at elevated temperatures (70°C). In contrast, for the aerospace application shelflife and cycle life is critical. EPEP has found that the major contributor to the loss in low temperature performance due to high temperature testing was the positive electrode. Eagle-Picher Energy Products will discuss recent results of variable temperature cycling and 100-Ah cell performance.

INTRODUCTION

Eagle-Picher Energy Products has been developing large lithium ion cells for several years. The initial efforts were the result of a contract funded by the USAF and the Canadian Department of Defense. The program successfully demonstrated that lithium ion cells could be scaled up to sizes useful for spacecraft and aircraft applications. The program included the delivery of 10, 25-Ah Design I cells, 12, 25-Ah Design II cells and 12, DD (7-Ah) cells to the USAF and JPL. The three cells are shown in Figure 1. As a follow on EPEP is participating in the USAF/NASA Li Ion Battery Consortium with the development of a 25-Ah cell for Mars Lander applications and a 7-Ah cell for Mars Rover applications. In the initial stages of this contract 40, 25-Ah Design II cells were delivered to JPL and Lockheed Martin Astronautics (LMA).

One of the test requirements for the Mars missions is cell performance under variable temperature cycling. The cells were alternatively cycled at 40°C and –20°C. During the program the need for EP Energy Products to improve variable temperature performance became evident and work was initiated in this area.

Figure 1. Eagle-Picher Energy Products 25-Ah, Design I, DD and 25-Ah Design II lithium ion cells.

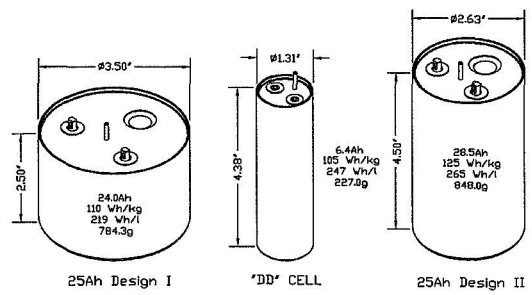

RESULTS AND DISCUSSION - VARIABLE TEMPERATURE CYCLING

With planetary exploration missions performance under large temperature variations is required. One of the first tests completed at JPL on EPEP lithium ion cells was performance as a function of temperature. During the test program JPL noted that low temperature performance was adversely affected by high temperature cycling. Since the mission profile called for high temperature cycling followed by low temperature performance this could be mission limiting. The test results obtained by JPL are shown in Figure 2.

Figure 2. Variable temperature cycling for Eagle-Picher Energy Products DD cell performed at JPL.

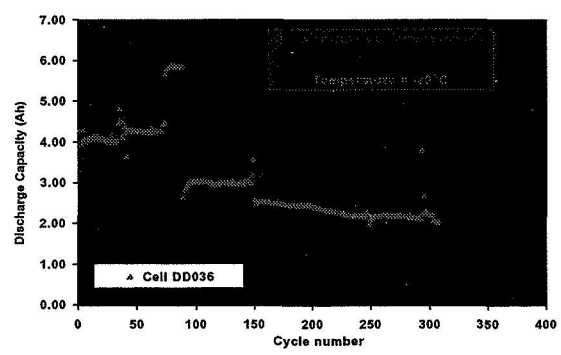

Therefore, work focused on improving the variable temperature performance of EPEP cells. The first step was to repeat the JPL test results and then systematically change parameters to improve performance. EPEP decided to use C cells as a test bed due to materials required and the ease in manufacturing. The initial test results in this test format under variable temperature conditions are shown in Figure 3.

Figure 3. Variable temperature cycling for Eagle-Picher Energy Products baseline 1.6-Ah cells.

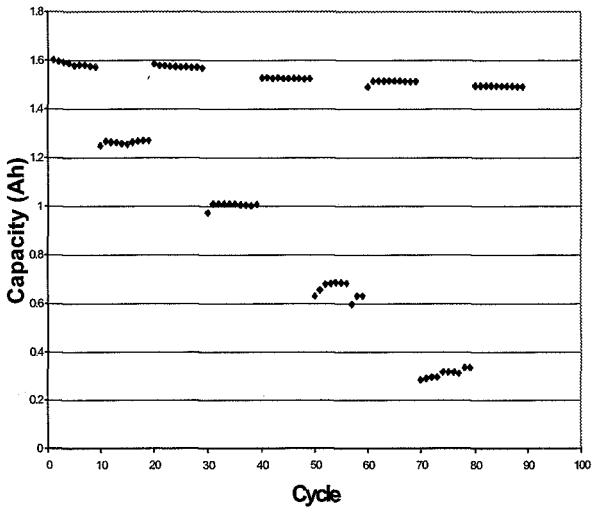

Of initial interest was that the cells tested by Eagle-Picher showed a far more rapid decline in capacity that the test results at JPL. This was found to be due to the difference in cell sizes. At –20°C the 25-Ah (tested by JPL) cell benefits more than the C cell (tested at EPEP) from self-heating. The first parameter tested was the binder used in the positive electrode. By consulting the manufacturer on solubility of PVDF binders in carbonate solvents the most insoluble binder was selected. Cells manufactured with this binder showed superior performance when compared to the baseline cells but further improvements were still required. The next parameter tested was positive electrode supplier. Samples of $LiCoO_2$ from two independent sources were obtained and tested. Surprisingly, the source of $LiCoO_2$ made a substranial difference in performance when compared to the baseline cells as shown in Figures 4 and 5.

The difference in performance was attributed to the physical characteristics of the positive electrode material. The main cause of the loss in low temperature performance due to high temperature cycling was attributed due to an increase in impedance on the positive electrode surface. This is thought to be the main driver since the performance at 40°C is not diminished as dramatically and cannot be attributed to $LiCoO_2$ dissolving in the electrolyte or to a structural change in the $LiCoO_2$.

Figure 4. Variable temperature cycling for Eagle-Picher Energy Products 1.6-Ah cells, $LiCoO_2$ from supplier A.

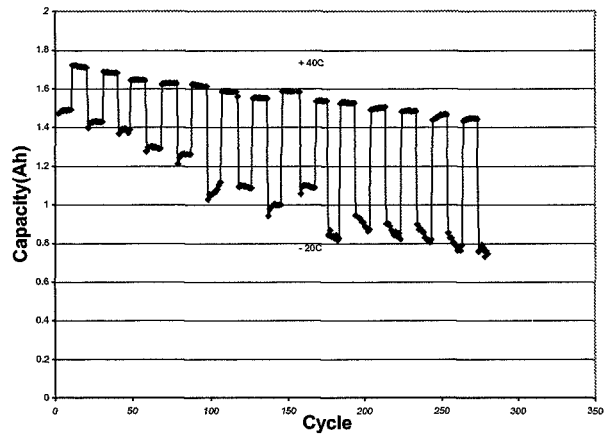

Figure 5. Variable temperature cycling for Eagle-Picher Energy Products 1.6-Ah cells, $LiCoO_2$ from supplier B.

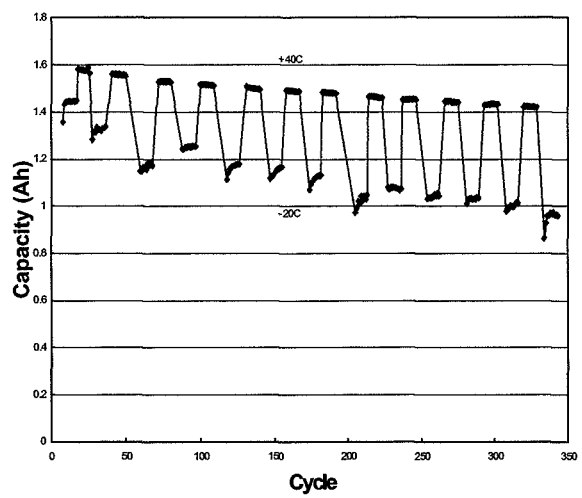

Since it became quite obvious that the major factor in low temperature performance was the active material two other metal oxide positive electrode materials were tested. The materials tested were $LiNi_{0.82}Co_{0.18}O_2$ and $LiNi_{0.80}Co_{0.15}Al_{0.05}O_2$. The results for the mixed metal oxide positive electrodes are shown in Figures 6 and 7.

Figure 6. Variable temperature cycling for Eagle-Picher Energy Products 1.6-Ah cells, $LiNi_{0.82}Co_{0.18}O_2$.

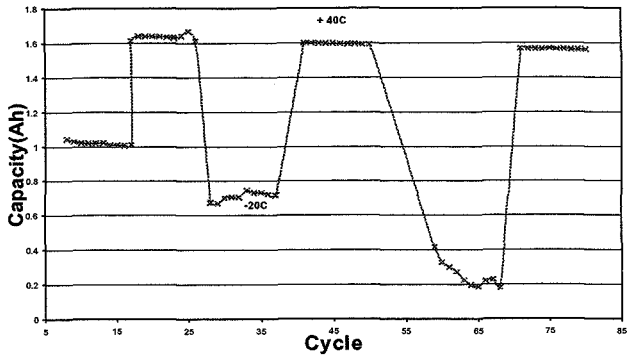

Figure 7. Variable temperature cycling for Eagle-Picher Energy Products 1.6-Ah cells, $LiNi_{0.80}Co_{0.15}Al_{0.05}O_2$.

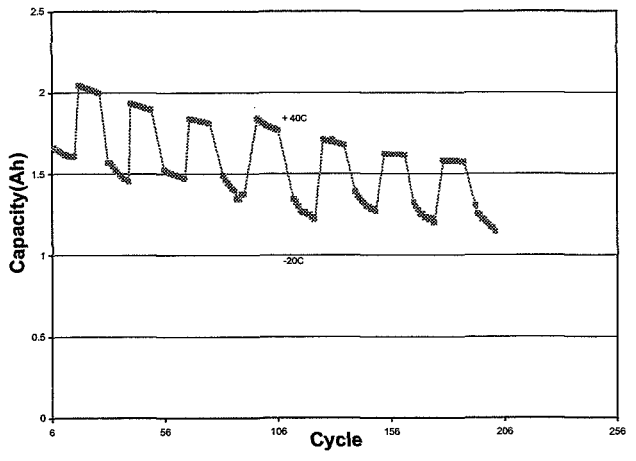

As can be seen from all the data presented two factors play in the loss in capacity at low temperature due to high temperature cycling. The first and primary factor is the positive electrode active material and the second is the binder. Work will continue to further enhance cell performance under these conditions.

CELL PERFORMANCE – 100-Ah CYLINDRICAL CELL

Recently, Eagle-Picher Energy Products has been working with very large lithium ion cells for use in spacecraft or aircraft applications. The latest cell developed is a 90 to 100-Ah cylindrical cell. The physical characteristics of the cell are given in Table 1. A general drawing of the cell is shown in Figure 8.

Table 1. Physical characteristics of 100-Ah, 86211 lithium ion cell.

Parameter	100-Ah, 86211
Cell height	8.30"
Cell diameter	3.406"
Positive electrode length	1112 cm
Positive electrode width	17.7 cm
Inter tab distance	93 cm
Negative electrode length	1142 cm
Negative electrode width	18.0 cm
Inter tab distance	95 cm

Figure 8. General drawing of the 86211 lithium ion cell.

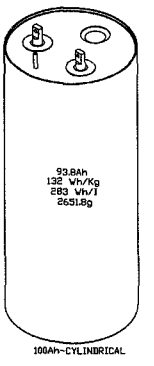

The cell utilizes a $LiCoO_2$ positive electrode and a graphite negative electrode. The electrodes have six tabs which are fusion welded to a 0.250" diameter molybdenum pin in at glass-to-metal feed-through. The cell has a rupture disc and shut-down separator for safety and uses a standard fill tube for cell activation. The physical characteristics accompanied with the performance characteristics for the 86211 cell are given in Table 2.

Table 2. Performance and physical characteristics of 86211 cell.

	Cell Weight g	Capacity Ah	Specific Energy Wh/kg	Energy Density Wh/l
Ave.	2651.8	93.8	132.0	282.6
Std. Dev.	23.1	2.1	2.3	6.5

As with all cylindrical cells when compared to a plate cell design the often cited drawbacks are rate capability and thermal management. The cell was tested for rate capability with various charge and discharge rates from C/10 (10A) to C (100A). In all cases the cell was charged to a voltage limit of 4.1V and then held at constant potential for 2.5 hours and then discharged to 3.0V. The results of these tests are shown in Figure 9.

Figure 9. Rate capability of the 86211 lithium ion cell at various charge and discharge rates.

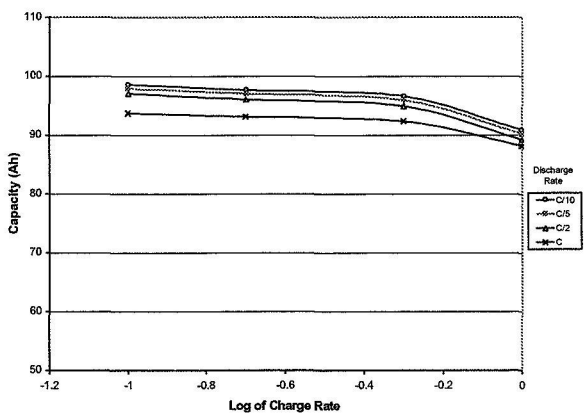

The data shows that the cell is starting to see rate limitations at the C rate.

The mass analysis of the 86211 cell is shown in Table 3. The relatively low values for the cap and can is related to the inherent tube strength of the cylindrical design.

Table 3. Mass analysis of 86211 Cell.

Component	Mass, g	% of Total
Can	213.0	8.0
Cap Assembly	54.0	2.0
Electrolyte	688.5	25.2
Positive electrode	1074.5	40.5
Negative electrode	517.5	19.5
Miscellaneous	124.3	4.7
Total	2651.8	100

The cells were tested for cycle life at the C/5 and the C/2 charge and discharge rates. The C/5 test was carried out at 20A to a 4.1V cut-off with a voltage clamp for a further 1.5 hours. The C/2 rate was tested at 45A with a voltage clamp of 4.1V for a total charge time of 6 hours. The C/5 results are shown in Figure 10 and the C/2 results are given in Figure 11.

Figure 10. Cycle life of 86211, 100-Ah cell at 20°C, 100% depth of discharge at C/5.

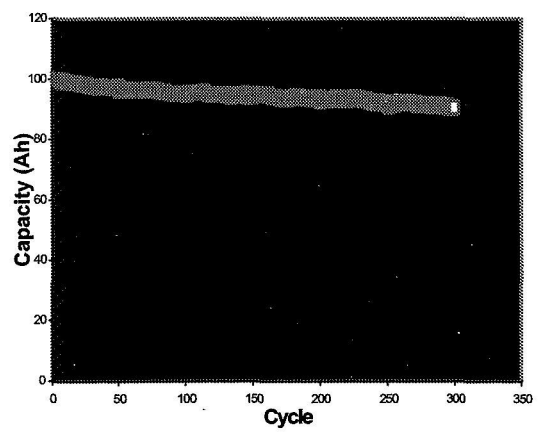

Figure 11. Cycle life of 896211 100-Ah cell at 20°C, 100% depth of discharge at C/2.

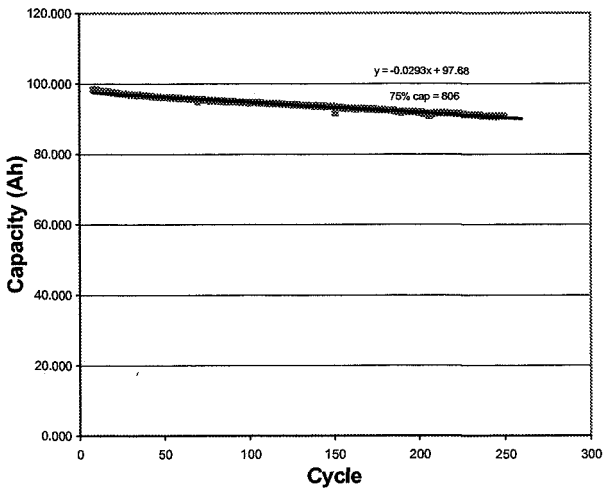

The cycle life projections for the two cells tested at the C/5 rate indicate that 75% of initial capacity will not be reached until 940 and 998 cycles. For the C/2 rate test the projection is for greater than 800 cycles to 75% of initial capacity.

CONCLUSION

The reduced capacity at low temperature due to high temperature cycling is attributed primarily to the positive electrode. The performance for the 86211 cell is quite impressive for a $LiCoO_2$ cathode with good specific energy and energy density and excellent cycle life.

ACKNOWLEDGMENTS

The continuing support, technical assistance and test data supplied by Marshall Smart and Kumar Bugga of JPL and Richard Mash and Steve Vukson of Wright-Patterson AFB is gratefully acknowledged.

R&D Status of Li-Ion Secondary Cells at Tsukuba Space Center, NASDA

Y. Sone, X. Liu, H. Kusawake, K. Kanno, and S. Kuwajima

Battery Group, Office of Research and Development
National Space Development Agency of Japan (NASDA)

Development of Space Batteries at NASDA

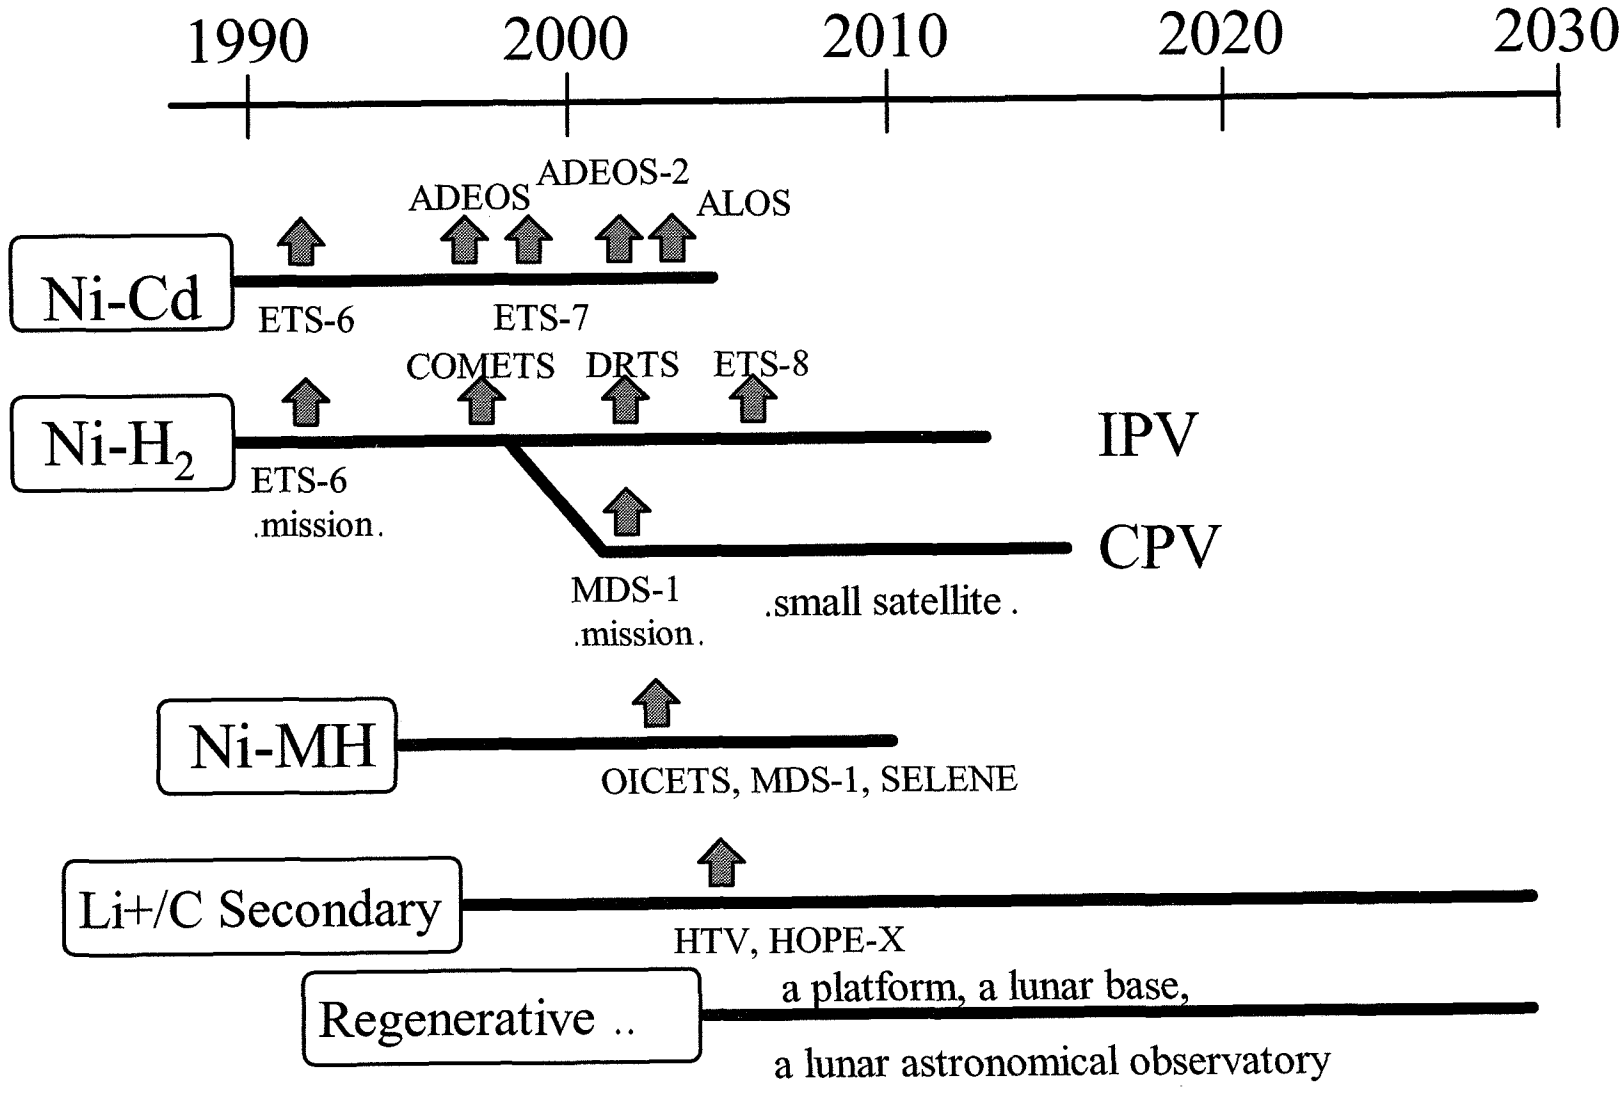

NASDA

List of Li-Ion Secondary Cells

Data Update
October 2000

Phase	Capacity /Ah	Package	Mode	Temp /?	DOD /%	Charge(CC-CV)		Discharge	C/D Ratio	Sample Number		Date Started	Cycle Number	
						CC/A	CV/V(/cell)	Current/A		Initial	Present		Ended	Present
Feasibility Study using Commercial Cells	0.7	CELL	LEO	20	35.7	0.3	4.1	0.5	1.01	2	End	May-95	--	13,000
	0.7	CELL	LEO	20	35.7	0.3	4.0	0.5	1.01	2	End	May-95	--	8,200
	1.0	CELL	LEO	20	25	0.3	4.2	0.5	1.01	2	2	May-95	--	22,000
	1.0	CELL	LEO	20	25	0.3	4.1	0.5	1.01	2	2	May-95	--	22,000
	1.2	CELL	LEO	20	20.8	0.3	4.1	0.5	1.01	2	End	May-95	18,151	--
	1.2	CELL	LEO	20	20.8	0.3	4.0	0.5	1.01	2	2	May-95	--	22,000
	0.7	CELL	LEO	20	25	0.21	4.1	0.35	1.01	2	End	Sept-96	7,353	--
	0.7	CELL	LEO	20	25	0.21	4.0	0.35	1.01	2	End	Sept-96	12,108	--
	1.0	CELL	LEO	20	18	0.21	4.2	0.35	1.01	2	2	Sept-96	--	15,000
	1.0	CELL	LEO	20	18	0.21	4.1	0.35	1.01	2	2	Sept-96	--	15,000
	0.98	CELL	LEO	20	31	0.36	4.2	0.6	1.01	2	End	Sept-96	3,322	--
	0.98	CELL	LEO	20	31	0.36	4.1	0.6	1.01	2	1	Sept-96	3,203	15,000
	1.0	CELL	LEO	20	30	0.36	4.2	0.6	1.01	2	2	Sept-96	--	15,000
	1.0	CELL	LEO	20	30	0.36	4.1	0.6	1.01	2	1	Sept-96	3,003	15,000
	1.2	CELL	LEO	20	18	0.36	4.1	0.6	1.01	2	1	Sept-96	14,143	15,000
	1.2	CELL	LEO	20	18	0.36	4.0	0.6	1.01	2	2	Sept-96	--	15,000
Simulation Tests for Satellite Applications	30	CELL	LEO	20	25	9	4.05	15	1.005	5	5	Sept-98	--	9,600
	30	CELL	LEO	20	40	15	4.05	24	1.005	5	4[1)]	Sept-98	--	9,200
	10	CELL	LEO	20	25	3	4.05	5	1.005	2	2	June-99	--	6,000
	10	CELL	LEO	20	40	5	4.05	8	1.005	3	3	June-99	--	6,000
	100	CELL	LEO	15	25	25	3.95	50	1.005	5	5	May-99	--	5,200
	100	CELL	LEO	15	40	50	3.95	80	1.005	5	5	July-99	--	4,800
	100	CELL	GEO	15	80	10	3.95	67	1.005	5	5	Aug-99	--	320
	90	CELL	LEO	10	40	45	4.2	72	1.000	5	5	June-00	--	1,100
	90	CELL	GEO	10	80	9	4.2	60	1.000	5	5	July-00	--	45

10Ah $LiCoO_2$/Graphite Cells

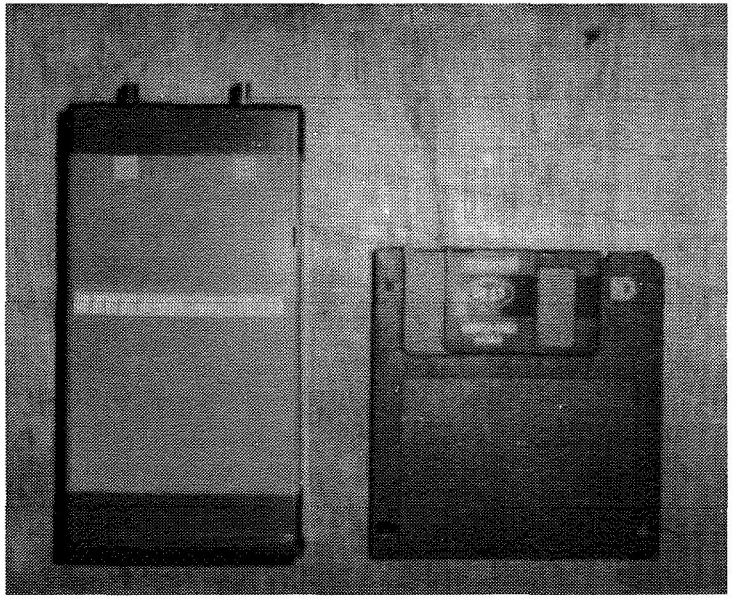

Cell Style		Prismatic
Electrode	Positive Electrode	LiCoO2
	Negative Electrode	C (graphite) over porous Nickel
Capacity Nominal / Typical		10Ah / 12 Ah
Weight		0.43 kg
Dimensions		70 mm (W) x 23.5 mm (D) x 130 mm (H)
Energy Density	per Weight	100 Wh/kg
	per Volume	202 Wh/L
Charge Voltage / Higher Limited Voltage		4.1 V
Discharge Voltage	Nominal Voltage	3.6 V
	Lower Limited Voltage	3.0 V

10 Ah Prismatic cells were prepared in 1999. The originality of th e cell design is the negative electrode. Instead of Cu sheet, porous Ni is used as a current collector. Graphite covers the surface of porous Ni, thus it performs as a negative electrode.

Trend Data of 10 Ah $LiCoO_2$/Graphite Cells

Data Update

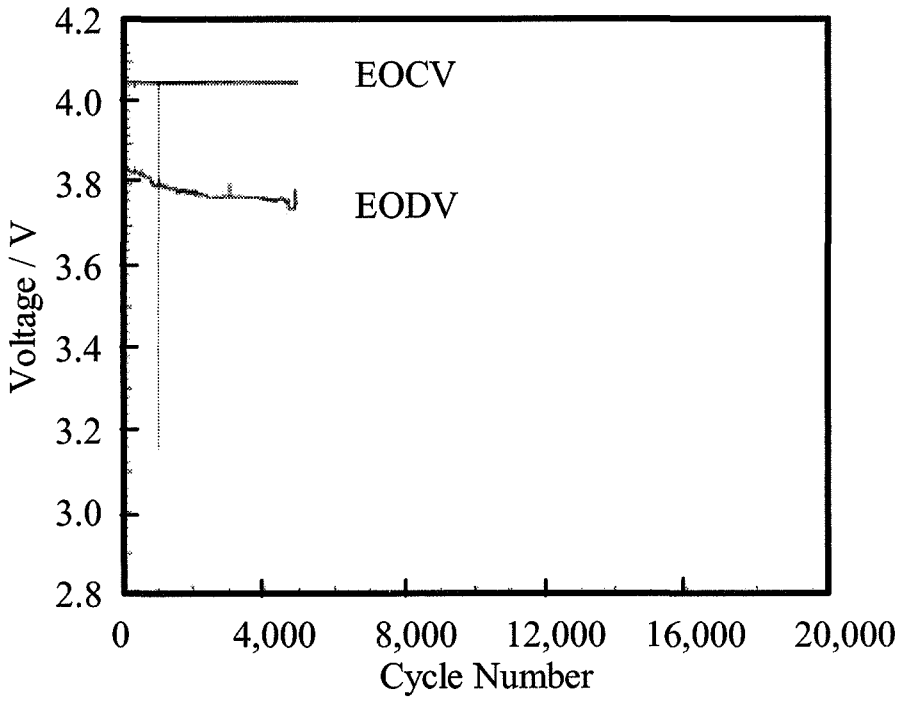

Fig. Life Cycle Trend of DOD=25% LEO Test
Two cells are connected in series.

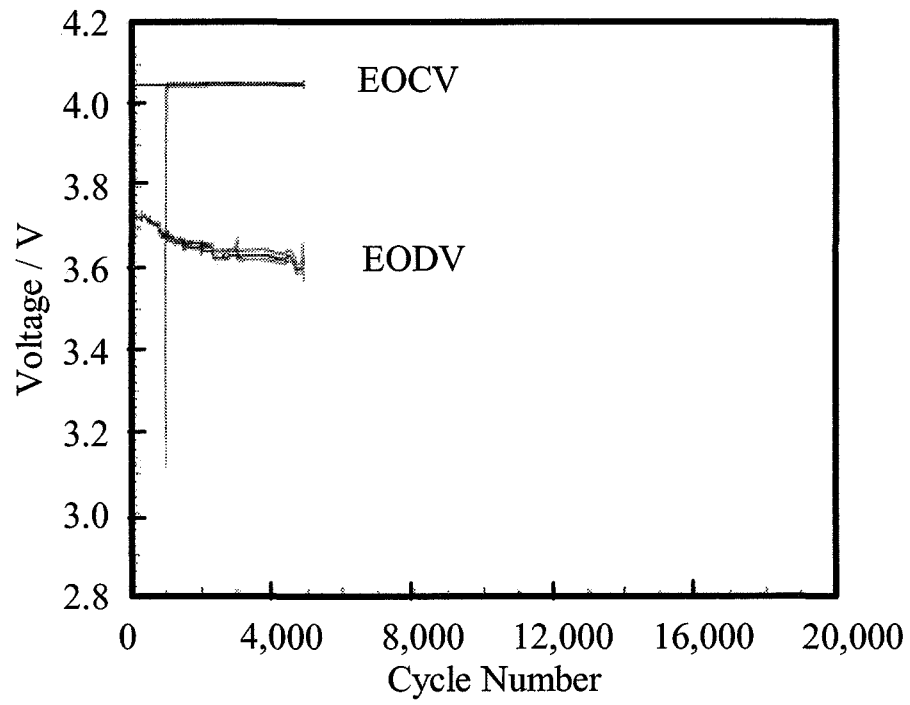

Fig. Life Cycle Trend of DOD=40% LEO Test
Three cells are connected in series.

Above figures show the trends of LEO tests using 10 Ah prismatic cells. We are testing the performance of the cells under two different DOD conditions. We have not observed any variety of EOCV or EODV of the cells with a series connection.

Trend Data of 10 Ah $LiCoO_2$/Graphite Cells

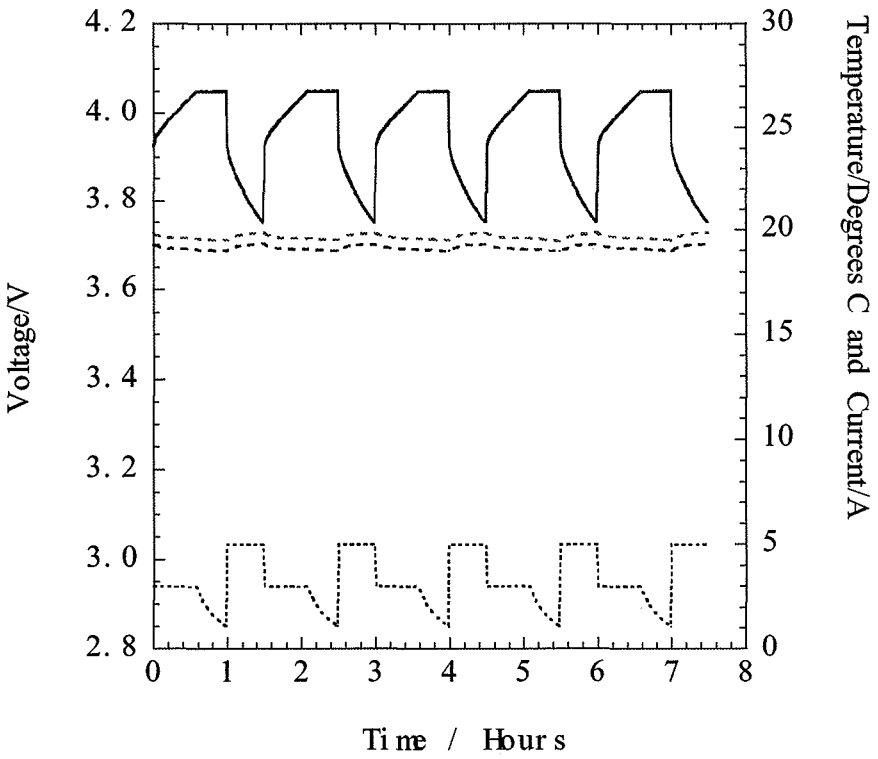

Fig. Recent Cycle Performance of DOD=25% LEO Test

Two cells are connected in series.

——— Voltage ——— Temperature · Current

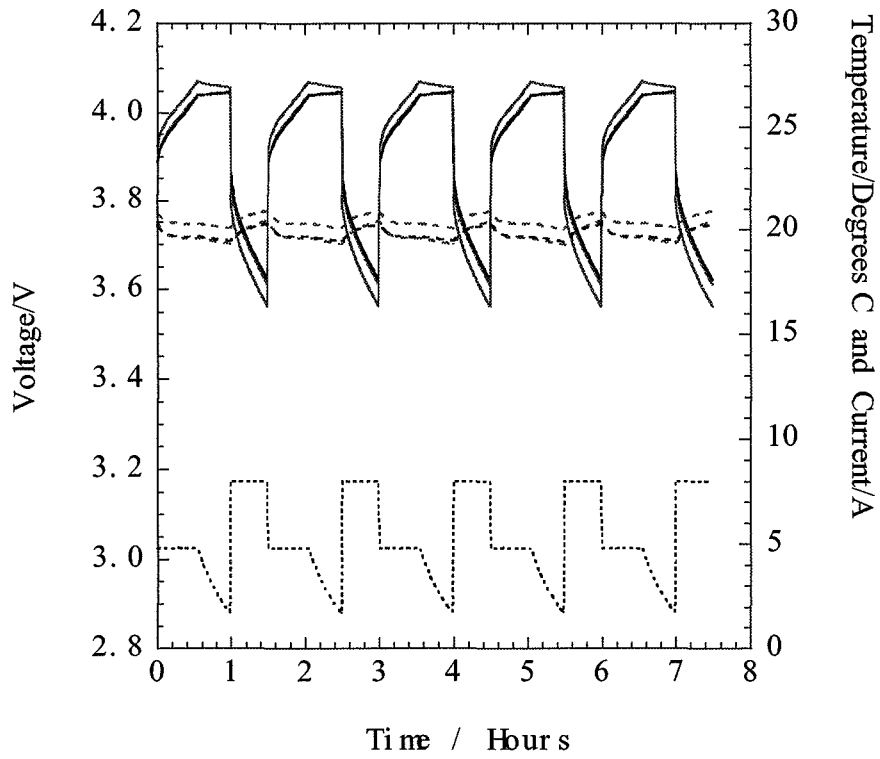

Fig. Recent Cycle Performance of DOD=40% LEO Test

Three cells are connected in series.

——— Voltage ——— Temperature · Current

Above figures are charge and discharge curves for recent five cy cles. The charge and discharge curves of two cells are almost identical in the case of DOD=25% LEO tes t, while one of the three cells shows a higher charge voltage and lower discharge voltage in the case of DOD40% LEO test. We believe that the impedance of the cell is increasing, now.

Trend Data of 10 Ah $LiCoO_2$/Graphite Cells

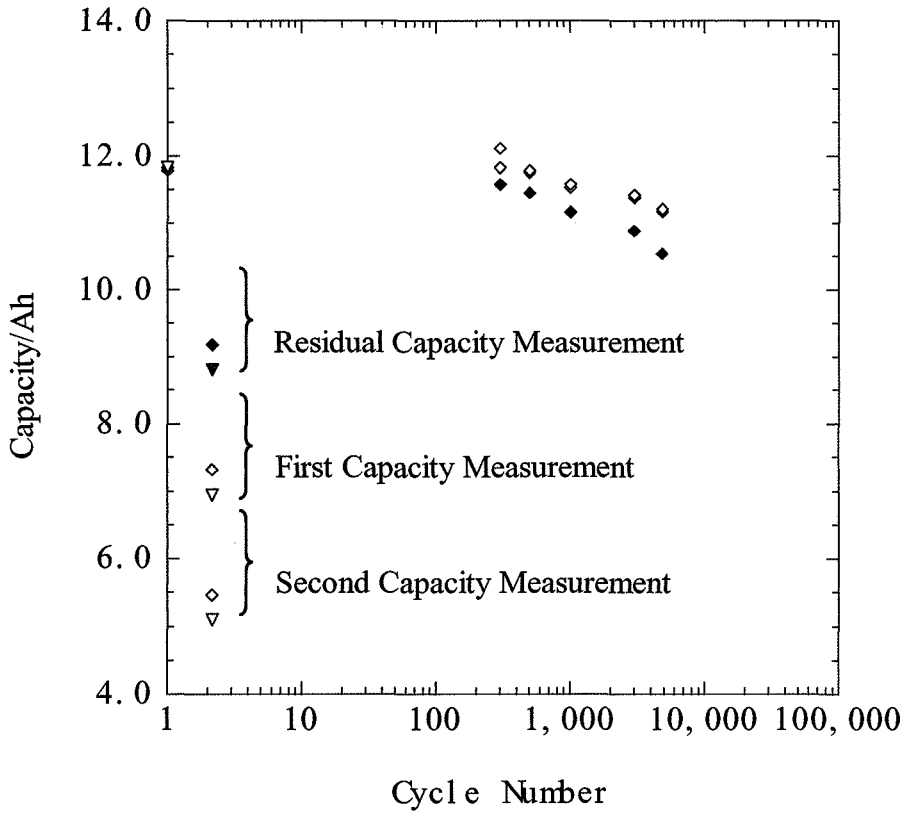

Fig. Capacity Trend by Cycles, LEO Test/DOD25%

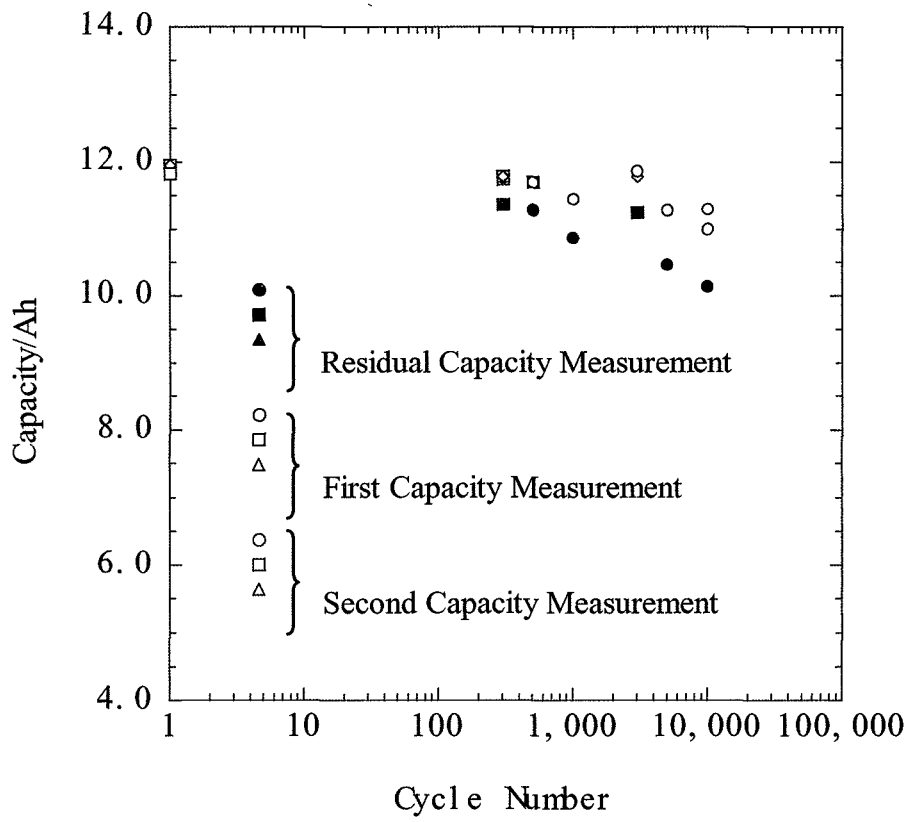

Fig. Capacity Trend by Cycles, LEO Test/DOD40%

Capacities of samples are slightly decreasing. However, in the both case, all samples still keep their nominal capacity.

30Ah $LiCoO_2$/Graphite Cells

Cell Style		Prismatic
Electrode	Positive Electrode	LiCoO2
	Negative Electrode	C (graphite)
Capacity	Nominal / Typical	30Ah / 39 Ah
Weight		1.3 kg
Dimensions		98.5 mm (W) x 27 mm (D) x 190 mm (H)
Energy Density	per Weight	108 Wh/kg
	per Volume	278 Wh/L
Charge Voltage / Higher Limited Voltage		4.1 V
Discharge Voltage	Nominal Voltage	3.6 V
	Lower Limited Voltage	3.0 V

30 Ah prismatic cells were prepared by Japan Storage Battery Co. (denoted as JSB) in 1998. Our request to JSB was to fabricate a 'Prismatic Cell' using popular electrode materials. Positive and Negative electrodes were $LiCoO_2$ and C (graphite), respectively. They prepared square sheets of electrodes on the basis of their conve ntional Li-Ion cells for ground applications that requested 7 hours for the ideal full ch arge.

Trend Data of $LiCoO_2$/Graphite Cells

Data Update

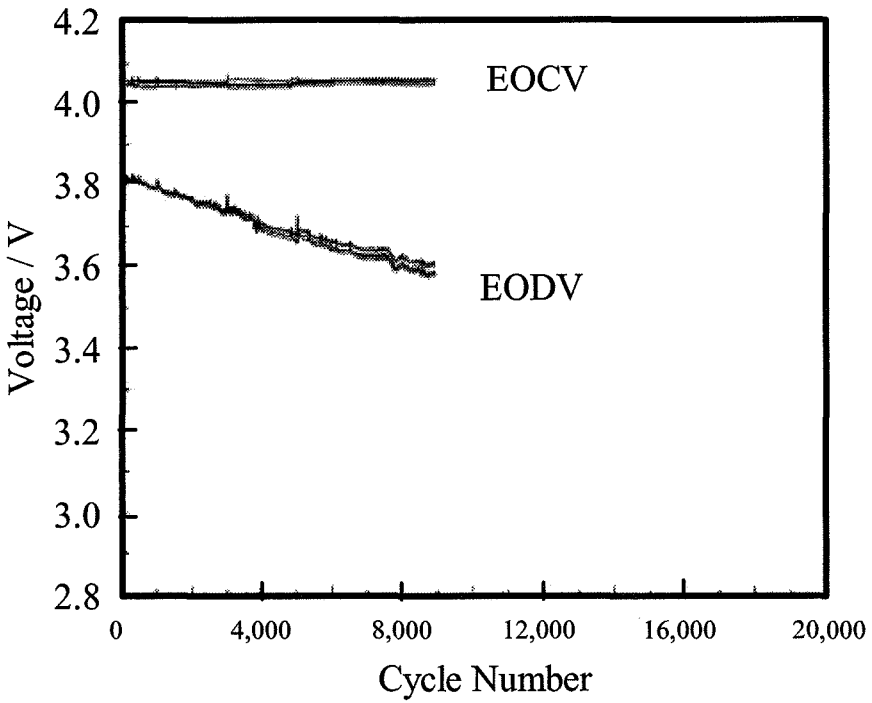

Fig. Life Cycle Trend of DOD=25% LEO Test
Five cells are connected in series.

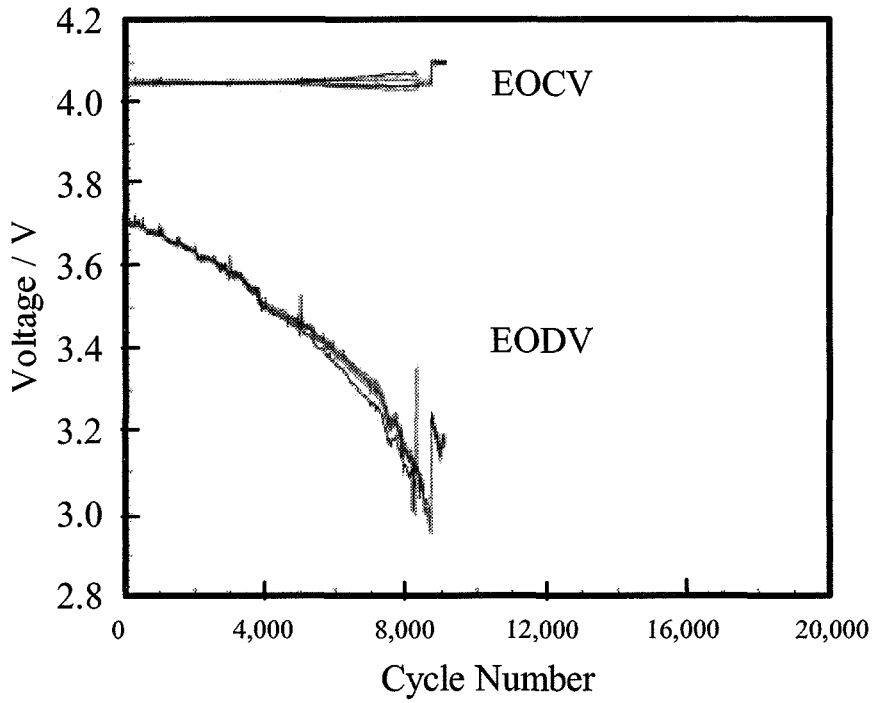

Fig. Life Cycle Trend of DOD=40% LEO Test
Five cells used to be connected in series. At 8,269 cycle, one of the cells was removed for DPA.

Five cells were connected in series for the above measurements. The performance of cells have been very stable in the case of DOD=25%, while a considerable decreas e in EODV was observed in the case of DOD=40%.

Trend Data of 30 Ah $LiCoO_2$/Graphite Cells

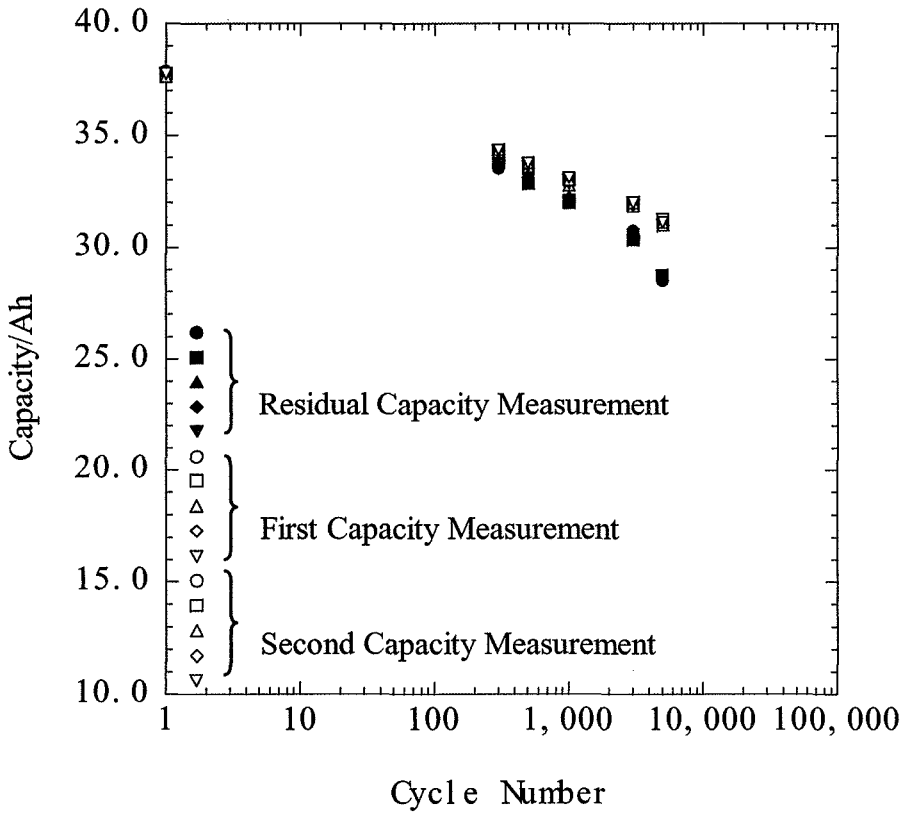

Fig. Capacity Trend by Cycles, LEO Test/DOD25%

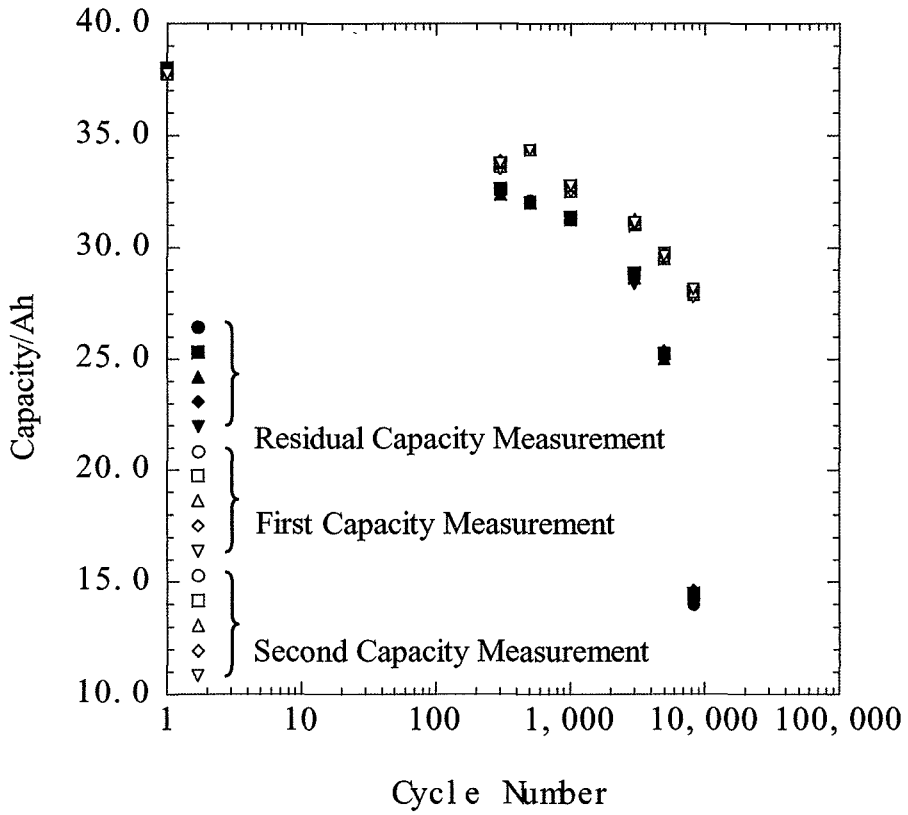

Fig. Capacity Trend by Cycles, LEO Test/DOD40%

In the test with DOD=25%, we observed a constant decrease in capacity. The residual capacity during cycle test was almost the same as the capacity obtained after full cha rge. In test with DOD=40%, high decrement of residual capacity was observed, which resulted in the conside rable decrease in EODV. It is notable that we obtained high capacity after full charge, which means that the charge amount during DOD=40% cycles was too small due to the lack of charge duration (60 min.) for '98 models to maintain its cycle performance.

Contract research with JSB

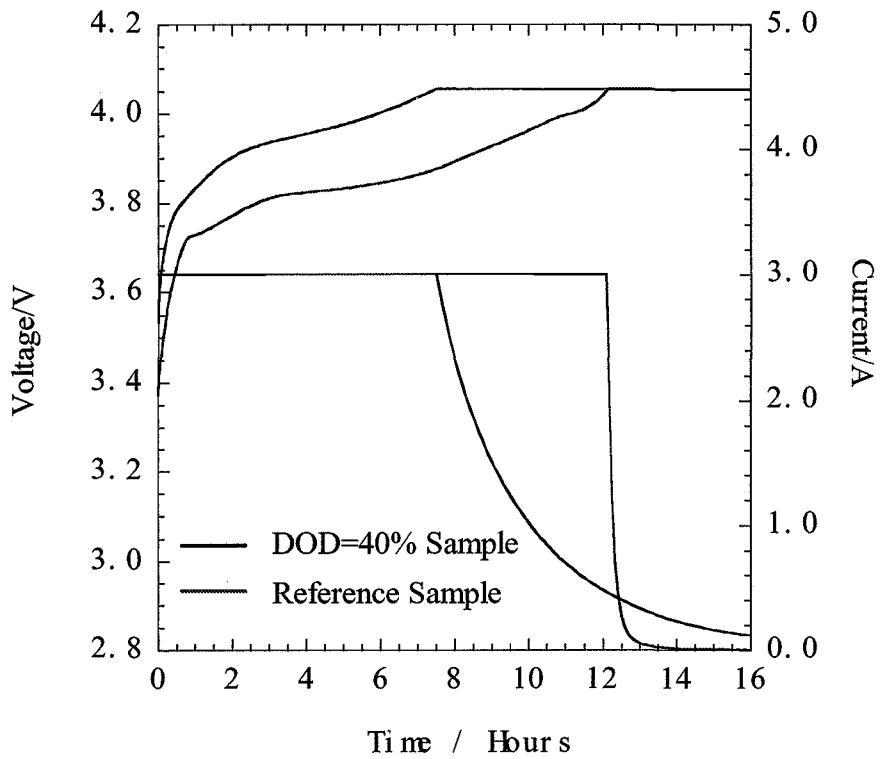

Fig. Charge curves of 30Ah cells
Charge Condition : CC(3A)-CV(4.05V), at 20.

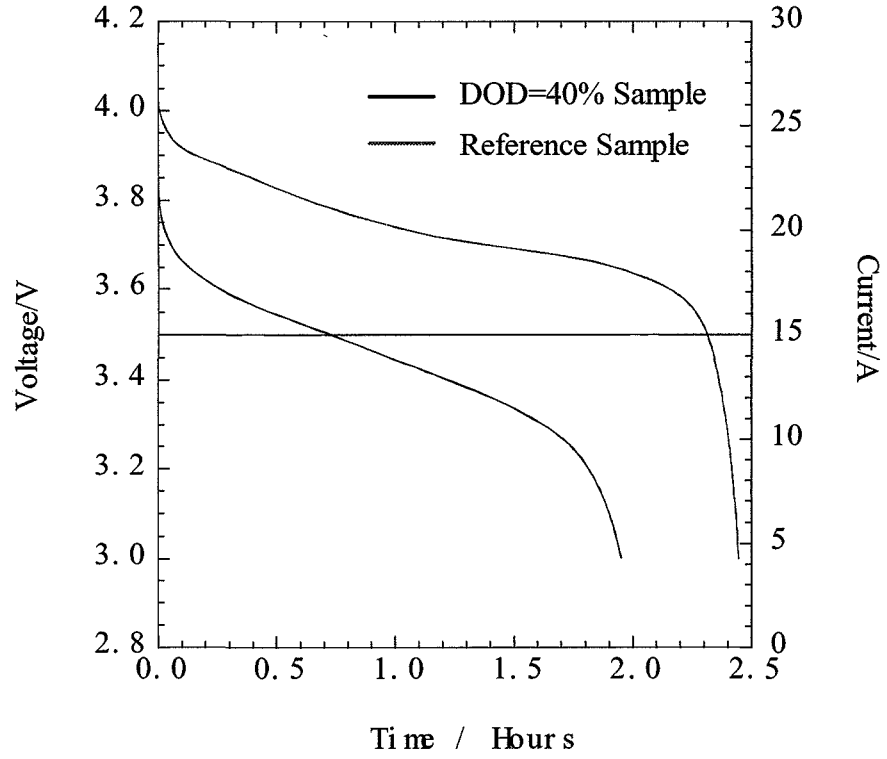

Fig. Discharge curves of 30Ah cells
Discharge Condition : CC(15A), at 20.

Fig. Capacity Measurement before DPA.

In order to understand the reason of the high decrease in EODV and residual capacity, we decided to perform destructive physical analysis (DPA) using a sample of DO D=40% cycle test. As a reference, we used an as-prepared cell which had been stored at room temperature by JSB. The charge and discharge curves of the sample after life cycle test suggested a n increase in impedance. The capacity of DOD=40% sample was ca. 20% smaller than that of the reference.

DPA of 30 Ah $LiCoO_2$/Graphite Cells

Contract research with JSB

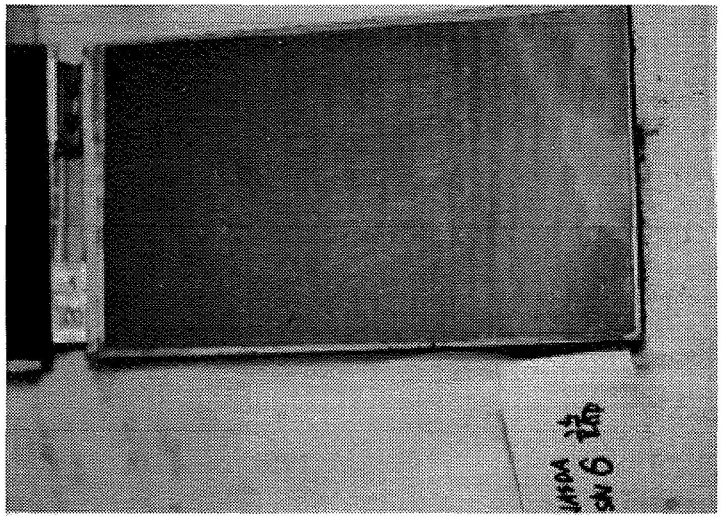

Fig. Positive Electrode

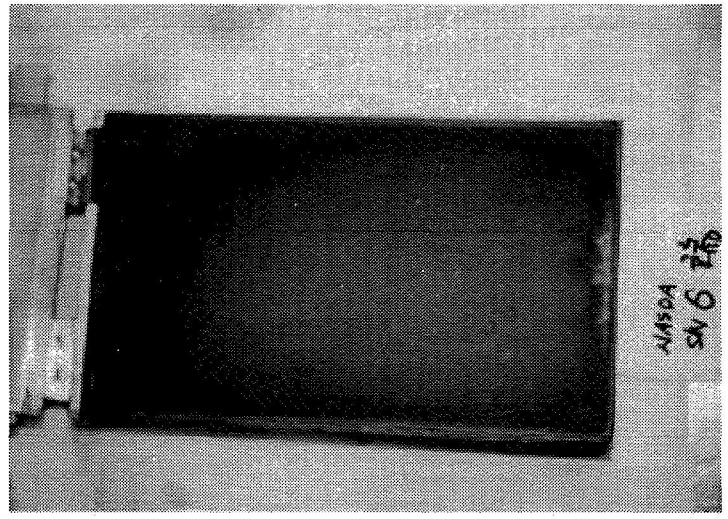

Fig. Negative Electrode

Fig. Pictures of electrodes after destruction.

These are photographs of electrodes after DPA. These appearances and SEM images revealed that the electrodes still kept a smooth surface condition. Separators and electrodes seemed to be enough wet for electrochemical conduction.

The significant increase in water content in the solvent and the composition change in the electrolyte were not detected by means of Karl Fischer Titration and LC-FTIR.

Electrochemical measurements were carried out using a glass cell with three electrodes configuration. Both reference and counter electrodes were lithium metal foils. Samples for working electrodes were taken out from an inner (central side) and an outer (case side) sheet of a stack.

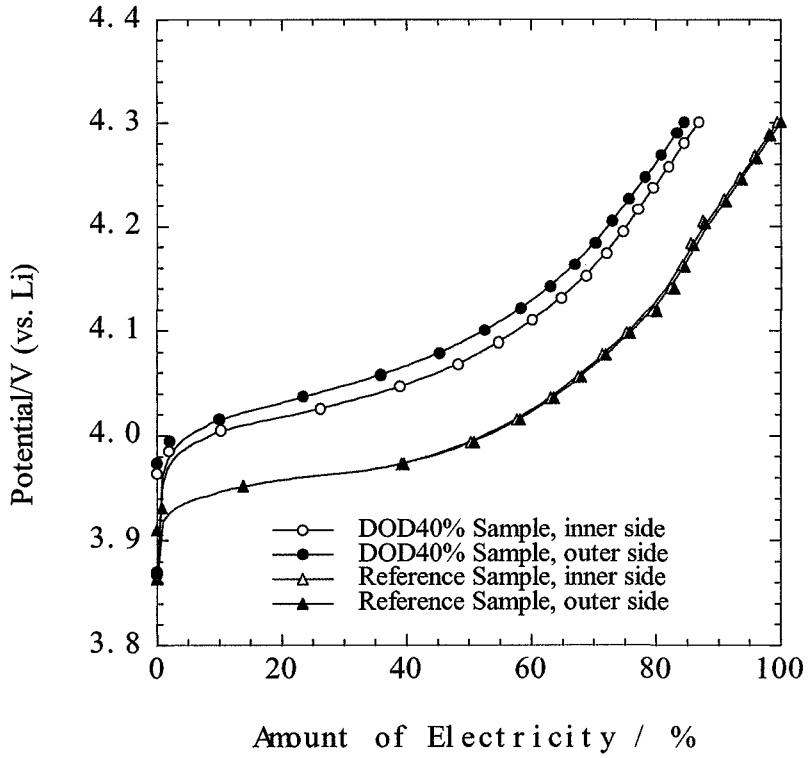

Fig. Charge curves of Positive Electrodes
Charge Condition : CC(0.5mA/cm^2) to 4.3V, at 25.

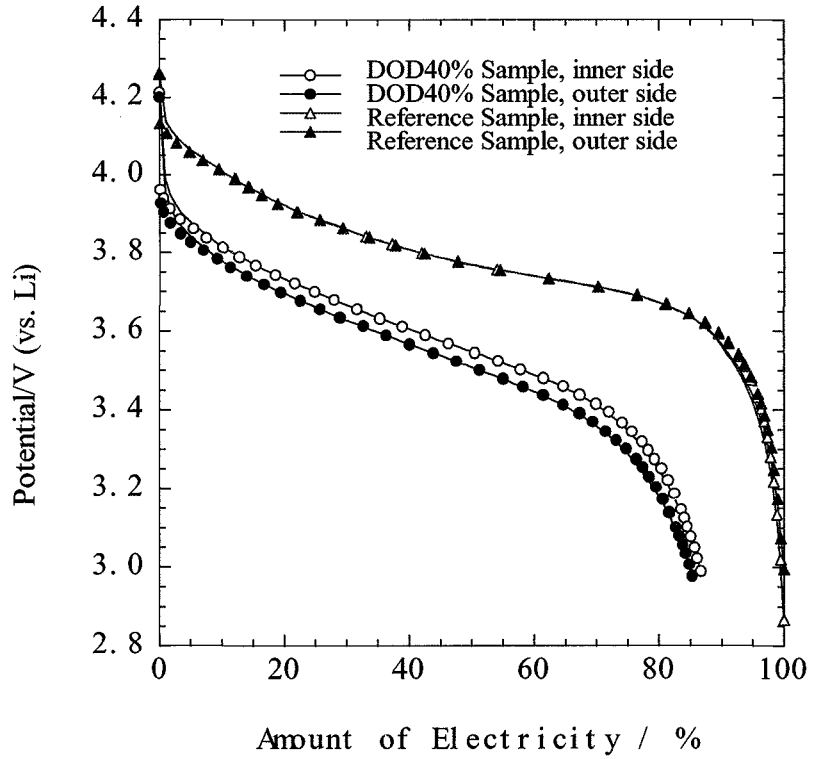

Fig. Discharge curves of Positive Electrodes
Discharge Condition : CC(2.0mA/cm^2) to 3.0V, at 25.

Fig. Capacity Measurement of Positive Electrodes.

Capacities of positive electrodes were measured. The samples fr om DOD=40% test cell showed a lower capacity than that from the as-prepared reference cell, while the samples coming from the common cell stack showed almost the same curves and capacities.

DPA of 30 Ah $LiCoO_2$/Graphite Cells

Contract research with JSB

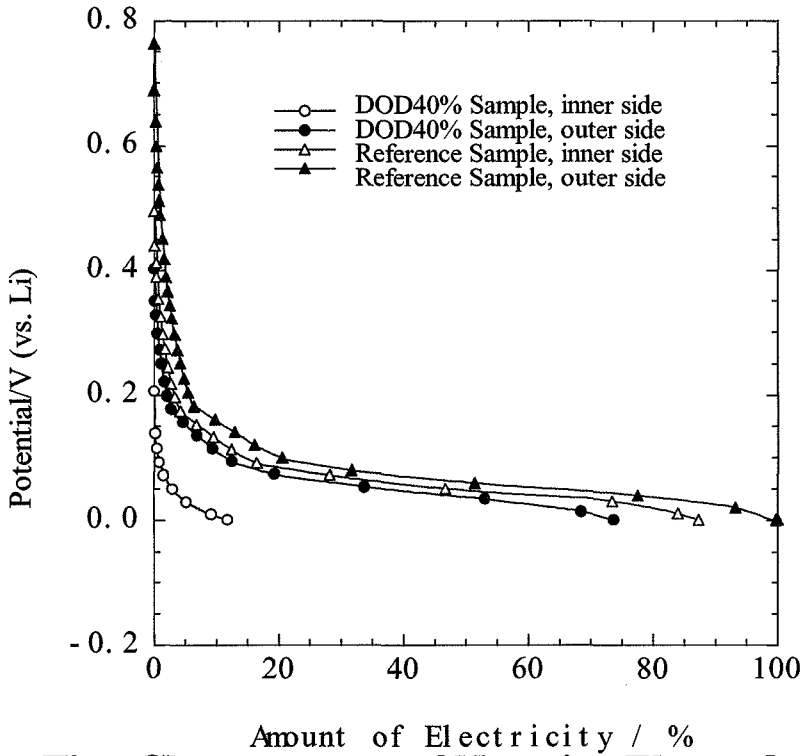

Fig. Charge curves of Negative Electrodes

Charge Condition : CC(0.5mA/cm^2) to 0.0V, at 25.

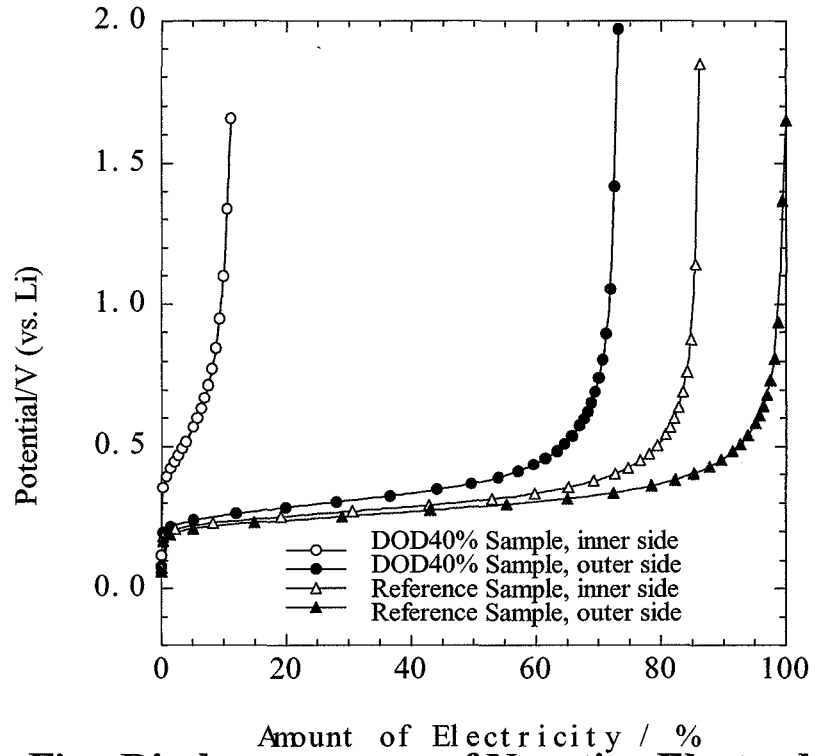

Fig. Discharge curves of Negative Electrodes

Discharge Condition : CC(2.0mA/cm^2) to 1.5V, at 25.

Fig. Capacity Measurement of Negative Electrodes.

Capacities of negative electrodes were also measured. A fairly degradation of performance was observed in the case of DOD=40% test cell. The degradation of the inner she et of a stack was more considerable than that of the outer sheet. An increase in thickness and impedance was also observed in the negative electrode. We believe that the degradation of negative electrodes played an important role in the decreasing residual capacity of DOD=40% test cells.

Based on these results, accompanied with the experience of 100Ah elliptic cylinder cells, we have started the discussion of the new trial cell which might enable high rate ch arge targeting LEO applications.

Trend Data of 30 Ah $LiCoO_2$/Graphite Cells

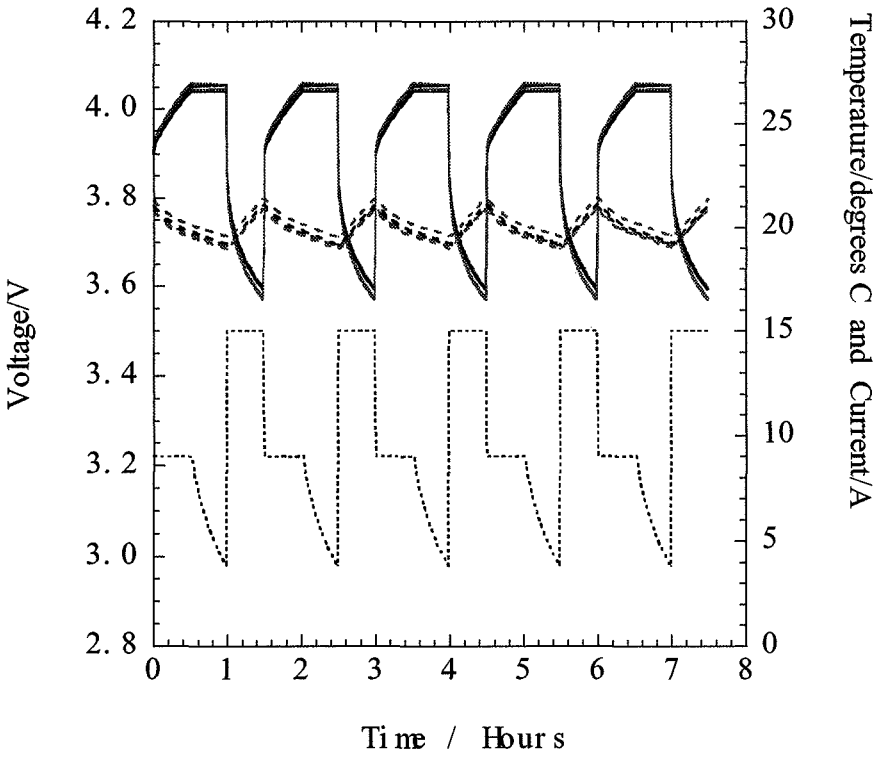

Fig. Recent Cycle Performance of DOD=25% LEO Test

Five cells are connected in series.

——— Voltage ——— Temperature · Current

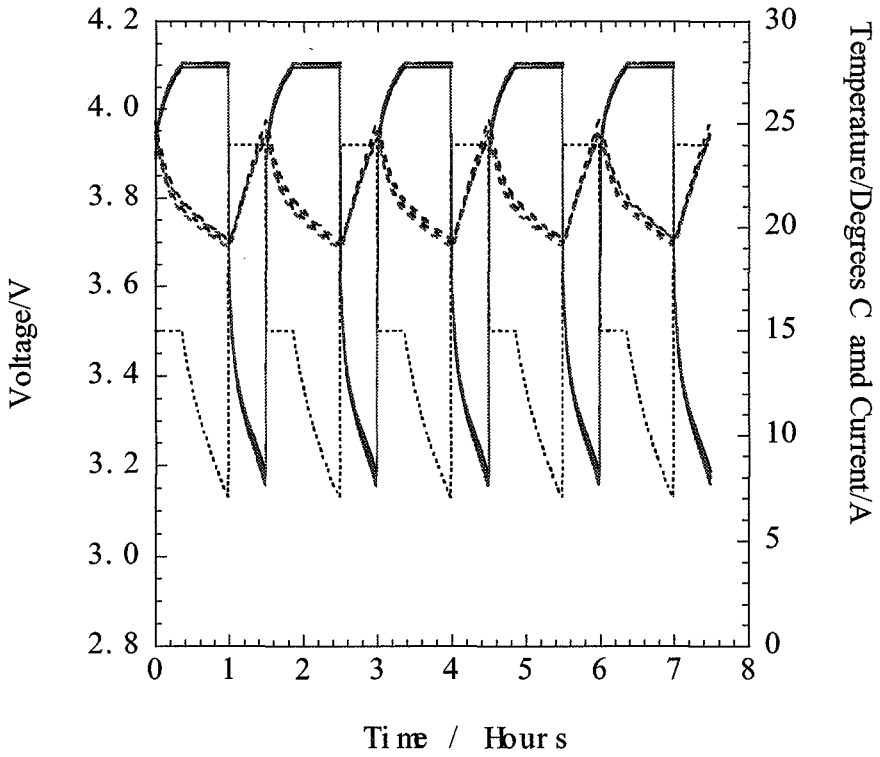

Fig. Recent Cycle Performance of DOD=40% LEO Test

Four cells are connected in series.

——— Voltage ——— Temperature · Current

Above figures are charge and discharge curves for recent five cy cles. When we restarted the cycle test with DOD=40% after the replacement of a cell for DPA, we raised the C V condition up to 4.1V to continue the cycles. As shown above, very stable performance is observed cur rently.

100 Ah $LiCoO_2$/Graphite Cells

Cell Style		Elliptic Cylinder
Electrode	Positive Electrode	LiCoO2
	Negative Electrode	C (graphite)
Capacity	Nominal / Typical	100Ah / 106 Ah
Weight		2.8 kg
Dimensions		130 mm (W) x 50 mm (D) x 207 mm (H)
Energy Density	per Weight	136 Wh/kg
	per Volume	309 Wh/L
Charge Voltage / Higher Limited Voltage		3.98 V
Discharge Voltage	Nominal Voltage	3.6 V
	Lower Limited Voltage	2.75 V

Mitsubishi Electric Co. (MELCO) and Japan Storage Battery Co. (JSB) have been cooperating for the development of lithium ion secondary battery for space applications. In 1998, we decided to collaborate with these companies to accelerate our R&D of lithium ion secondary battery for the NASDA future satellites.

.MELCO is going to establish the battery system including the charge method. For example, MELCO studies the electric circuits, safety unit, and others to maintain and evaluate the safety of the whole battery system.

.JSB performs the cell design, manufacturing, and checking the single cell performance. Life cycle test, safety test of cells, storage effects are included in its study. JSB has improved the cell design for this 100Ah cell to reduce the increase in impedance during cycles.

.NASDA focuses the evaluation on the long-term performance as a battery.

Trend Data of 100 Ah $LiCoO_2$/Graphite Cells

Data Update

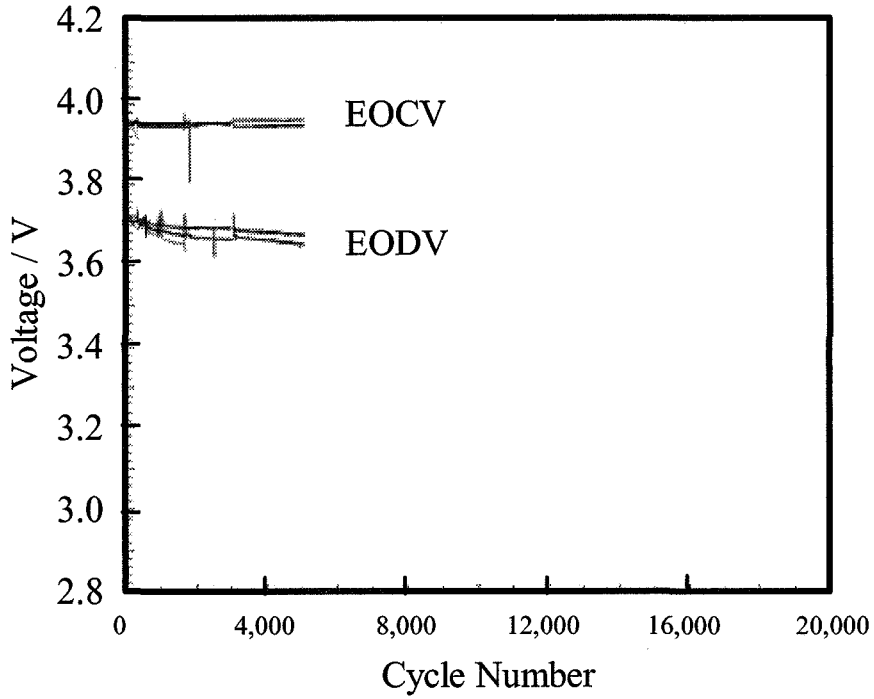

Fig. Life Cycle Trend of DOD=25% LEO Test
Five cells are connected in series.

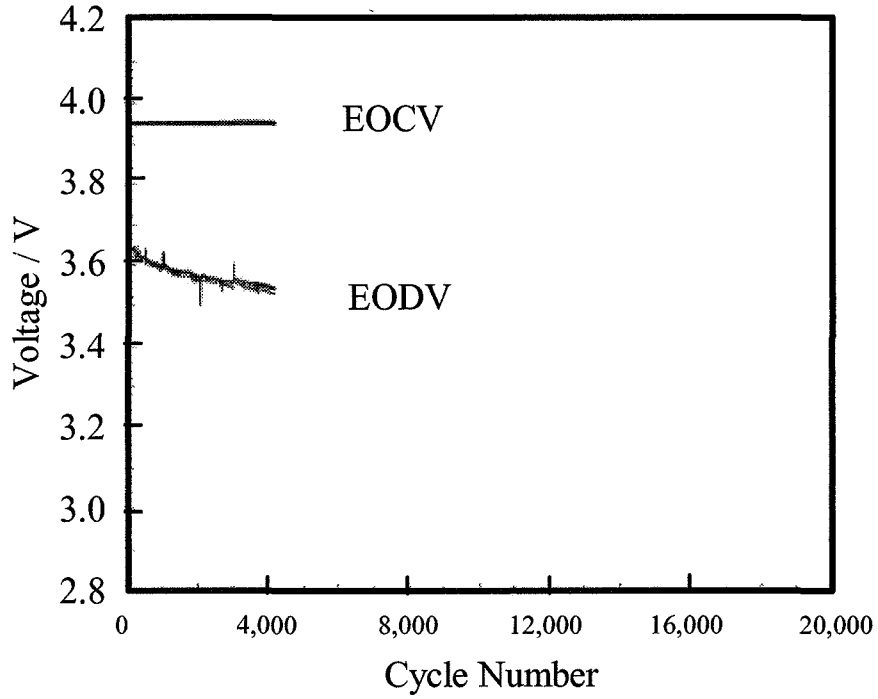

Fig. Life Cycle Trend of DOD=40% LEO Test
Five cells are connected in series.

In the case of DOD=25% test, we observed lower EODV of a cell until ca. 1,600 cycles. It was because of the loose contact between the terminal of the cell and the external lead from the instruments. Today, though both EOCV and EODV sprit into different levels, we have almost the same cycle trends of the cells connected together in series.

In the case of DOD=40%, we observed nearly no difference in the performance of five cells connected in series.

Trend Data of 100 Ah $LiCoO_2$/Graphite Cells

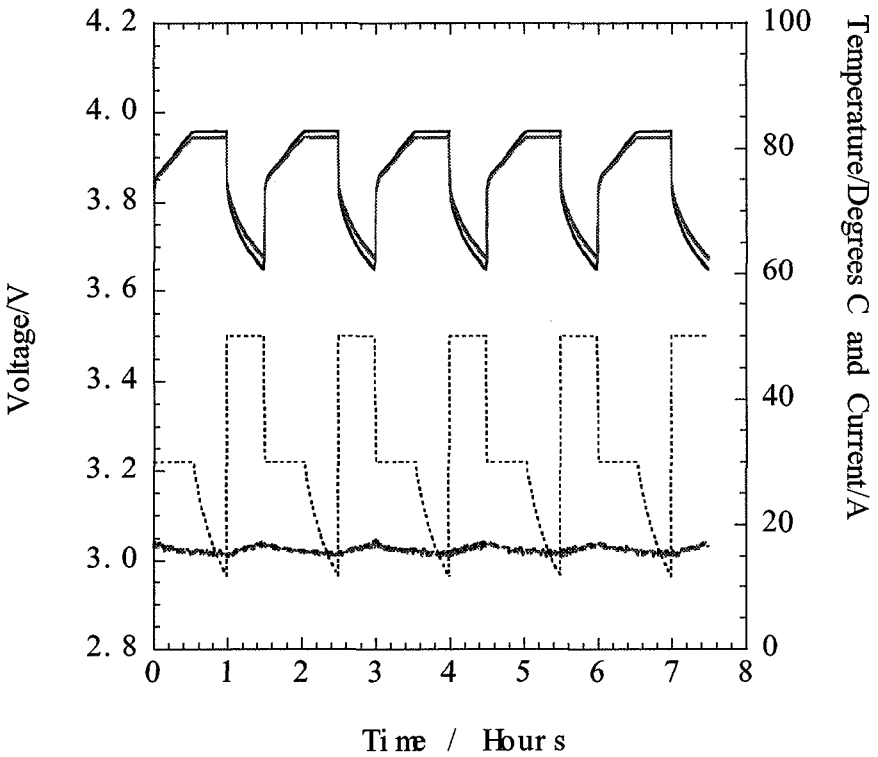

Fig. Recent Cycle Performance of DOD=25% LEO Test

Five cells are connected in series.

——— Voltage ——— Temperature · Current

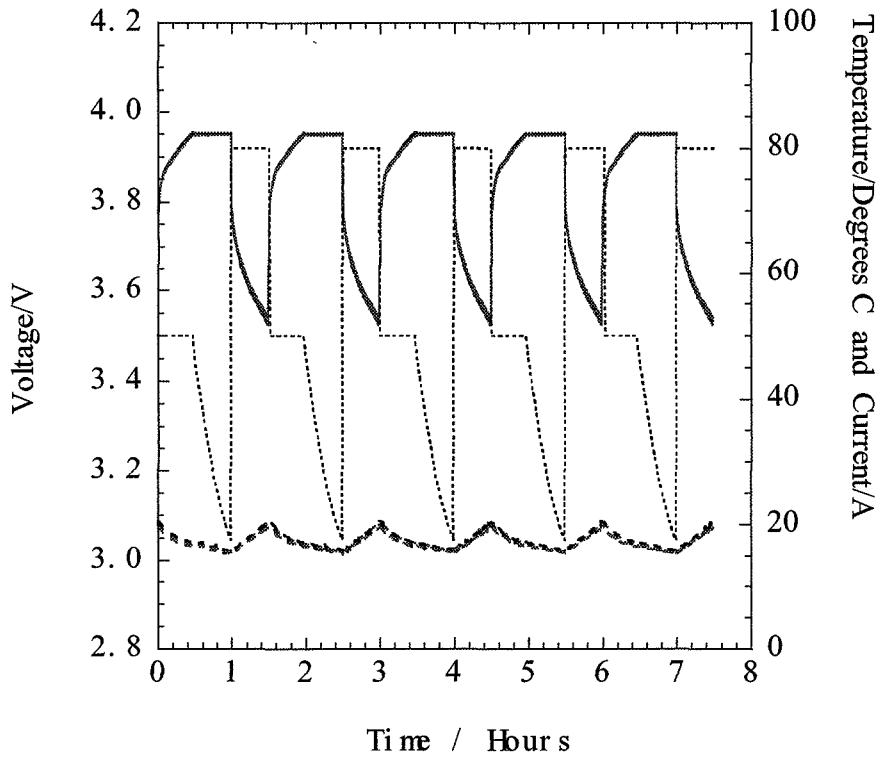

Fig. Recent Cycle Performance of DOD=40% LEO Test

Five cells are connected in series.

——— Voltage ——— Temperature · Current

Above figures are charge and discharge curves for recent five cy cles. Very stable performance is still observed.

Trend Data of 100 Ah $LiCoO_2$/Graphite Cells

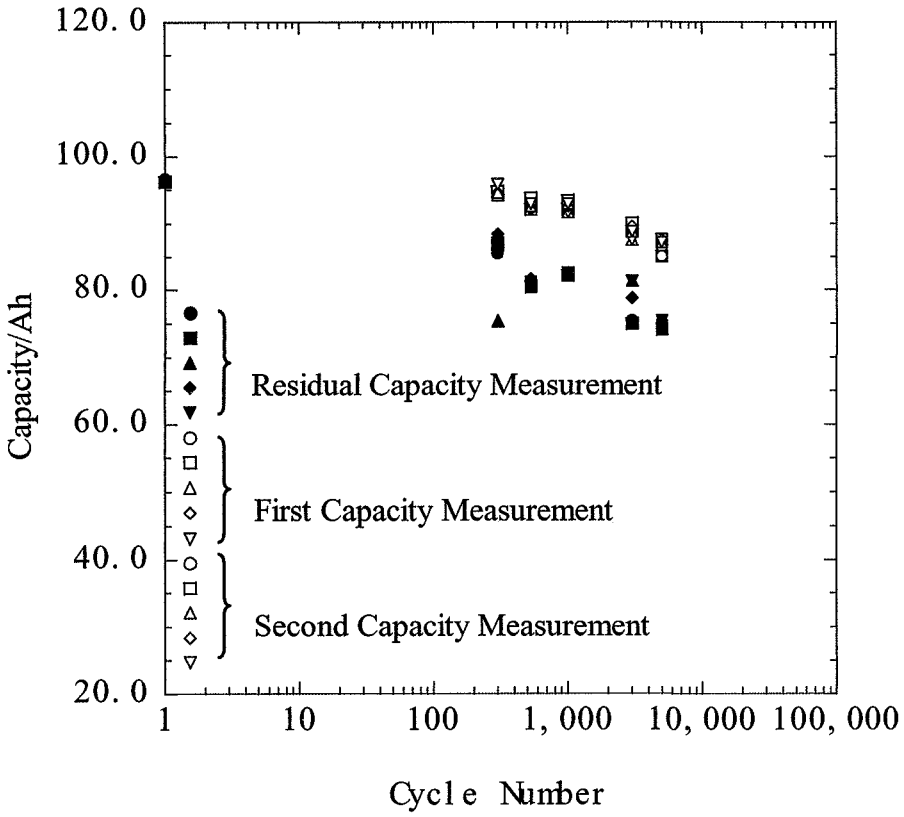

Fig. Capacity Trend by Cycles, LEO Test/DOD25%

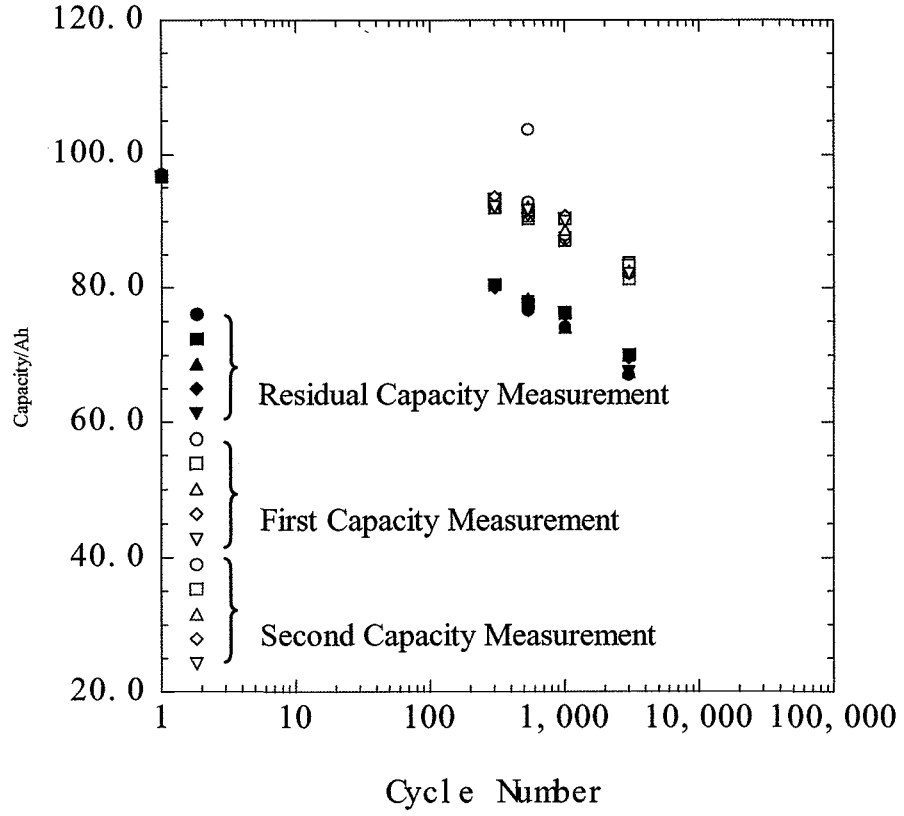

Fig. Capacity Trend by Cycles, LEO Test/DOD40%

Capacities of samples are decreasing slightly. Significant degr adation has not been observed, yet.

Trend Data of 100 Ah $LiCoO_2$/Graphite Cells

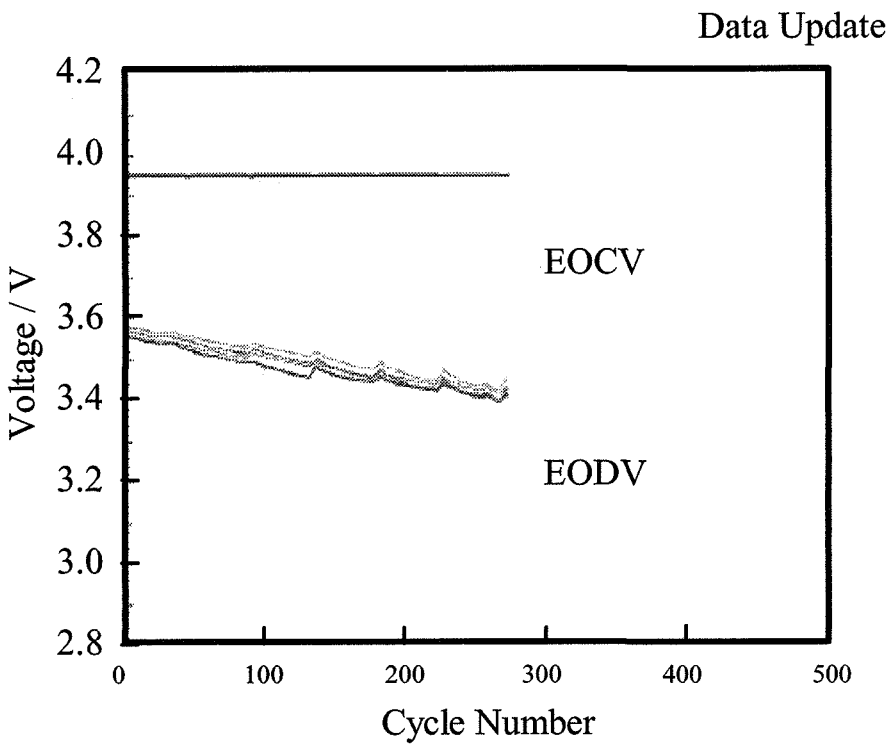

Fig. Life Cycle Trend of DOD=80% GEO Test
Five cells are connected in series.

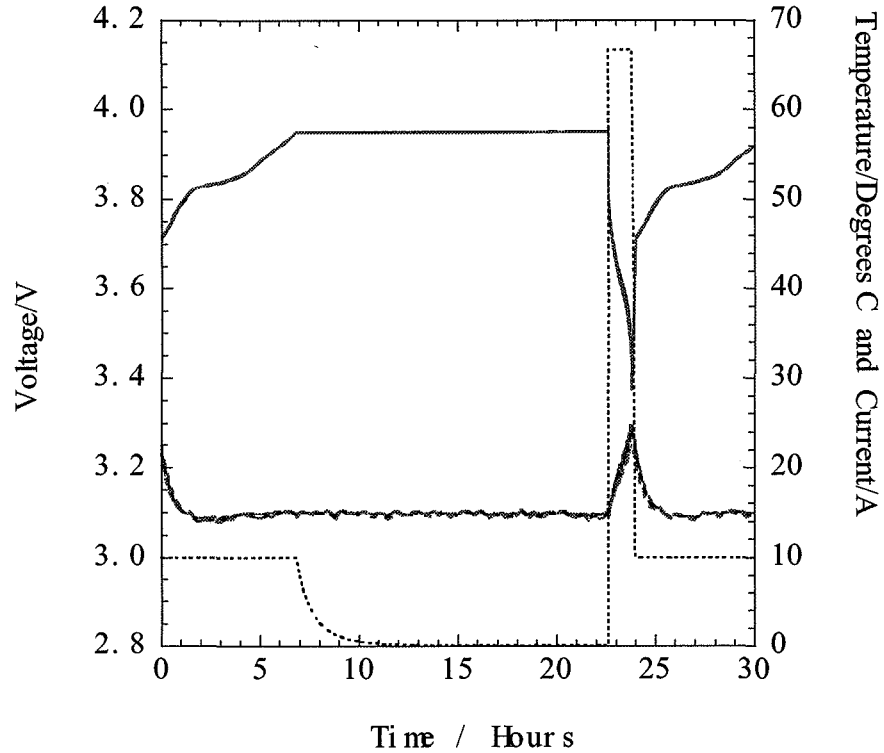

Fig. Cycle Curve of DOD=80% GEO Test
Five cells are connected in series.
——— Voltage ——— Temperature · Current

After 300 cycles, the end of discharge voltage decreased to 3.4 V. A constant decrease in the end of discharge voltage is still observed.

Trend Data of 100 Ah $LiCoO_2$/Graphite Cells

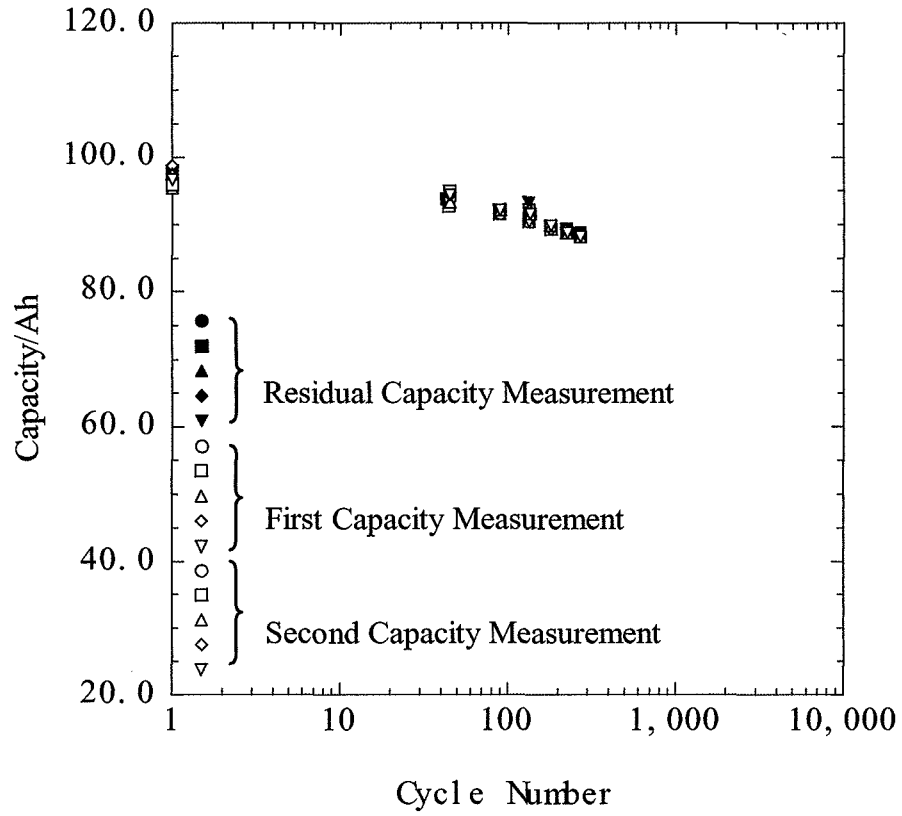

Fig. Capacity Trend by Cycles, GEO Test/DOD80%

Capacity of samples is decreasing slightly. Significant degrada tion has not been observed, yet.

Temperature Dependence of Capacity, 100 Ah $LiCoO_2$/Graphite Cells

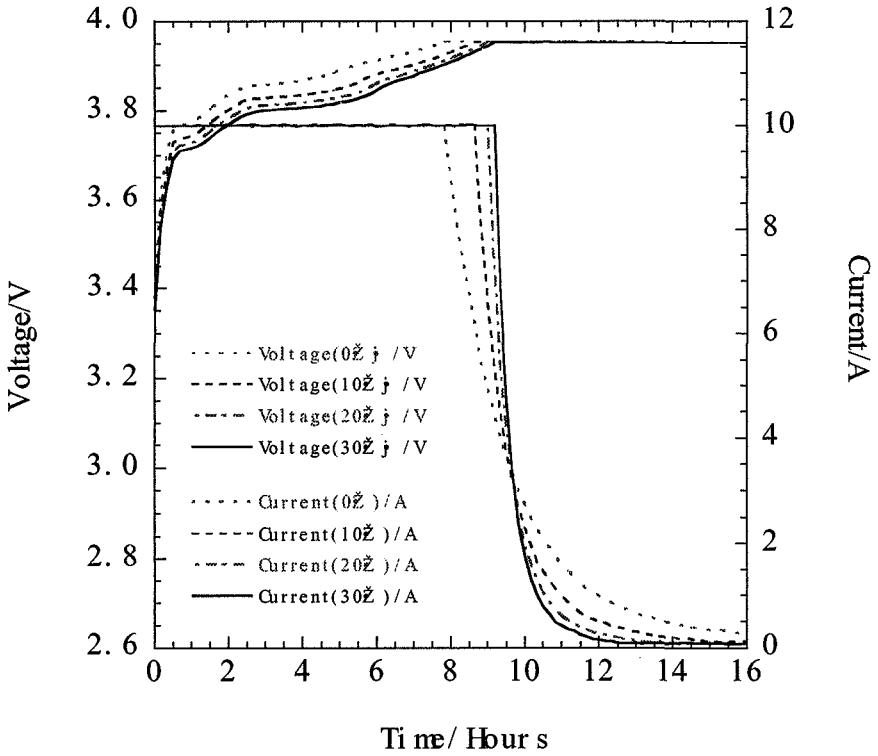

Fig. Charge curves

Charge Condition : CC(10 A)-CV(3.95 V)

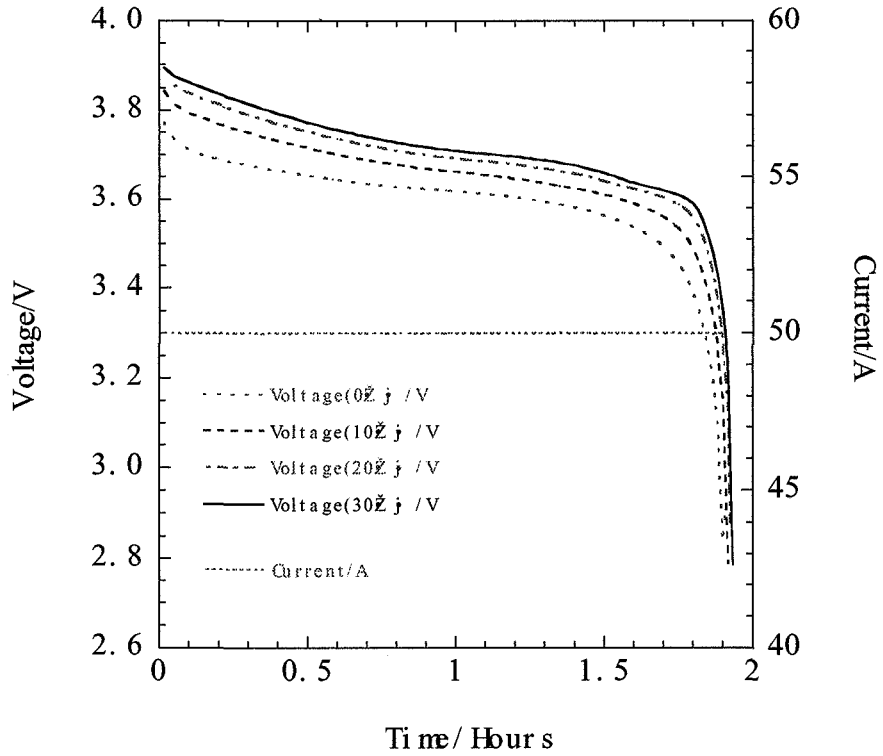

Fig. Discharge curves

Discharge Condition : CC(50 A) to 2.8 V

Fig. Capacity Measurement at different temperatures, measured before we started life cycle test.

We measured capacities of a cell at different temperatures. The re was an increase in charge voltage and a decrease in discharge voltage with decreasing temp erature, while we could obtain almost the same capacity in every measurement.

Temperature Dependence of Capacity, 100 Ah $LiCoO_2$/Graphite Cells

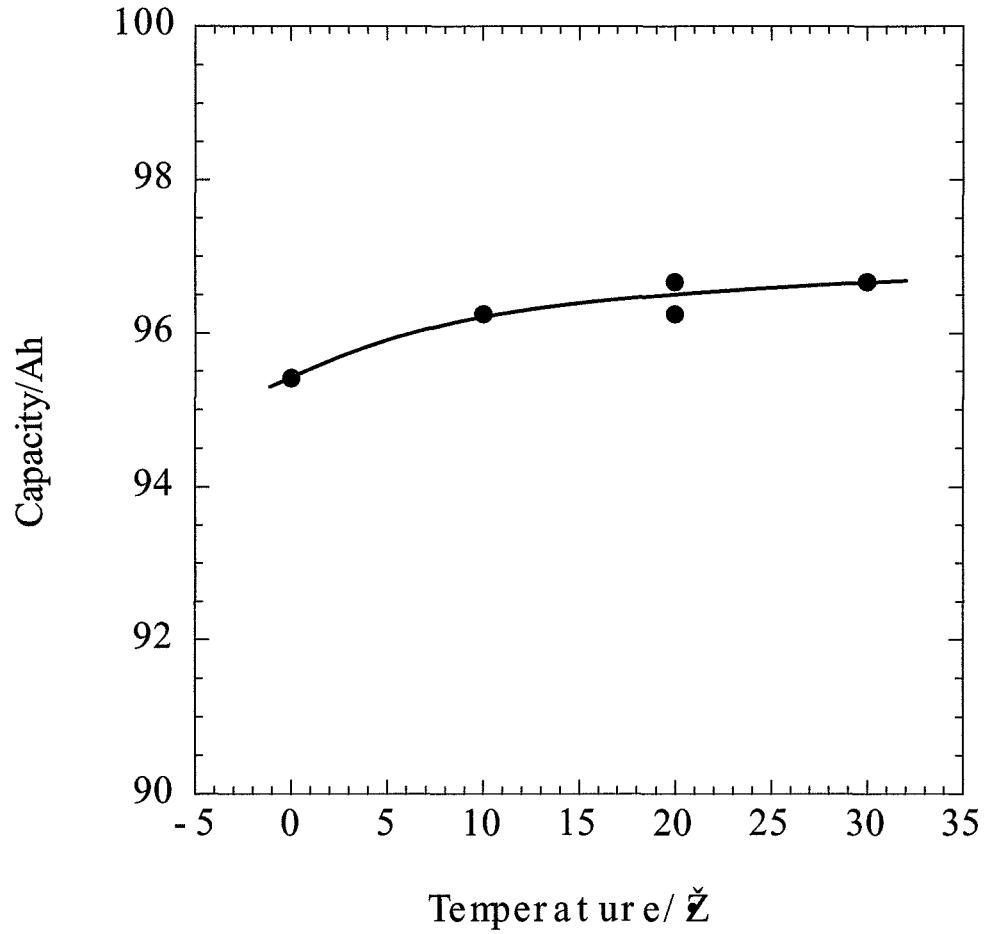

Fig. Temperature dependence of capacity
100 Ah Elliptic Cylindrical Cell from JSB.

We obtained a smaller capacity at 0 ., though the decrement was almost negligible.

90Ah $LiMn_2O_4$/Non-Graphite Cells

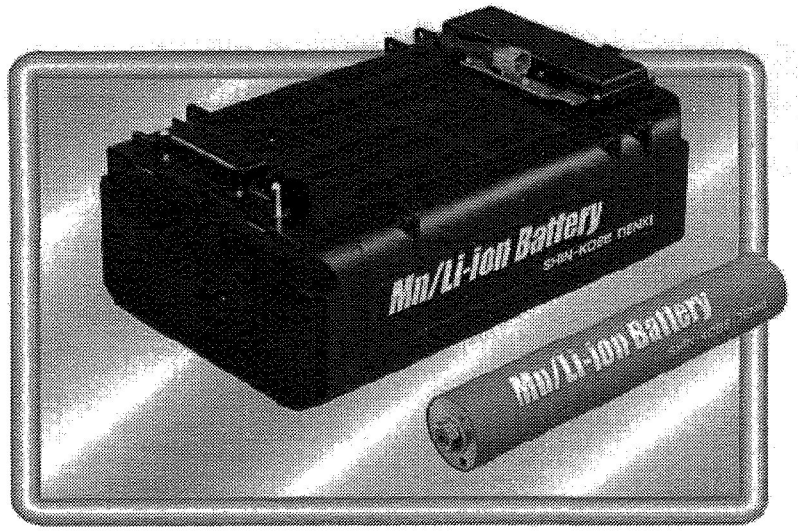

Cell Style		Cylinder
Electrode	positive electrode	LiMn 2O4
	negative electrode	C (non-graphite)
Capacity		90 Ah
Weight		3.3 kg
Dimensions		ƒ 67mm x 410 mm
Energy Density	per weight	104 Wh/kg
	per volume	237 Wh/L
Charge Voltage / Higher Limited Voltage		4.2 V
Discharge Voltage	Nominal Voltage	3.8 V
	Lower Limited Voltage	2.5 V

Above battery and cell are under development by the cooperation of IHI Aerospace Co. (IAC) and Shinkobe Electric Machinery Co. We started the collaboration with these companies, too, in 1999. They used $LiMn_2O_4$ and C (non-graphite) for the positive and negative electrode, respectively.

Trend Data of 90 Ah $LiMn_2O_4$/Non-Graphite Cells

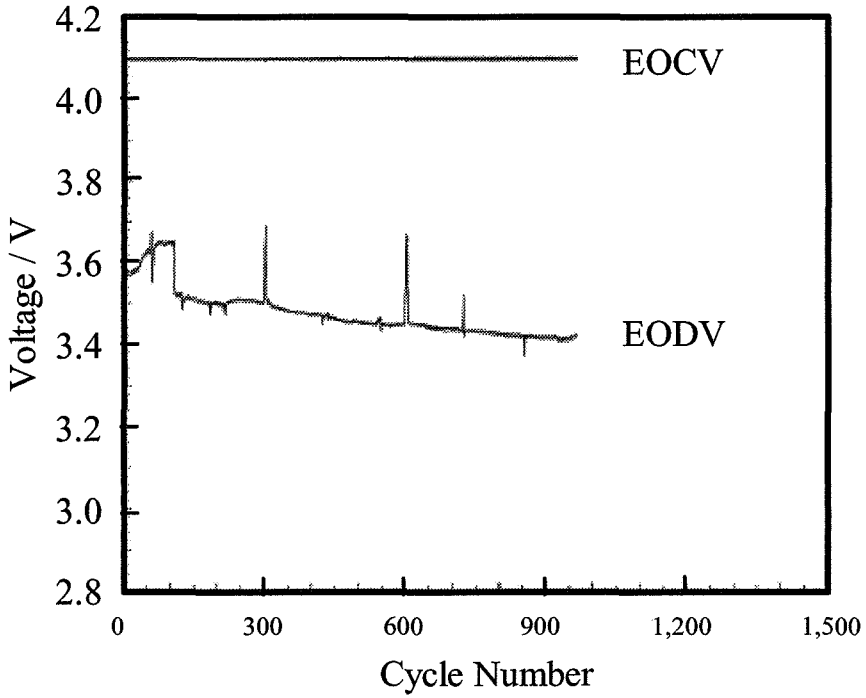

Fig. Life Cycle Trend of DOD=40% LEO Test
Five cells are connected in series.

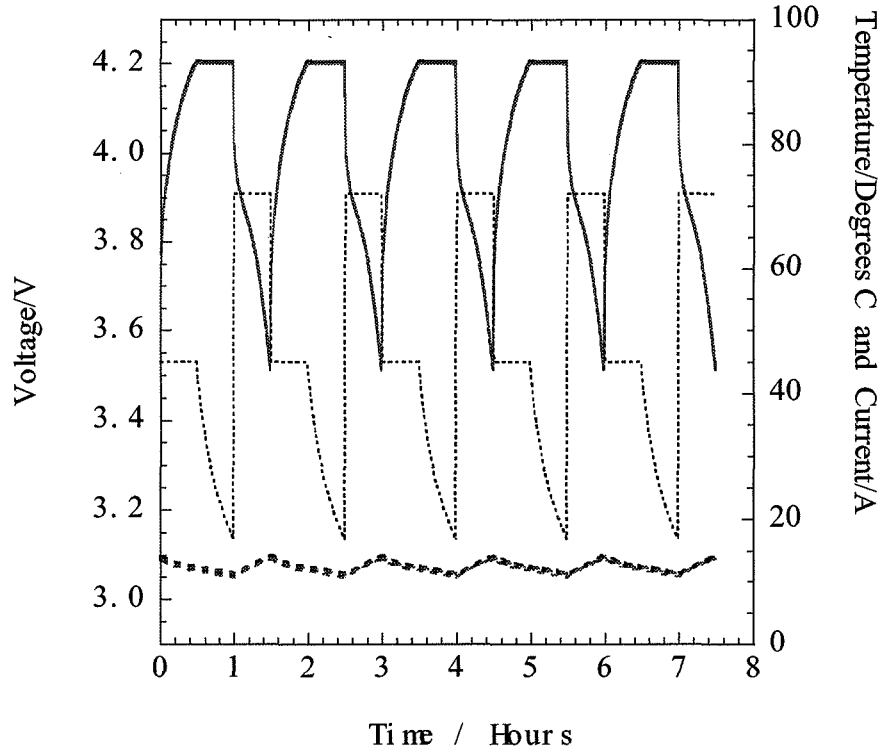

Fig. Recent Cycle Performance of DOD=40% LEO Test
Five cells are connected in series.
——— Voltage ——— Temperature · Current

Above figures show the trends of the performance during DOD=40% life cycle test. The charge and discharge curves of five cells in series have been al most identical through the test.

Trend Data of 90 Ah $LiMn_2O_4$/Non-Graphite Cells

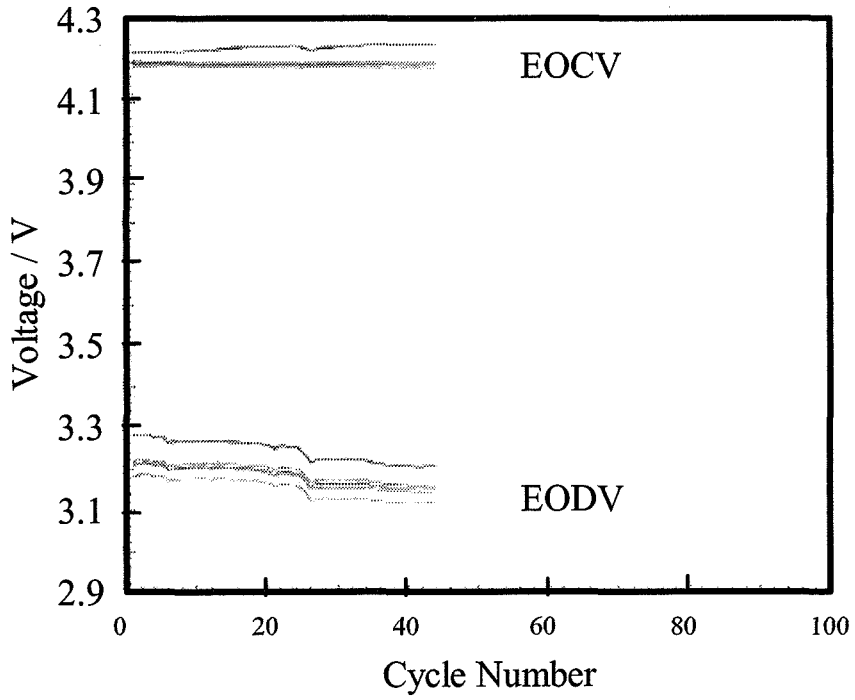

Fig. Life Cycle Trend of DOD=80% GEO Test

Five cells are connected in series.

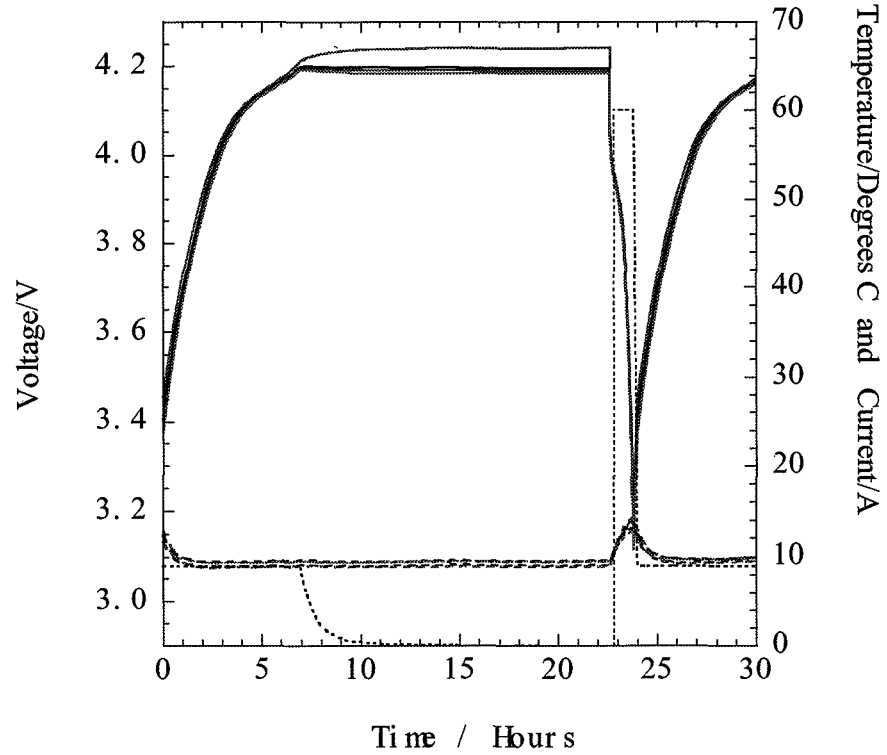

Fig. Recent Cycle Performance of DOD=80% GEO Test

Five cells are connected in series.

——— Voltage ——— Temperature · Current

One of the cells showed higher voltage in the both case of charg e and discharge. When we checked the capacity after 45 cycles, we discharged each cell down to 2.5V. We expected the same state of charge among these five cells by this treatment.

Trend Data of 90 Ah $LiMn_2O_4$/Non-Graphite Cells

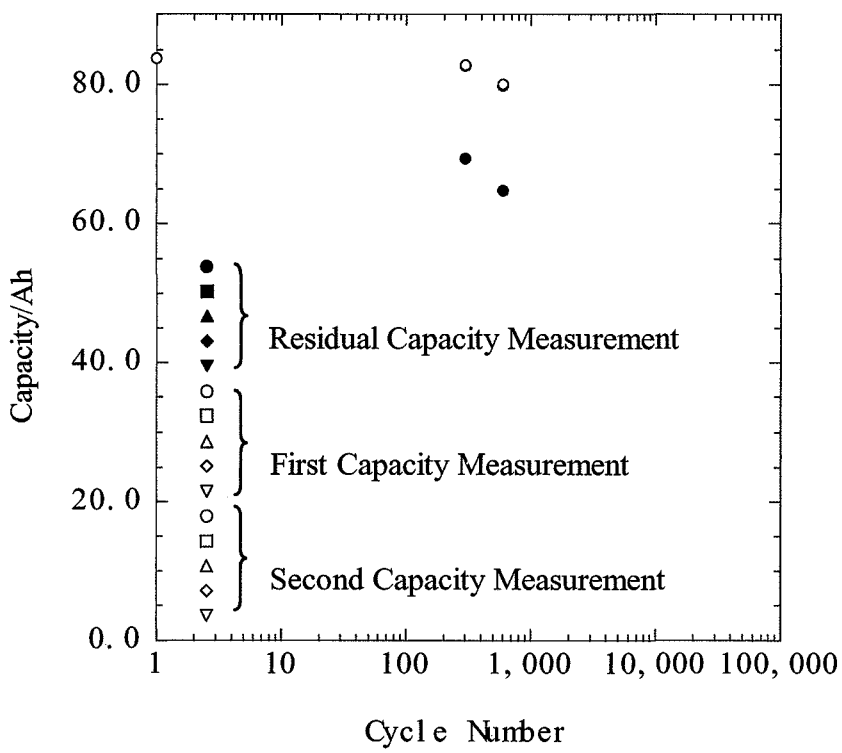

Fig. Capacity Trend by Cycles, LEO Test/DOD40%

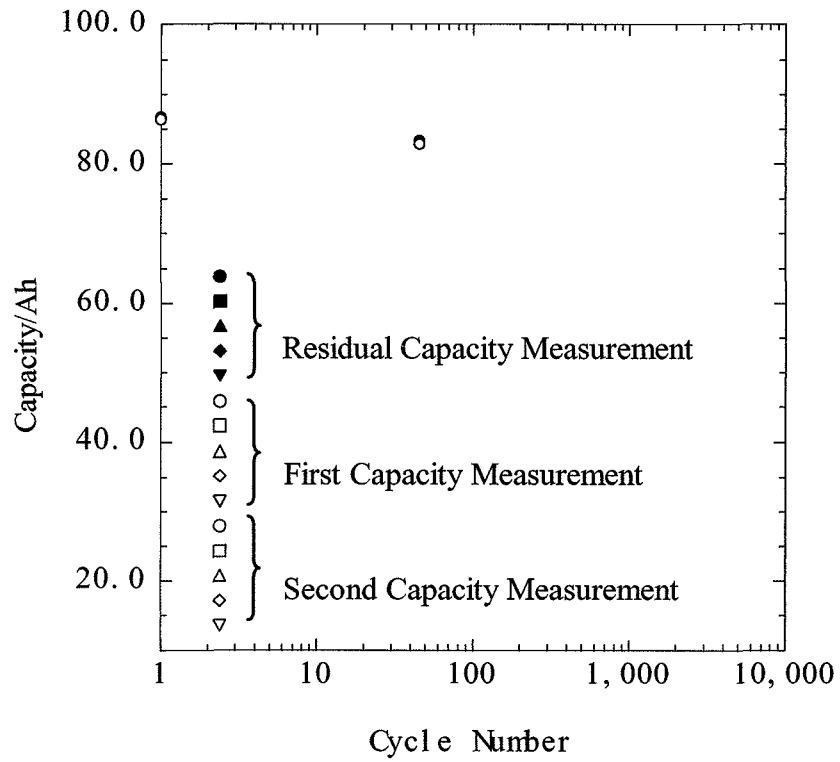

Fig. Capacity Trend by Cycles, GEO Test/DOD80%

Temperature Dependence of Capacity, 90 Ah $LiMn_2O_4$/Non-Graphite Cells

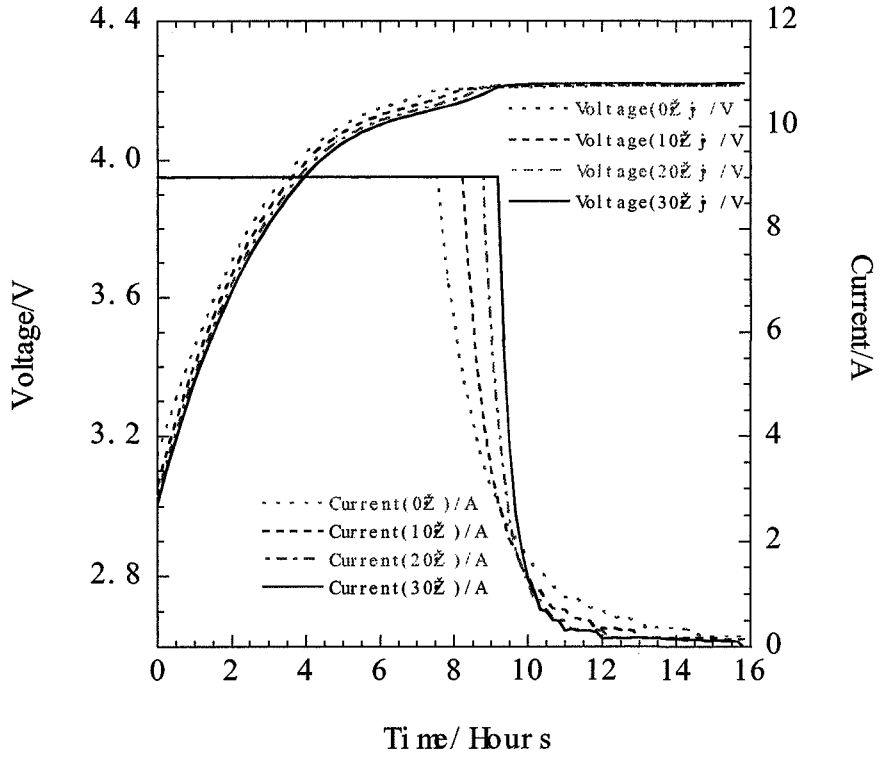

Fig. Charge curves

Charge Condition : CC(9 A)-CV(4.2 V)

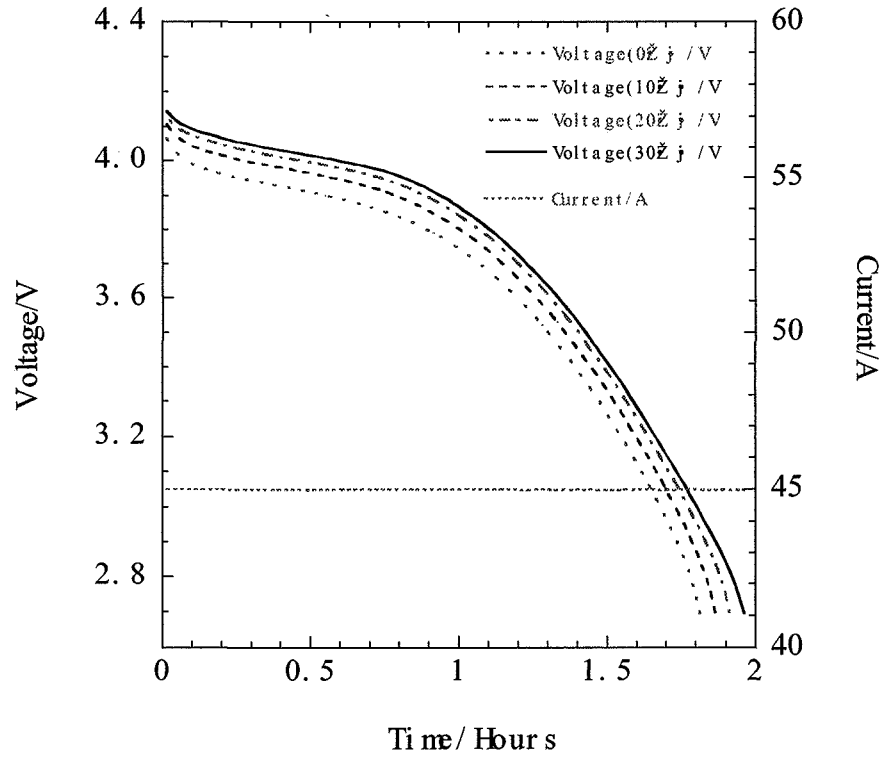

Fig. Discharge curves

Discharge Condition : CC(45 A) to 2.7 V

Fig. Capacity Measurement at different temperatures, measured at 45 cycle of GEO test.

We measured capacities of a cell at different temperatures. The typical curves of the cell using C (non-graphite) were observed. Because of this discharge curve, at lower temperature, we observed the decrease in capacity.

Temperature Dependence of Capacity, 90 Ah $LiMn_2O_4$/Non-Graphite Cells

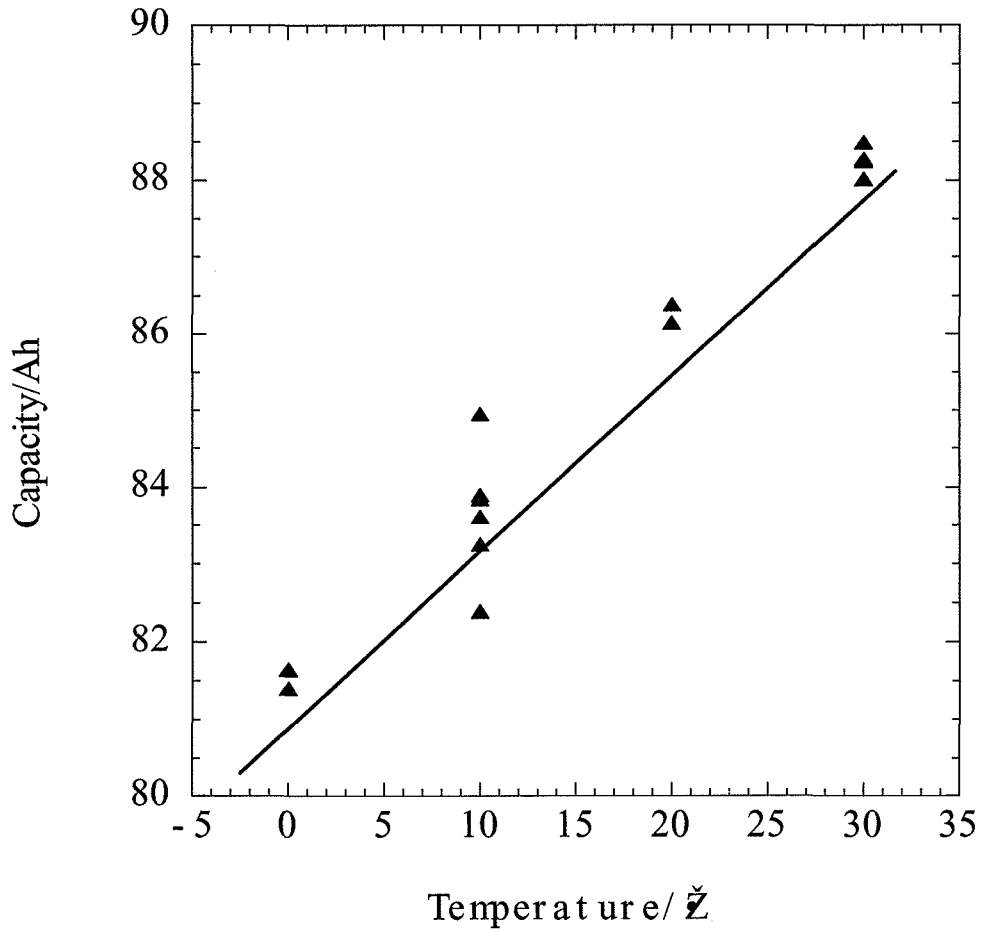

Fig. Temperature dependence of capacity
90 Ah Cylinder Cell from IAC.

Capacity of 90Ah cells linearly increased with temperature. The capacity at 0. was almost 8% smaller than that obtained at 30..

Summary

Life cycle performance of large size Li -Ion secondary cells is studied at Tsukuba Space Center, NASDA.

.10 Ah $LiCoO_2$/Graphite Cell
LEO simulating test reveals stable cycle performance of the cell s with series connection. We have already tested more than 6,000 life cycles in DOD=25/40% test.

.30 Ah $LiCoO_2$/Graphite Cell
More than 9,000 cycles have passed in DOD=25 /40% LEO cycle test .
The performance of cells have been very stable in the case of DO D=25%, while a considerable decrease in EODV and residual capacity was observed in the case of DOD=40%. In order to understand the degradation of DOD=40% samples, we performed destructive physical analysis. The analysis suggested us that the degradation of negative electrode played an important role in th e degradation of cell performance.
Based on these results, accompanied with the experience of 100Ah elliptic cylinder cells, we have started the discussion of the new trial cell which might enable high rate ch arge targeting LEO applications.

.100 Ah $LiCoO_2$/Graphite Cell
More or less than 5,000 cycles have passed in DOD=25/40% LEO cyc le test, and more than 300 cycles have passed in DOD=80% GEO cycle test. No significant degradation of the performance has been observed, yet. Thermal effect on capacity was also presented.

.90 Ah $LiMn_2O_4$/Non-Graphite Cell
The study of this type of cells has just started. More than 1,000 cycles in DOD=40% LEO test and 45 cycles in DOD=80% GEO test have passed. Thermal effect on capacity was also presented.

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

NASA/GSFC Testing of Li-Ion Cells: Update

Hari Vaidyanathan
Lockheed Martin Global Telecommunications
Clarksburg, Maryland
And
Gopalakrishna M. Rao
NASA-Goddard Space Flight Center
Greenbelt, Maryland

2000 NASA Aerospace Battery Workshop
Huntsville, Alabama
November 14-16, 2000

519/20/1/44
20011834 7 538086
16pr

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Objective

- Cell Characterization
  - Capacity
  - Self-discharge
  - Mid-discharge voltage
- Determination of Cycling Performance as a Battery Pack under LEO regime
  - Number of cycles
  - Charge voltage
  - Temperature

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Cells Under Study

- Prismatic Cells
  - 20 AH Yardney
  - 1.5 AH Wilson Greatbatch
- Cylindrical Cells
  - 12 AH, 4 AH and 1.25 AH SAFT
- Polymer cells
  - 3 AH Alliant Tech.
  - 8 AH Lithium Technology, Inc.

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Characterization Data

- Self-discharge - 72 hours charged open-circuit stand
  - Yardney = 1.4%
  - SAFT =1.4%
  - Alliant Tech (ATK) = 2%
  - Wilson Greatbatch (WG) =1.4%
- Capacity Decrease when the discharge rate is increased to C/2 from C/5
  - Yardney - 2%
  - SAFT - 0.9%
  - ATK - 2%
  - WG - 25%

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Characterization Data -Contd.

- Mid-discharge voltages at C/2 discharge rate
  - Yardney = 3.51V
  - SAFT = 3.56V
  - ATK = 3.54 V
  - WG = 3.65V
- Cell impedance (mohms) at 50% SOC
  - SAFT = 1.74
  - Yardney = 10.2
  - ATK = 51
  - WG = 68

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

Characterization Data -Contd.

- Capacity at 0°C in percentage of capacity at 25°C

  - Yardney = 92%
  - SAFT = 91%
  - WG = 91%
  - ATK = 51%

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

LEO Cycling: Conditions

- Continuous cycling in a regime consisting of 30 min. discharge and 60 min. charge at the rate of 16 cycles/day
- Temperature = -20°C to 40°C
- Depth of discharge = 40%
- Charge voltage clamped at a Battery/Pack voltage at C/2 rate with current taper
- Recharge ratio = 1-1.01

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

LEO Cycling: Data

Number of cells and cell type	CAP, AH AT 25°C	Charge V limit	CYCLES	STATUS
8 - SAFT 12AH	11.4	3.85	2745	Continuing
8 - Yardney 20AH*	24.9	4	2739	Continuing
5 - Alliant Tech 3AH	2.06	4	2359	Discontd
8 - WG 1.5AH	1.43	4.1	10	Discontd
8 - Li-Tech 8AH	7.1	4.1	2	Discontd
2 - SAFT 4AH	4	3.85	7472	Continuing
2 - SAFT 1.25AH	1.3	3.85	11323	Continuing

* Cells 192, 194, 195 and 196 have previously completed 2966 cycles.

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VARIATION OF EOD VOLTAGE FOR SAFT 12 Ah CELLS AT 20°C, 3.85V LIMIT

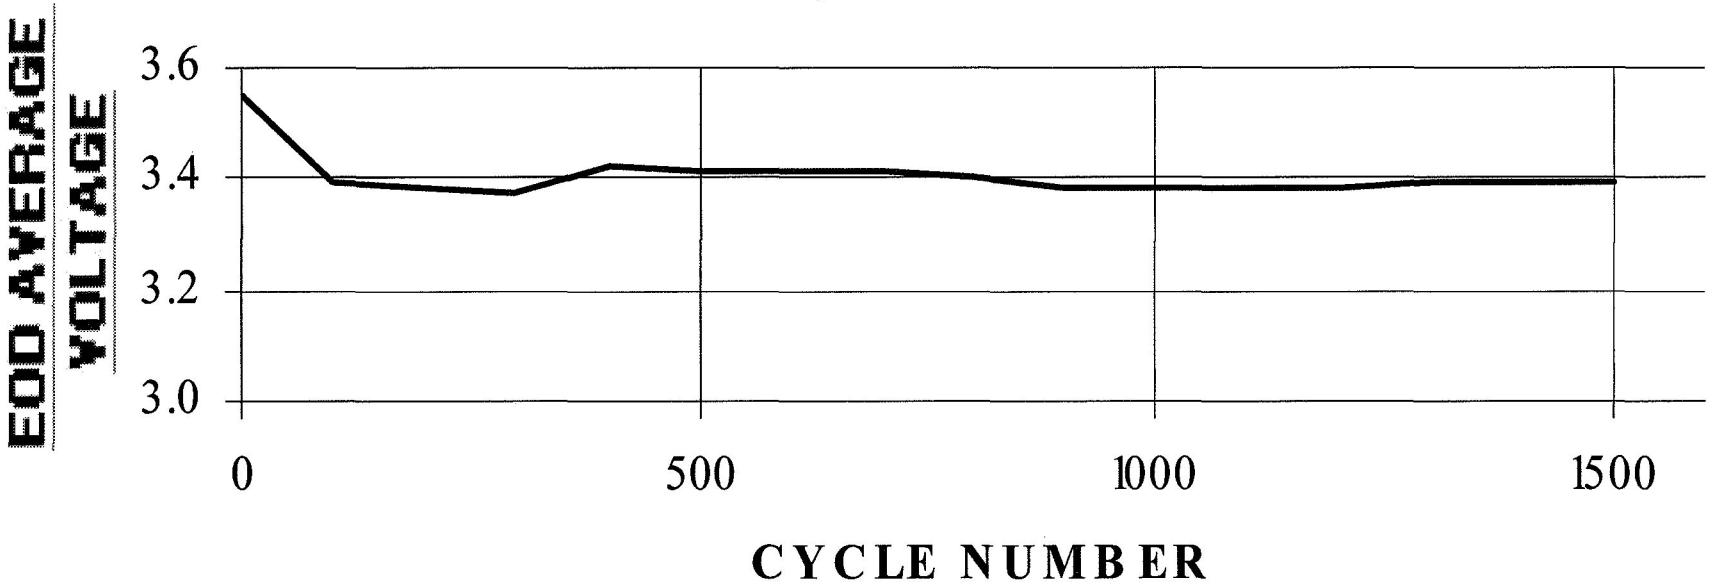

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VARIATION OF END OF DISCHARGE VOLTAGE WITH CYCLING FOR WG CELLS AT 20°C, 4.1 V LIMIT

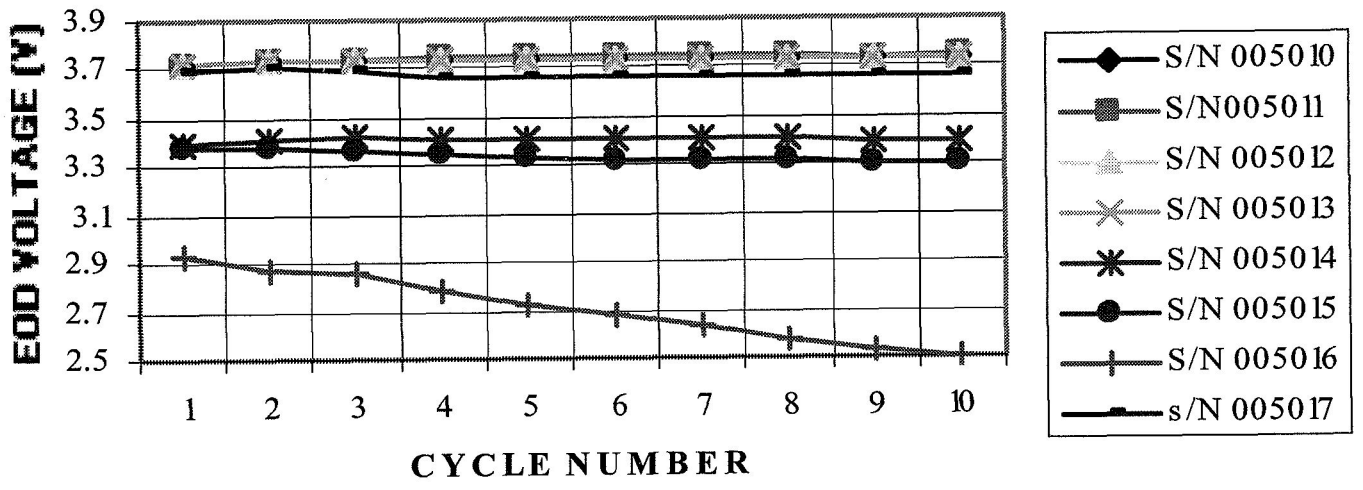

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VARIATION OF EOD WITH CYCLING FOR SAFT 1.25 AH CELL AT 30°C, 3.85V LIMIT

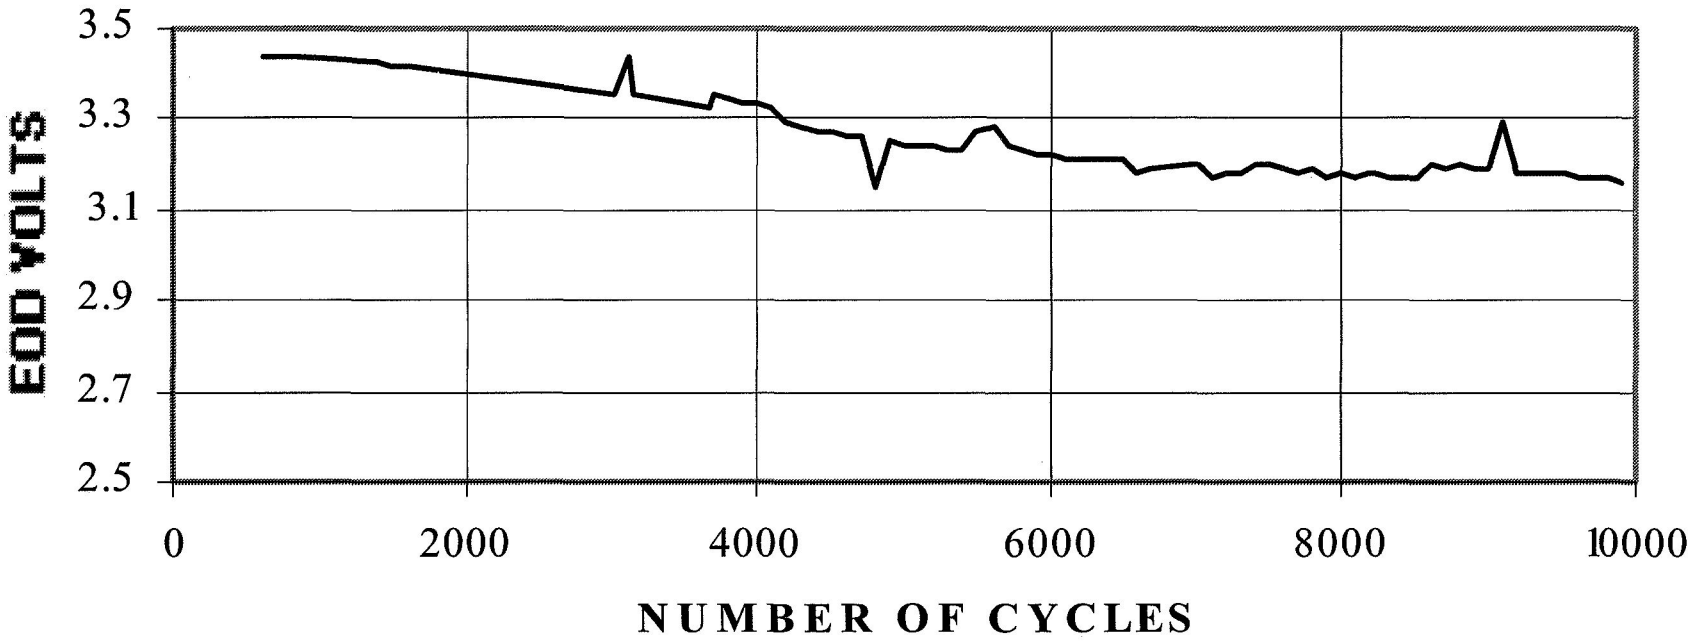

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VARIATION OF EOD VOLTAGE WITH CYCLING FOR YARDNEY 20 AH CELLS AT 20°C, 4V LIMIT

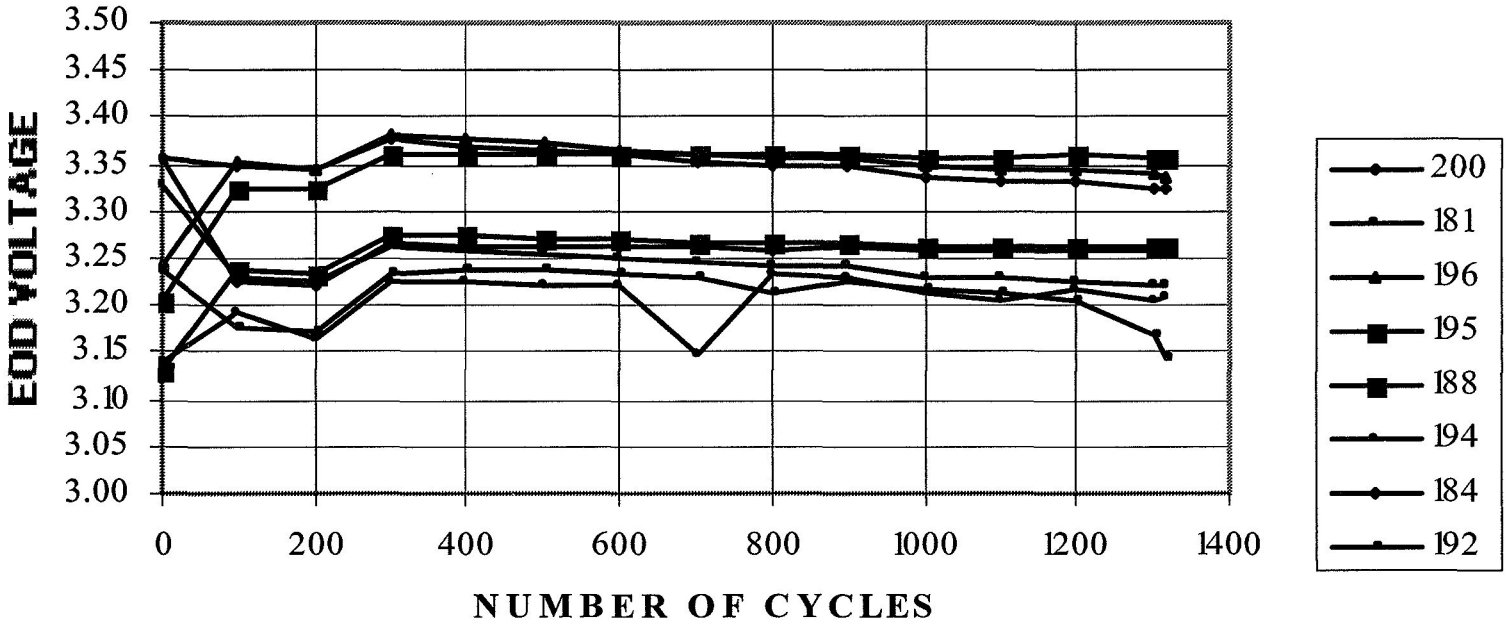

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

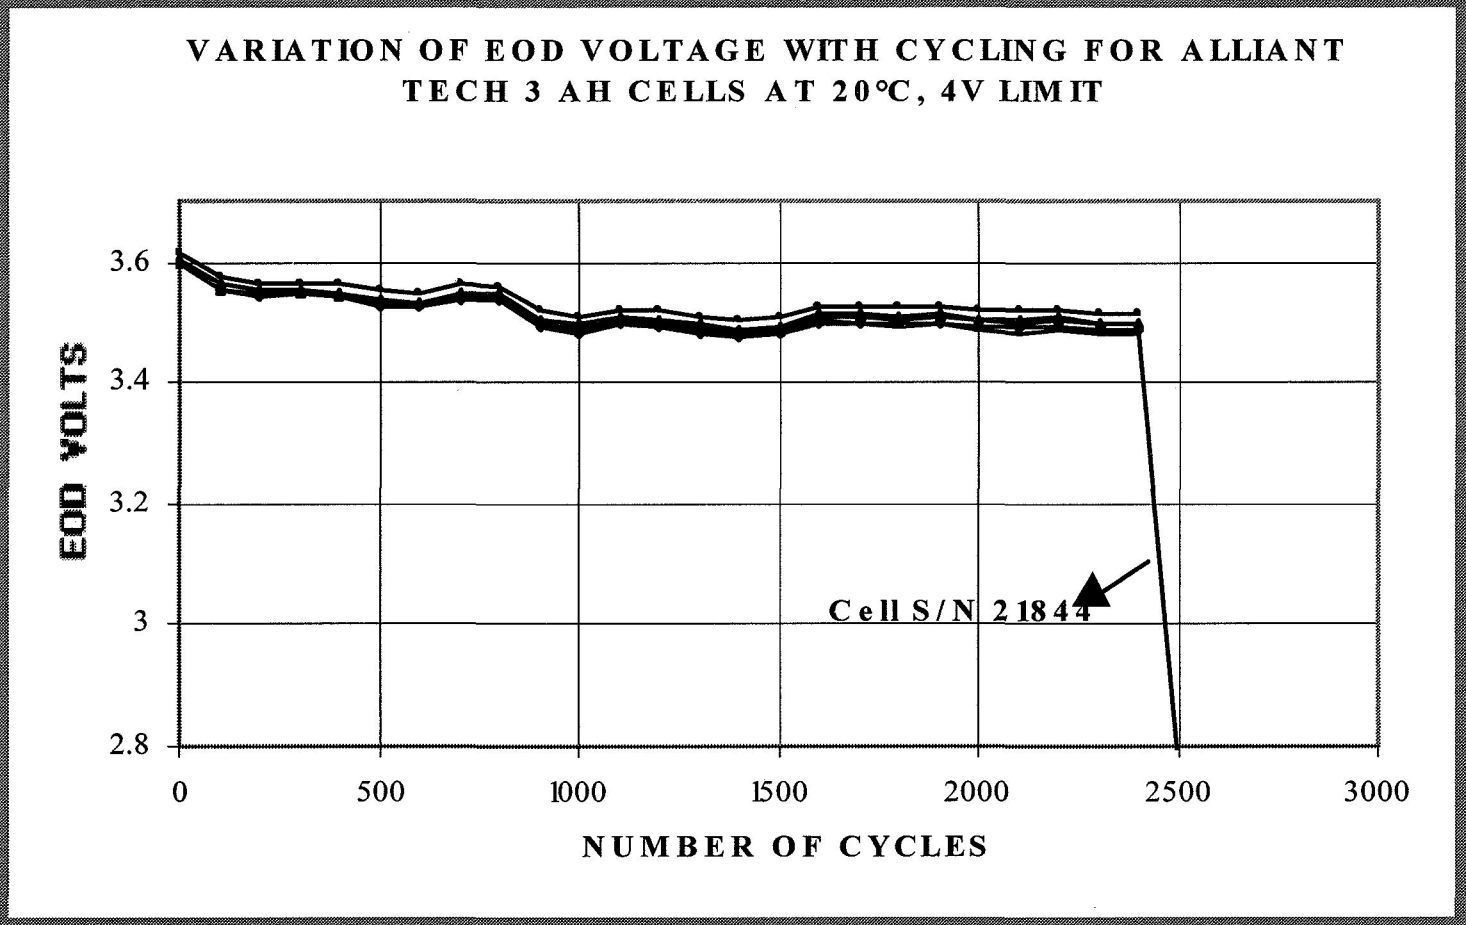

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

PERFORMANCE TWO 2-CELL SAFT 4 AH BATTERIES

Temp °C	Number of cycles	End of dischg voltage	Comments
30	4289	3.217	cell charged to 3.85V
40	550	3.266	cell charged to 3.85V
0	560	2.816	cell charged to 4.1V
-20	2	2	cell charged to 4.3V
-10	39	2.755	cell charged to 4.48V
10	442	3.039	cell charged to 4.1V
20	6157	3.17	cell charged to 3.85V

LOCKHEED MARTIN
GLOBAL TELECOMMUNICATIONS

VOLTAGE BEHAVIOR DURING CYCLING FOR SAFT 4AH CELLS

20°C, 3.85 V LIMIT

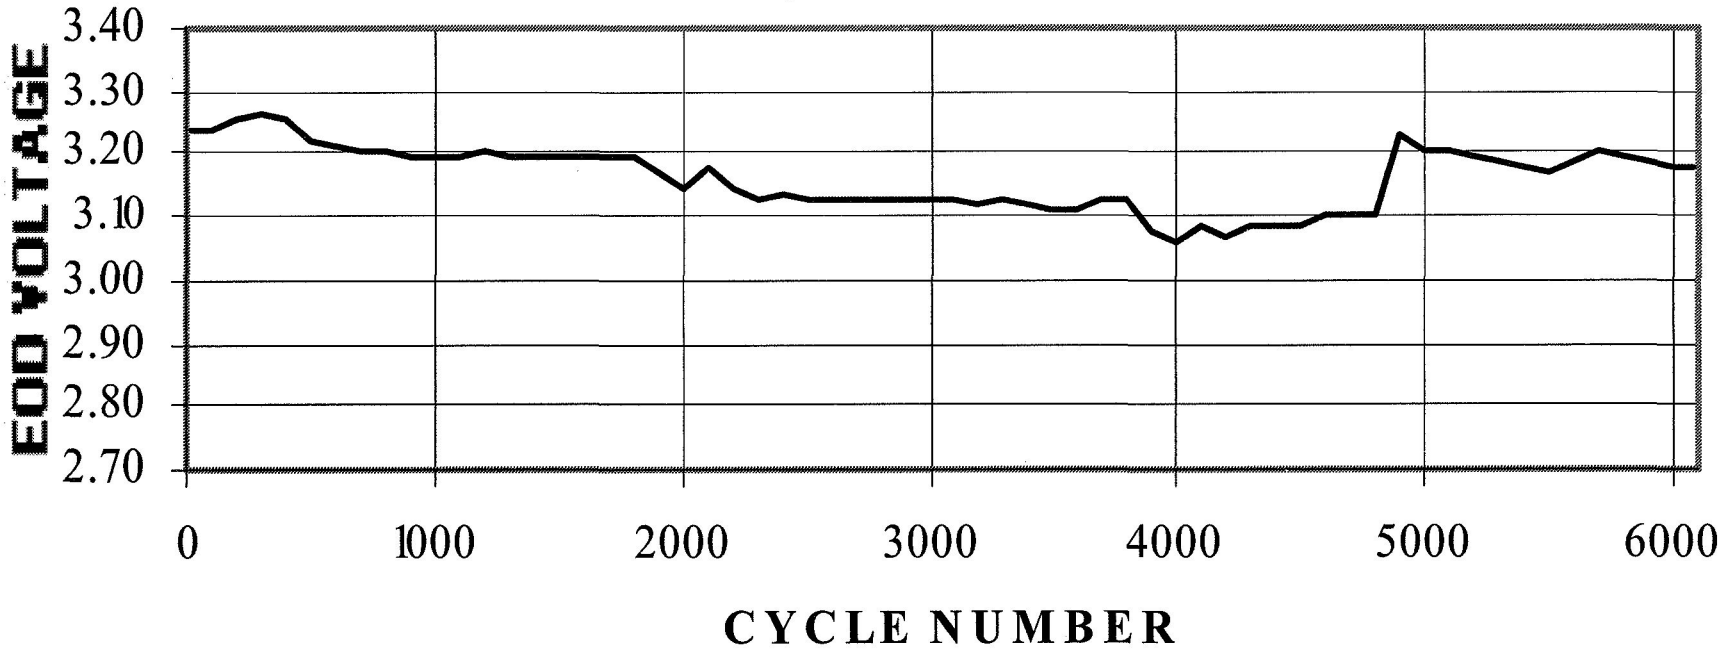

Conclusions

- The self-discharge rate of Li-ion cells is 1.4% in the 72 -hr charged open-circuit stand test that is superior to NiCd and NiH_2 Batteries
- Charge acceptance of the cells decreases with temperature
- Cells cannot be cycled in a 90 -minute orbit and 40% DoD at minus 10°C unless the voltage limit on charge is increased to 4.5V
- Limited cycling excursion to minus 20°C (low temperatures) does not appear to impair the cycling behavior at 20°C
- The solid electrolyte and gel electrolyte cells' performance is inferior to the liquid electrolyte cells under our LEO test conditions
- The data suggests the potential use of a battery level charging by monitoring and managing the cell parameters

LOCKHEED MARTIN

Li-ion EMU Battery Testing

Raymond Rehm

Lockheed Martin Space Operations

Bobby Bragg

NASA Johnson Space Center

Brad Strangways

Symmetry Resources

Sept 1 of 1 mt 1 of 1

20011183 49

538093

12 p 5

EMU BATTERY LIFE TESTING OBJECTIVES

- A 45Ah Li-ion battery comprised of five (5) Yardney prismatic cells is being evaluated to replace the silver-zinc cells in the Extra-vehicular Mobility Unit (EMU).
- The tests being conducted at Symmetry Resources are to determine if the 5 cell battery can meet the mission objective of 500 duty cycles and maintain a minimum voltage of 16.0 V without an individual cell voltage dropping below 3.0V.
- 40 Real Time cycles were conducted to develop BOL trend data (This accomplishment would exceed the current silver-zinc capability).
- Decision to switch to accelerated cycling for the remaining 460 cycles was made since “Real Time” cycling requires 1 day/cycle.

This presentation covers the initial test data

WHY CHANGE THE EMU BATTERY?

Silver Zinc Design	Li-ion Design
11 Zn/AgO Cells in Series	5 $LiNi_{1-X}Co_xO_2$ Cells in Series
Cell Compliment Wt = 11.6 lbs	Cell Compliment Wt = 12.2 lbs
Cell Compliment Cost = $10K	Cell Compliment Cost = $20K
45Ah Capacity BOL (Full Cap)	45Ah Capacity BOL (Full Cap)
425 Day Wet Life, 32 Cycle Life	Goal of 5 yr Wet Life, 500+ Cycle Life
237.6 Wh/L BOL	262.8 Wh/L BOL
141.0 Wh/Kg BOL	148.8 Wh/Kg BOL

EMU BATTERY LIFE TESTING

Characterization Testing at 50°C, 25°C, -10°C

40 Real Time Cycles at 25°C

460 Accelerated Cycles at 25°C

Characterization Testing at 50°C, 25°C, -10°C

YTP 45A-h Li-Ion EMU Battery Cycling Tests

Initial Conditioning Cycle, 25 deg. C

Battery/Cell Charge Voltage Profiles

4.50A to 21.0V (4.25V) battery (cell) voltage

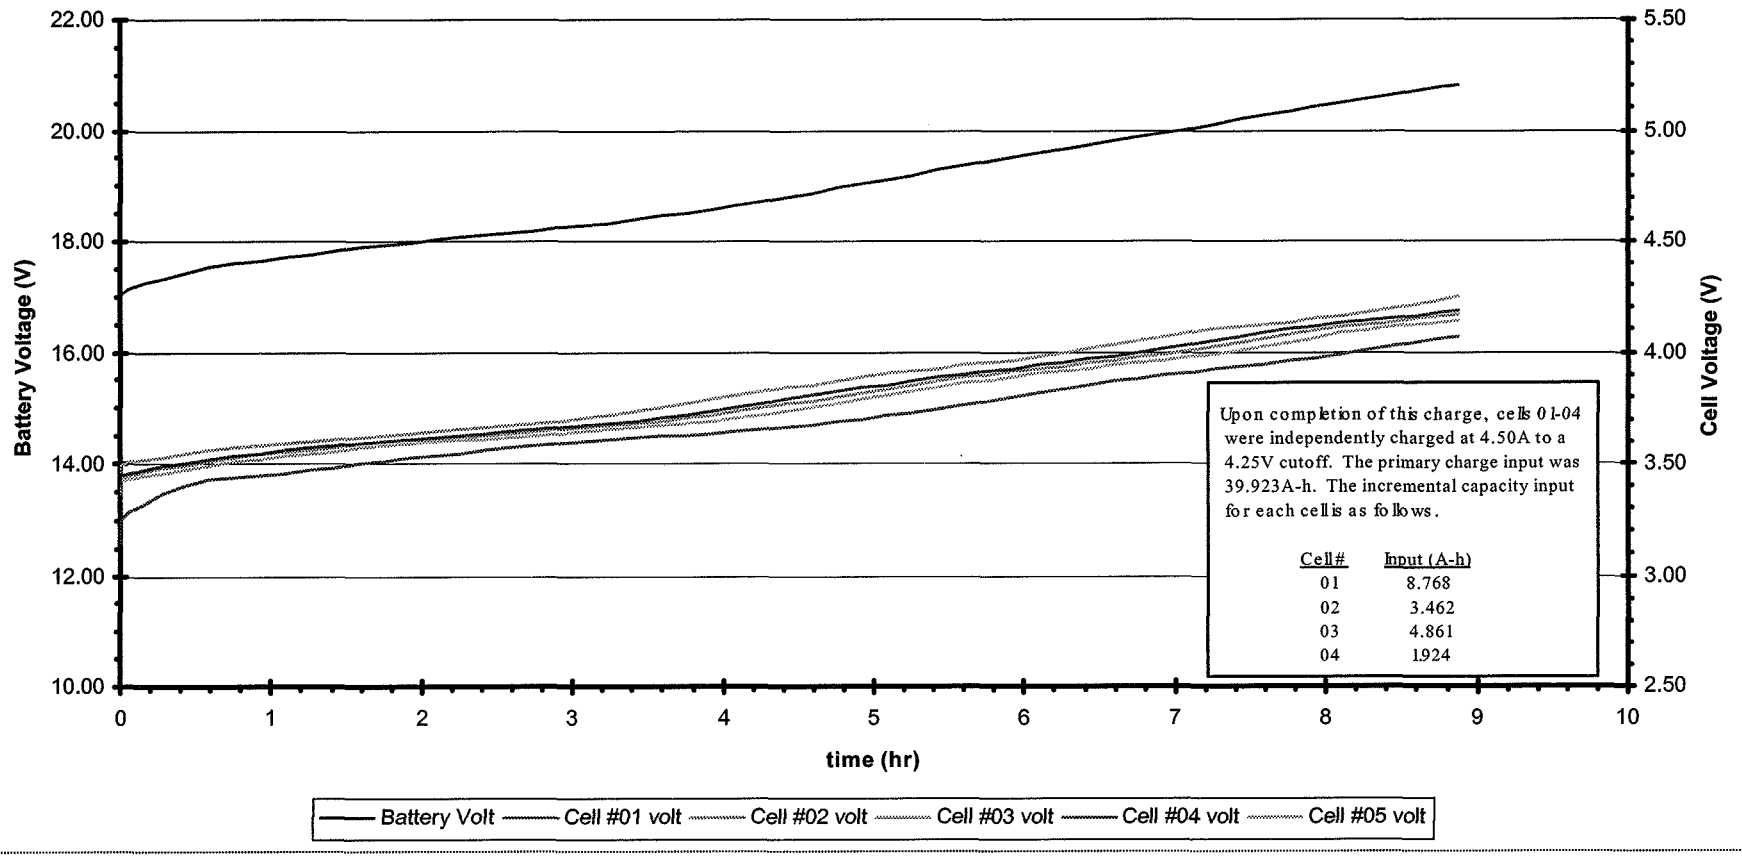

CHARACTERIZATION TESTING

Stabilize at Temperature

Charge at 4.5 amps to Battery Voltage of 21.0V or Cell Voltage 4.2V

Discharge at 10.0 amps to Battery Voltage of 14.5V or Cell Voltage of 2.7V

50°C Capacity = 48.09Ah (107.0% of 25°C)

25°C Capacity = 44.96Ah

-10°C Capacity = 31.31Ah (69.6% of 25°C)

REAL TIME CYCLING

Discharge at 3.8 amps for 7 hours or Battery Voltage of 16.0V, Cell Voltage of 3.0V

Charge at 1.55 amps for 20 hours or Battery Voltage of 20.5V, Cell Voltage of 4.1V

Every 20th Cycle, Continue Discharge to Battery Voltage of 16.0V, Cell Voltage of 3.0V

40 CYCLES COMPLETED

ACCELERATED CYCLING

Discharge at 11.0 amps for 2 hours 25 minutes or Battery Voltage of 16.0V, Cell Voltage of 3.0V

Charge at 11.0 amps to a Battery Voltage of 20.5V, Cell Voltage of 4.1V.

Then charge at 5.0 amps to a Battery Voltage of 20.5V, Cell Voltage of 4.1V.

Then charge at 2.0 amps to a Battery Voltage of 20.5V, Cell Voltage of 4.1V.

Then charge at 1.0 amp to a Battery Voltage of 20.5V, Cell Voltage of 4.1V.

Every 20 Cycles Discharge Battery at 3.8 amps to 16.0V (Cell Voltage of 3.0V)

CYCLING IN PROGRESS

CYCLE 19, 40 AND 120 BATTERY DISCHARGE VOLTAGE COMPARISONS

(Discharged at 3.8amps to 16.0V)

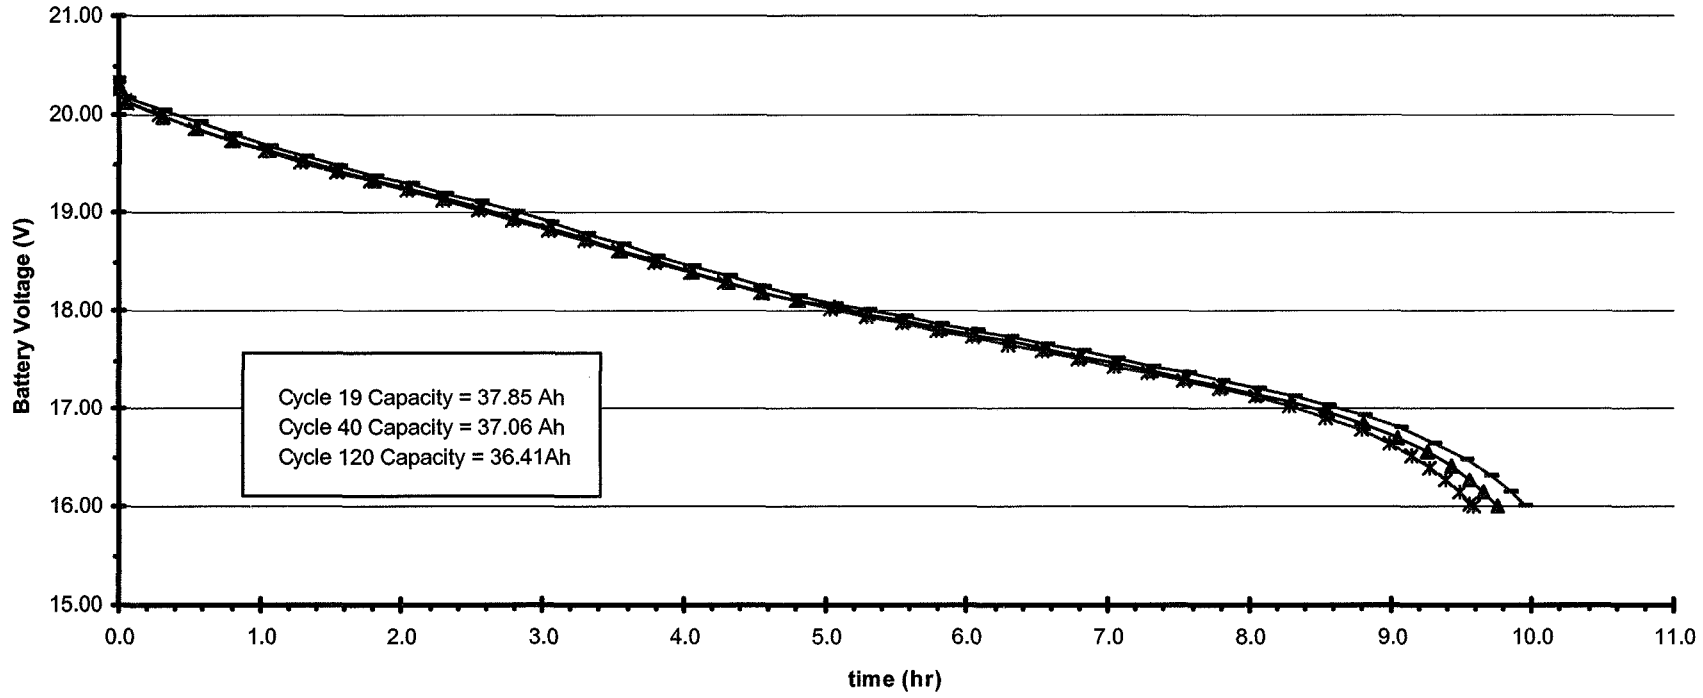

YTP 45A-h, 5-cell Li-Ion EMU Battery Cycling Tests

Real Time and Accelerated Cycling at Room Temp.

End-of-Discharge Battery Voltage versus Cycle Trend

3.8A to 16V (3.0V) battery (cell) voltage on 20 cycle interval; All other cycles to 26.6A-h

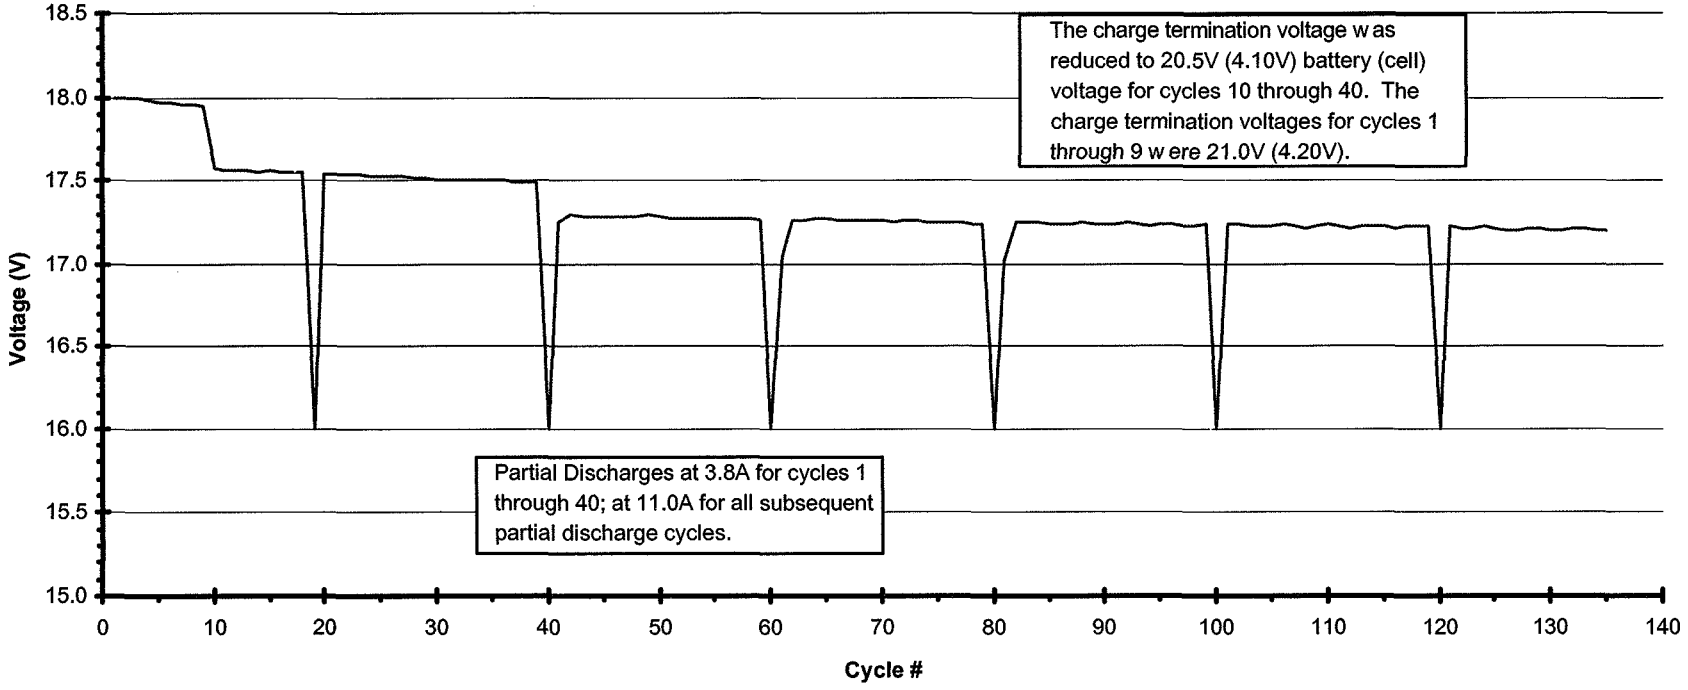

LOCKHEED MARTIN

YTP 45A-h, 5-cell Li-Ion EMU Battery Cycling Tests

Real Time and Accelerated Cycling at Room Temp.

End-of-Discharge and End-of-Charge Cell Voltage Differentials

3.8A to 16V (3.0V) battery (cell) voltage on 20 cycle interval; All other cycles to 26.6A-h

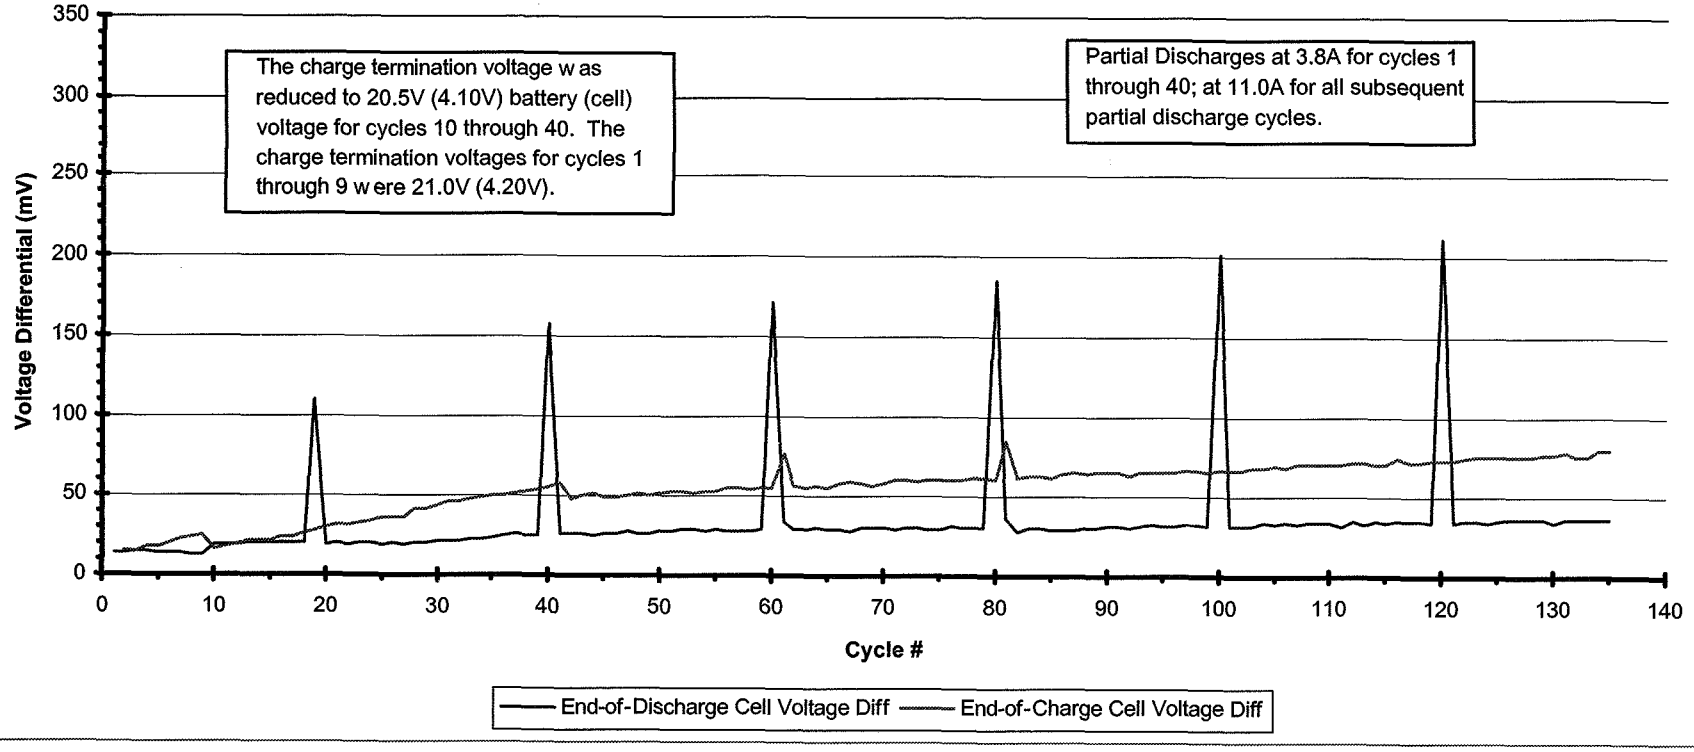

SUMMARY

- The Data Indicates the Potential to Meet the 500 Cycle Objective Within the EMU Mission Requirements.
- Capacity to 16.0 Volts at 120 Cycles (36.41Ah) Exceeds Requirement by 36.9 %.
- Battery Charge Method and Cell Protective Circuitry Need to be Addressed.
- 40 Additional Cells Have Been Ordered for Additional Performance and Safety/Abuse Testing for This Cell Design.

PERFORMANCE AND ABUSE TESTING OF 5 YEAR OLD LOW RATE AND MEDIUM RATE LITHIUM THIONYL CHLORIDE CELLS

2000 NASA AEROSPACE BATTERY WORKSHOP

Rick Frerker

Wenlin Zhang, PhD

Schlumberger

Judith Jeevarajan

Lockheed Martin / NASA-JSC

Bobby J. Bragg

NASA-JSC

521/CP/NI/444 20011183 50 33849 33P

5 Year Old Lithium Thionyl Chloride Cells Used In The Test (18 each type)

- Low Rate ‘ D’ Part No. LTC-114
  - 14 Ahr (@50 ohms and 3.0V cutoff)
  - Sandia Design
- Medium Rate ‘ D’ Part No. LTC-111
  - 12 Ahr (90 mA and 2.5V cutoff at 25 °C
- Medium Rate ‘ sub D’ Part No. LTC-115
  - 11 Ahr (100 mA and 2.0 V cutoff at 25 °C
  - Sandia Design, Military Aviation qualified cell

Test Plan (Overview)

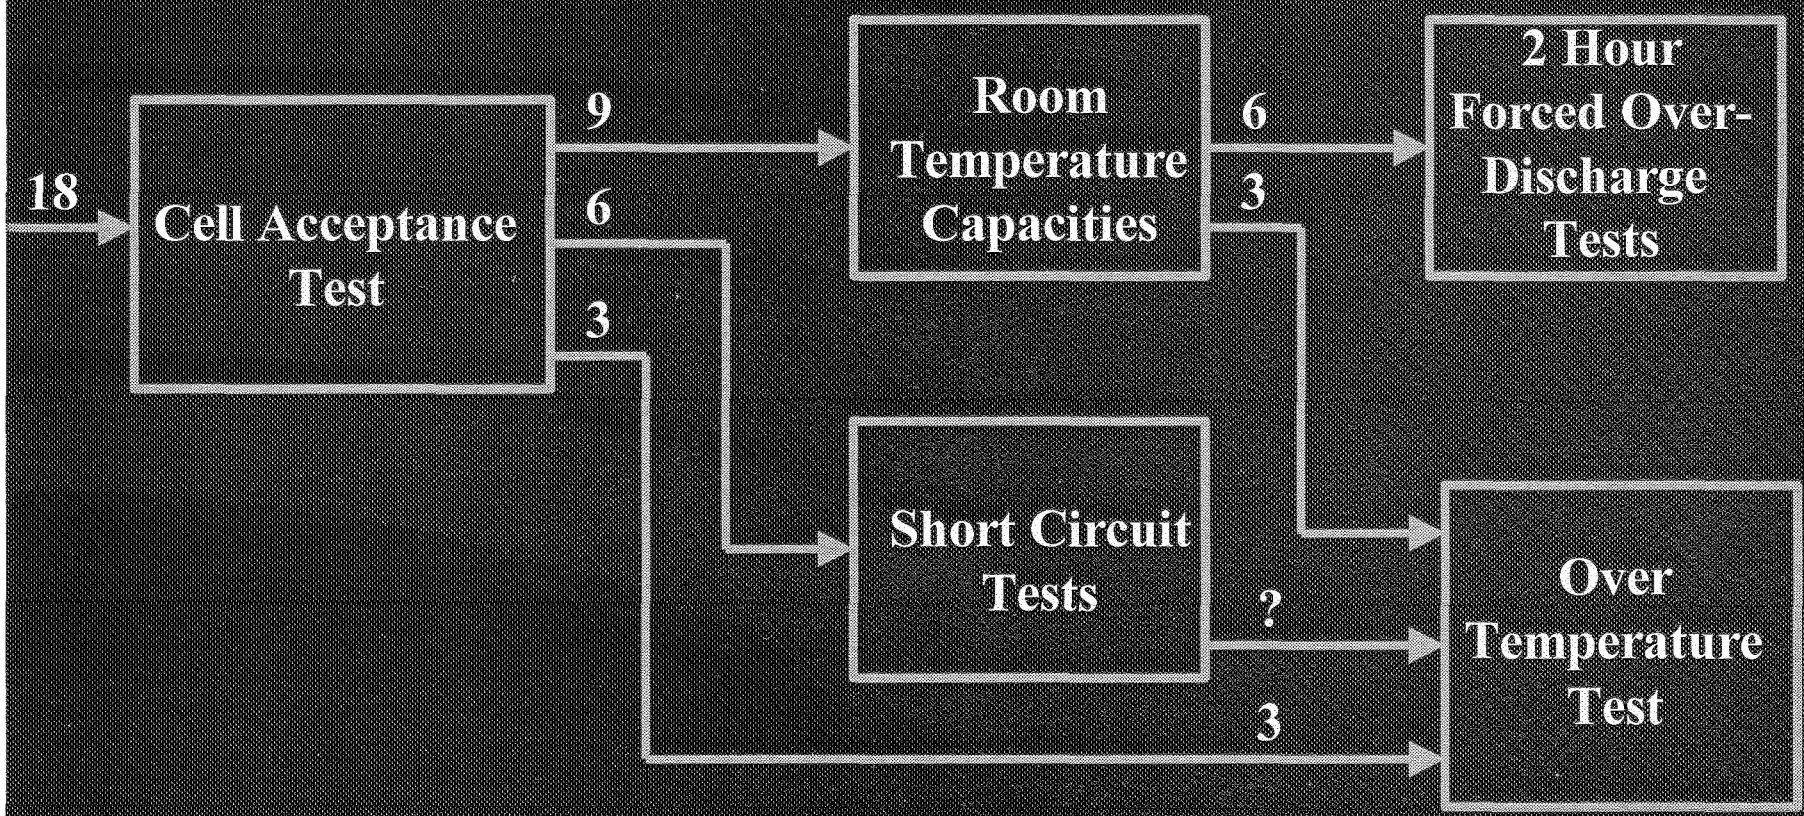

Schlumberger

Cell Acceptance Test

Measure OCV
Voc > 3.6 Volts

→

5 Ohm Load for 90 s
Vcc ≥ 3.5 Volts

→

160 °F - 2 hours
No Leaks

→

Cell Acceptance Test Results
All 54 Cells

Measure OCV
Voc > 3.6 Volts

→ **PASS**
3.65 V

→ **5 Ohm Load for 90 s**
Vcc ≥ 3.5 Volts

→ **160 °F - 2 hours**
No Leaks

→

Schlumberger

Cell Acceptance Test Results
All 54 Cells

Measure OCV
Voc > 3.6 Volts

→ **PASS**
3.65 V

→ **5 Ohm Load for 90 s**
Vcc ≥ 3.5 Volts

→ **160 °F - 2 hours**
No Leaks

↓

All Cells Failed

3.05V	3.00V	3.01V
LTC-114	LTC-111	LTC-115

Cell Acceptance Test (Revised)

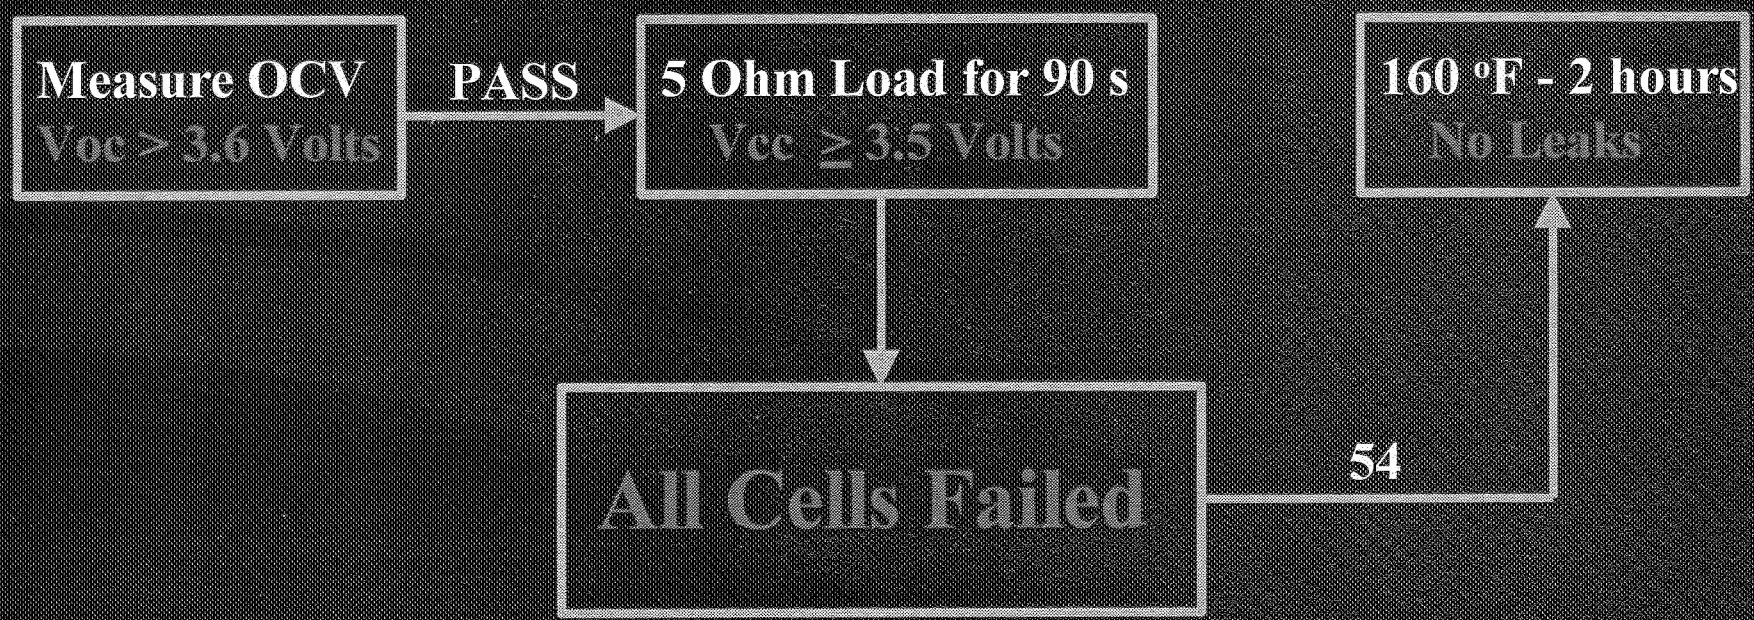

Schlumberger

Test Plan - Part 1
Cell Acceptance Test Results

160 °F - 2 hours
No Leaks

54 PASS

Test Plan (Overview)

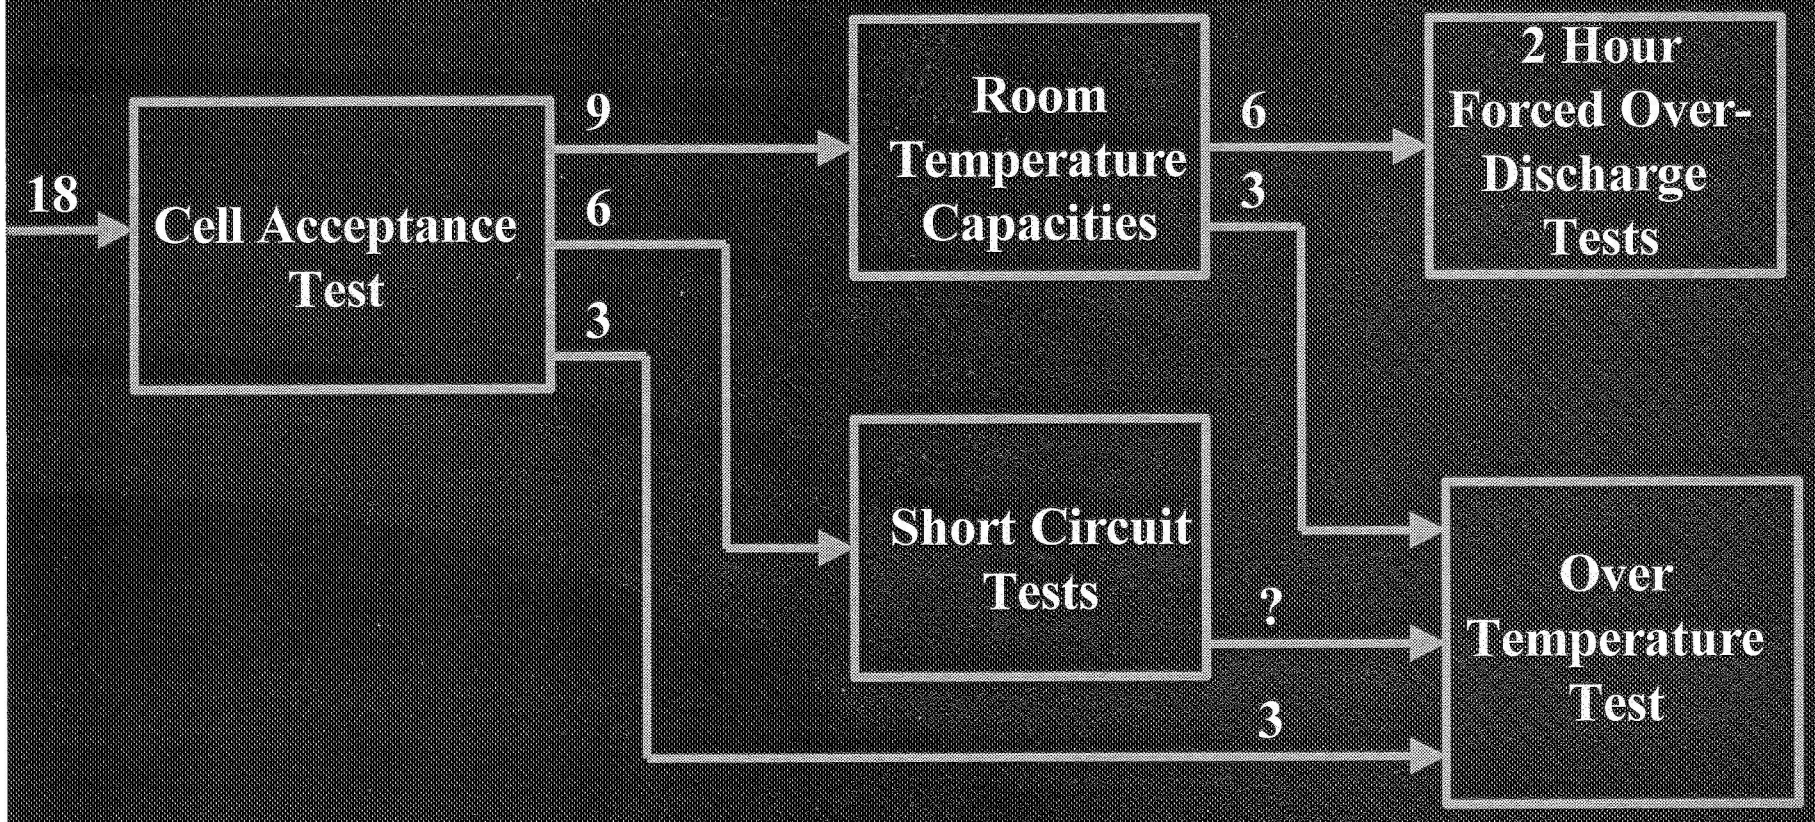

Test Plan (Overview)

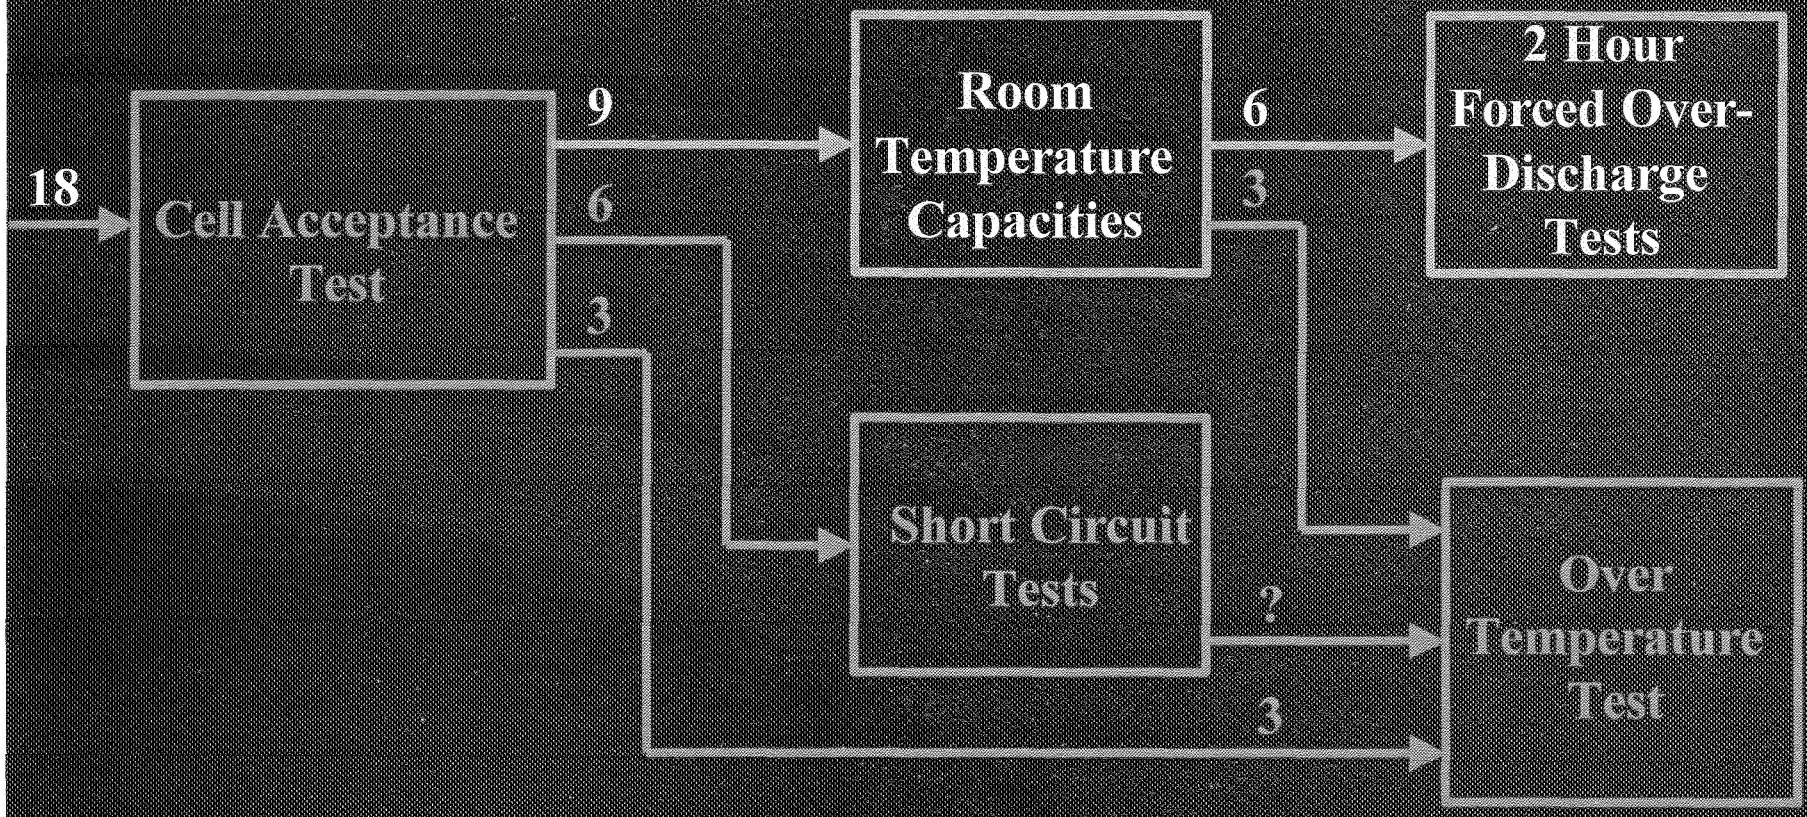

Room Temperature Capacity and Forced Overdischarge Test

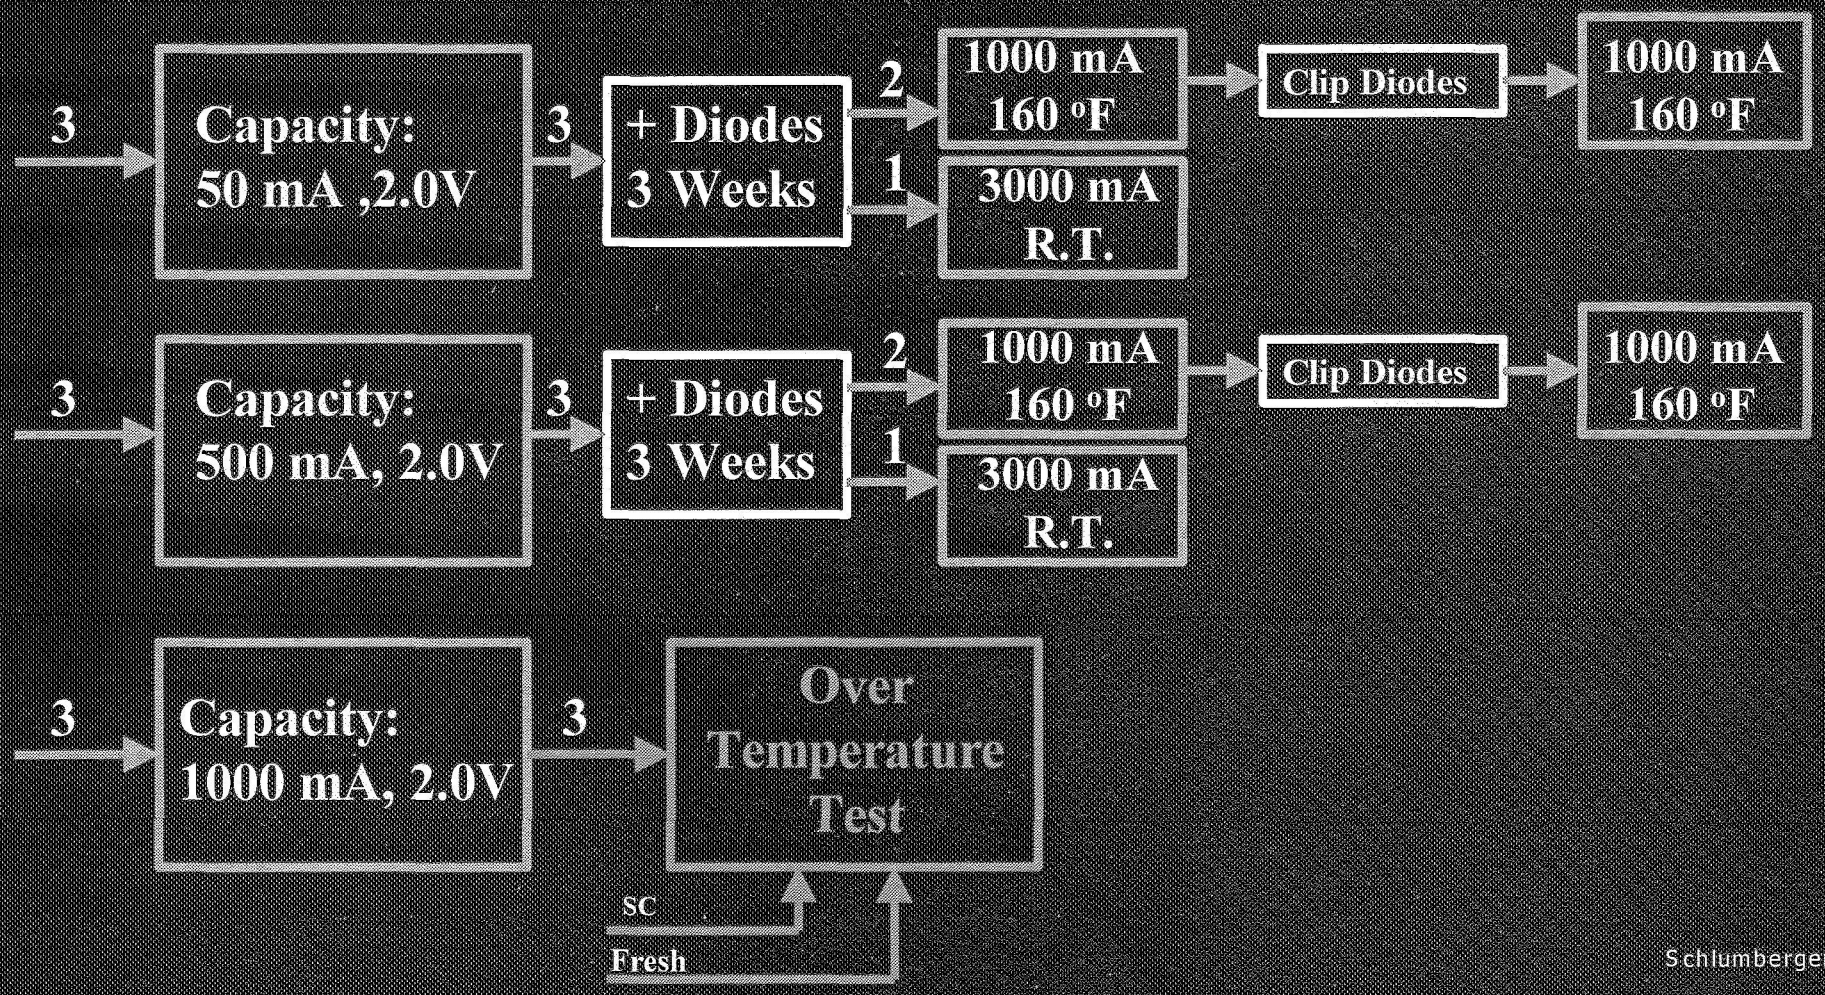

Schlumberger

Room Temperature Capacity and Forced Overdischarge Test

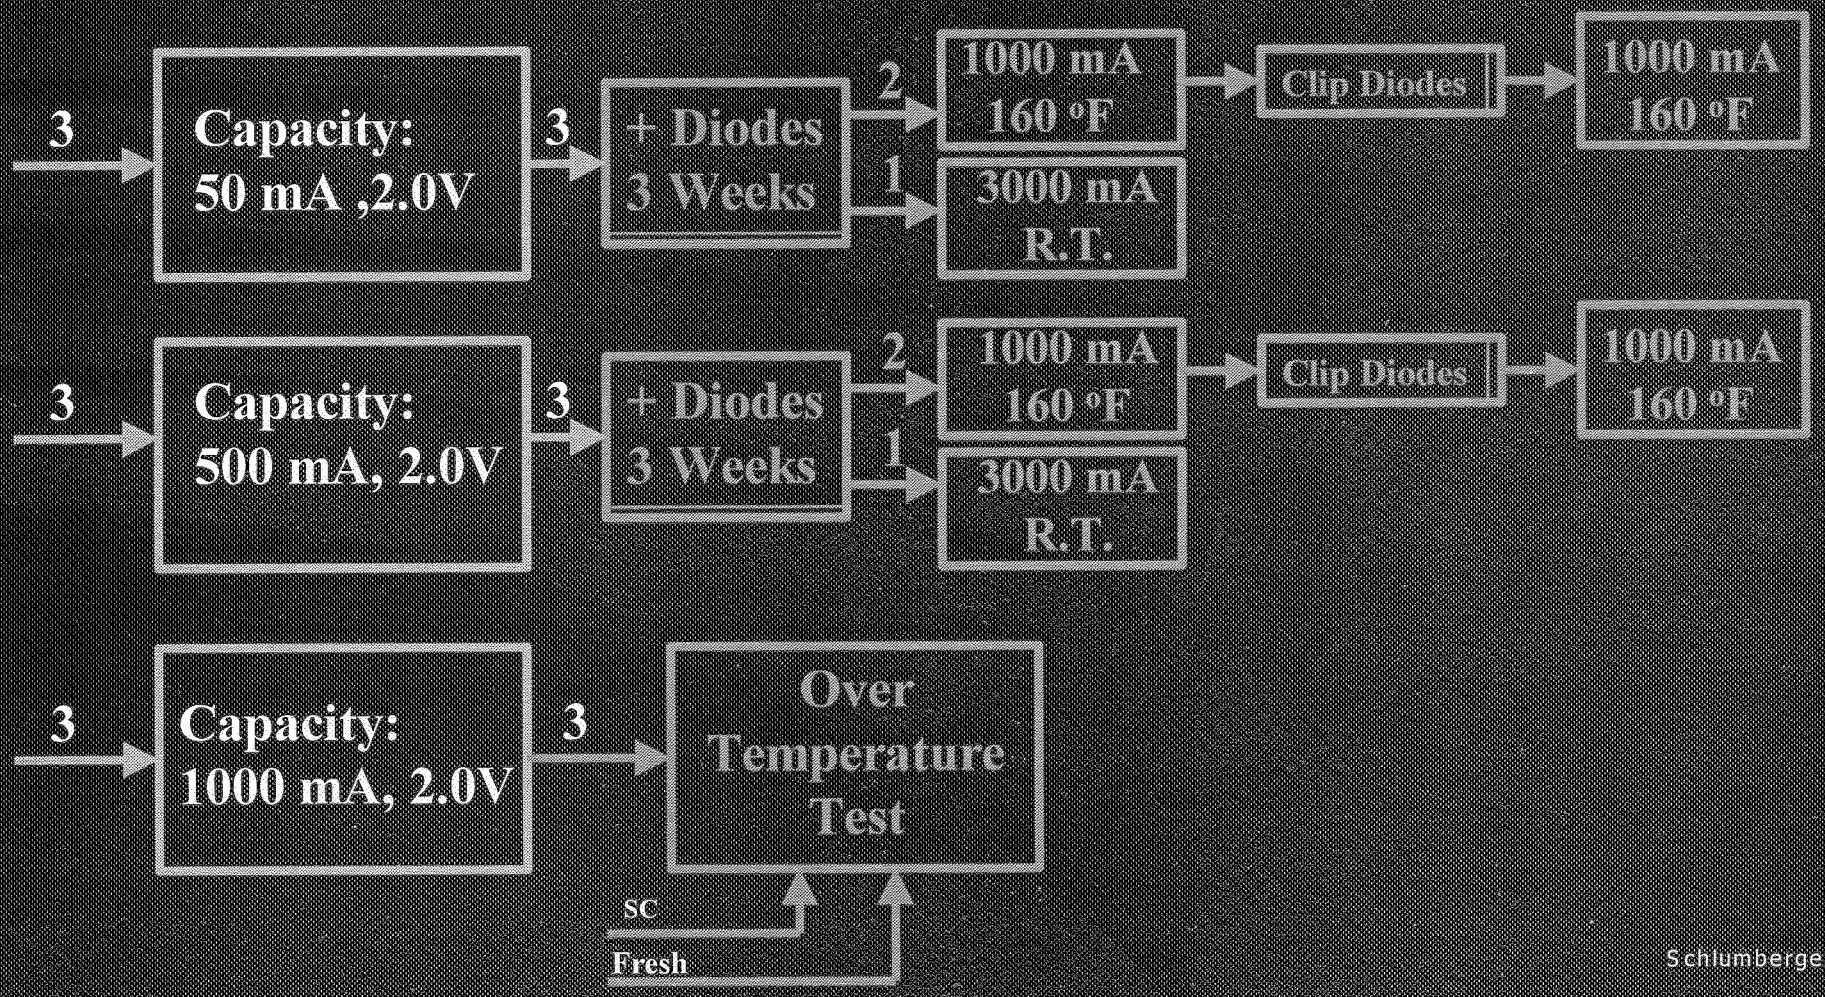

Schlumberger

Capacity Test Results

Capacity (Ah)								
50 mA			500 mA			1000 mA		
LTC-114	LTC-111	LTC-115	LTC-114	LTC-111	LTC-115	LTC-114	LTC-111	LTC-115
15.7	15.0	11.8	8.6	13.7	5.3	4.4	12.2	3.3
15.6	14.9	12.7	8.9	13.8	5.6	4.9	12.8	3.1
15.7	14.9	13.0	8.7	13.3	5.2	4.8	12.7	Note

	LTC-114	LTC- 111	LTC 115
Rated Capacities:	14 Ah	12 Ah	11 Ah

Note: One LTC-115 cell had tab break off and repair was not possible

Average Cell Capacity

	LTC-114	LTC- 111	LTC 115
Rated Capacity (Ah)	14	12	11
50 mA Capacity (Ah)	15.7	14.9	12.5
500 mA Capacity (Ah)	8.7	13.6	5.4
1000 mA Capacity (Ah)	4.7	12.6	3.2

	LTC-114	LTC- 111	LTC 115
Rated Capacities:	14 Ah	12 Ah	11 Ah

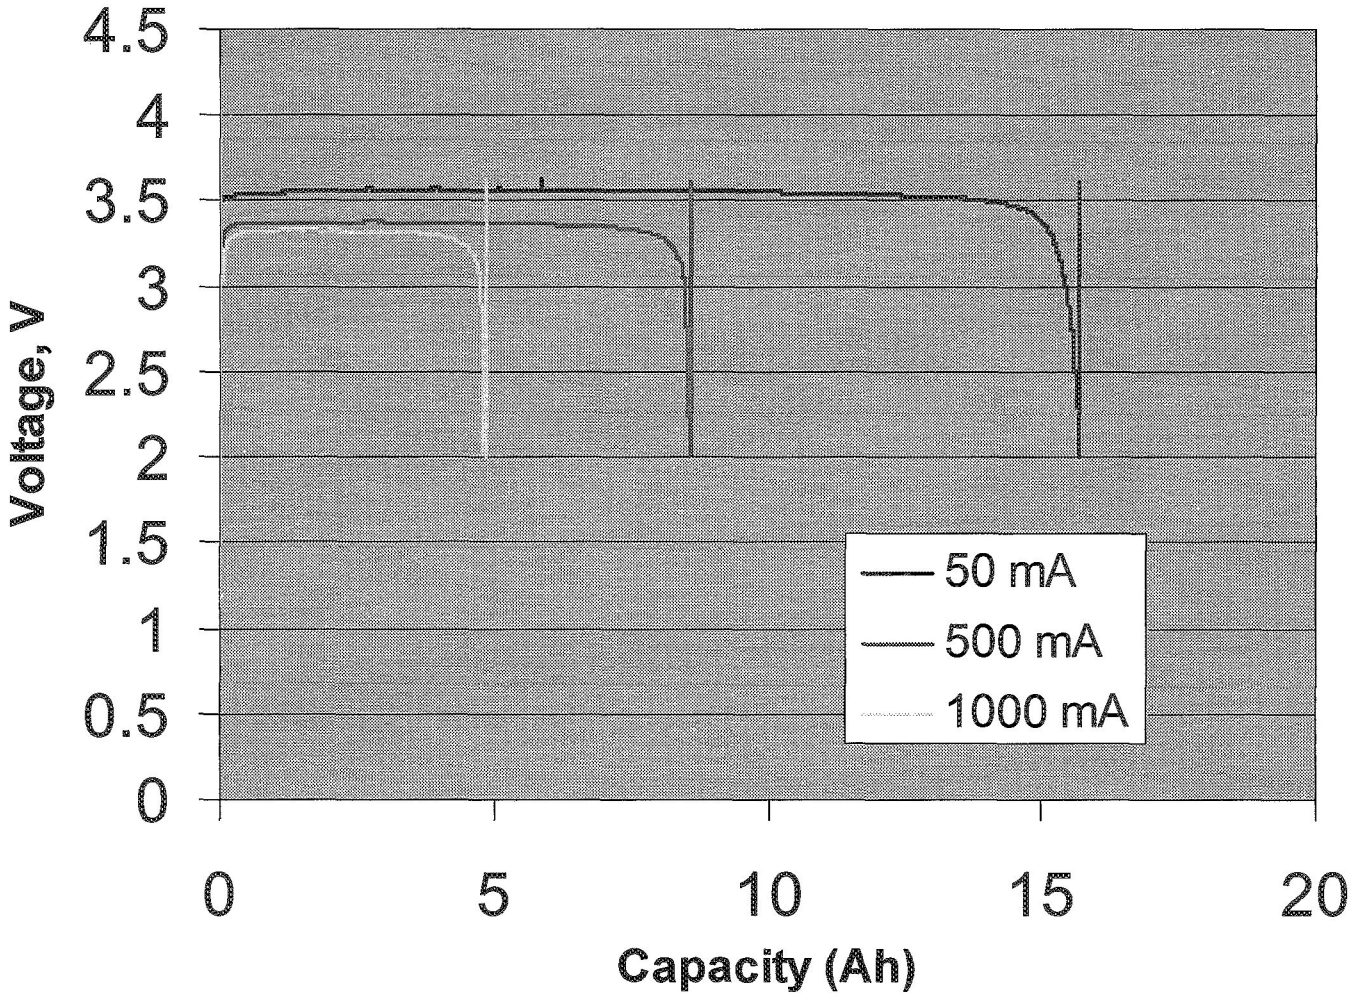

Typical Discharge Curves - LTC-114

Schlumberger

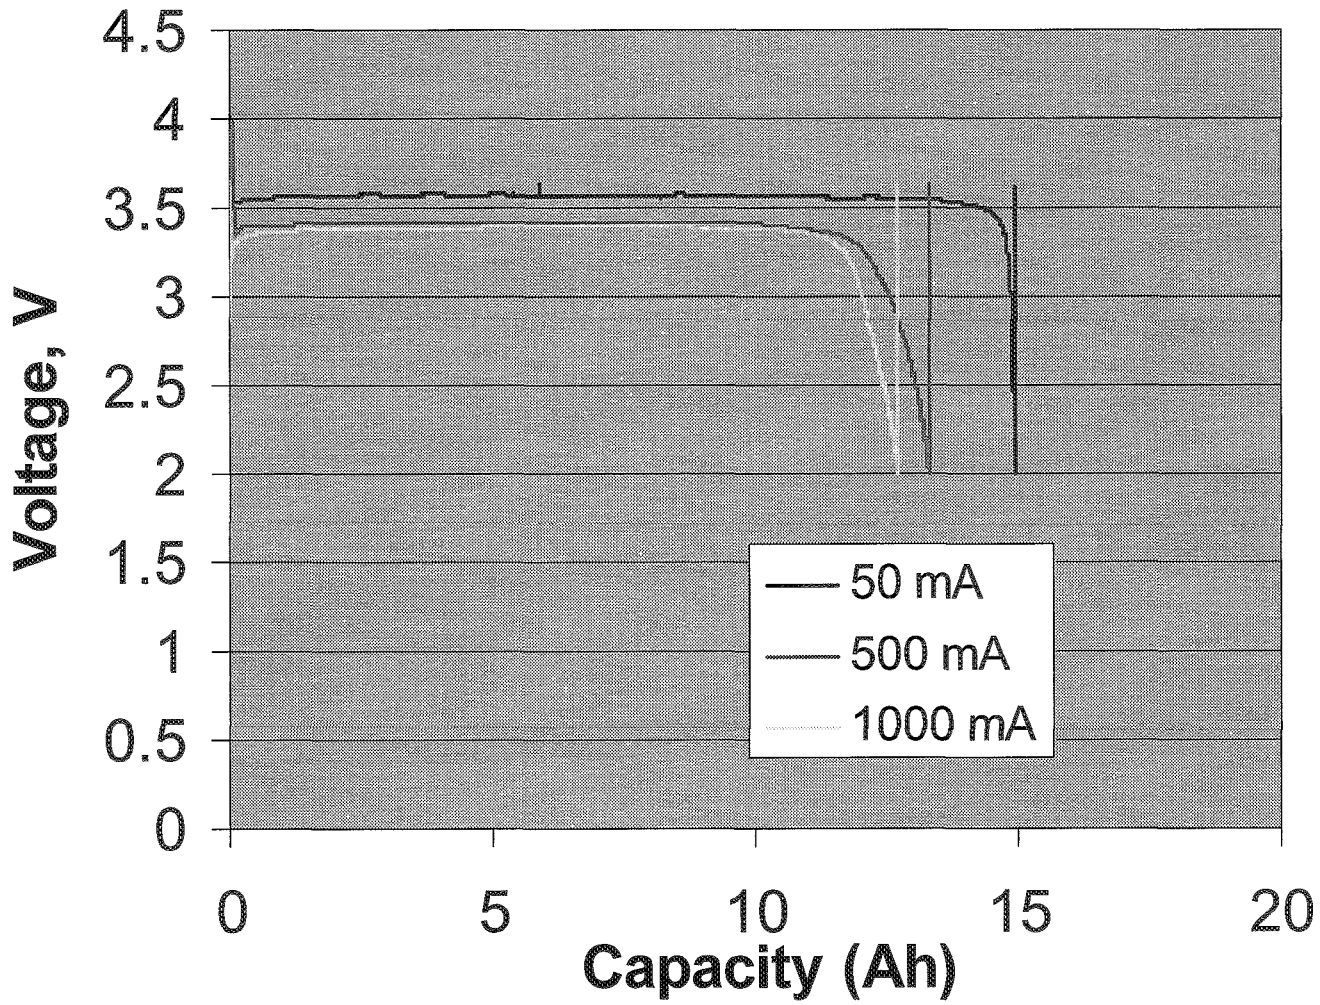

Typical Discharge Curves - LTC-111

Schlumberger

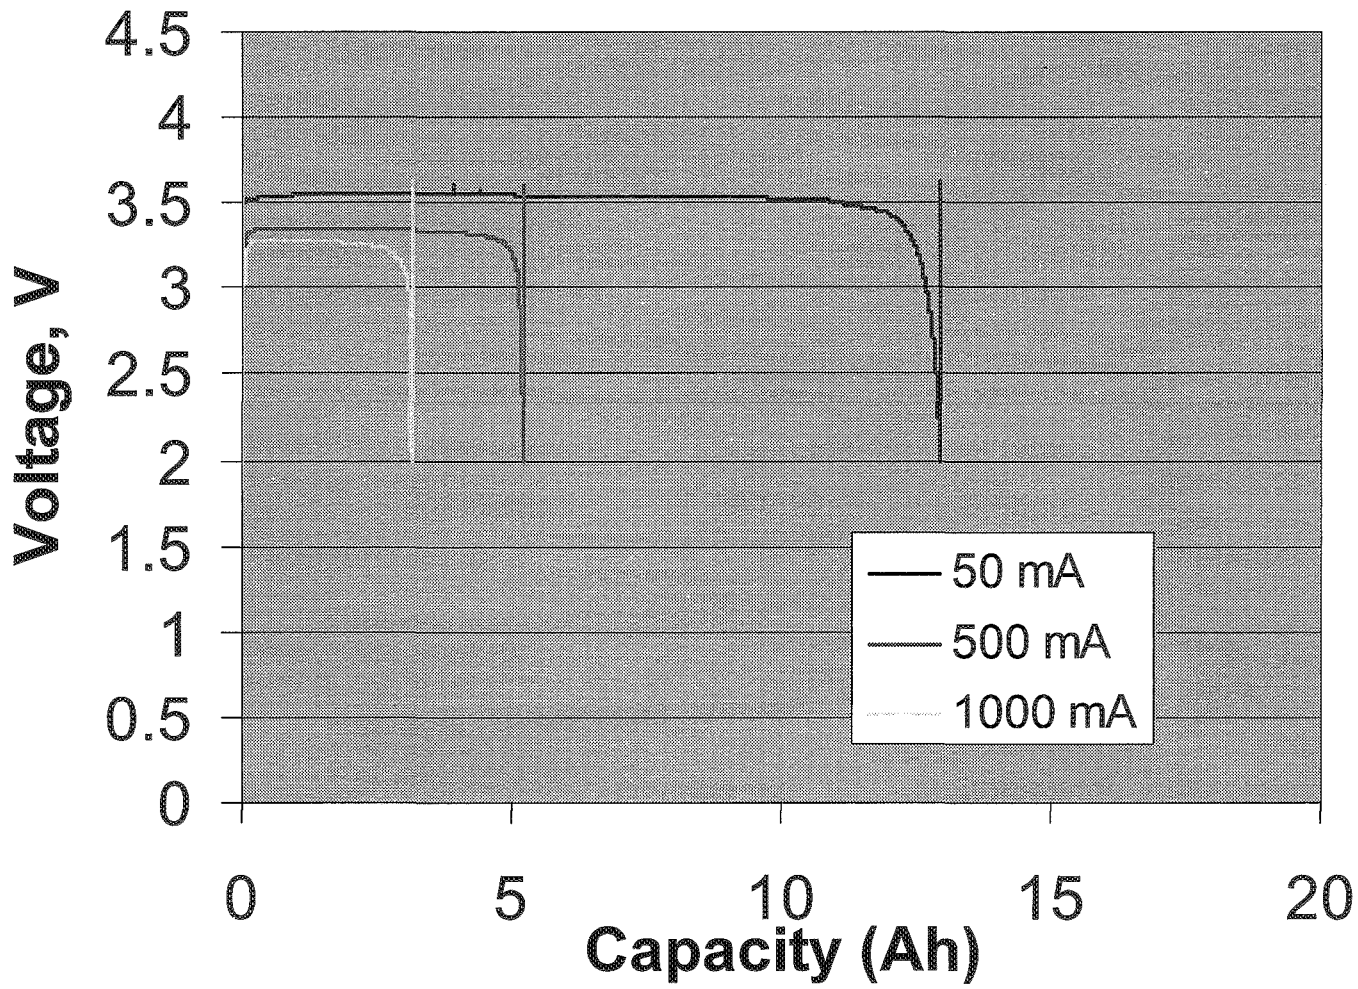

Typical Discharge Curves - LTC-115

Room Temperature Capacity and Forced Overdischarge Test

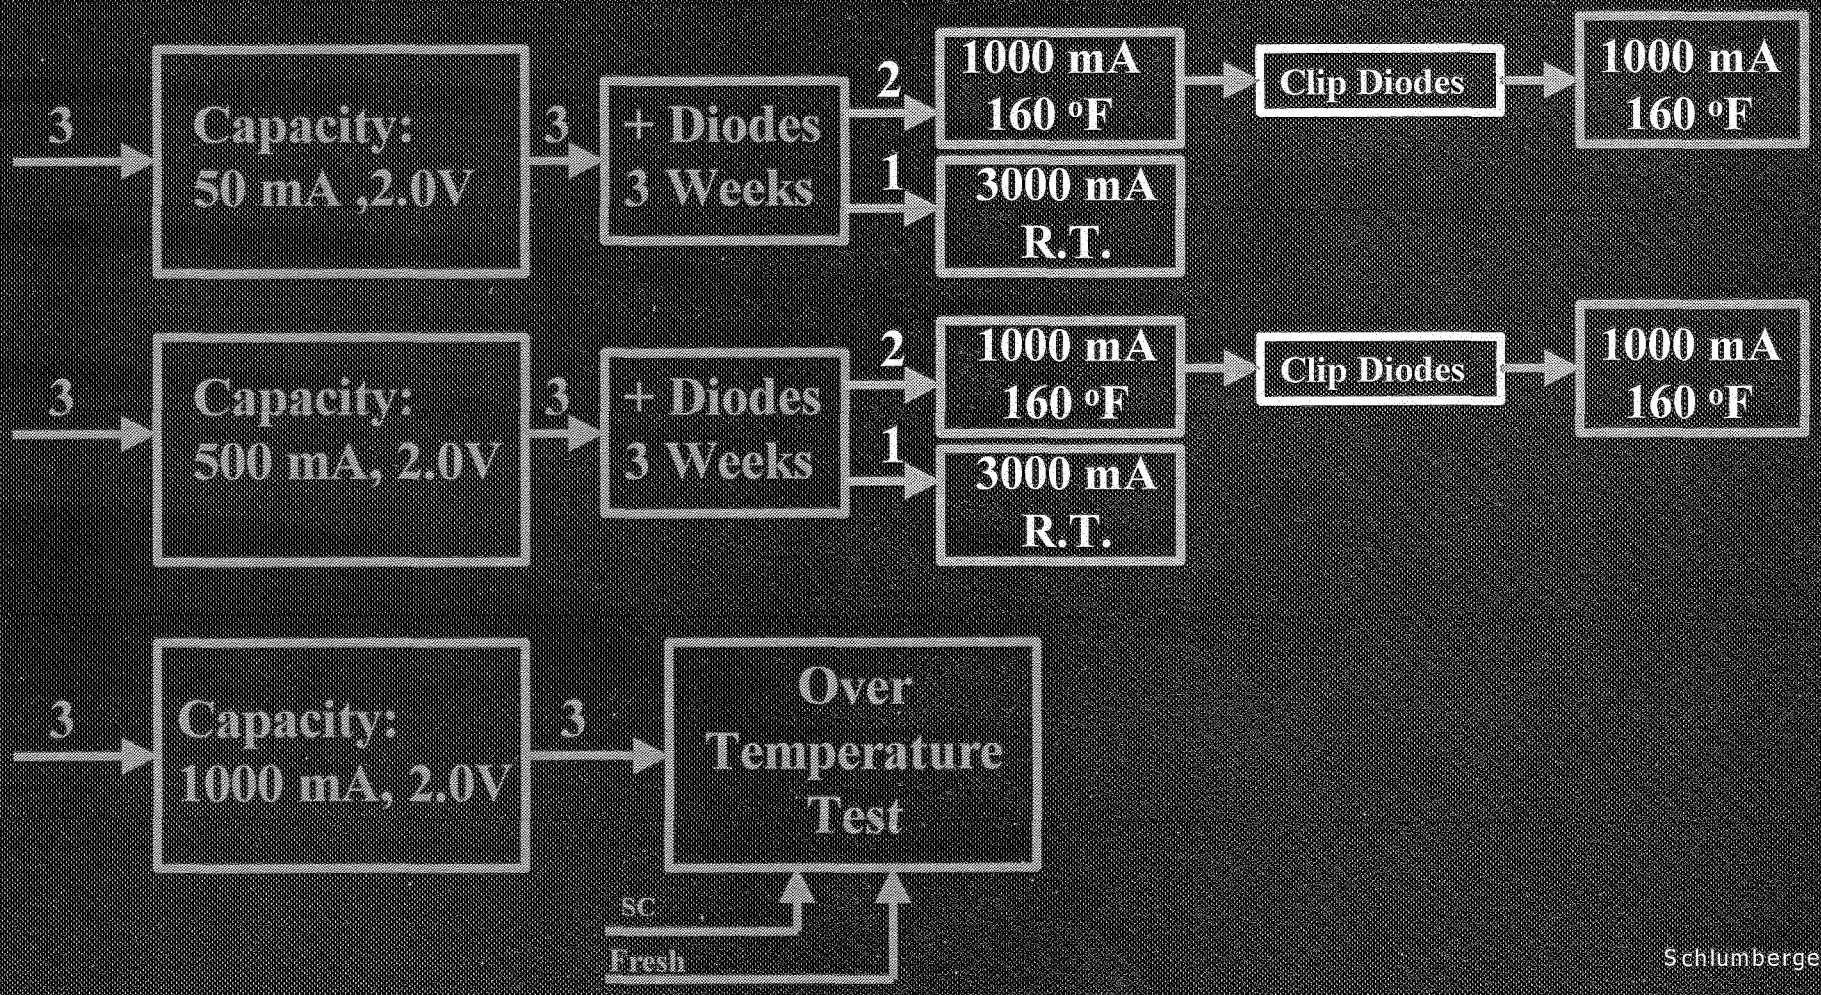

Schlumberger

1 Amp at 160F Over-Discharge Test Results

Cell Type	With Diodes	Without Diodes
After 50 mA discharge capacity test		
LTC-114	ok	ok
	ok	ok
LTC-111	ok	ok
	ok	ok
LTC-115	ok	ok
	ok	ok
After 500 mA discharge capacity test		
LTC-114	ok	ok
	ok	ok
LTC-111	vented	not available
	vented	not available
LTC-115	ok	ok
	ok	ok

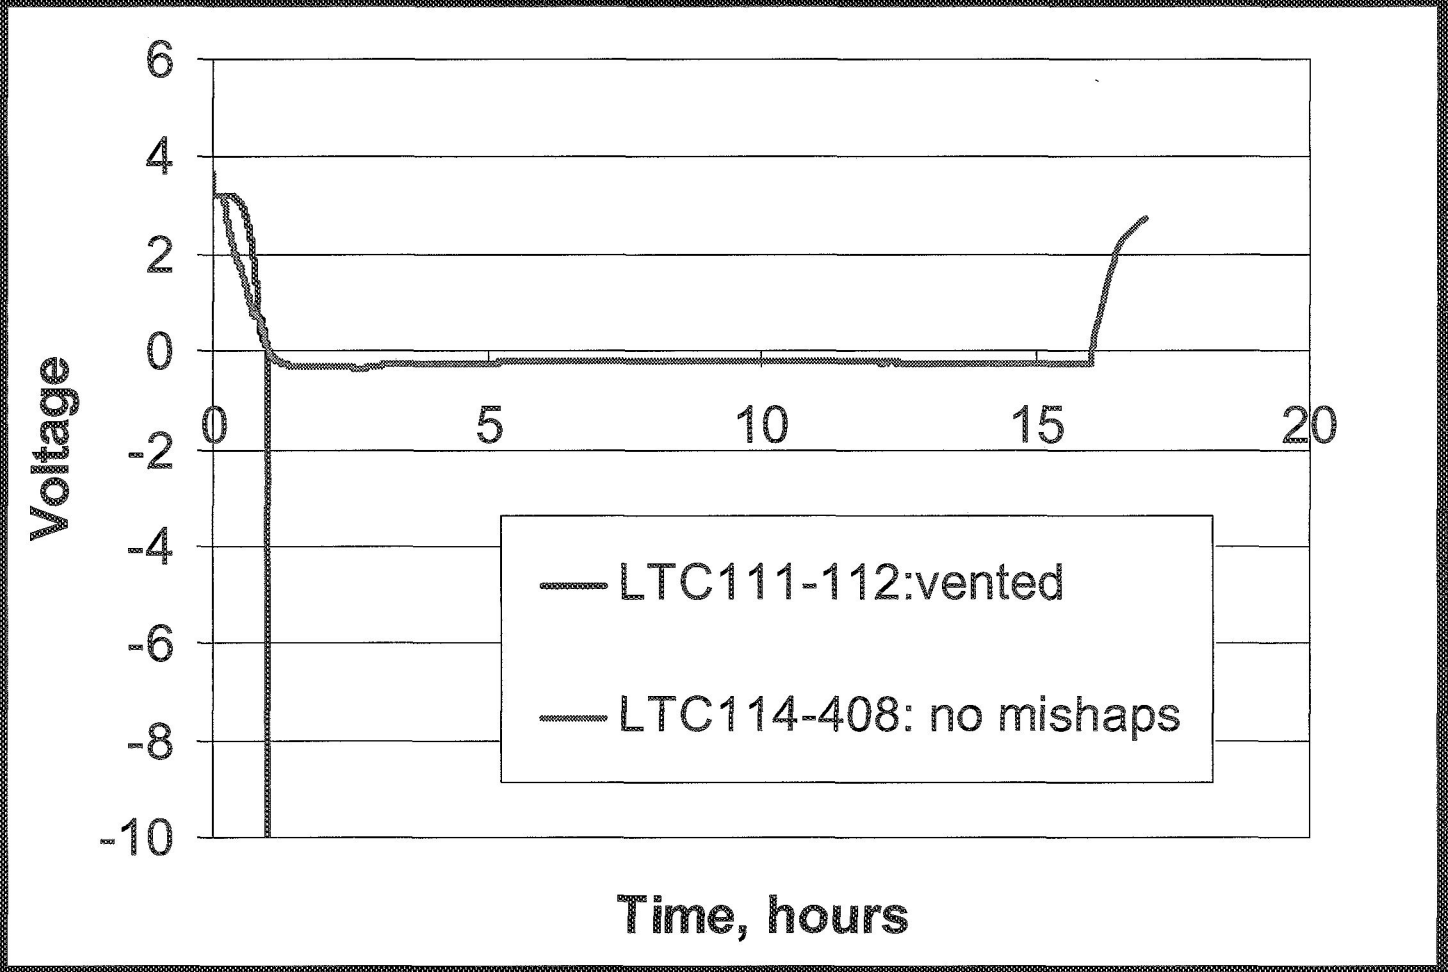

Voltage behavior during 1 A over-discharge with diode at 160°F - LTC-111 (vented) and LTC-114 (no mishaps)

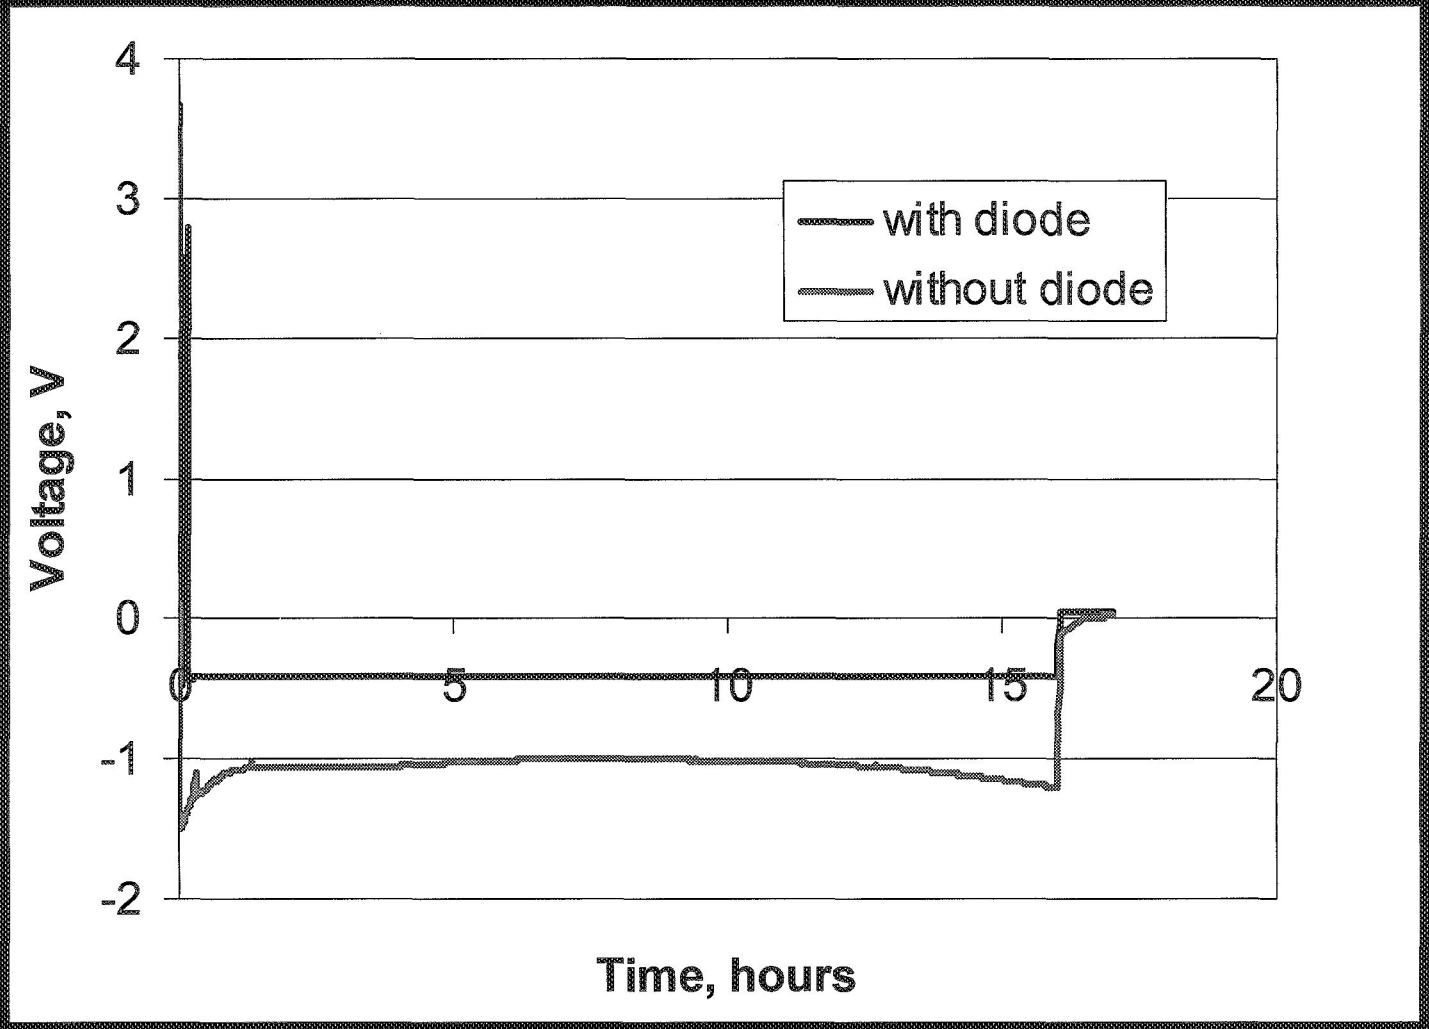

Voltage behavior during 1 A over-discharge with diode at 160 °F and afterwards without diode at 160 °F - LTC-111

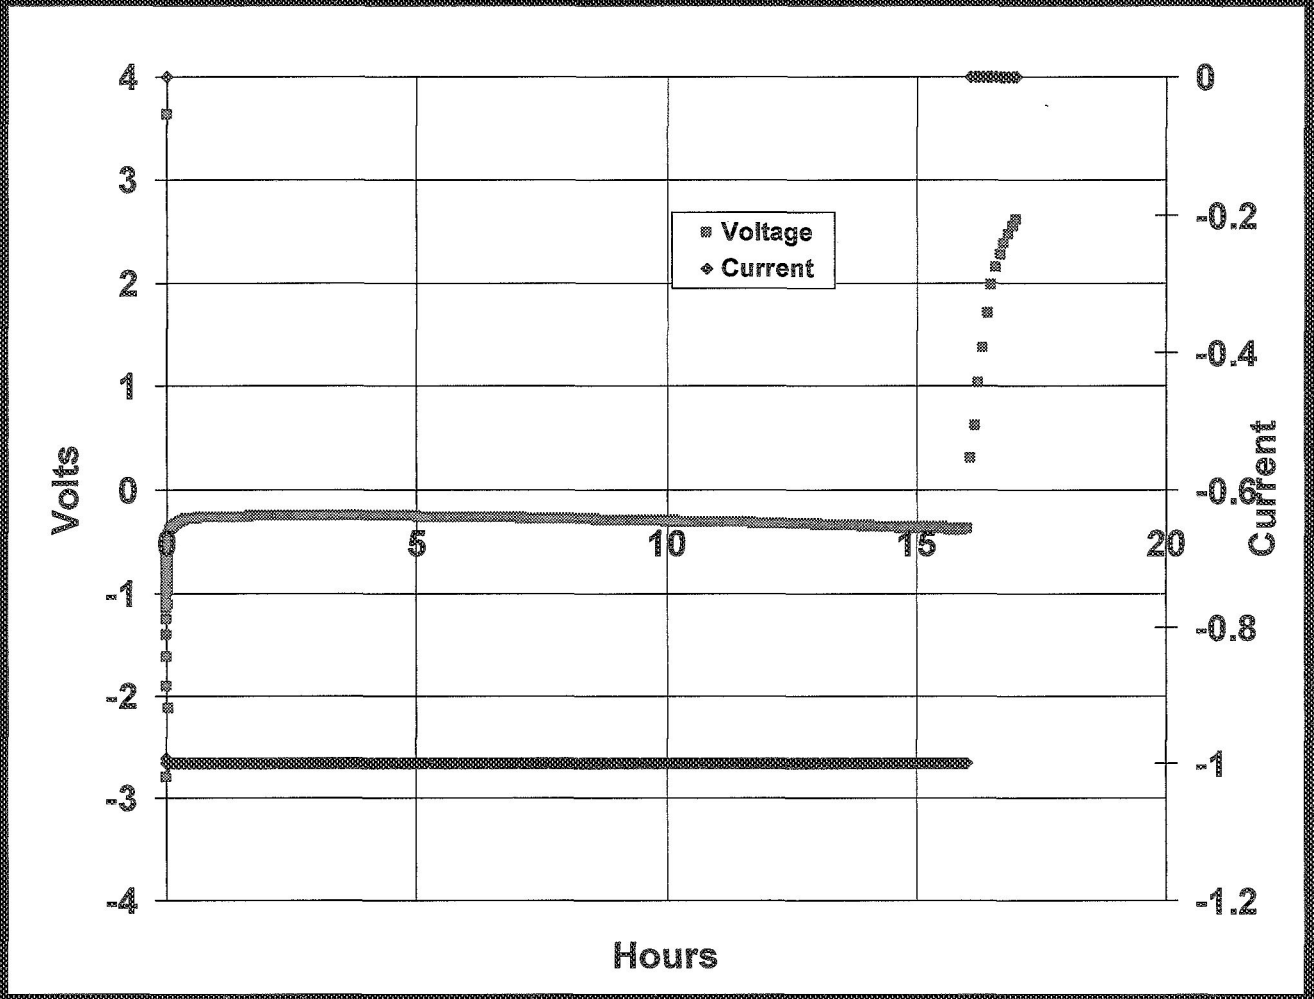

Voltage behavior during 1 A over-discharge without diode at 160 °F - LTC-114

3 Amps at R.T. Over-Discharge Test Results

Cell Type	With Diodes
After 50 mA discharge capacity test	
LTC-114	ok
	ok
LTC-111	ok
	ok
LTC-115	ok
	ok
After 500 mA discharge capacity test	
LTC-114	ok
	vented
LTC-111	ok
	ok
LTC-115	ok
	ok

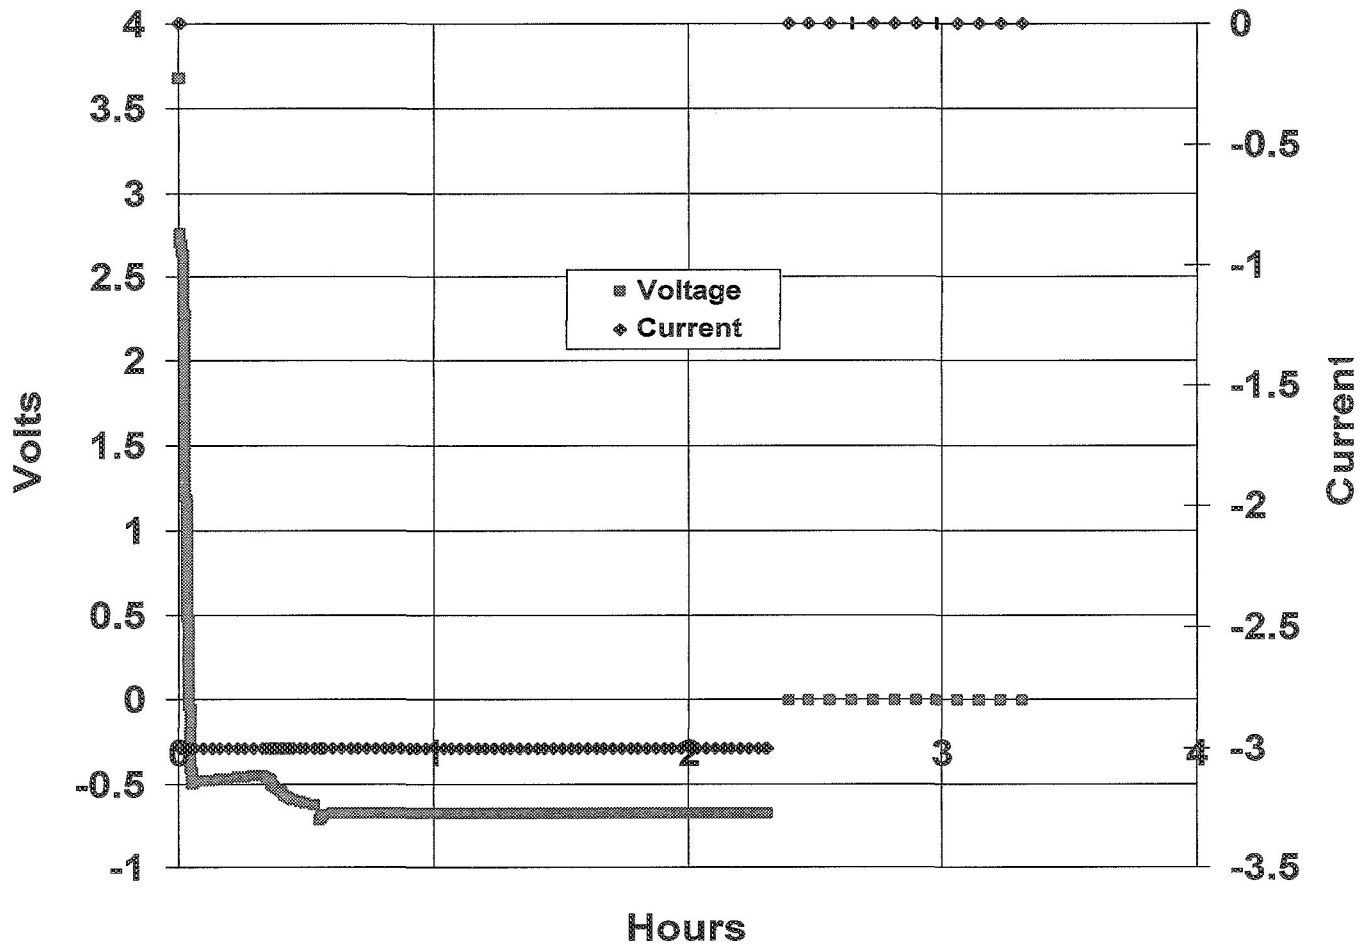

3 Amp Over Discharge Curve (Vented) - LTC-114

Schlumberger

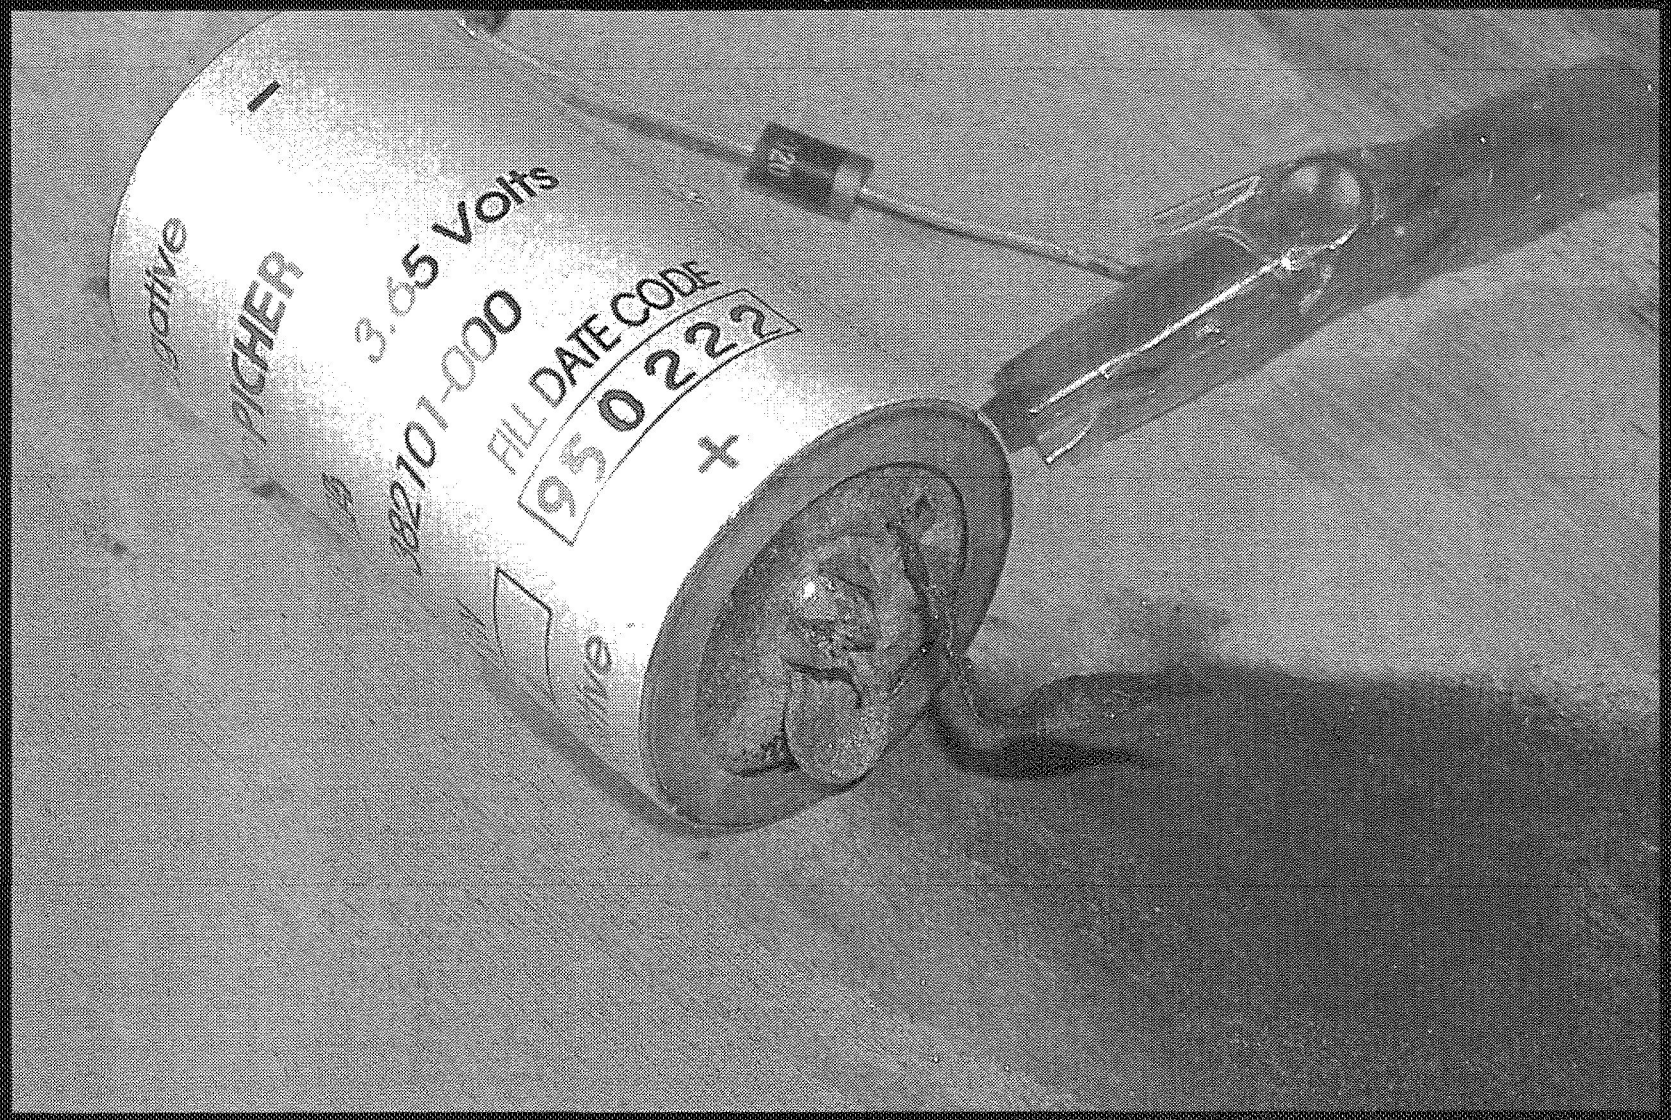

LTC-114 Cell Vented during 3A Over-Discharge

Test Plan (Overview)

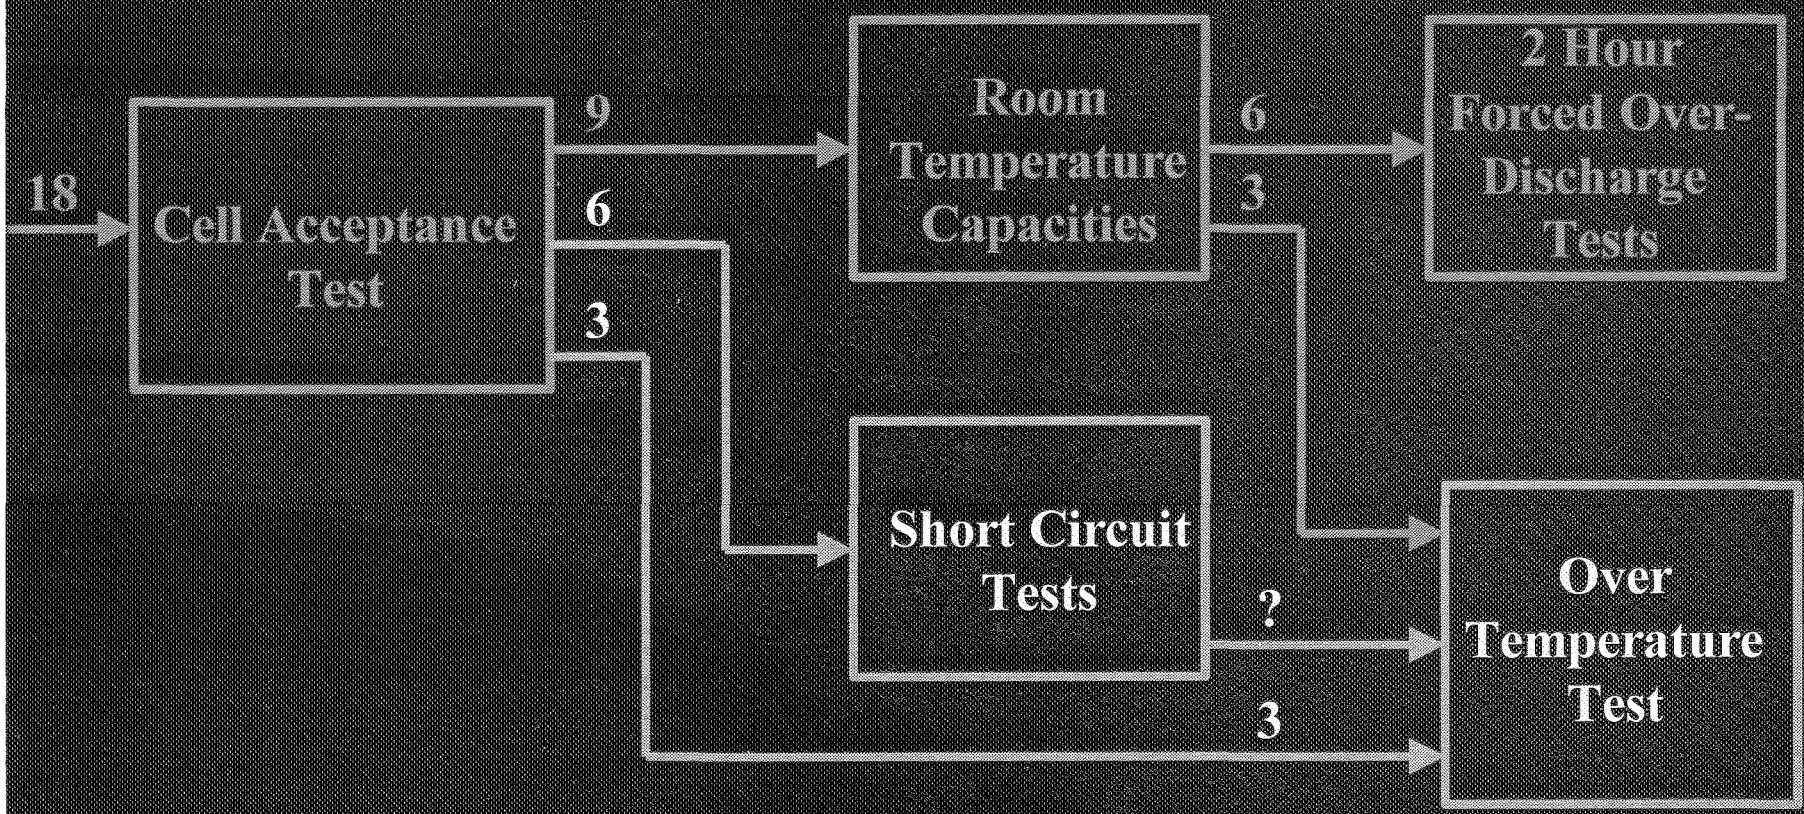

Room Temperature Short Circuit Test Results

Cell Type	0.050 Ohm short	1 Ohm short
LTC-114	Ok - Cell open in 20 min.	Cell open in 1 hour
	Ok - Cell open in 15 min.	Cell open in 1 hour
	Ok - Cell open in 20 min.	Cell open in 1 hour
LTC-111	Exploded	Ok - No Mishaps
	Leaked	Ok - No Mishaps
	Exploded	Ok - No Mishaps
LTC-115	Cell open immediately	Cell open in 1 hour
	Cell open immediately	Cell open in 1 hour
	Cell open immediately	Cell open in 1 hour

Note: Cells with 'Ok' went on to the Over Temperature Test

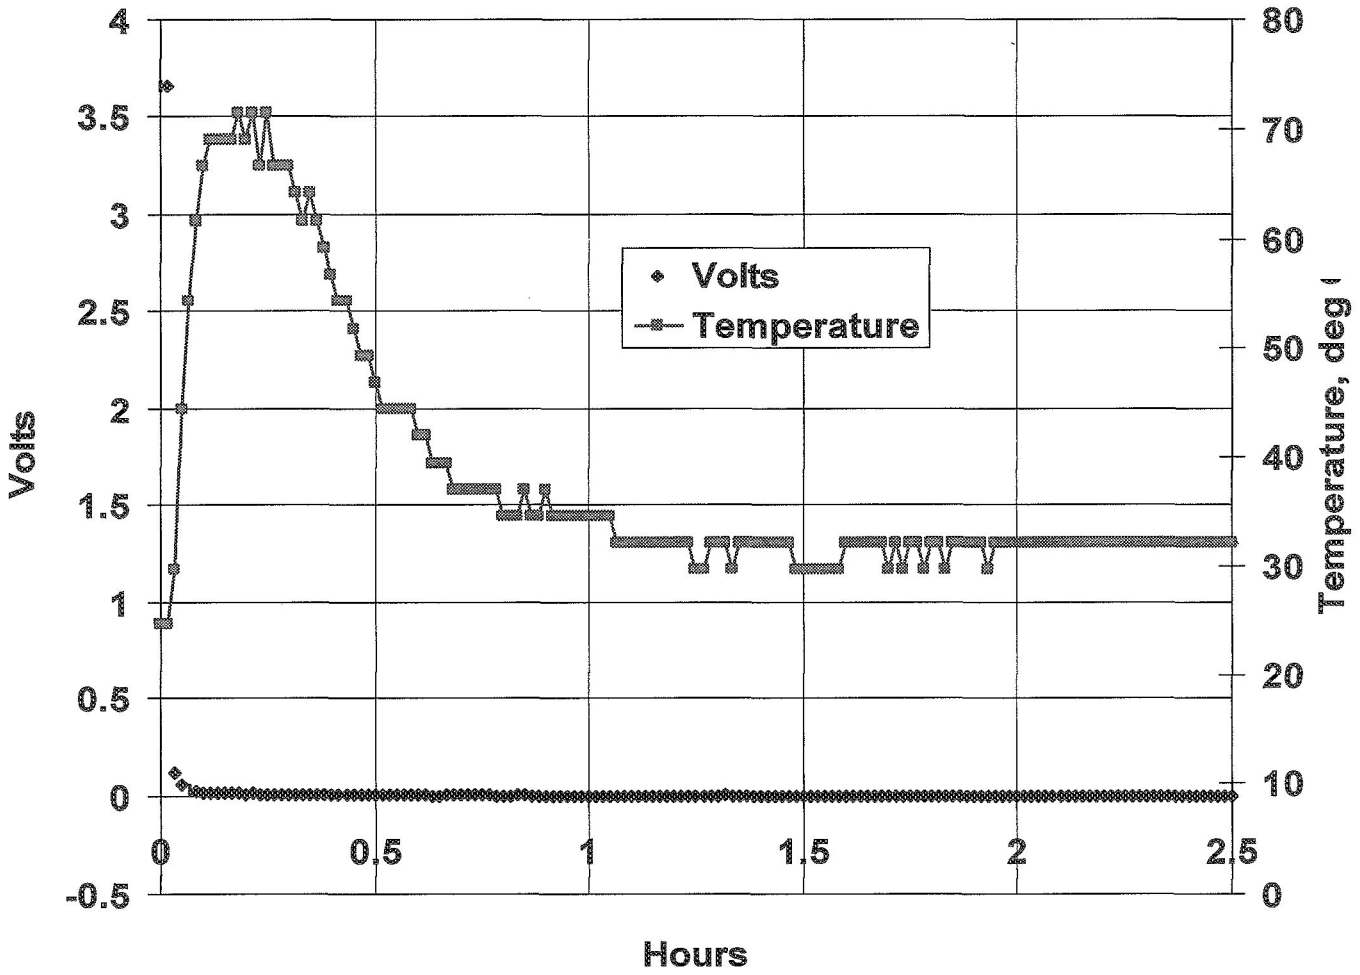

Typical Short Circuit (50 mΩ) Curve - LTC-114

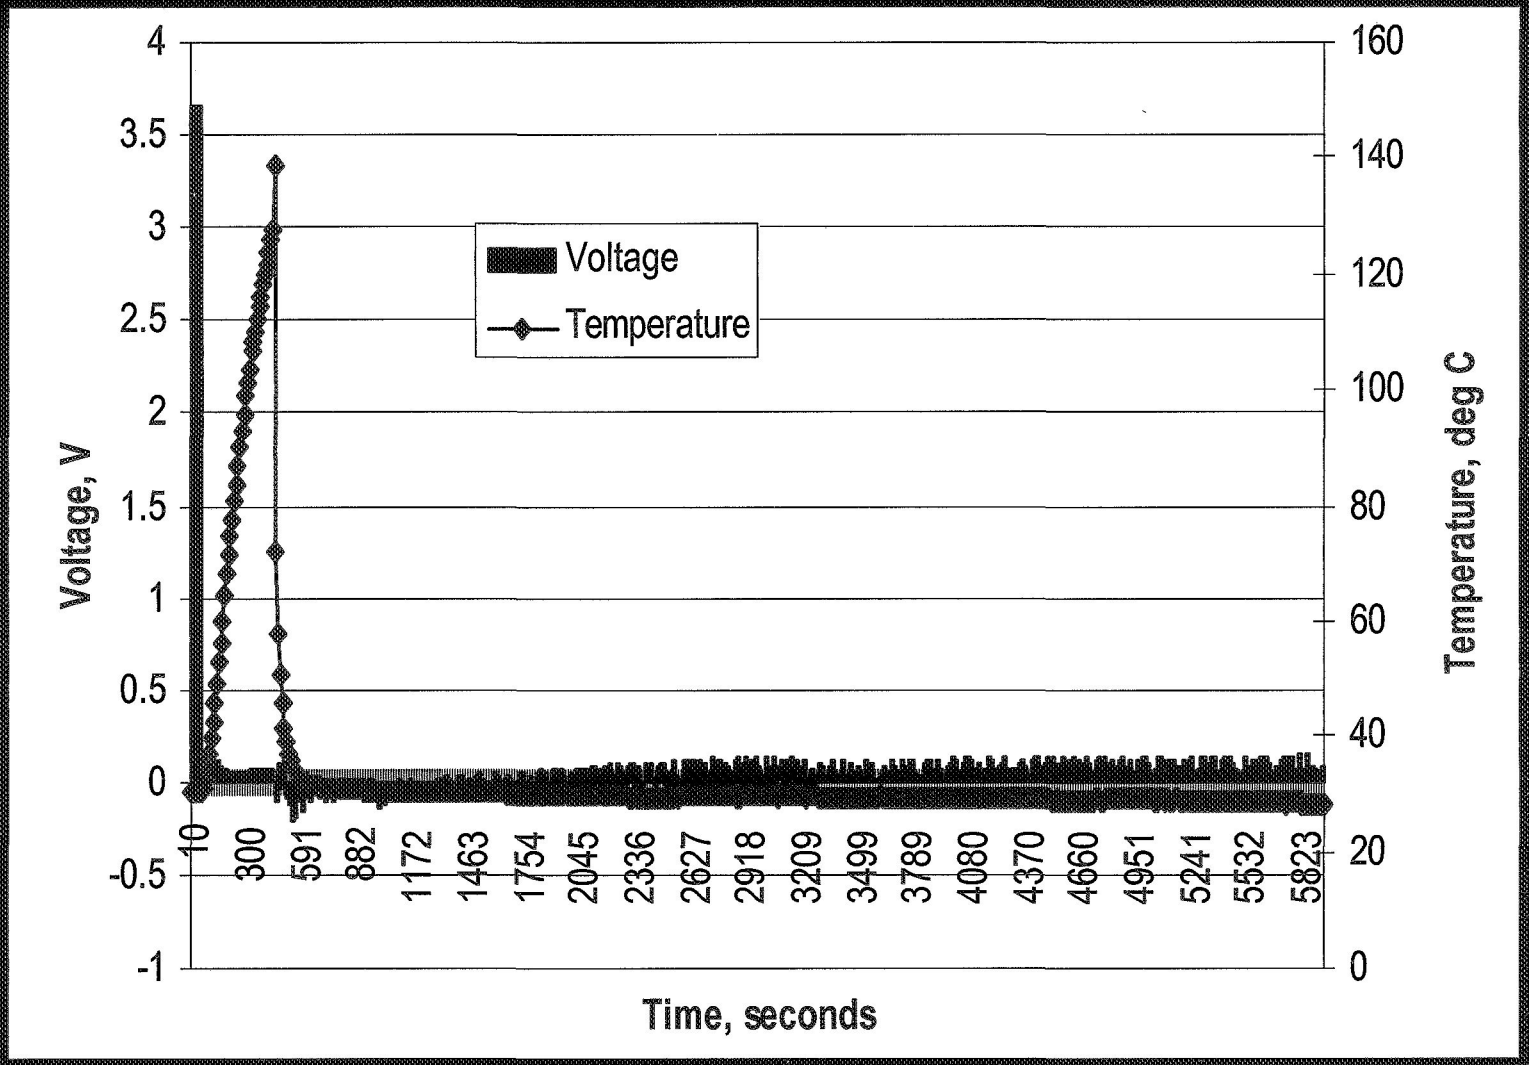

Typical Short Circuit (50 mΩ) Curve - LTC-111

Over Temperature Test Results

Condition	Samples	Status
After 1 A Discharge Capacity Test	LTC-114	Ok up to 120 ºC
		Ok up to 120 ºC
		Ok up to 120 ºC
	LTC-111	Vented at ~115 ºC
		Vented at ~116 ºC
		Vented at ~120 ºC
	LTC-115	Ok up to 120 ºC
		Ok up to 120 ºC
Short Circuit Test Survivors	LTC-114	Ok up to 120 ºC
		Ok up to 120 ºC
		Ok up to 120 ºC
	LTC-111	Vented at ~100 ºC
		Vented at ~100 ºC
		Vented at ~100 ºC
	LTC-115	Not tested - All Cells Open Circuit
Fresh Cells	LTC-114	Vented at ~170 ºC
		Vented at ~170 ºC
	LTC-111	Ok up to 170 ºC
		Ok up to 170 ºC
		Ok up to 170 ºC
	LTC-115	Vented at ~120 ºC

Conclusions

- Cells passed most of the acceptance test including consistent Voc of 3.65V and no mishaps during 2 hour 160 °F thermal exposure. However, all cells failed minimum loaded voltage under the 5 Ohm load test probably due to their 5 year storage conditions.
- The medium rate LTC-111 demonstrated very good discharge rate capability. The low rate LTC114 ' D' and the medium rate LTC-115 ' sub D' both showed significant capacity loss at high discharge rates of 500 mA and greater.
- The medium rate LTC-115 ' sub D' had 5% capacity dispersion at 50 mA discharge, while the LTC-111 had 0.2% and the LTC-114 had 0.4% capacity dispersion.
- The medium rate LTC-111 tend to explode or leak when force over-discharged at 160 °F following high rate discharge of 500 mA. The LTC-114 and LTC115 both survived 1 Amp over-discharge with and without diodes for 16 hours.

Conclusions

- Most cells survived the 3 A over-discharge at room temperature for 2 hours. The cell that failed was the LTC-114 after high rate discharge of 500 mA similar to the results of the 1 A over-discharge test.
- Most cells opened during 0.05 Ohm short circuit test without incident but three LTC-111cells exploded apparently due to a lack of a thermal cutoff switch. The LTC-114 cells exposed to a hard short of 0.05 Ohms recovered but the LTC-114 cells exposed to a soft short of 1 Ohm did not. This is probably due to the activation of a resetable fuse during a hard short.
- Fresh cells tend to survive exposure to higher temperatures than cells previously discharged at high rate (1 Amp). LTC-111 cells tend to vent at lower temperatures than the all LTC-114 cells and the LTC-115 cells that were previously discharged at rates exceeding 1 Amp.

Acknowledgements

NASA Johnson Space Center - Funding for this investigation under Program NASA/T-4551 W

Lithium-Ion Satellite Batteries Using Small Cells

By

David Lizius & Phil Cowles, COM DEV

Rob Spurrett & Carl Thwaite, AEA Technology

NASA Aerospace Battery Workshop, Huntsville

November 2000

S2/CP/M/44

20011183S3

22 gs

538119

STRV 1d: Launched 16 November 2000

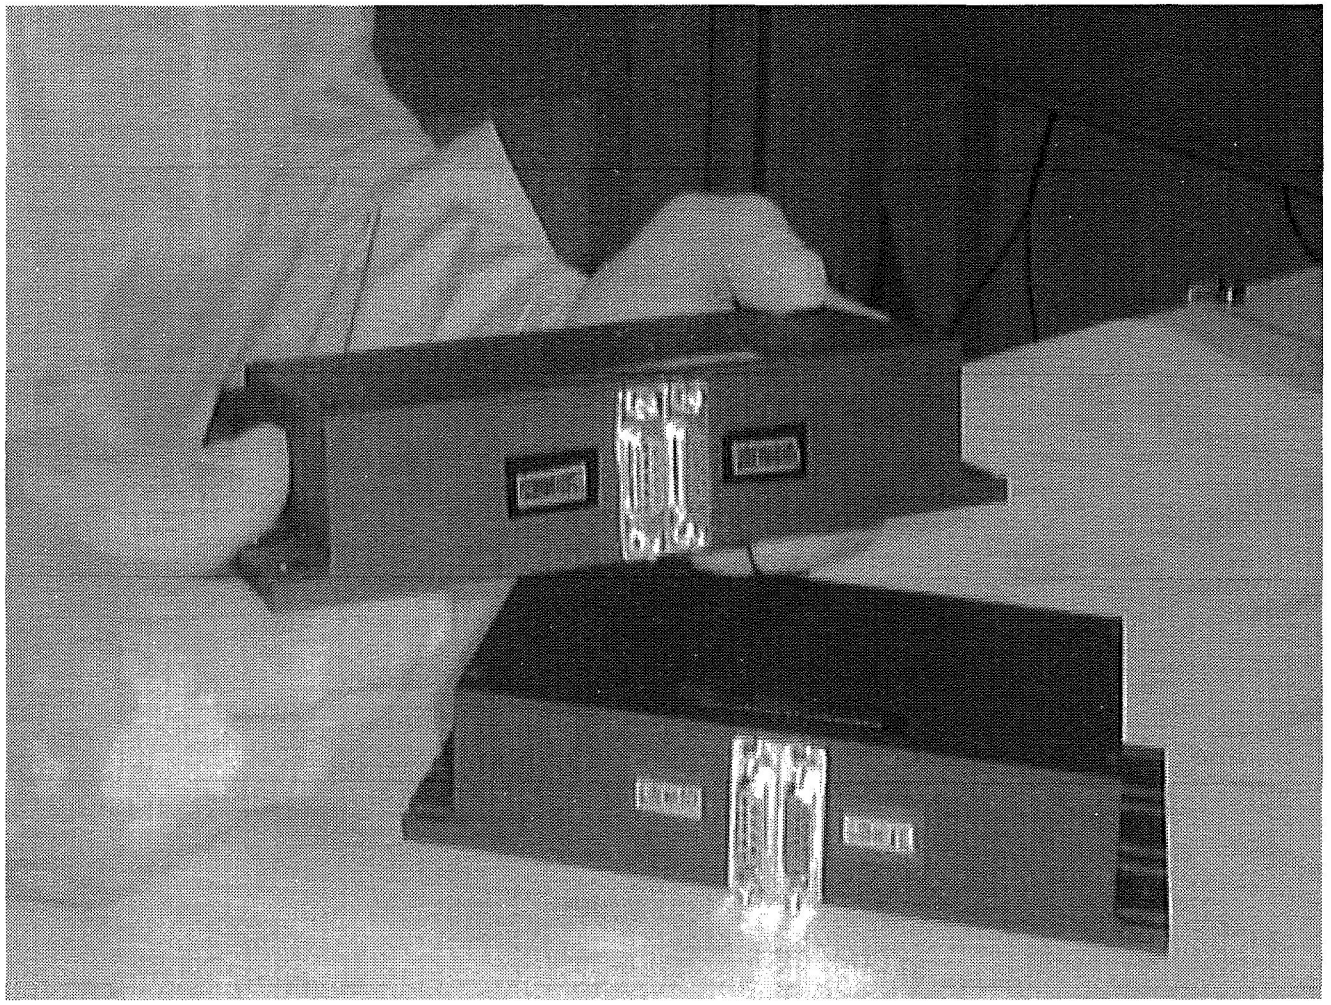

Contents

- Why small cells ?
- Using Sony cells in flight applications
- Battery Design
- Life Tests

Small Lithium-Ion Cells

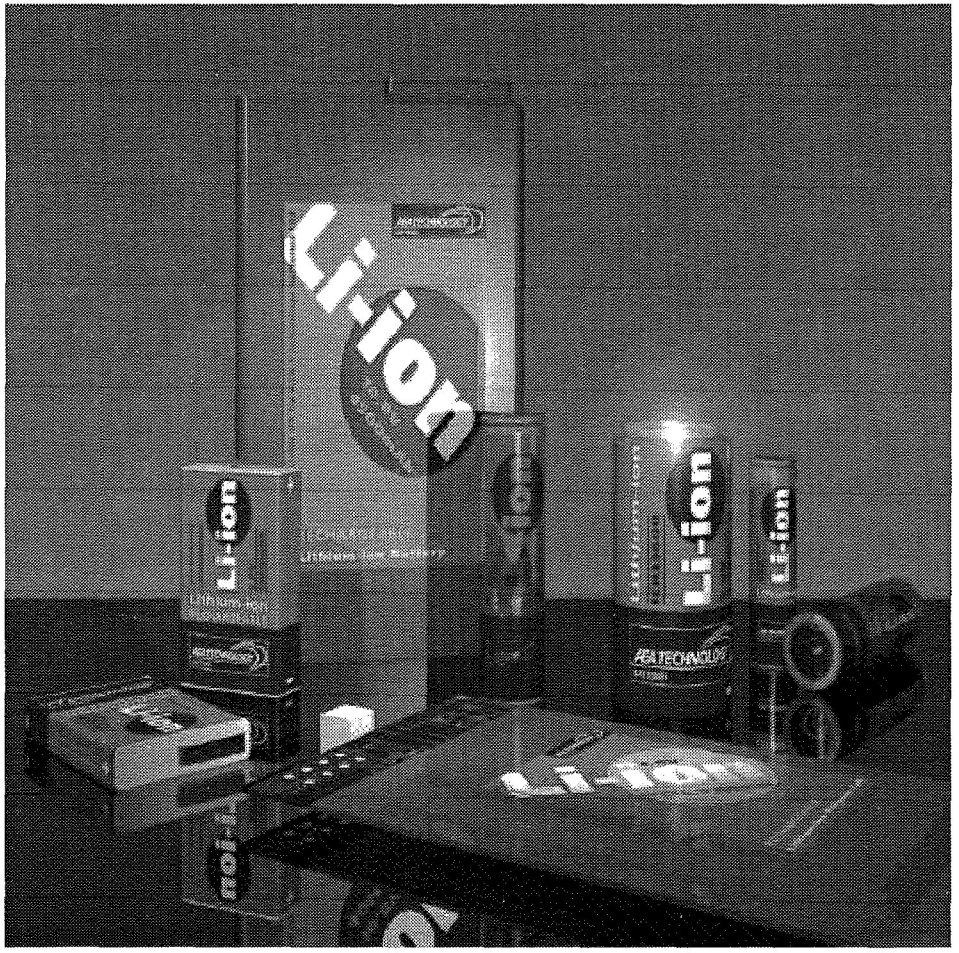

Small Beginnings

- Early Lithium-ion cells were generally small cells
  - Small means <5Ah
  - Sony 18650 gained early commercial success
- Tests on small cells showed potential benefits for space
  - Weight, volume, thermal advantages widely recognized
- The space industry requires many sizes of battery
  - Voltages from ~8V to ~125V
  - Capacity from 3Ah to several 100Ah
- Different paths to adopting Lithium-ion technology for space
  - 'Large batteries need large cells' approaches
  - 'Small cell' approaches

Small Cell Approach

- Use a single design of small cell in all applications
- Implies the use of an array of cells
  - Use a larger array for a large battery – not a larger cell
  - Similar philosophy to solar array
- Initial motivation for a small cell approach
  - Design & qualify a single cell design
  - Small cells are easier to design and manufacture
  - Negligible thermal gradient within cell
  - Scalability, redundancy & reliability
  - Experience with early small batteries is directly applicable to later large batteries
- Small cell approach is rapidly gaining acceptance

Flight Programs

Mission	Customer	Mission Type	Launch Date	Status
STRV-1c	UK MOD	GTO	Nov 2000	In Orbit
PROBA	ESA	LEO	Q1 2001	FM in test
ROSETTA	Astrium, UK	Interplanetary platform	2003	FM in test
MARS-EXPRESS	Astrium, Fr	Interplanetary platform	2003	PFM in manufacture
RoLand	CNES, Fr	Lander	2003	FM delivered
Beagle2	Astrium, UK	Lander	2003	BDR complete
SciSat	CSA	LEO	2002	Program KO

Sony 18650 Hard Carbon

- Mature technology - in mass production since 1992
- Production standard frozen since 1995
- Good performance and lifetime characteristics
- 5.4Wh @ 40.5g =>133Wh /kg when battery delivered
- Highly uniform production
- Tested by many organizations
- Sony now manufacture several 18650 Lithium -ion cells: only the hard carbon type is considered here

Cell Qualification Tests

CELL QUALIFICATION PARAMETER	VALUE
Non-Operating TVAC	-50°C to +70°C
Operating TVAC	Charge –25 to 60°C Discharge –25 to 60°C
Short term (emergency) temperature excursion limits	Charge and discharge at 80°C Charge and discharge at -60°C
Random Vibration	Three axis, 240 seconds per axis In-plane: $30.4g_{rms}$ (peak PSD $2g^2$/Hz) Out of plane: $30.4g_{rms}$ (peak PSD $2g^2$/Hz)
Shock	100 g, 0.5 ms half-sine (2000g qual at module level)
Radiation Tolerance	100krad and 20krad at 0%, 50% and 100% SOC
Fuse Blowing	10*C* for >250 ms @ 100% SoC 4*C* for >250 ms @ 70% SoC

Cell Quality Control

- Sony implement high level of material & process control
  - High volume production
  - 5000 cells per hour
- Long term, close relationship with Sony
- Long term supply agreement with Sony
  - Regularly procure batches > 10,000
- Lot Acceptance Test on each batch procured for space use
- Screening tests on every cell

Lot Acceptance Test

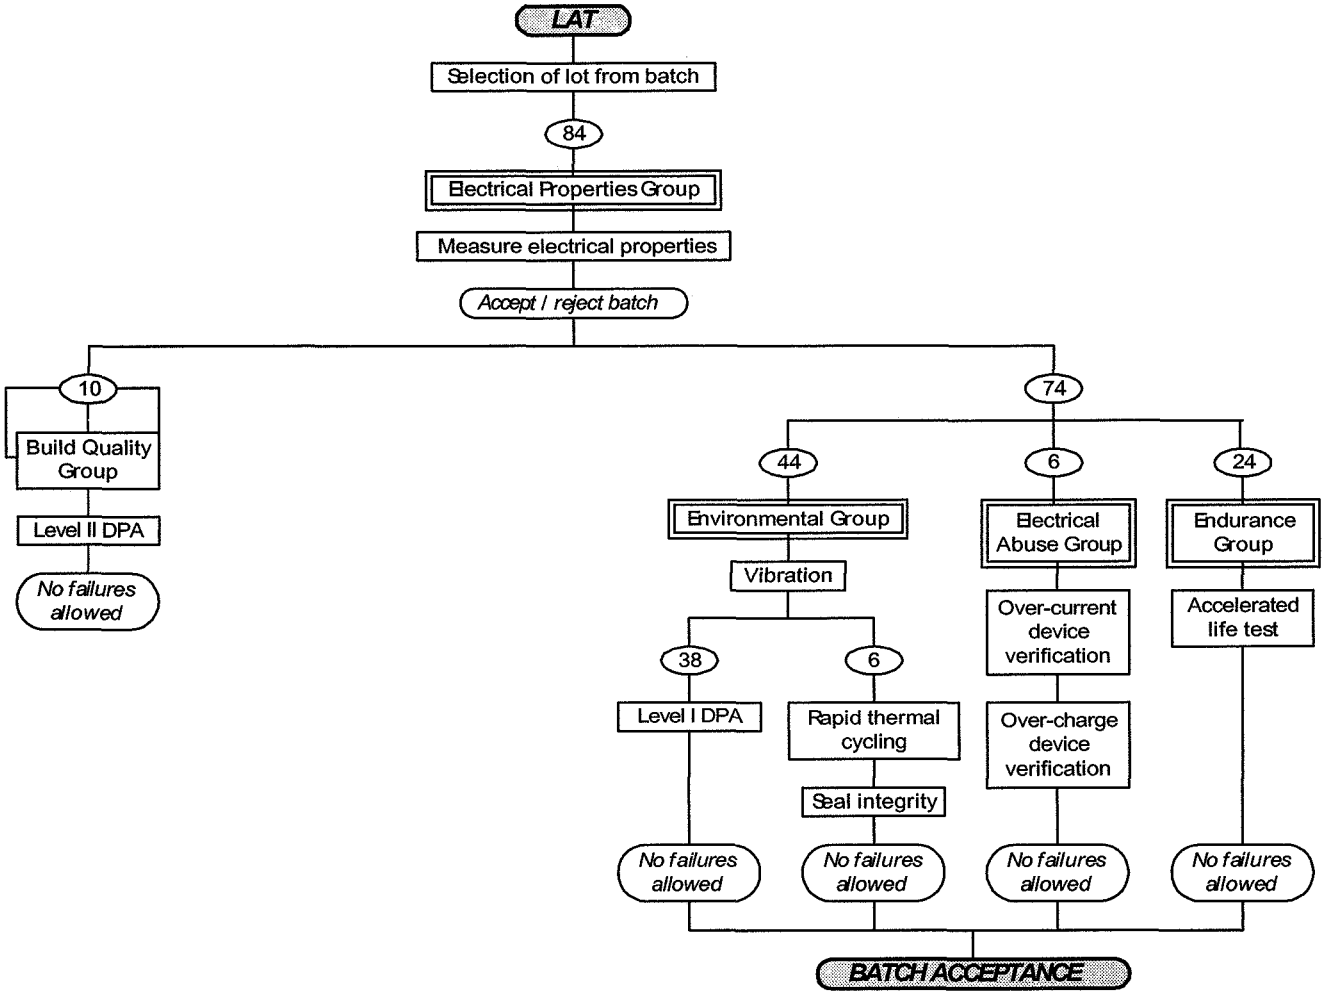

Small Cell – Small & Large Batteries

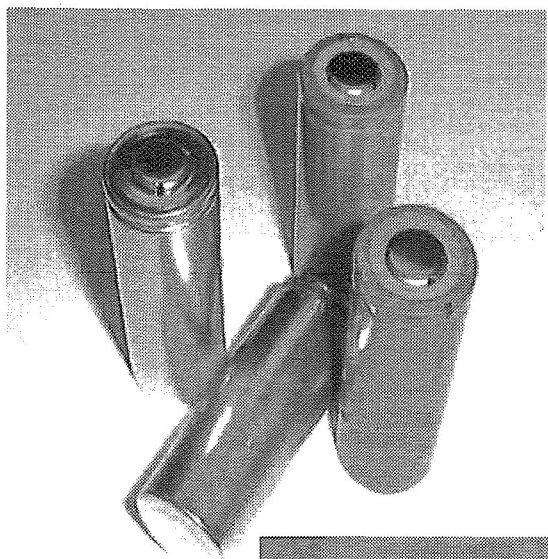

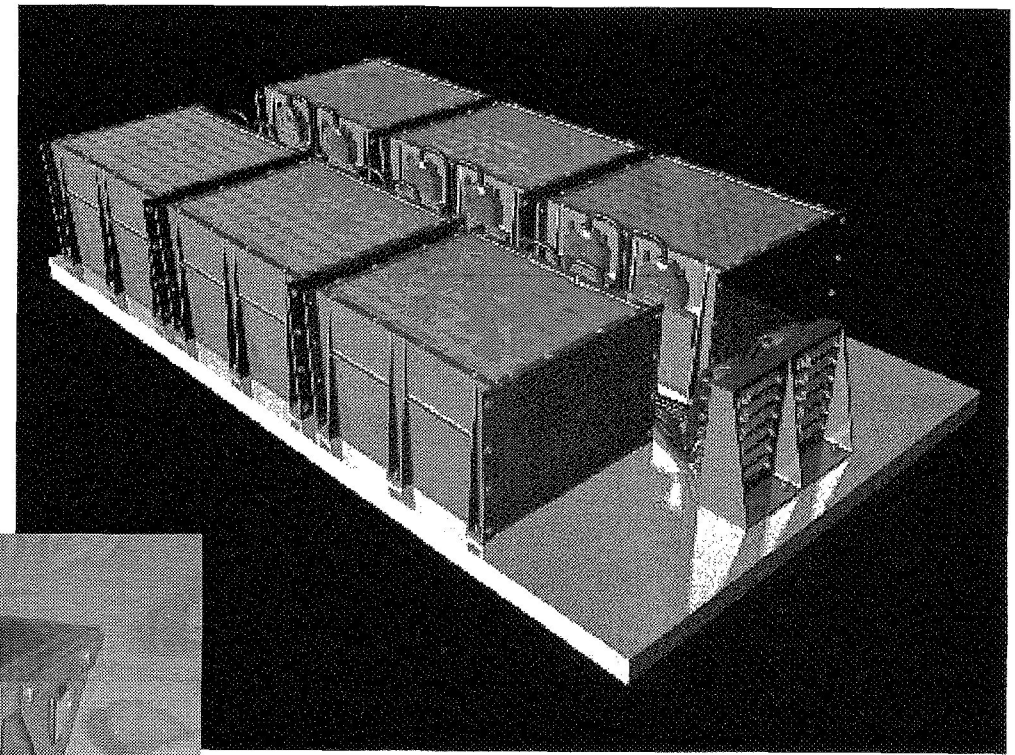

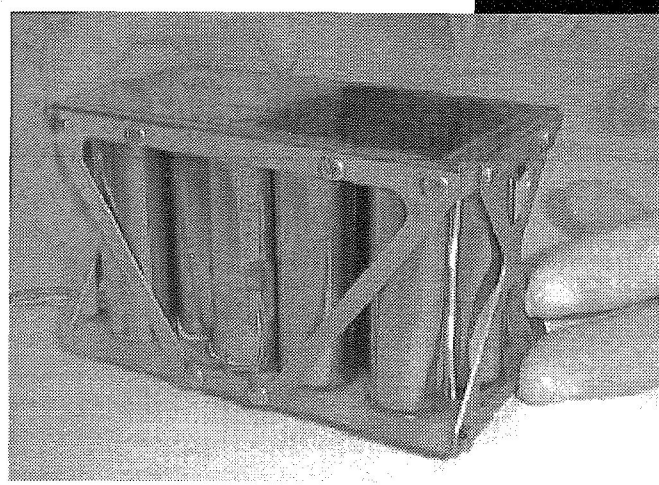

Battery Electrical Design

- Connect cells in series to provide the required voltage
- Connect strings in parallel to provide the required capacity
- Battery is a two terminal device- charge management is at battery level only
- Packaged into modules. Each module contains complete strings

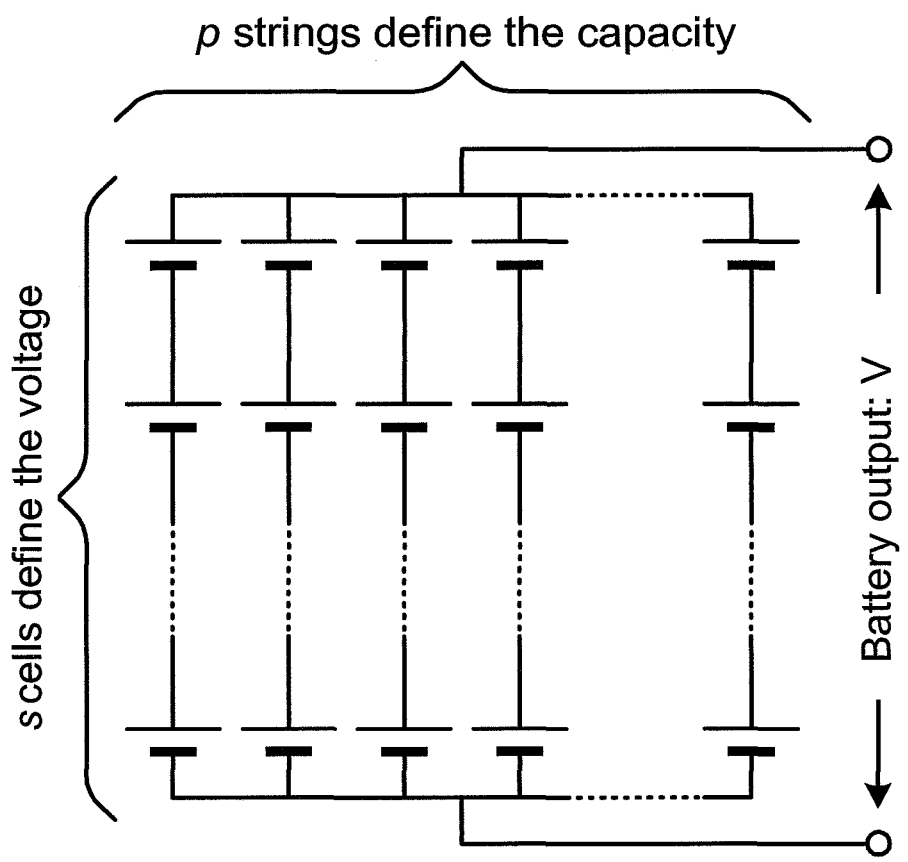

s-p topology

Reliability

- Found the Sony cells to be robust & reliable
- Assessment using MIL HBK has been performed
- Small cell approach allows redundant strings to be included at very low mass penalty
- Provision of modest levels of redundancy allows high reliability to be easily achieved and reduces stress on cells
- (Try getting a solar array manufacturer to use a small number of very large solar cells !)

Cell Packaging Concept

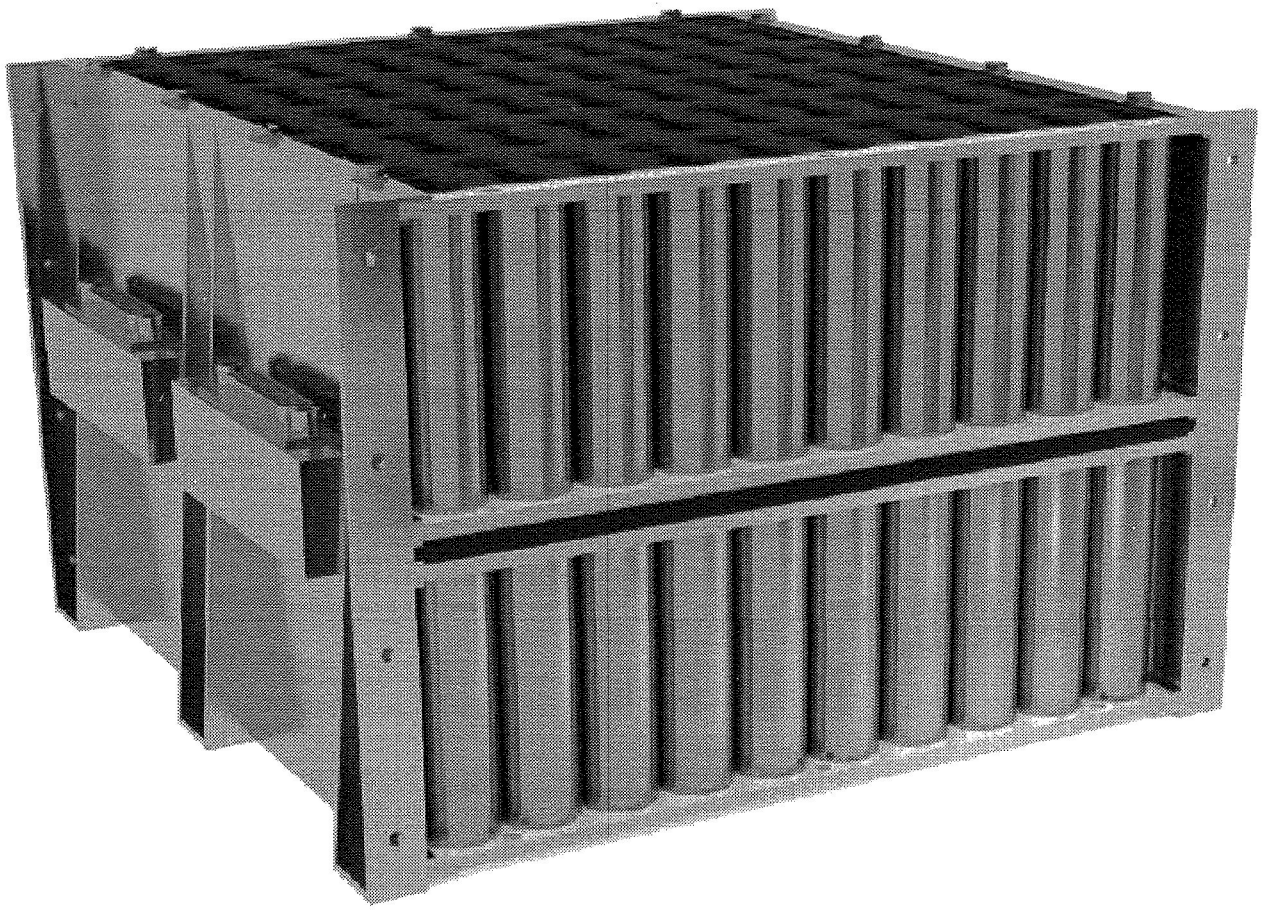

Qualified Battery Module

- Qualification of a point design of a highly scalable concept
- Each string has 11 cells for 50V operation
- Module contains 20 strings for 30Ah capacity
- Testing completed Jan 1999
- Measured battery energy density is 117 Wh/kg

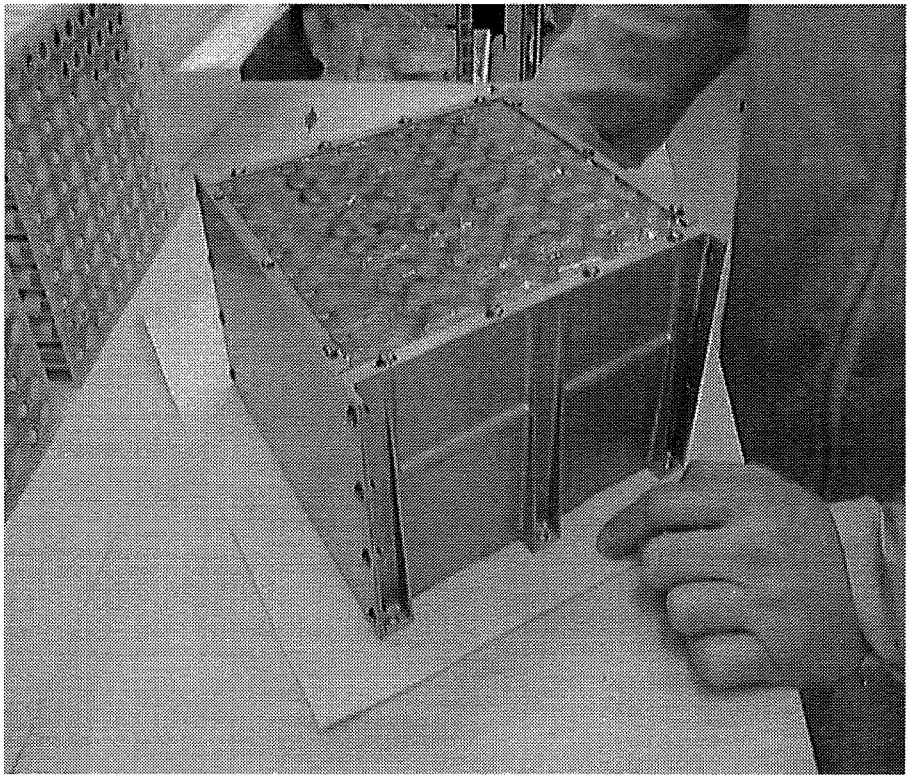

Characterization & Life Test

- Extensive testing for space applications
  - 2 million cell -hours
- Most tests performed on small 6s 2p modules
- All generic life tests performed at 4.2V per cell EOCV
- Temperature sensitivity
  - 0°C, 10°C, 20°C, 40°
- Depth of discharge (relative to BOL 4.2V capacity)
  - 10% to 100%
- Rate
  - C/2 to 1.8C in discharge, C/20 to 1.8C in charge
- Real time tests

Internal Resistance

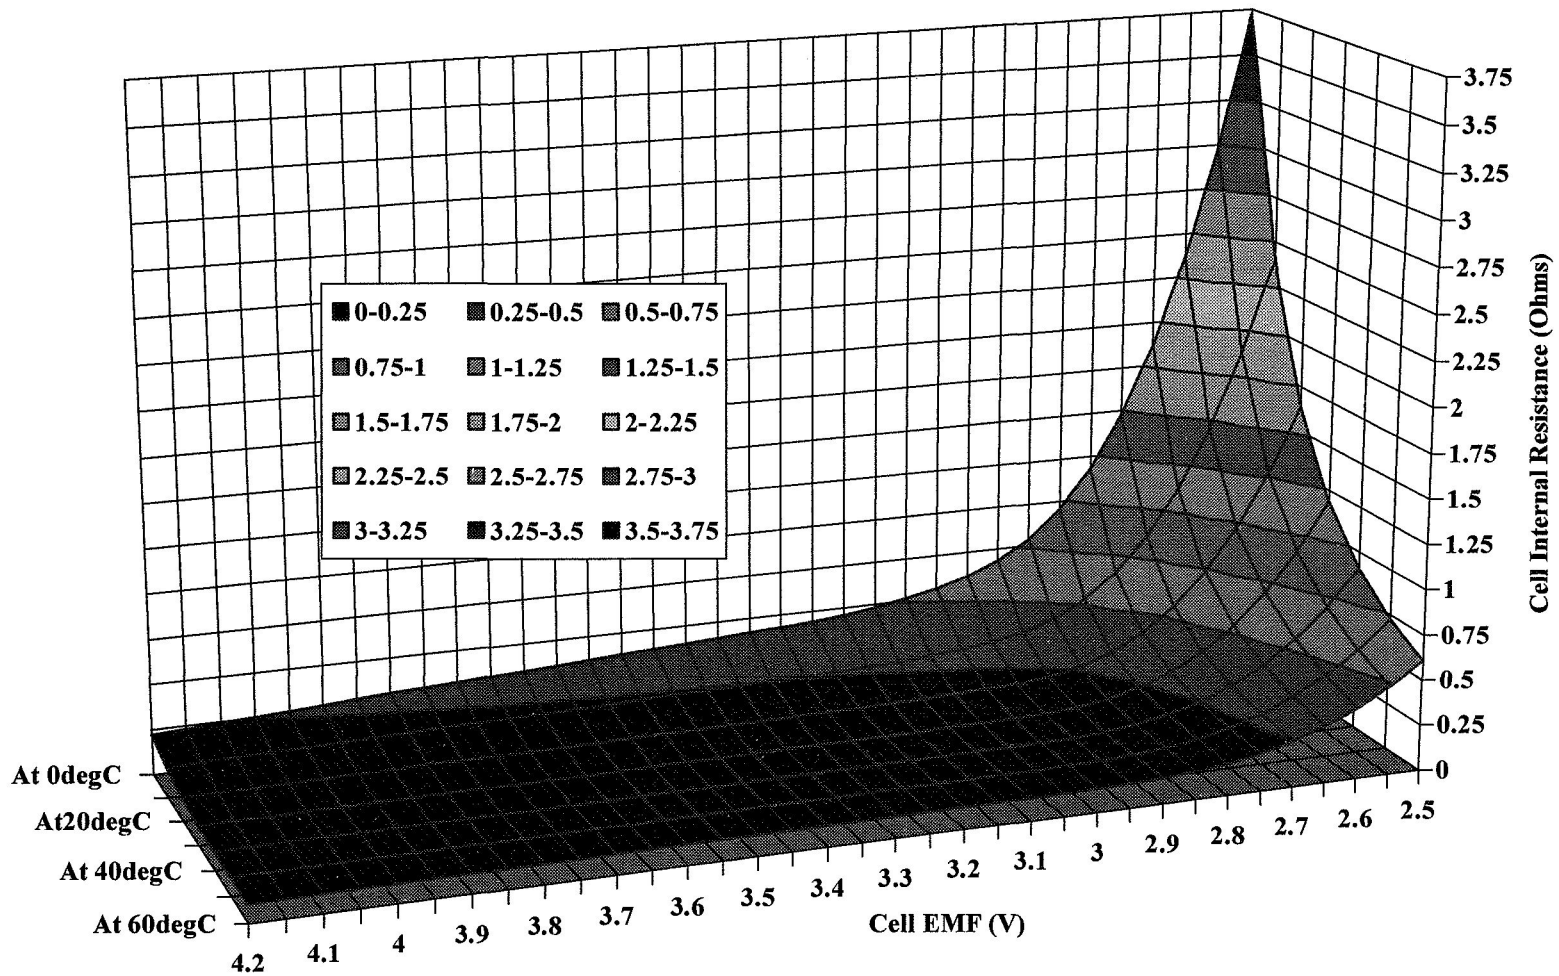

72 Simulated GEO Eclipse Seasons

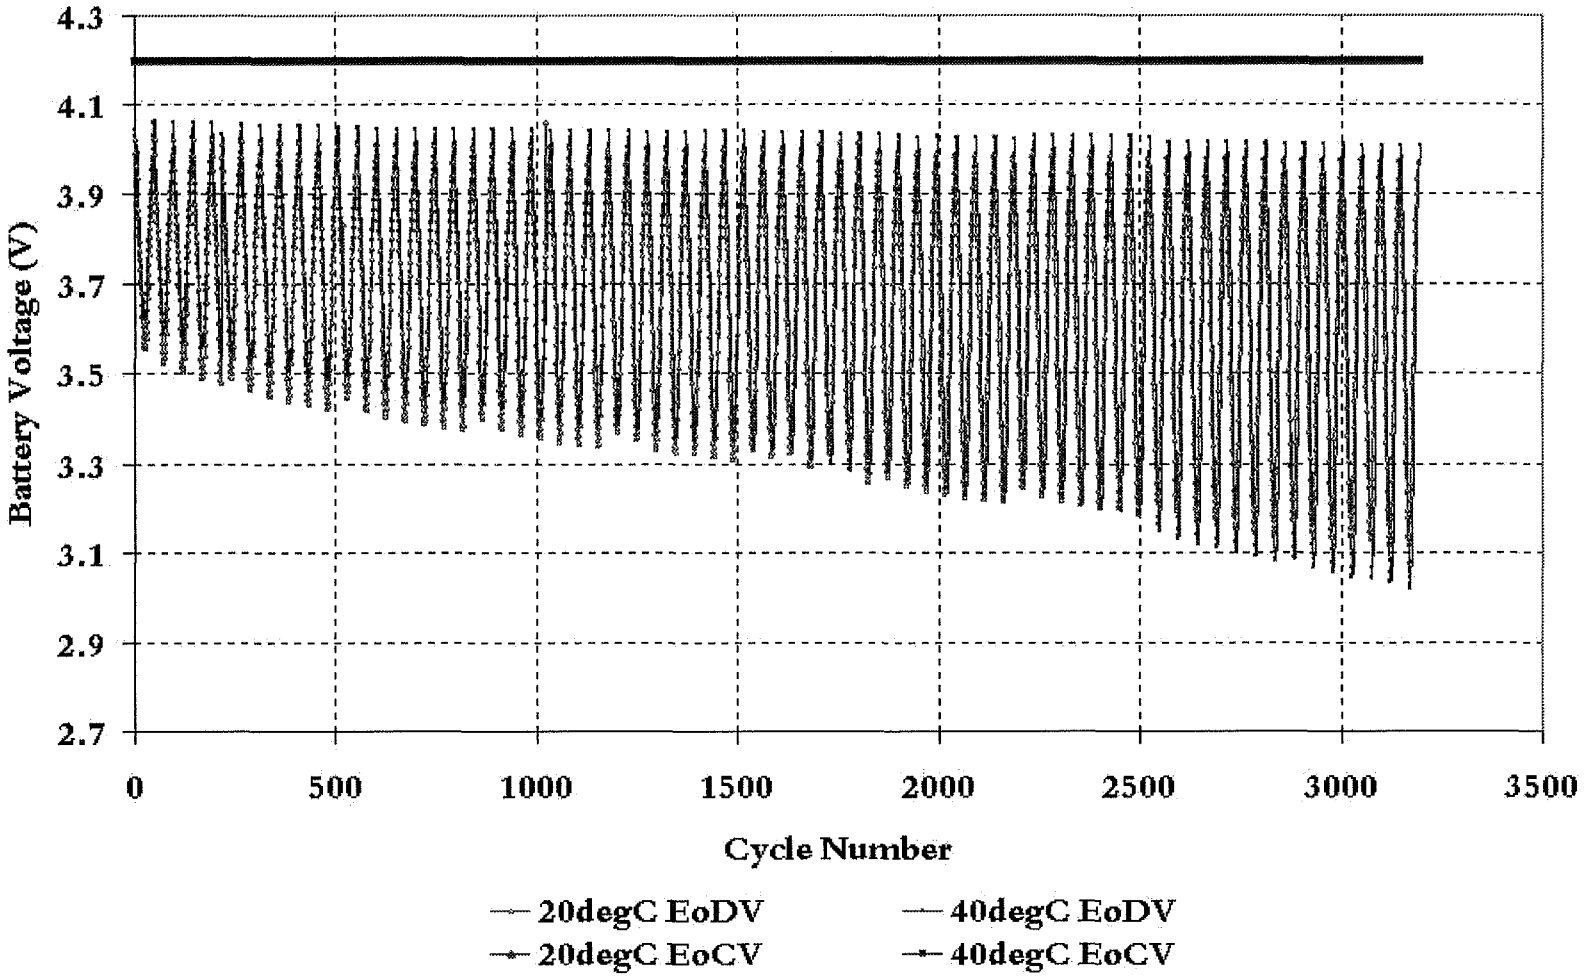

Capacity After Variable DOD Cycling

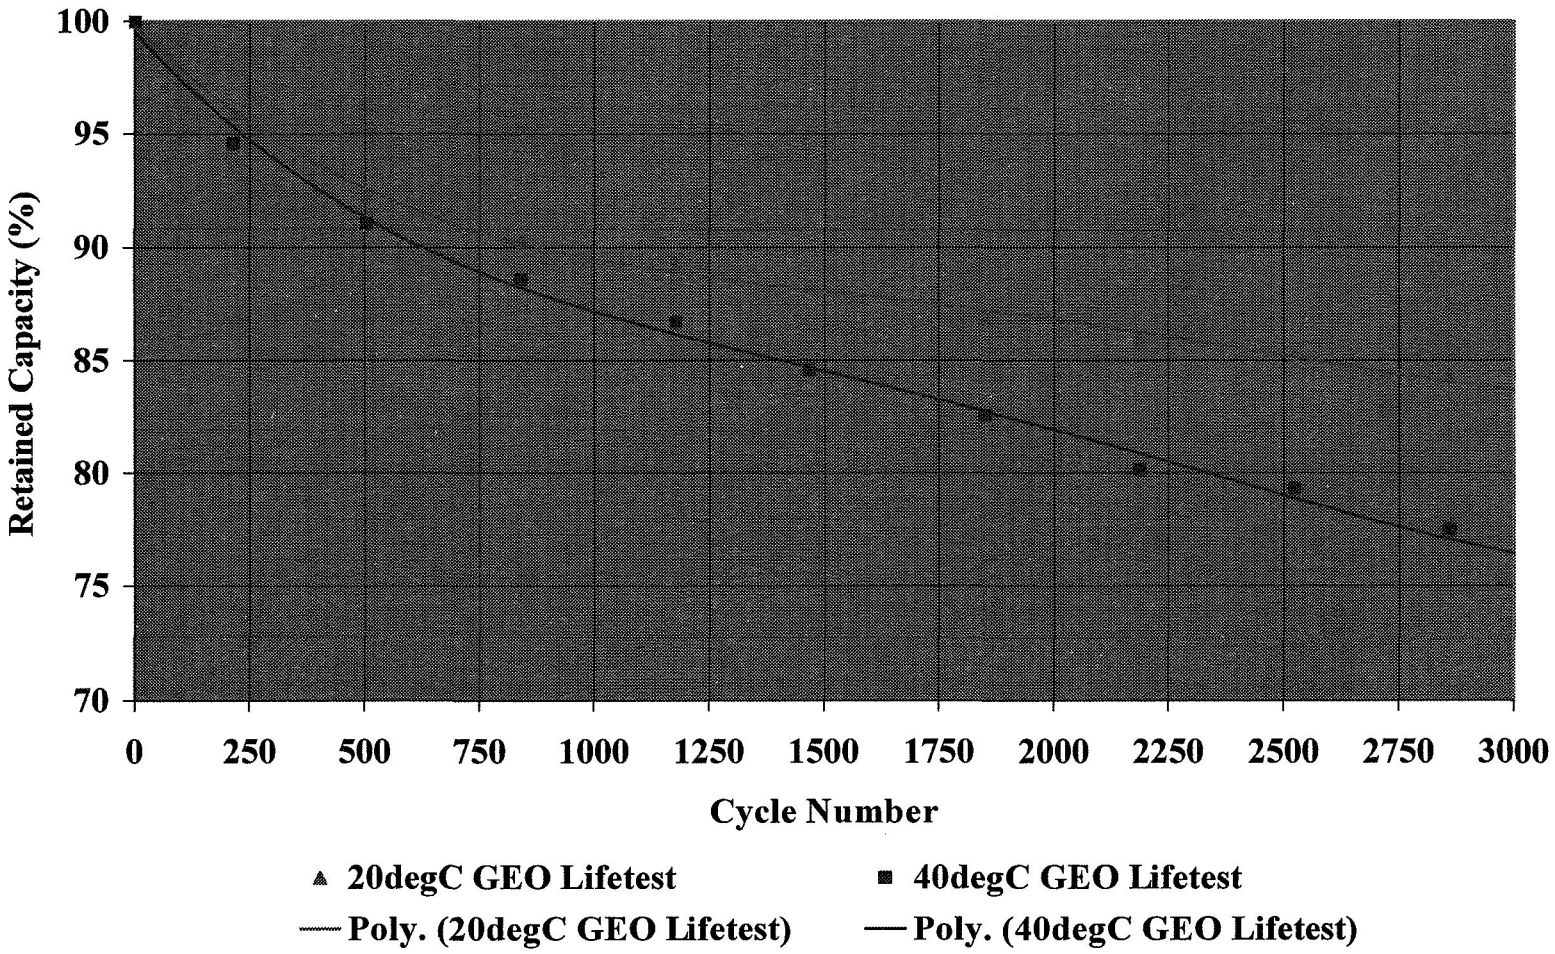

Constant DOD GEO cycling

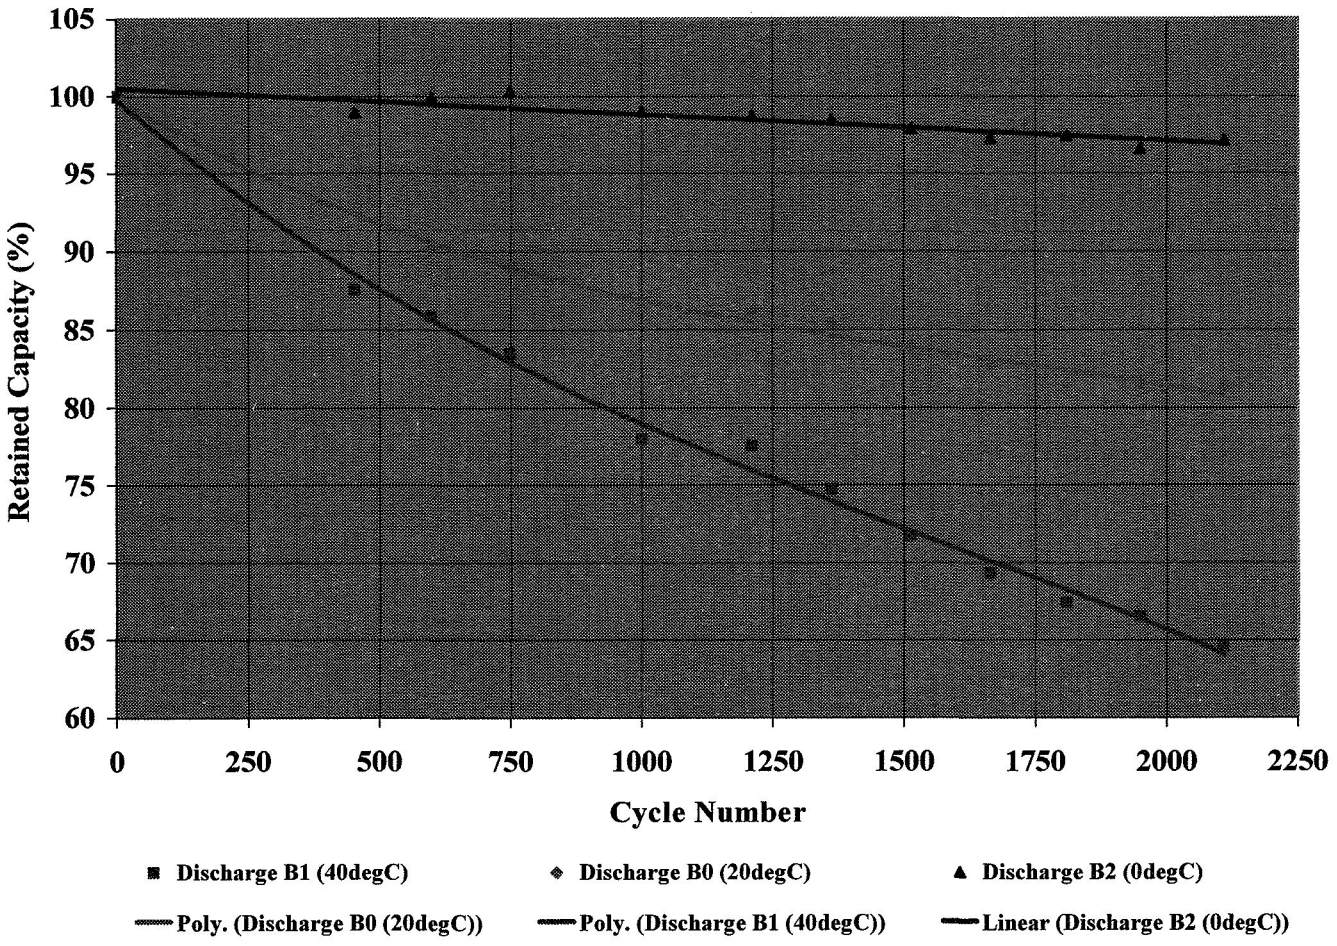

Calendar Aging

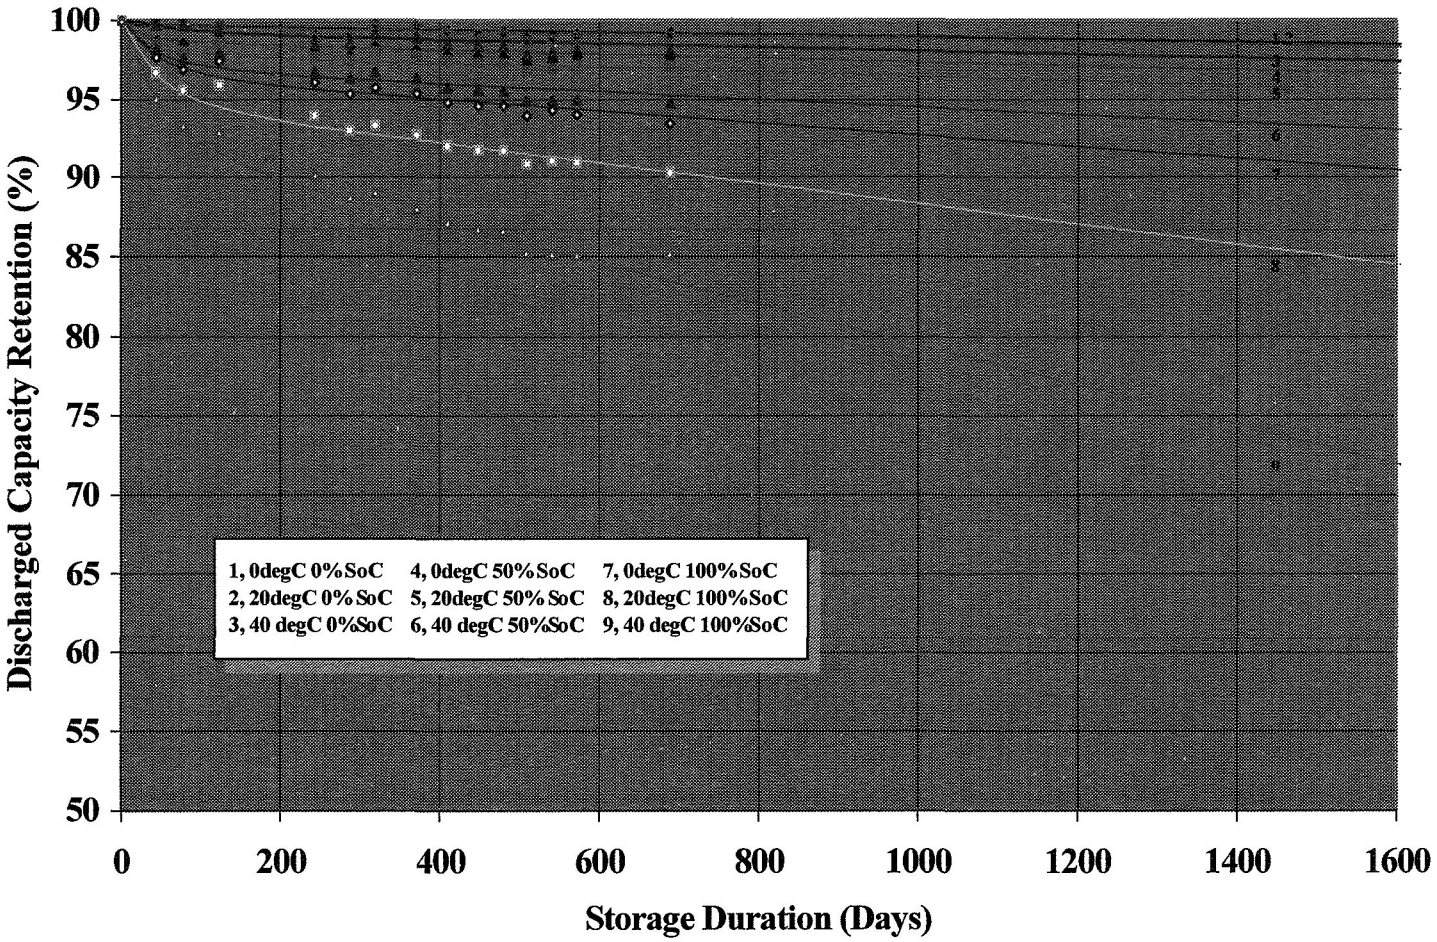

Larger Modules

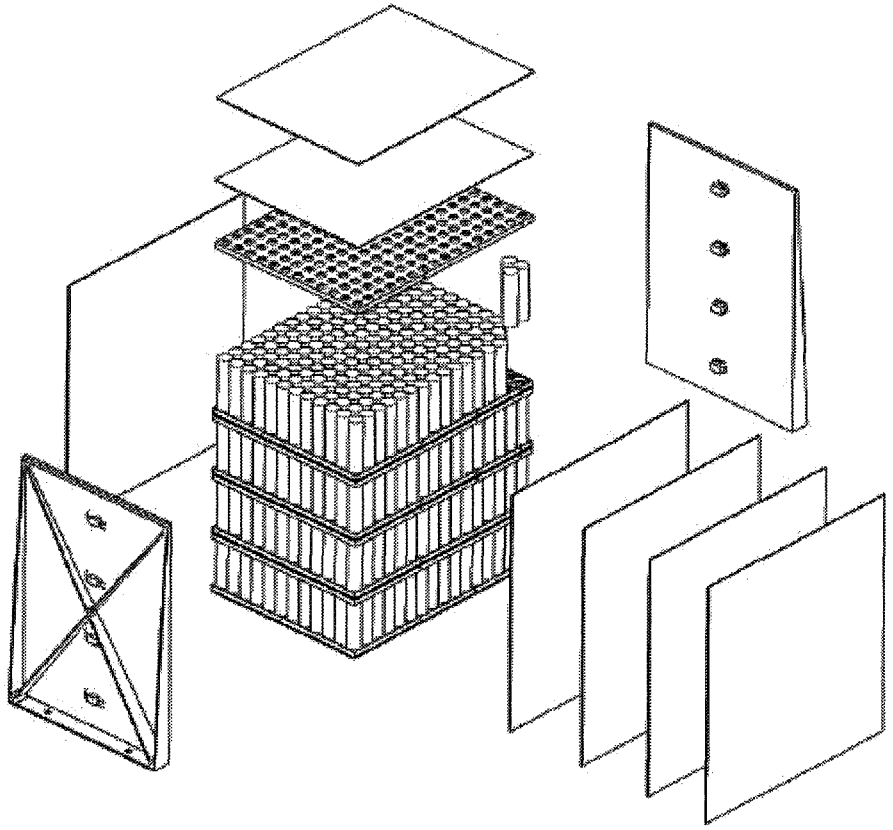

Scale – Up Tests

- Series of planned ground tests
- Voltages between 50V and 100V
- Single & multiple module tests
- Several different test locations

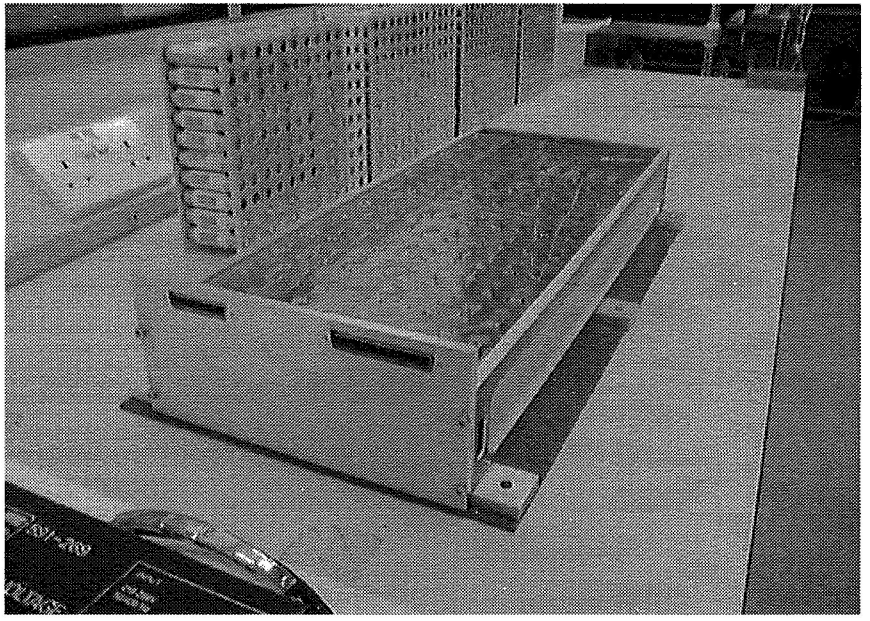

Conclusions

- Small cell approach to satellite Lithium -ion batteries is both viable and attractive
- Small cells can be used to build large batteries
- Use of Sony 18650 HC cells maximizes maturity and delivers excellent performance
- Excellent possibilities for delivering much higher performance in the future

Simulated LEO Cycling of AEA-STRV Lithium-Ion Battery Modules

Philip Johnson and Chuck Lurie
TRW Space and Electronics Group
Redondo Beach, California 90278

R. Spurrett
AEA Technology plc
Abingdon, Oxon., England

The 2000 NASA Aerospace Battery Workshop
Holiday Inn -- Research Park
Huntsville, Alabama
November 14 - 16, 2000

53/ar/11/4pf
20011183 56
538 NB
16 95

Scope

- Lithium-ion battery modules, similar to the modules to be flown on the STRV spacecraft, have been on test for almost two years.
- The modules, designed and assembled by AEA Technology plc, each contain twelve Sony 26650 cells.
- Characterization testing and LEO cycling through 2700 25% DOD cycles were reported at this workshop last year.
- This presentation summarizes the results of the simulated LEO cycling to date.

Test Articles

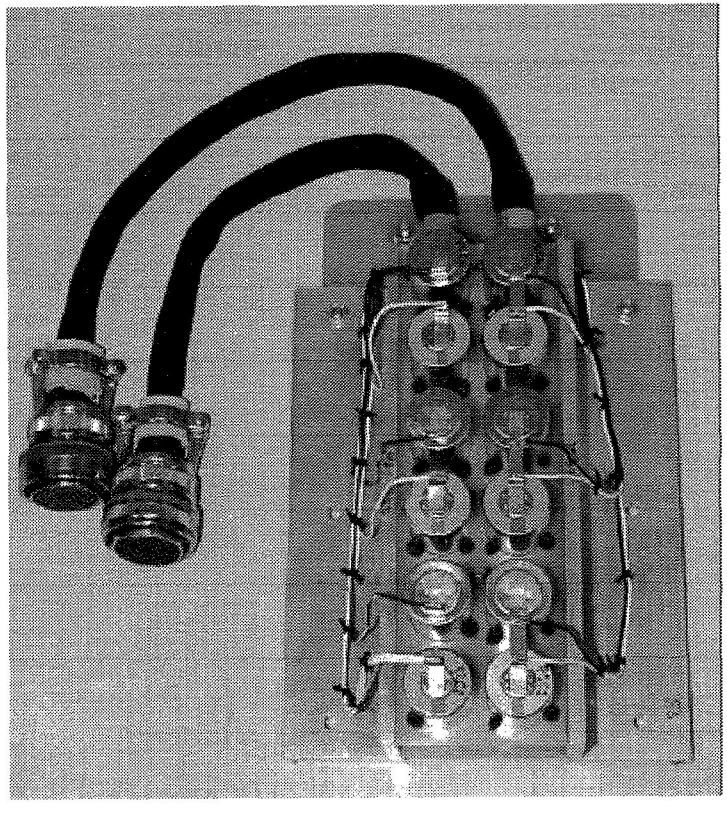

- STRV modules consist of two 6-cell strings of Sony 26650 cells.
- Test modules were reconfigured
  - one 6-cell string
  - two 2-cell strings
  - two individual cells
- Each cell is equipped with a thermocouple at its midpoint.

Test Plan
Simulated Leo Cycling

- Depth of Discharge: 25% (basis 2.7 Ah nameplate capacity)
- Orbit: 100 minutes with 36 minute eclipse periods
- Charge regime: 0.5C to CVL; taper until eclipse discharge
- Charge management: Pack level, e.g.,
  - 6-cell average voltage for the 6-cell packs
  - 2-cell average voltage for the 2-cell packs
  - individual cell control for the single cells
- Discharge: 0.42C (36 minutes)
- Two modules were tested; one at 25°C and one at 15°C

Test Setup

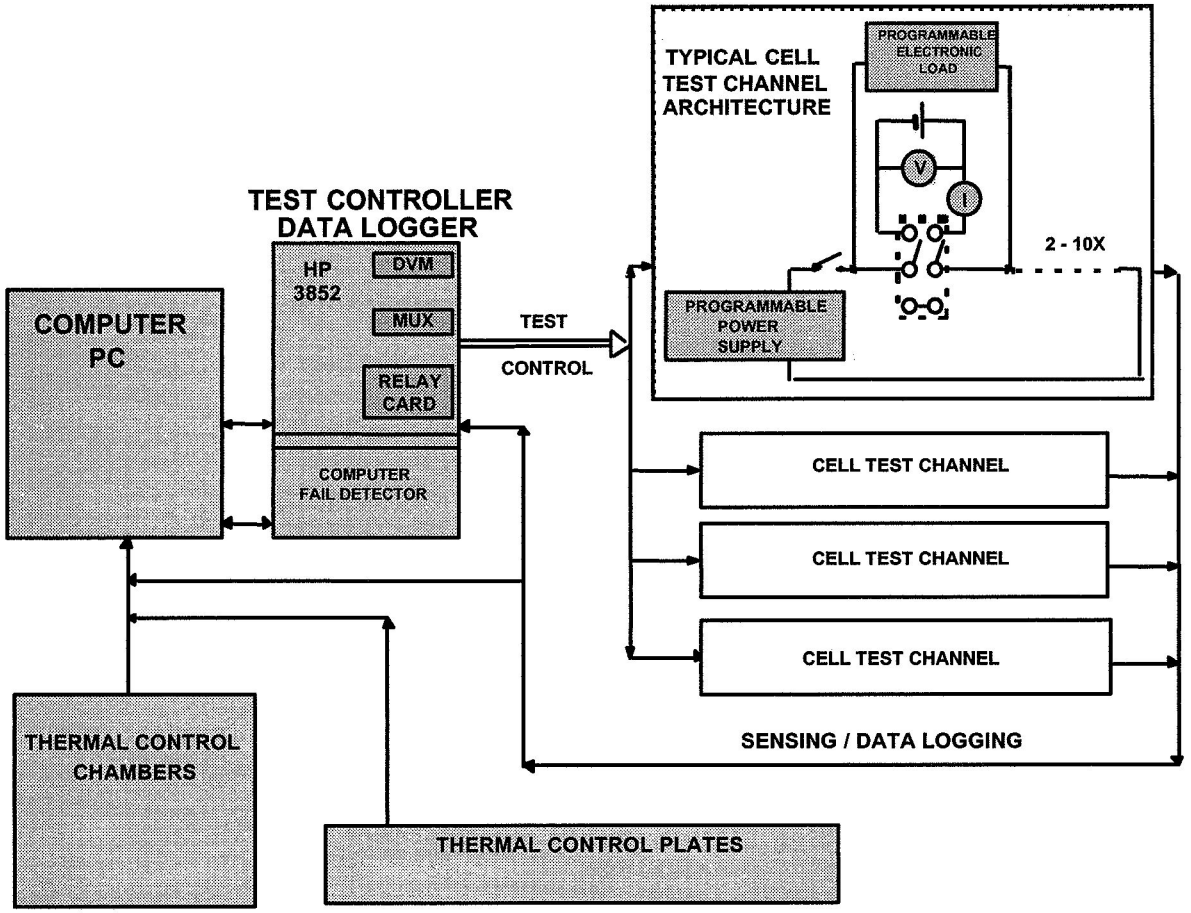
TYPICAL CELL
TEST CHANNEL
ARCHITECTURE
PROGRAMMABLE
ELECTRONIC
LOAD
V
I
2 - 10X
PROGRAMMABLE
POWER
SUPPLY
TEST CONTROLLER
DATA LOGGER
HP
3852
DVM
MUX
RELAY
CARD
COMPUTER
FAIL DETECTOR
COMPUTER
PC
TEST
CONTROL
CELL TEST CHANNEL
CELL TEST CHANNEL
CELL TEST CHANNEL
SENSING / DATA LOGGING
THERMAL CONTROL
CHAMBERS
THERMAL CONTROL PLATES

Simulated LEO Cycling Results

- 25°C End of Discharge Voltage trend charts
  - 6-cell Pack
  - 2-cell pack (typical of two)
  - single cells (both cells on one plot)
- 15°C End of Discharge Voltage trend charts
  - 6-cell Pack
  - 2-cell pack (typical of two)
  - single cells (both cells on one plot)
- 6-cell pack dispersion analysis
  - EODV Trending
  - Rate of Change of EODV
  - EOCV Trending

25% DOD LEO Cycling at 25 Deg C -- 6-Cell Pack

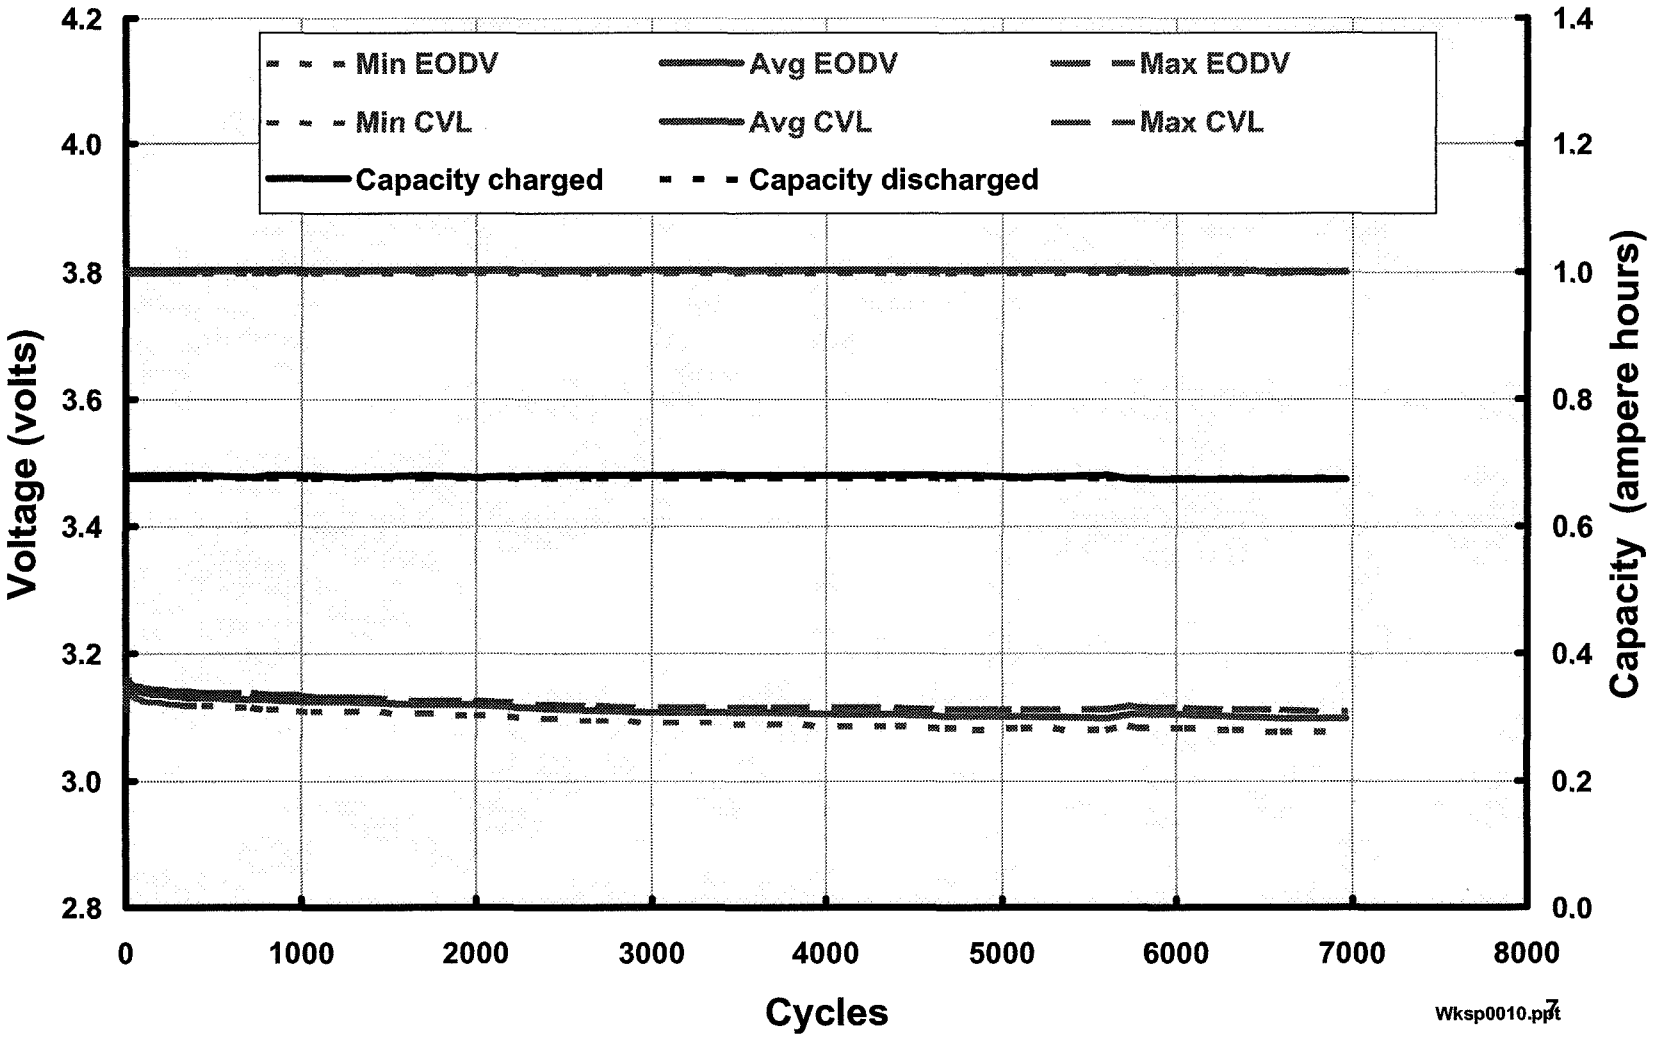

25% DOD LEO Cycling at 25 Deg C -- 2-Cell Pack

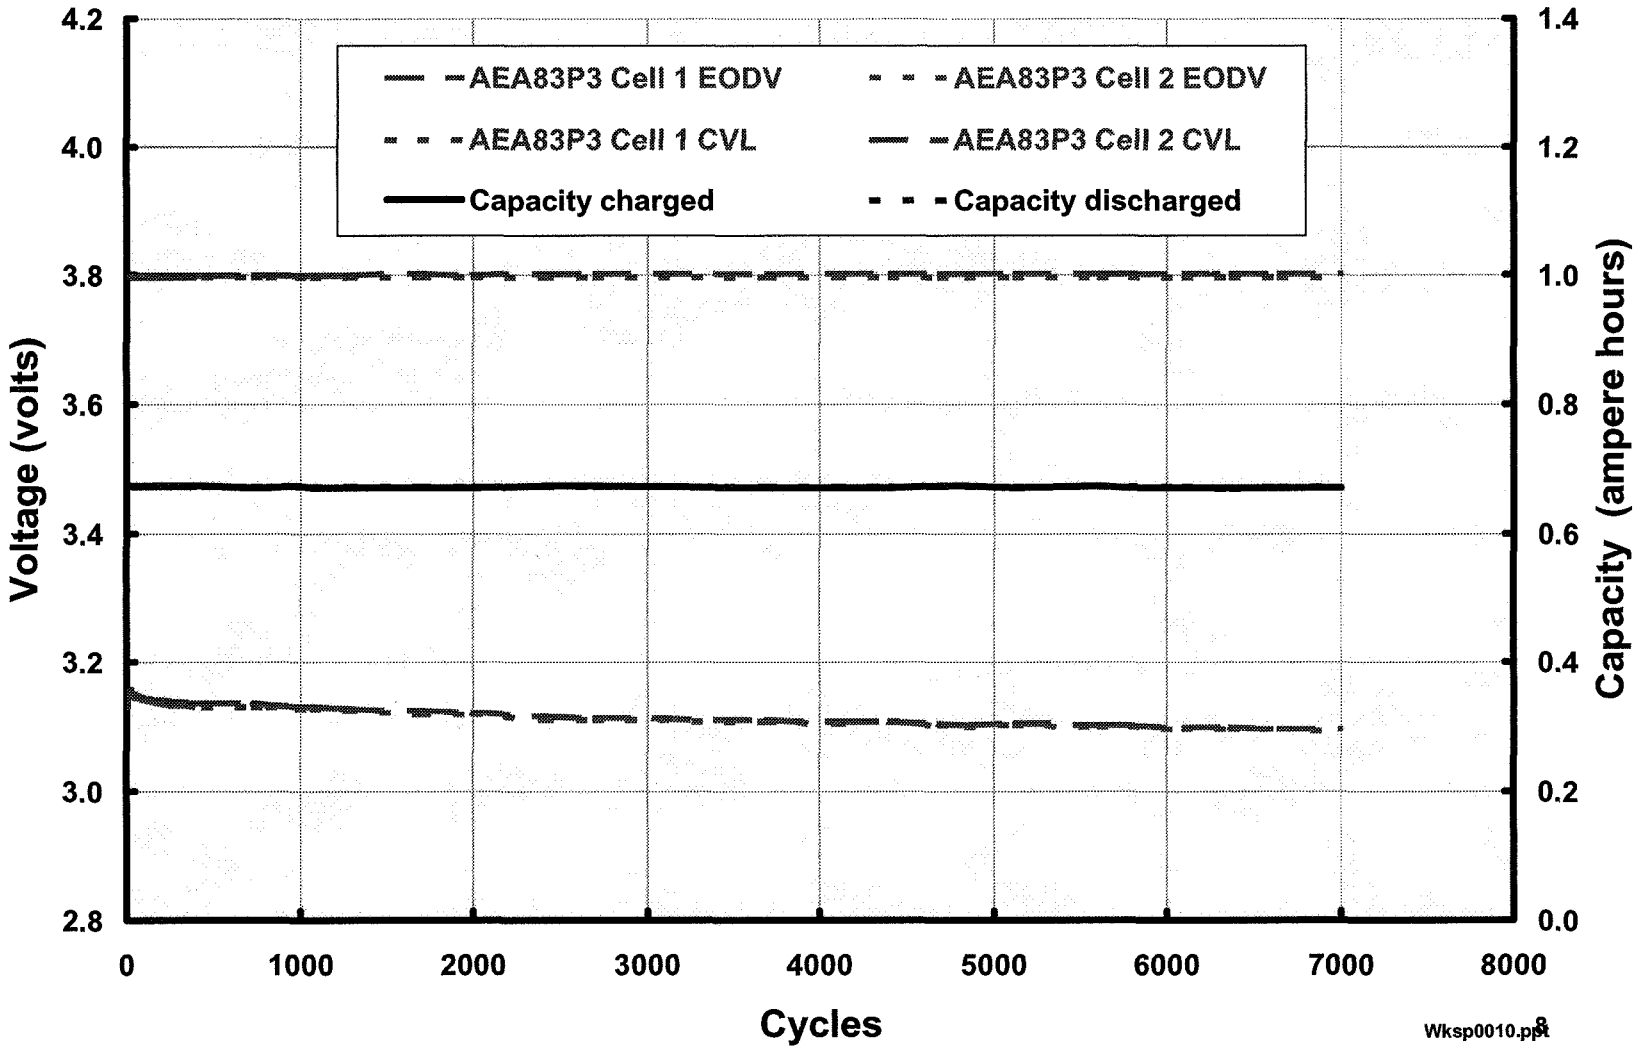

25% DOD LEO Cycling at 25 Deg C -- Single Cells

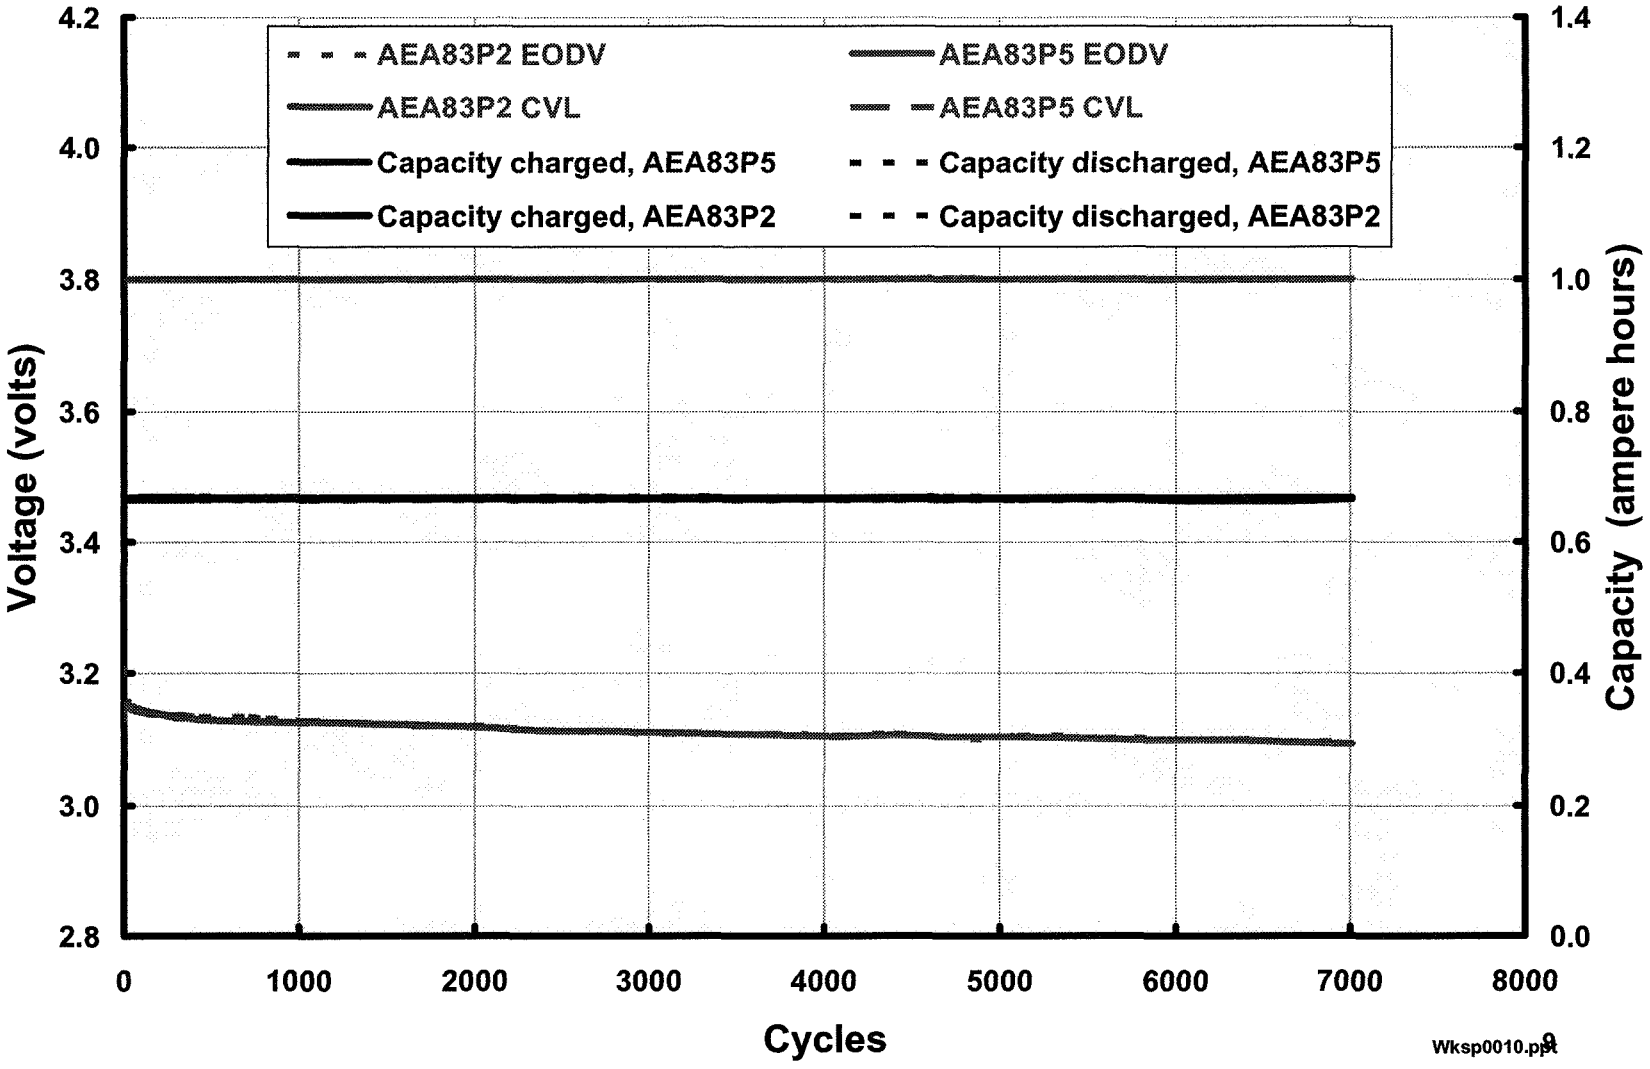

25% DOD LEO Cycling at 15 Deg C -- 6-Cell Pack

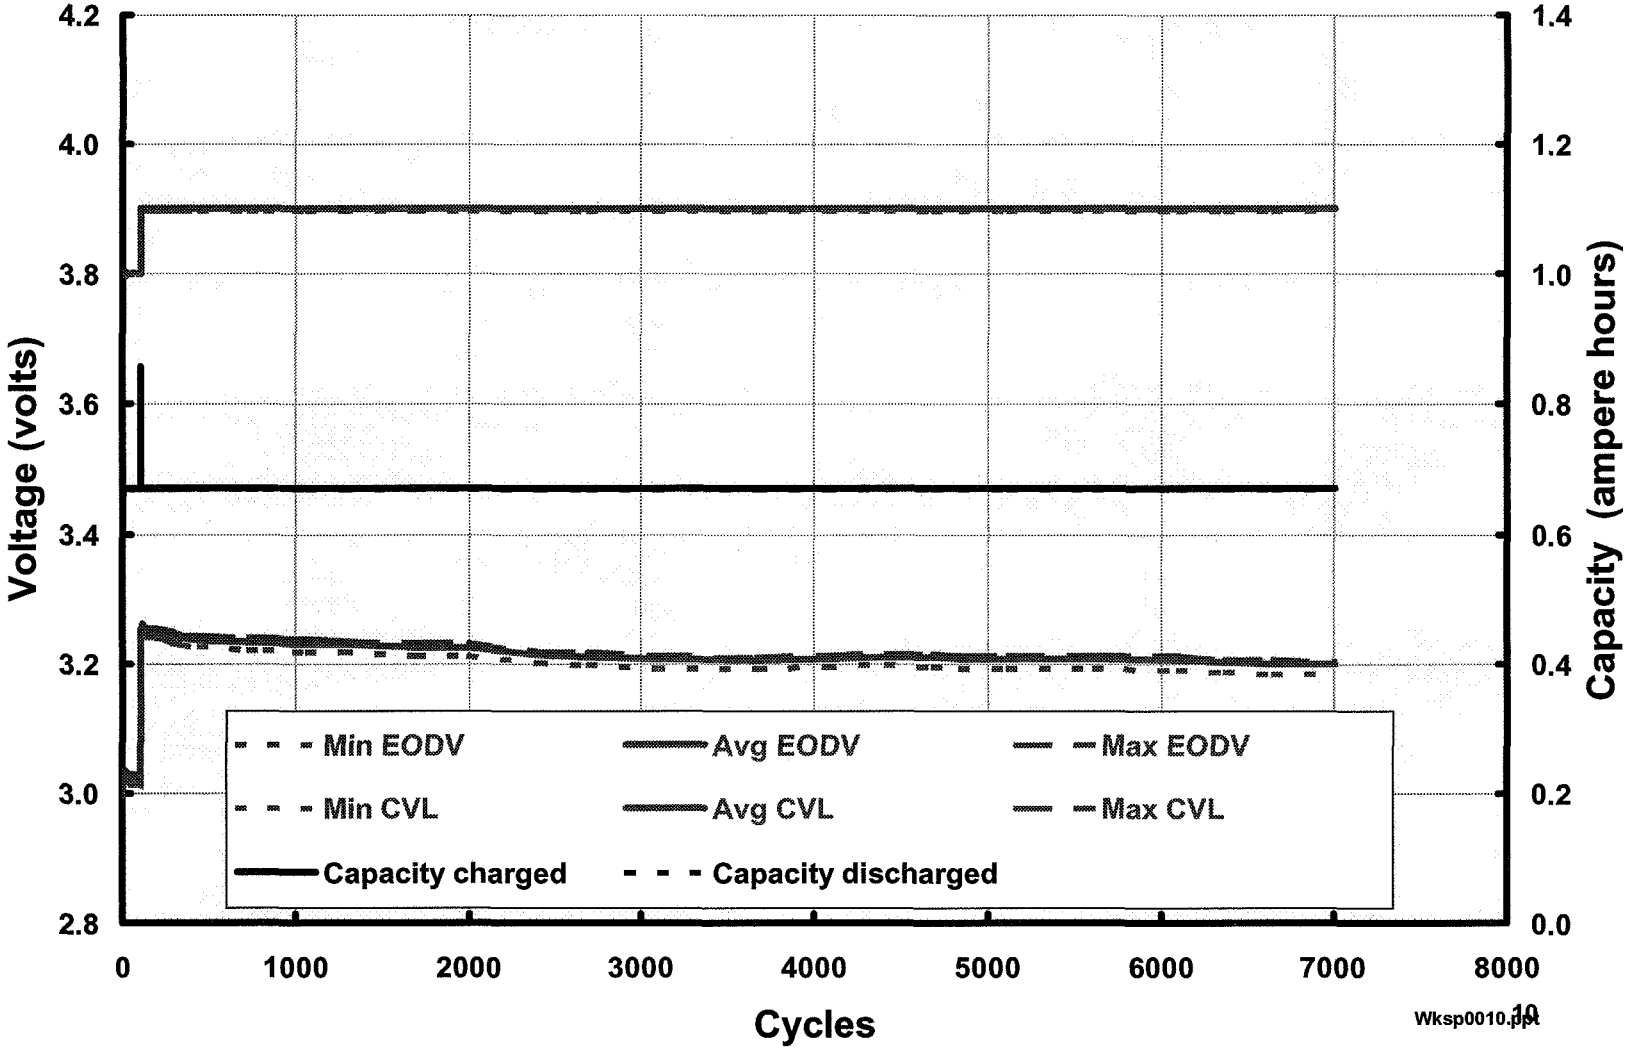

25% DOD LEO Cycling at 15 Deg C -- 2-Cell Pack

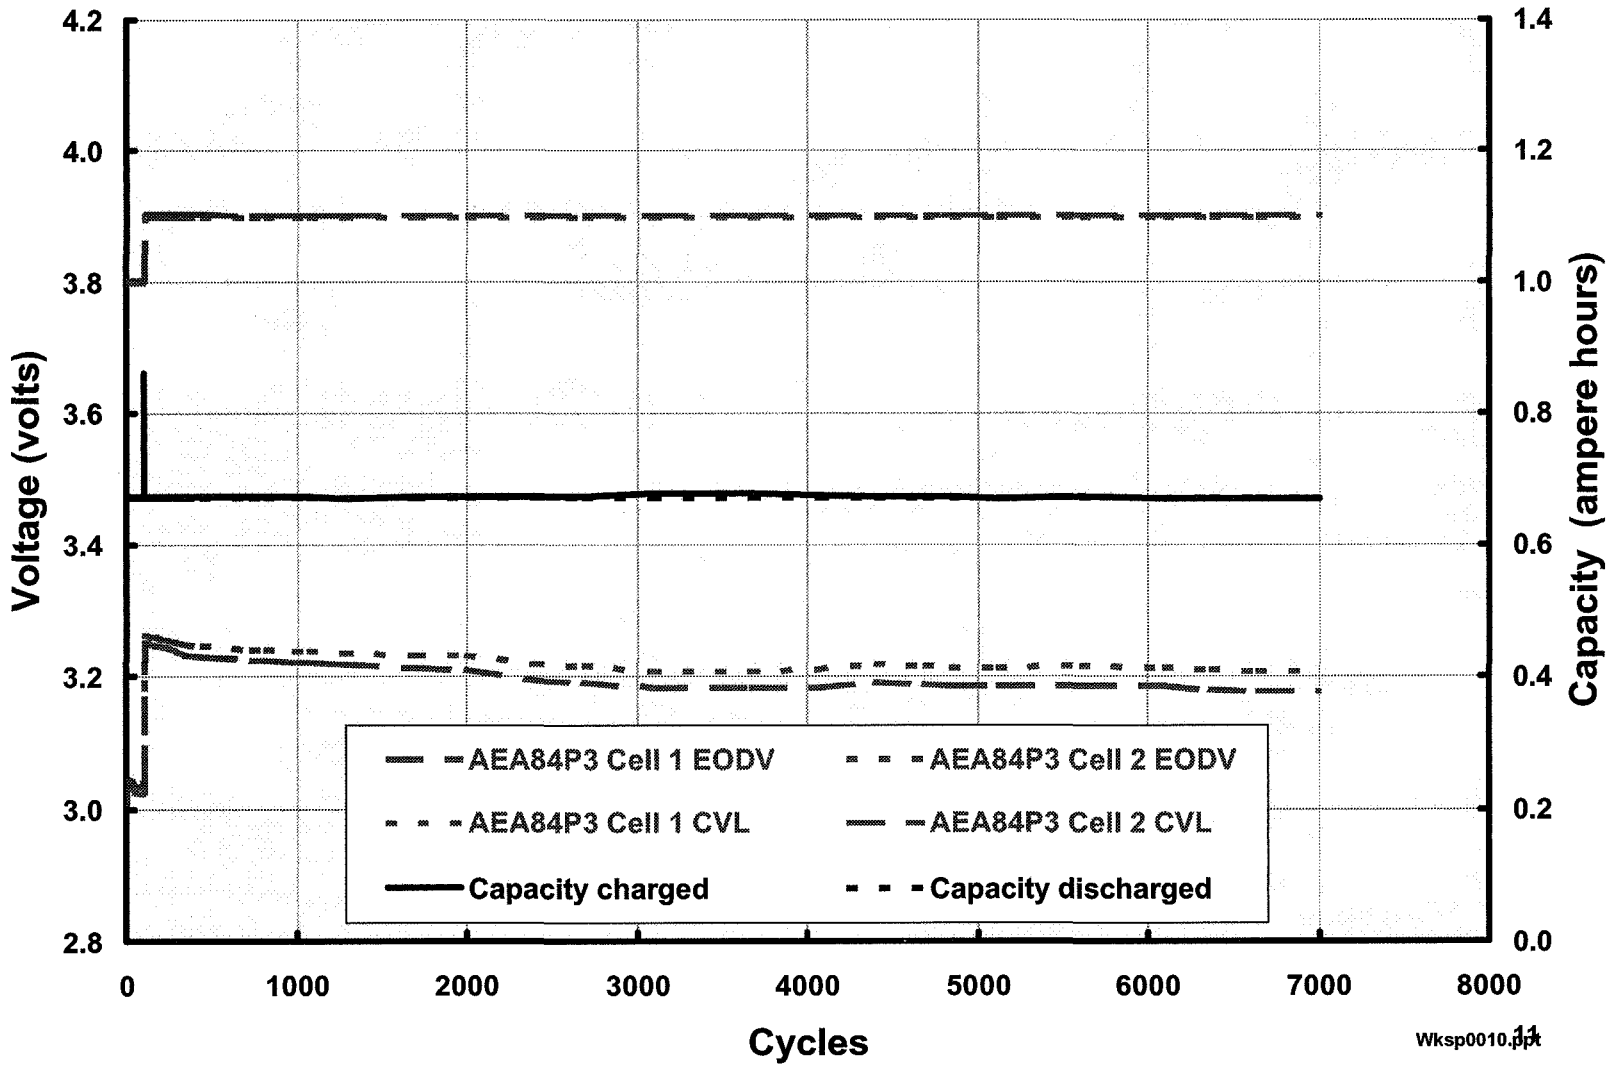

25% DOD LEO Cycling at 15 Deg C -- Single Cells

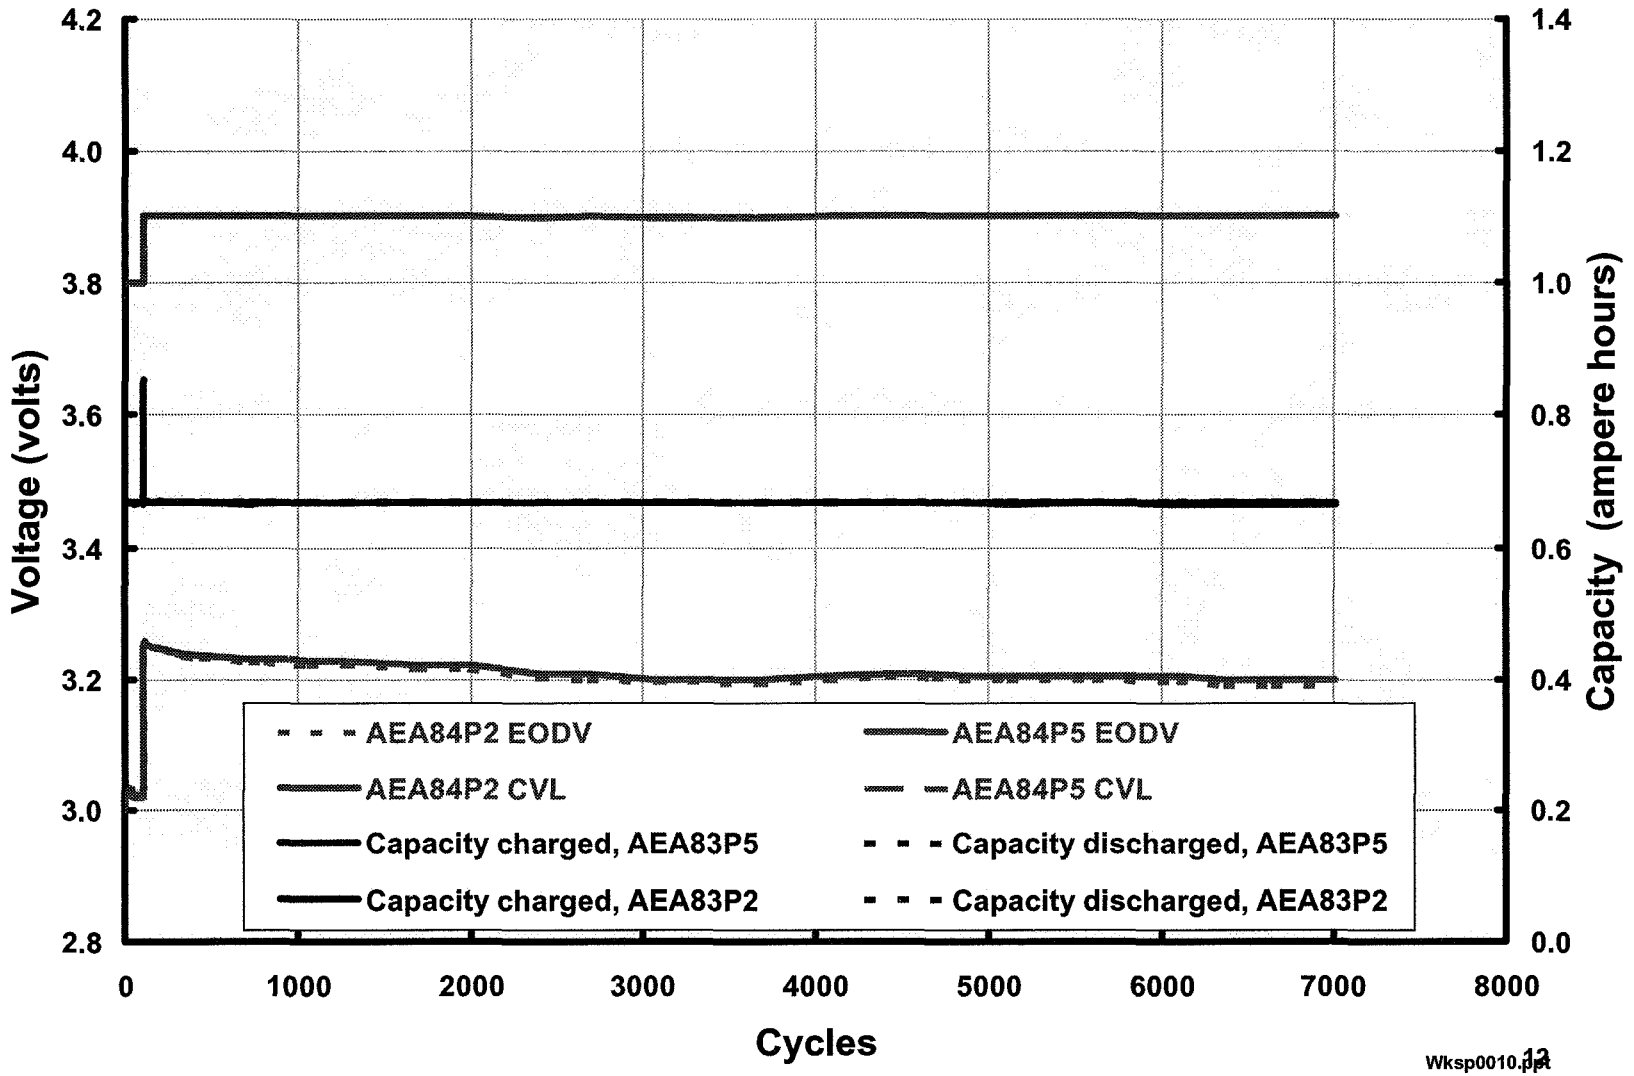

EODV Dispersion Trending

AEA STRV 6-Cell Packs at 15ºC and 25ºC

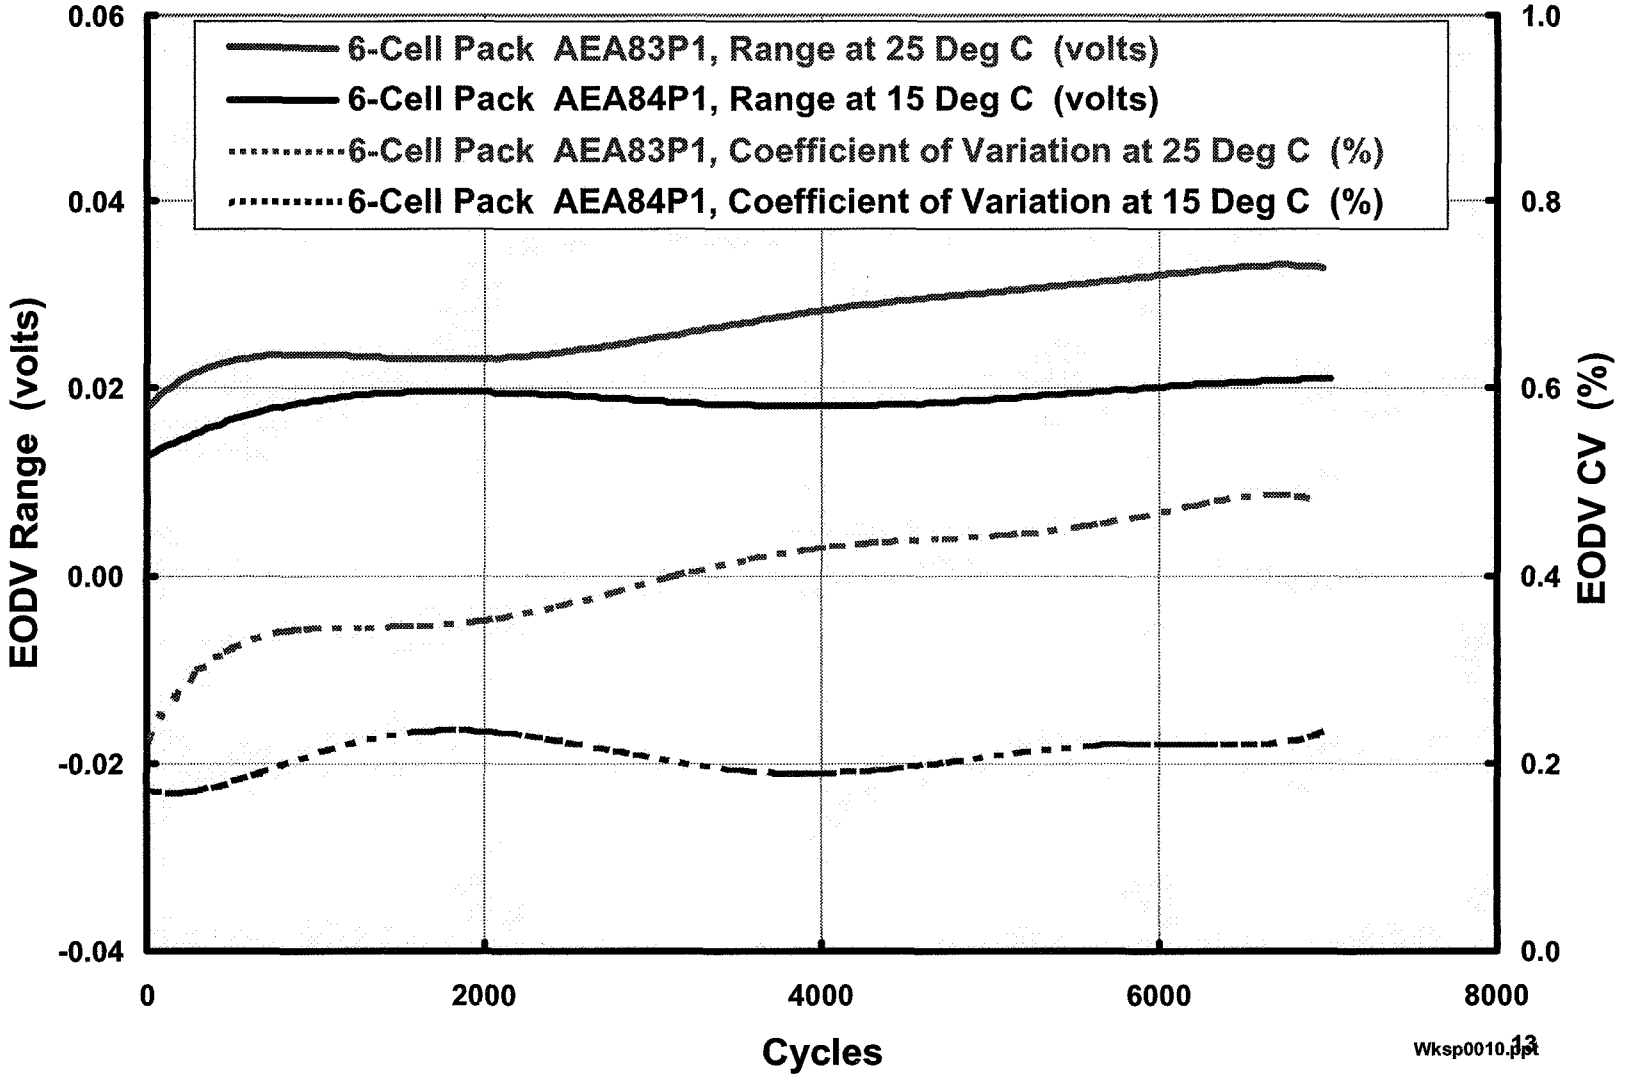

Rate of Change of EODV Dispersion as a Function of Cycling
AEA STRV 6-Cell Packs

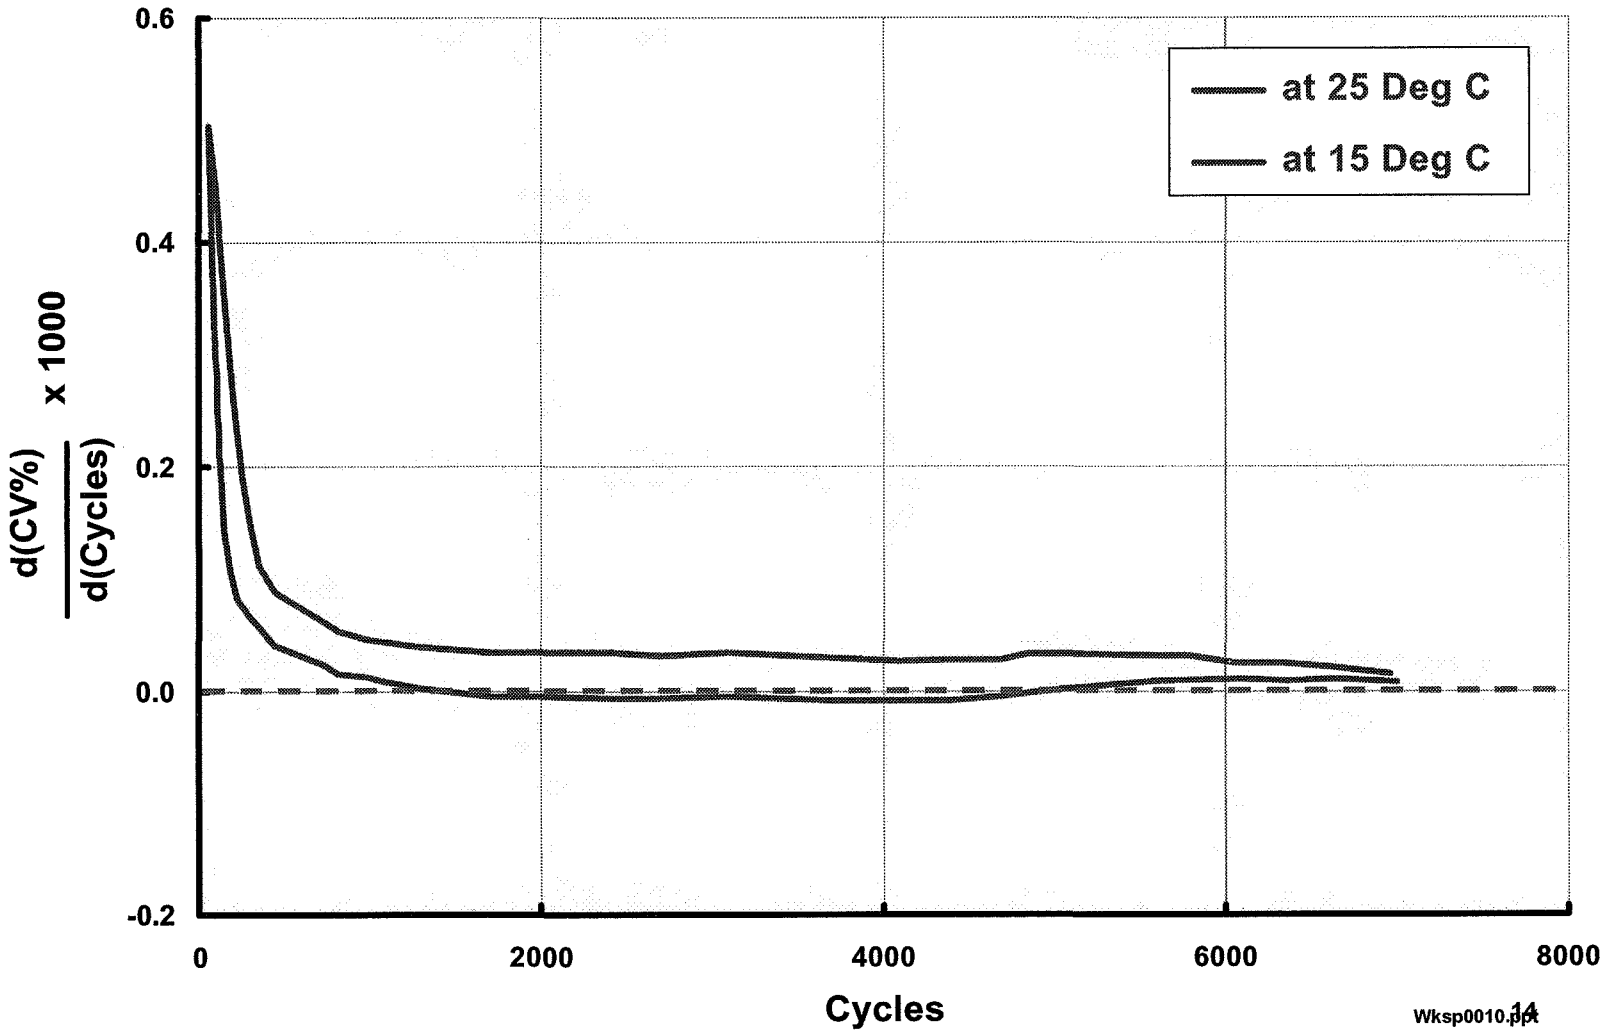

EOCV Dispersion Trending

AEA STRV 6-Cell Packs at 15ºC and 25ºC

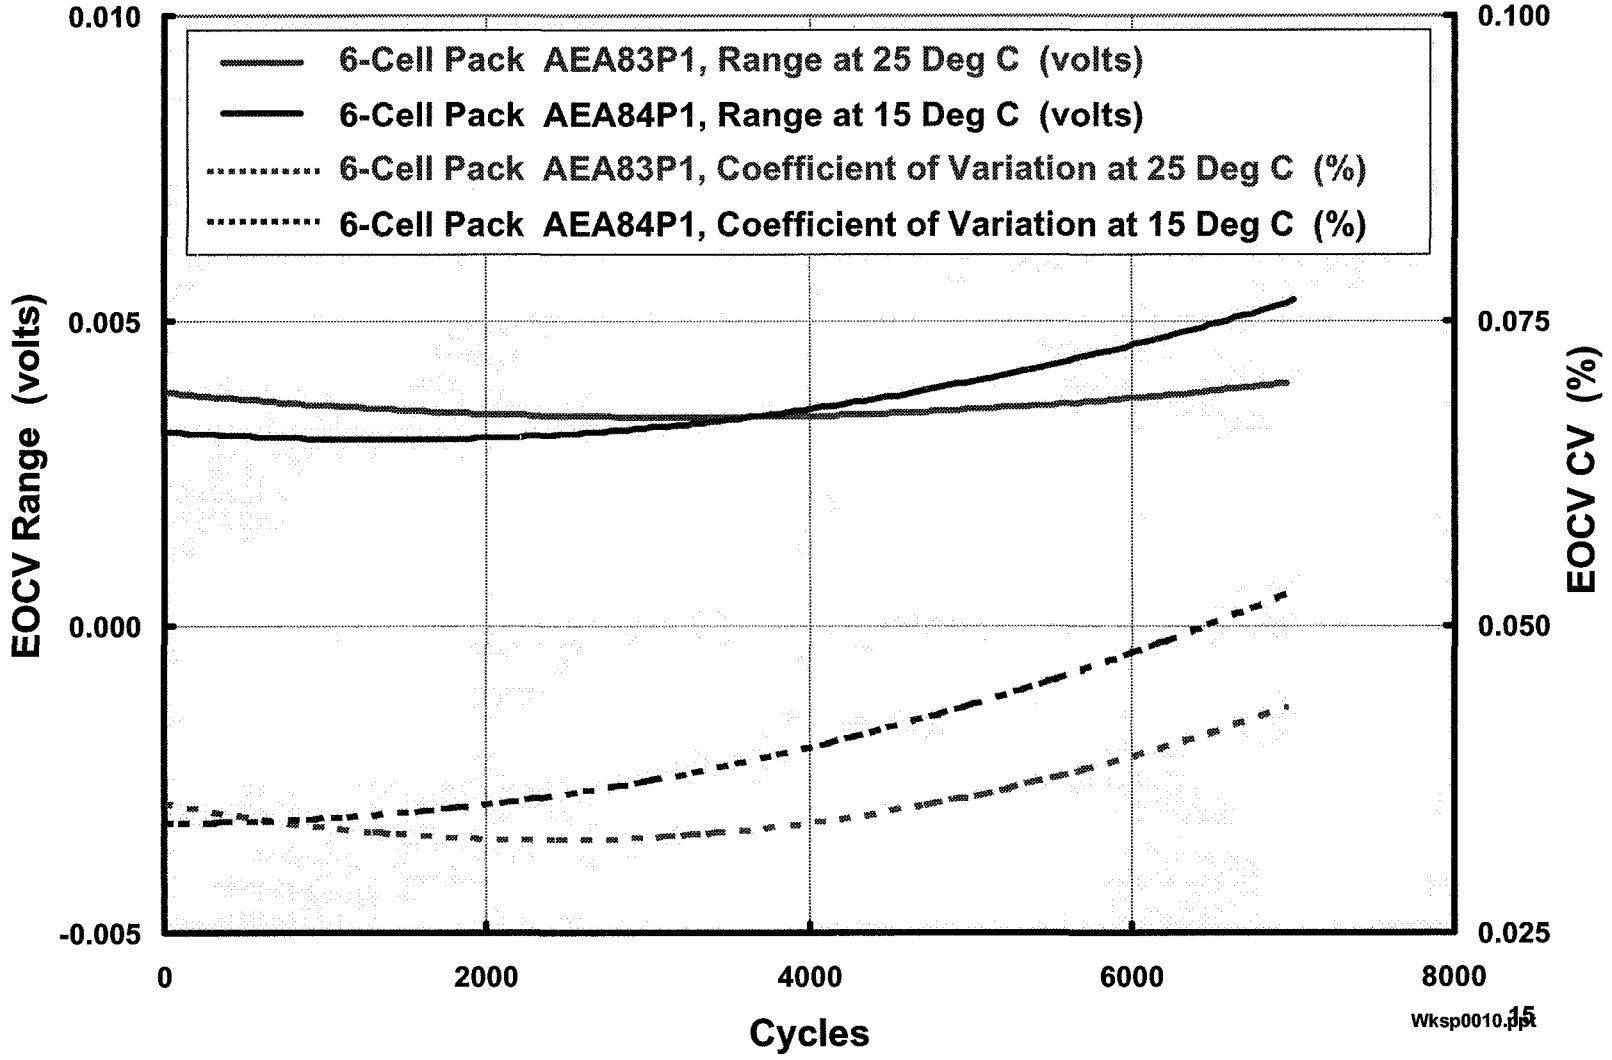

Summary

- Simulated 25% DOD LEO cycling of AEA STRV battery modules is continuing at 15ºC and 25ºC
  - The STRV "two 6-cell strings" configuration was modified to provide 6-cell strings, 2-cell strings and individual cells.
  - Charge control is at the pack level.
- 7700 cycles have been completed without incident.
- EODV voltage dispersion (in the absence of cell level balancing) is stable at 15ºC and increasing slightly at 25ºC.
- The test is continuing.

EAGLE PICHER
Technologies, LLC

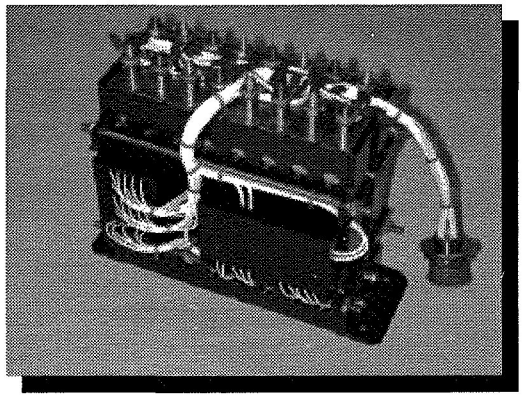

SAFETY & ABUSIVE TESTS on DIFFERENT Li-ION SYSTEMS

JAMES DeGRUSON & CHAD KELLY

16 NOVEMBER 2000

NASA AEROSPACE BATTERY WORKSHOP

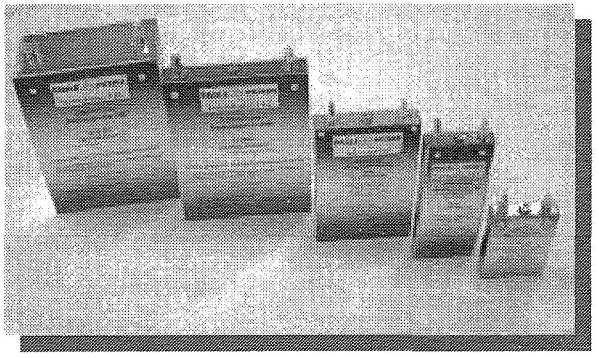

EAGLE PICHER
Technologies, LLC

SLC-16002 CELL DESCRIPTION

- ~ SIZE: 3 IN. X 7 IN. X 1 IN.
- WEIGHT: 815 GRAMS
- CAPACITY: 35 Ah
- IMPEDANCE: .0014 Ω
- ENERGY DENSITY: >380 Wh/L
- SPECIFIC ENERGY: >150 Wh/Kg

EAGLE PICHER Technologies, LLC

SLC-16002 CELL DESIGN FEATURES

- ✦STAINLESS STEEL CONTAINMENT
- ✦BURST DISC DIAPHRAM
  - .25 INCH DIAMETER
  - OPENS AT 125 PSI
- ✦POLYMERIC TERMINAL SEALS
- ✦ELECTROLYTE: $LiPF_6$ in EC/DEC
- ✦SEPARATOR: CELGARD 2300
- ✦$LiNiCoO_2$ AND $LiCoO_2$

EAGLE PICHER Technologies, LLC

SLC-16002 DISCHARGE RATE CHARACTERISTICS

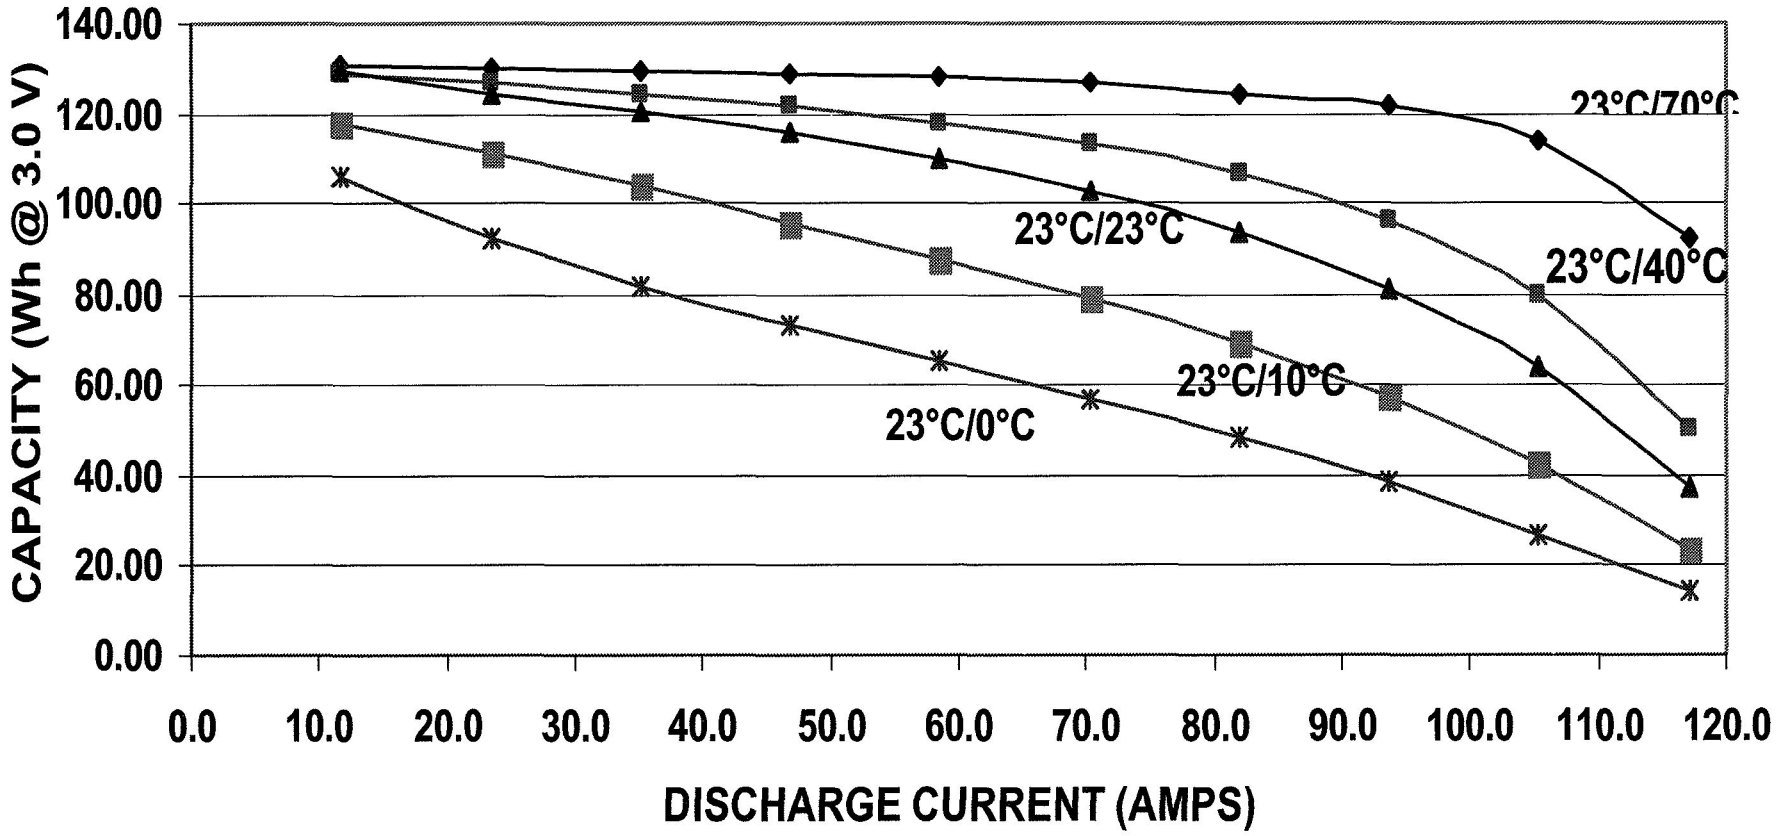

EAGLE PICHER Technologies, LLC

SAFETY & ABUSE TEST PLAN

- RANDOM VIBRATION
- SHOCK
- TEMPERATURE SHOCK
- HIGH TEMPERATURE EXPOSURE
- ALTITUDE SIMULATION
- EXTERNAL SHORT CIRCUIT
- OVER-DISCHARGE
- OVER-CHARGE
- CRUSH
- PUNCTURE

EAGLE PICHER
Technologies, LLC

VIBRATION SET-UP

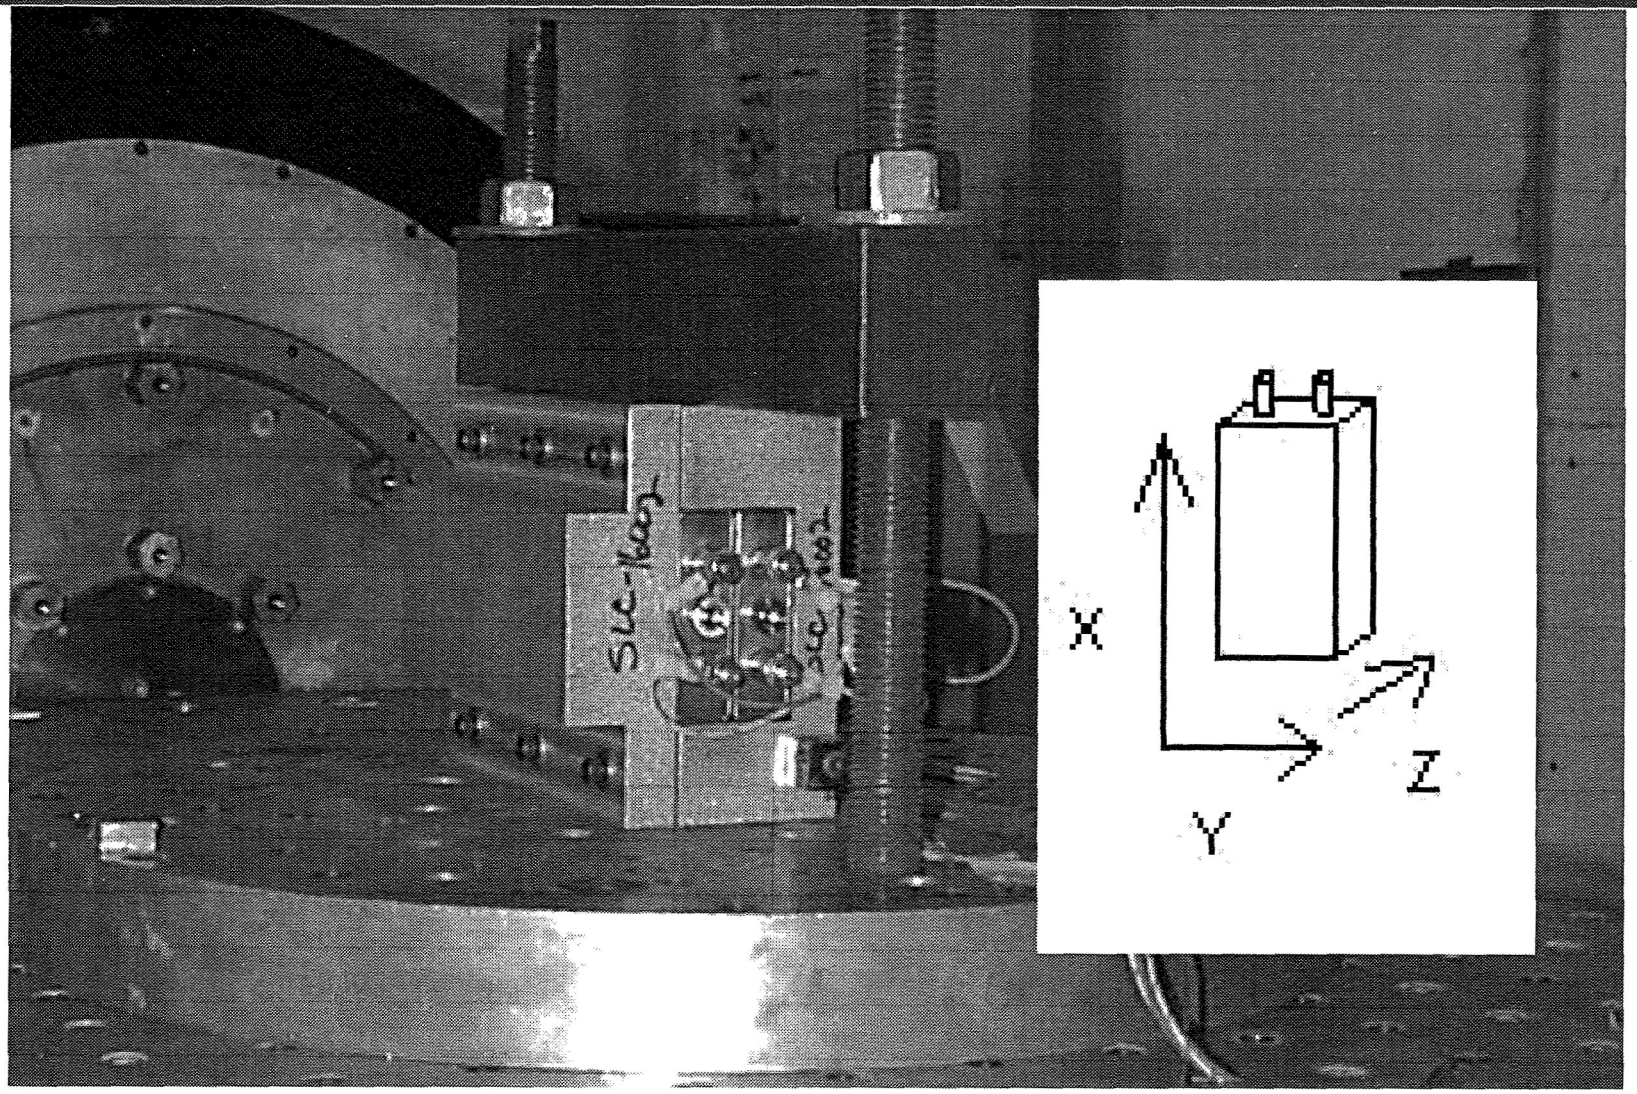

EAGLE PICHER
Technologies, LLC

VIBRATION SAFETY SHROUD

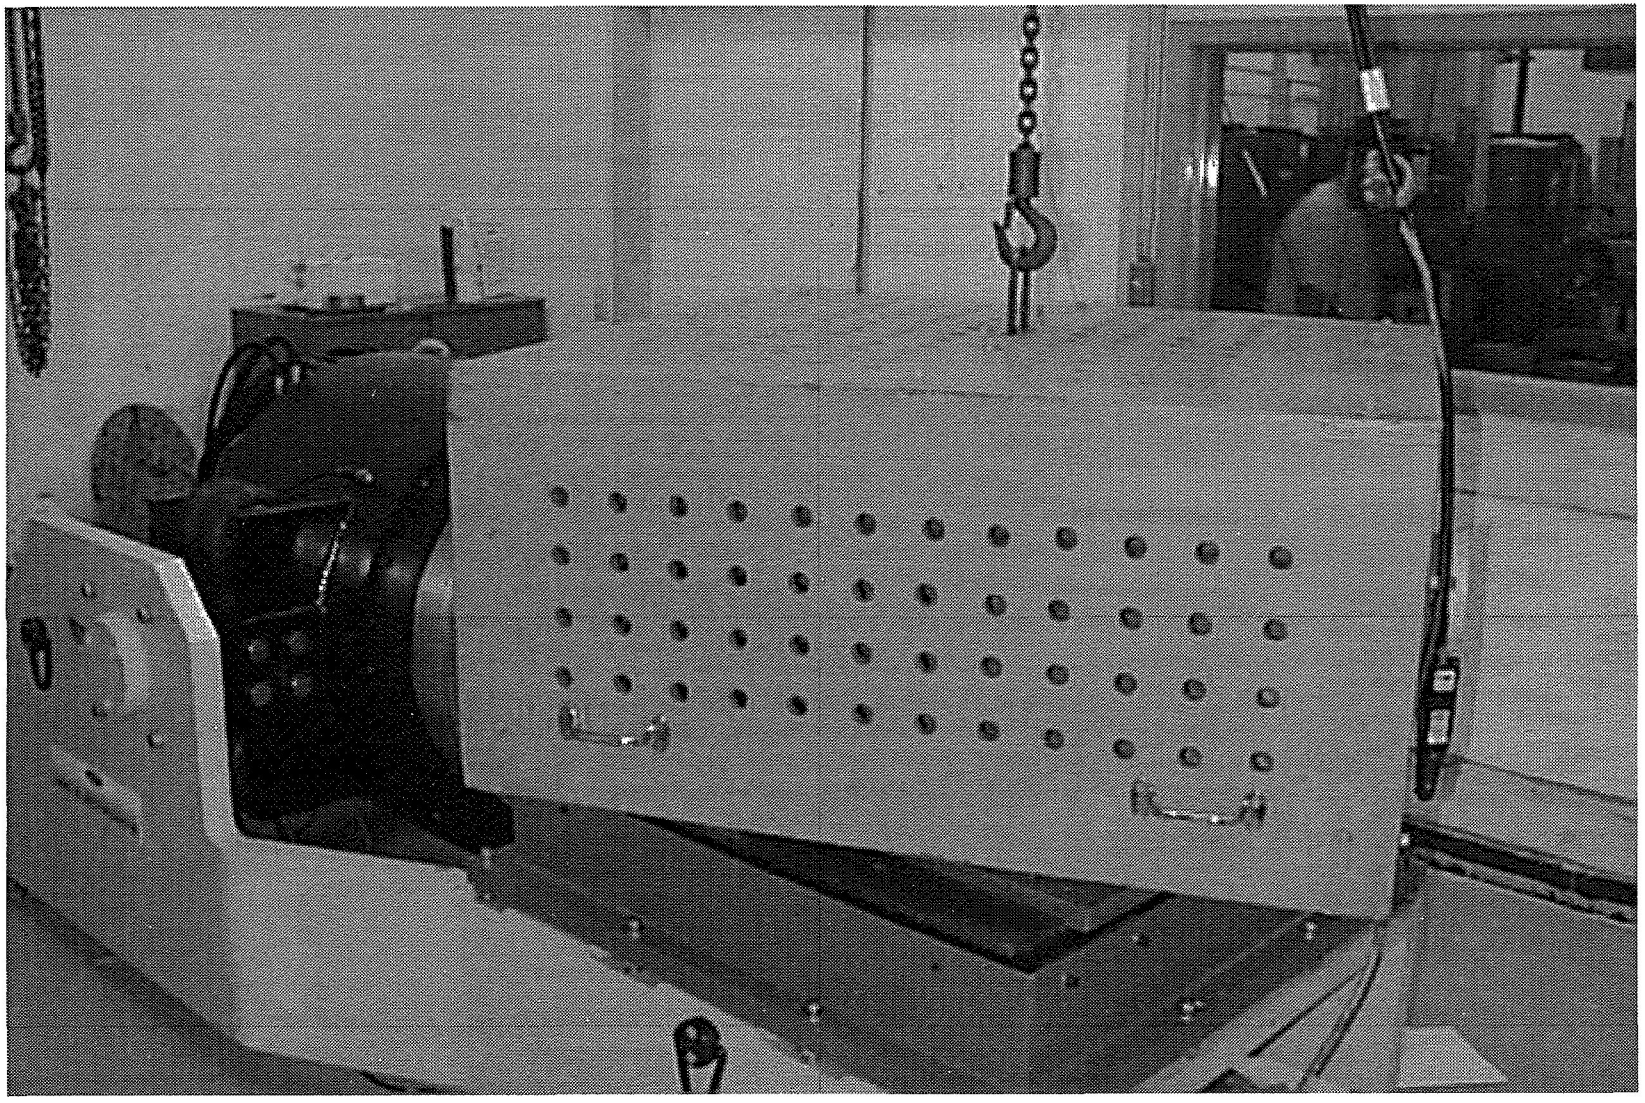

EAGLE PICHER Technologies, LLC

VIBRATION TEST DESCRIPTION

- RANDOM VIBRATION
- CELLS AT 100% SOC & 50% SOC
- OCV MONITORED DURING TEST
- DURATION: 4 HRS/AXIS FOR TOTAL OF 12 HOURS
- 31.4 Grms
- FREQUENCY: 60 to 2000 Hz
- PSD: .03 to .20 G^2/Hz

EAGLE PICHER Technologies, LLC

NO ADVERSE EFFECTS FROM RANDOM VIBRATION

Charge/Discharge Curves
for
S/N 879009
11.7 Amp Chg. & 35 Amp Dchg.

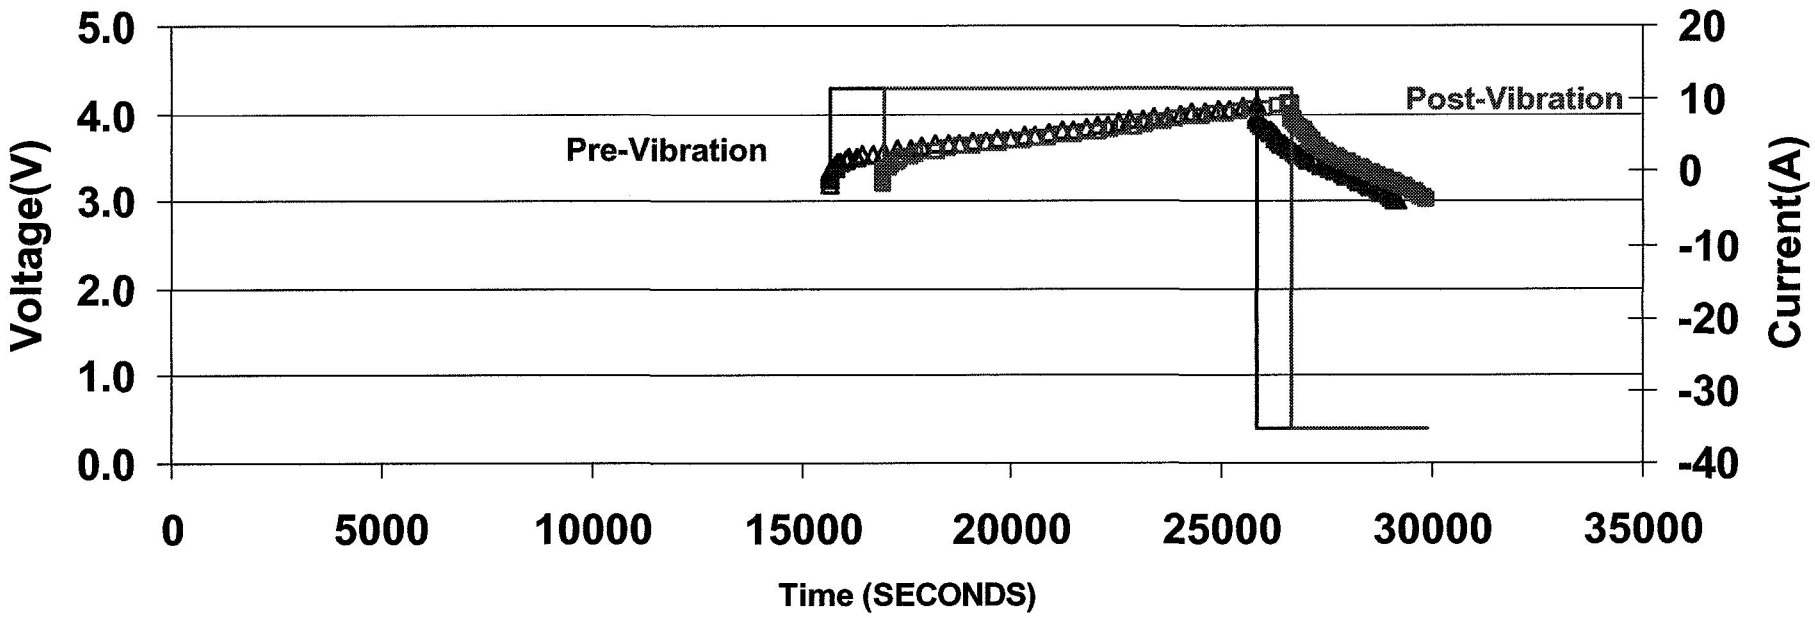

EAGLE PICHER
Technologies, LLC

SHOCK TEST SET-UP

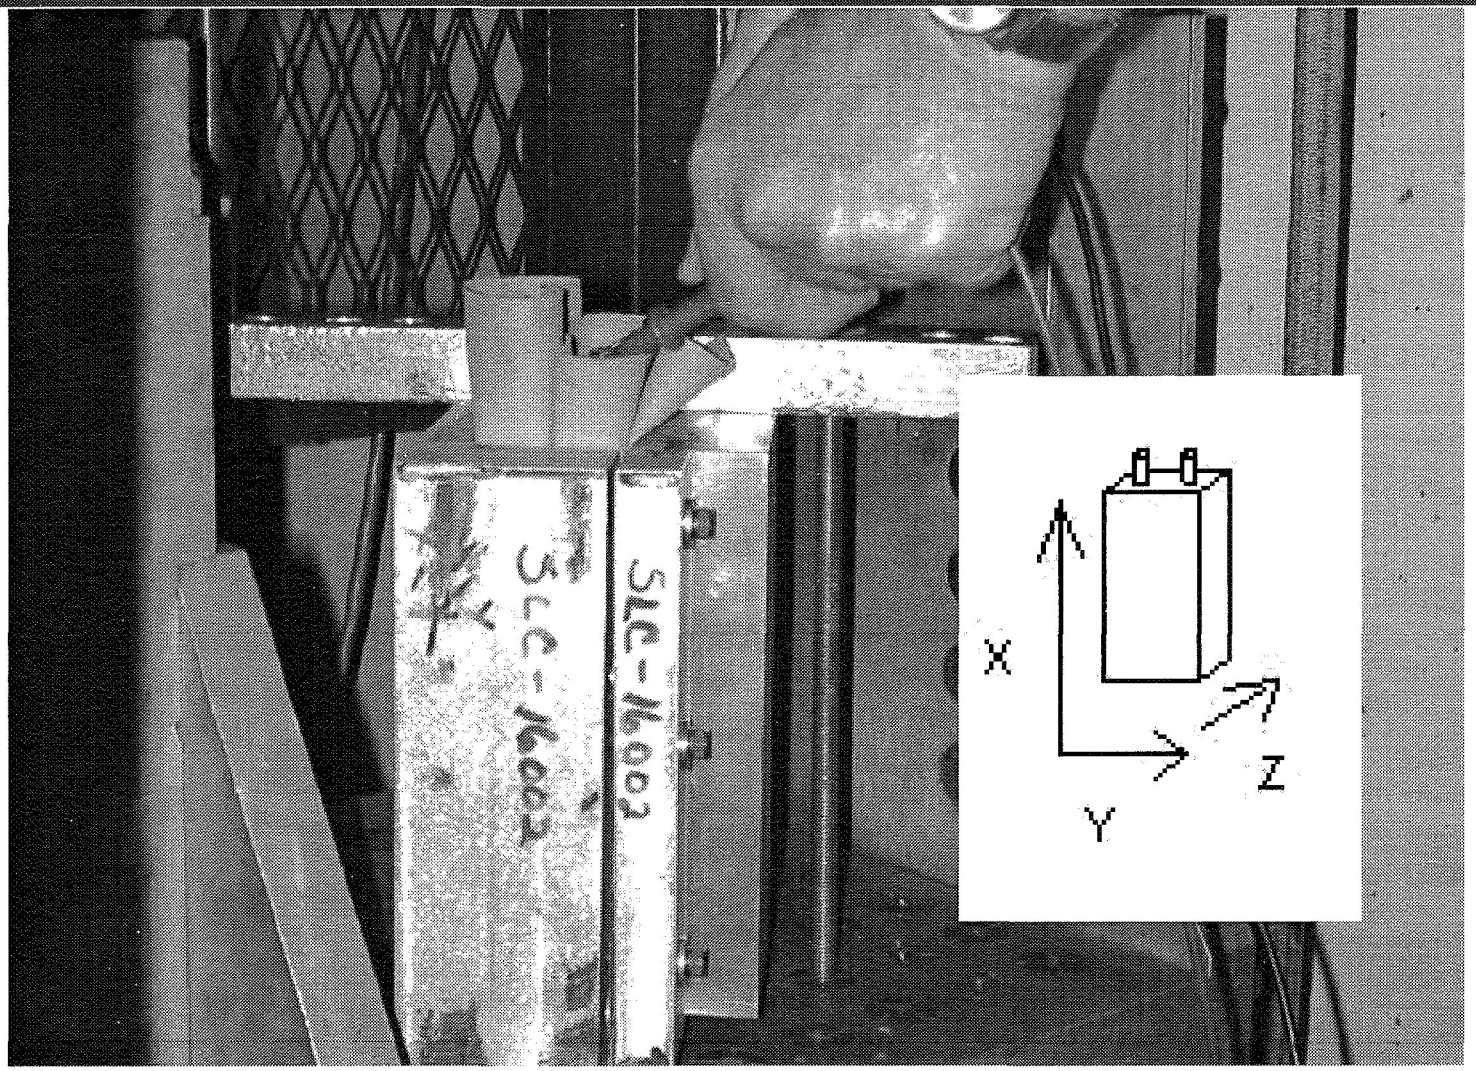

EAGLE PICHER Technologies, LLC

SHOCK TEST DESCRIPTION

- AFTER VIBRATION, SAME TWO CELLS WERE SHOCK TESTED
- CELLS WERE AT 100% SOC & 50% SOC
- ONE SHOCK/AXIS for a TOTAL OF 3 SHOCKS
- MINIMUM ACCELERATION: 75 Gs DURING 1st THREE MS
- PEAK ACCELERATION: 165 Gs
- TEST REFLECTS TRANSPORTATION REQUIREMENTS
- CELLS WERE UNPACKAGED
- AIRCRAFT REQUIREMENTS NOT AS SEVERE

EAGLE PICHER Technologies, LLC

SHOCK TEST RESULTS

- X-RAY PRIOR & AFTER SHOCK
- SHOCK HAD NO EFFECT ON CELLS
- CELL VOLTAGE UNCHANGED
- ELECTRICAL PERFORMANCE UNCHANGED

EAGLE PICHER Technologies, LLC

HIGH-TEMPERATURE EXPOSURE TEST

✦ TEST DESCRIPTION

- $LiCoO_2$ CHEMISTRY
- TEST PERFORMED ON CELL IN 100% SOC
- HEAT BLANKET WRAPPED AROUND CELL
- CELL HEATED TO ≅550°C

✦ TEST RESULTS

- CELL VENT OPENED AT 360°C
- SMOKE BUT NO FLAME OR FIRE
- NO RUPTURE OF CELL CONTAINER

EAGLE PICHER Technologies, LLC

HIGH TEMPERATURE EXPOSURE TEST

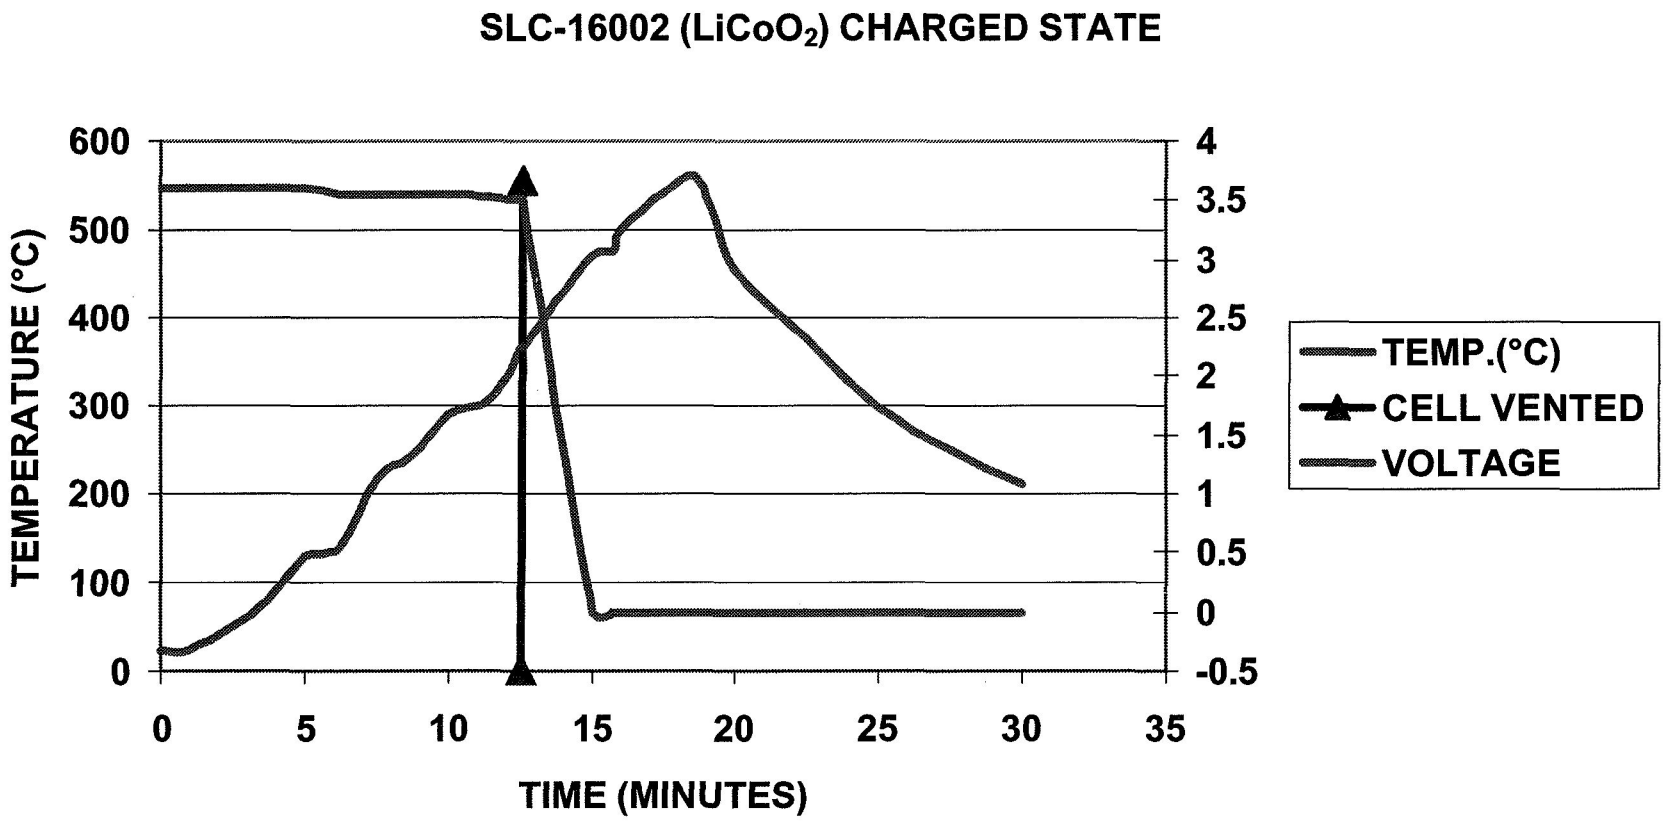

EAGLE PICHER Technologies, LLC

ALTITUDE SIMULATION TESTING

✦ TEST DESCRIPTION

- THREE CELL CONTAINERS COMPLETE WITH VENTS/TERMINALS
- TABLE 1 of MIL-E-5400 for CLASS 2 EQUIPMENT
- SIMULATION OF 70,000 FEET, AMBIENT TEMPERATURE

✦ TEST RESULTS

- NO EFFECT ON CONTAINER OR VENT
- ALL REQUIREMENTS MET

EAGLE PICHER
Technologies, LLC

SHORT-CIRCUIT TEST

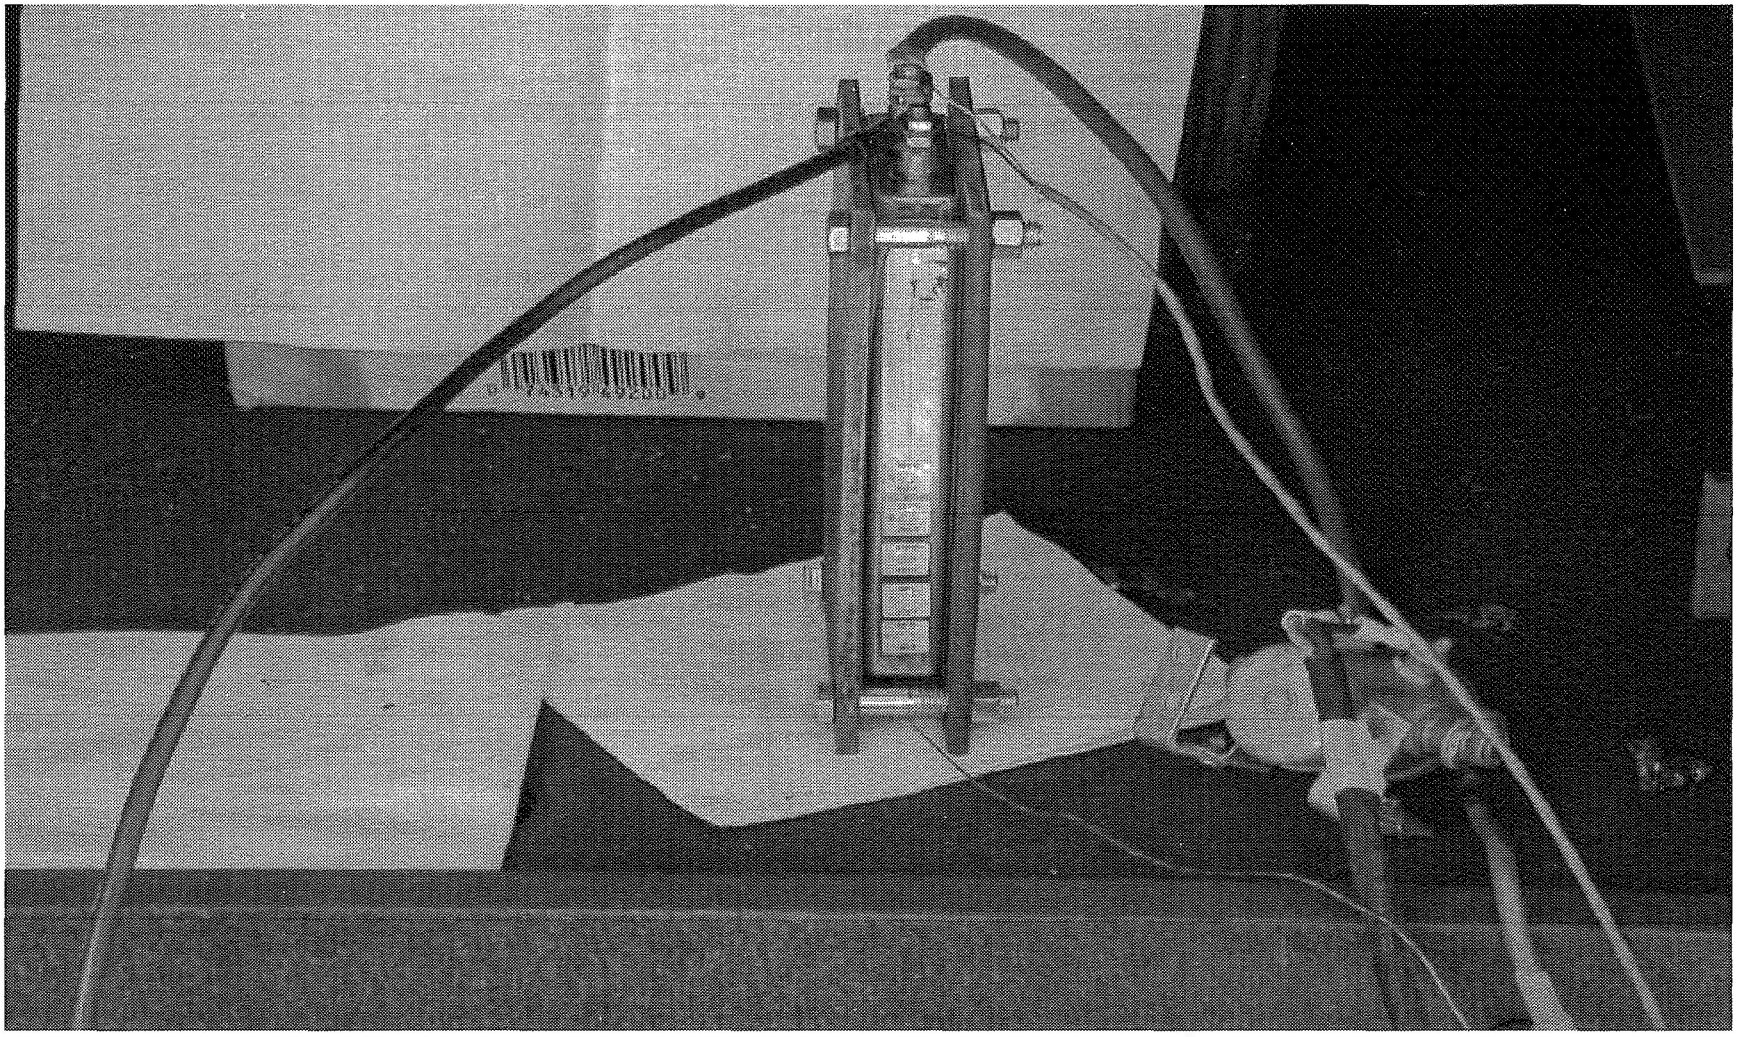

EAGLE PICHER Technologies, LLC

SHORT-CIRCUIT TEST DESCRIPTION

- $LiNiCoO_2$ CELL IN 100% SOC
- .09 OHM RESISTOR APPLIED ACROSS TERMINALS
- VOLTAGE, CURRENT, TIME & TEMPERATURE MONITORED
- TEST TIME: APPROXIMATELY 20 HOURS

EAGLE PICHER Technologies, LLC

SHORT-CIRCUIT TEST RESULTS

- INITIALLY CELL PEAKED AT 3.87 VOLTS @ 44.1 AMPS
- INITIAL TEMPERATURE 26°C
- PEAK TEMPERATURE: 45°C AT 1 Hr & 3 MINUTES
- AFTER 2 HOURS: VOLTAGE <.02 VOLTS & TEMP. 33°C
- NO VENTING OR RUPTURE

EAGLE PICHER Technologies, LLC

SHORT-CIRCUIT TEST

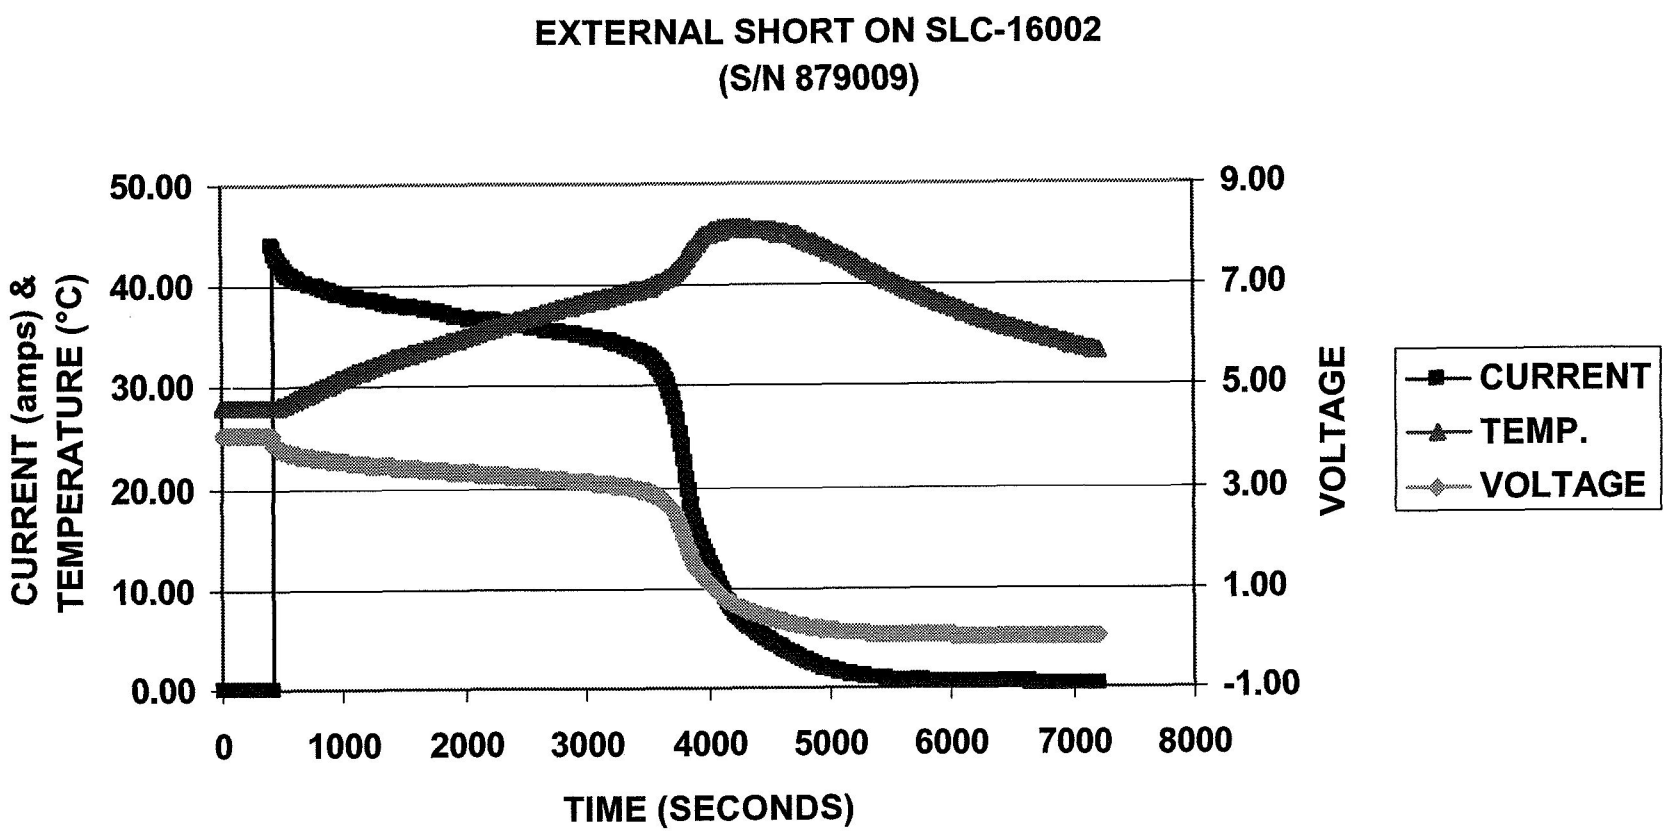

EAGLE PICHER Technologies, LLC

OVER-DISCHARGE TEST

- **TEST DESCRIPTION:**
  - SLC-16002 CELL – $LiNiCoO_2$ CHEMISTRY
  - CELL IN 50% SOC
  - DISCHARGE CELL AT "C/2" RATE TO NEGATIVE ONE VOLT
  - MONITOR VOLTAGE, CURRENT, TIME, & TEMPERATURE

- **TEST RESULTS:**
  - NO VENT
  - ALL REQUIREMENTS MET

EAGLE PICHER Technologies, LLC

OVER-DISCHARGE TEST

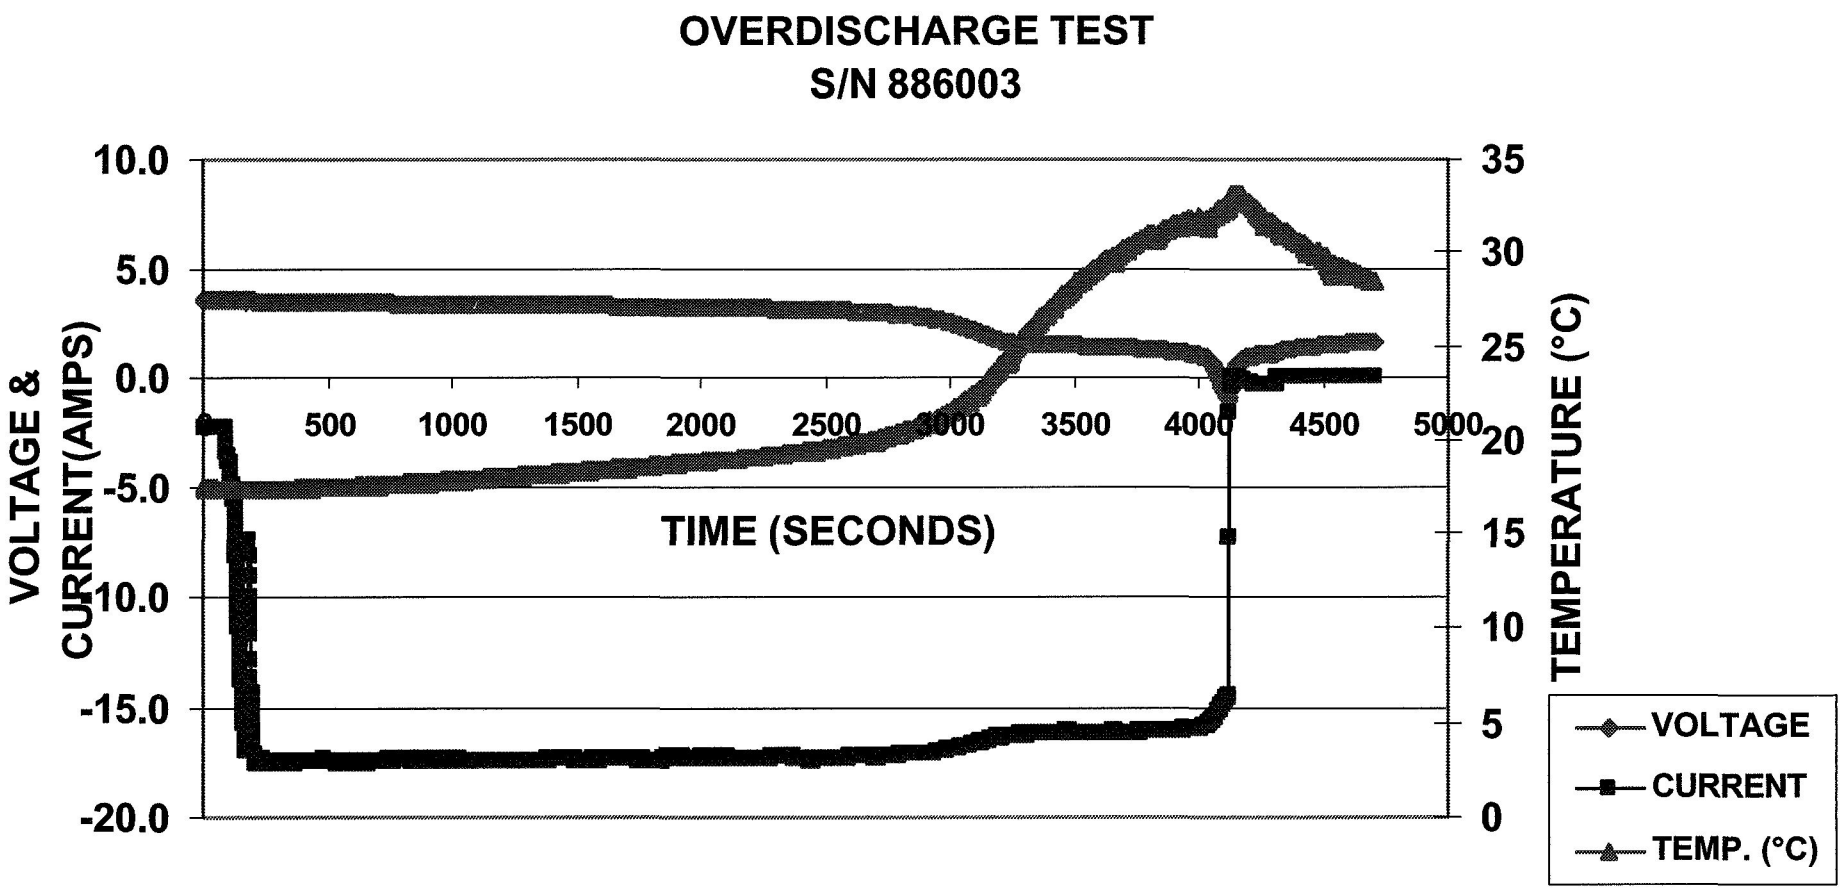

EAGLE PICHER Technologies, LLC

POST-TEST OVER-DISCHARGE RESULTS

- VENT DIAPHRAGM INTACT
- NO COLOR CHANGE IN THERMAL SENSITIVE DOTS
- NO PHYSICAL CHANGE IN CELL

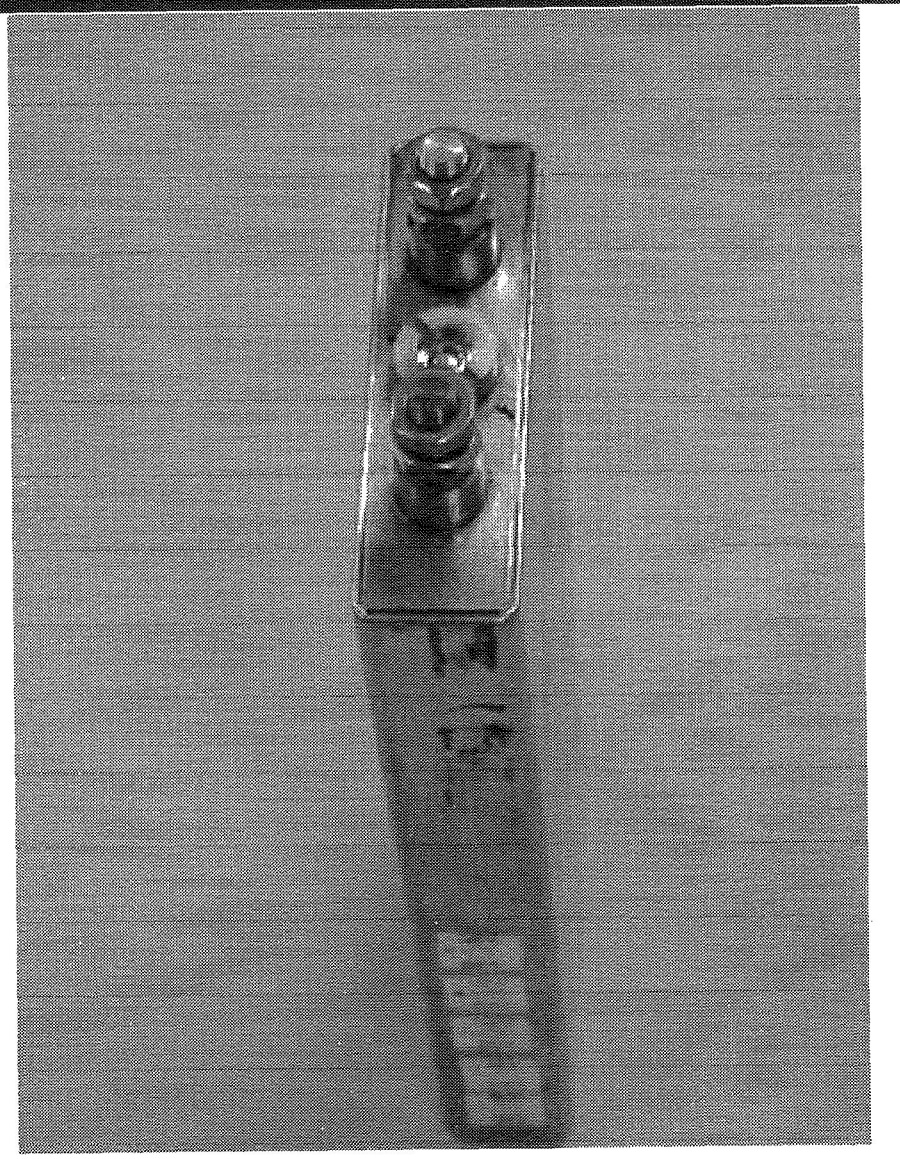

EAGLE PICHER Technologies, LLC

OVER-CHARGE TEST

✦ TEST DESCRIPTION

- SLC-16002 ($LiNiCoO_2$)
- CELL IN 100% SOC
- AMBIENT TEMPERATURE
- CHARGE RATE: "C" RATE to 200% of RATED CAPACITY (70 Ah)

✦ TEST RESULTS

- CELL DID VENT AT VENT DIAPHRAGM
- NO FLAME OR RUPTURE
- ALL REQUIREMENTS MET

EAGLE PICHER Technologies, LLC

OVER-CHARGE TEST

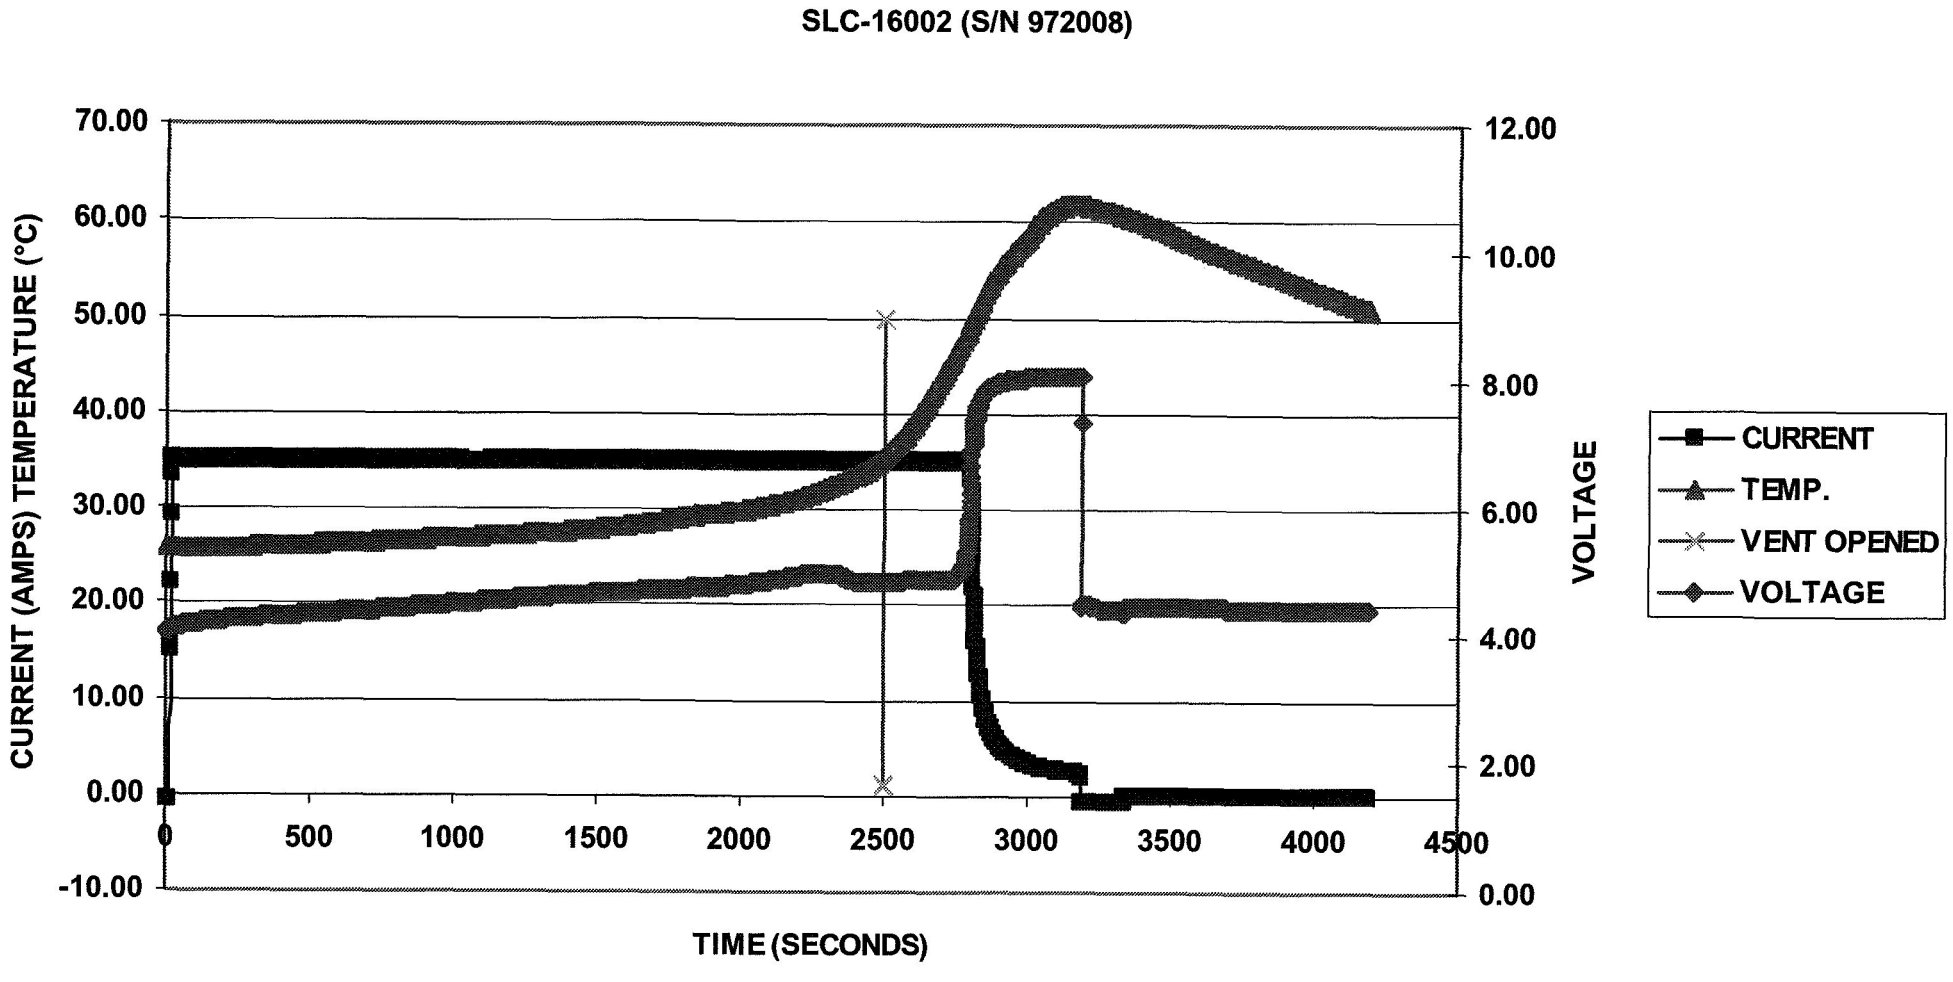

EAGLE PICHER Technologies, LLC

POST-TEST OVER-CHARGE RESULTS

- VENT DIAPHRAGM OPEN
- TERMINAL SEALS UNAFFECTED
- NO DISTORTION OF CELL

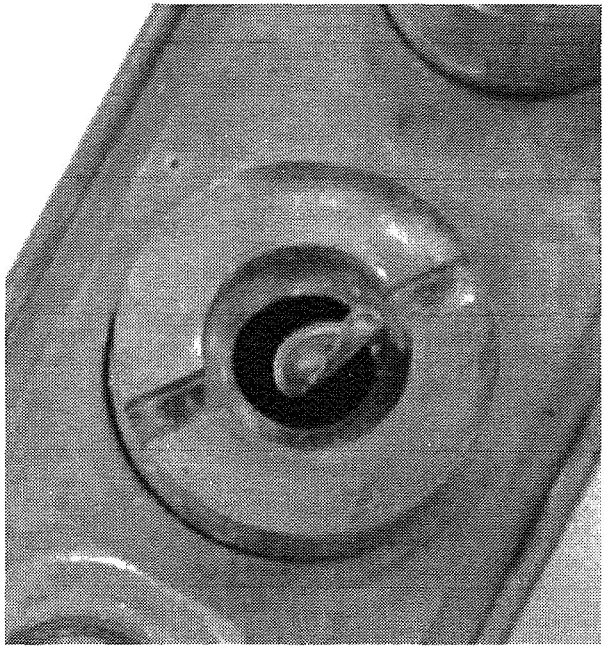

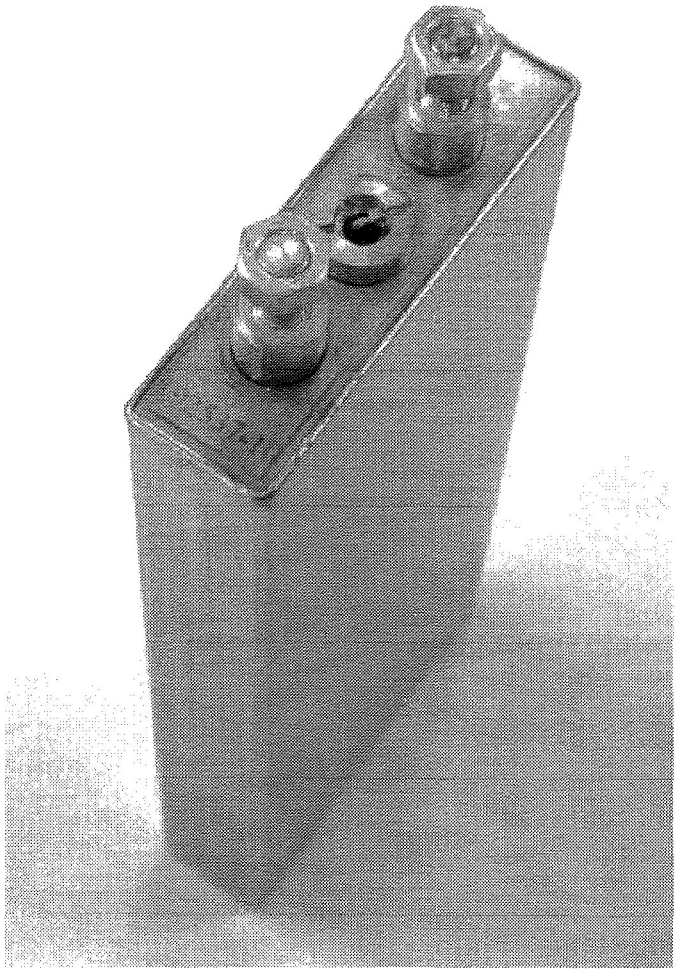

EAGLE PICHER Technologies, LLC

CONCLUSIONS

- NO EXPLOSIONS OR CELL CASE RUPTURES
- PRESSURE VENT WORKS AS INTENDED
  - SHORT CIRCUIT & OVER-DISCHARGE DID NOT VENT
- POLYMERIC TERMINAL SEALS PRESENT NO PROBLEMS
- PRISMATIC CELL DESIGN RESULTS IN RUGGED CONSTRUCTION WHICH WITHSTANDS EXTREME ENVIRONMENTS

EAGLE PICHER Technologies, LLC

FUTURE SAFETY WORK

- ADDITIONAL TESTING BEING CONDUCTED ON $LiNiCoO_2$
- LARGE QUANTITY OF CELLS FOR EACH TEST
- DOT TESTING BEING ADDRESSED
- CRUSH, PUNCTURE, & TEMP. SHOCK BEING CONDUCTED

Lithium Ion Battery Design and Safety

The NASA Aerospace Battery Workshop, Marshall Space Flight Center, and the NASA Aerospace Flight Battery Systems Program at Huntsville AL.

George Au and Laura Locke

Presented by George Au

US Army CECOM RDEC

AMSEL-RD-C2-AP-BA

Fort Monmouth, NJ 07703

732-427-4886

George.Au@mail1.monmouth.army.mil

14-16 Nov. 2000

CECOM Bottom Line: THE SOLDIER

Life Cycle Test for commercial 1.4 AH Polymer Cell

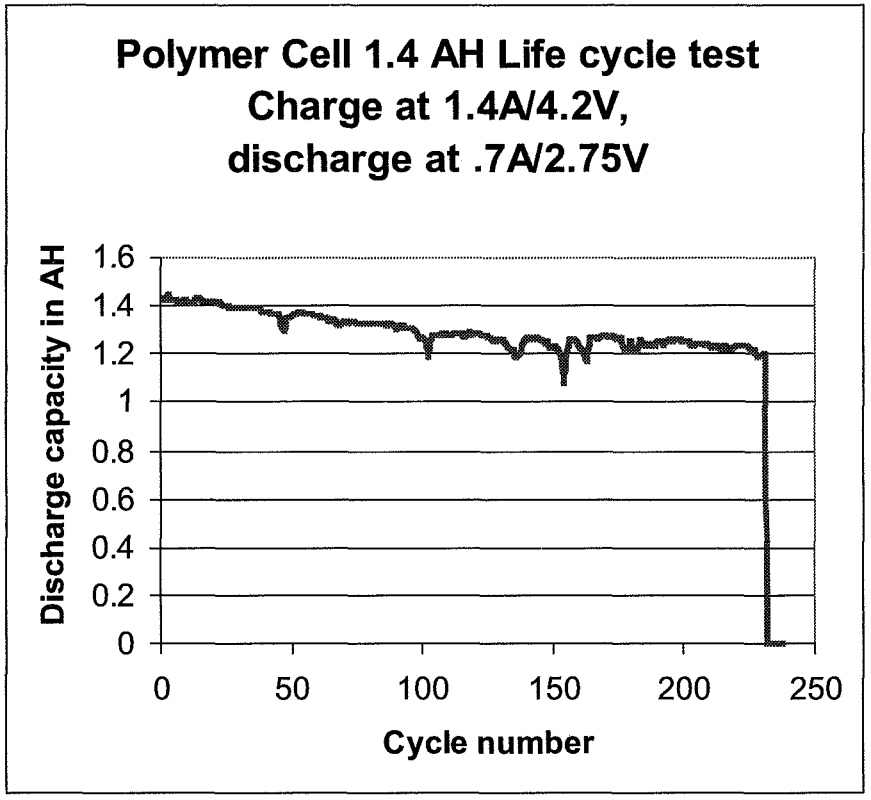

CECOM Bottom Line: THE SOLDIER

Burned 1.4 AH Polymer Lithium ion Cell During Cycling

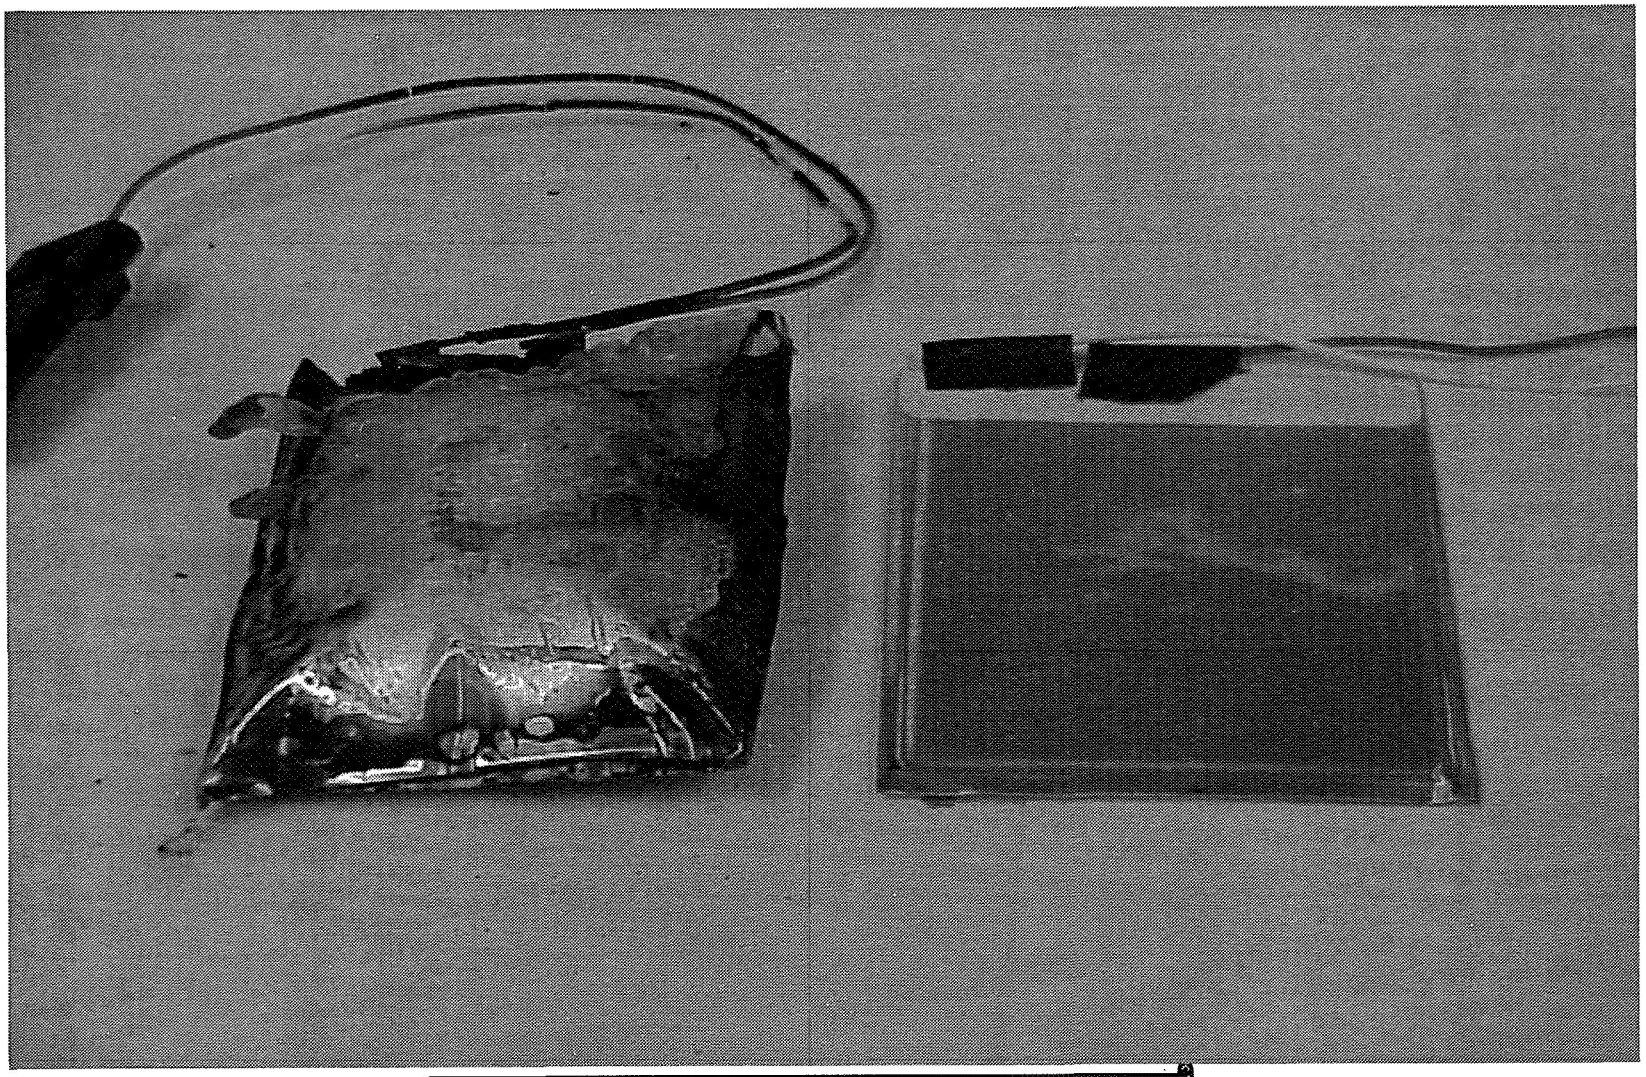

CECOM Bottom Line: THE SOLDIER

Shorted Polymer Lithium ion Cell During Cycling From 231 to 238

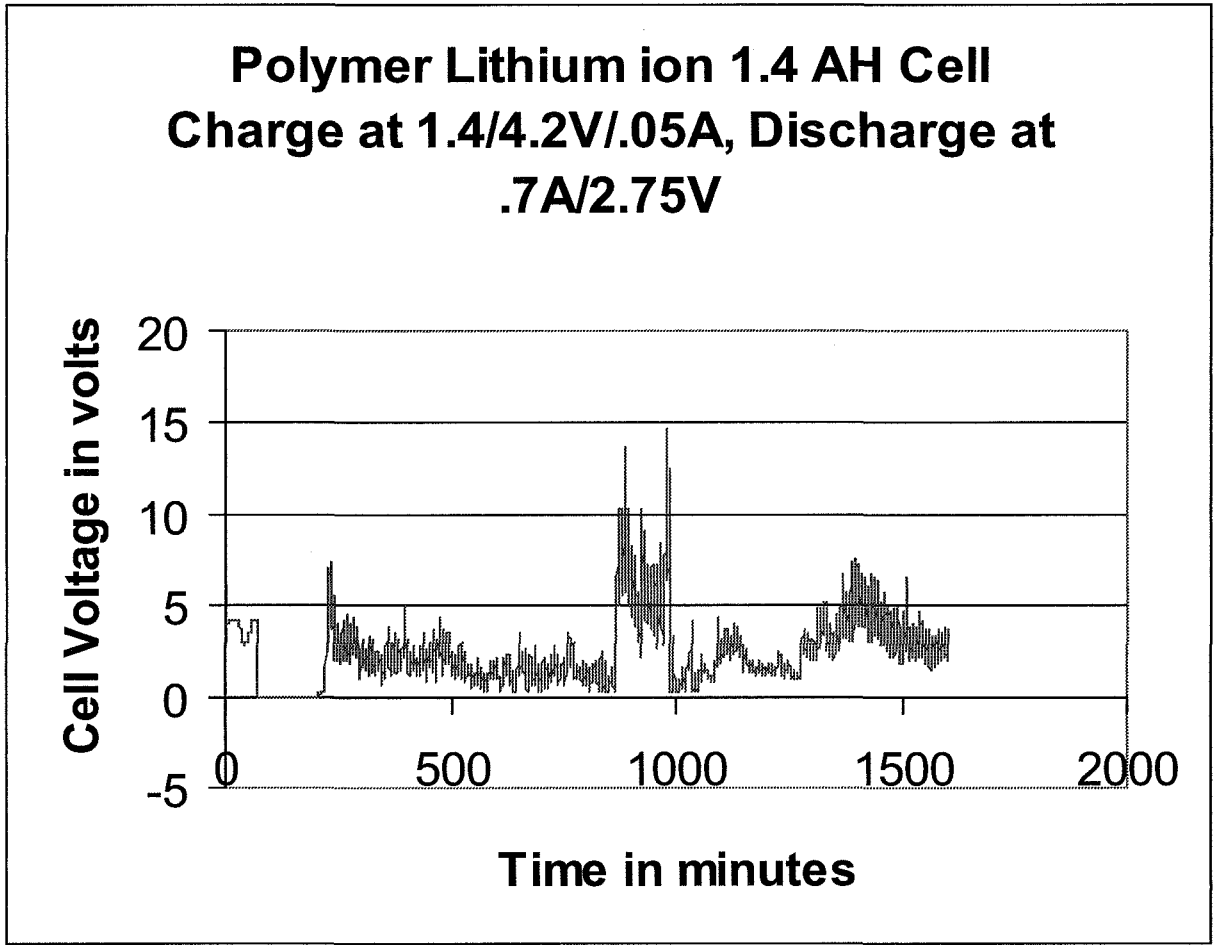

CECOM Bottom Line: THE SOLDIER

Shorted 1.4 AH Polymer Lithium ion Cell During Cycling

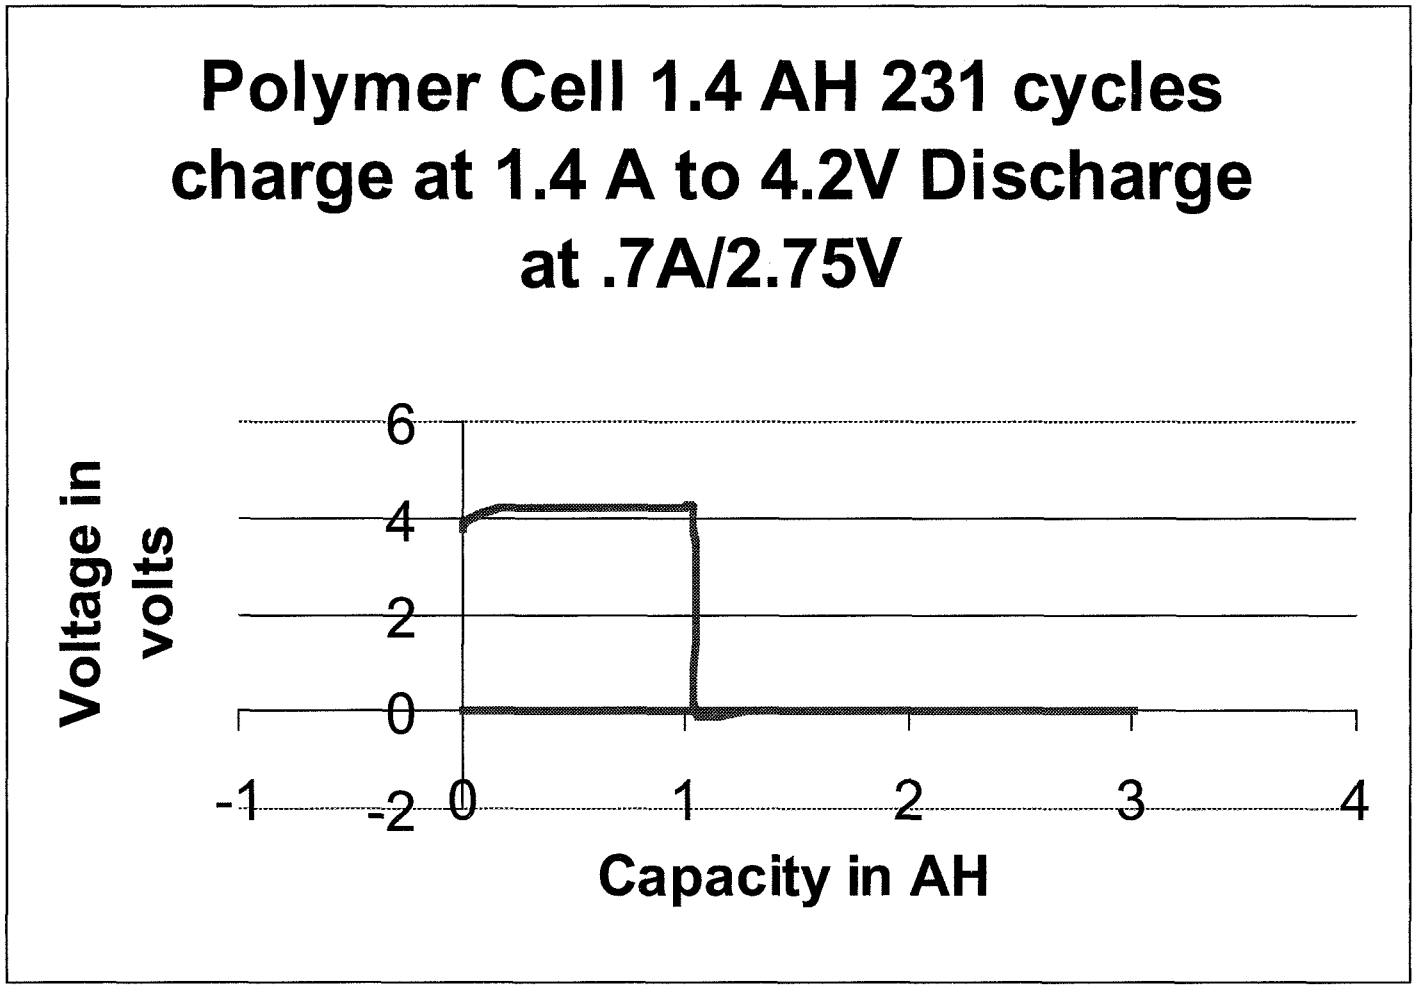

CECOM Bottom Line: THE SOLDIER

Shorted Polymer Lithium ion Cell During Cycling

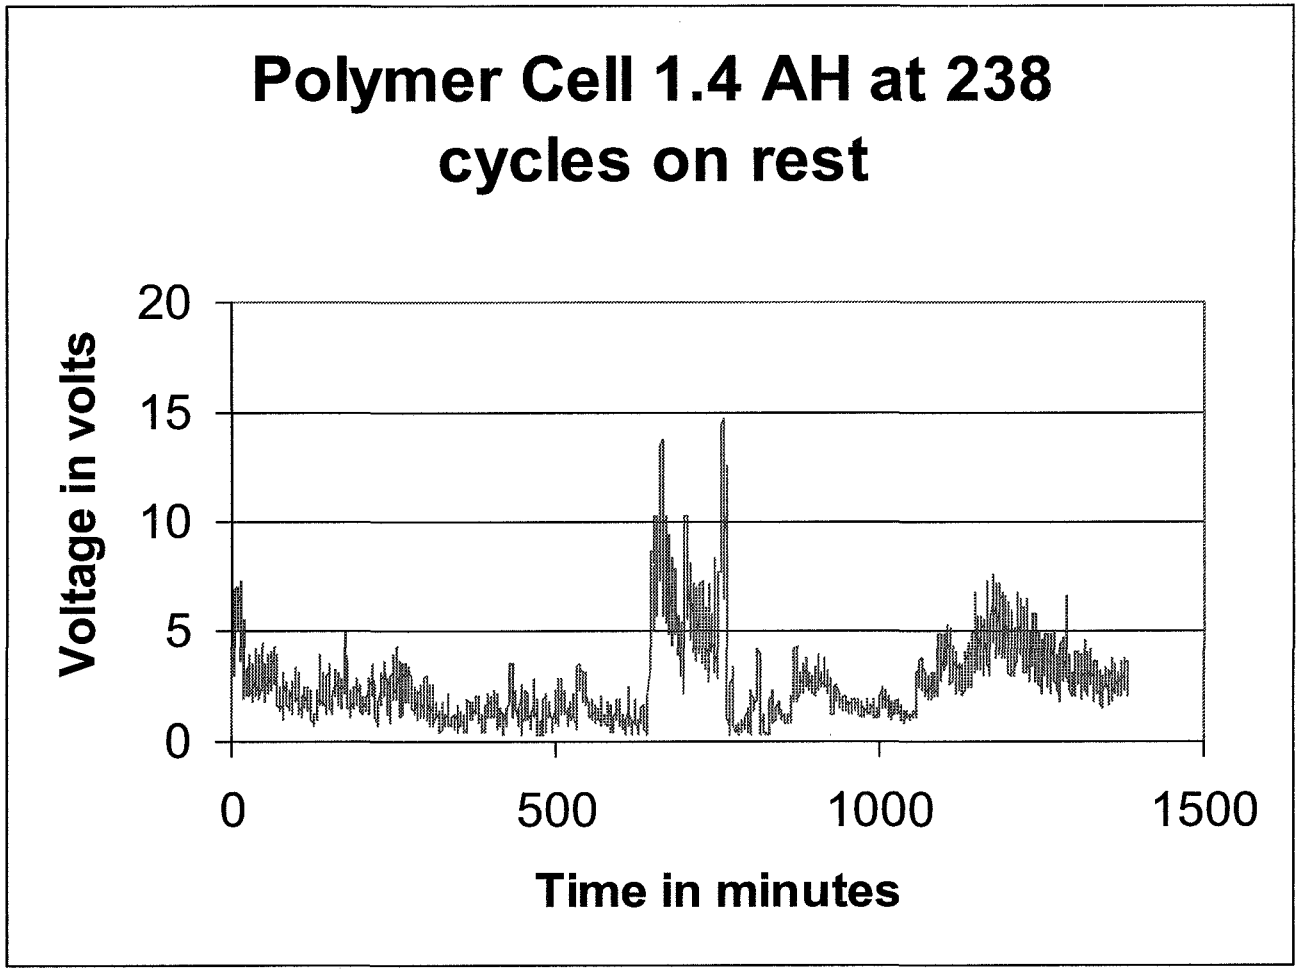

CECOM Bottom Line: THE SOLDIER

Polymer Lithium ion Cell Cycle Data

					AH	WH	A	V	
12318	231	4	62d 16:46	0d 01:00	0	0	0	3.57116	R
12319	231	5	62d 16:46	0d 00:00	6.23E-05	0.000233	1.399863	3.78265	C
12320	231	5	62d 16:47	0d 00:00	0.007572	0.029184	1.400015	3.882628	C
12321	231	5	62d 16:48	0d 00:01	0.034713	0.136102	1.400015	3.983154	C
12322	231	5	62d 16:50	0d 00:03	0.088652	0.353757	1.399939	4.083131	C
12323	231	5	62d 16:54	0d 00:07	0.170985	0.694314	1.399939	4.183108	C
12324	231	5	62d 17:04	0d 00:17	0.373095	1.542775	1.067292	4.199588	C
12325	231	5	62d 17:14	0d 00:27	0.532285	2.21114	0.872969	4.200137	C
12326	231	5	62d 17:24	0d 00:37	0.664404	2.765814	0.701534	4.200137	C
12327	231	5	62d 17:34	0d 00:47	0.771445	3.215159	0.588388	4.200137	C
12328	231	5	62d 17:44	0d 00:57	0.858548	3.580753	0.468299	4.199588	C
12329	231	5	62d 17:54	0d 01:07	0.929777	3.879686	0.379568	4.200137	C
12330	231	5	62d 18:04	0d 01:17	0.986491	4.117654	0.310979	4.200137	C
12331	231	5	62d 18:14	0d 01:27	1.032339	4.309986	0.243534	4.199588	C
12332	231	5	62d 18:16	0d 01:29	1.042173	4.351228	0.268788	1.900114	C
12333	231	5	62d 18:16	0d 01:29	1.042175	4.351228	0.391012	0	C
12334	231	5	62d 18:26	0d 01:39	1.27551	4.351228	1.400015	0	C
12335	231	5	62d 18:36	0d 01:49	1.508846	4.351228	1.400015	0	C
12336	231	5	62d 18:46	0d 01:59	1.742182	4.351228	1.399939	0	C
12337	231	5	62d 18:56	0d 02:09	1.975518	4.351228	1.400015	0	C
12338	231	5	62d 19:06	0d 02:19	2.208854	4.351228	1.399939	0	C
12339	231	5	62d 19:16	0d 02:29	2.44219	4.351228	1.400015	0	C
12340	231	5	62d 19:26	0d 02:39	2.675526	4.351228	1.400015	0	C

Polymer Lithium ion Cell Cycle Data

					AH	WH	A	V
12245	230	3	62d 08:36	0d 01:14	0.873924	3.171562	0.700008	3.356374
12261	230	4	62d 09:35	0d 00:31	0	0	0	3.535454
12262	230	4	62d 09:55	0d 00:51	0	0	0	3.560174
12269	230	5	62d 10:21	0d 00:17	0.375898	1.554214	1.038605	4.200137
12270	230	5	62d 10:31	0d 00:27	0.53513	2.222758	0.87686	4.200137
12271	230	5	62d 10:41	0d 00:37	0.666299	2.773442	0.701839	4.200137
12272	230	5	62d 10:51	0d 00:47	0.773657	3.224118	0.587701	4.200137
12273	230	5	62d 11:01	0d 00:57	0.860612	3.589092	0.467994	4.199588
12274	230	5	62d 11:11	0d 01:07	0.931791	3.887816	0.385214	4.200137
12275	230	5	62d 11:21	0d 01:17	0.988114	4.124145	0.305257	4.200137
12276	230	5	62d 11:31	0d 01:27	1.034228	4.3176	0.244984	4.200137
12277	230	5	62d 11:41	0d 01:37	1.070484	4.469645	0.19791	4.200137
12278	230	5	62d 11:51	0d 01:47	1.100572	4.595777	0.159075	4.199588
12279	230	5	62d 12:01	0d 01:57	1.124518	4.696127	0.13344	4.199588
12280	230	5	62d 12:11	0d 02:07	1.144839	4.781248	0.105058	4.199588
12281	230	5	62d 12:21	0d 02:17	1.16137	4.85045	0.093462	4.199588
12282	230	5	62d 12:31	0d 02:27	1.175664	4.910261	0.072938	4.199588
12283	230	5	62d 12:41	0d 02:37	1.187588	4.960122	0.06836	4.200137
12284	230	5	62d 12:51	0d 02:47	1.197909	5.003245	0.052949	4.200137
12285	230	5	62d 13:01	0d 02:57	1.206755	5.040179	0.051499	4.200137
12288	230	6	62d 13:23	0d 00:20	0	0	0	4.171572
12289	230	6	62d 13:43	0d 00:40	0	0	0	4.16553
12295	231	3	62d 14:28	0d 00:24	0.289628	1.10583	0.700008	3.693111
12296	231	3	62d 14:38	0d 00:34	0.406296	1.532536	0.699931	3.62884
12297	231	3	62d 14:48	0d 00:44	0.522964	1.952393	0.699931	3.573358
12298	231	3	62d 14:58	0d 00:54	0.639632	2.366408	0.700008	3.527214
12299	231	3	62d 15:08	0d 01:04	0.7563	2.774047	0.700008	3.456901
12300	231	3	62d 15:18	0d 01:14	0.872968	3.172226	0.700008	3.371206
12316	231	4	62d 16:17	0d 00:30	0	0	0	3.539849
12317	231	4	62d 16:37	0d 00:50	0	0	0	3.564569
12324	231	5	62d 17:04	0d 00:17	0.373095	1.542775	1.067292	4.199588

12374	233	4	63d 01:49	0d 01:00	0	0	0	0	R
12375	233	5	63d 01:49	0d 00:00	6.23E-05	0	1.400015	0	C
12376	233	5	63d 01:59	0d 00:10	0.233398	0	1.399939	0	C
12377	233	5	63d 02:09	0d 00:20	0.466734	0	1.400015	0	C
12378	233	5	63d 02:19	0d 00:30	0.70007	0	1.400015	0	C
12379	233	5	63d 02:29	0d 00:40	0.933406	0	1.399939	0	C
12380	233	5	63d 02:39	0d 00:50	1.166742	0	1.400015	0	C
12381	233	5	63d 02:49	0d 01:00	1.400078	0	1.399939	0	C
12382	233	5	63d 02:59	0d 01:10	1.633413	0	1.400015	0	C
12383	233	5	63d 03:09	0d 01:20	1.866749	0	1.400015	0	C
12384	233	5	63d 03:19	0d 01:30	2.100085	0	1.399939	0	C
12385	233	5	63d 03:29	0d 01:40	2.333421	0	1.399939	0	C
12386	233	5	63d 03:39	0d 01:50	2.566757	0	1.400015	0	C
12387	233	5	63d 03:49	0d 02:00	2.800093	0	1.399939	0	C
12388	233	5	63d 03:57	0d 02:08	3.000003	0	1.399939	0	C
12389	233	6	63d 03:57	0d 00:00	0	0	0	0	R
12390	233	6	63d 04:17	0d 00:20	0	0	0	0	R
12391	233	6	63d 04:37	0d 00:40	0	0	0	0	R
12392	233	6	63d 04:57	0d 01:00	0	0	0	0	R
12393	234	3	63d 04:57	0d 00:00	0	0	0	0	D
12394	234	4	63d 04:57	0d 00:00	0	0	0	0	R
12395	234	4	63d 05:17	0d 00:20	0	0	0	0	R
12396	234	4	63d 05:37	0d 00:40	0	0	0	0	R
12397	234	4	63d 05:57	0d 01:00	0	0	0	0	R
12398	234	5	63d 05:57	0d 00:00	6.23E-05	0	1.399939	0	C
12399	234	5	63d 06:07	0d 00:10	0.233398	0	1.400015	0	C
12400	234	5	63d 06:17	0d 00:20	0.466734	0	1.399939	0	C
12401	234	5	63d 06:27	0d 00:30	0.70007	0	1.399939	0	C
12402	234	5	63d 06:37	0d 00:40	0.933406	0	1.399939	0	C
12403	234	5	63d 06:47	0d 00:50	1.166742	0	1.399939	0	C
12404	234	5	63d 06:57	0d 01:00	1.400078	0	1.400015	0	C
12405	234	5	63d 07:07	0d 01:10	1.633413	0	1.399939	0	C
12406	234	5	63d 07:17	0d 01:20	1.866749	0	1.399939	0	C
12407	234	5	63d 07:27	0d 01:30	2.100085	0	1.400015	0	C
12408	234	5	63d 07:37	0d 01:40	2.333421	0	1.400015	0	C
12409	234	5	63d 07:47	0d 01:50	2.566757	0	1.399939	0	C
12410	234	5	63d 07:57	0d 02:00	2.800093	0	1.400015	0	C
12411	234	5	63d 08:06	0d 02:08	3.000003	0	1.400015	0	C
12412	234	6	63d 08:06	0d 00:00	0	0	0	0	R

Overcharge Tests for Commercial 18650

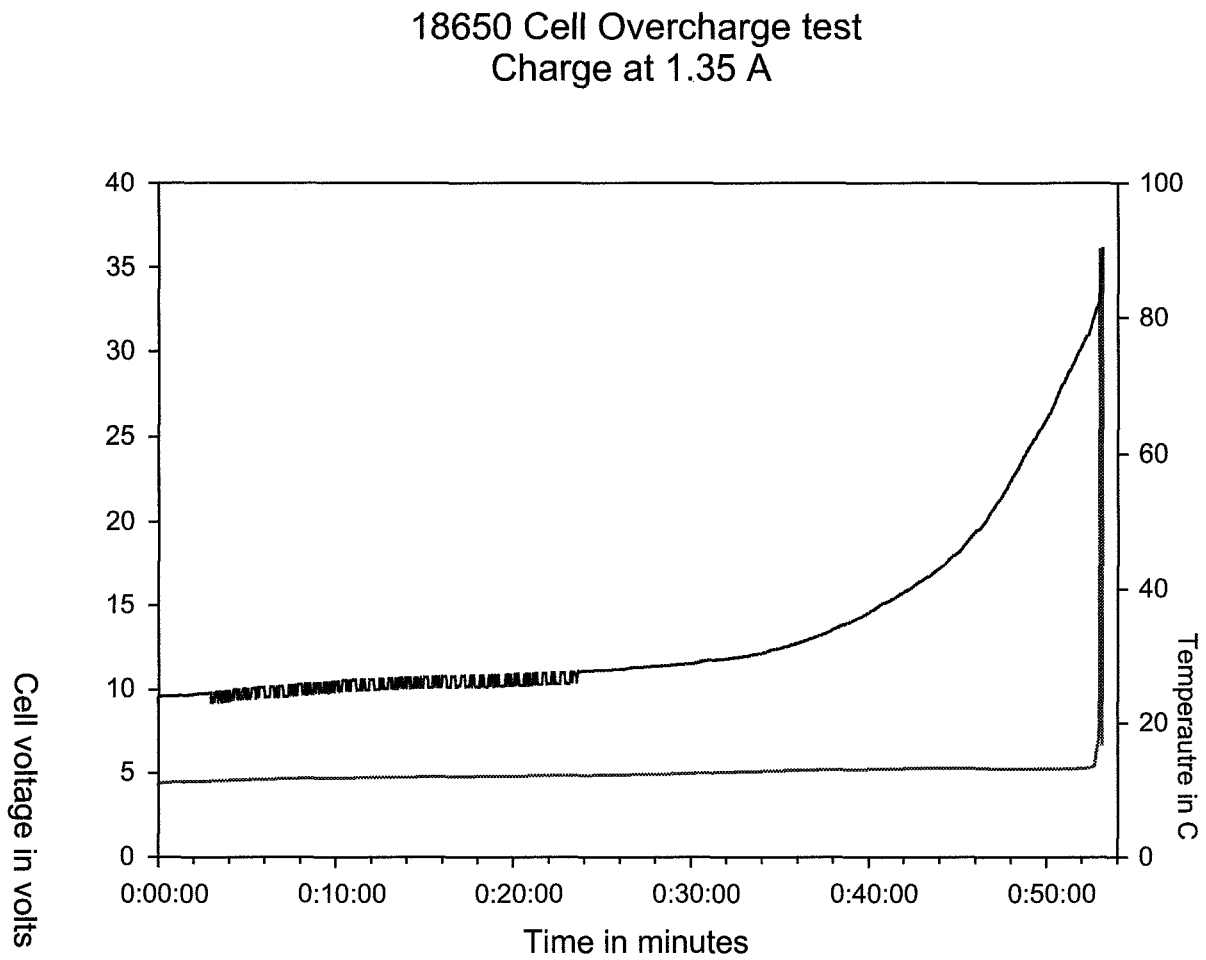

CECOM Bottom Line: THE SOLDIER

Overcharge Tests for Commercial 18650

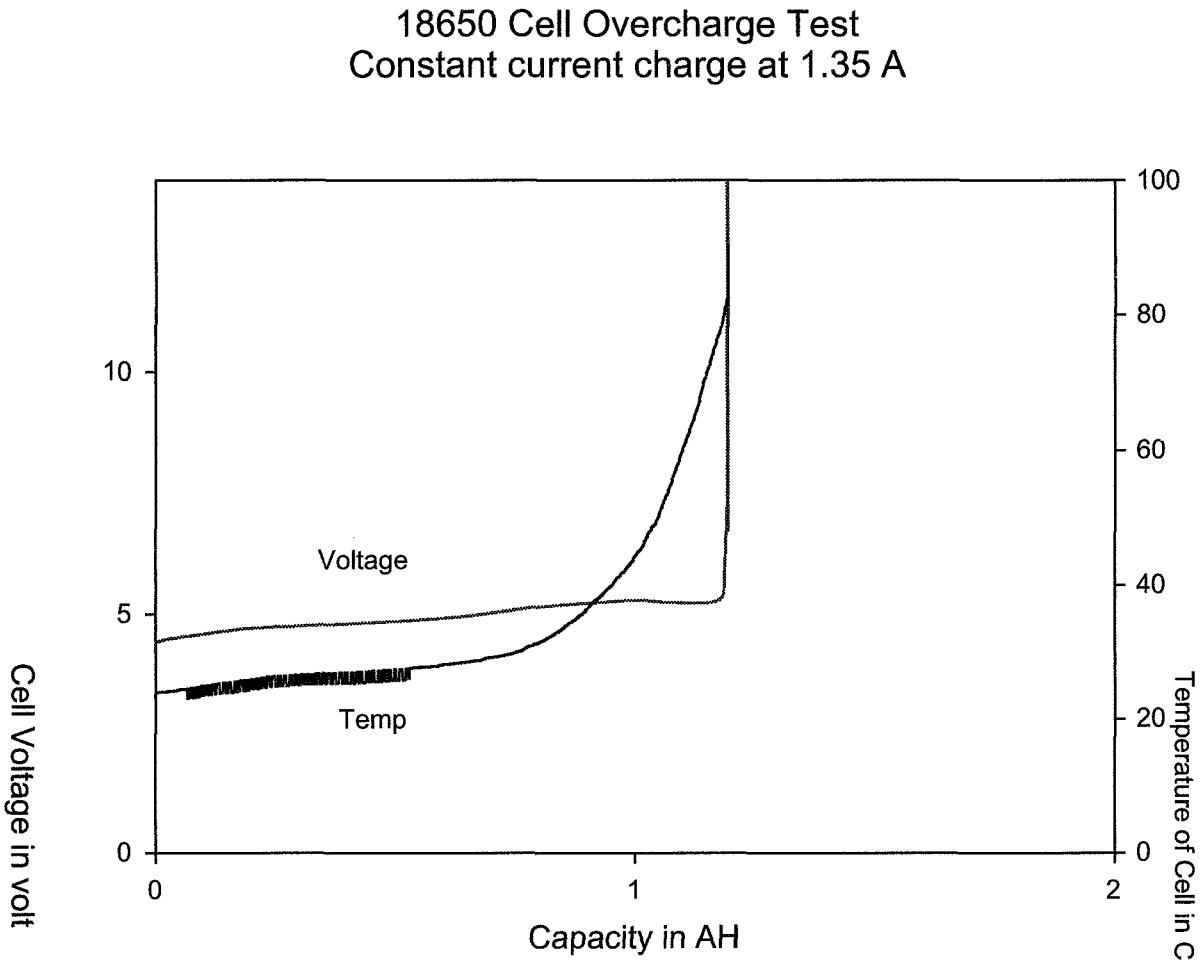

CECOM Bottom Line: THE SOLDIER

Overcharge Test for Commercial 26650

Lithium ion Cell 26650 overcharge tests
Constant at 2.5 Amps

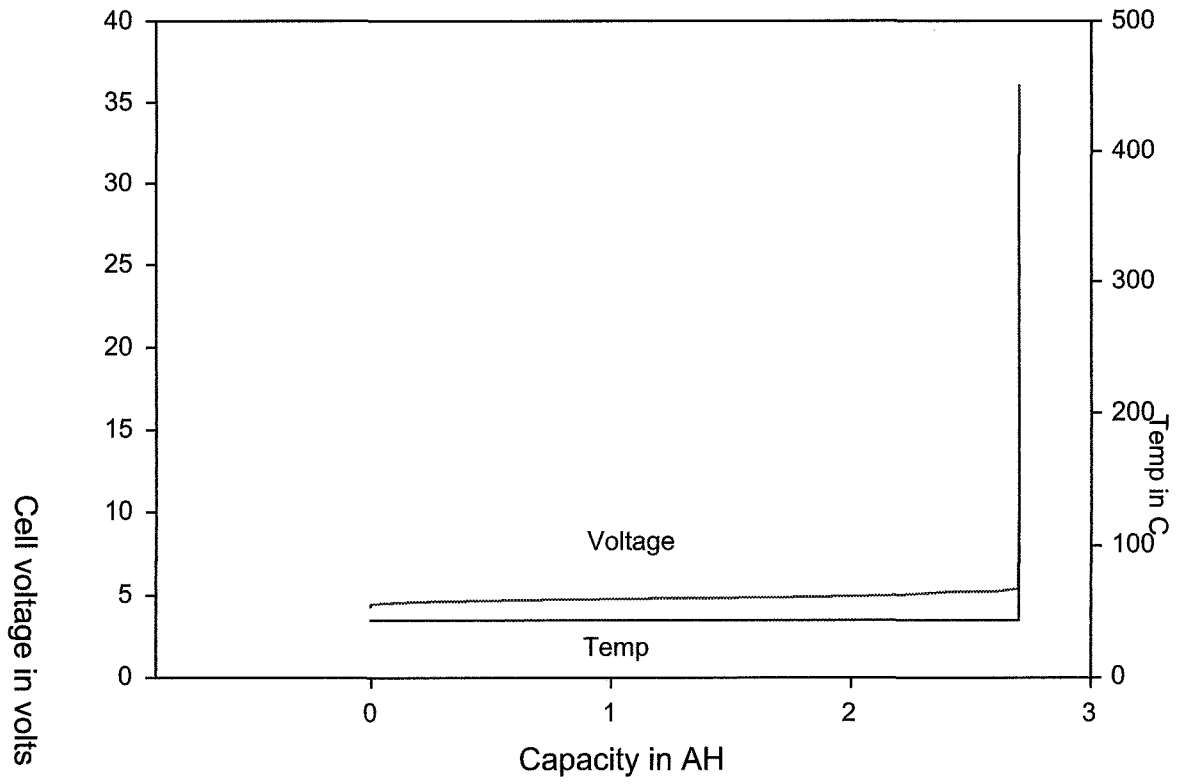

CECOM Bottom Line: THE SOLDIER

Overcharge Test for Commercial 26650

Lithium ion Cell 26650 Overcharge tests
Constant Current Charge at 2.5 amperes

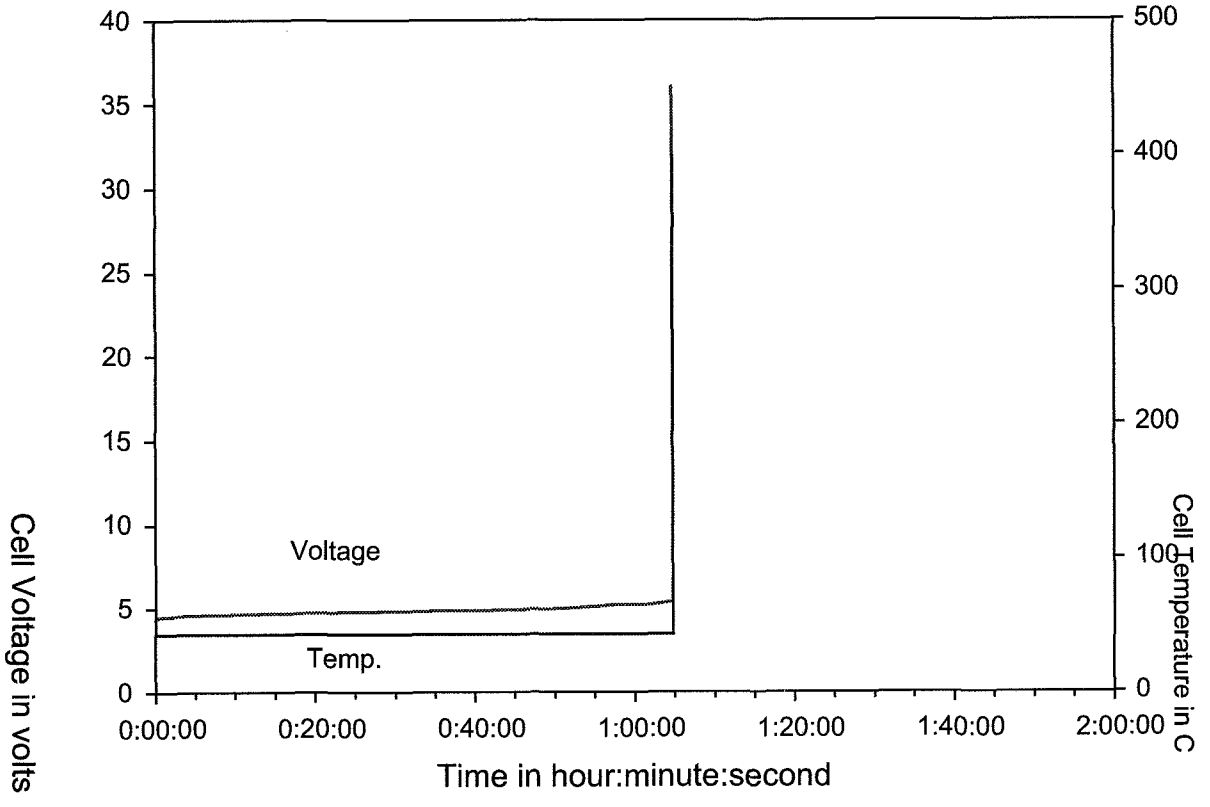

CECOM Bottom Line: THE SOLDIER

Lithium ion D cell cycling at 20 C, 70 C, and 90 C

Fig 9: 34570 (D) cell #20, #18, and #21 w/1.0M $LiPF_6$ 1EC:1DMC:1EMC
Discharge 2A / Charge 4A
#20 at 70°C, #18 at 20°C, #21 at 90°C
Lifecycle Test

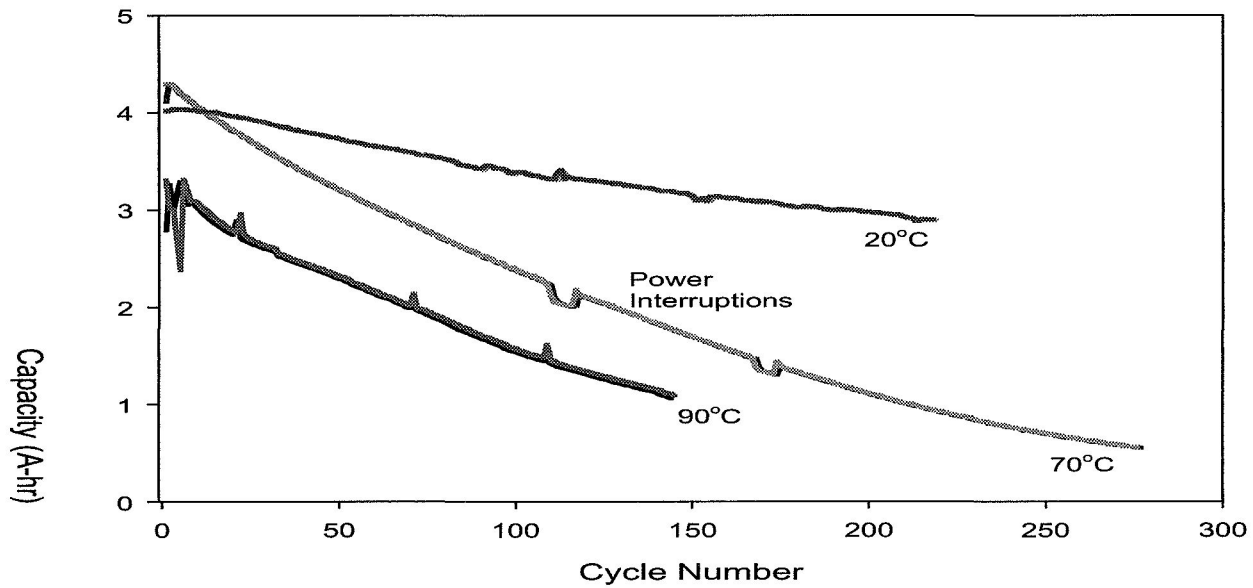

Discharge at 70C
Charge at 70C
Discharge at 20C
Charge at 20C
Discharge at 90C
Charge at 90C

Discharge capacity fade rate:
20°C: 0.147% for 1st 127 cycles; 0.128% for 1st 219 cycles
70°C: 0.416% for 1st 136 cycles; 0.313% for 1st 277 cycles
90°C: 1.547% for 1st 144 cycles

Overcharge Test Lithium ion D Cell with Rupture disk and Electrolyte Started to Leak out

CECOM Bottom Line: THE SOLDIER

Overcharge Test D cell Spark Come out of Rupture vent

CECOM Bottom Line: THE SOLDIER

Overcharge Test D cell, Voltage went to Zero and Temperature rise to 256 C

CECOM Bottom Line: THE SOLDIER

Overcharge Test Lithium ion "D" Size

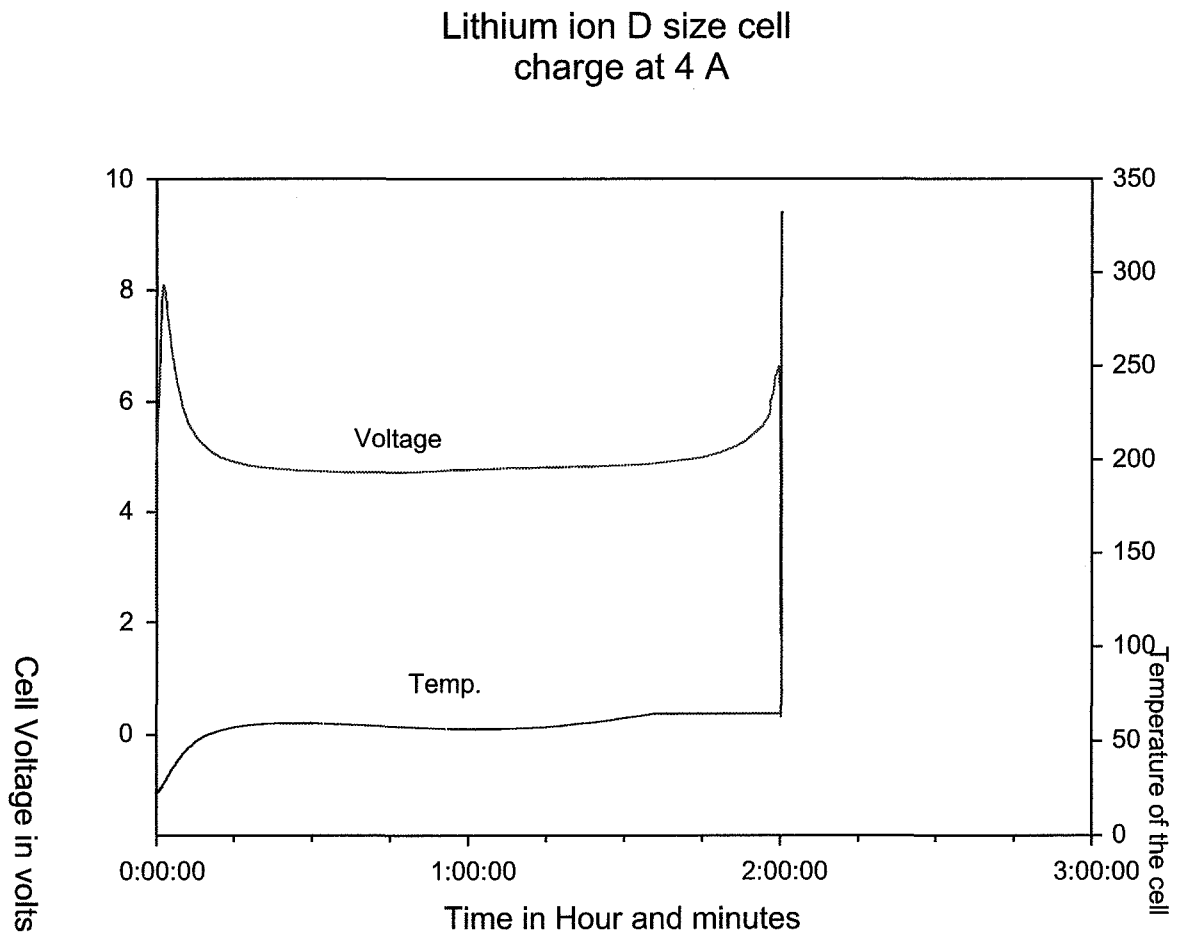

CECOM Bottom Line: THE SOLDIER

Overcharge Test Lithium ion "D" Size

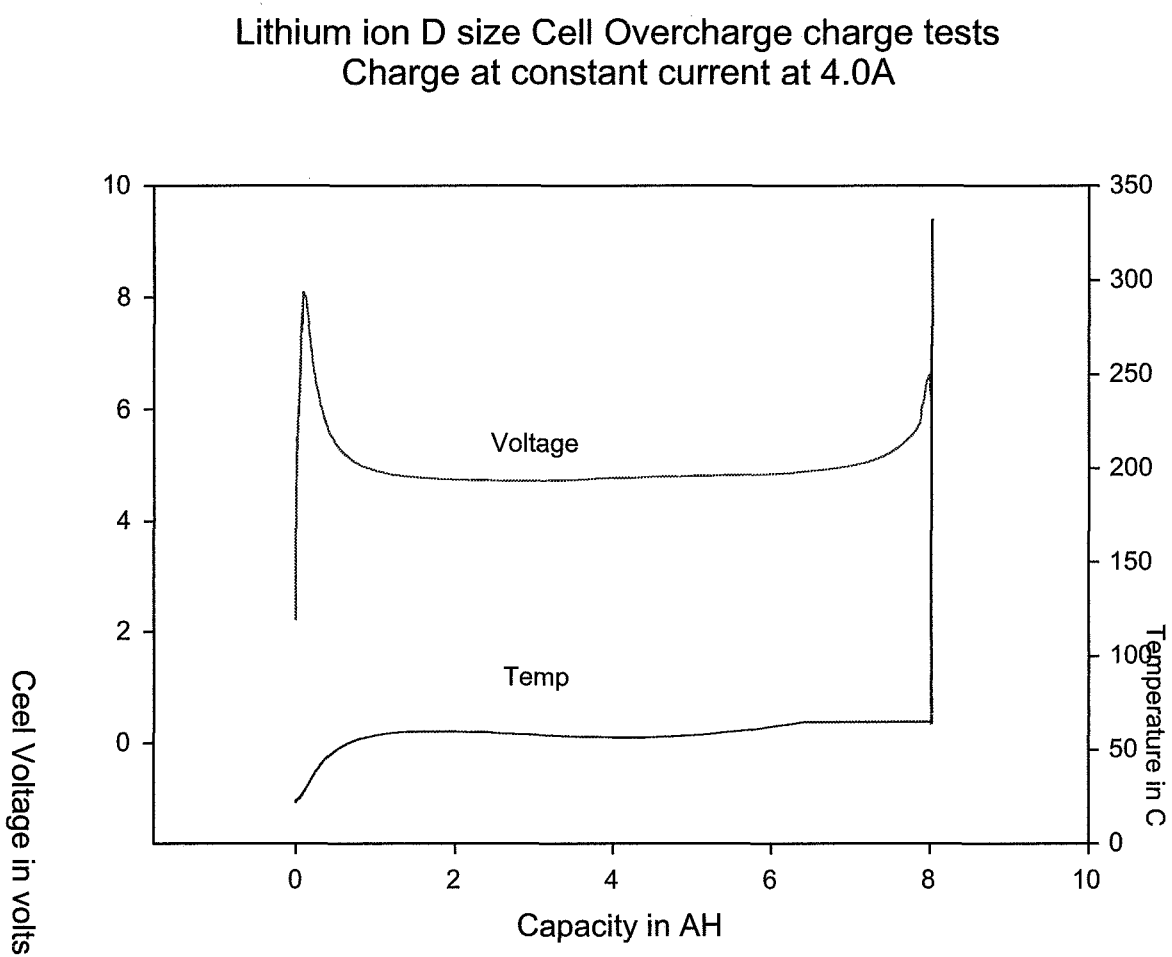

CECOM Bottom Line: THE SOLDIER

Commercial 18650 Pressure Disconnect Vent

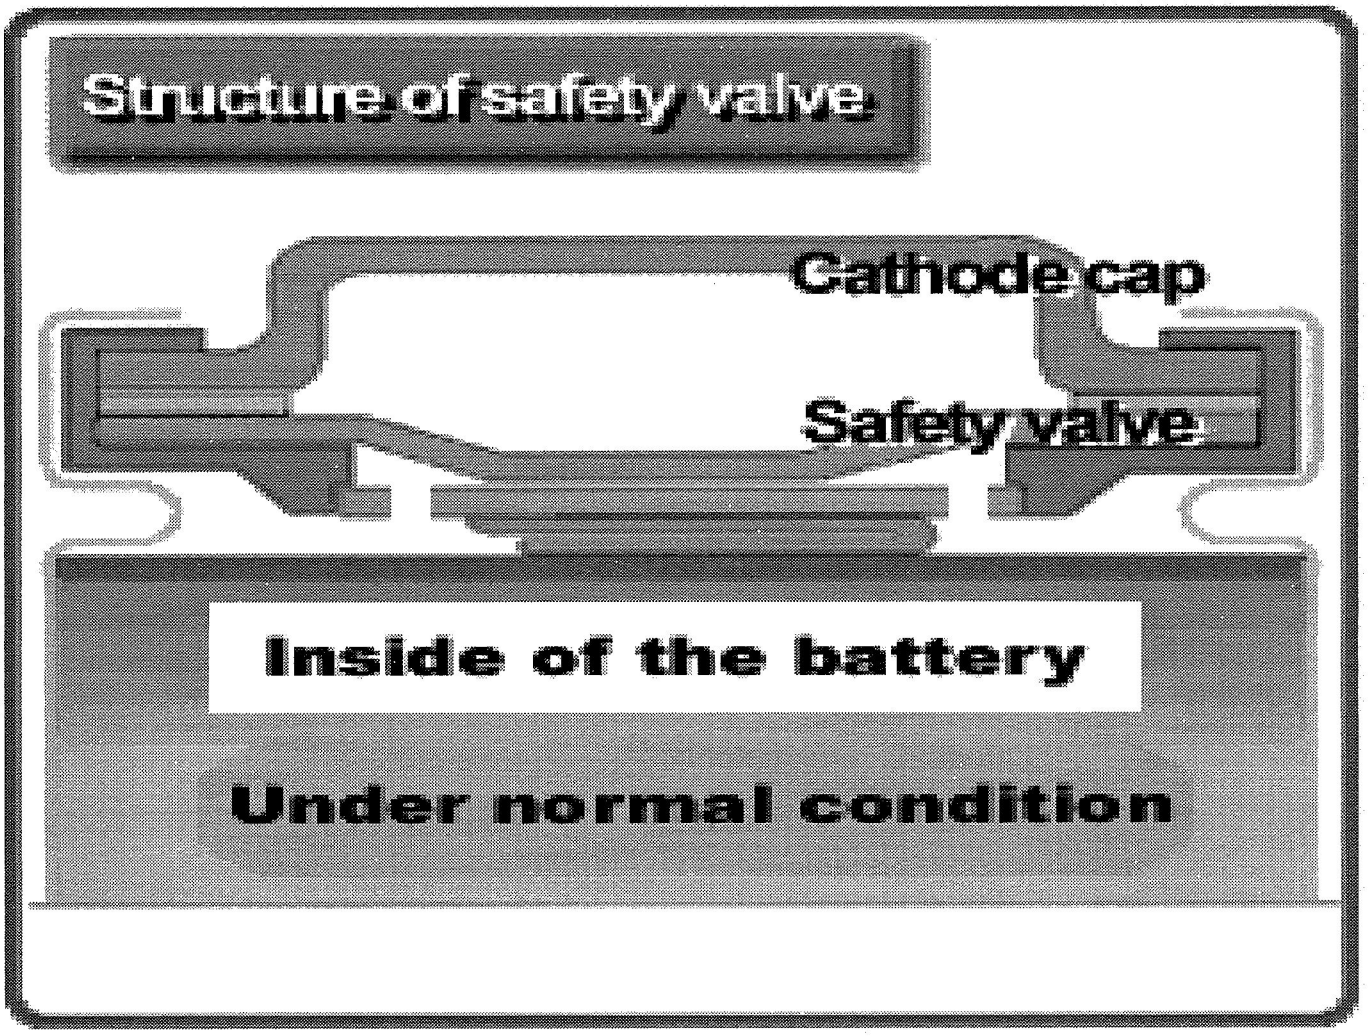

From M.Reid, E-One Moli Energy Limited

CECOM Bottom Line: THE SOLDIER

Commercial 18650 Pressure Disconnect Vent

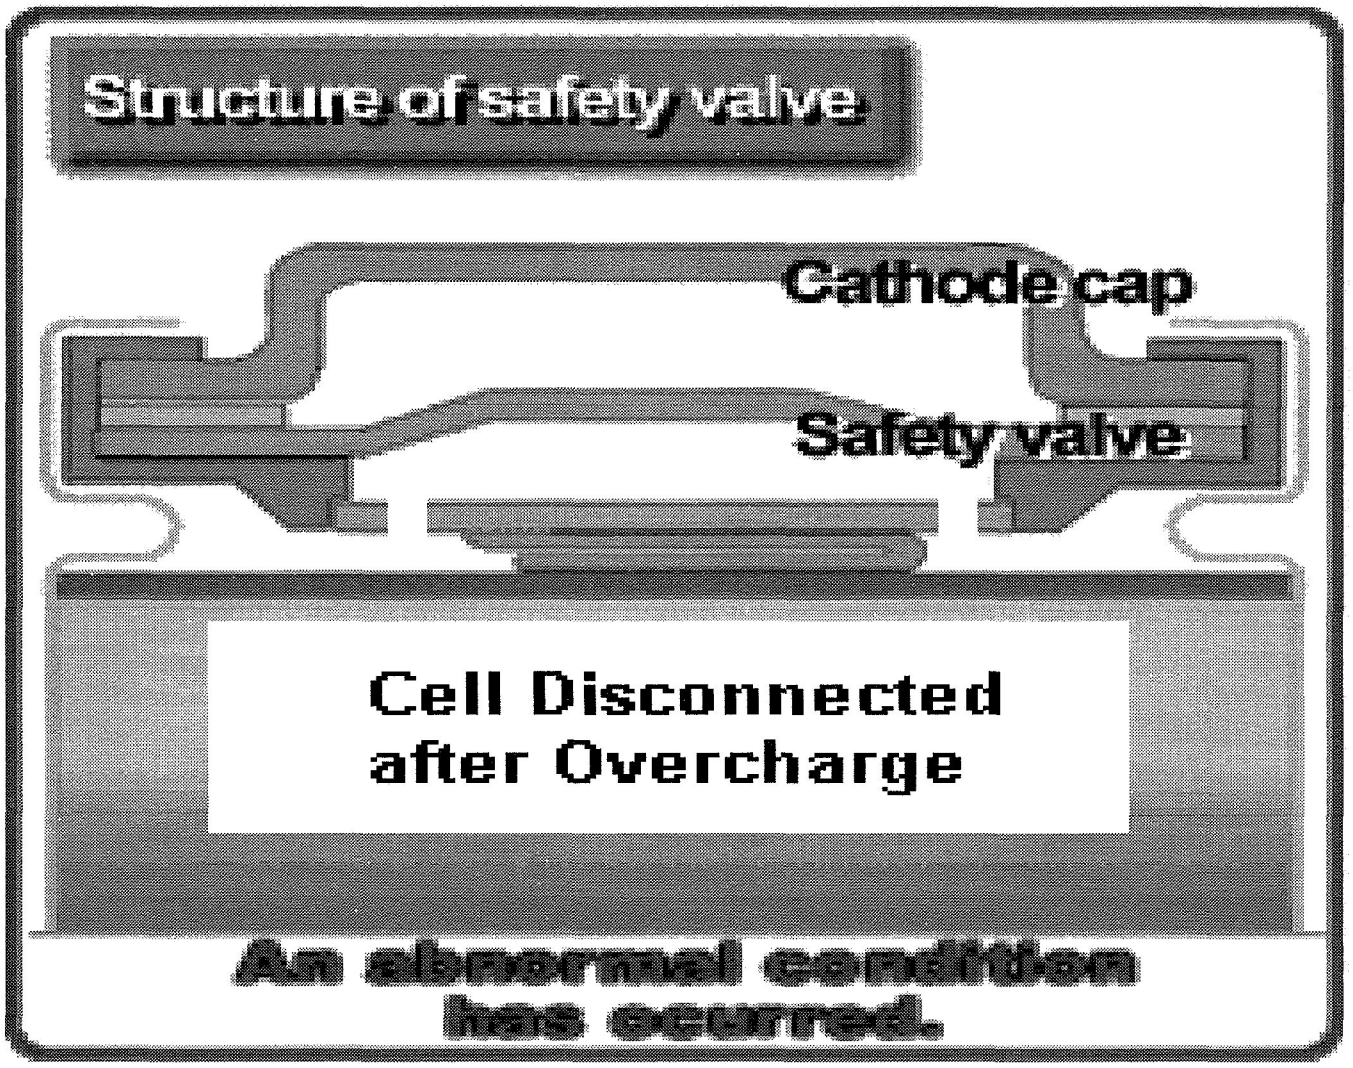

From M.Reid, E-One Moli Energy Limited

CECOM Bottom Line: THE SOLDIER

Commercial 18650 Pressure Disconnect Vent

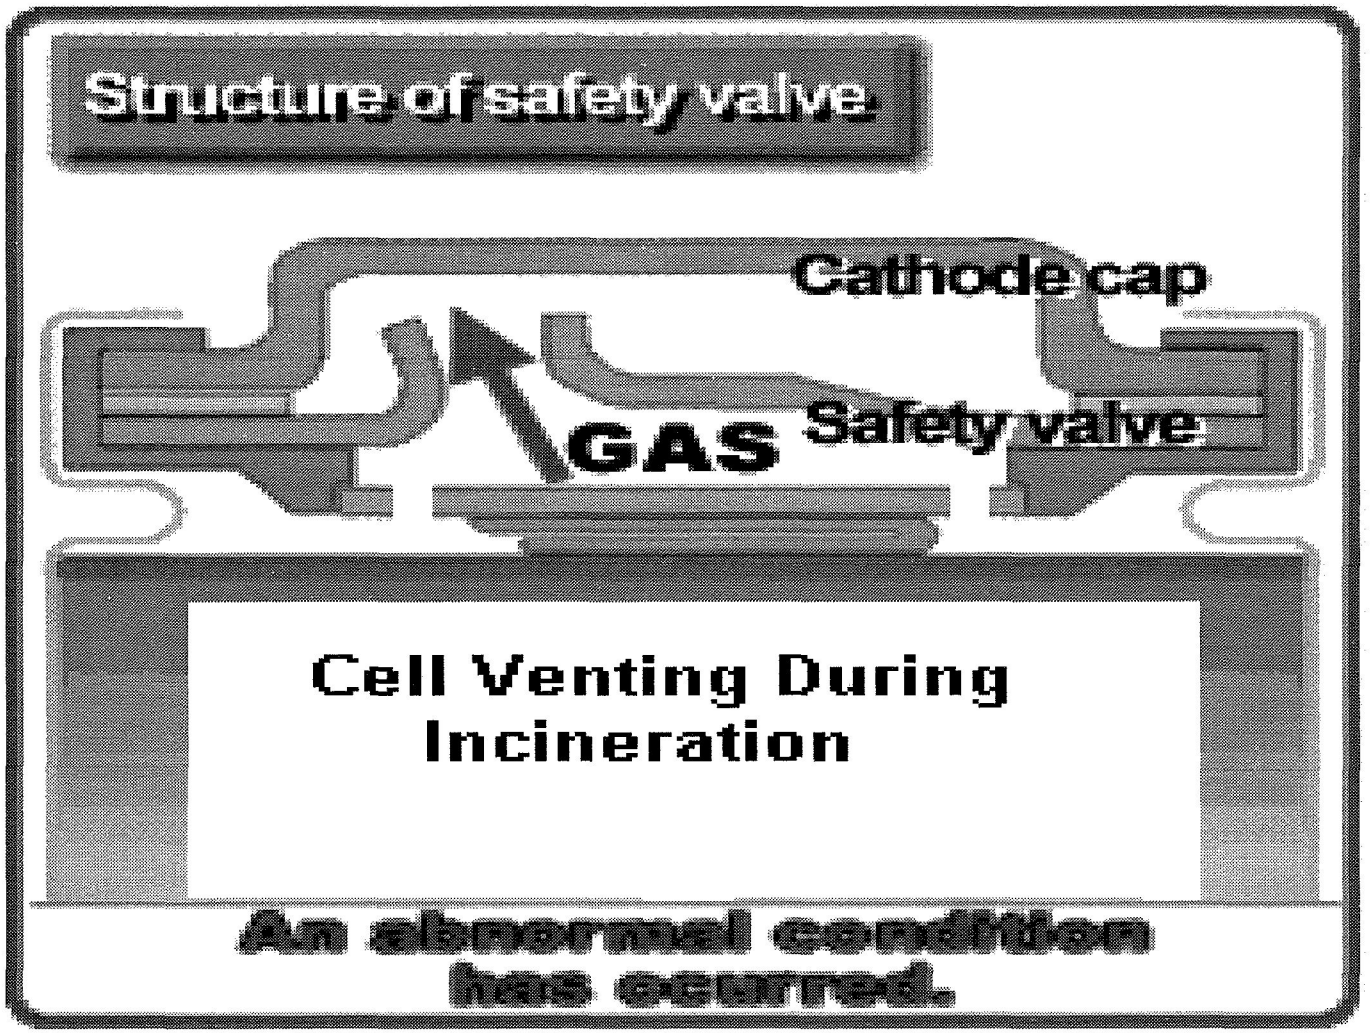

From M.Reid, E-One Moli Energy Limited

CECOM Bottom Line: THE SOLDIER

Nicad BB-542/U using Pressure Switch for Fast Charge Termination or Cutoff

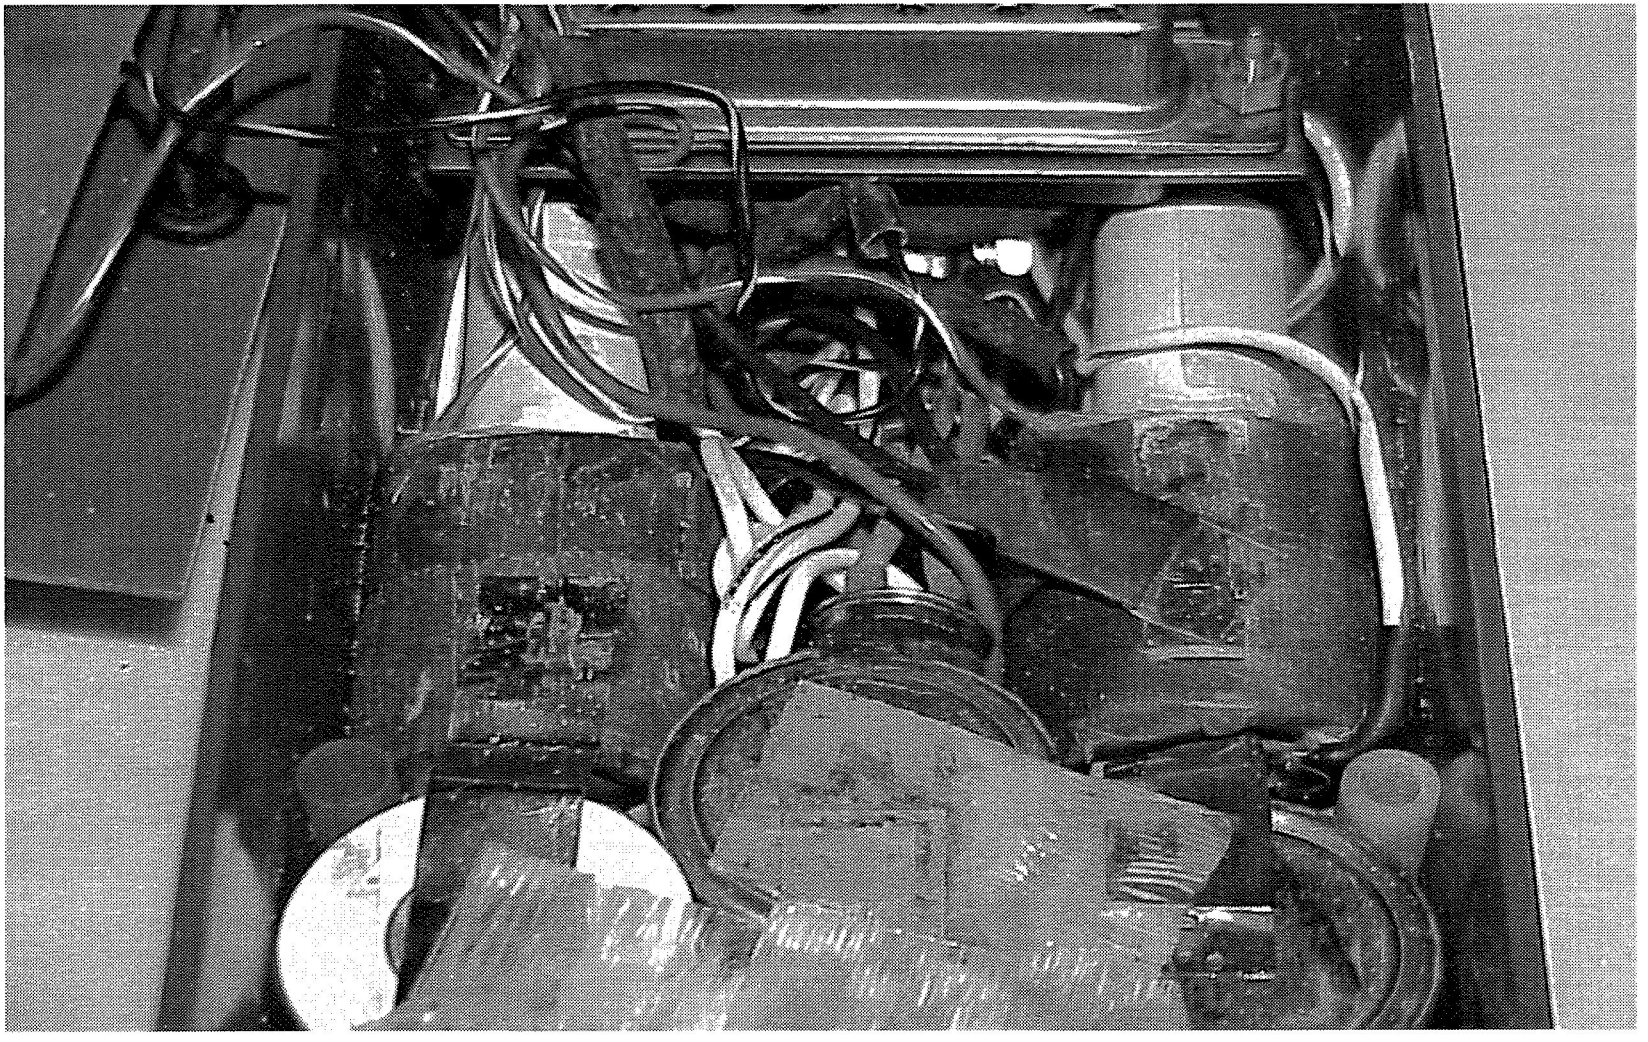

CECOM Bottom Line: THE SOLDIER

Large Lithium ion Cell and Batteries using the rupture disk

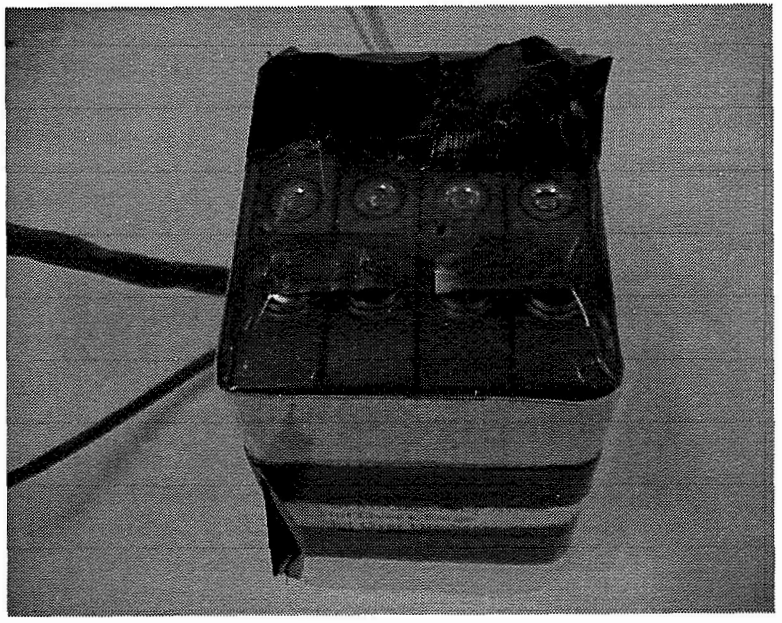

20 AH, 14.4 V Battery

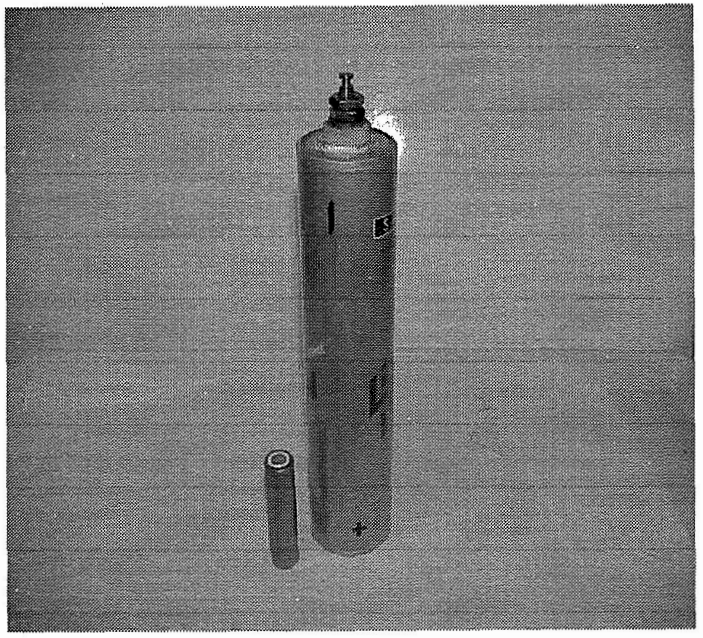

40 AH, Single Cell

Propose Mechanical Pressure Switch for a large Lithium ion Cell

CECOM Bottom Line: THE SOLDIER

40 AH Cell Charge at C rate to 4.0V

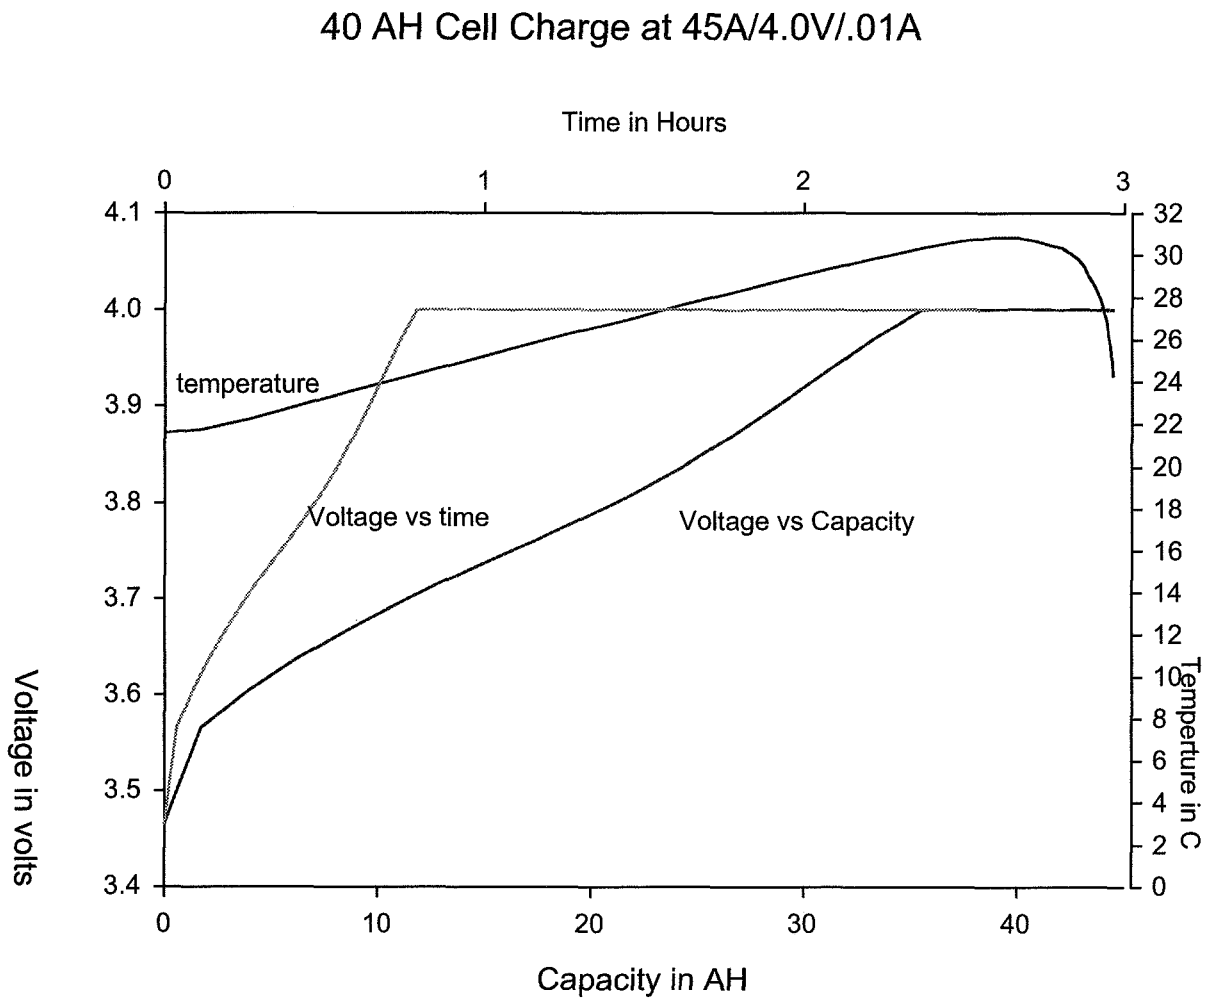

CECOM Bottom Line: THE SOLDIER

40 AH Lithium ion Cylindrical Cell Discharge at 55 Amperes to 2.75V Cutoff

Lithium ion Cell 40AH, Discharge at 55A to 2.75V at 18 C

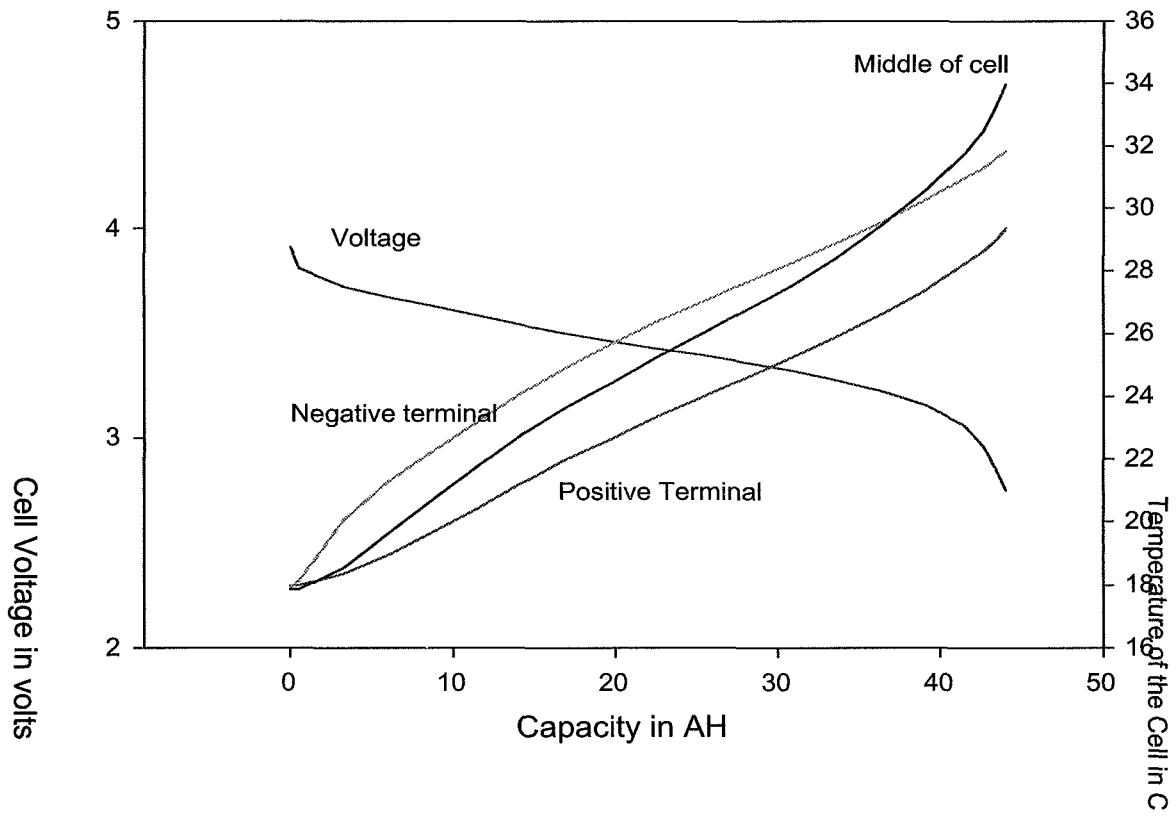

CECOM Bottom Line: THE SOLDIER

40 AH Cell Discharge at 2C

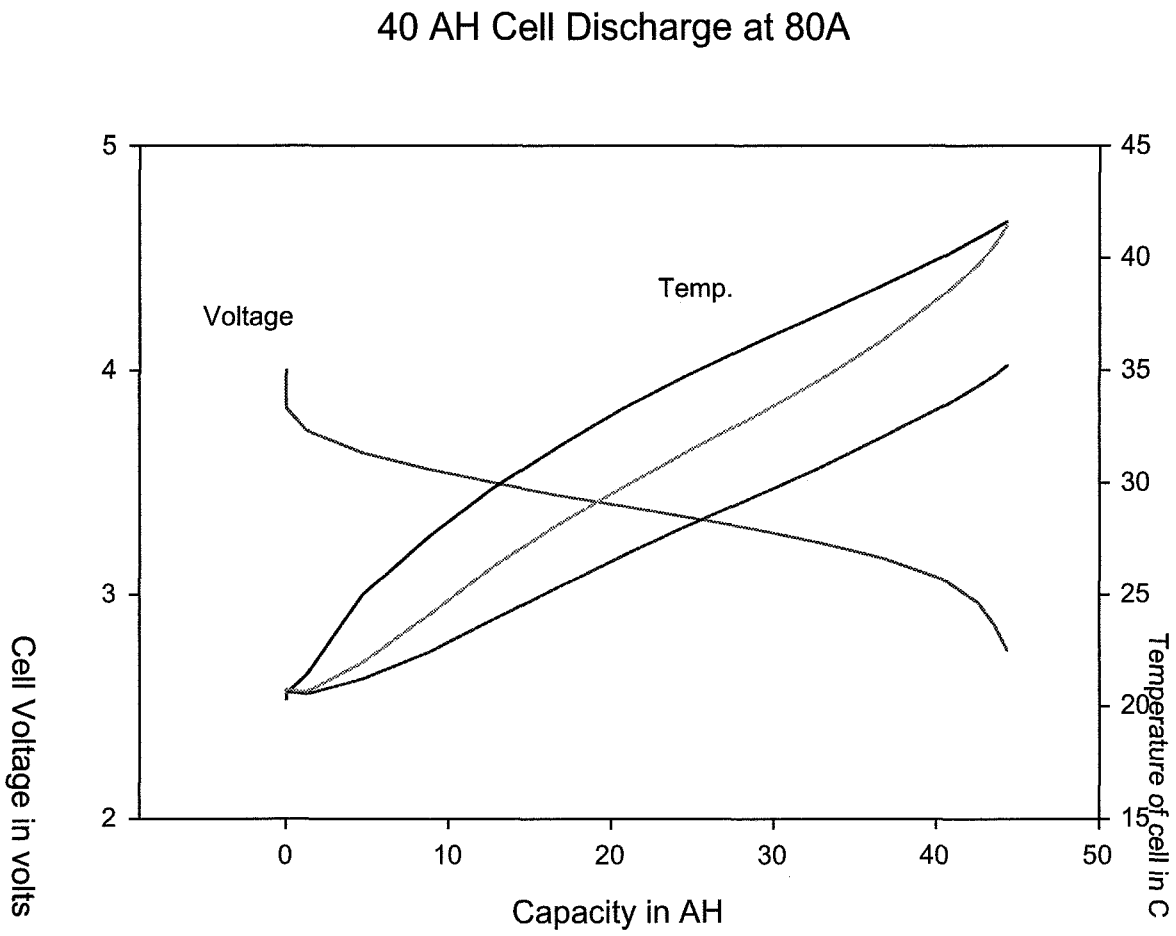

CECOM Bottom Line: THE SOLDIER

Propose Cell Specification For a Large Lithium ion Cell

3.5.3 Cell safety A single cell that does not contain any electronics shall meet all the safety requirement listed below:

3.5.3.1 Cell overcharge . After being subjected to the test as specified in 4.4.2.3.1 the cell shall not explode or catch fire or spark. No electrodes or separator material of the cell shall be outside of the cell case.

3.5.3.2 Cell short circuit. After being subjected to the test as specified in 4.4.2.3.2 the cell shall not explode or catch fire.

3.5.3.3 Cell Forced-Discharge. After a single cell in the string has been subjected to the test as specified in paragraph 4.4.2.3.3 , there shall be no leaking, venting, fire or explosion.

4.4.2.3.1 Cell overcharge. A single cell shall be placed in a temperature chamber set at 25°C. A thermocouple shall attach to the side of the cell, and current carrying and voltage monitoring leads shall be attached to the terminals. A constant C/2 current charging rate shall be applied for 8 hours continuously. Cell temperature, voltage, and current shall be recorded. A single cell shall meet the requirement for 3.5.3.1.

4.4.2.3.2 Cell short circuit. A single cell shall be shorted by connecting the positive and negative terminals of the cell with a less than 8 inch in length of No. 0 AWG or equivalent copper wire. The cell shall be completely discharged and the battery case temperature has returned to near ambient temperature. The cell shall meet the requirement of 3.5.3.2.

4.4.2.3.3 Cell forced-discharge. A completely discharged single cell (less than 0.2 volts) is to be forced-discharge in accordance with method 2 of the forced-discharge test of UL-1642. One cell for each cell string shall be discharged at the rate specified (see 3.1) to a test end voltage of two-thirds of its open circuit voltage. It shall then be connected in series with the appropriate number of charged cells which shall then be discharged at the rate specified (see 3.1) to a test end voltage of the applicable specification sheet. All cells shall comply with requirements (see 3.5.3.3).

Conclusion and Recommendation for Lithium ion Cell & Battery Safety Design

Cell Level

• Shall have Pressure Switch for large Lithium ion Cell and Pressure Disconnect and /or PTC device for small lithium ion Cell. These Devices must capable to disrupt of current flow.

Battery Level

• Charge controller – Overvoltage and undervoltage, Temperature devices.

Charger Level

• Overvoltage, Undervoltage, overcharge, temperature termination.

Acknowledgements

DARPA, Technology Reinvestment Program

Saft America, Inc.

Yardney (Lithion) Inc.

E-One Moli Energy Limited

Maxell Inc.

NASA, Mars Exploration Program

JPL, California Institute of Technology

US Army, CECOM, Ft. Monmouth

US Airforce, Wright Paterson AFB

CECOM Bottom Line: THE SOLDIER

Performance and Safety Of Lithium Ion Cells

B. V. Ratnakumar, M. C. Smart, L. Whitcanack and S. Surampudi
Jet propulsion Laboratory, Pasadena, California
and
R. Marsh
Wright-Patterson Air Force Base, Dayton, OH

JPL

Supported by Mars Program Office and NASA Code S Battery Programs

NASA Battery Workshop, Nov. 14-16, 2000, Huntsville, AL

538228 28 p
20011836

Evaluation of Lithium-Ion Cells at JPL

- Cycle life performance at room temperature (25°C)
- Cycle life performance at low temperature (-20°C)
- Cycle life at alternating temperatures (40 and -20°C)
- Discharge rate characterization (at 40, 25, 0, and -20°C)
- Charge rate characterization (at 40, 25, 0, and -20°C)
- Capacity retention tests
- Accelerated LEO Tests
- Storage characterization tests (cruise conditions)
- VT charge characterization tests
- Electrical characterization by a.c. impedance
- Thermal characterization

NASA-DOD Interagency Li Ion Program

Objectives

- DEVELOP HIGH SPECIFIC ENERGY AND LONG CYCLE LIFE Li -ION BATTERIES
- ESTABLISH U.S. PRODUCTION SOURCES
- DEMONSTRATE TECHNOLOGY READINESS
  - LANDERS BY 2001
  - ROVERS BY2003
  - GEO MISSIONS BY 2003
  - AVIATION/UAV's BY 2001
  - MILITARY TERRESTRIAL APPLNS's BY 2001
  - LEO MISSIONS BY 2003

Technology Drivers

Mission	Technology Driver
Lander Rover	Low Temperature Operation High rate Pulse Capability
GEO S/C	10-20 Year Operating life Large Capacity cells (50-200 Ah)
LEO PlanetaryS/C	Long Cycle life(30,000) Medium Capacity Cells (50 Ah)
Aircraft	Low temperature Operation High Voltage Batteries (270 V)
UAV	Large Capacity cells (200 Ah) High Voltage Batteries (100V)

Cycle Life of Li Ion Cells

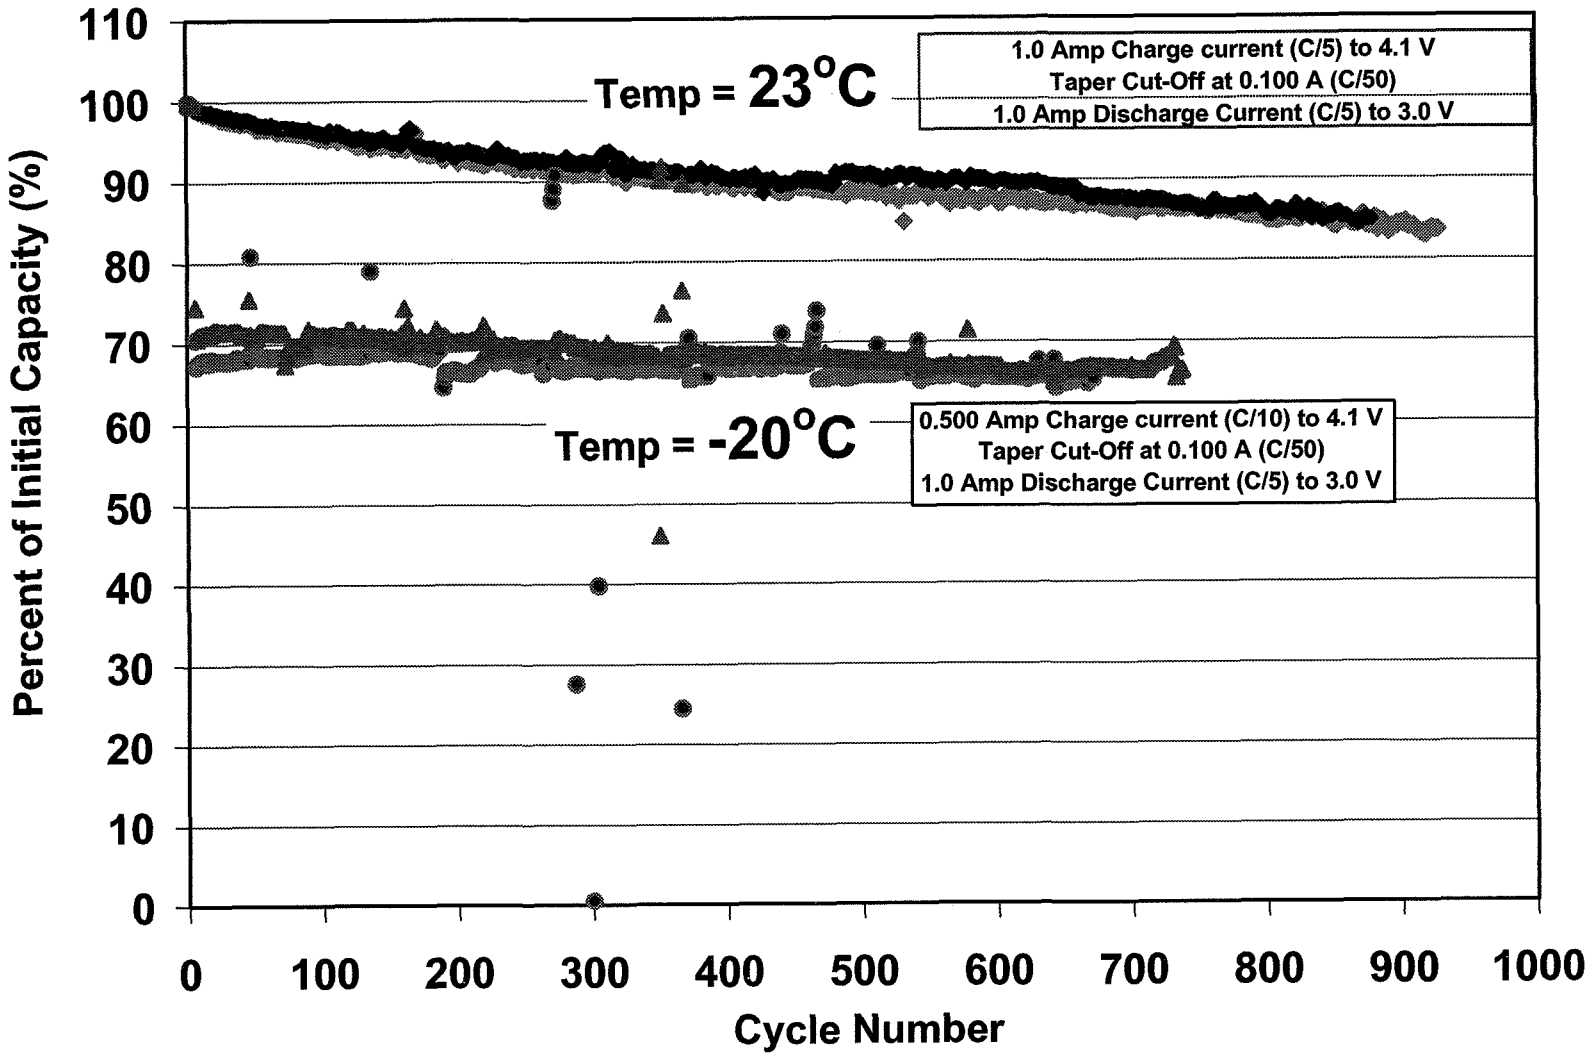

Cycle Life of Li Ion Cells-Energy efficiency

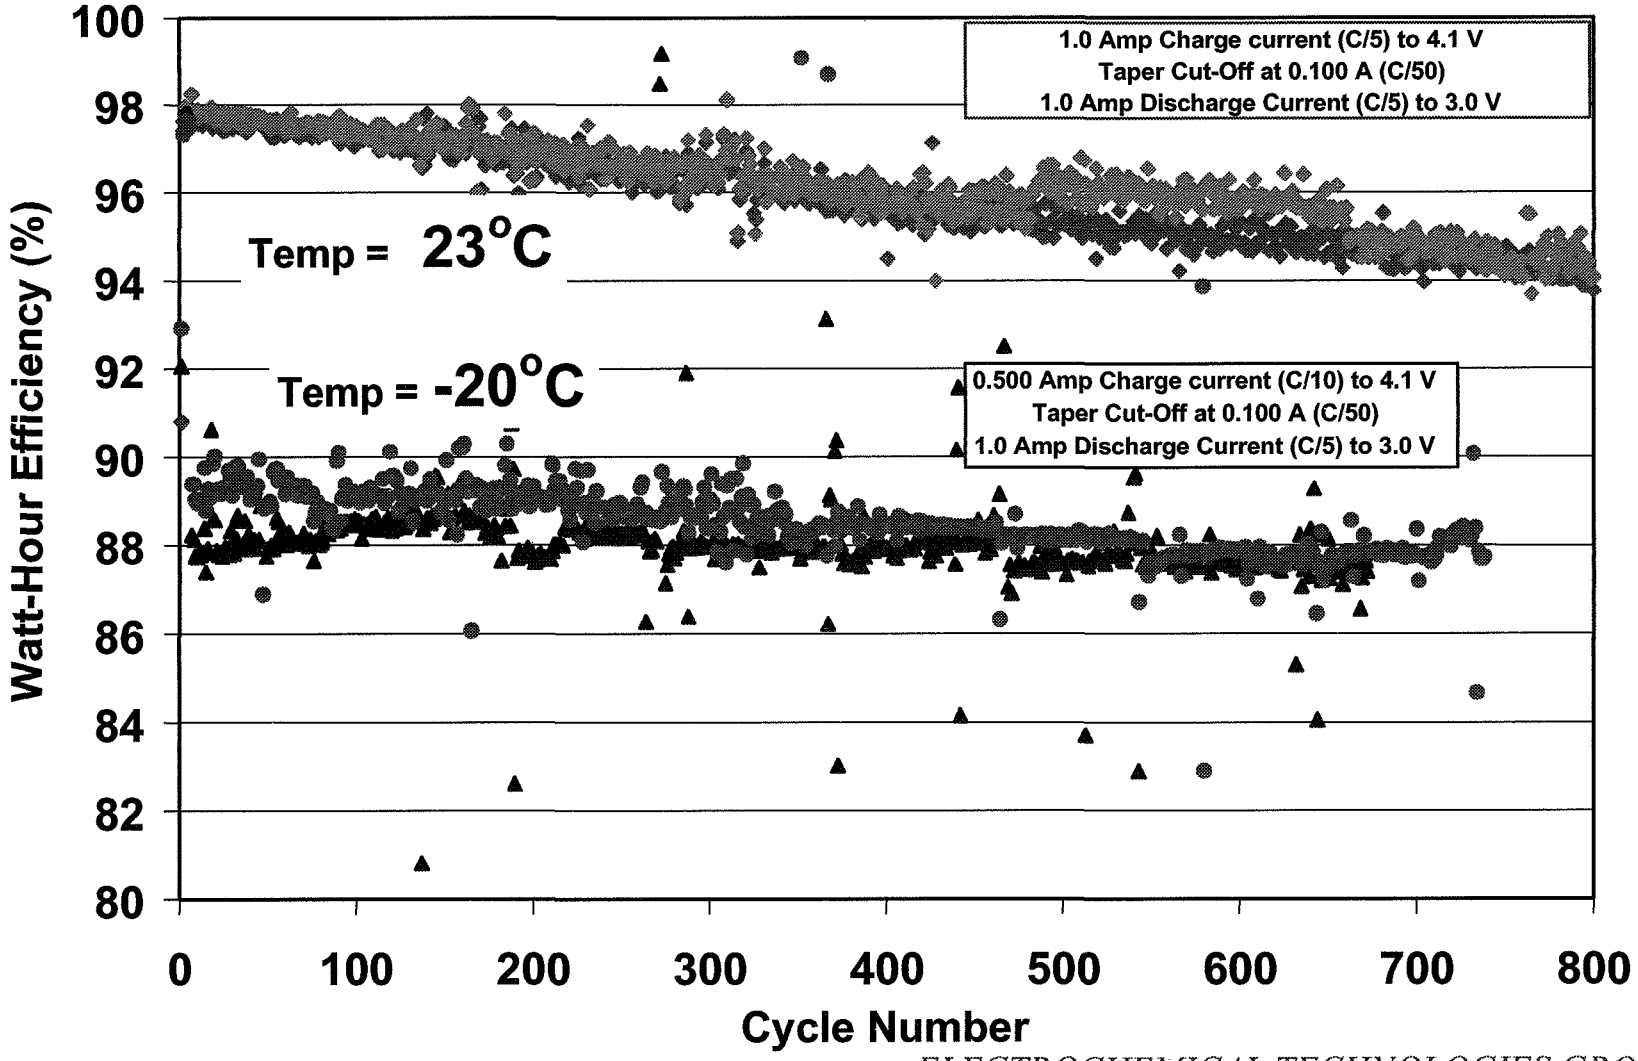

Cycle Life of Li Ion Cells to Partial DOD Accelerated LEO

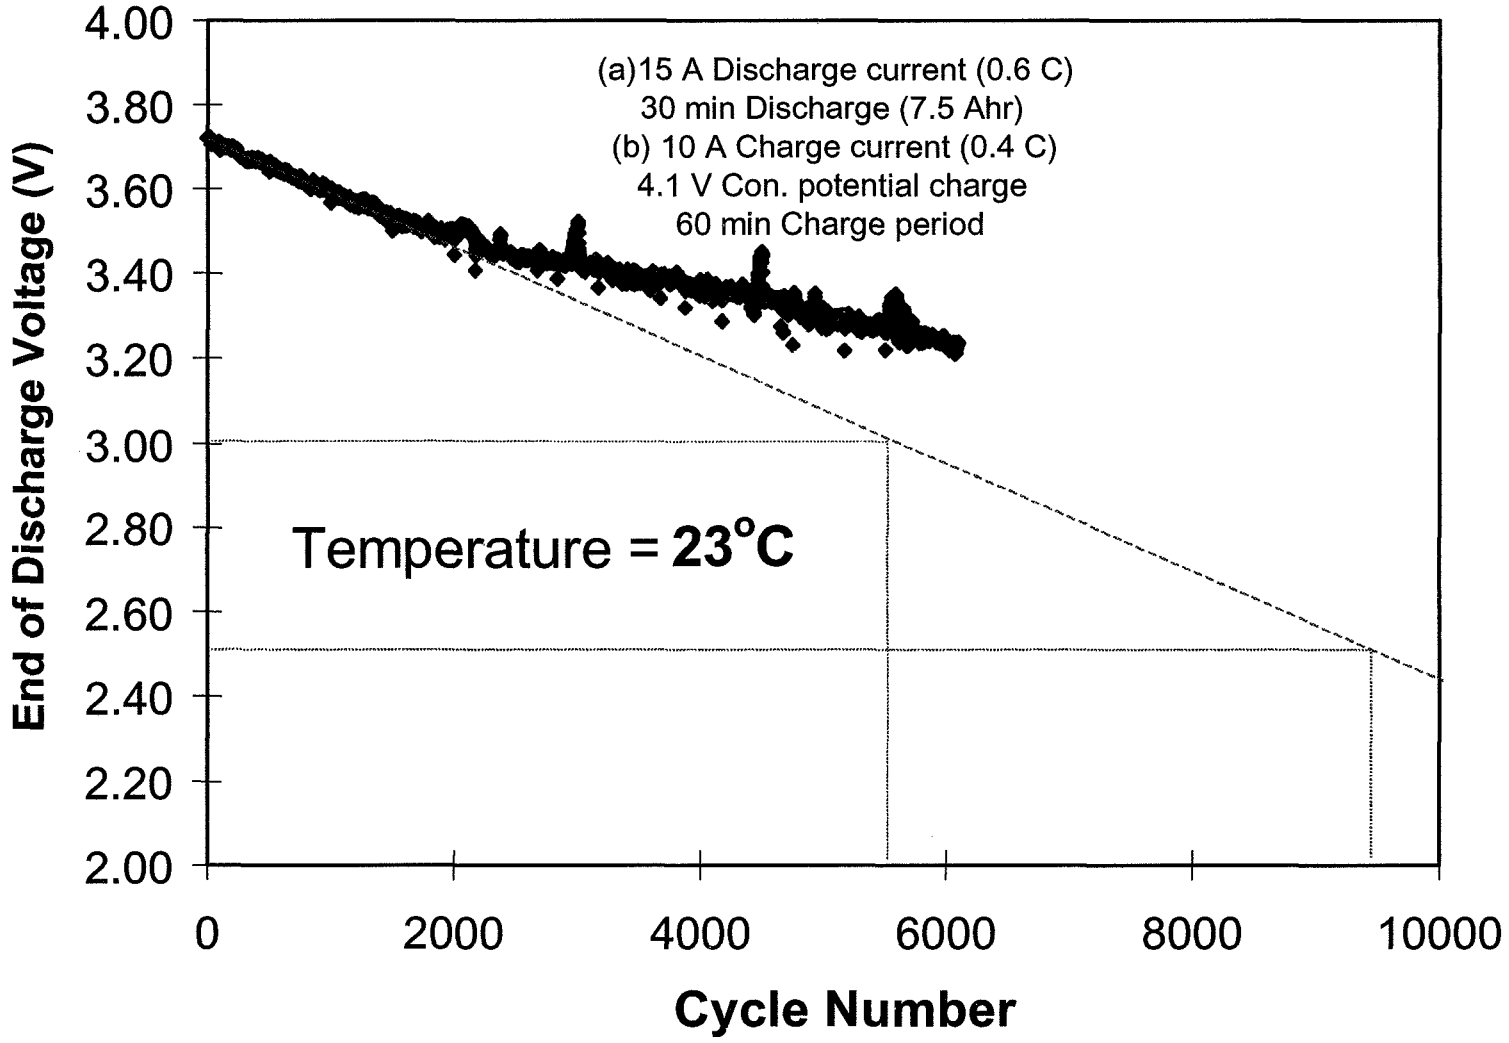

Tolerance to Higher Charge Voltage

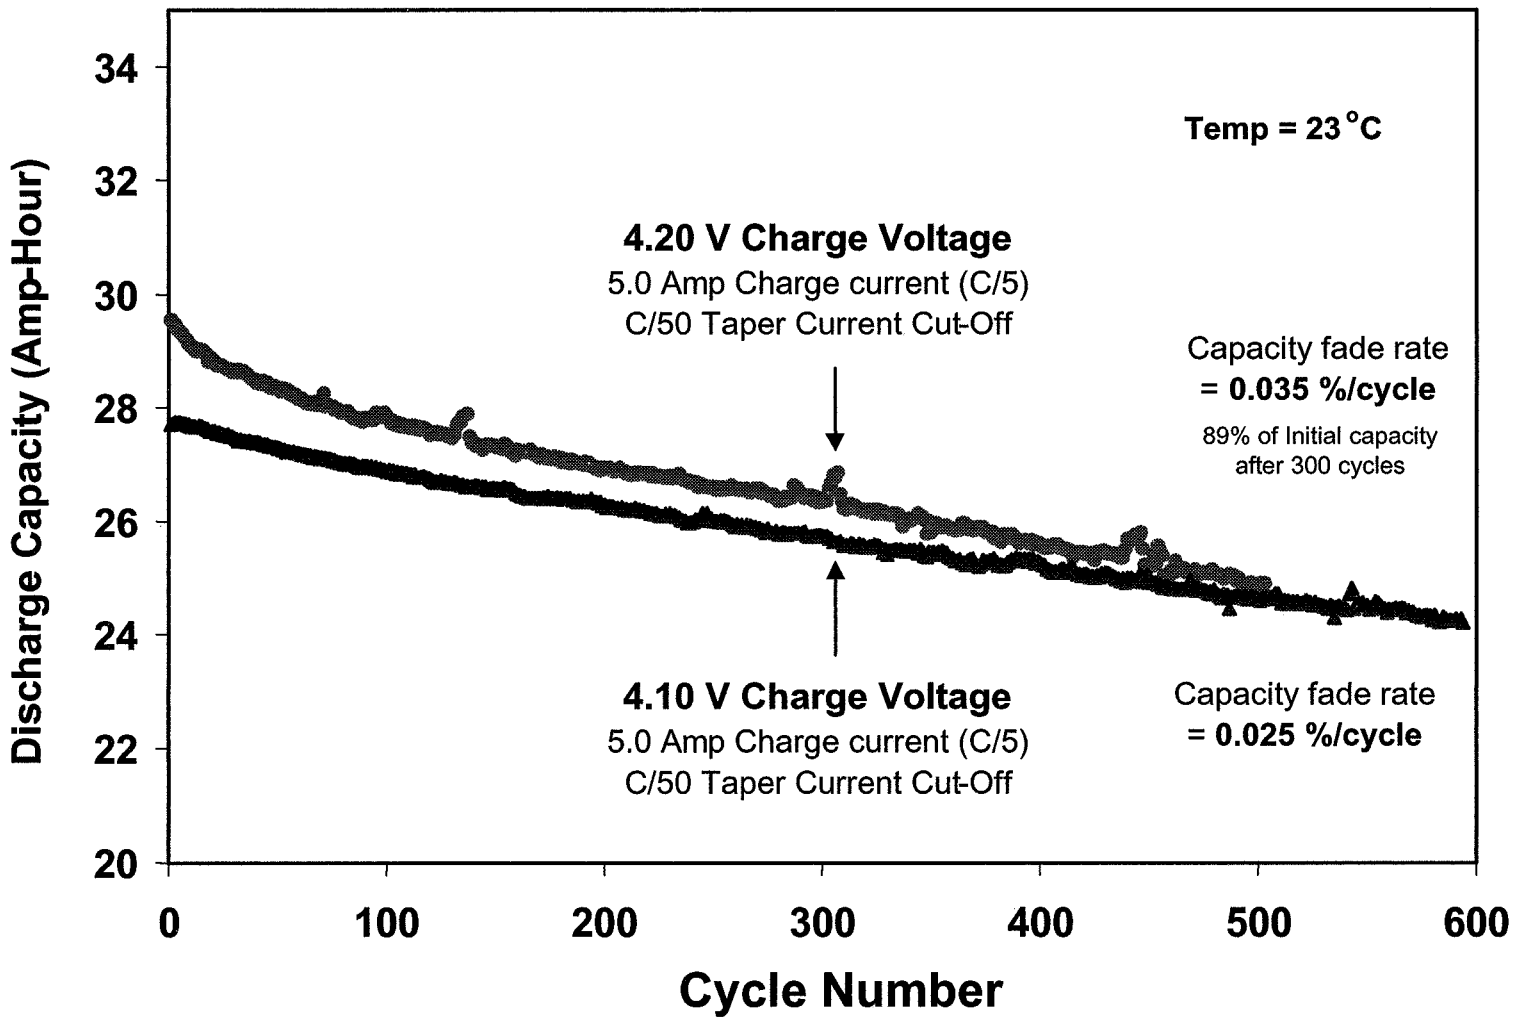

Tolerance to Extended Tapered Charge

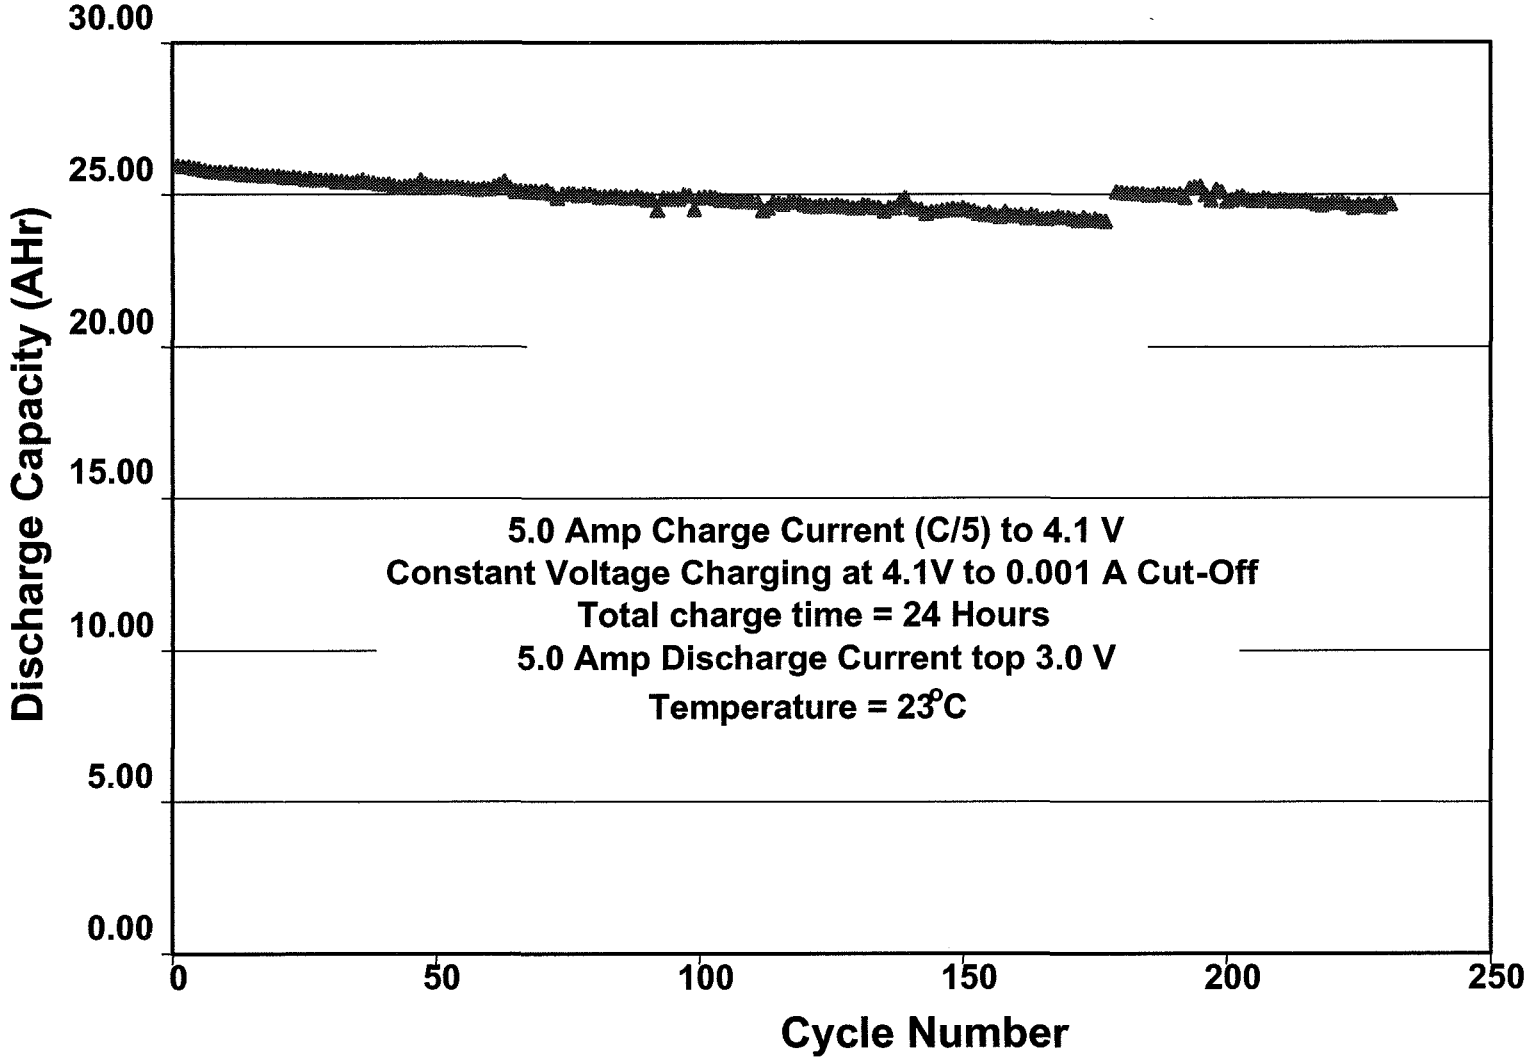

Charge on Cycling

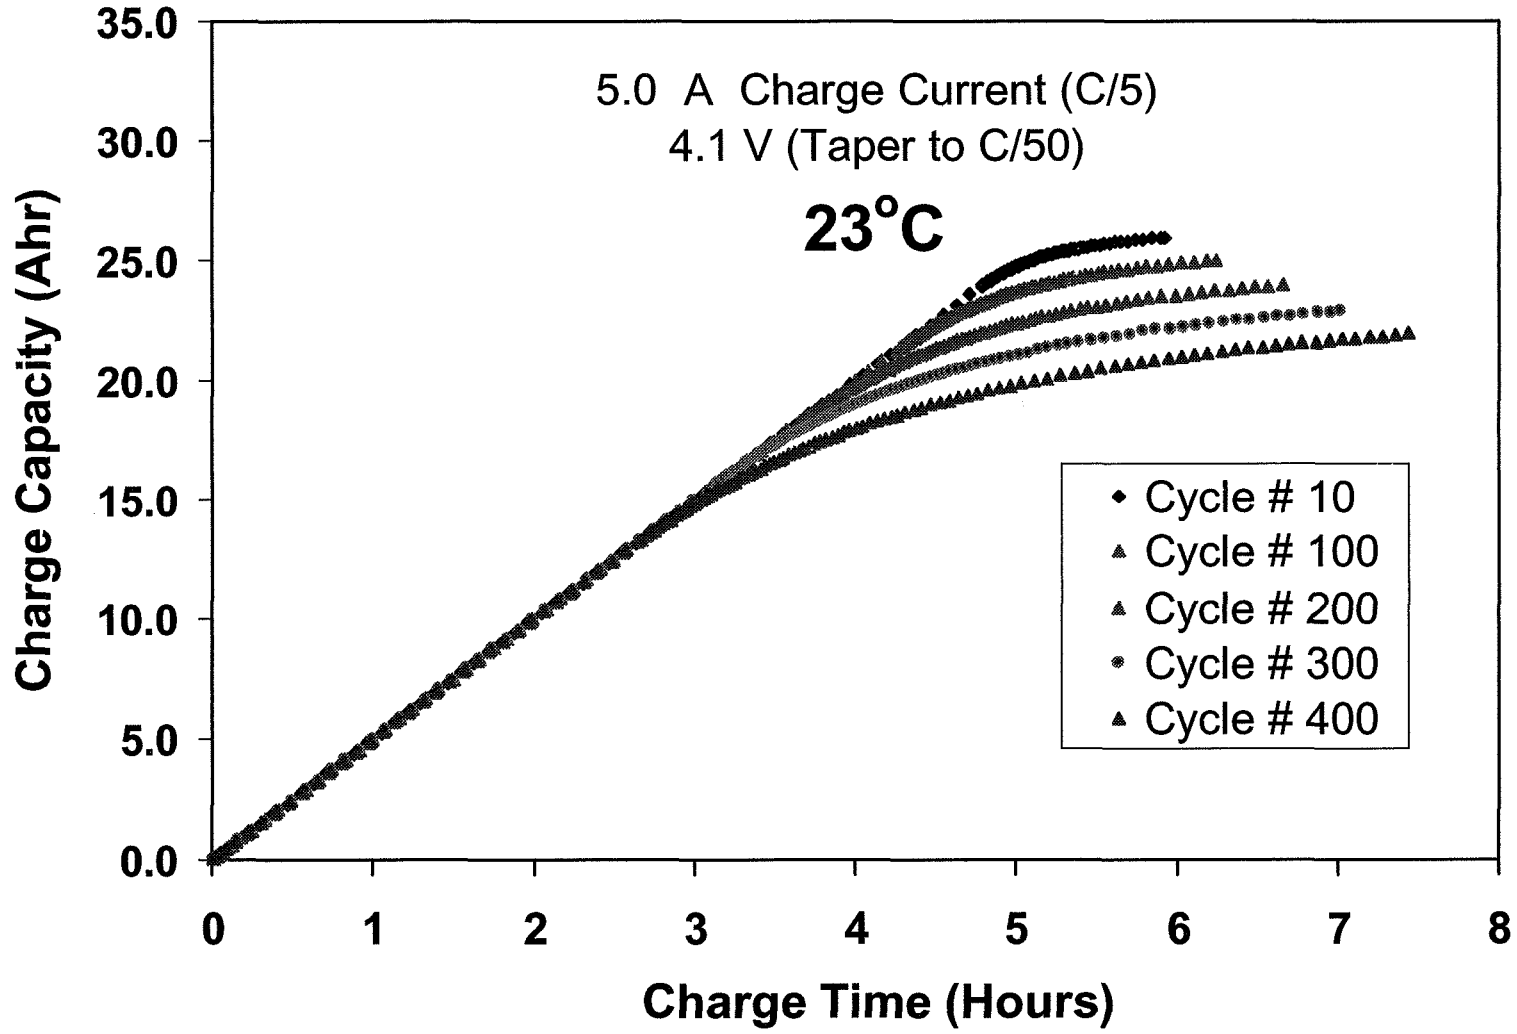

Specific Energy

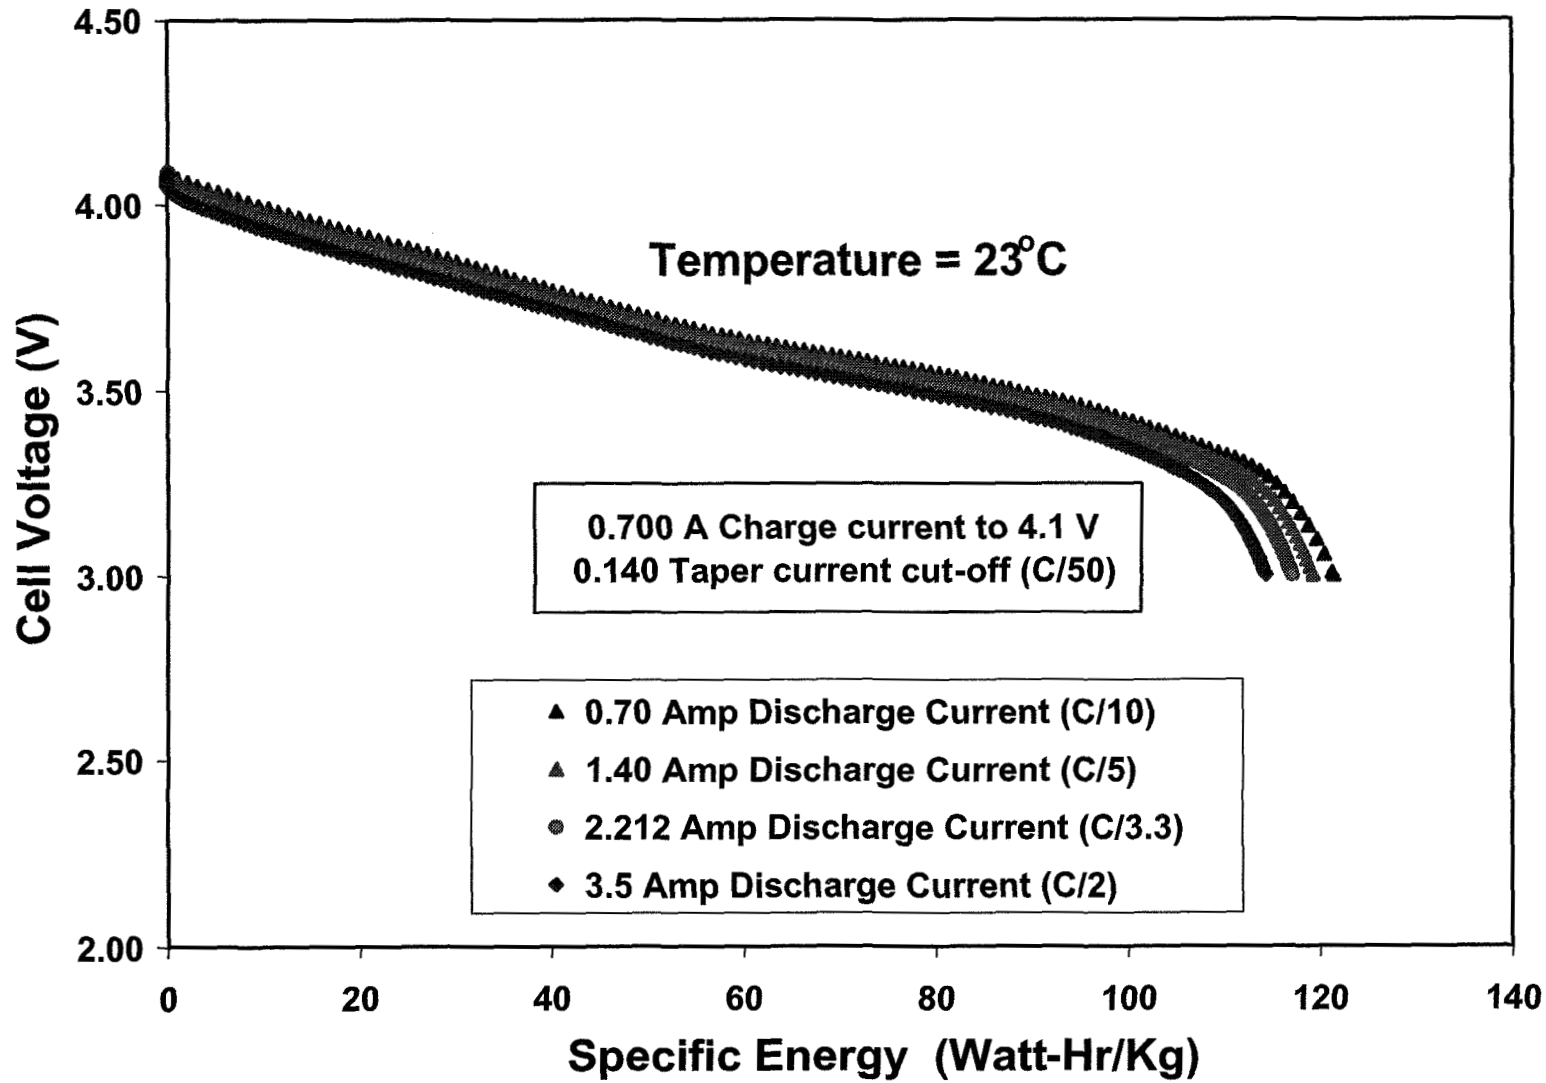

Low Temperature Discharge

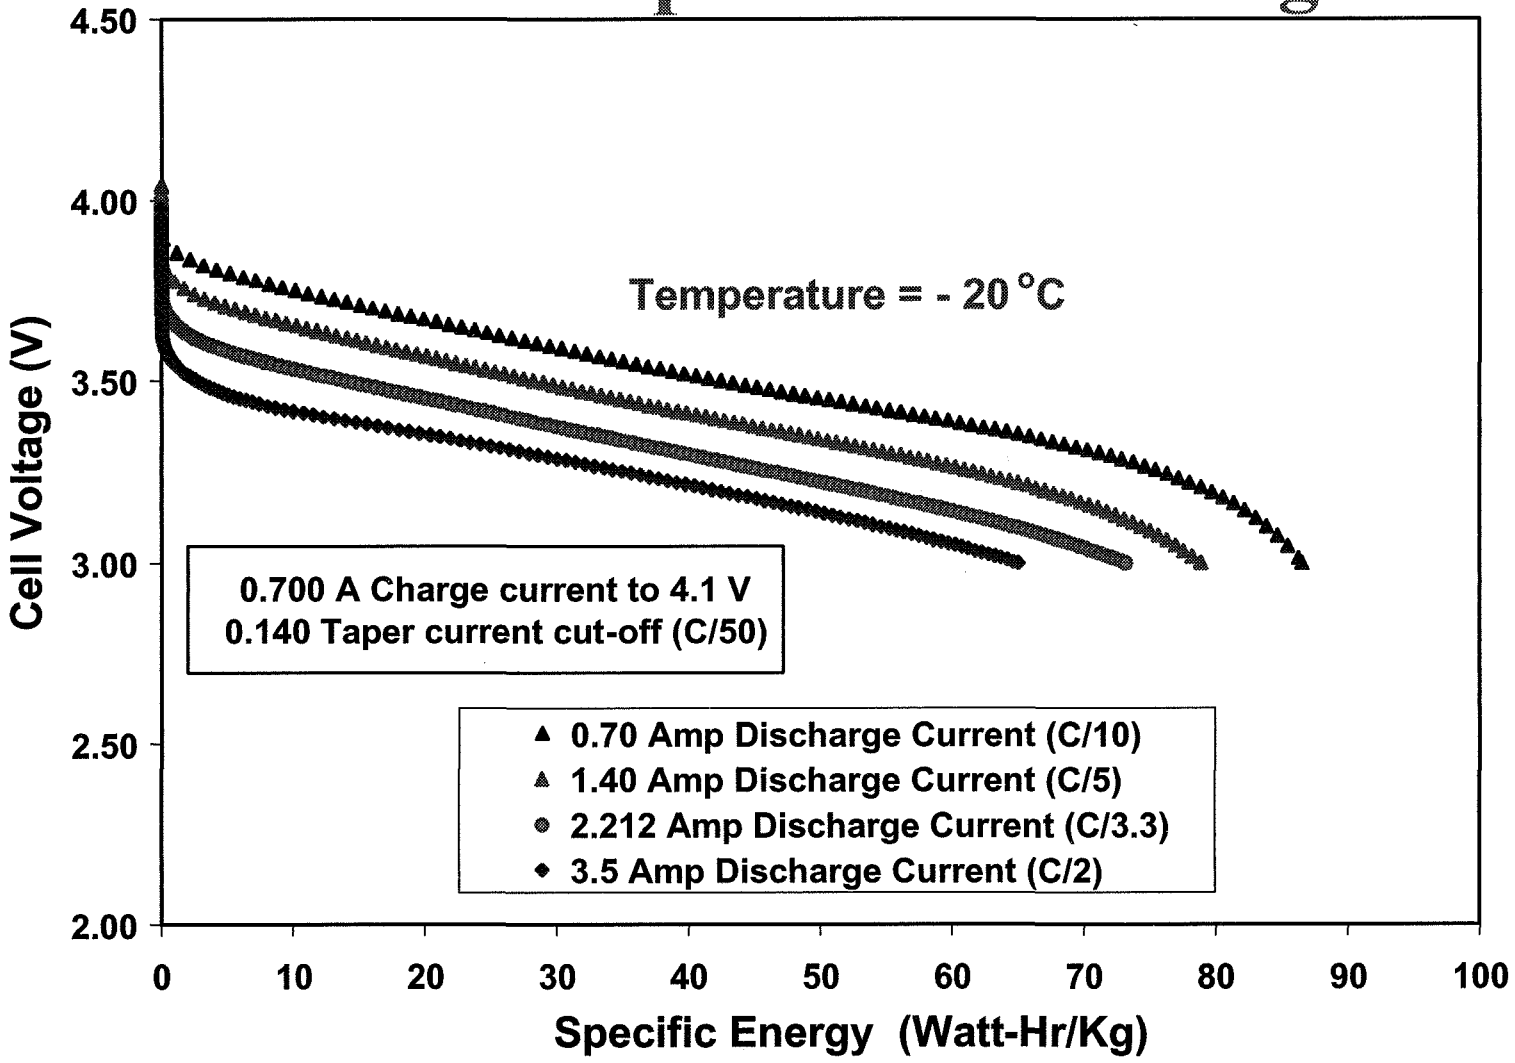

Low Temperature Charge

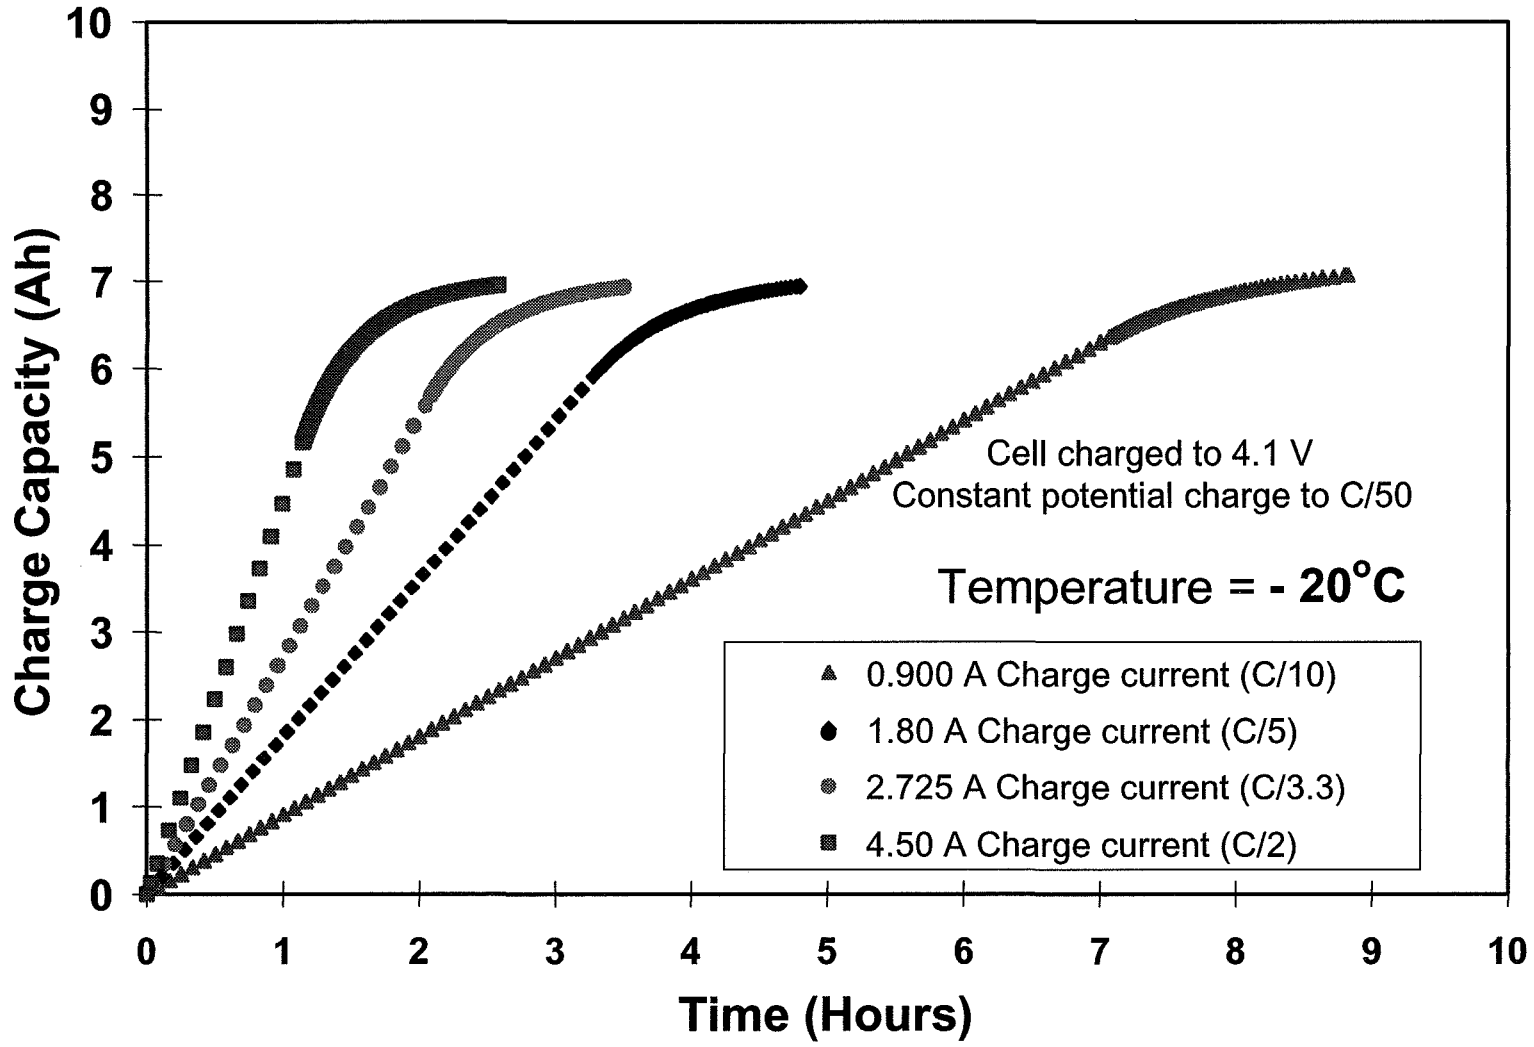

Charge Characteristics of a 25 Ah cell

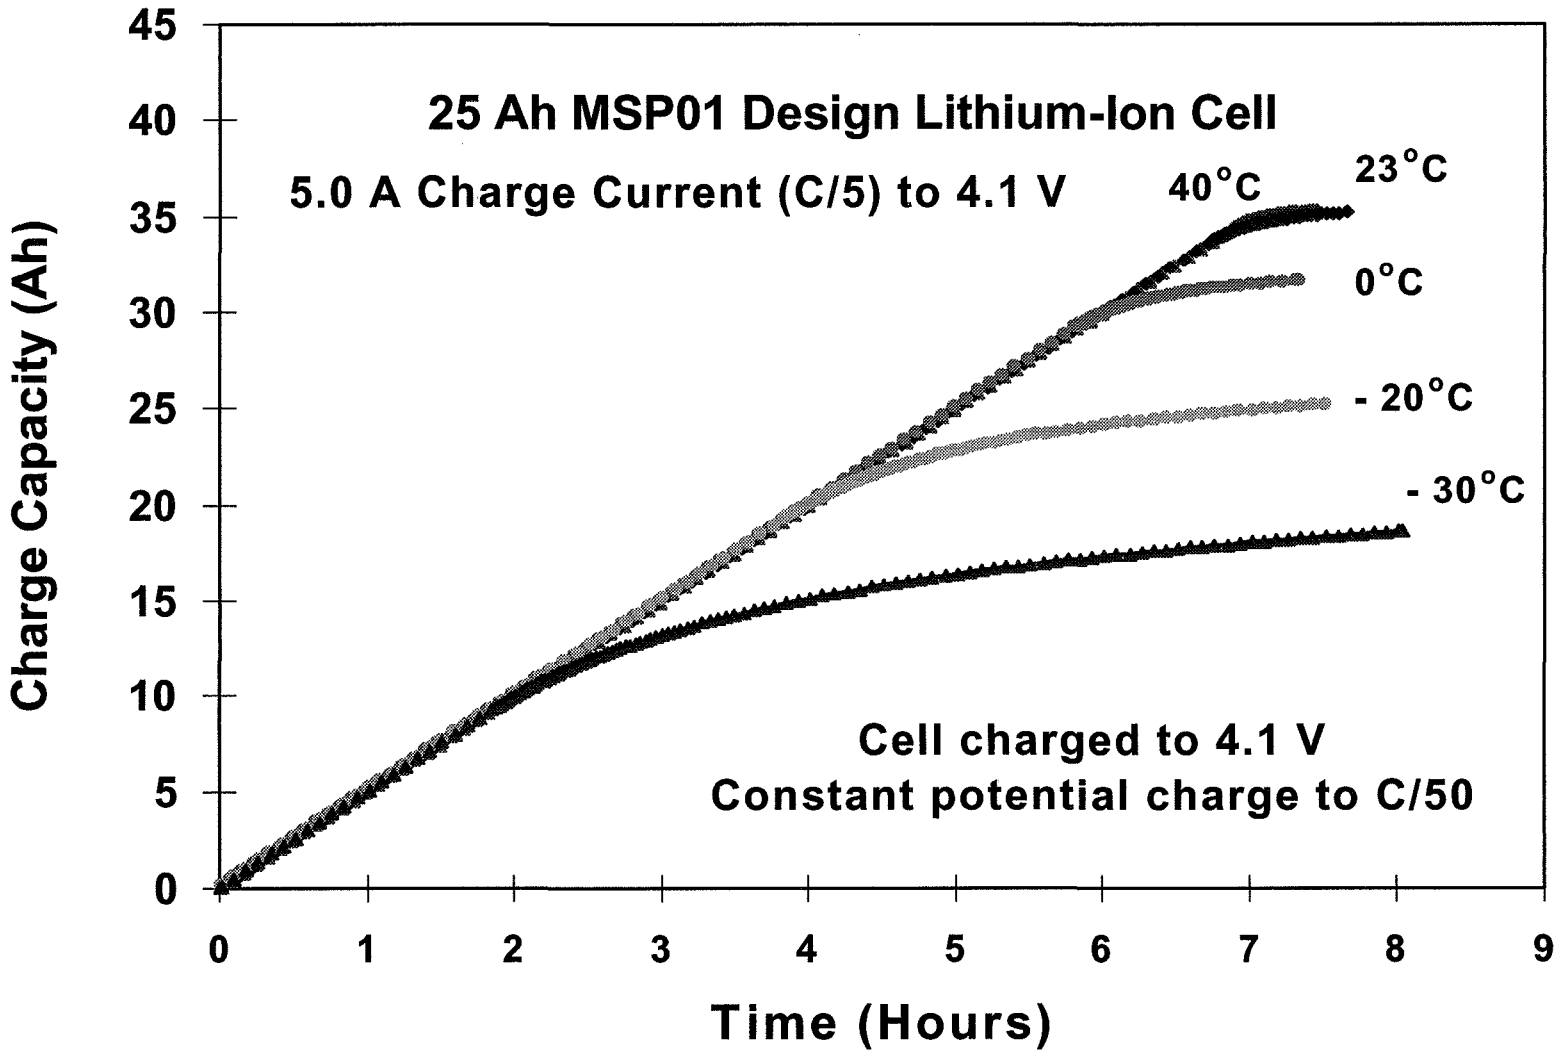

Storage Characteristics

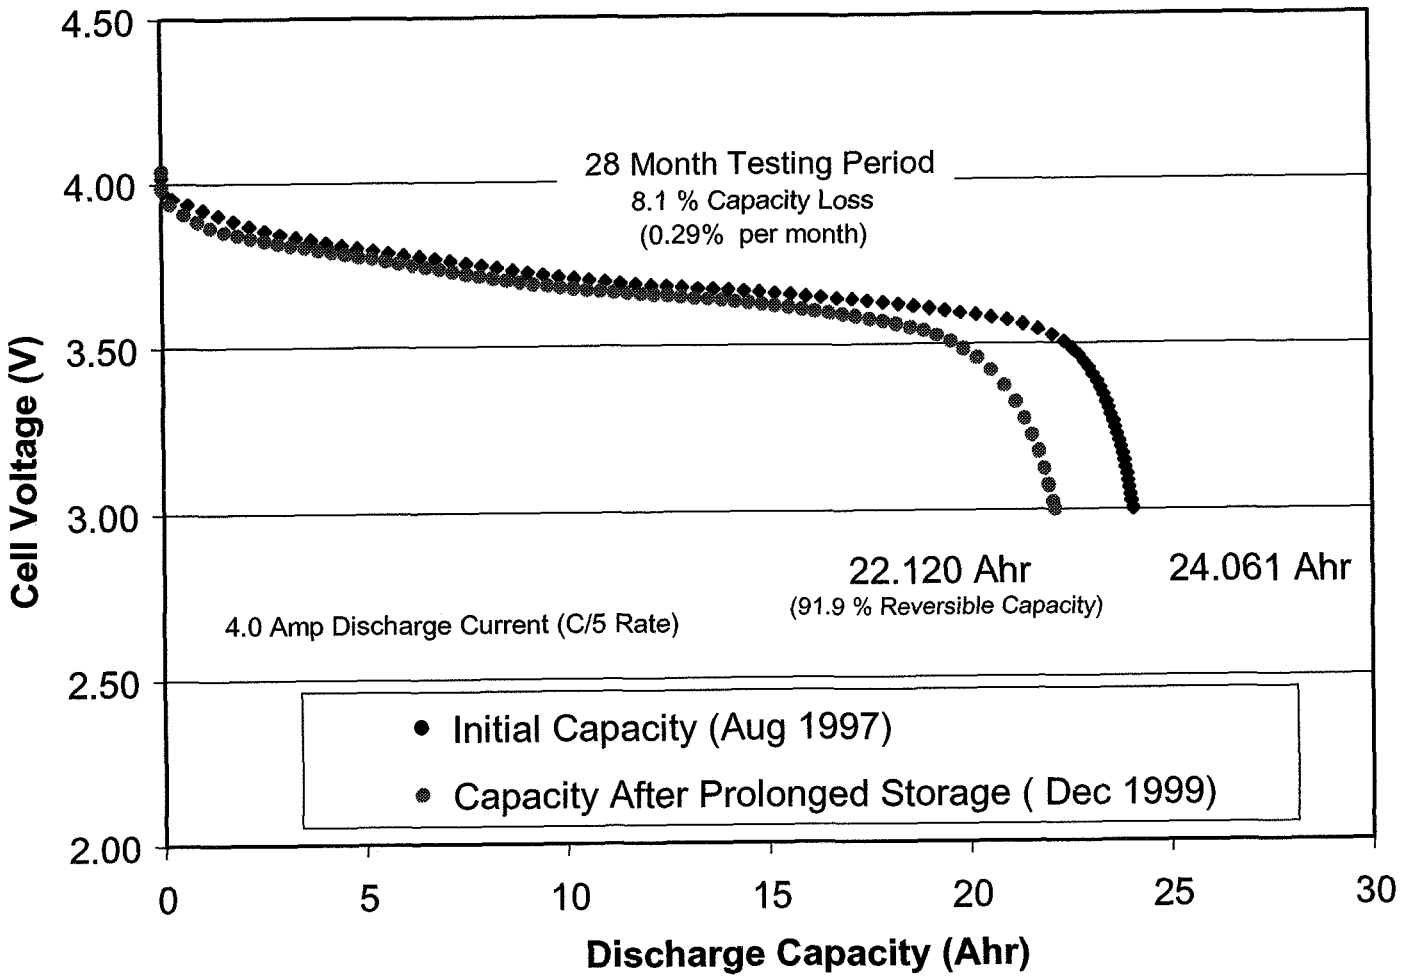

Storage Characteristics

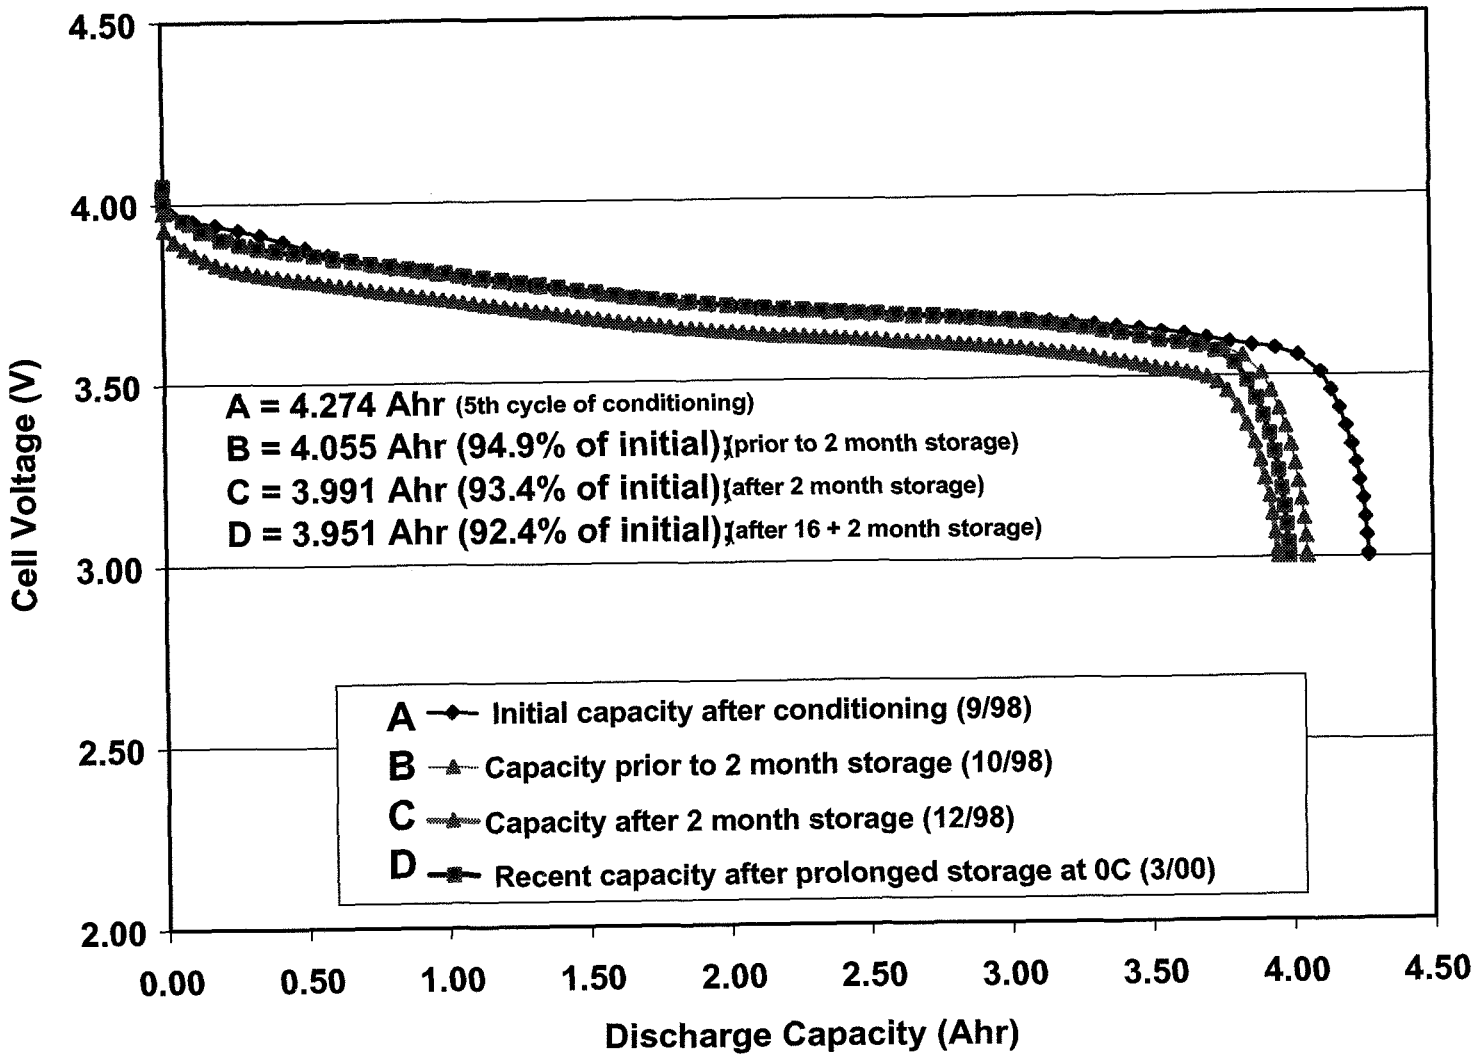

V/T Curves of Li Ion Cells

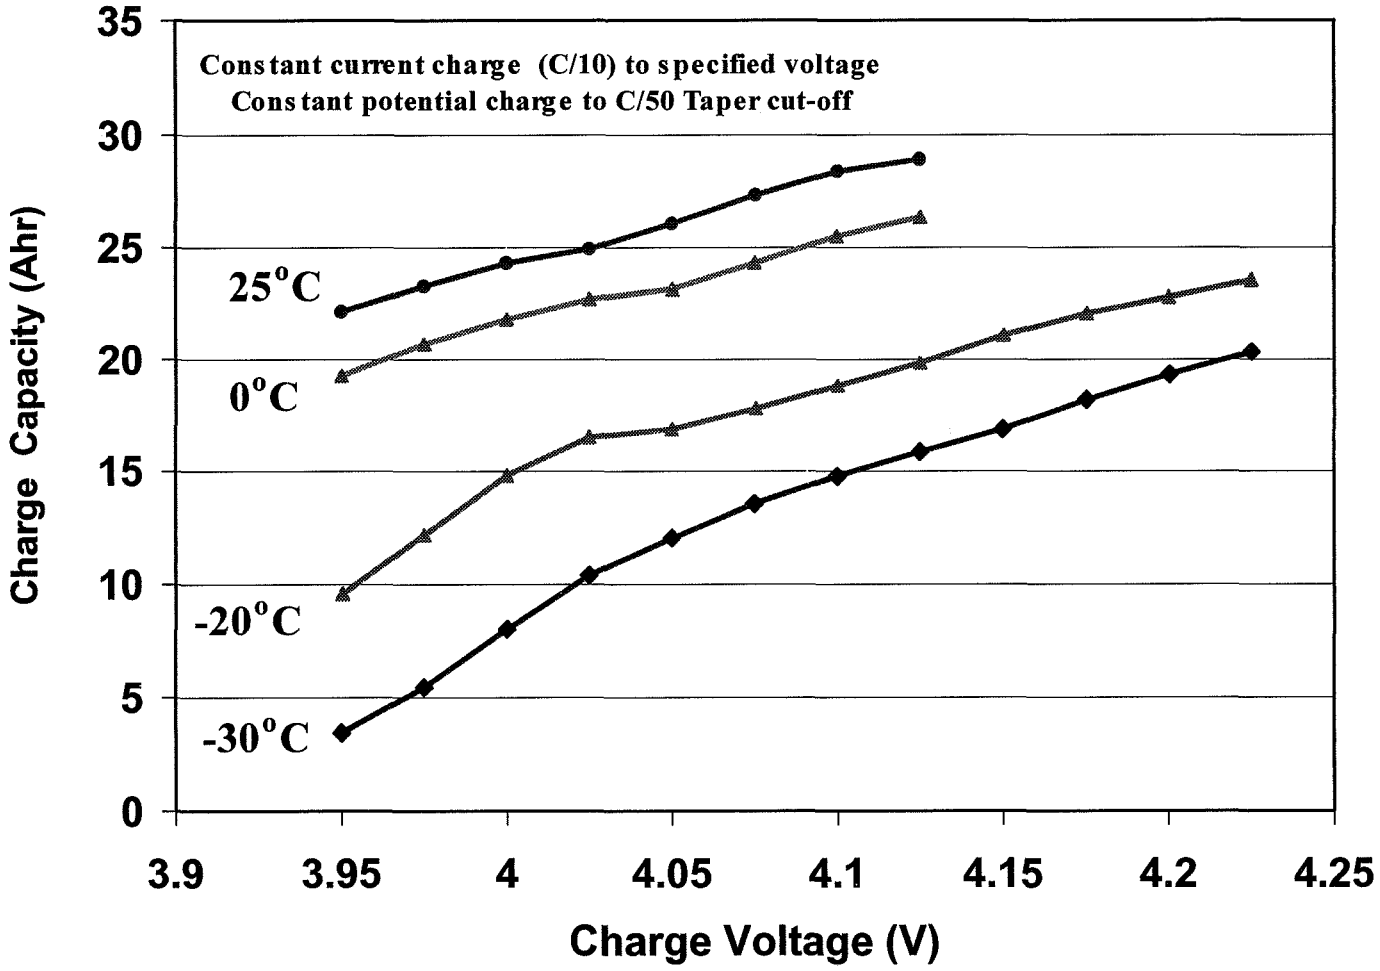

- Are higher charge voltages justified at lower temperature ?
- Need to define specific conditions under which lithium plating can occur (rate and system dependent).

Impedances in a Li Ion Cell

EIS of a Li Ion Cell

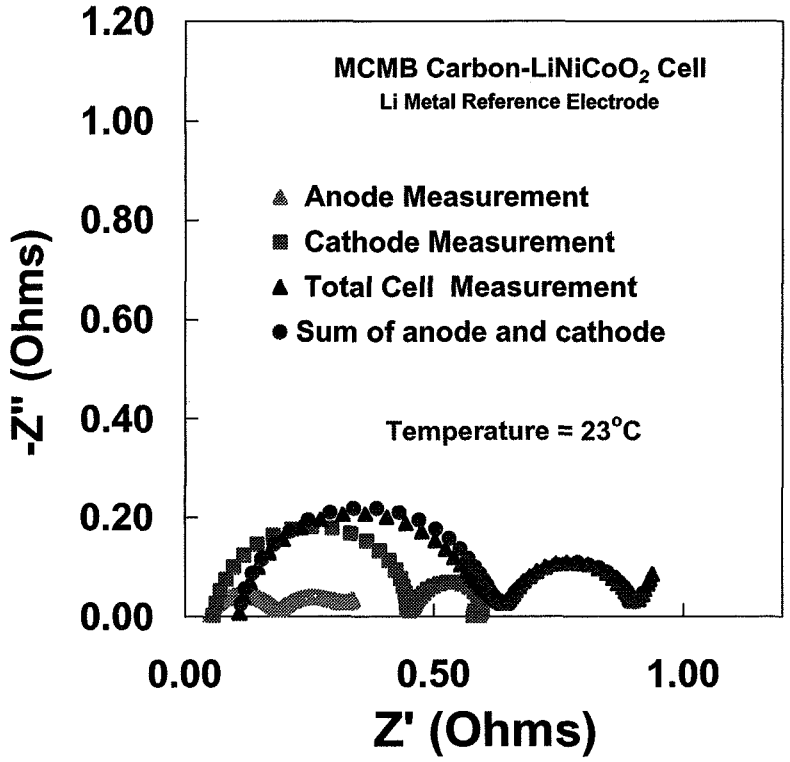

DC Polarizations in Li Ion Cell

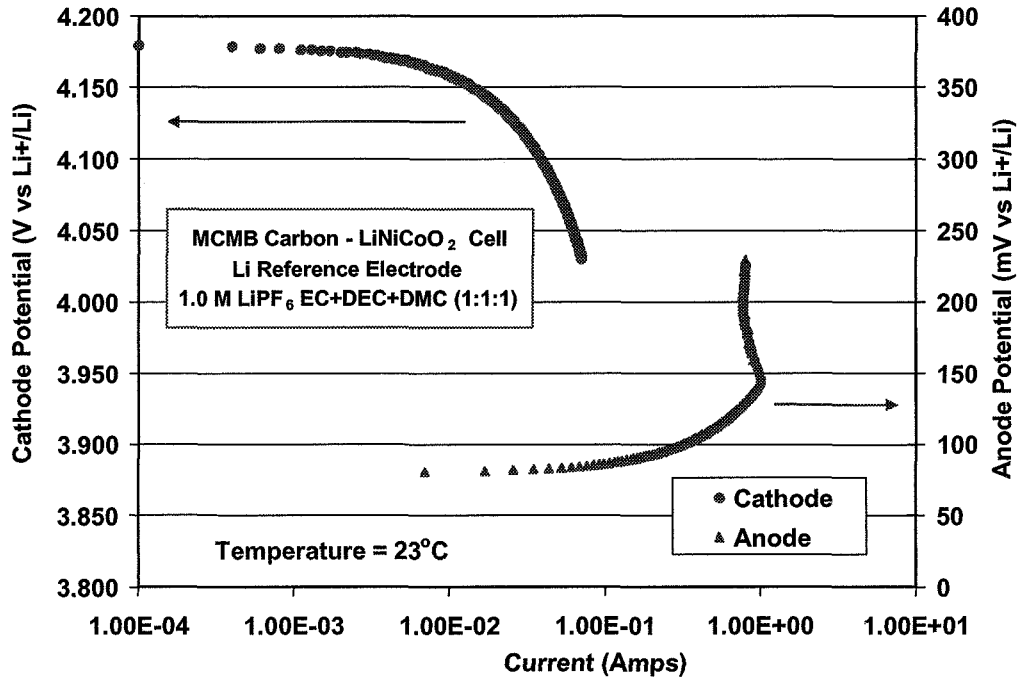

Cycling (100%DOD) at 25°C

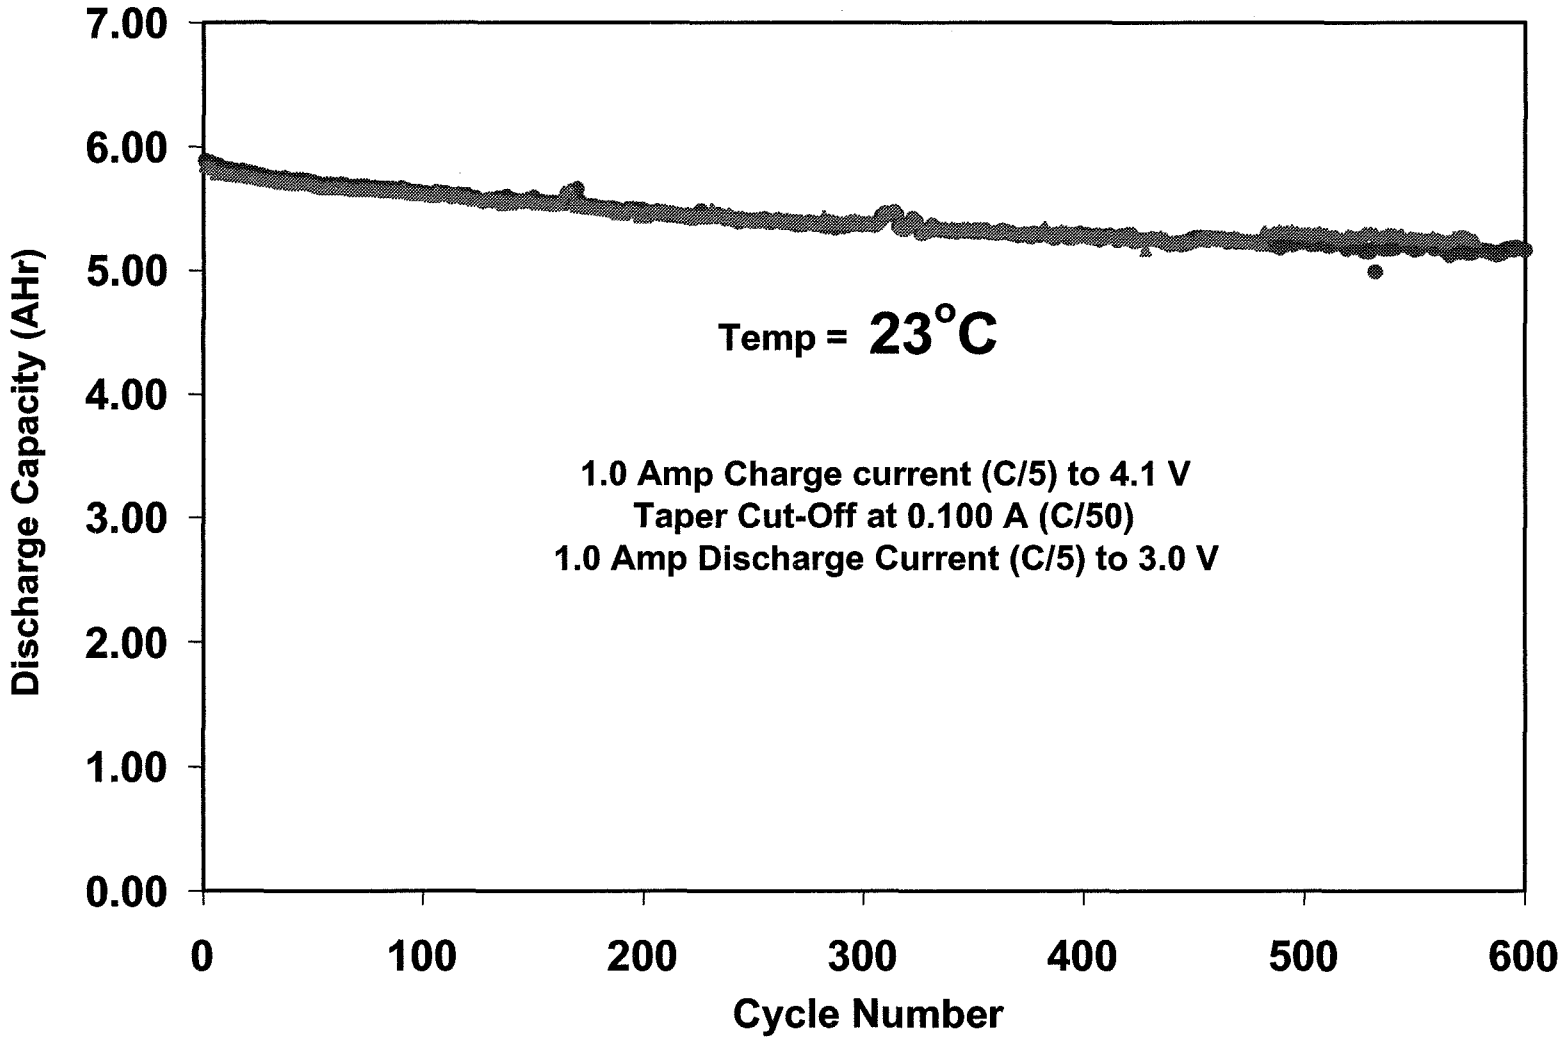

EIS During Cycling

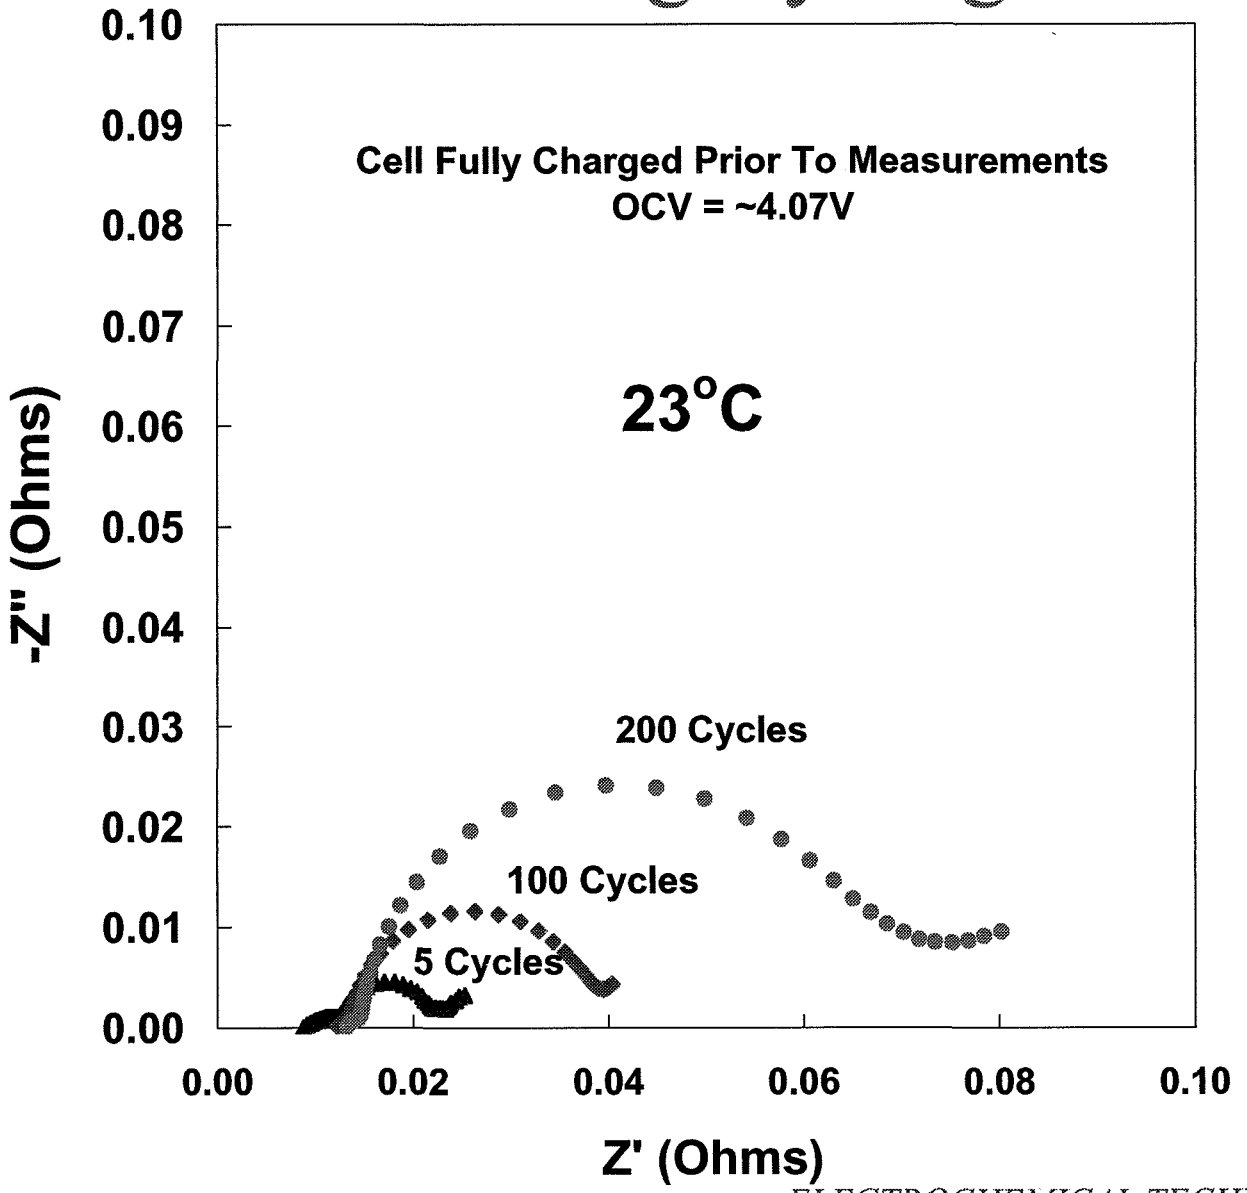

Variable Temperature Cycling

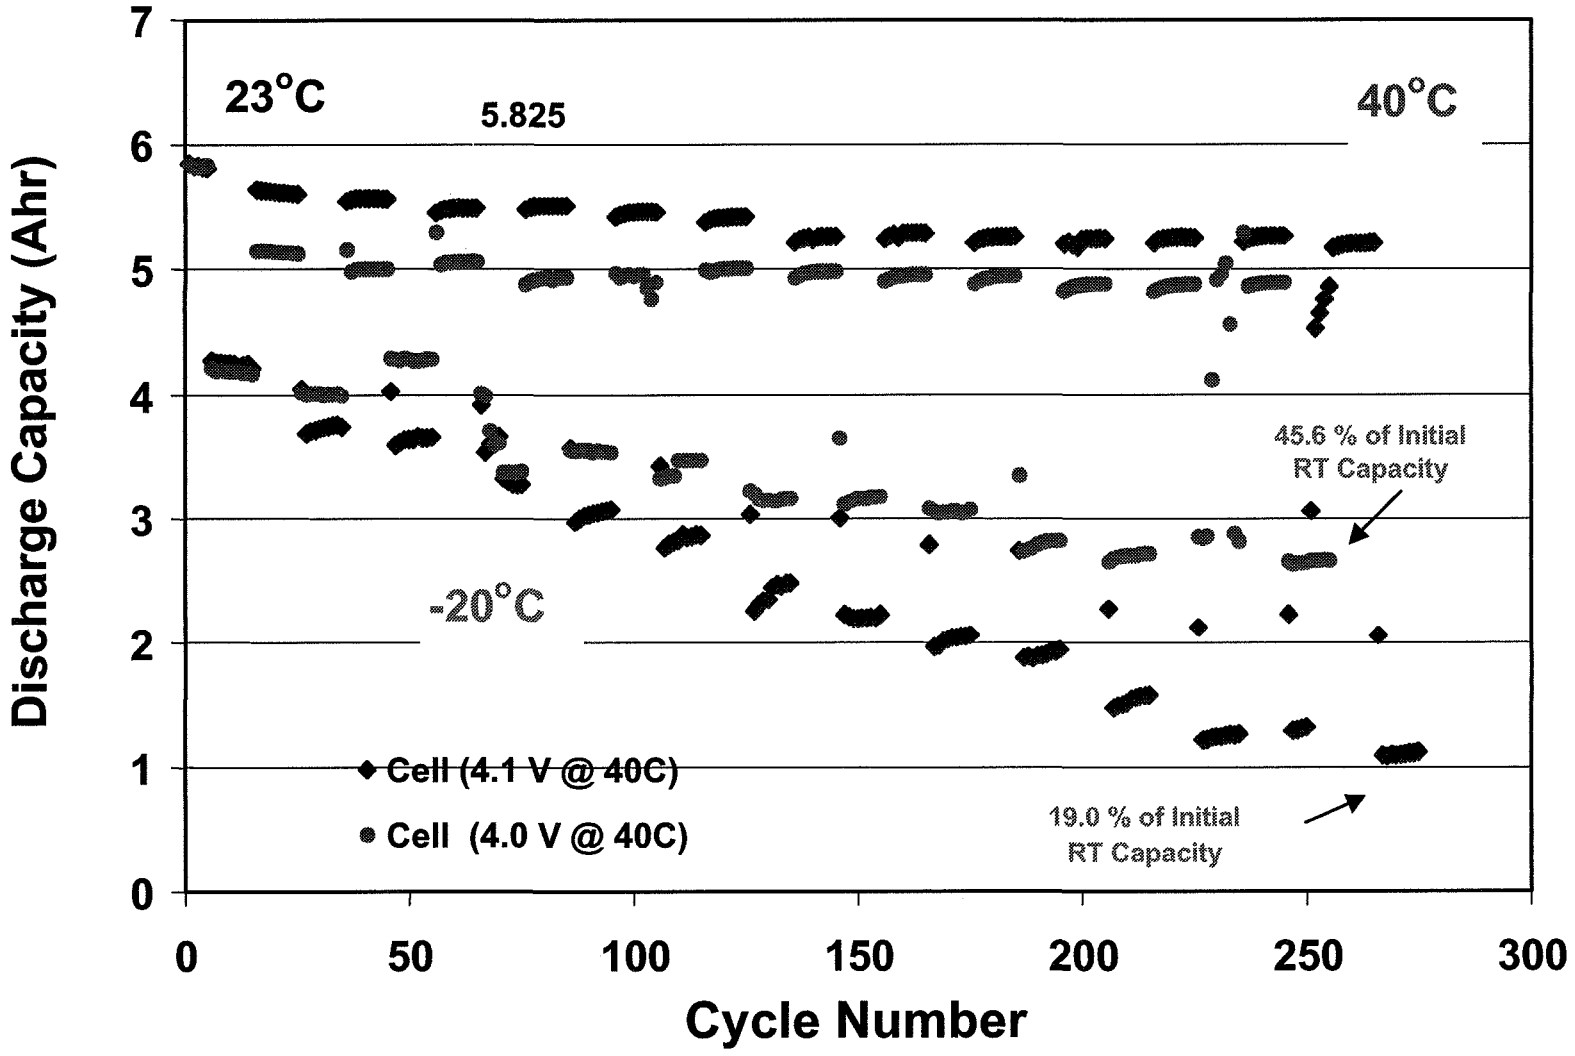

EIS During Variable Temperature Cycling

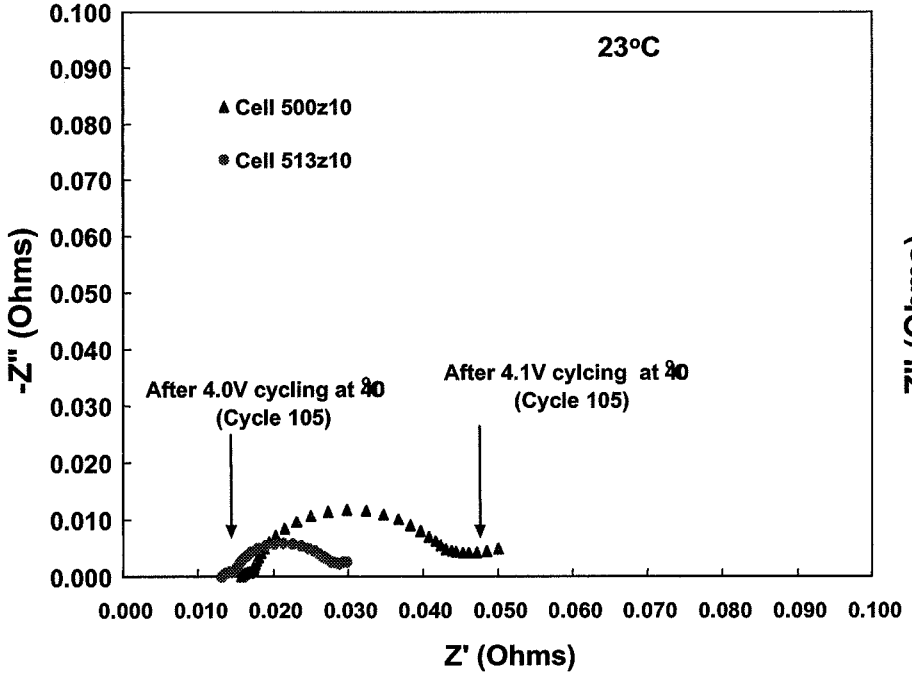

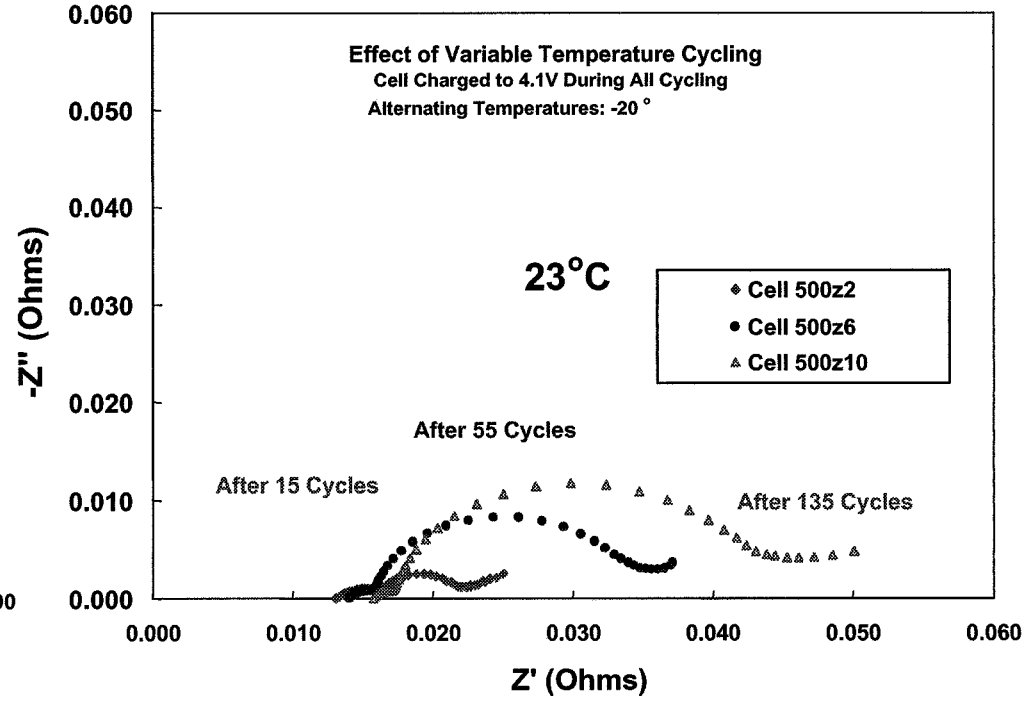

Heat Generation Rates on Discharge

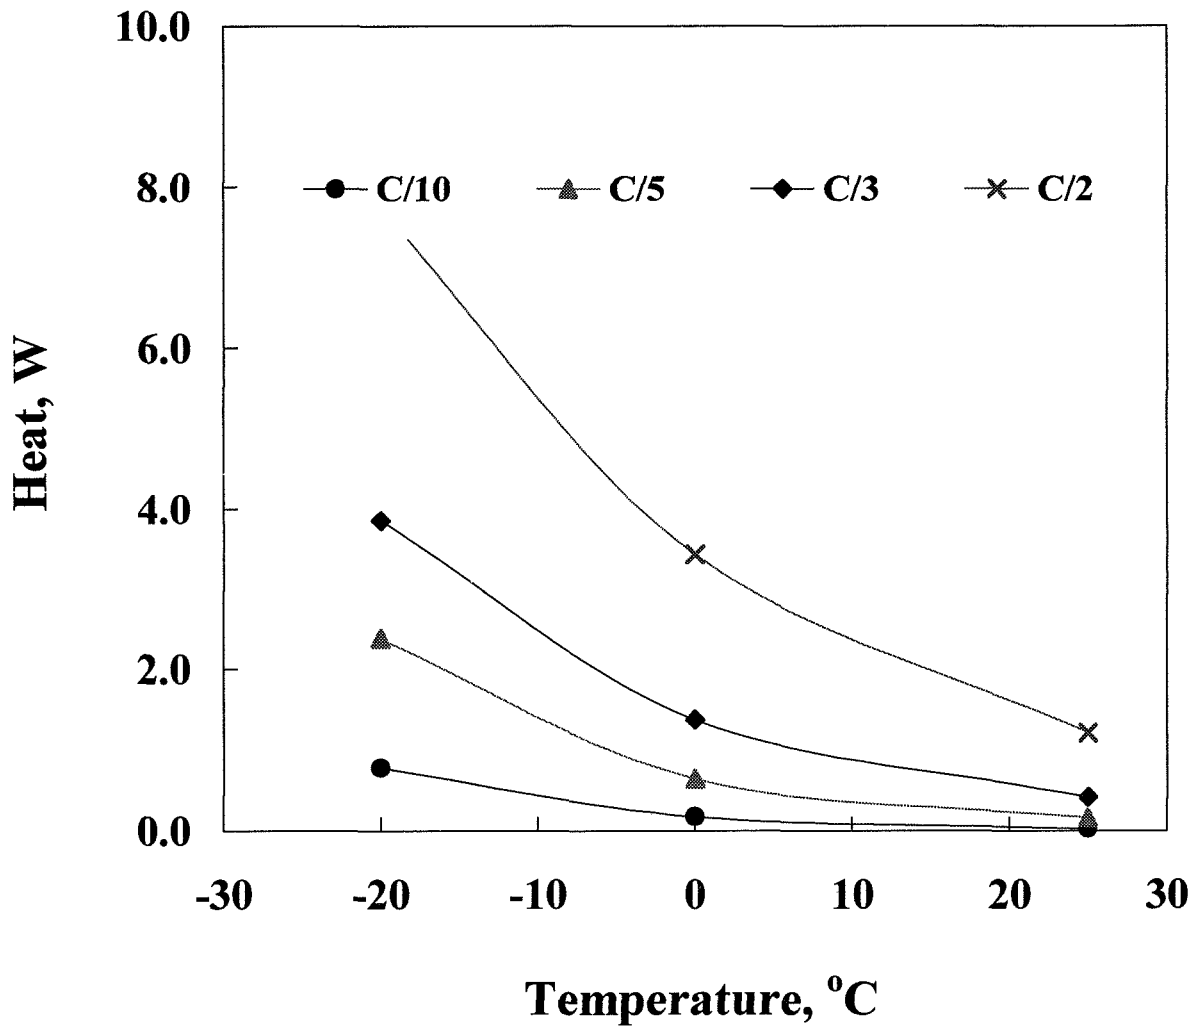

Safety Events at JPL

- Li Ion Cell Venting upon Inadvertent External short (20-35Ah)
  - No injuries to personnel
  - No damage to equipment
- Li Ion Cell Venting on Extended LT Cycling (5 - 10 Ah)
  - No injuries to personnel
  - No damage to equipment
- Venting of a pouch (Polymer) cell
  - No damage to equipment

Short Circuit Incident
History of the Cell

- 2 Month storage in Open Circuit.
- 10 Month on OCV stand.
- Extended storage at 0°C
- Mars Mission Profile
- AC impedance *

Storage

25 Ahr Generation I Lithium-Ion Cells

	Initial	Two Month Storage							Ten Month Storage							
Cell Number and Storage Mode	Initial Capacity (After Cond.)	Capacity Prior To Storage (Ah)	Stored Capacity	Cell Voltage after 10 Month Storage	Capacity After Storage (Ah) 1st Disch.	Capacity After Storage (Ah) 5th Disch.	Capacity Loss (% of stored capacity)	Rever. Capacity (%)	Capacity Prior To Storage (Ah)	Stored Capacity	Cell Voltage after 10 Month Storage	Capacity After Storage (Ah) 1st Disch.	Capacity After Storage (Ah) 5th Disch.	Capacity Loss (% of stored capacity)	Rever. Capacity (%)	Total Reversible Capacity After 12 Months (% from Initial)
151 (0°C and 50 % SOC)	27.879	27.609	14.000	2.565 V	0.000	27.327	100	98.976	26.972	14.000	0.578 V	0.000	27.602	100	102.337	99.006
152 (40°C and 50 % SOC)	28.749	28.021	14.000	3.308 V	1.968	27.479	85.943	98.065	27.918	14.000	0.482 V	0.000	27.675	100	99.129	96.263
178 (0°C and 100 % SOC)	25.475	25.471	25.487	3.982 V	23.114	24.781	9.310	97.289	24.607	24.623	3.762 V	16.996	25.279	30.975	102.731	99.227
201 (40°C and 100 % SOC)	25.674	25.670	25.584	3.834 V	19.611	25.156	23.349	97.998	23.912	23.807	3.608 V	10.309	23.789	56.699	99.486	92.659

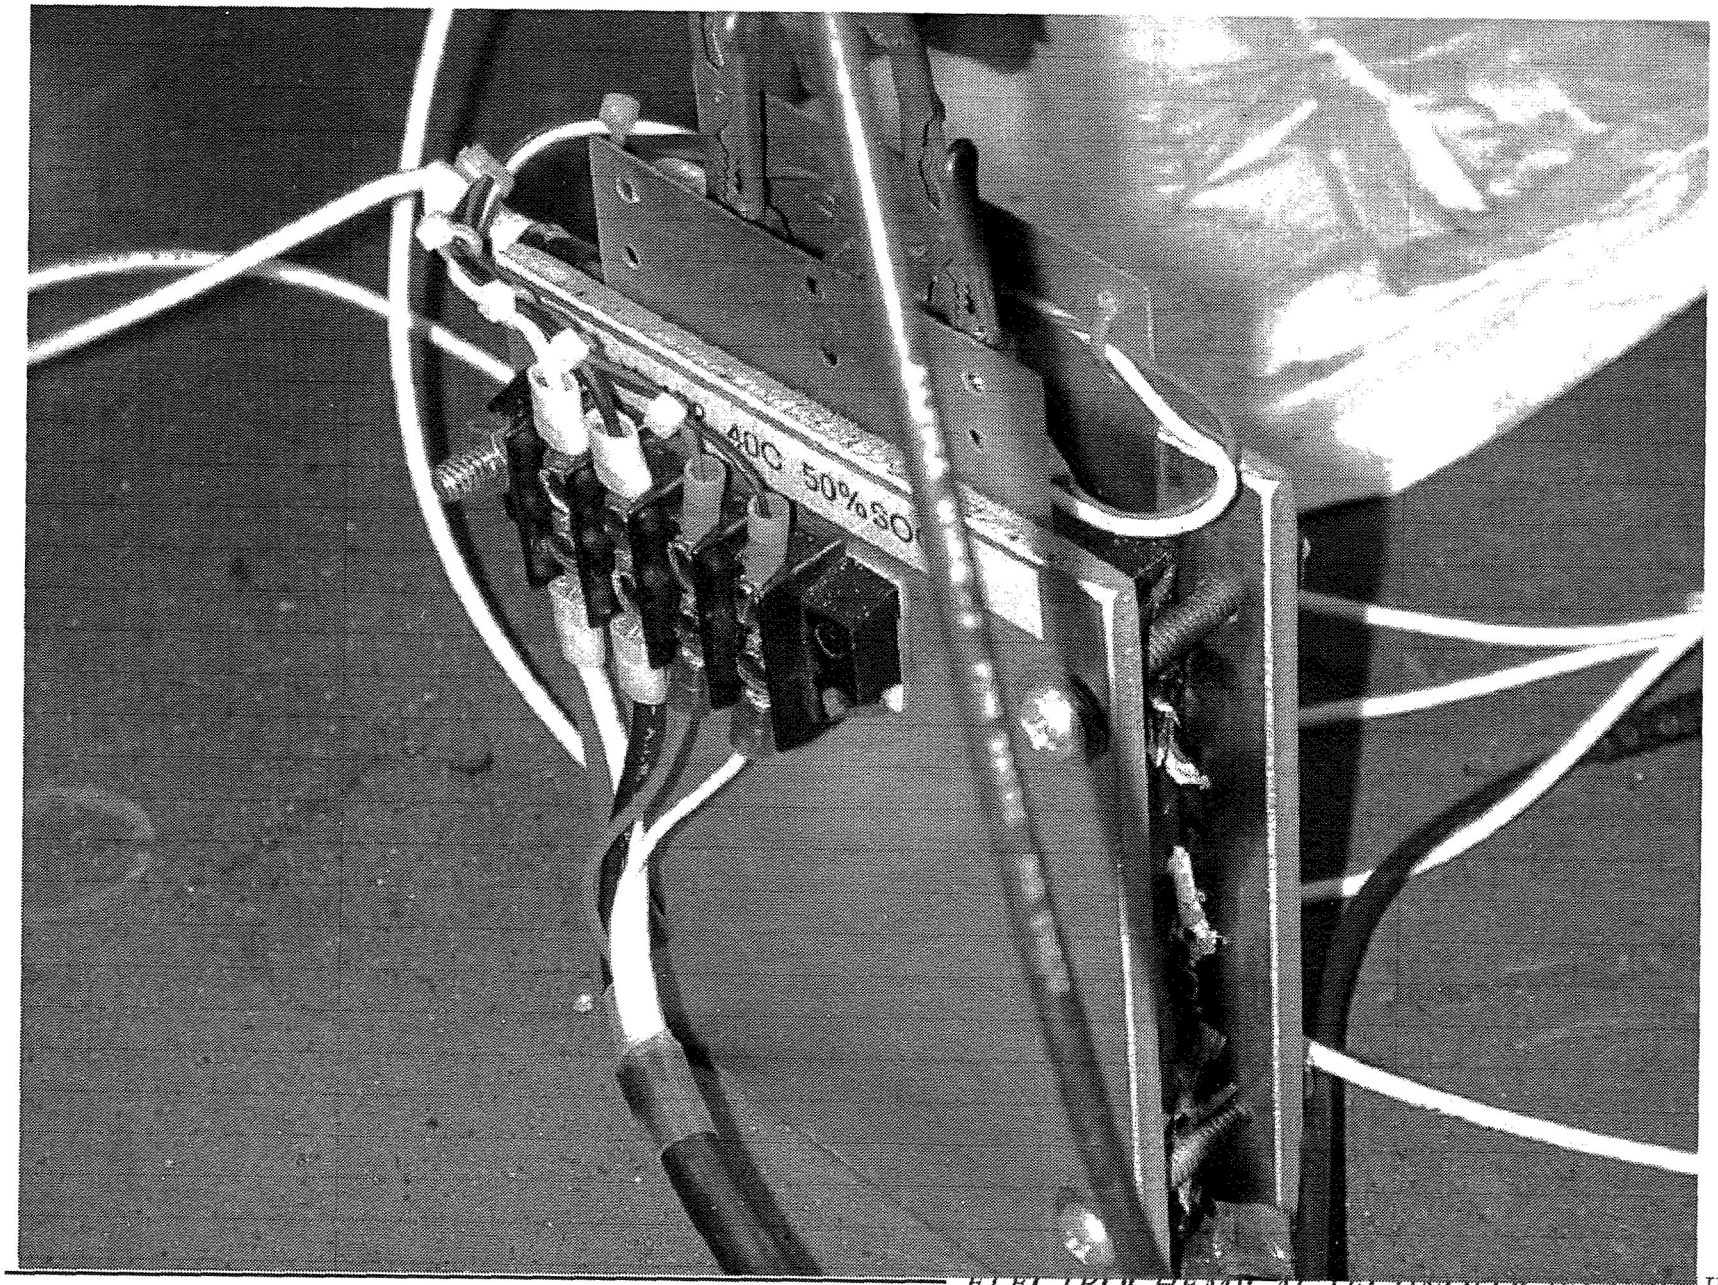
40C 50%SO

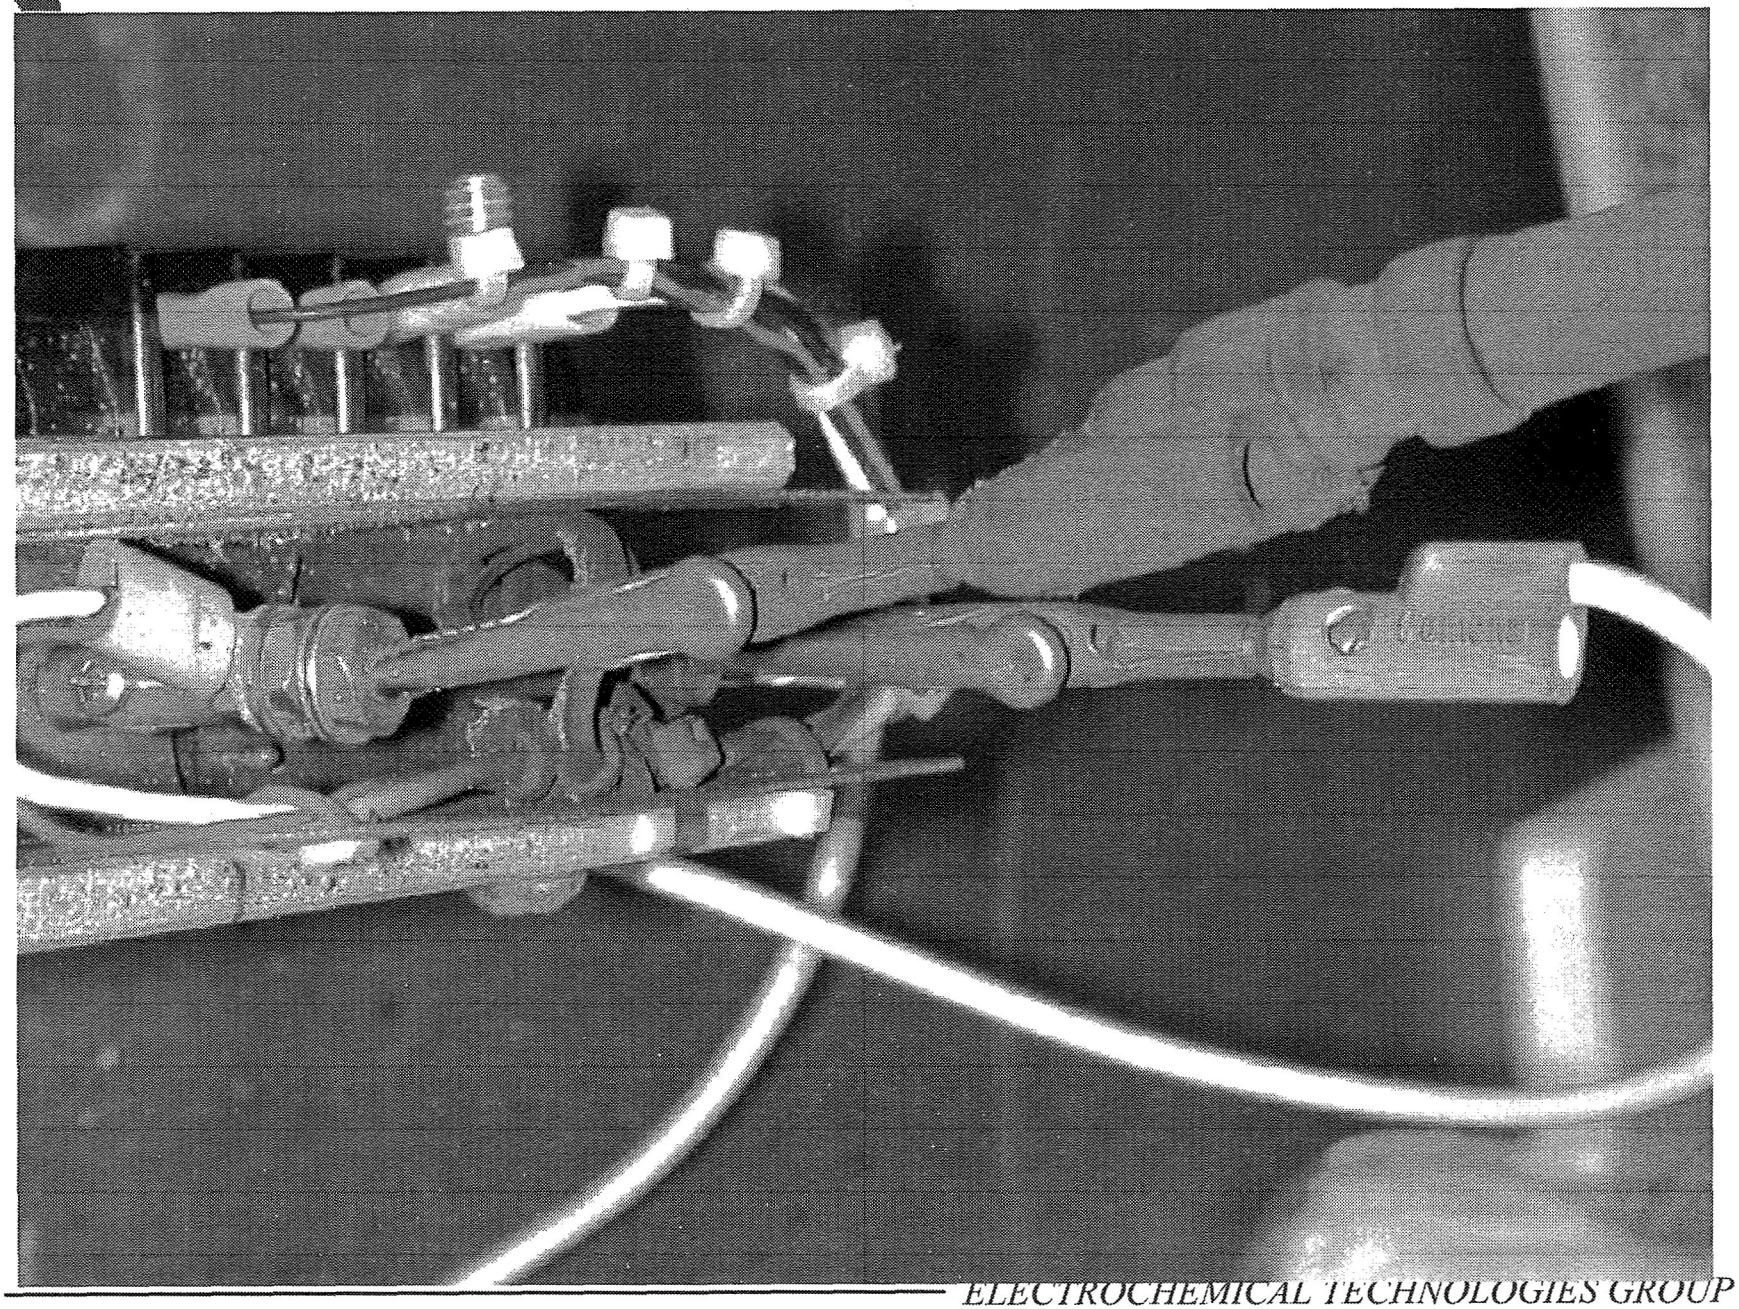

Summary

- Lithium ion cells developed under the DOD/NASA consortium were found to exhibit:
  - High specific energy (>120 Wh/kg) and High energy density (300 Wh/l)
  - Long cycle life (over 1000 Cycles)
  - Excellent low temperature performance(-20 C Operation)
  - Good storage characteristics
- Three minor safety incidents occurred over a period of three years of testing more than five hundred lithium ion cells of 1 -35 Ah sizes.
- Further improvements in cell design will minimize such safety events.

The author has respectfully requested that this paper be withheld from publication in these proceedings.

On the Behavior of Lithium Ion Batteries During Short Circuit and Extended Overcharge

Randolph A. Leising,[a] Marcus J. Palazzo,[a]
David M. Spillman,[a] Esther S. Takeuchi,[a]
and Kenneth J. Takeuchi[b]

[a]Wilson Greatbatch Ltd., Clarence, NY
[b]SUNY at Buffalo, Department of Chemistry, Buffalo, NY

527/ep/mi/ffp

20011183267
538254
33695

Introduction

- The safety of lithium ion batteries under abusive conditions is a primary concern of battery manufacturers and their customers.
- Placement of thermocouples within a battery will provide more accurate information on the internal temperature during these reactions.
- Short circuit conditions or extreme overcharge of lithium ion batteries may result in high temperatures, and can lead to violent reactions under some circumstances.

Introduction

- External short circuit tests were conducted on medium sized prismatic batteries while the voltage, current, case temperature, and internal temperature were monitored and recorded.
- The rate of overcharge was systematically varied for batteries having the same cell balance.
- Extended overcharge tests were conducted on medium size prismatic batteries which contained thermocouples that were positioned within the wound electrode stack.

Introduction

- The effects of cell balance, i.e. ratio of lithiated cobalt oxide to carbon weight, on the overcharge reaction was investigated.
- Partially delithiated cathodes were placed into batteries containing non-lithiated anodes and subjected to an extended overcharge test.
- Several mechanisms may contribute to lithium ion battery instability during abusive conditions.

Experimental

- Battery Materials:
  - Cathode: $LiCoO_2$
  - Anode: Graphite
  - Electrolyte: 1.0 M $LiPF_6$ in alkyl carbonates
  - Separator: Polyethylene
- Battery Design:
  - Nominal capacity: 1.5 Ah
  - Stainless steel case
  - Hermetically sealed
  - Internal (sealed with epoxy) and external Type -K thermocouples

External Short Circuit Test

- Conducted on medium size prismatic batteries at room temperature in still air within an explosion proof chamber.
- Electrode weight ratio was 2.8, and batteries were charged to 4.10 volts prior to test.
- External circuit resistance was approximately six milliohms. The battery voltage, current, case temperature, and internal temperature were recorded.

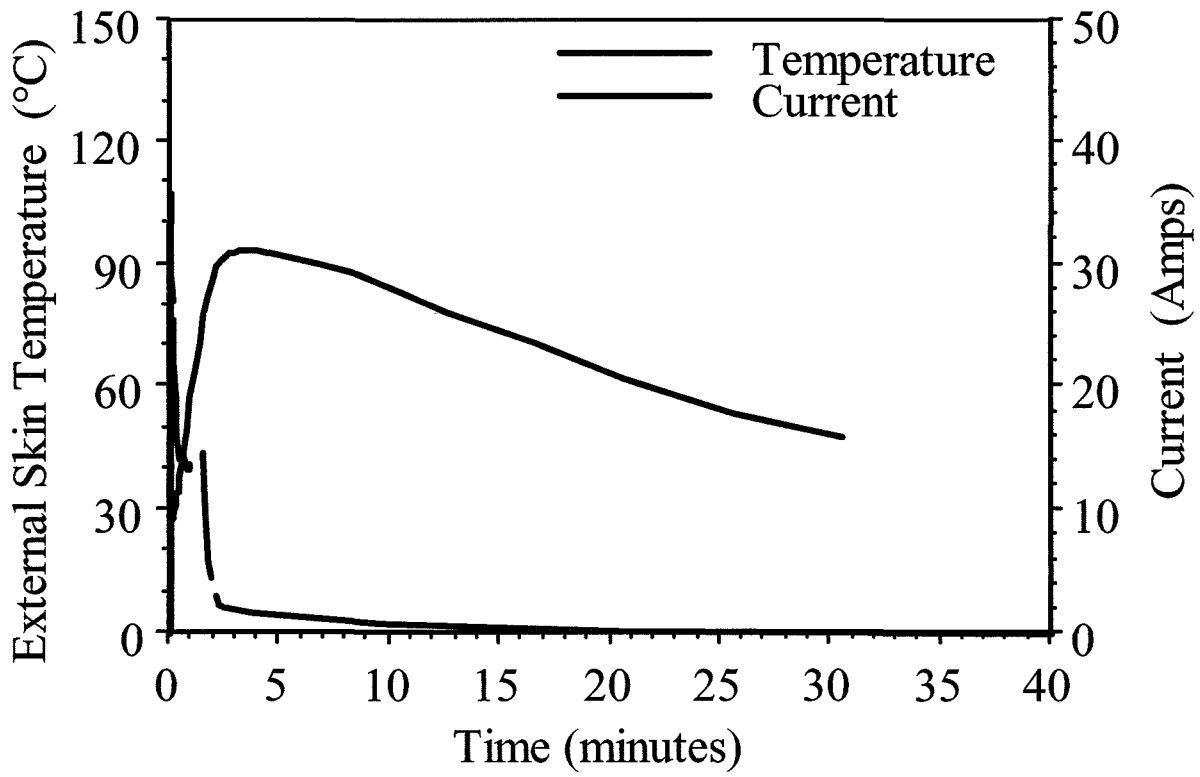

Figure 1: External case skin temperature during 10 mž short circuit test.

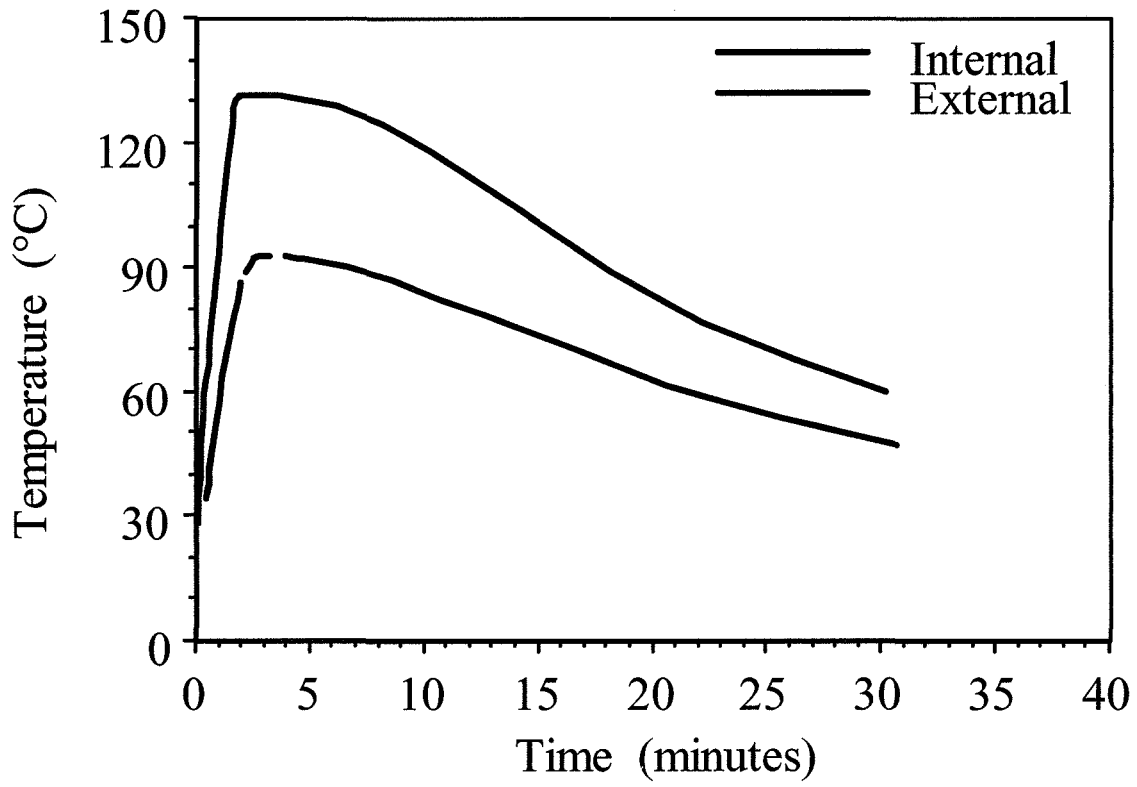

Figure 2: Cell temperature during 10 mž short circuit test.

Short Circuit Test Summary

- The current peaked at about 36 amps (24C rate) within 0.2 seconds when the external short circuit was applied. The battery voltage simultaneously decreased from 4.10 volts to less than 0.25 volts.
- The current stabilized at 14 to 15 amps during the first 1.5 minutes, sharply decreased to about two amps, and then slowly decayed thereafter.

Short Circuit Test Summary

- The external case temperature increased to between 94 and 109°C within two minutes, while the internal temperature of the battery increased to about 132°C at a faster rate.
- The polyethylene separator fused, and greatly reduced the short circuit current.
- The batteries remained hermetic, and swelled only slightly.
- Placing thermocouples within the battery provided important temperature data.

Effect of Charge Rate on Overcharge Reaction

- Medium size prismatic batteries having a cell balance of 2.8 were outfitted with external thermocouples, charged to 4.10 volts, and subjected to an extended overcharge test in an explosion-proof chamber.
- Batteries were tested at rates of 150 mA, 300 mA, 525 mA, and 1.5 amps, i.e. C-rates of about 0.10, 0.2, 0.35, and 1.0, respectively.

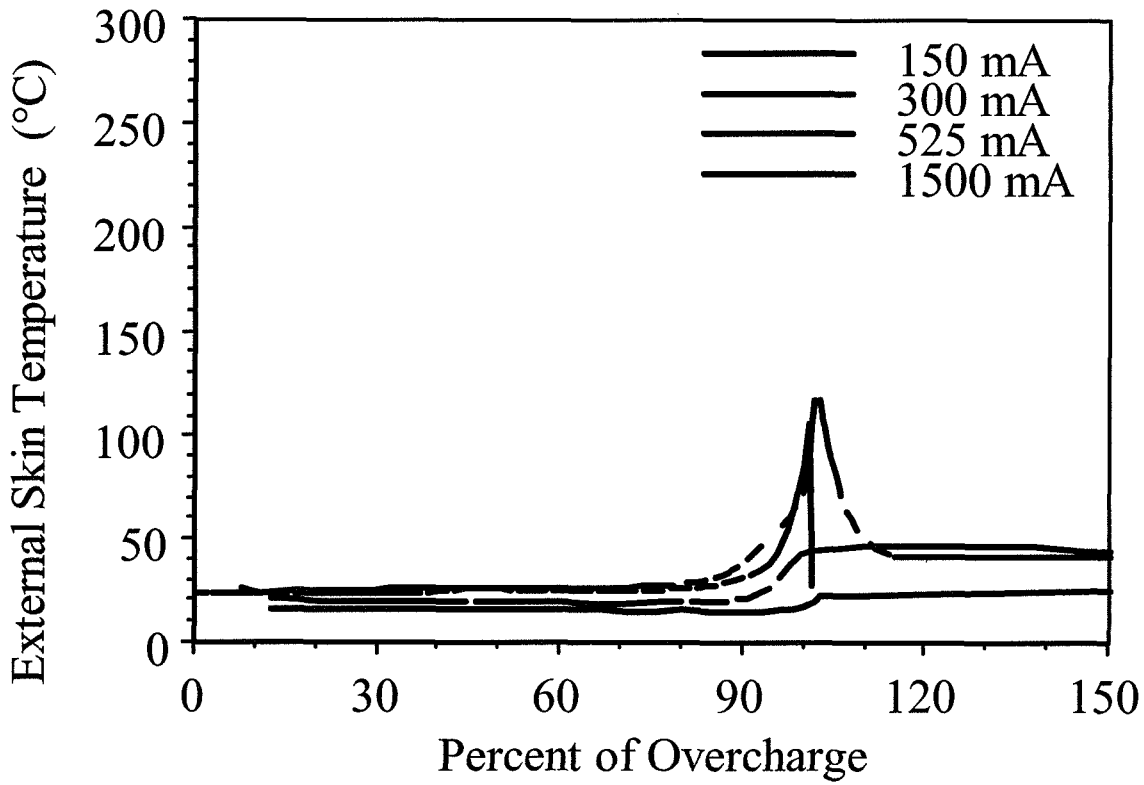

Figure 3: External case skin temperature at various overcharge rates.

Summary of Charge Rate Effect on Overcharge Reaction

- External case temperature remained constant until >75% overcharge.
- At higher charge rates, the external case temperature was observed to increase at lower states of overcharge. The highest temperature was observed after full delithiation of the cathode.
- Under lower charge rates, batteries swelled but remained hermetic. Under a 1.5 amp charge rate, the battery ruptured.

Thermal Profile during Overcharge Reaction

- Medium size prismatic batteries having a cell balance of 2.8 were outfitted with internal and external thermocouples, and tested within an explosion proof chamber.
- Batteries were initially charged to 4.10 volts, and then subjected to an extended overcharge test at room temperature in still air. The overcharge rates were 525 mA, i.e. about C/3 rate, and 1.5 amps, i.e. 1C rate.

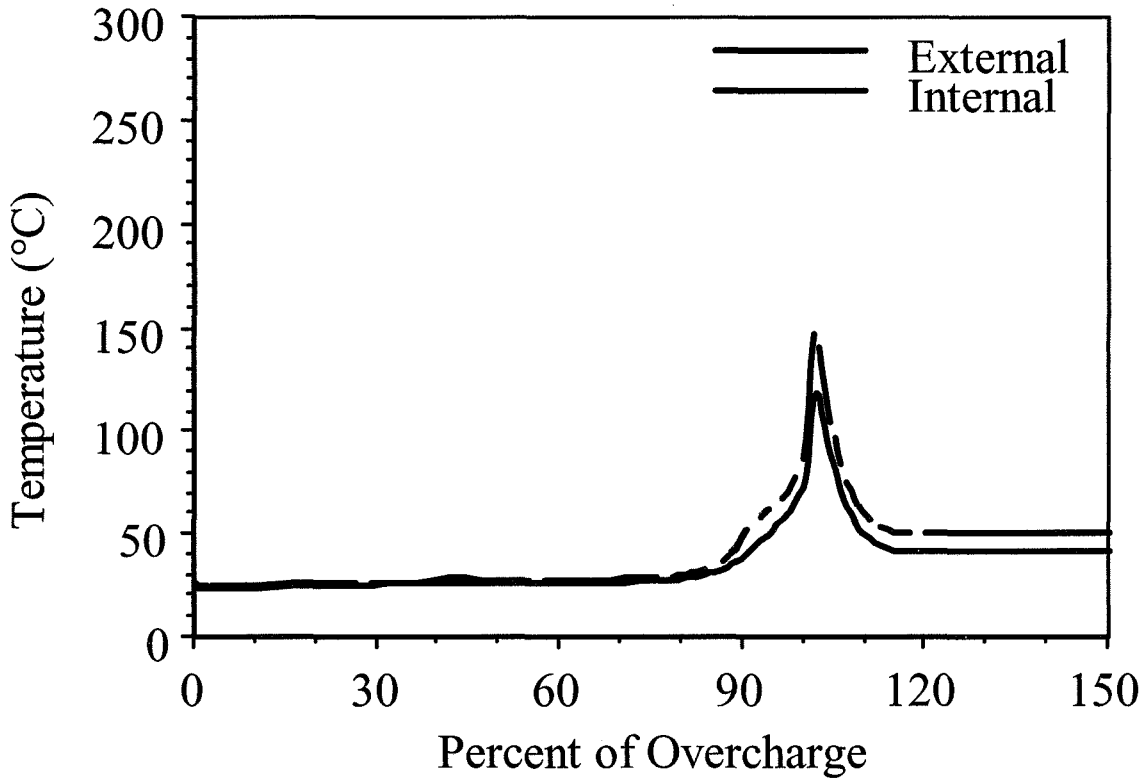

Figure 4: Cell temperature during 525 mA overcharge test.

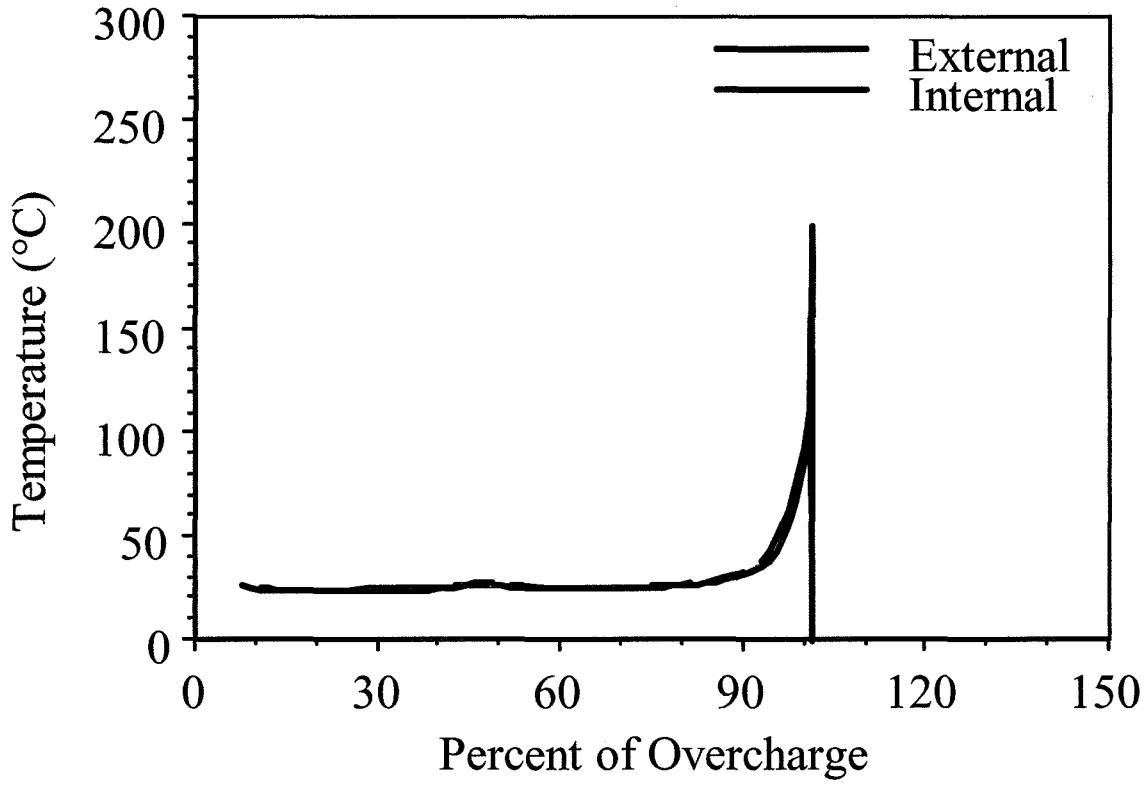

Figure 5: Cell temperature during 1.5 amp overcharge test.

Summary of Thermal Profile during Overcharge Reaction

- Batteries overcharged at 525 mA did not vent, exhibited a case temperature of about 120°C, and an internal temperature of about 148°C.
- Batteries overcharged at 1.5 amps ruptured, exhibited a case temperature of about 107°C, and an internal temperature of about 199°C.

Effect of Cell Balance on Overcharge Reaction

- Medium size prismatic batteries having a nominal capacity of 1.5 Ah were built with the following modifications in order to achieve an overall balance of about 2.3, 2.8, and 3.3:
  - Fixed cathode weight combined with varying anode weight.
  - Fixed anode weight combined with varying cathode weight.

Effect of Cell Balance on Overcharge Reaction

- Batteries were initially charged to 4.10 volts, and then subjected to an extended overcharge test at room temperature in still air. The test was conducted in an explosion proof chamber.
- The overcharge rate was 1.0 amp, i.e. C/1.5 rate, and the battery voltage and external case temperature were monitored throughout test.

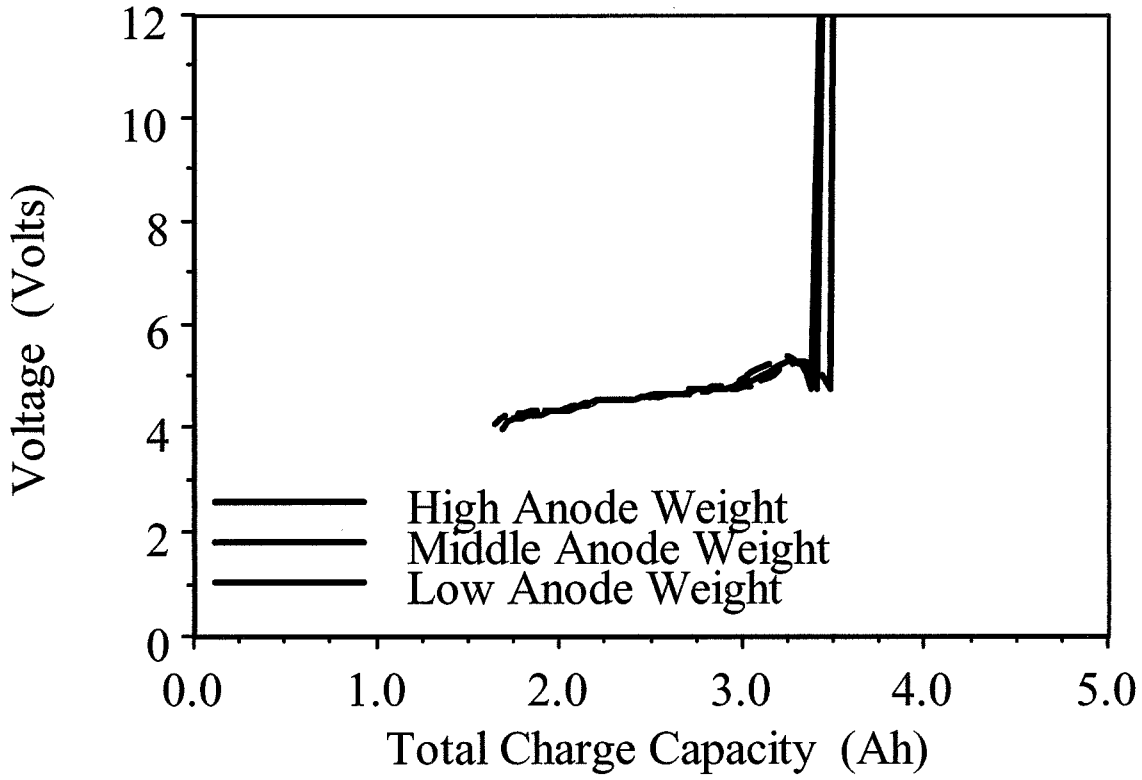

Figure 6: Overcharge test at 1 amp with anode weight varied.

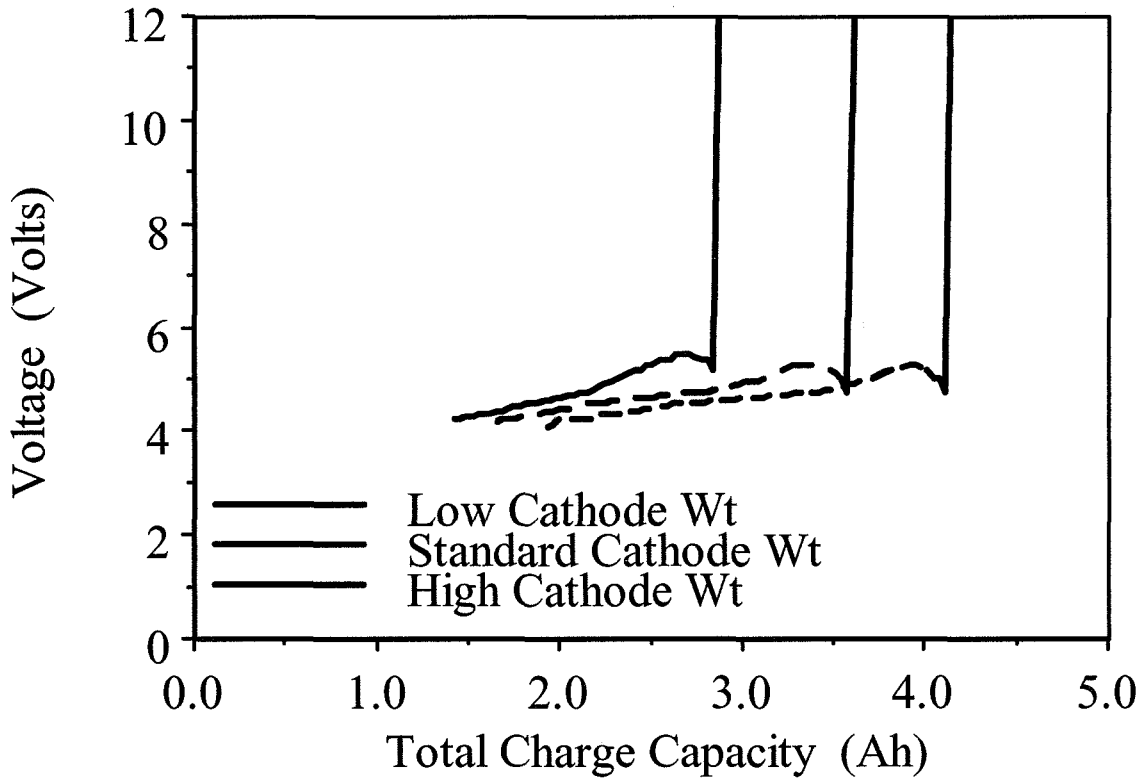

Figure 7: Overcharge test at 1 amp with cathode weight varied.

Summary for Effect of Cell Balance on Overcharge Reaction

- All batteries ruptured as a result of extended overcharge at 1.0 amp, i.e. C/1.5 rate.
- Batteries containing a fixed cathode weight exhibited an external case temperature of up to 105°C, and the rupture point was independent of the amount of anode material.
- Batteries containing a fixed anode weight exhibited an external case temperature of up to 112°C, and the rupture point tracked the amount of cathode material.

Evaluation of Partially Delithiated Cathodes

- Partially delithiated cathodes were removed from batteries that were subjected to formation and discharge, i.e. the nominal formula was $Li_{0.9}CoO_2$, or that were charged to 4.10 volts following formation, i.e. the nominal formula was $Li_{0.5}CoO_2$.
- Batteries containing partially delithiated cathodes and non-lithiated anodes were then assembled. They contained both internal and external thermocouples.

Evaluation of Partially Delithiated Cathodes

- Batteries were charged to 4.10 volts, and then subjected to an extended overcharge test at room temperature in still air. The test was conducted in an explosion proof chamber.
- The overcharge rate was 0.75 amps, i.e. C/2 rate, and the battery voltage, external case temperature, and internal temperature were monitored throughout test.

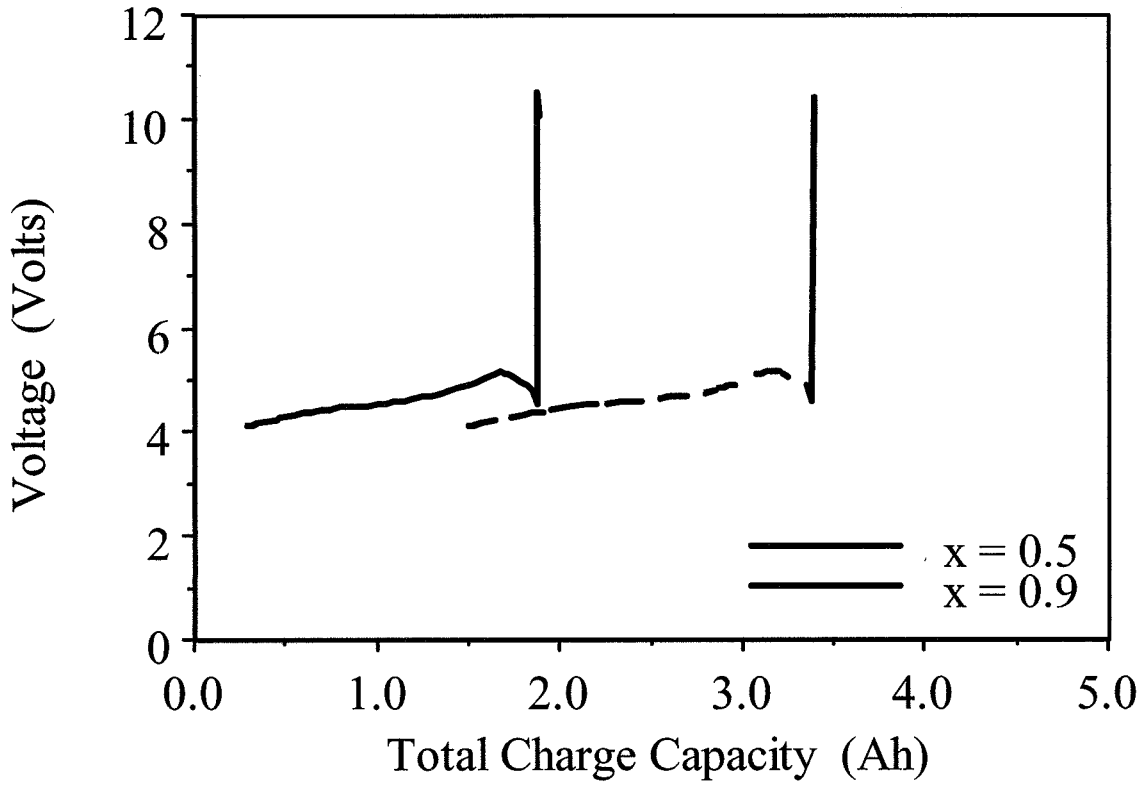

Figure 8: Voltage on 750 mA overcharge test for cells containing LixCoO2.

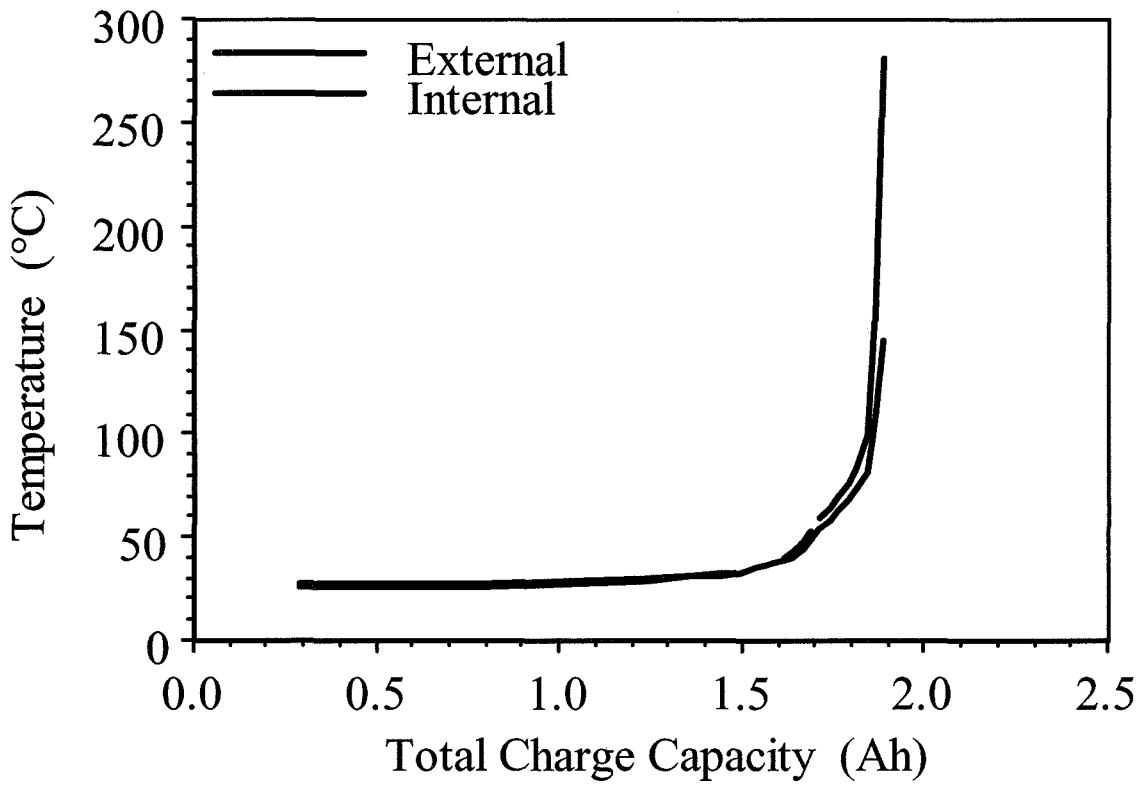

Figure 9: Temperature on 750 mA overcharge test for cells containing Li0.5CoO2.

Summary for Evaluation of Partially Delithiated Cathodes

- Both batteries ruptured during overcharge test.
- The shape of both voltage curves was similar, with the noticeable difference being the time, i.e. charge capacity, until the batteries reached full overcharge.
- Batteries containing the slightly delithiated cathode material, $Li_{0.9}CoO_2$, exhibited an external case temperature of 116°C, and an internal temperature of 215°C.

Summary for Evaluation of Partially Delithiated Cathodes

- Batteries containing the more highly delithiated cathode material, $Li_{0.5}CoO_2$, exhibited an external case temperature of 145°C, and an internal temperature of 281°C.
- Melting of lithium may be a cause of cell rupture on extended overcharge in standard batteries.
- Batteries that are unlikely to contain deposited lithium metal on the anode still ruptured on extended overcharge, although at a higher temperature.

Mechanisms Contributing to Battery Instability during Abuse

- Reaction of lithiated carbon and electrolyte.
- Reaction of lithiated carbon with PVDF binder.
- Melting of lithium.
- Autocatalytic exothermic reaction of Li_xCoO_2 above 150°C.

Mechanisms Contributing to Battery Instability during Abuse

- Oxidation of electrolyte due to high potential of cathode following complete removal of lithium.
- Reaction of highly delithiated Li_xCoO_2 and electrolyte near 250°C.
  - Evolution of oxygen near 230°C.
  - Decomposition of CoO_2 to Co_3O_4 at 245 °C.

Conclusions

- Short circuit and extended overcharge reactions were studied in medium size prismatic lithium ion batteries containing graphite anodes and lithiated cobalt oxide cathodes.
- Placement of thermocouples within batteries can provide more detailed information of battery temperature during abusive tests.
- During short circuit tests, batteries swelled slightly, and the shutdown separator was capable of limiting the internal temperature to 132°C.

Conclusions

- The overall response of a battery during extended overcharge is dependent, among other things, upon the charge rate, indicating that the ability of the battery to adequately dissipate heat is an important design consideration.
- While reduction of lithium plating during overcharge via the use of a low cell balance may improve the safety tolerance of the battery, it alone is not likely to be sufficient to prevent rupture during abuse.

Conclusions

- The overall reactivity of lithium ion batteries is due to a combination of chemical reactions that can occur on the anode and the cathode, and that may also involve the electrolyte and binder.

LiTech LLC

Lithium-ion Battery Technology Configured to Tolerate Overcharge and Overdischarge

S. Hossain, Y. Saleh, R. Loutfy
LiTech, LLC
7960 S. Kolb Road
Tucson, AZ 85706

NASA Aerospace Battery Workshop
Holiday Inn-Research Park
Huntsville, Alabama
November 13-16, 2000

538253
21p
20011183691

LiTech LLC

Limitations of Present Lithium-ion Battery Technology

$$LiMO_2 + C \rightleftharpoons Li_{0.5}MO_2 + Li_{0.5}C$$

Overdischarge → **Copper Dissolution** → **Cell Fails**

Overcharge → **Lithium Deposition + Solvent Decomposition** → **Explosion/Fire**

LiTech LLC

There are Shortfalls of Present Lithium-ion Battery Technology for the Production of High Capacity, High Voltage Batteries

- Almost Zero Tolerance
- Huge Capital Investment
- Complicated Electronic Circuits
- High Cost
- Safety Concerns

LiTech LLC

LiTech Lithium-ion Cell Components

Cathode or Positive Electrode	**: $LiCoO_2$, $LiNiCoO_2$, $LiMn_2O_4$**
Anode or Negative Electrode	**: C-C Composite**
Electrolyte	**: $LiPF_6$ in Carbonate-based Organic Solvent**
Separator	**: Poly-olefin**
Cell Design	**: Prismatic, Cylindrical**

LiTech LLC

Why C-C Composite as Anode for Lithium-ion Batteries?

- Substrate is Carbon - no Dissolution of Substrate during Overdischarge
- Substrate can act as Li^+ Sink - can accept lithium ion during Overcharge
- Strong Mechanical Integrity - High Cycle Life
- No Binder, no Carbon Black, high Compression - High Thermal Conductivity, Flame Retardant and Low Self Discharge
- C-C Composite Anodes are Reusable

LiTech LLC

C-C Composite Exhibits High Reversible Capacity and almost Zero Irreversible capacity Loss

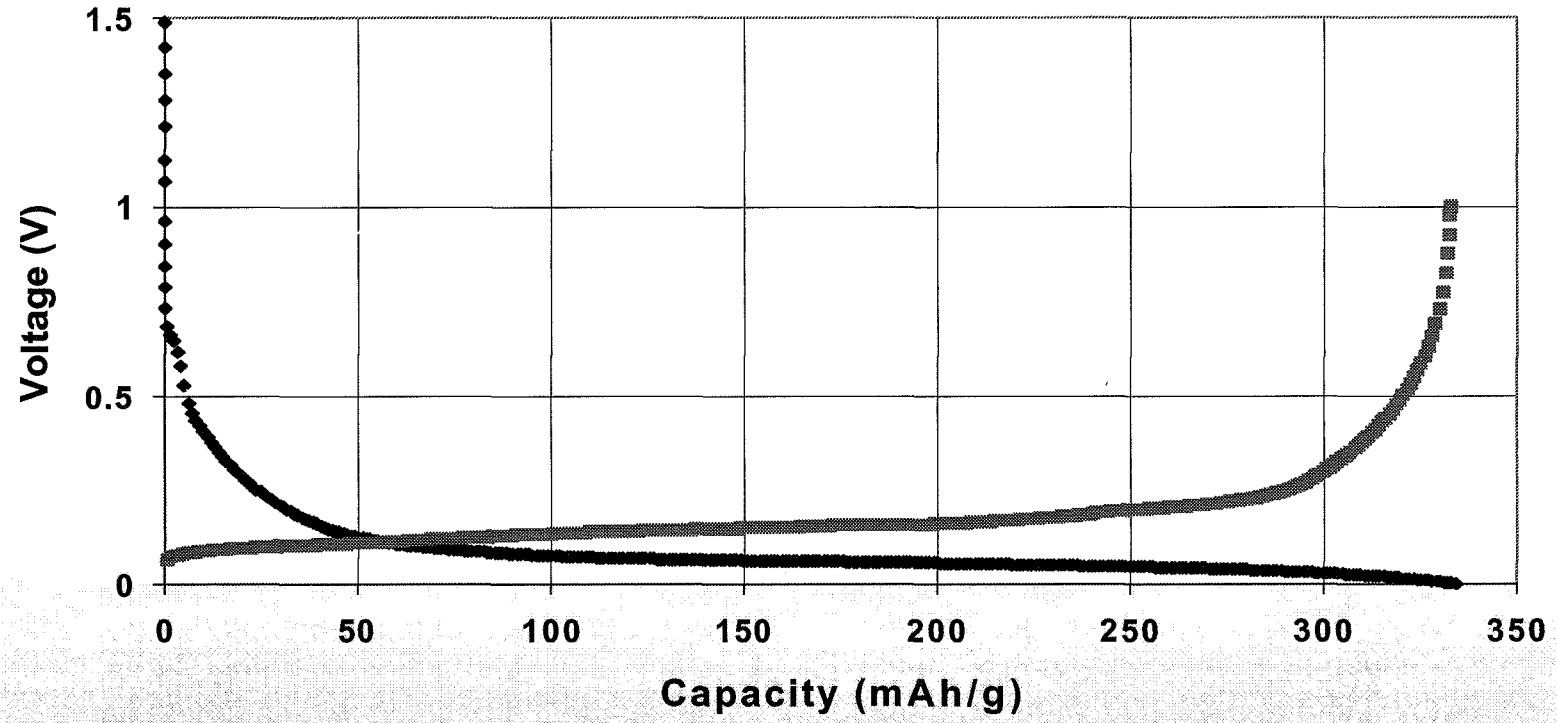

First Discharge-Charge Behavior of C-C Composite at 0.5 mA/cm2 in 1M LiPF6 Electrolyte (EC:DMC 1:1 v/v). Counter Electrode: Li.

LiTech LLC

Specifications and Characteristics of LiTech's Lithium-ion Cells

Cell Type	T (mm)	W (mm)	L (mm)	Nominal Capacity (mAh)	Cell Weight (g)	Energy Density (Wh/l)	Specific Energy (Wh/kg)
ICP-015674	0.7	56	74	215	6.8	274	117
ICP-033555	2.3	35	55	350	10.0	292	130
ICP-025674	1.9	56	74	650	16.5	305	145
ICP-035674	2.6	56	74	1,000	23.0	343	160

LiTech LLC

LiTech's Lithium-ion Cell can Accept Repeated Overdischarge

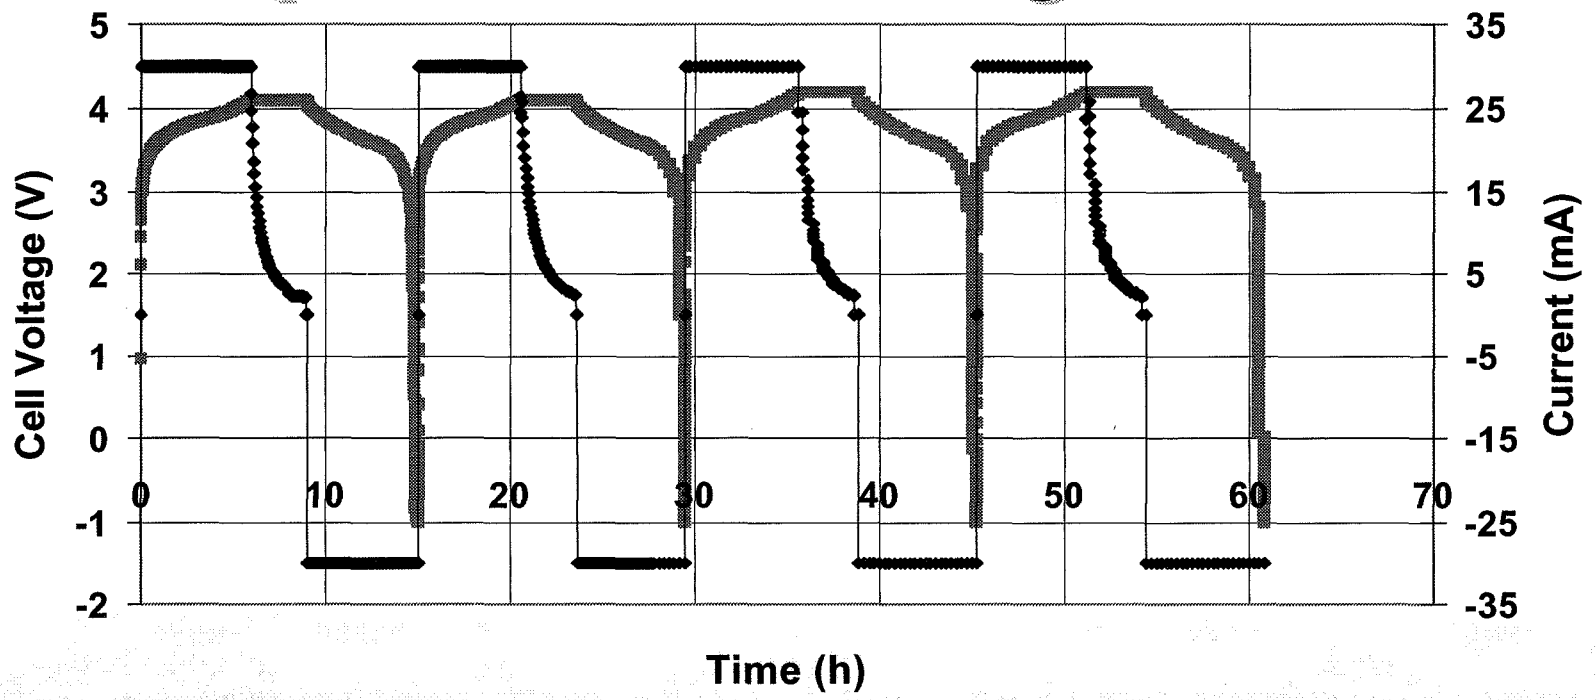

Charge-Overdischarge Behavior of a LiTech Lithium-ion Cell. Cathode: LiCoO2. Electrolyte: 1M LiPF6 in EC/DMC (1:1 v/v).

LiTech LLC

No Significant increase in Cell Temperature on Overcharge

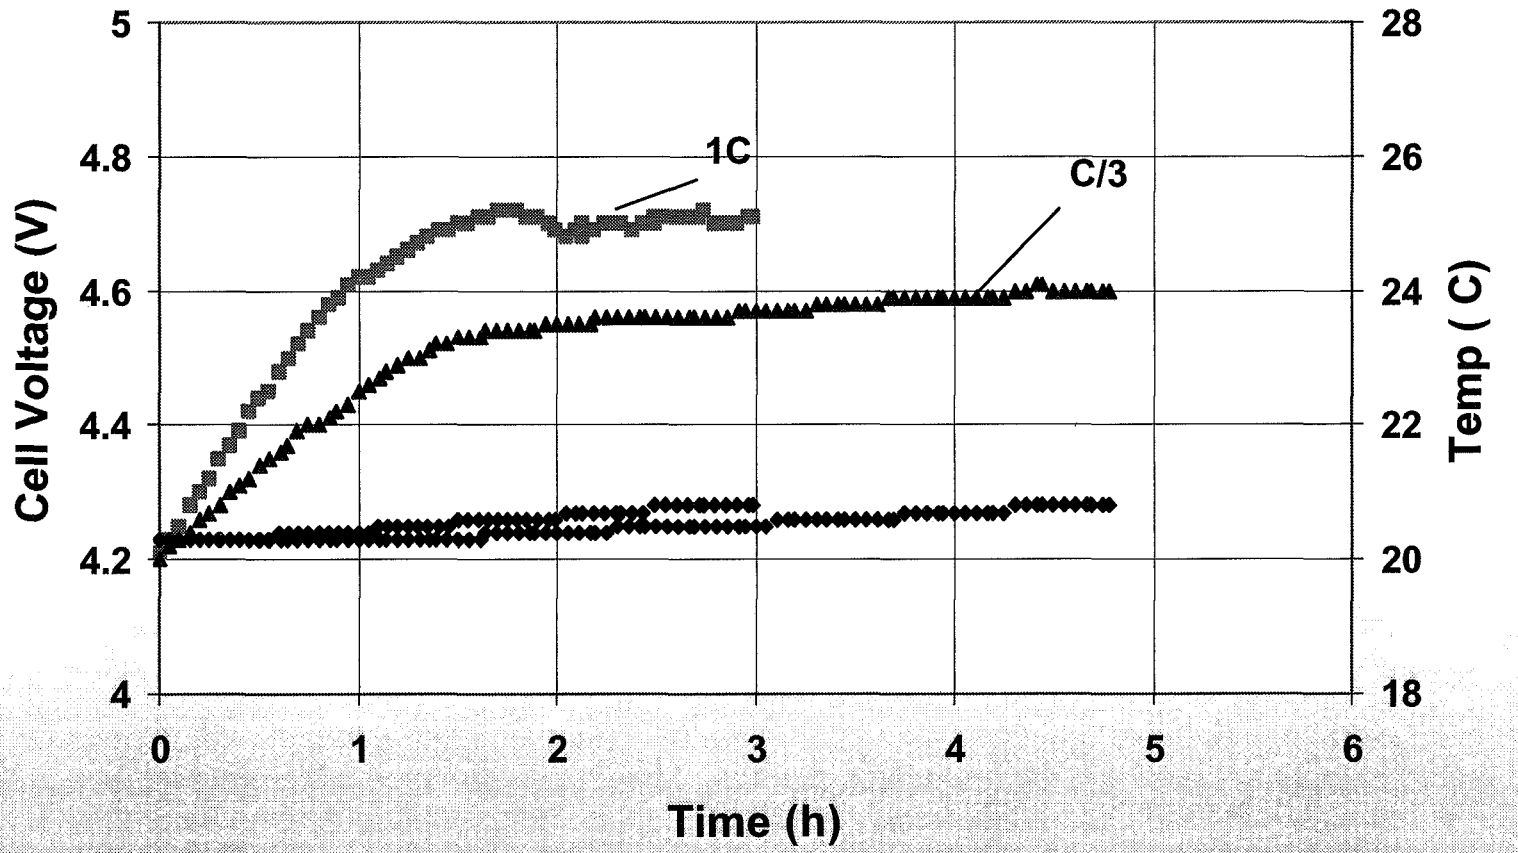

Voltage-Temperature Response of LiTech's Lithium-ion Cell during Overcharge at two Different Rates.

LiTech LLC

No Smoke, Fire, or Explosion during Overcharge of a 1Ah Cell

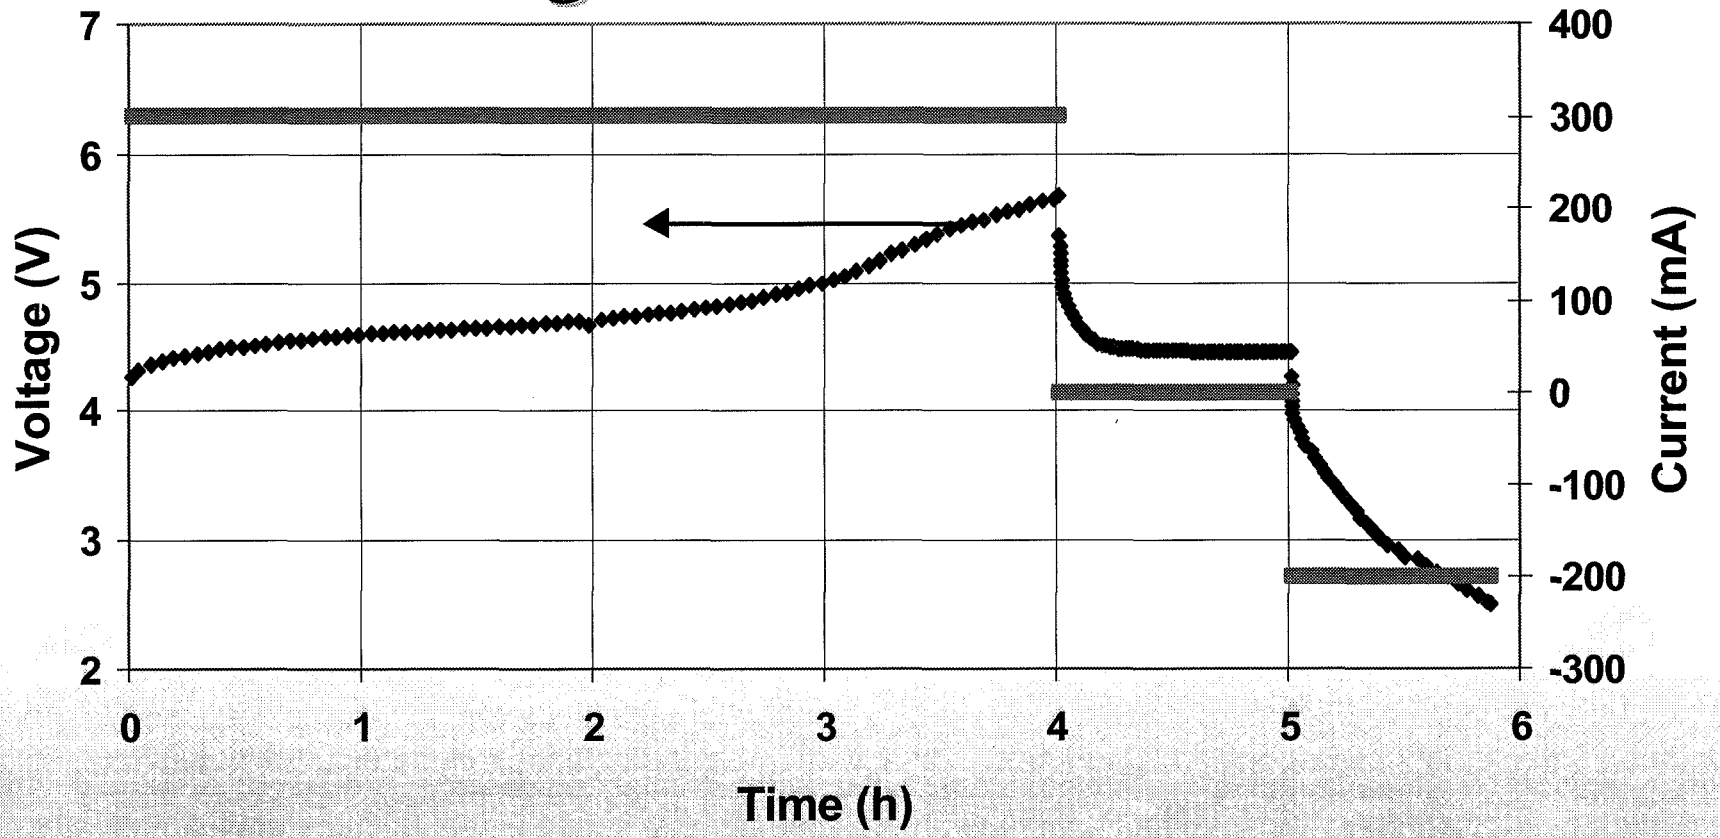

Voltage Response during Overcharge followed by Rest and Discharge of a 1Ah Lithium-ion Cell.

LiTech LLC

No Significant increase in Cell Temperature on Overcharge

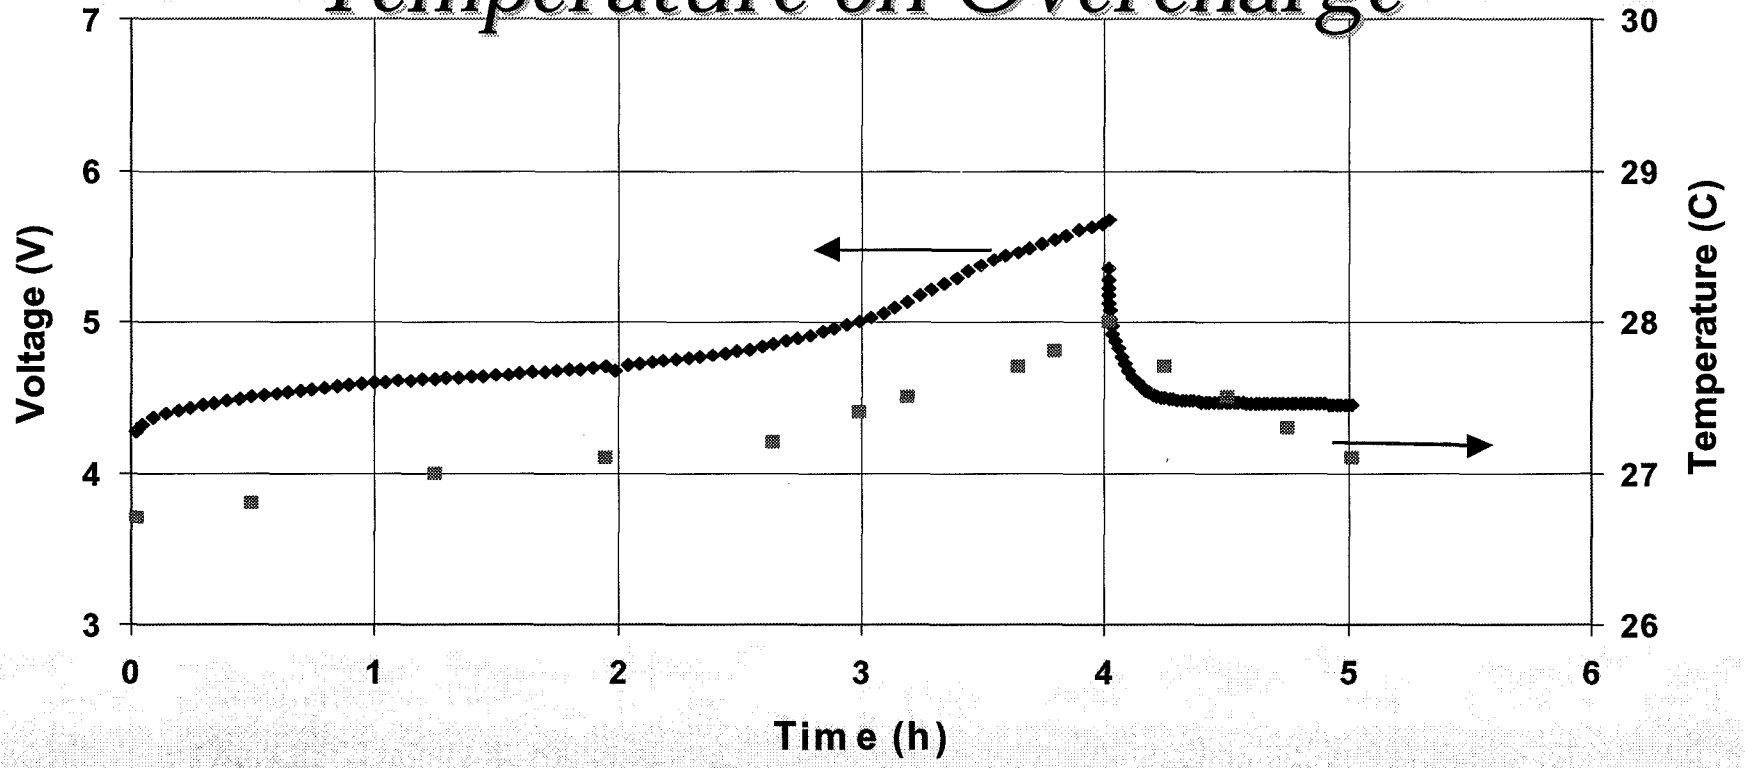

Voltage-Temperature Responses during Overcharge followed by Rest of a 1Ah Lithium-ion Cell.

LiTech LLC

Overcharged Cell can be Discharged

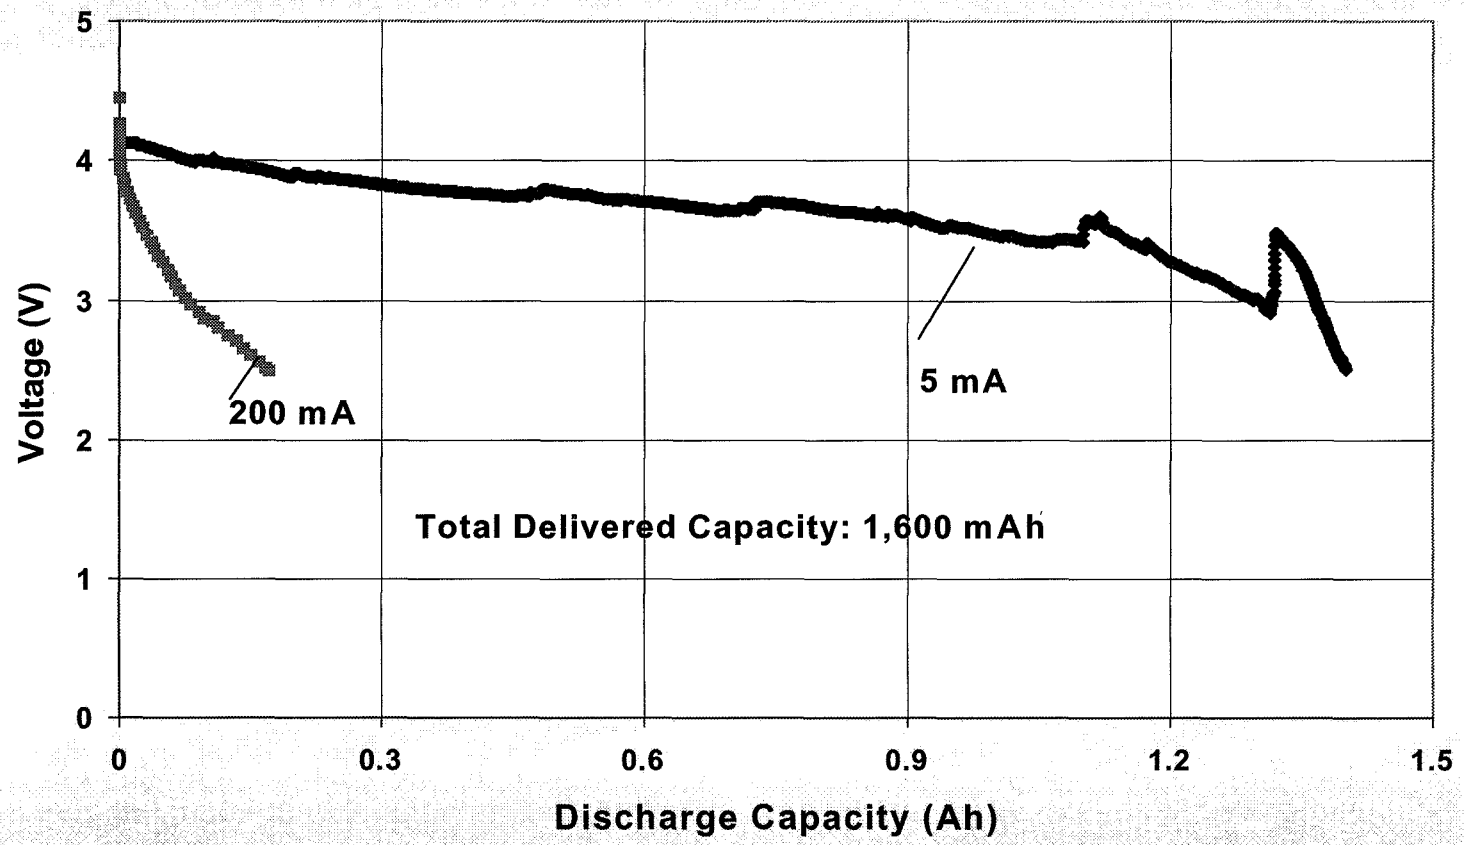

Discharge Behavior of an Overcharged Lithium-ion Cell first at 200 mA and then at 5 mA Current Drains.

LiTech LLC

Lithium-ion Cells Exposed to Overcharge can Deliver over 85% Capacity

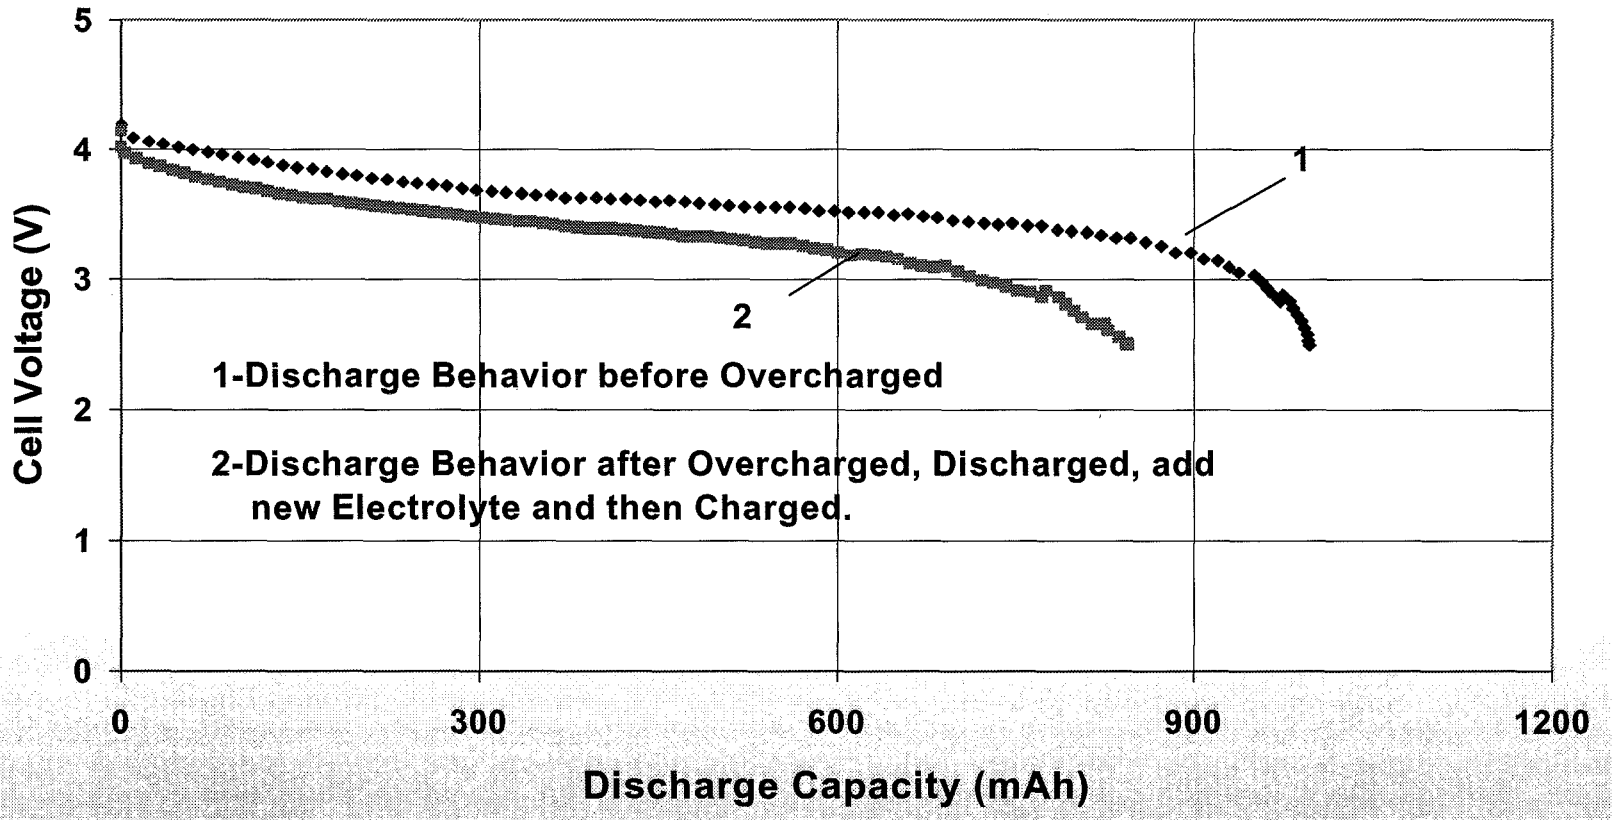

Discharge Behavior of a Lithium-ion Cell before and after Exposed to Overcharge.

LiTech LLC

Overcharged Cell, after fully Discharged and Adding fresh Electrolyte, can also be Cycled

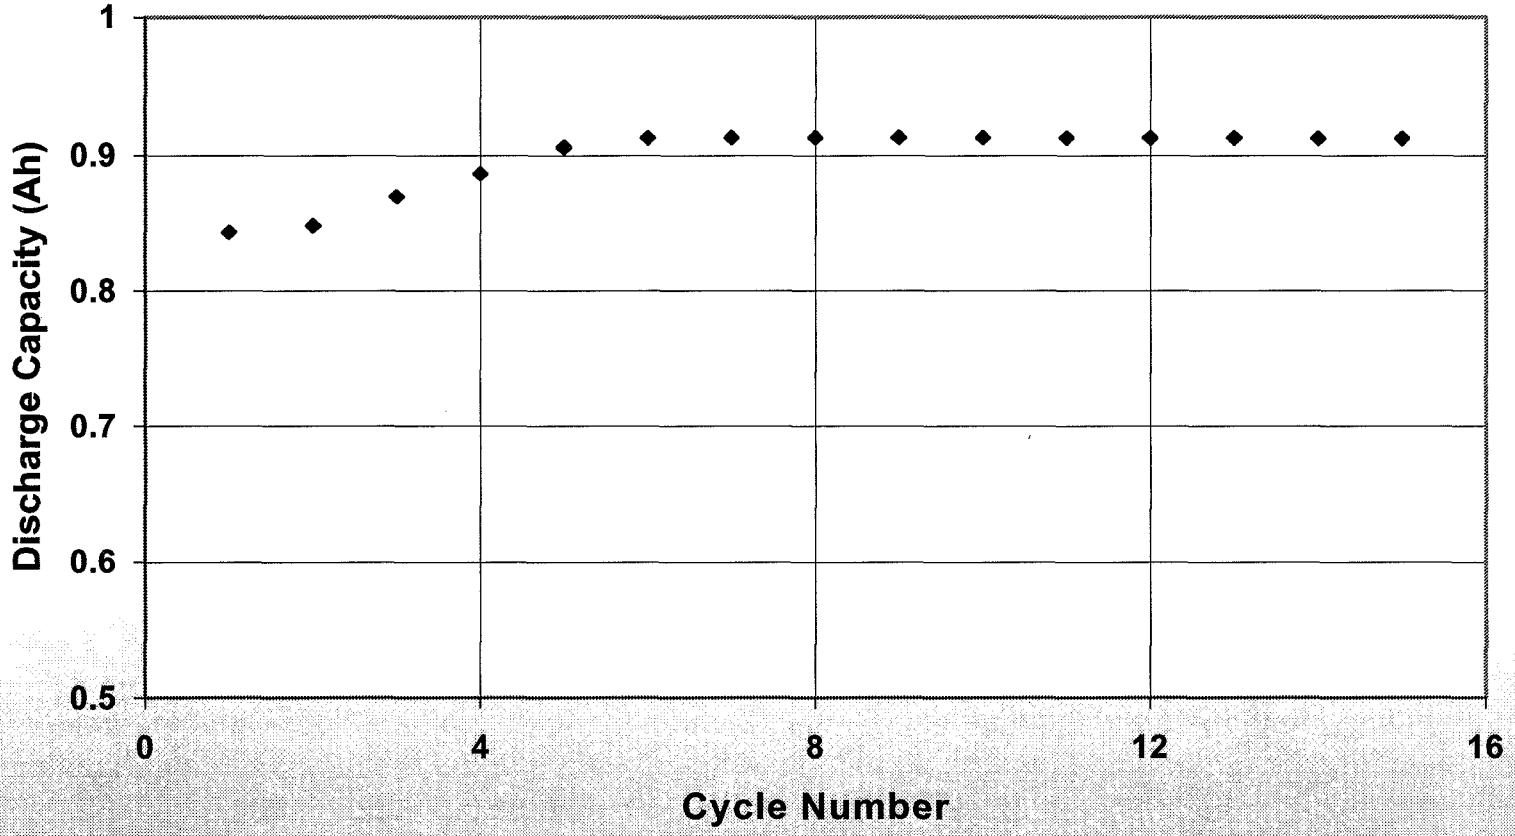

Cycling Behavior of an Overcharged Cell. Rated Cell Capacity was 1 Ah.

LiTech LLC

LiTech Lithium-ion Cells can Accept Repeated Overcharge/Overdischarge

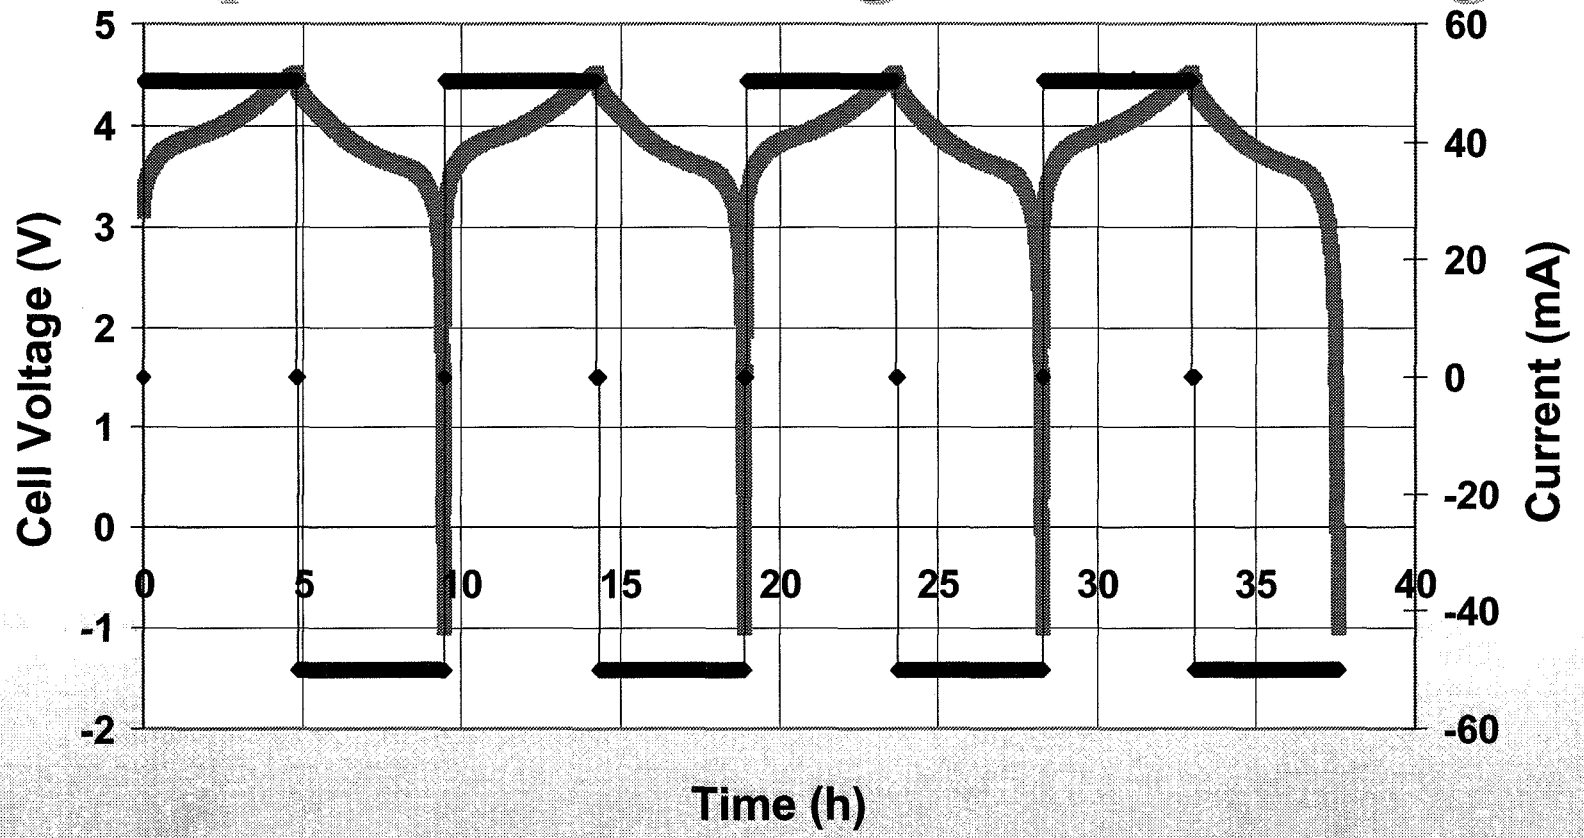

Repeated Overcharge/Overdischarge Behavior of a LiTech Lithium-ion Cell.

LiTech LLC

Delivers 550 cycles with over 90% Capacity Retention

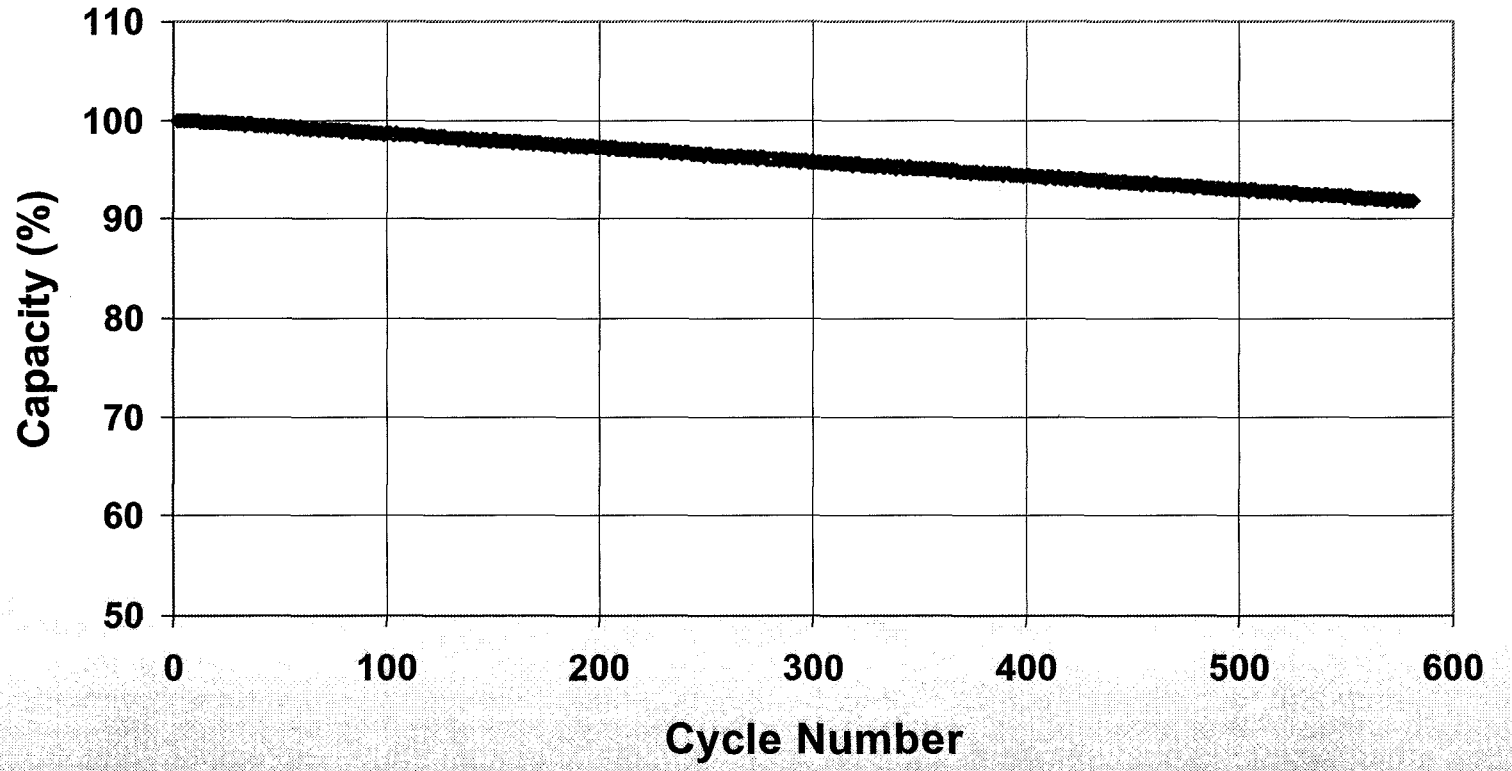

Cycling Behavior of a LiTech Lithium-ion Cell at C/5 Rate. Cathode: LiCoO2. Electrolyte: 1M LiPF6 in EC/DMC (1:1 v/v).

LiTech LLC

Only 10 mV Voltage Decay after Storage for 1 Month at Ambient Temperatures

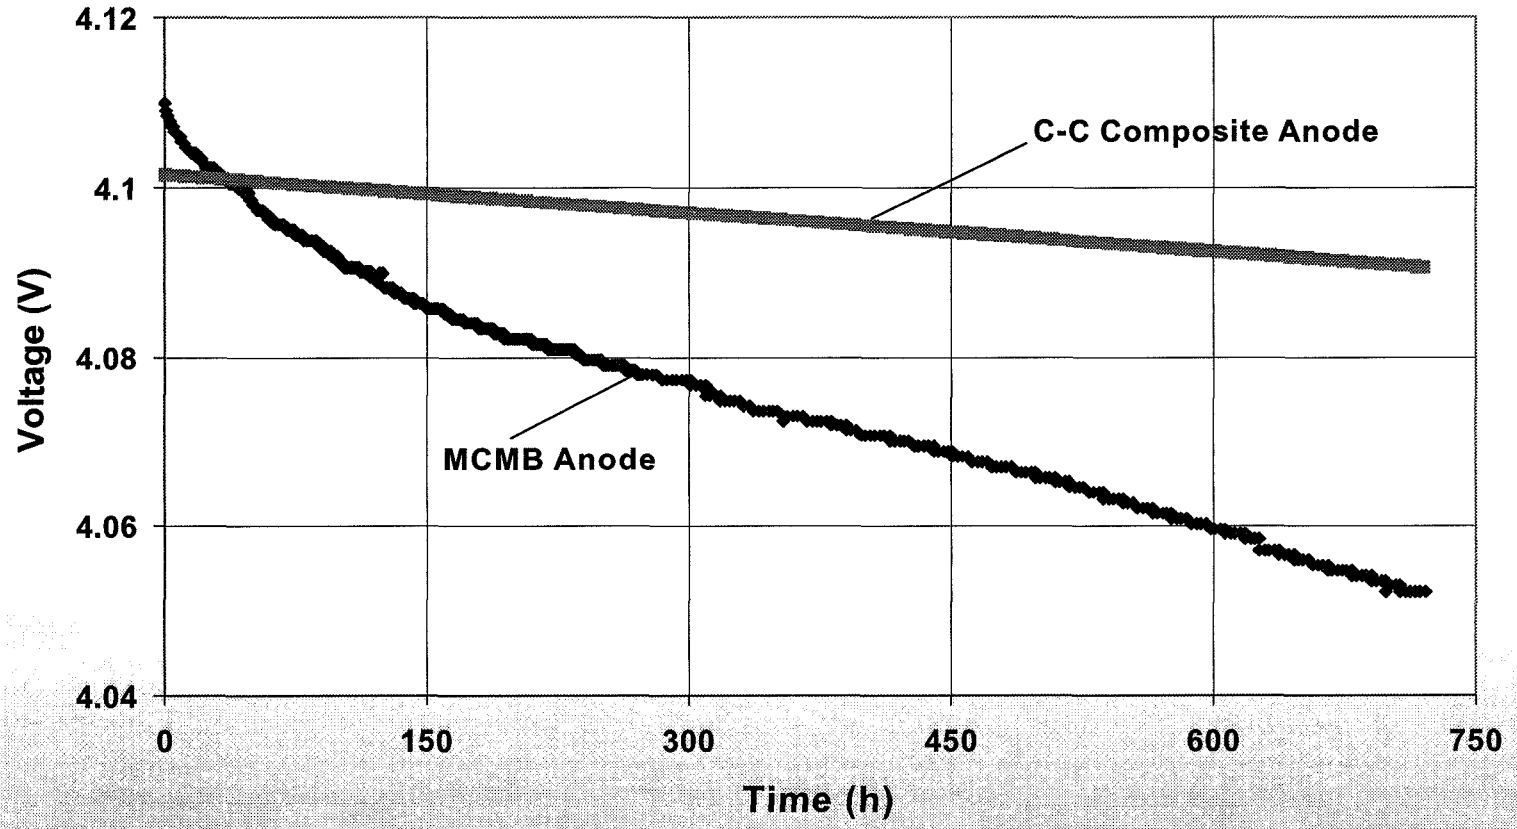

Voltage Decay of Lithium-ion Cells at OCV stored at Ambient Temperatures.

LiTech LLC

Only 2% Capacity Loss After 1 Month of Storage at Ambient Temperatures.

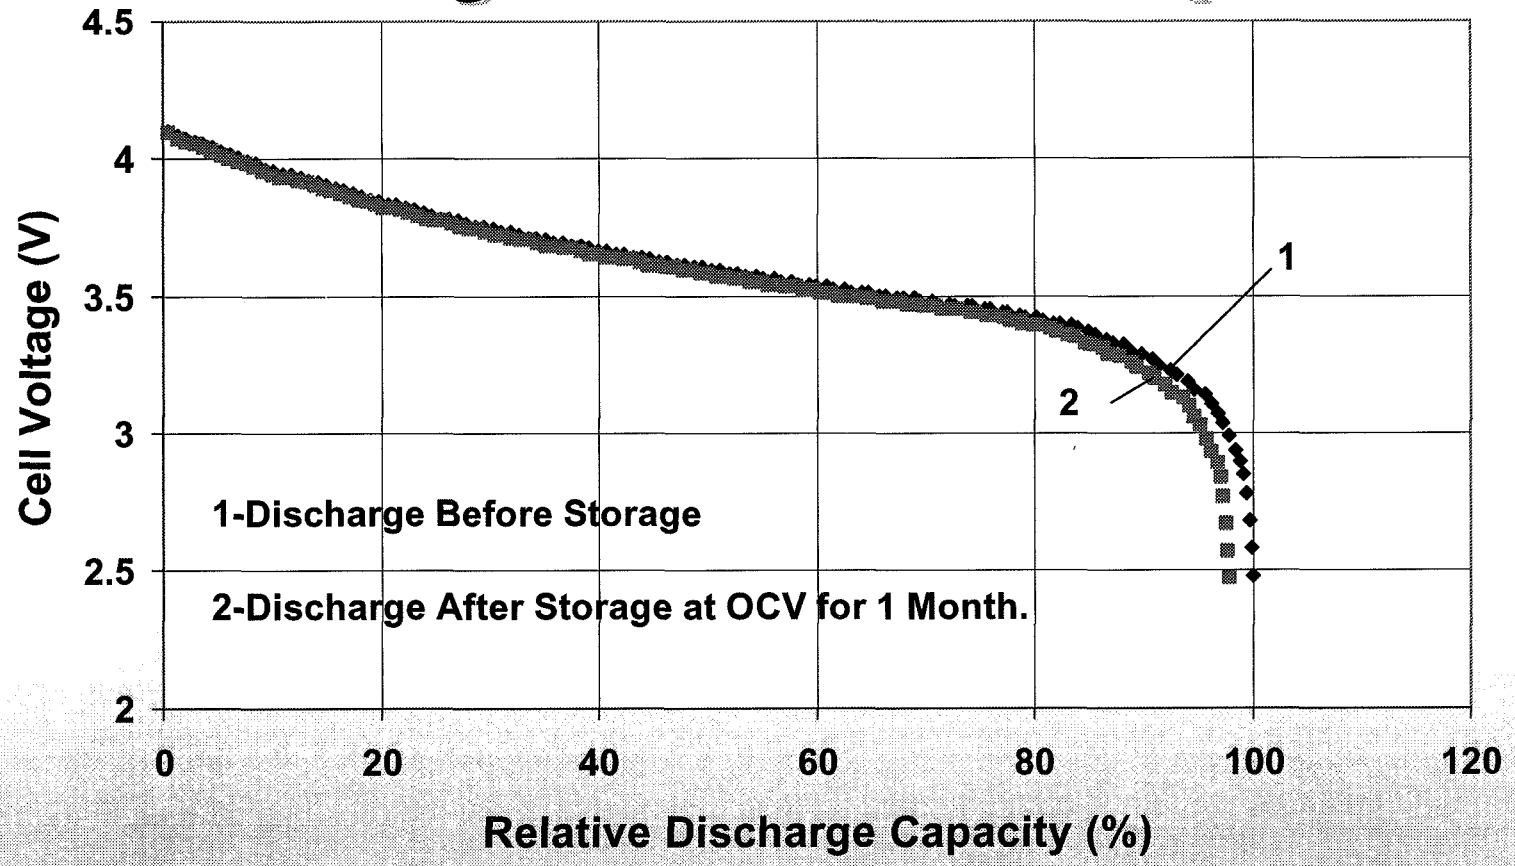

Discharge Behavior (Before and After Storage) of a LiTech Lithium-ion Cell at C/4 Rate.

LiTech LLC

At 1C Rate, the Cell Delivers 95% Capacity

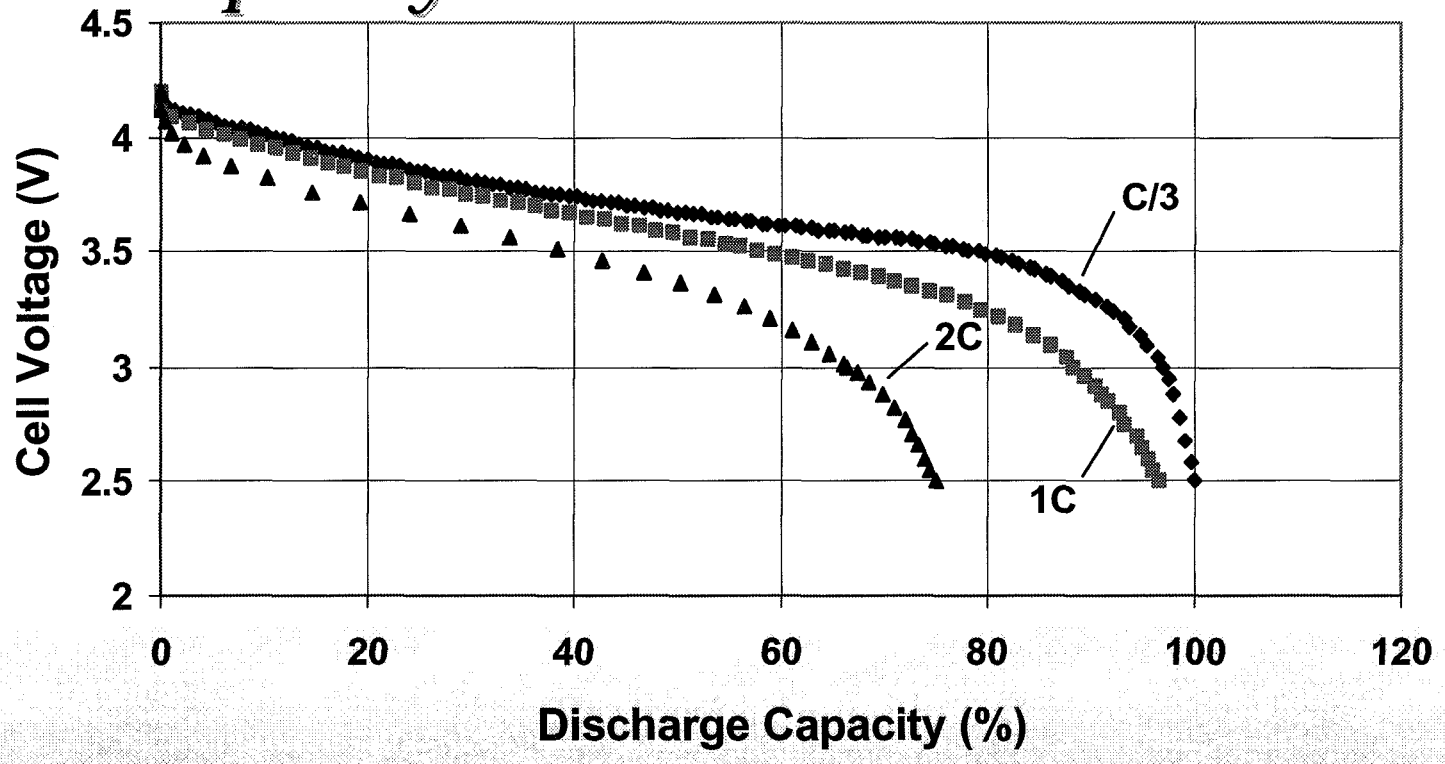

Discharge Behavior of LiTech's Lithium-ion Cell at Different Current Drains. Cathode: LiCoO2. Electrolyte: 1M LiPF6 in EC/DMC (1:1 v/v).

LiTech LLC

Safety and Abuse Test Results

Tests	Results
Overdischarge	No Performance Degradation.
Overcharge	No Fumes, No Fire, No Explosion.
External Short-circuit	No Fumes, No Fire, No Explosion.
Internal Short-circuit (Nail Penetration)	No Fumes, No Fire, No Explosion.

LiTech LLC

LiTech Lithium-ion Battery Technology offers:

- **Low Cost**
- **Enhanced Safety**
- **High Energy Density**
- **Long Life, and**
- **Low Self-Discharge**

The Technology is the Right Choice for the Production of High Capacity, High Voltage Batteries.

Secondary Lithium-ion Cell and Battery Safety

NASA Battery Workshop 2000

Rob Spurrett & Carl Thwaite, AEA Technology plc, UK

Philip Cowles, COM DEV Ltd, Canada

AEA TECHNOLOGY SPACE

COM DEV SPACE GROUP

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Introduction

- AEA Technology and COM DEV teamed to build Lithium -ion batteries currently based on the Sony 18650HC (hard -carbon), widely regarded as the safest cell.
- This paper describes
  - the safety features built into Sony 18650HC cell.
  - the formal safety approval tests performed on the cell.
  - safety tests performed as part of the LAT test.
  - supplementary test data from on-going programmes.
- Briefly discusses safety with respect to battery level safety.

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Cell Safety Trades - 1

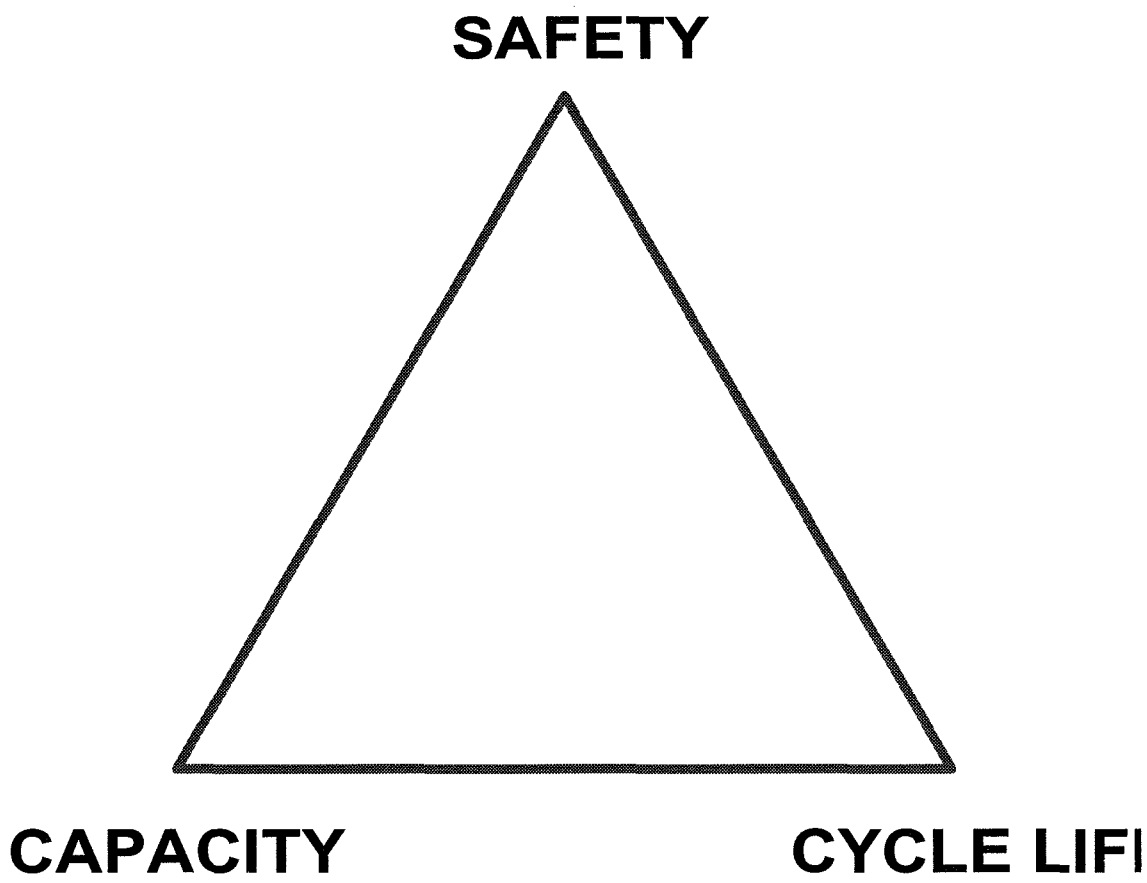

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Cell Safety Trades - 2

- AEA Technology provides contract R&D to every major Japanese cell producer.
- Secondary Lithium-ion cell design is a trade of safety, capacity and cycle-life.
- Optimise any two from three, but optimising all three is tough.
- Sony 18650HC, the first generation commercial cell, was principally optimised for cycle-life and safety.
- Most commercial cells are optimised for capacity and cycle-life, leaning very strongly towards capacity.
- For most new producers, safety is always a secondary concern, until the required capacity/cycle-life has been achieved. This is a BIG MISTAKE!

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Sony 18650HC Cell

- ∅18mm, 65mm long
- 1.5 Ah capacity
- 5.4 Wh energy
- 133 Wh/kg
- Hard carbon anode with PVDF binder
- $LiCo_2$ with PVDF binder
- DEC/PC electrolyte, 1M $LiPF_6$

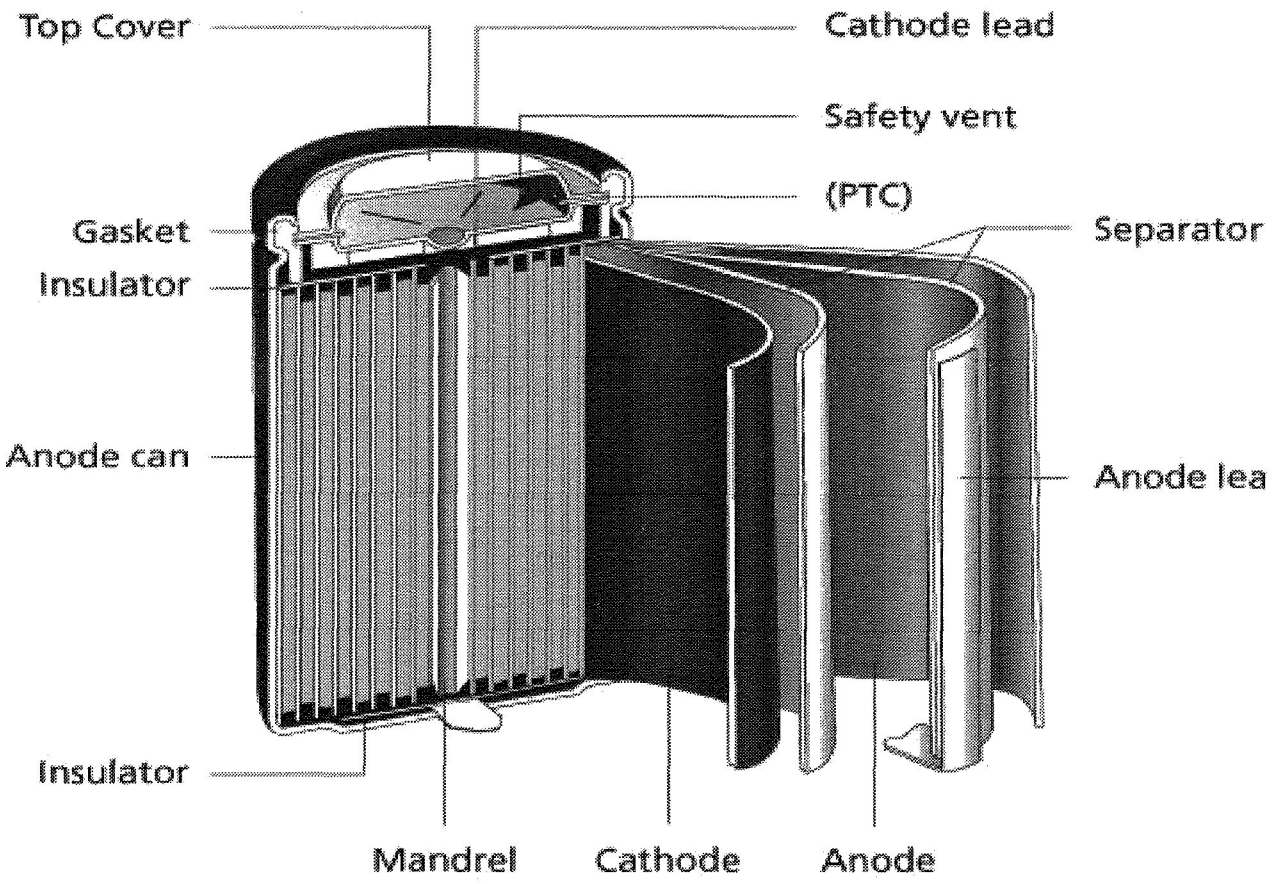

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Safety Features - 1

- Over-charge Protection
  - Non-reversible, triggered on over 100% overcharge
  - Internal pressure rises to ~10 bar and breaks an internal connec tion
  - Ensures that the cell fails open circuit
- Shut-down Separator
  - Non-reversible
  - Microporous, melts at T>120degC to shut down reaction
- Over-current (short-circuit) Protection
  - Reversible Positive Temperature Coefficient (PTC)
  - Thermally operated in seconds - does not impact fuse blowing capability
- Cell vent
  - Operates to release internal pressure if safety mechanisms descr ibed above fail

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Safety Features - 2

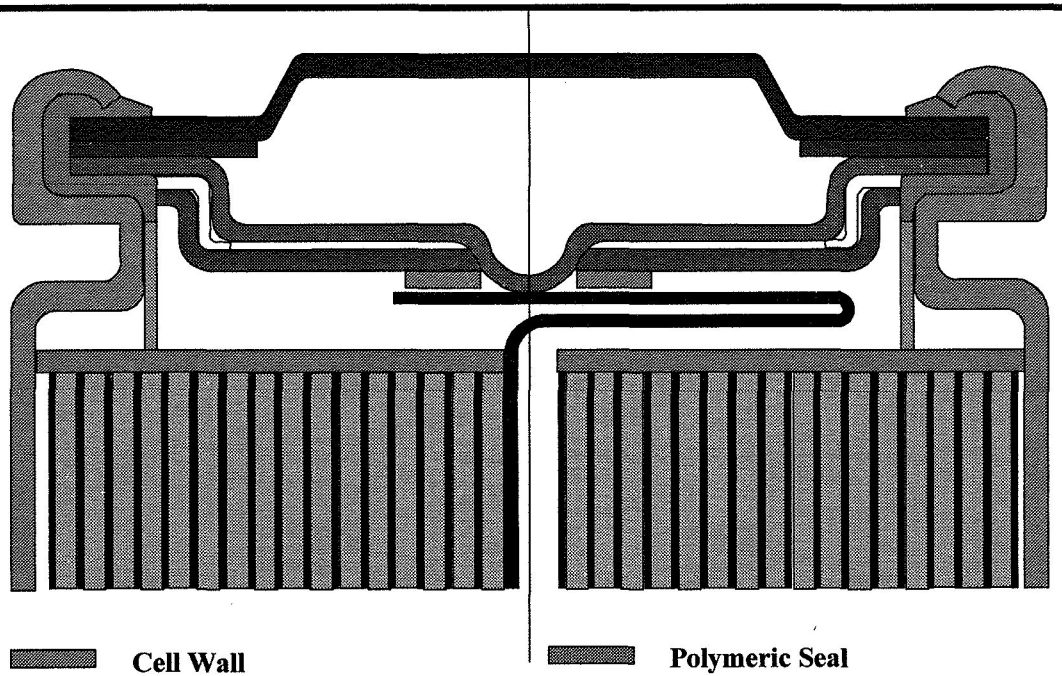

- Cell Wall
- Top Cover
- PTC Annular Ring
- Pressure Disk
- Cathode Tag Support
- Cathode Tag Mounting Disk
- Cathode Tag
- Polymeric Seal
- Possible Seal Extent (SONY Diag)
- White Polymer Collar
- Polymer Electrode Roll Isolator Disk
- Cathode
- Anode
- Electrode Separator

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcharge Design - 1

- Cell overcharge protection is **essential** for safe battery operation
- For complete safety, we think the device should be - autonomous, highly repeatable, non -electronic, safe against inadvertent operation
- Typical properties from a constant current charge on a Lithium -ion cell are shown on next slide
- A protection mechanism can trigger on: temperature, pressure, chemical, or over-voltage
- Sony picked pressure (on the grounds of inadvertent operation)
- Downside is that to trigger on pressure, a gassing agent must be added, Sony add $LiCo_2O_3$
- Gassing agents have an impact on capacity/cycle -life

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcharge Design - 2

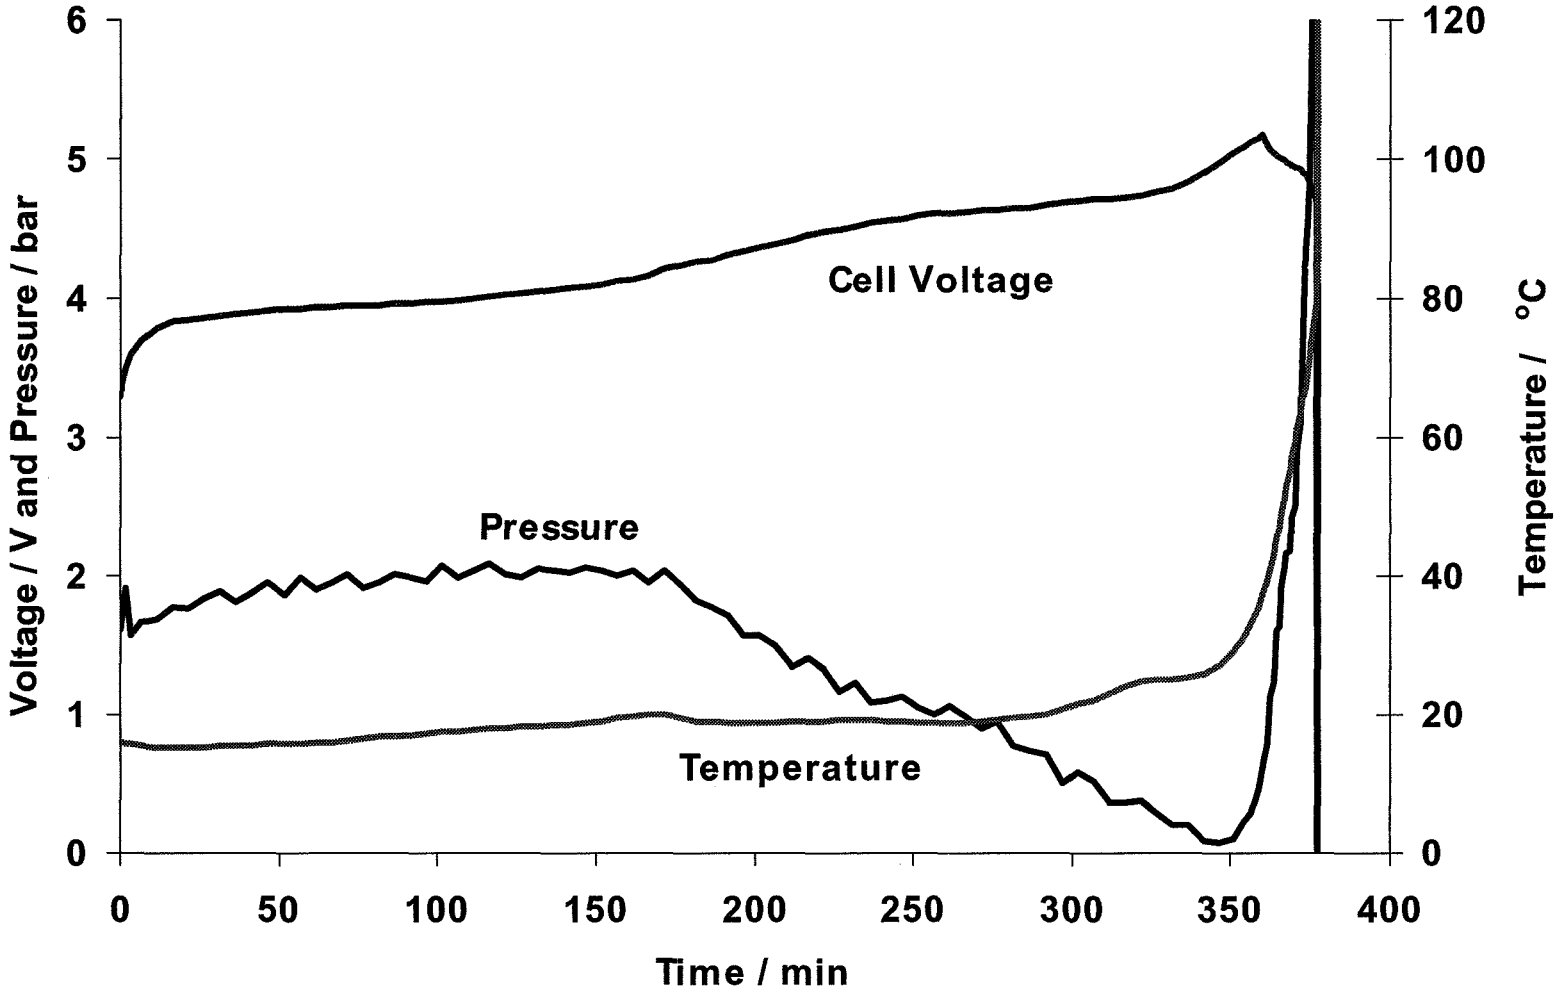

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcharge Design - 3

- For the Sony 18650HC cell recommended EOCV is 4.2V +/- 50mV
- Hard-carbon + DEC/PC electrolyte, tolerant to high charge voltage
- High margin on overcharge
- Up to 4.3V little impact on cycle-life - data later
- Typically need 100% overcharge to trigger the device
- Device operates at 4.7V to 5V
- Despite many 'incidents' over eight years of making batteries fo r space and terrestrial applications, we have **never** had an explosion or fire with Sony cells .

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

SAFETY TESTS

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Safety Tests - 1

- Tests to standard IEC requirements performed by Sony and some tests repeated by AEA Technology
- All tests repeated for accreditation by Underwriters Laboratory in US - http://www.ul.com
- Conform to standards
  - UL-1642 Lithium-ion cells
  - see http://ulstandardsinfonet .ul.com/scopes/1642.html
  - SU-2054 Lithium-ion battery packs
  - see http://ulstandardsinfonet .ul.com/scopes/2054.html
- Following table summarises the tests and pass/fail criteria
- All cells passed

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Safety Tests - 2

	Condition	Results
Spike Penetration	Five Inch Spike	No Gas
Crush I	13 kg Iron	No Fire
Crush II	ϕ 16 Bar	No Fire
Drop I	1.5m Height	No Leakage
Drop II	1.0 m Height	No Difference
Drop III	10 m Height	No Gas
Abnormal Voltage I	+35V 46A	No Gas
Abnormal Voltage II	-35V 46A	No Gas
Abnormal Voltage III	-13V 46A	No Gas
Over Charge	2A 5V	No Gas
Salt Water	5% Salt, 24H	No Fire
Burn	Gas Burner	No Explosion
Heat	Hot Plate	No Explosion

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Safety Tests - 3

	Condition	Results
Micro Wave	Micro Wave Oven	No Fire
Hot Water	100°C	No Gas
Heated Oil	180°C	No Fire
Melted Solder	230°C	No Explosion
Internal Short Circuit	Pin Holed Separator	No Gas
Short Circuit	<15 mΩ	No Fire
AC Input	100 V	No Explosion
Drilling	ϕ 4	No Fire
Weak Welding		No Difference
Low Pressure	1mm Hg 1 min	No Difference
Weather	-20°C, 1H - 25°C, 1 Day	No Leakage
Hot Temperature	85°C, 72 H	No Difference
Low Temperature	-40°C, 3 Days	No Difference

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

LAT SAFETY TESTS

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

LAT Safety Tests

- Lot Acceptance Test (LAT) performed by AEA Technology/COM DEV on samples of 84 cells taken from every batch
- LAT is adapted from ESA SCC hi-rel component specifications
- LAT includes relevant abuse testing and verification of cell saf ety features

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcurrent Protection - 1

- Purpose: to validate operation of the overcurrent protection
- Performed on six fully charged cells from each 84 cell sample
- Cells shorted with a 100mΩ resistor at ambient temperature
- Pass/fail is for peak current > 15 A (10C)
- Falling to < 2C in 10 seconds
- Allowed to stabilised for 1 hour
- Repeatability tested - deliver same peak current within 10%
- Following slide shows typical current history - time base 5 sec per division and volts 0.5V per division measured across 100mΩ
- Typical spacecraft fuse blowing requirements are easily met

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcurrent Protection - 2

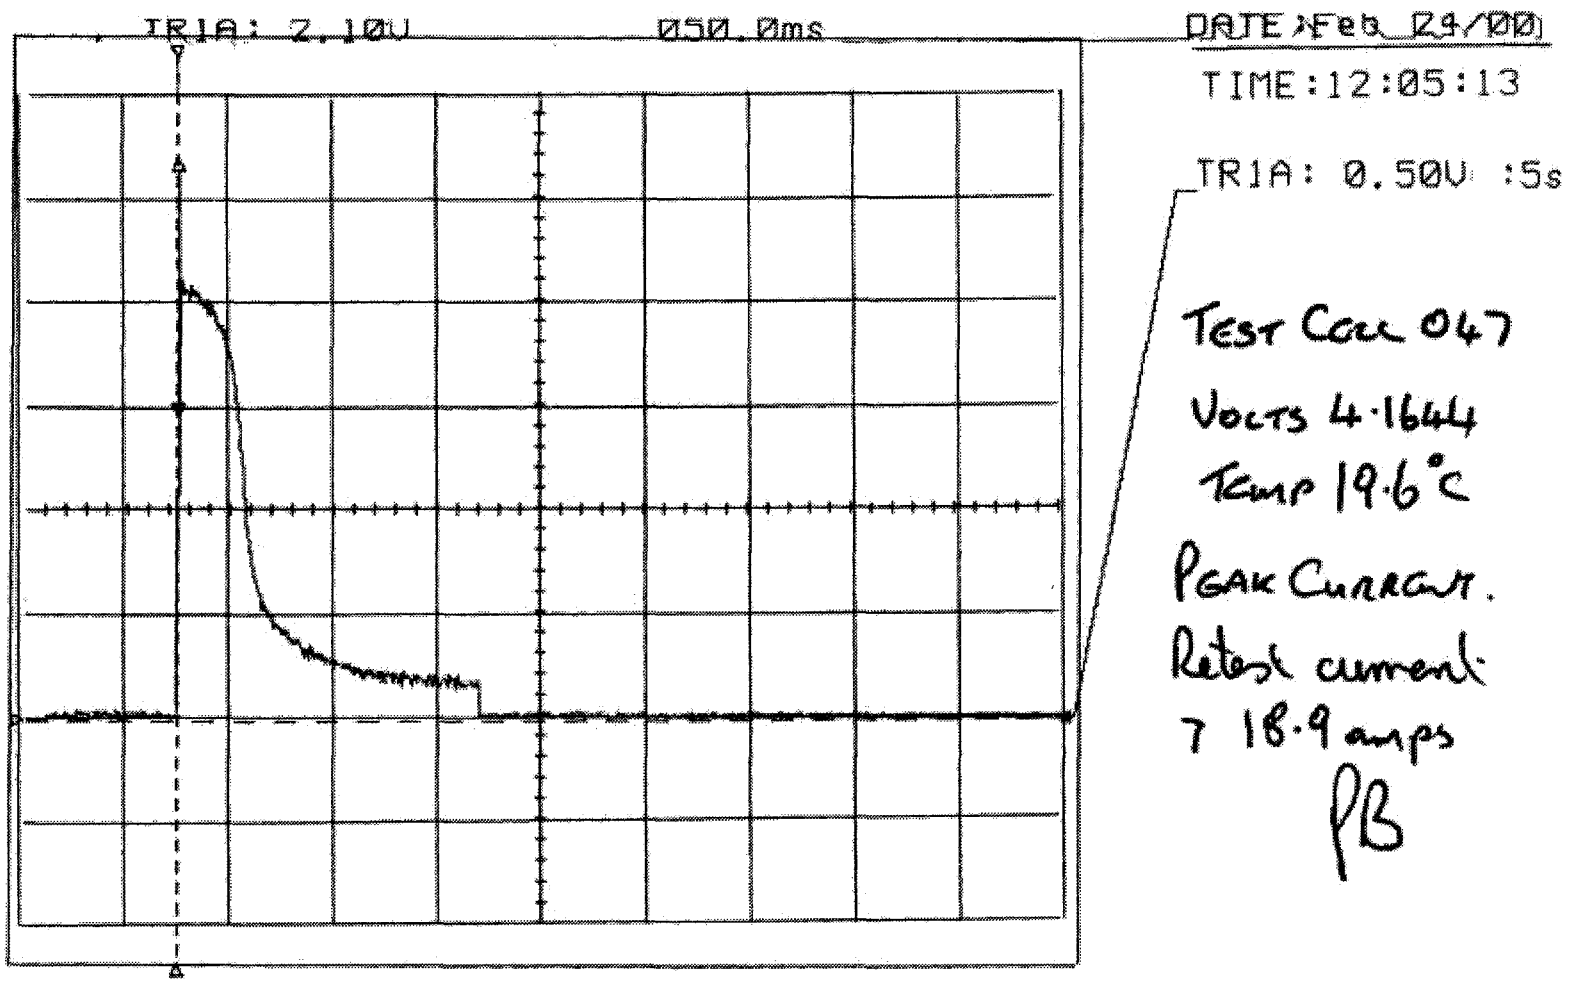

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcharge Protection - 1

- Performed on the same 6 cells subjected to overcurrent test
- Cells charged at C/10 until failure (overcharge operates)
- Typically takes 10 - 11 hours from fully charged to operate the disconnect, i.e. an overcharge of at least 100%
- Voltage and temperature monitored
- No significant temperature rise (<3 degrees)
- Disconnect operates between 4.7V and 5.0V
- Current drops to 0mA - high impedance tested
- Test followed by Destructive Physical Analysis to verify correct operation of the device.

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Overcharge Protection - 2

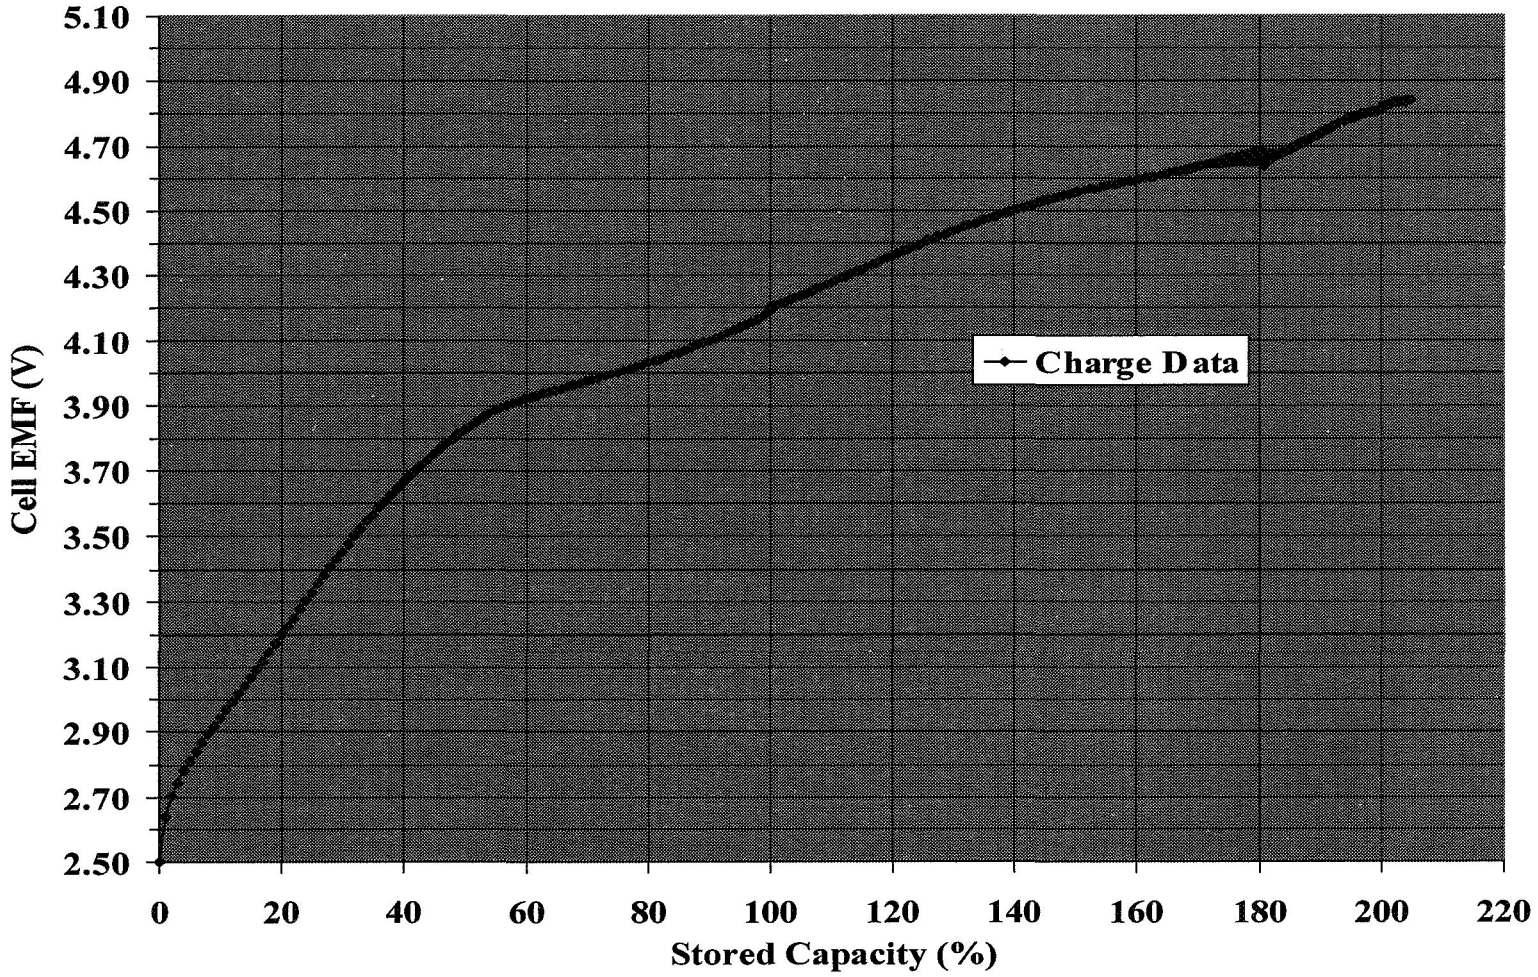

AEA TECHNOLOGY SPACE

COM DEV SPACE GROUP

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Thermal Shock/High Temperature

- More demanding than *IEC 5.3.2 Thermal Shock Test*
- Also performed at higher temperature than *IEC High Temperature Storage Test*
- Before cycling cells are subjected to qualification level vibrat ion (LLS, HLS, random at $30g_{rms}$ 4 minutes per axis, plus 100g 0.5msec shock)
- Cycle up to 80°C then down to -20°C
- Repeated three times
- Dwell time at each temperature 2hours
- Time for temperature transition < 1 hour
- Performed on six cells from each 84 cell sample
- Full electrical performance required for a 'pass'

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Burst Pressure Tests

- Really a test of the cell seal rather than the cell can
- Lower end of cylindrical can removed
- Active contents of cell removed
- Pressure applied hydraulically to limit of test set-up
- 450 p.s.i. (31 bar)
- No detectable leakage or fall in pressure
- (Additionally, as part of the LAT, the leak-rate of the seal is measured in a vacuum with a helium leak detector.)

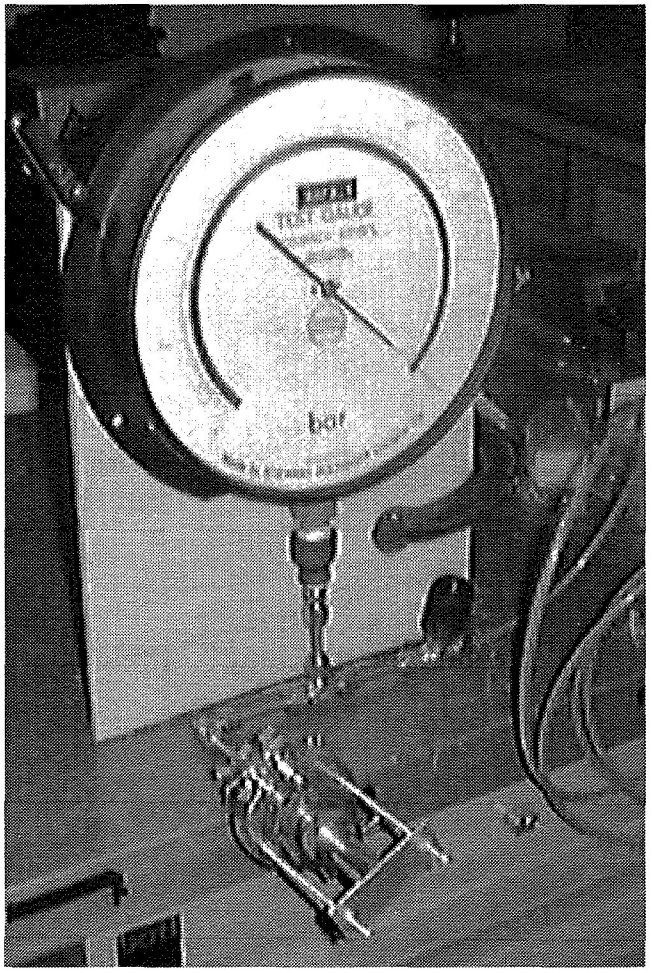

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

SUPPLEMENTARY DATA

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

ROSETTA Satellite Battery

- ESA Cornerstone mission to comet Wirtanen
- Battery of 1070 Wh
- Three modules, each 6s - 11p
- Battery mass 9.99 kg
- Battery energy 107 Wh/kg
- Qualification complete
- Flight models manufactured and undergoing acceptance testing
- Launch date: 2003

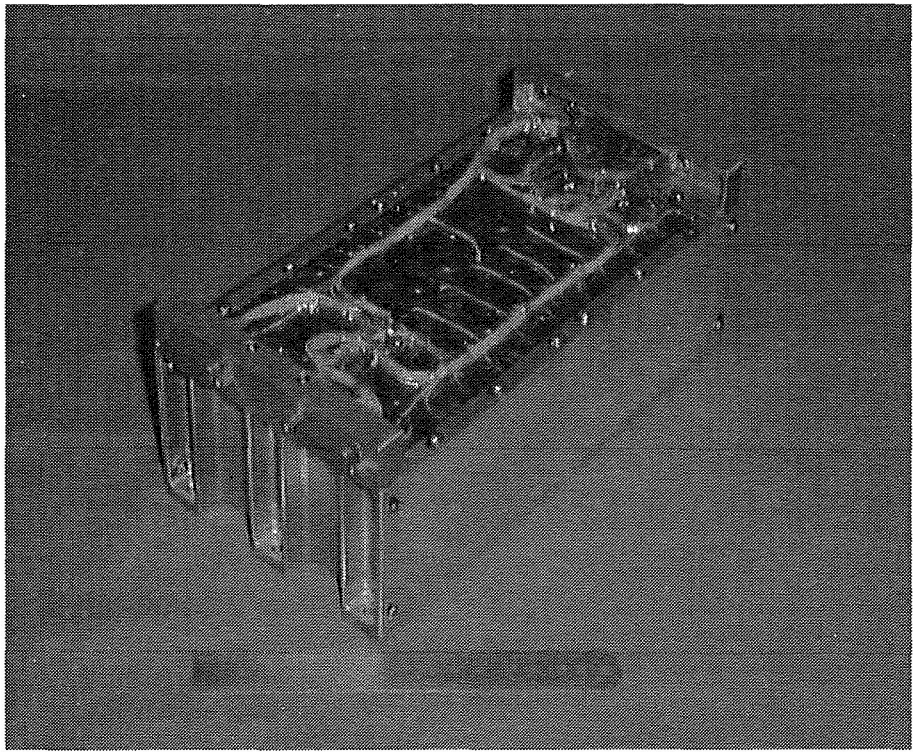

AEA TECHNOLOGY SPACE

COM DEV SPACE GROUP

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Shock

- Recent spacecraft requirements well in excess of IEC 5.2.1
- ROSETTA qual at 2,000g at 1.5 to 10 kHz (+9dB,-6dB)
- Actual pyrotechnic qualification test achieved peak levels >10,000g at 6kHz
- Repeated in all three axes
- Followed by sine and random vibration
- No failures

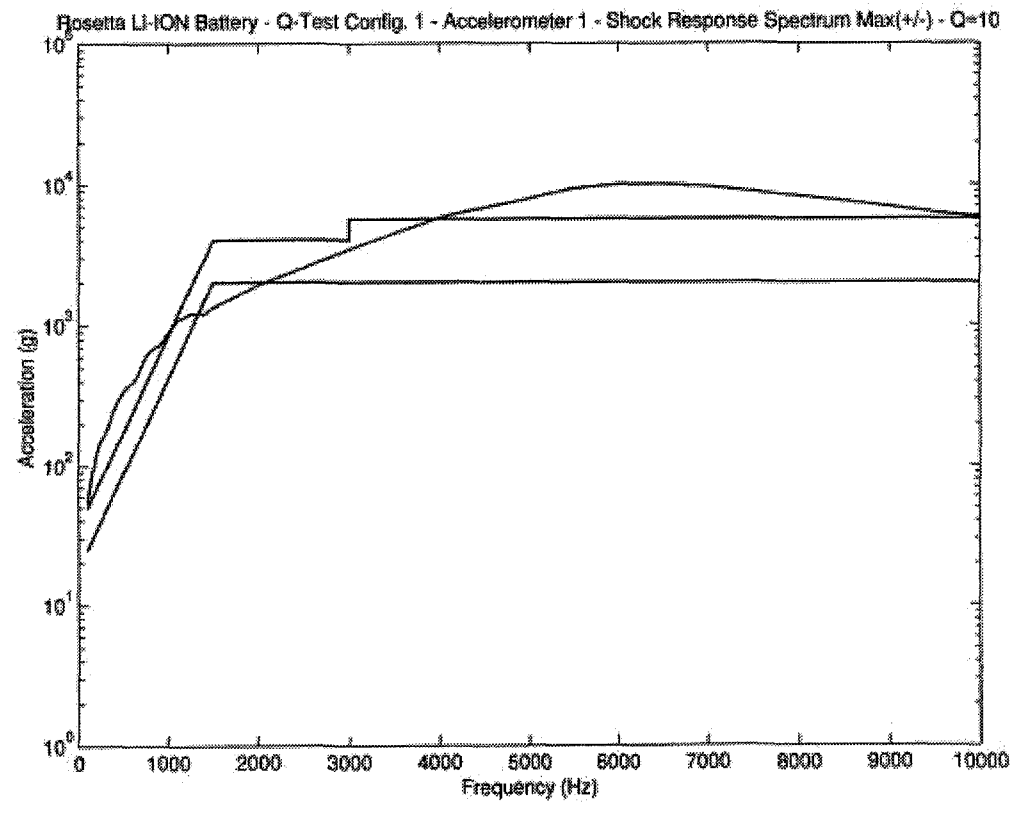

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Reverse Polarity - 1

- Three batteries undergoing life -test at 0, 20, 40degC
- Battery configuration 6s-2p
- GEO throughput cycling regime - 60% constant DOD
- Accidental reverse polarity at 350 cycles following a capacity measurement
- Battery cells severely imbalanced
- Half of the cells over discharged
- Half the cells overcharged to almost 4.3V
- Since completed 2,250 cycles and ongoing (equivalent to a 25 yea r life)
- The incident had no apparent effect upon battery cycle -life

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Reverse Polarity - 2

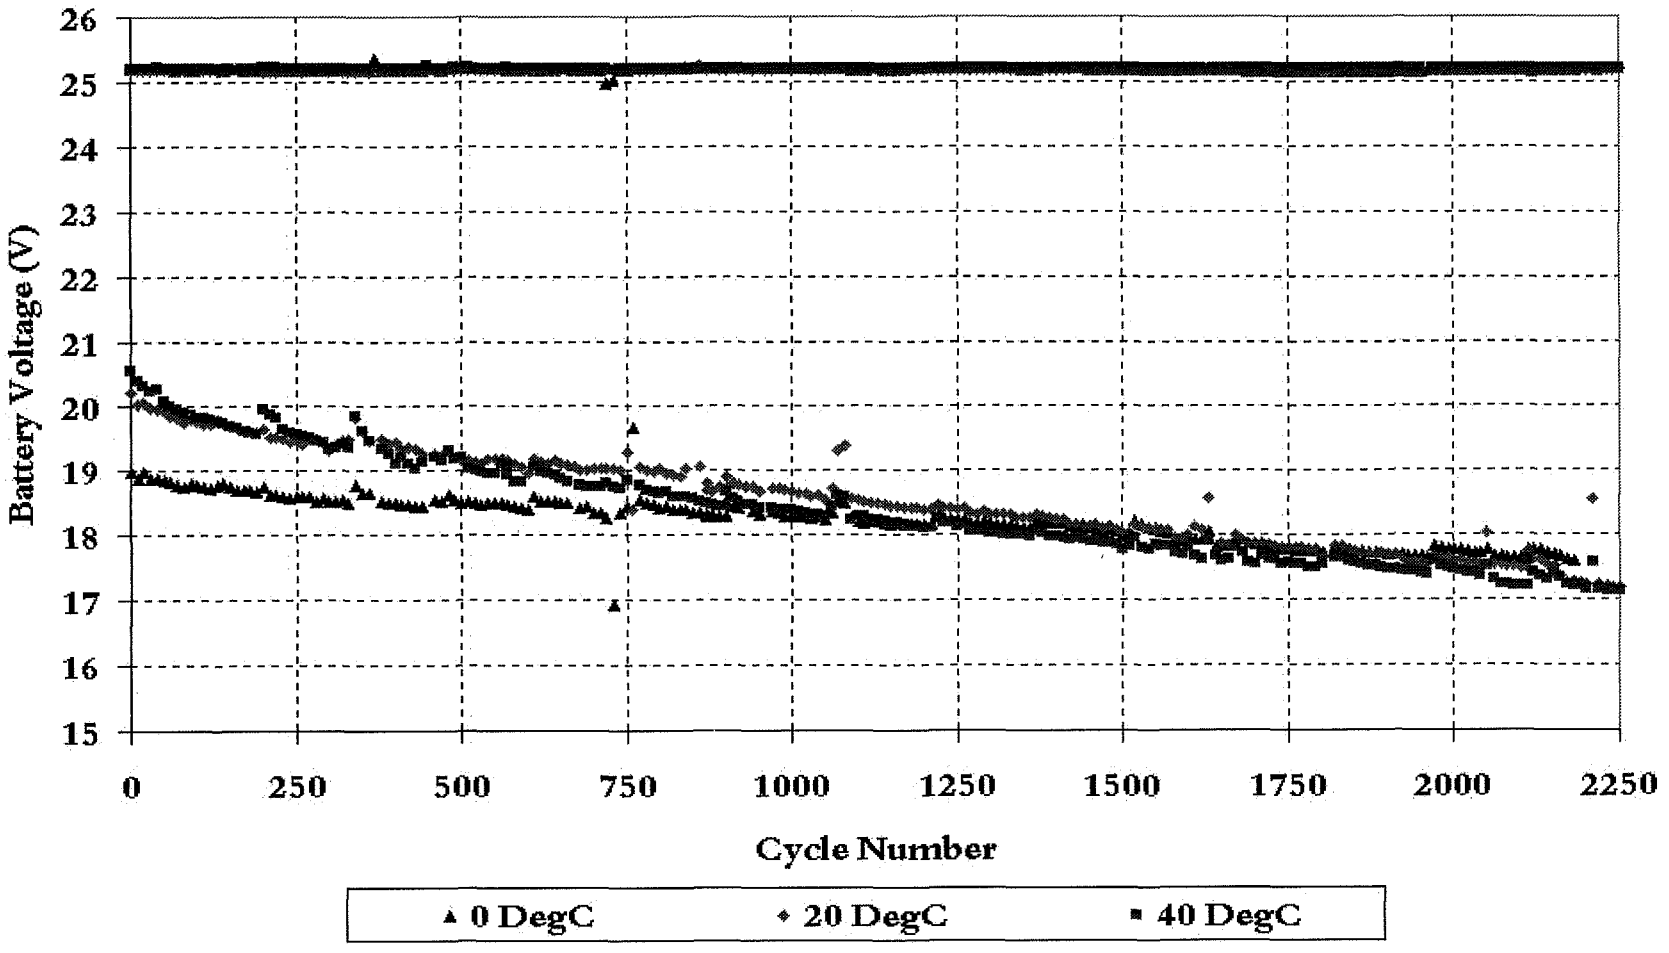

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

An Alternative Crush Test!

- Sony cells from a mobile phone
- Phone crushed by a SUV - cell ends severely crushed!!
- Cells still work fine!
- Capacity 1.36 Ah each
- Energy 4.99 Wh
- Some capacity fade from 2 years use, as expected

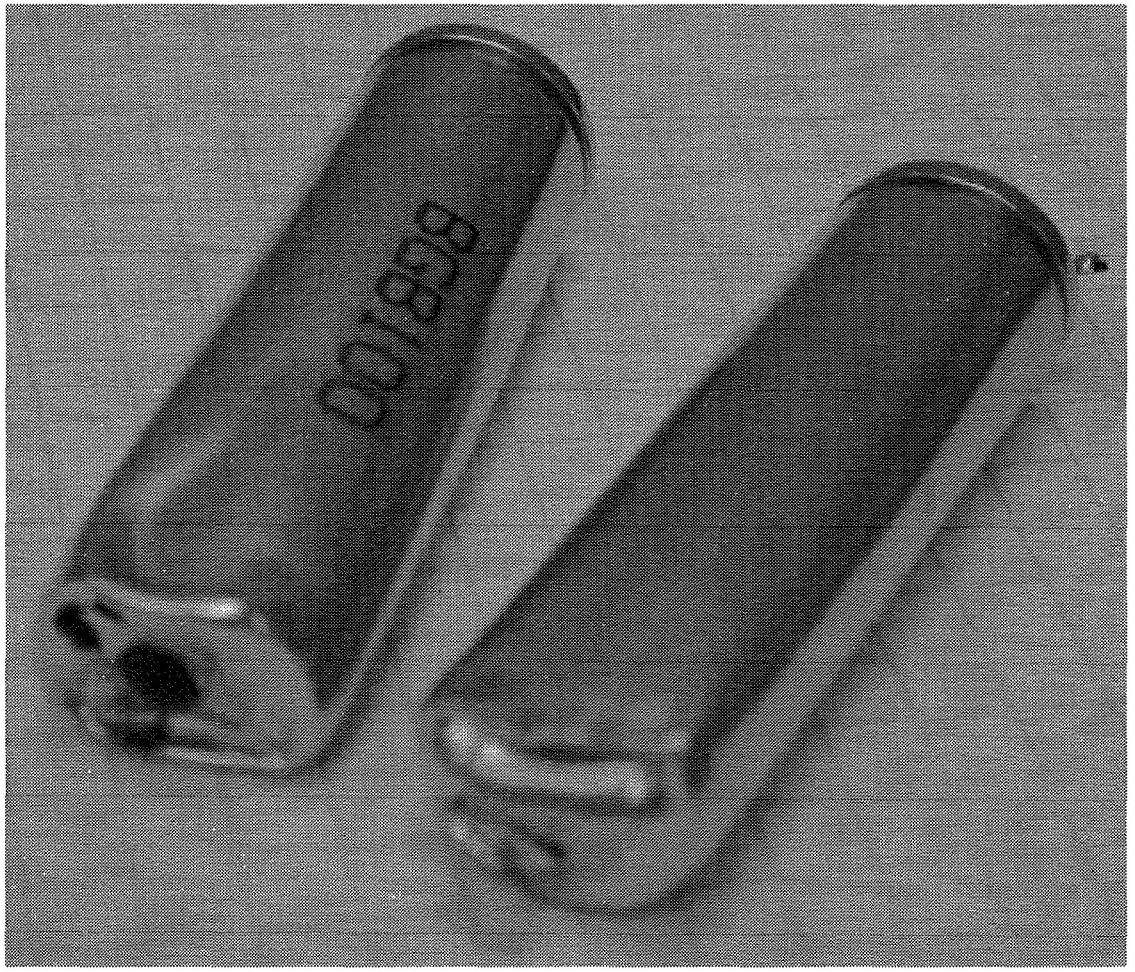

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Battery Protection

- Charge/discharge at battery level voltage to *s x 4.2V*
- Cell O/C failure
  - Loose a string (not acceptable for 'big' cells)
- Cell C/C failure
  - Overcharge cells in the same string
  - Each string has many other 'fuses' in series with failed cell
  - Loose string O/C (for Sony cell)
- Topology is highly robust to cell failures

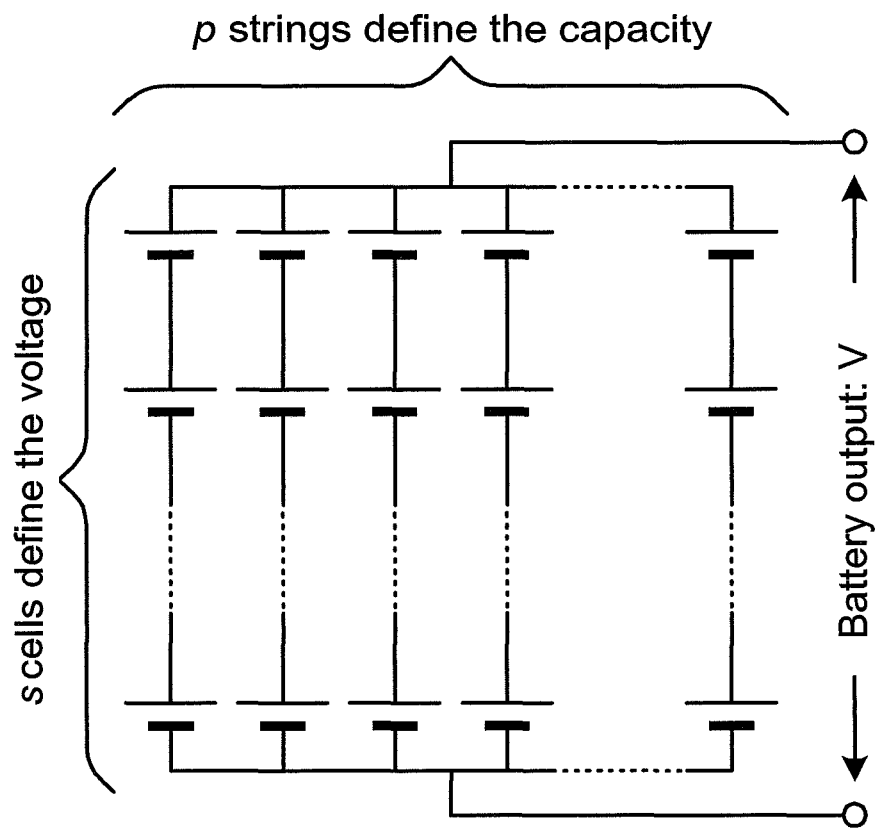

s-p topology

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Conclusions

- Over 2 million cell -hours of space testing, plus many more cells used to make military batteries from Sony cells, without serious inci dent
- Safety reviews conducted by ESA and most European Primes in anticipation of forthcoming launches of:
  - Mars-Express
  - PROBA
  - RoLand
  - ROSETTA
  - Beagle2 batteries
- STRV-1d battery also passed full safety reviews by Arianespace
- Successfully launched on Ariane 507 last night (November 15th 2000)

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

STRV-1d

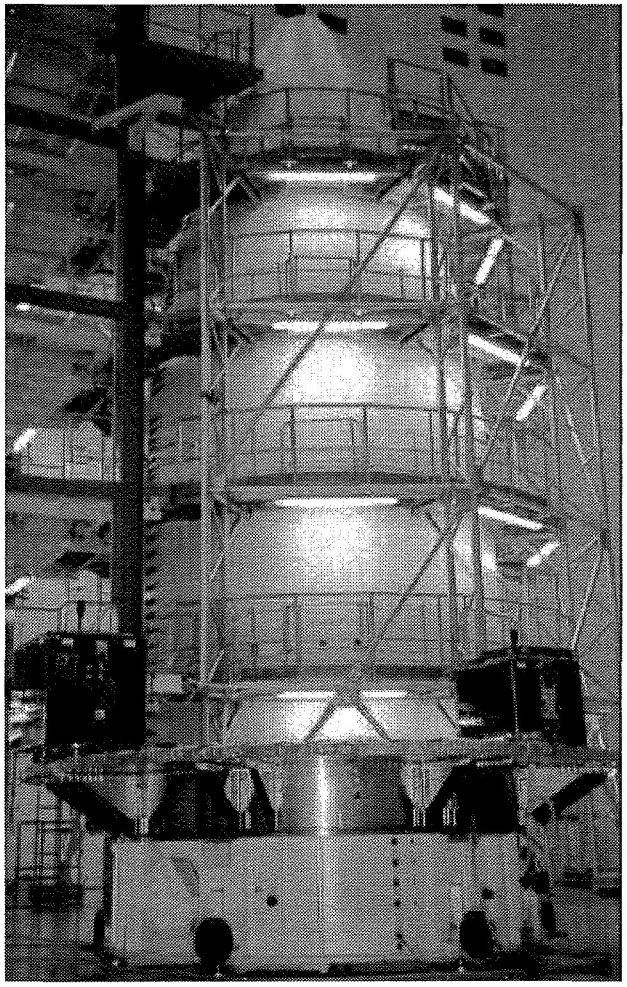

AEA TECHNOLOGY SPACE

COM DEV SPACE GROUP

PROPRIETARY INFORMATION
© 2000 AEA Technology plc & COM DEV Ltd

Adobe Acrobat Menu Bar Functions 4.0

Click on an icon on the toolbar to view an explanation of its function.



Return to Main Menu

View On-Line Help

Primary / Cour Mos / IN / 44

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operation and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503

1. AGENCY USE ONLY *(Leave Blank)*	2. REPORT DATE	3. REPORT TYPE AND DATES COVERED
	March 2001	Conference Publication

4. TITLE AND SUBTITLE

The 2000 NASA Aerospace Battery Workshop

5. FUNDING NUMBERS

6. AUTHORS

J.C. Brewer, Compiler

7. PERFORMING ORGANIZATION NAMES(S) AND ADDRESS(ES)

George C. Marshall Space Flight Center
Marshall Space Flight Center, AL 35812

8. PERFORMING ORGANIZATION REPORT NUMBER

M–1009

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)

National Aeronautics and Space Administration
Washington, DC 20546–0001

10. SPONSORING/MONITORING AGENCY REPORT NUMBER

NASA/CP—2001–210883

11. SUPPLEMENTARY NOTES

Proceedings of a workshop sponsored by the NASA Aerospace Flight Battery Systems Program, hosted by the Marshall Space Flight Center, and held at the Holiday Inn–Research Park on November 14–16, 2000

12a. DISTRIBUTION/AVAILABILITY STATEMENT

Unclassified-Unlimited
Subject Category 44
Standard Distribution

12b. DISTRIBUTION CODE

13. ABSTRACT *(Maximum 200 words)*

This document contains the proceedings of the 33nd annual NASA Aerospace Battery Workshop, hosted by the Marshall Space Flight Center on November 14–16, 2000. The workshop was attended by scientists and engineers from various agencies of the U.S. Government, aerospace contractors, and battery manufacturers, as well as international participation in like kind from a number of countries around the world.

The subjects covered included nickel-hydrogen, lithium-ion, lithium-sulfur, and silver-zinc technologies.

14. SUBJECT TERMS

battery, cell, nickel-hydrogen, lithium, lithium-ion, silver-zinc, lithium-sulfur, separator, modeling, safety

15. NUMBER OF PAGES

772

16. PRICE CODE

A99

17. SECURITY CLASSIFICATION OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT
Unclassified	Unclassified	Unclassified	Unlimited